

Magnetism of CoO polymorphs

Thomas Archer, Ruairi Hanafin and Stefano Sanvito
School of Physics and CRANN, Trinity College, Dublin 2, Ireland
 (Dated: February 6, 2020)

A microscopic explanation for the room temperature ferromagnetism in diluted ZnO:Co is at present rather elusive. Although standard secondary phases can usually be ruled out, it is less clear whether regions with high Co concentration coexist with undoped portions of the film, i.e. whether some form of CoO polymorph can be responsible for the magnetic signal. Since X-ray usually excludes the presence of the native rock-salt phase, the study of CoO polymorphs becomes particularly interesting. In this work we investigate theoretically the magnetism of CoO in both the wurtzite and zincblende phases. By using a combination of density functional theory with the LDA+ U approximation and Monte Carlo simulations we demonstrate that wurtzite and zincblende CoO have a complex frustrated anti-ferromagnetic ground state with no net magnetic moment in the bulk. Most importantly the estimated critical temperatures are well below room temperature for both cases, suggesting that CoO polymorphs are not responsible for the room temperature magnetism observed for ZnO:Co.

PACS numbers:

Diluted magnetic semiconductors (DMS) [1] are a new class of materials in which ordinary semiconductors are doped with transition metal ions, whose spins align in a ferromagnetic ground state. Their remarkable properties, in particular the interplay between ferromagnetism and free carriers, promise a generation of novel electronic devices based on the spin degree of freedom [2]. Unfortunately after almost a decade of research the Curie temperature (T_C) of GaAs:Mn, the most studied among all the DMS, is still at around 170 K [3] and it is not clear whether it will ever be possible to overcome all the limiting material issues [4]. It is therefore understandable that the magnetic community became excited by the announcement of room temperature ferromagnetism in ZnO:Co [5].

ZnO is transparent, conducting [6] and piezoelectric [7]. If ferromagnetism is also demonstrated, this will be the ultimate multi-functional material. Unfortunately, in contrast to GaAs:Mn, the phenomenology associated with ZnO:Co is extremely vast and often contradictory, with the microscopic origin of the RTF remaining elusive. In particular it is often difficult to exclude the presence of secondary phases, indeed metallic Co clusters are often identified in thin films [8]. It is even more difficult to exclude the presence of high Co density regions. In these, the concentration of transition metals can exceed the percolation limit resulting in magnetism, as recently demonstrated for ZnTe:Cr [9]. This result was then extrapolated to ZnO:Co and uncompensated spins at the surface of hypothetical CoO antiferromagnetic clusters were proposed as the source of the observed room temperature magnetism [10]. Therefore, as wurzite (WZ) CoO can be considered the end member of the $Zn_{1-x}Co_xO$ alloy, the study of its magnetic properties becomes of paramount importance. In this work we investigate the magnetic state of various CoO polymorphs, including rocksalt (RS), zincblende (ZB) and wurtzite (WZ), and conclude that these phases

cannot support any room temperature magnetic order.

In this work we use a combination of density functional theory (DFT) and Monte Carlo (MC) simulations to investigate both the ground state and the magnetic critical temperature T_C , of CoO polymorphs. Importantly we go beyond the simple local density approximation (LDA) and use the LDA+ U scheme in the Czyzyk-Sawatzky form [11] as implemented [12] in the pseudopotential code *Siesta* [13]. The empirical Coulomb U and exchange J parameters are chosen to be $U=5$ eV and $J=1$ eV. These values reproduce the lattice constant of RS CoO in the ground state structure. Our U and J values are also in good agreement with previously determined values from constrained DFT [14]. In all our calculations we used norm-conserving Troullier-Martins' pseudopotentials [15] with non-linear core corrections [16] and a real-space regular grid with a grid spacing equivalent to a plane-wave cut-off of 800 Ry. Reciprocal space integration was performed on a grid with an equivalent real space distance of 20 Å. We relaxed all structures until the forces and pressure are smaller than 0.005 eV/Å and 5 kbar respectively.

Supercells were constructed for the RS, WZ and ZB structures, containing 32, 48 and 36 atoms respectively. For each polymorph 62 total energy calculations were performed for randomly assigned collinear spin configurations. We then mapped the DFT energy onto the classical Heisenberg Hamiltonian

$$H_H = E_0 - \frac{1}{2} \sum_{i,j} J_{r_{ij}} \vec{S}_i \cdot \vec{S}_j, \quad (1)$$

where $J_{r_{ij}}$ is the Heisenberg exchange constant, \vec{S}_i the classical spin associated to the i -th site ($|\vec{S}_i| = 3/2$ for CoO) and E_0 the energy of the corresponding paramagnetic phase. This was then used in our MC simulations to determine the ground state and T_C . In the case of WZ CoO we also include a uniaxial

	a	c	u	V (\AA^3)	E_0	J_1	J_2	J_3	J_4	T_C
RS	4.260	–	–	19.32	0	1.5	-12.2	–	–	210
WZ	3.244	5.203	0.084	23.71	200.6	6.1	-36.7	-0.2	-5.2	160
WZ*	3.476	4.292	0.0	22.05	120.6	0.0	-55.2	-0.8	-24	100
ZB	3.245	–	–	23.83	313.2	-5.0	0.7	0.6	-2.0	55

TABLE I: Summary of the calculated structural and magnetic properties for the various CoO polymorphs: a , c (in \AA) and u (fractional) are the lattice constants, V is the volume per formula unit (in \AA^3), E_0 (in meV) is the Heisenberg energy of the paramagnetic phase, J_n (in meV) are the exchange constants, and T_C (in K) is the critical temperature calculated from the specific heat.

anisotropy term setting an hard-axis along the c -axis, with the value of the zero-field split taken from EPR measurements $D = 2.76 \text{ cm}^{-1}$ [17]. Spins were reoriented using the standard Metropolis algorithm. The acceptance probability of a new state is 1 if the new configuration has a lower energy, otherwise it is given by the Boltzmann distribution $e^{-\Delta E/k_B T}$ [18], where ΔE is the energy difference between the old and the new configurations. Each system was first equilibrated at a given temperature, then the specific heat and Binder cumulants were calculated over several million MC steps. These were used to extract T_C . Simulations were performed with lattices containing 512 and 1000 Co atoms with periodic boundary conditions.

We begin our analysis by investigating RS CoO, since both its structure and magnetic properties are experimentally very well established, and therefore represents a good test for our computational scheme. RS CoO is a type-II antiferromagnet (AFII) below the Néel temperature $T_N = 287 \text{ K}$. In this magnetic configuration ferromagnetic planes align antiferromagnetically along the [111] direction [19]. Our calculated lattice parameters are reported in table I and agree by construction with previously published experimental data [20]. The calculated density of states (DOS) is shown in figure 1. The valence band is a hybrid band formed from the O- p and the Co- d orbitals, while the conduction band is of purely d in character. This places the material on the Zaanen-Sawatzky-Allen [21] diagram between charge transfer and Mott-Hubbard insulators, as reported by several other calculations [14]. The Mulliken populations for the Co- d orbitals returns a magnetic moment of $2.77\mu_B$ with no contributions from O, in good agreement with the 2+ oxidation state. The exchange constants J_n are presented next (Tab. I). We find that the first and second nearest neighbor constants J_1 and J_2 are sufficient to reproduce the DFT total energies with a standard deviation of less than 3 meV/Co. This corresponds to about 3% of the total magnetic energy of the AFII structure (see Fig. 2). The MC calculated specific heat, C as a function of temperature, is presented in figure 3. A clear peak is observed, indicating the Néel temperature is $T \sim 210 \text{ K}$. This also agrees with the value we calculated by using the Binder cumulants and scaling theory, but it

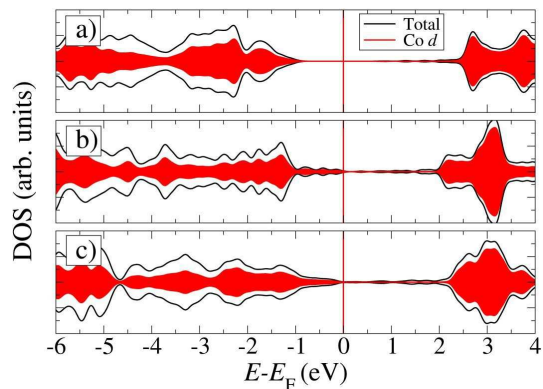


FIG. 1: Projected density of states for (a) rock-salt, (b) wurtzite and (c) zinc-blende CoO. The antiferromagnetic configurations used are type-II for the RS phase, c -type for WZ and antiferromagnetic with alternating ferromagnetic planes along the [100] direction for the ZB.

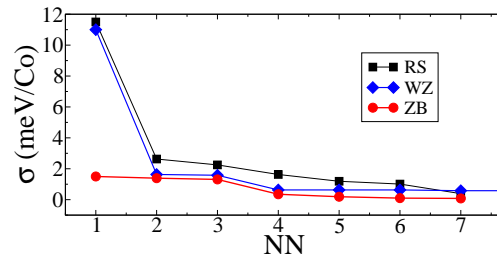


FIG. 2: Standard deviation σ for the fit of the calculated DFT total energies onto the Heisenberg Hamiltonian as a function of the number of nearest neighbors (NN) included in the model.

is 30% lower than the experimental $T_N = 287 \text{ K}$ [19]. Considering the various approximations introduced in our scheme, such as collinearity and the possible errors originating from the exchange and correlation functional, we regard this value as satisfactory. Moreover, since 2+ oxidation state for Co is also observed for the WZ and ZB polymorphs, one can expect a similar underestimation of T_C ($\sim 30\%$).

We will now consider the WZ phase. Since this is the same lattice structure of ZnO, WZ CoO is the most likely candidate as secondary phase in ZnO:Co. Although WZ CoO was first grown in the early sixties [22] and it can now be synthesized by several groups [23, 24, 25], relatively little is known about its electronic and magnetic properties. Risbud et al. [23] found no ferromagnetism, but confirmed the presence of rather strong magnetic coupling between the Co ions. DFT-LDA calculations by the same authors indicate that the ferromagnetic state has lower energy than the non-magnetic one, although it is not necessarily the ground state. In fact a later study by Han et al. demonstrates that the ferromagnetic ground state is higher in energy than a magnetic configuration in which ferromagnetic a , b planes align antiferromagnetically along the WZ c -axis

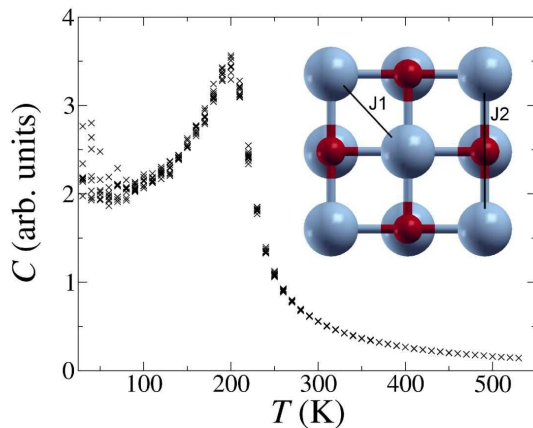


FIG. 3: Monte-carlo calculated specific heat for cubic CoO. Note a rather sharp peak at $T \sim 210$ K, that we associate with the Néel temperature T_N . In the inset we present the RS CoO cell and we indicate the various J constants.

(c -type antiferromagnetic) [26]. Whether or not this is the ground state is unknown.

For the calculations of the WZ phase we use the experimental lattice parameters measured by Risbud et al. [23] ($a = 3.244$ Å, $c = 5.203$ Å and $u = 0.084$), which give a small pressure (18 kbar) and forces (< 0.005 eV/Å). The calculated paramagnetic energy per formula unit E_0 is 200.6 meV higher than that of the RS structure. This is obtained at a considerably larger volume (19.32 Å³ for RS, 23.71 Å³ for WZ), suggesting that the WZ polymorph will not form at equilibrium in the bulk. However, these are not large energy differences and one expects that the WZ phase can be indeed stabilized in thin films.

Interestingly the structure proposed by Risbud et al. [23] does not appear to be a stable phase in DFT. Conjugate gradient relaxation move the oxygen atoms along the c -axis so that they lie in the same plane as Co ($u \rightarrow 0$). For such a distorted phase (denoted as WZ*) E_0 is 80 meV lower than that of the experimental WZ phase and thus only 120 meV higher than that of the RS. WZ* has a volume slightly smaller than that of undistorted WZ, although still substantially larger than that of the naturally occurring RS. Interestingly the c -axis in WZ* is considerably compressed and the a and b axes are expanded with respect to the WZ phase. This distortion lowers the cell volume and increases the Co-O coordination number from 4 to 5. Since such a highly distorted phase has never been observed experimentally, we believe it may merely be an intermediary state in the transition from WZ to RS. This is supported by experimental evidence that the WZ polymorph is metastable and reverts back to the RS when annealed [24].

WZ CoO shows a similar electronic structure to that of RS with considerable O- p /Co- d hybridization in the valence band (Fig. 1). In this case the Mulliken populations of the Co d orbitals are found to be 4.76

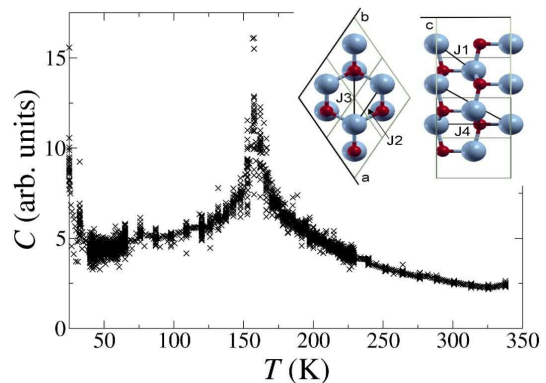


FIG. 4: Monte-carlo calculated specific heat for wurtzite CoO. Note a rather sharp peak at $T \sim 160$ K, that we associate with the magnetic critical temperature. In the inset we present the WZ CoO cell and we indicate the various J constants.

and 2.12 for the majority and minority spins respectively. The oxygen atoms carry no magnetic moment so a total Mulliken magnetic moment of $2.64\mu_B$ is observed, consistent with the 2+ valence state. In the case of WZ CoO (both WZ and WZ*) four J constants are sufficient to yield a standard deviation of less than 1 meV/Co (see figure 2).

The dominant interaction in WZ CoO is a strong nearest neighbor antiferromagnetic coupling in the $\{001\}$ planes, leading to a Néel frustrated state, in which adjacent spins in the planar triangular lattice are rotated by 120° with respect to each other. Along the c axis the interaction is ferromagnetic between nearest neighbor planes and antiferromagnetic between second nearest neighbor, resulting in an overall ferromagnetic coupling between the $\{001\}$ planes. $C(T)$ for WZ CoO is presented in figure 4, from which we can estimate a critical temperature of about 160 K. A similar analysis for the WZ* phase gives $T_C = 100$ K. Assuming that the error found for the RS phase is transferable to WZ CoO, we obtain critical temperatures in the range 100-200 K. These are well below room temperature and suggests that WZ CoO cannot be responsible for the room temperature magnetic signal often found in ZnO:Co.

Finally we consider ZB CoO. This has been discovered experimentally during the synthesis of WZ CoO, that indeed is always accompanied by the formation of the ZB phase [23]. The ZB structure is now characterized [27], although no information is available about its magnetic state. For the purpose of comparing the atomic and electronic structures we set the spin configuration of the ZB cell to have ferromagnetic planes arranged in an antiferromagnetic stack along the $[100]$ direction. Our relaxed structure has a lattice parameter of 3.245 Å, which compares well with the experimental value of 3.230 Å [27]. Similarly to the other polymorphs, ZB CoO shows a strong O- p /Co- d hybridization in the valence band (Fig. 1) and the Mulliken magnetic moment is around $3 \mu_B$ ($2.74 \mu_B$ with a Co d Mulliken occupation

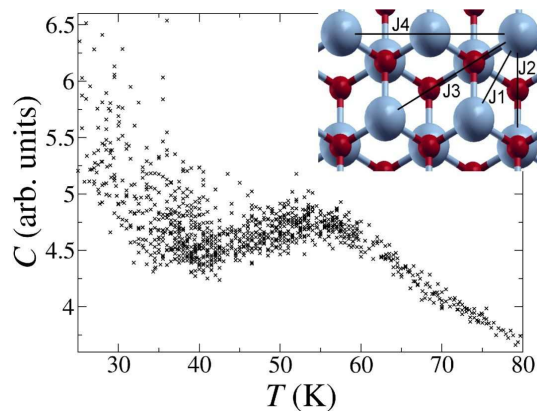


FIG. 5: Monte-carlo calculated specific heat for zincblende CoO. Note a rather diffuse peak at $T \sim 55$ K, that we associate with the magnetic critical temperature. In the inset we present the ZB CoO cell and we indicate the various J constants.

of 4.77 and 2.03 for the majority and minority spins respectively). The ZB phase is found to be the least stable phase among all the CoO polymorphs studied, with $E_0 = 313.2$ meV. At equilibrium the volume is essentially identical to that of WZ and the energy difference between the ZB and WZ phases is small, supporting the experimentally observed co-existence of the WZ and ZB phases [23].

The first four J s already describe accurately the

total magnetic energy of the ZB phase with a standard deviation of less than 1 meV/Co. We find that in the case of ZB CoO the first nearest neighbor interaction is by far the largest and accounts for most of the magnetic energy. This however is considerably lower than the dominant J for both the WZ and the RS phases and one expects a considerably lower critical temperature. This is confirmed by our MC simulations (Fig. 5), which gives us $T_C = 55$ K. Importantly J_1 is antiferromagnetic leading to three-dimensional frustration, evident in the rather diffuse peak in $C(T)$.

In conclusion a combination of DFT and Monte Carlo methods have been used to calculate the thermodynamic properties of CoO polymorphs. The scheme was tested first for the RS phase and then applied to both the WZ and the ZB structures. Interestingly the ground state of the three polymorphs is rather different, RS has a type-II antiferromagnetic structure, WZ CoO is a two-dimensional frustrated system and ZB CoO is three dimensionally frustrated. In addition a second WZ structure was identified. Crucially, despite these differences, all the polymorphs show critical temperature considerably below room temperature, and thus cannot be candidates for explaining the room temperature magnetism of diluted ZnO:Co.

This work is sponsored by Science Foundation of Ireland (SFI02/IN1/I175). We thank TCHPC and ICHEC for providing computational support.

-
- [1] T. Dietl et al., *Science* **287**, 1019 (2000).
 [2] S. A. Wolf et al., *Science* **294**, 1488 (2001).
 [3] T. Jungwirth et al., *Phys. Rev. B* **72**, 165204 (2005).
 [4] A.H. MacDonald et al., *Nature Materials* **4**, 195 (2005).
 [5] K. Ueda et al., *Appl. Phys. Lett.* **79**, 988-990 (2001).
 [6] Special issue on Transparent Conducting Oxides, edited by D.S. Ginley and C. Bright [*MRS Bull.* **25** (2000)]
 [7] V.E. Wood and A.E. Austin, *Magnetolectric interaction phenomena in crystals* [London: Gordon and Breach (1975)].
 [8] J.M.D. Coey, *Curr. Opin. Solid State Mater. Sci.* **10**, 83 (2006).
 [9] S. Kuroda et al., *Nature Materials* **6**, 440 (2007).
 [10] T. Dietl, T. Andrearczyk, A. Lipińska, M. Kiecana, M. Tay and Y. Wu, *Phys. Rev. B* **76**, 155312 (2007).
 [11] M.T. Czyzyk and G.A. Sawatzky, *Phys. Rev. B* **49**, 14211 (1994).
 [12] M. Wierzbowska, D. Sánchez-Portal and S. Sanvito, *Phys. Rev. B* **70**, 235209 (2004).
 [13] J.M. Soler et al., *J. Phys. Cond. Matter* **14**, 2745 (2002).
 [14] W.E. Pickett, S.C. Erwin and E.C. Ethridge, *Phys. Rev. B* **58**, 1201 (1998).
 [15] N. Troullier and J. L. Martins, *Phys. Rev. B* **43**, 8861 (1991).
 [16] J. Zhu, X. W. Wang and S. G. Louie. *Phys. Rev. B* **45**, 8887 (1992).
 [17] P. Sati et al., *Phys. Rev. Lett.* **96**, 017203 (2006).
 [18] *A Guide to Monte Carlo Simulations in Statistical Physics*, D. P. Landau, K. Binder, Cambridge University Press, United Kingdom (2000)
 [19] F.B. Lewis and N.H. Saunders, *J. Phys C: Solid State Phys* **6**, 2525 (1973)
 [20] W.B. Pearson, *A Handbook of Lattice Spacings and Structures of Metals and Alloys* (Pergamon, New York, 1958).
 [21] J. Zaanen, G.A. Sawatzky and J. W. Allen, *Phys. Rev. Lett.* **55** 418 (1985).
 [22] M.J. Redman and E.G. Steward, *Nature (London)* **193**, 867 (1962).
 [23] A.S. Risbud, L.P. Snedeker, M.M. Elcombe, A.K. Cheetham and R. Seshardi, *Chem. Matter.* **17**, 834 (2005).
 [24] J.F. Liu, et al., *J. Phys. Chem. B* **110**, 21588 (2006).
 [25] R.W. Grimes and K.P. Lagerlöf, *J. Am. Ceram. Soc.* **74**, 270 (1991); K. An et al., *J. Am. Chem. Soc.* **128**, 9753 (2006).
 [26] M.J. Han and J. Yu, *J. Korean Phys. Soc.* **48**, 6 1496-1500 (2006)
 [27] L.P. Snedeker, A.S. Risbud, O Masala, J Ping, and R Seshadri, *Solid State Sciences* **7**, 1500 (2005).