

Superconducting Transition in the β -Pyrochlore AOs_2O_6 (A=Cs, Rb, K) under Pressure

Kiyotaka MIYOSHI, Yuta TAKAICHI, Yusuke TAKAMATSU, Motonobu MIURA and Jun TAKEUCHI

Department of Material Science, Shimane University, Matsue 690-8504

Pressure dependence of superconducting transition temperature T_c has been determined through the DC magnetic measurements under pressure up to $P=10$ GPa for β -pyrochlore oxides AOs_2O_6 with A=Cs ($T_c=3.3$ K), Rb (6.3 K) and K (9.6 K). Both for A=Rb and Cs, T_c increases with increasing P and shows a saturation at $T_{\text{cm}}\sim 8.8$ K, which is considered as the upper limit of T_c inherent in AOs_2O_6 . In contrast, the $T_c - P$ curve for KOs_2O_6 shows a sharp maximum of ~ 10 K at $P\sim 0.5$ GPa, and T_c is higher than T_{cm} for $0\leq P\leq 1.5$ GPa, suggesting the enhanced superconductivity due to the rattling of K ions.

KEYWORDS: β -pyrochlore, high pressure, KOs_2O_6 , RbOs_2O_6 , CsOs_2O_6 , superconductivity, DC magnetization, diamond anvil cell

In recent years, there has been a great deal of interest in pyrochlore or spinel oxides, in which a variety of remarkable low-temperature properties *e.g.*, metal-insulator¹⁻⁴ or superconducting transition,⁵⁻⁷ the exotic magnetic ground state such as spin ice^{8,9} and heavy mass Fermi-liquid behavior,¹⁰ have been found, exploring new types of electronic behavior on the geometrically frustrated lattice. Among these, the recent discovery of β -pyrochlore superconductor AOs_2O_6 (A=Cs,¹¹ Rb^{12,13} and K¹⁴) may stimulate renewed interest in superconductivity on geometrically frustrated structures, as in LiTi_2O_4 ⁷ and $\text{Cd}_2\text{Re}_2\text{O}_7$.^{5,6} Indeed, the superconductivity in AOs_2O_6 has been the subject of intensive research and several experiments suggest the conventional s-wave superconductivity.¹⁵⁻²⁰

One of the characteristic features of AOs_2O_6 is the anharmonic "rattling" motion of A ions in an oversized cage of Os-O network,²¹ which has been experimentally inferred from the specific heat data showing the existence of low frequency Einstein mode contribution,^{22,23} and also demonstrated by the recent NMR experiments.²⁴ Especially for KOs_2O_6 , the superconducting transition at $T_c=9.6$ K is followed by a second transition concerning to the rattling freedom of K ion at $T_p\sim 7.5$ K, and a field-independent specific heat anomaly of first order transition has been observed at T_p .^{25,26} The measurements of electrical resistivity ρ as a function of temperature T in high magnetic fields have revealed that $\rho(T)$ changes the curvature from a concave-downward one at high temperatures to a Fermi-liquid behavior $\rho(T)\propto AT^2$ below T_p , suggesting that the electron-rattling phonon scattering disappears below T_p .^{27,28} In RbOs_2O_6 and CsOs_2O_6 , such a crossover of $\rho(T)$ has been observed at $T^*\sim 15$ K and ~ 20 K, respectively, suggesting that the rattling motion is frozen below T^* .²⁸ Moreover, a strong coupling between the rattling motion of K ions and quasiparticles has been evidenced through the recent microwave penetration depth study, where it is suggested that the rattling phonons help to enhance superconductivity and K sites freeze to an ordered state below T_p .¹⁹ Also, the ordering of K ions at T_p has been suggested from the the-

oretical side.²⁹ Thus, there exists an intriguing possibility that novel superconductivity enhanced by the rattling phonons is realized between T_p and T_c in KOs_2O_6 .

To gain more insight into the mechanism of the superconductivity in KOs_2O_6 , it is important to clarify the intrinsic T_c inherent in AOs_2O_6 by the application of physical pressure P , which elevates T_c as expected from the relation between T_c and lattice constant ranging from 10.099 Å (A=K) to 10.148 Å (A=Cs), and examine whether or not T_c for KOs_2O_6 is really enhanced compared with that for other members. In this view, to establish the $T_c - P$ relations for AOs_2O_6 is of significant importance. In the present work, we have performed DC magnetization measurements for AOs_2O_6 (A=Cs, Rb, K) under high pressure up to $P=10$ GPa and determined the precise $T_c - P$ relations. It has been found that the $T_c - P$ curve both for A=Rb and Cs saturates at $T_{\text{cm}}=8.8$ K, which is thought of to be the upper limit of T_c inherent in AOs_2O_6 . On the other hand, T_c for A=K is higher than $T_{\text{cm}}=8.8$ K for $0\leq P\leq 1.5$ GPa, suggesting the enhanced superconductivity in KOs_2O_6 .

The polycrystalline samples of AOs_2O_6 (A=Cs, Rb, K) used in this study were synthesized by the solid-state reaction technique similar to that described in the literatures.^{11,12,14} For the products, powder X-ray diffraction measurements were examined and most of the diffraction peaks were indexed as a pyrochlore structure with a lattice parameter consistent with earlier results.^{11,12,14} A small amount of OsO_2 was also detected as an impurity. T_c at ambient pressure for all samples was confirmed to agree with literatures.^{11,12,14} For the magnetic measurements under high pressure up to 10 GPa, a miniature diamond anvil cell (DAC) with an outer diameter of 8 mm was used to generate high pressure and combined with a sample rod of a commercial SQUID magnetometer. The details of the DAC are given in elsewhere.³⁰ The AOs_2O_6 sample was loaded into the gasket hole together with a small piece of high purity lead (Pb) to realize *in situ* observation of pressure by determining the pressure from the T_c shift of Pb. Daphne oil 7373 was used as a pressure transmitting medium.

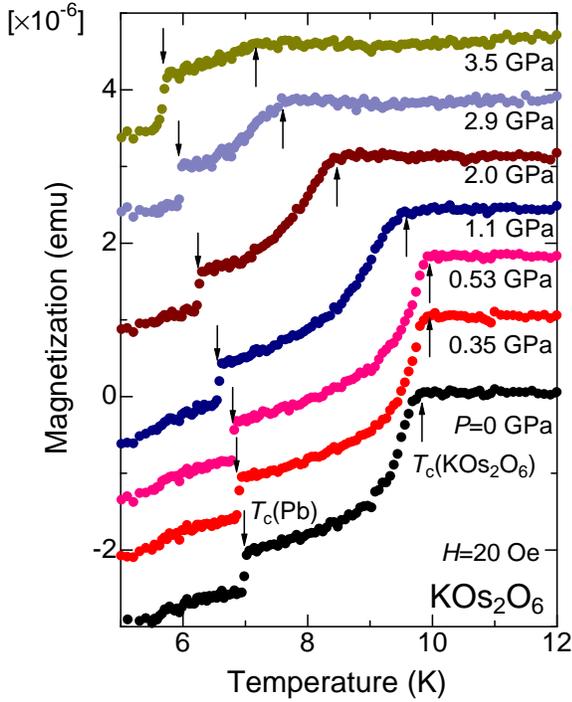


Fig. 1. (Color on line) Temperature dependence of zero-field-cooled DC magnetization for KOs_2O_6 under various pressures. The positions of T_c for KOs_2O_6 and Pb are indicated by upward and downward arrows, respectively. The data are intentionally shifted along the vertical axis for clarity.

To investigate the T_c - P relations, zero-field-cooled DC magnetization M versus temperature data were collected at each pressure and the diamagnetic onset temperature was defined as T_c . For all samples, the M - T curve at ambient pressure was confirmed to remain unchanged after pressure cycling. First, we show the M - T curves for KOs_2O_6 under various pressures in Fig. 1. In the figure, the M - T curve at ambient pressure exhibits a sudden decrease indicating the superconducting transition in KOs_2O_6 at $T_c \sim 9.6$ K in addition to a sharp drop at ~ 7 K corresponding to the diamagnetic onset of Pb for the pressure calibration. Both of the M - T curves at $P=0.35$ and 0.53 GPa shows a diamagnetic onset at $T_c \sim 10$ K, higher than T_c at ambient pressure. However, the M - T curve at $P=1.1$ GPa indicates a lower T_c of ~ 9.4 K, and T_c appears to be systematically decreased as the pressure is increased as $P \geq 0.53$ GPa in Fig. 1. These results indicate that T_c for KOs_2O_6 exhibits a maximum of ~ 10 K at $P \simeq 0.4$ – 0.5 GPa, consistent with the results of the magnetic measurements under pressure $P \leq 1.2$ GPa by Muramatsu *et al.*³¹ The M - T curves at $H=20$ Oe does not show an anomaly corresponding to the transition at T_P , different from those at $H \geq 1$ T.^{26,27}

Next, we show typical results of the M - T measurements under pressure for RbOs_2O_6 and CsOs_2O_6 in Figs. 2 and 3, respectively. As seen in Fig. 2, the M - T curve at $P=0$ GPa for RbOs_2O_6 exhibits a two-step decrease with decreasing temperature corresponding to the superconducting transition in Pb at ~ 7 K and RbOs_2O_6 at ~ 6.3 K. T_c for RbOs_2O_6 shifts toward higher tempera-

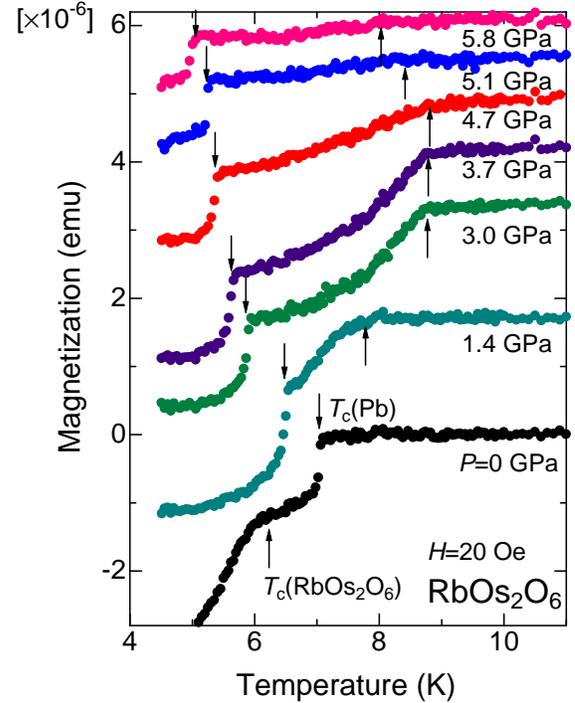


Fig. 2. (Color on line) Temperature dependence of zero-field-cooled DC magnetization for RbOs_2O_6 under various pressures. The positions of T_c for RbOs_2O_6 and Pb are indicated by upward and downward arrows, respectively. The data are intentionally shifted along the vertical axis for clarity.

ture side as increasing P and reaches ~ 8.8 K at $P=3.0$ GPa. For the further increase of pressure, T_c becomes pressure independent but appears to be decreased for $P > 4.7$ GPa. For $P \geq 4.7$ GPa, the decreasing rate of M below T_c becomes smaller, suggesting that the superconducting transition is more gradual in connection with the decrease of T_c . On the other hand, the superconducting transition for CsOs_2O_6 is almost overlapped with that for Pb at $P=2.7$ GPa in Fig. 3. In the figure, T_c appears to be monotonically increased by the application of pressure and is achieved to ~ 8.8 K at $P=6.2$ GPa but appears to be independent of pressure for 6.2 GPa $< P < 8.2$ GPa. Since the diamagnetic onset was unclear due to the broadening of the superconducting transition for $P > 8.2$ GPa, it is uncertain whether or not T_c for CsOs_2O_6 is lowered from ~ 8.8 K under high pressure as in RbOs_2O_6 .

In Fig. 4(a), T_c versus pressure data for AOs_2O_6 are summarized. In the figure, the T_c - P curve for RbOs_2O_6 displays a monotonic increase for $P < 3$ GPa and a plateau between $P \sim 3$ GPa and 5 GPa. The T_c - P curve for CsOs_2O_6 also shows a monotonic increase and a saturation for $P > 6$ GPa. The T_c - P curve both for A=Rb and Cs saturates at the same temperature $T_{c_m}=8.8$ K. The increasing rate of the T_c - P curve for $T_c < T_{c_m}$ is 0.9 – 1.0 K/GPa for both materials. The shapes of the T_c - P curves are similar to each other although a decrease from T_{c_m} at high pressure was not observed for CsOs_2O_6 . In striking contrast, the T_c - P curve for KOs_2O_6 exhibits a sharp maximum of ~ 10 K which is nearly 1 K higher than T_{c_m} . The T_c - P curves previously reported by Mu-

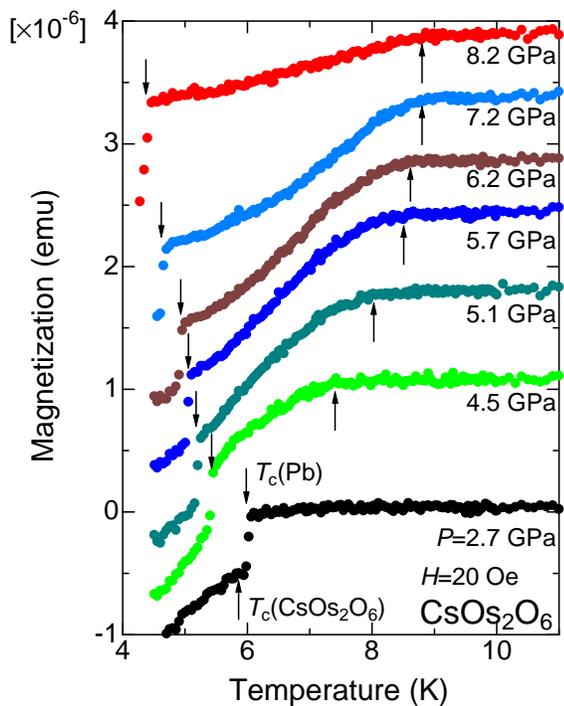


Fig. 3. (Color on line) Temperature dependence of zero-field-cooled DC magnetization for CsOs_2O_6 under various pressures. The positions of T_c for CsOs_2O_6 and Pb are indicated by upward and downward arrows, respectively. The data are intentionally shifted along the vertical axis for clarity.

ramatsu *et al.*³² are also described in the figure for comparison. They have determined T_c through the $\rho-T$ measurements for polycrystalline samples under pressure up to 10 GPa using a cubic anvil press except for $P \leq 1.2$ GPa. They have adopted the diamagnetic onset of the $M-T$ curve as T_c for $P \leq 1.2$ GPa.³¹ For KOs_2O_6 , the T_c-P curve coincides with that by Muramatsu *et al.* for $P < 2$ GPa but not for $P > 2$ GPa. The T_c-P curve based on the $\rho-T$ measurements for RbOs_2O_6 (CsOs_2O_6) displays a broad maximum of ~ 8 K at $P=2$ GPa (~ 7.5 K at $P=6$ GPa), different from that based on the $M-T$ measurements, but is coincident with each other for $P < 2$ GPa ($P < 4$ GPa). The inconsistency is mainly coming from the difficulty to determine T_c from the $\rho-T$ curve, which shows a resistive drop over wide temperature range of $\Delta T=1-5$ K under high pressure.³² Muramatsu *et al.* has determined T_c as the midpoint of the resistive drop. The onset of the resistive drop would be rather close to the diamagnetic onset in the present work.

As seen in Fig. 4(a), our magnetic measurements under pressure reveal the characteristic T_c-P curves, although the evolution of the overall band structures for the physical compression is known to be rather small.³³ Particularly for KOs_2O_6 , the T_c-P curve takes a maximum of ~ 10 K higher than those for other members ($T_{\text{cm}}=8.8$ K) indicating the enhanced superconductivity or the extension of the superconducting region in the $T-P$ phase diagram. An enhancement of superconductivity in KOs_2O_6 is also suggested by Shimono *et al.* through the measurements of microwave surface impedance.¹⁹ They have

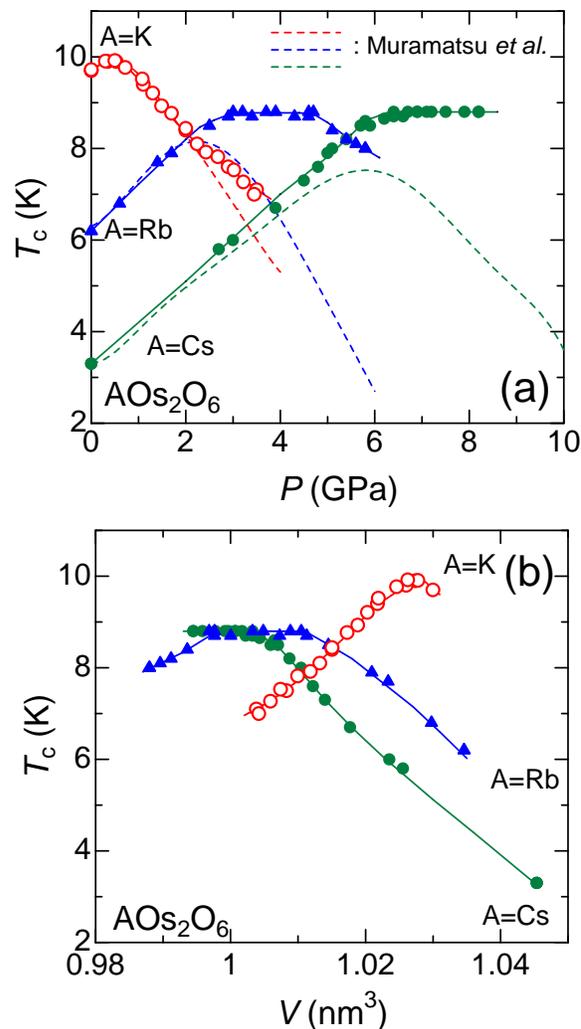


Fig. 4. (Color on line) (a) Pressure (P) dependence of superconducting transition temperature T_c for AOs_2O_6 ($A=\text{Cs, Rb, K}$). The solid lines are guides for the eyes. The dashed lines represent the T_c-P curves determined from the electrical resistivity measurements by Muramatsu *et al.* reproduced from ref. 32. (b) Plots of T_c versus unit cell volume (V) for AOs_2O_6 ($A=\text{Cs, Rb, K}$) obtained by transforming the T_c-P data using the relation $\Delta V/V_0 = -\alpha P + \beta P^2$ in ref. 28. The solid lines are guides for the eyes.

shown that the temperature dependence of superfluid density exhibits a step-like change near T_p and extrapolates to zero at $T_0=8.7$ K. T_0 is the effective T_c estimated from the behavior below T_p where the rattling motion freezes, and $T_c(=9.6$ K) is surely higher than T_0 , suggesting the enhanced superconductivity and the importance of the rattling motion for the enhancement. In a similar context, the recent Hall-sensor magnetometry has revealed that the lower critical field versus temperature data below T_p extrapolates to zero at 9.2 K, lower than T_c , suggesting that the superconducting gap is reduced below T_p .³⁴ Indeed, $T_0(=8.7$ K) is considered as the original T_c in the absence of the rattling of K ions, and is in good agreement with the upper limit of T_c for $A=\text{Rb}$ and Cs ($T_{\text{cm}}=8.8$ K) inferred from the saturation of the T_c-P curve. This suggests that the upper limit

of T_c is basically $T_{cm}=8.8$ K in AOs_2O_6 superconductor but T_c for KOs_2O_6 is markedly enhanced from the upper limit probably due to the rattling motion of K ions. It is expected that, in case of the absence of the rattling motion in KOs_2O_6 , the maximum of T_c would be limited to 8.8 K, and then a plateau of the T_c - P curve would be realized for $0 \leq P \leq 1.5$ GPa.

In Fig. 4(b), T_c versus unit cell volume V data are plotted. We obtained the T_c - V data by transforming the T_c - P data using the relation $\Delta V/V_0 = -\alpha P + \beta P^2$, where $\alpha=0.00726$ (GPa) $^{-1}$ and $\beta=0$ for KOs_2O_6 , $\alpha=0.00777$ (GPa) $^{-1}$ and $\beta=0$ for RbOs_2O_6 , and $\alpha=0.00756$ (GPa) $^{-1}$ and $\beta=0.000198$ (GPa) $^{-2}$ for CsOs_2O_6 .²⁸ Since T_c systematically changes with A ion radius or lattice constant in AOs_2O_6 , one may expect that the T_c versus cell volume data for all members are interpolated by a universal curve indicating that T_c is determined by lattice constant independently on whether the lattice is compressed by chemical or physical pressure, such as the ferromagnetic transition temperature in $\text{R}_2\text{Mo}_2\text{O}_7$ pyrochlore (R=Nd-Gd).³⁵ As seen in Fig. 4(b), the T_c - V curves are however different from each other even between A=Rb and Cs. The increasing rate of T_c for the chemical compression $|dT_c/dV|$ is estimated to be $\sim 2.7 \times 10^2$ K/nm³ considering the value of T_c and V for A=Cs and Rb at ambient pressure, and is much larger than that for the physical one for A=Cs and Rb ($\sim 1.2 \times 10^2$ K/nm³) in Fig. 4(b). This is probably due to the difference between the modifications of local lattice structure induced by chemical and physical pressure. The relation between T_c and the detailed crystal structure under high pressure should be clarified for each system to advance towards further understanding of the mechanism of the superconductivity.

In summary, it has been found that the T_c - P curve saturates with increasing P reaching $T_{cm}=8.8$ K both for A=Rb and Cs, while that for KOs_2O_6 exhibits a sharp maximum of ~ 10 K at $P \sim 0.5$ GPa. T_{cm} is thought of to be the upper limit of T_c inherent in AOs_2O_6 superconductor. For KOs_2O_6 , the superconducting region is extended in the T - P phase diagram for $0 \leq P \leq 1.5$ GPa. Since the rattling motion does not survive at low temperature below T_{cm} for A=Rb and Cs, it is inferred that the rattling of K ions plays a crucial role for the enhanced superconductivity in KOs_2O_6 .

Acknowledgements

This work is financially supported by a Grant-in-Aid for Scientific Research (No. 17740229) from the Japanese Ministry of Education, Culture, Sports, Science and Technology.

- 1) Y. Shimakawa, Y. Kubo and T. Manako: *Nature* **379** (1996) 53.
- 2) D. Mandrus, J. R. Thompson, R. Gaal, L. Forro, J. C. Bryan, B. C. Chakoumakos, L. M. Woods, B. C. Sales, R. S. Fishman and V. Keppens: *Phys. Rev. B* **63** (2001) 195104.
- 3) K. Miyoshi, T. Yamashita, K. Fujiwara and J. Takeuchi: *J. Phys. Soc. Japan* **72** (2003) 1855.
- 4) A. Yamamoto, P. A. Sharma, Y. Okamoto, A. Nakao, H. A. Katori, S. Niitaka, D. Hashizume and H. Takagi: *J. Phys. Soc.*

- Japan **76** (2007) 043703.
- 5) M. Hanawa, Y. Muraoka, T. Tayama, T. Sakakibara, J. Yamaura and Z. Hiroi: *Phys. Rev. Lett.* **87** (2001) 187001.
- 6) H. Sakai, K. Yoshimura, H. Ohno, H. Kato and S. Kambe, R. E. Walstedt, T. D. Matsuda, Y. Haga, Y. Onuki: *J. Phys. Condens. Matter* **13** (2001) L785.
- 7) D. C. Johnston: *J. Low Temp. Phys.* **25** (1976) 145.
- 8) M. J. Harris, S. T. Bramwell, D. F. McMorrow, T. Zeiske and K. W. Godfrey: *Phys. Rev. Lett.* **79** (1997) 2554.
- 9) S. T. Bramwell and M. J. P. Gingras: *Science* **294** (2001) 1495 and references therein.
- 10) S. Kondo, D. C. Johnston, C. A. Swenson, F. Borsa, A. V. Mahajan, L. L. Miller, T. Gu, A. I. Goldman, M. B. Maple, D. A. Gajewski, E. J. Freeman, N. R. Dilley, R. P. Dickey, J. Merrin, K. Kojima, G. M. Luke, Y. J. Uemura, O. Chmaissem and J. D. Jorgensen: *Phys. Rev. Lett.* **78** (1997) 3729.
- 11) S. Yonezawa, Y. Muraoka and Z. Hiroi: *J. Phys. Soc. Japan* **73** (2004) 1655.
- 12) S. Yonezawa, Y. Muraoka, Y. Matsushita and Z. Hiroi: *J. Phys. Soc. Japan* **73** (2004) 819.
- 13) M. Brühwiler, S. M. Kazakov, N. D. Zhigadlo, J. Karpinski and B. Batlogg: *Phys. Rev. B* **70** (2004) 020503(R).
- 14) S. Yonezawa, Y. Muraoka, Y. Matsushita and Z. Hiroi: *J. Phys. Condens. Matter* **16** (2004) L9.
- 15) R. Khasanov, D. G. Eshchenko, J. Karpinski, S. M. Kazakov, N. D. Zhigadlo, R. Brühwiler, D. Gavillet, D. Di Castro, A. Shengelaya, F. La Mattina, A. Maisuradze, C. Baines and H. Keller: *Phys. Rev. Lett.* **93** (2004) 157004.
- 16) K. Magishi, J. L. Gavilano, B. Pedrini, J. Hinderer, M. Weller, H. R. Ott, S. M. Kazakov and J. Karpinski: *Phys. Rev. B* **71** (2005) 024524.
- 17) M. Brühwiler, S. M. Kazakov, J. Karpinski and B. Batlogg: *Phys. Rev. B* **71** (2005) 214517.
- 18) Y. Kasahara, Y. Shimono, T. Shibauchi, Y. Matsuda, S. Yonezawa, Y. Muraoka and Z. Hiroi: *Phys. Rev. Lett.* **96** (2006) 247004.
- 19) Y. Shimono, T. Shibauchi, Y. Kasahara, T. Kato, K. Hashimoto, Y. Matsuda, J. Yamaura, Y. Nagao and Z. Hiroi: *Phys. Rev. Lett.* **98** (2007) 257004.
- 20) T. Shimojima, Y. Shibata, K. Ishizaka, T. Kiss, A. Chainani, T. Yokoya, T. Togashi, X.-Y. Wang, C. T. Chen, S. Watanabe, J. Yamaura, S. Yonezawa, Y. Muraoka, Z. Hiroi, T. Saitoh and S. Shin: *Phys. Rev. Lett.* **99** (2007) 117003.
- 21) J. Kuneš, T. Jeong and W. E. Pickett: *Phys. Rev. B* **70** (2004) 174510.
- 22) Z. Hiroi, S. Yonezawa, T. Muramatsu, J. Yamaura and Y. Muraoka: *J. Phys. Soc. Japan* **74** (2005) 1255.
- 23) M. Brühwiler, S. M. Kazakov, J. Karpinski and B. Batlogg: *Phys. Rev. B* **73** (2006) 094518.
- 24) M. Yoshida, K. Arai, R. Kaido, M. Takigawa, S. Yonezawa, Y. Muraoka and Z. Hiroi: *Phys. Rev. Lett.* **98** (2007) 197002.
- 25) Z. Hiroi, S. Yonezawa, J. Yamaura, T. Muramatsu and Y. Muraoka: *J. Phys. Soc. Japan* **74** (2005) 1682.
- 26) Z. Hiroi, S. Yonezawa and J. Yamaura: *J. Phys. Condens. Matter* **19** (2007) 145283.
- 27) Z. Hiroi, S. Yonezawa, Y. Nagao and J. Yamaura: *Phys. Rev. B* **76** (2007) 014523.
- 28) Z. Hiroi, J. Yamaura, S. Yonezawa and H. Harima: *Physica C* **460-462** (2007) 20.
- 29) J. Kuneš and W. E. Pickett: *Phys. Rev. B* **74** (2006) 0940302.
- 30) M. Mito, M. Hitaka, T. Kawae, K. Takeda, T. Kitai and N. Toyoshima: *Jpn. J. Appl. Phys.* **40** (2001) 6641.
- 31) T. Muramatsu, S. Yonezawa, Y. Muraoka and Z. Hiroi: *J. Phys. Soc. Japan* **73** (2004) 2912.
- 32) T. Muramatsu, N. Takeshita, C. Terakura, H. Takagi, Y. Tokura, S. Yonezawa, Y. Muraoka and Z. Hiroi: *Phys. Rev. Lett.* **95** (2005) 167004.
- 33) R. Saniz and A. J. Freeman: *Phys. Rev. B* **72** (2005) 024522.
- 34) T. Shibauchi, M. Konczykowski, C. J. Van der Beek, R. Okazaki, Y. Matsuda, J. Yamaura, Y. Nagao and Z. Hiroi: *Phys. Rev. Lett.* **99** (2007) 257001.
- 35) K. Miyoshi, Y. Takamatsu and J. Takeuchi: *J. Phys. Soc. Japan* **75** (2006) 065001.