

Superconductivity at 43 K in Samarium-arsenide Oxides



X. H. Chen* and T. Wu, G. Wu, R. H. Liu, H. Chen and D. F. Fang

Hefei National Laboratory for Physical Science at Microscale and Department of Physics,

University of Science and Technology of China,

Hefei, Anhui 230026,

People's Republic of China

(Dated: October 23, 2018)

arXiv:0803.3603v2 [cond-mat.supr-con] 29 Mar 2008

*Corresponding author; Electronic address: chenxh@ustc.edu.cn

Since the discovery of high-transition temperature (T_c) superconductivity in layered copper oxides, extensive efforts have been devoted to explore the higher T_c superconductivity. However, the T_c higher than 40 K can be obtained only in the copper oxide superconductors so far. The highest reported value of T_c for non-copper-oxide bulk superconductivity is 39 K in MgB_2 . [1] The T_c of about 40 K is close to or above the theoretical value predicted from BCS theory. [2] Therefore, it is very significant to search for non-copper oxide superconductor with the transition temperature higher than 40 K to understand the mechanism of high- T_c superconductivity. Here we report the discovery of bulk superconductivity in samarium-arsenide oxides $SmFeAsO_{1-x}F_x$ with ZrCuSiAs type structure. Resistivity and magnetization measurements show strong evidences for transition temperature as high as 43 K. $SmFeAsO_{1-x}F_x$ is the first non-copper oxide superconductor with T_c higher than 40 K. The T_c higher than 40 K may be a strong argument to consider $SmFeAsO_{1-x}F_x$ as an unconventional superconductor.

Layered rare-earth metal oxypnictides LaOMPn (M=Fe, Co, Ni, Ru and Pn=P and As) have attracted great attention recently due to the discovery of superconductivity at $T_c = 26$ K in the iron-based $LaO_{1-x}F_xFeAs$ (x=0.05-0.12). [3] $LaO_{1-x}F_xFeAs$ adopts ZrCuSiAs type structure. The quaternary equiatomic ZrCuSiAs type structure is very simple with only eight atoms in the tetragonal cell. A series of equiatomic quaternary compounds RFeAsO and RFePO (R=La-Nd, Sm, Gd) with ZrCuSiAs type structure has been reported by Quebe et al. and Zimmer et al. [4, 5] The crystal structure of the tetragonal ZrCuSiAs type compound SmFeAs(O,F) is shown in Fig.1.

The polycrystalline samples with nominal composition $SmFeAsO_{1-x}F_x$ (x=0.15) were synthesized by conventional solid state reaction using high purity SmAs, SmF_3 , Fe and Fe_2O_3 as starting materials. SmAs was obtained by reacting Sm chips and As pieces at 600 °C for 3 hours and then 900 °C for 5 hours. The raw materials were thoroughly grounded and pressed into pellets. The pellets were wrapped into Ta foil and sealed in an evacuated quartz tube. They are then annealed at 1160 and 1200 °C for 40 hours, respectively. The sample preparation process except for annealing was carried out in glove box in which high pure argon atmosphere is filled. The samples were characterized by X-Ray diffraction (XRD) using Rigaku D/max-A X-Ray diffractometer with Cu $K\alpha$ radiation ($\lambda=1.5418\text{\AA}$) in the 2θ range of 10–70° with the step of 0.02° at room temperature.

Figure 2 shows the XRD pattern for the sample annealed at 1160 °C, respectively. It is found that the peaks in XRD pattern can be well indexed to the tetragonal ZrCuSiAs-type structure with $a=0.3943$ nm and $c=0.8514$ nm except for some tiny peaks from impurity phase *SmOF* for the sample with $x=0.15$ annealed at 1160 °C, the lattice parameters are slightly larger than $a=0.3940$ nm and $c=0.8496$ nm of F-free SmFeAsO due to substitution of large anion F^- for small anion O^{2-} .

The susceptibility measurement was performed in Quantum Design MPMS-7T system (Quantum Design). The magnetic characterization of the superconducting transitions is shown in Fig.3 under magnetic field of 10 Oe in the zero-field cooled and field-cooled measurements for the sample annealed at 1160 °C. The magnetic onset for the superconducting transition is 41.8 K for the sample annealed at 1160 °C, and 41.3 K for the sample annealed at 1200 °C (not shown), respectively. The existence of the superconducting phase was unambiguously confirmed by the Meissner effect on cooling in a magnetic field. A superconducting volume fraction of about 50% under a magnetic field of 10 Oe was obtained at 5 K, indicating that the superconductivity is bulk in nature.

Resistivity measurements were performed on a AC resistance bridge (Linear Research Inc., Model LR700) by the standard four-probe method. Figure 4 shows the temperature dependence of the resistivity under magnetic field $H=0, 5$ and 7 Tesla for the samples annealed at 1160 °C and 1200 °C, respectively. Under zero field, the onset transition and midpoint temperatures of the resistive transition are 43 K and 41.7 K for the sample annealed at 1160 °C, 43.7 K and 41.2 K for the sample annealed at 1200 °C, respectively. The 90%-10% transition width is 2.5 K and 3 K for the samples annealed at 1160 °C and 1200 °C, respectively. It is found that the onset transition temperature in susceptibility is consistent with the transition midpoint temperature in resistivity. External magnetic field of 5 and 7 Tesla makes the transition width broadening, but the onset transition temperature is not sensitive to magnetic field, indicating that the upper critical field is very high for this superconductor. Therefore, this superconductor has potential application due to high transition temperature and high upper critical field. Replacement of La by Sm leads to a big increase in T_c from 26 K in $LaO_{1-x}F_xFeAs$ [3] to 43 K in $SmFeAsO_{1-x}F_x$. It suggests that it is possible to realize higher T_c in such layered oxypnictides. The T_c of 43 K in $SmFeAsO_{1-x}F_x$ higher than the theoretical value predicted from BCS theory[2] provides strong argument to

consider layered oxypnictide superconductors as an unconventional superconductor.

-
- [1] Nagamatsu, J. et al., Superconductivity at 39 K in magnesium diboride. *Nature* **410**, 63-64(2001).
 - [2] McMillan, W.L., Transition Temperature of Strong-coupled superconductors. *Phys. Rev.* **167**, 331-344(1968).
 - [3] Kamihara, Y. et al., Iron-based layered superconductor $LaO_{1-x}F_xFeAs$ ($x=0.05-0.12$) with $T_c=26$ K. *J. Am. Chem. Soc.* **130**, 3296(2008).
 - [4] Quebe, P. et al., Quaternary rare earth transition metal arsenide oxides RTAsO (T=Fe, Ru, Co) with ZrCuSiAs type structure. *J. Alloys and Compounds* **302**, 70-74(2000).
 - [5] Zimmer, B. I. et al., The rare earth transition metal phosphide oxides LnFePO, LnRuPO and LnCoPO with ZrCuSiAs type structure. *J. Alloys and Compounds* **229**, 238-242(1995).

Acknowledgment: This work is supported by the Nature Science Foundation of China and by the Ministry of Science and Technology of China (973 project No: 2006CB601001) and by National Basic Research Program of China (2006CB922005).

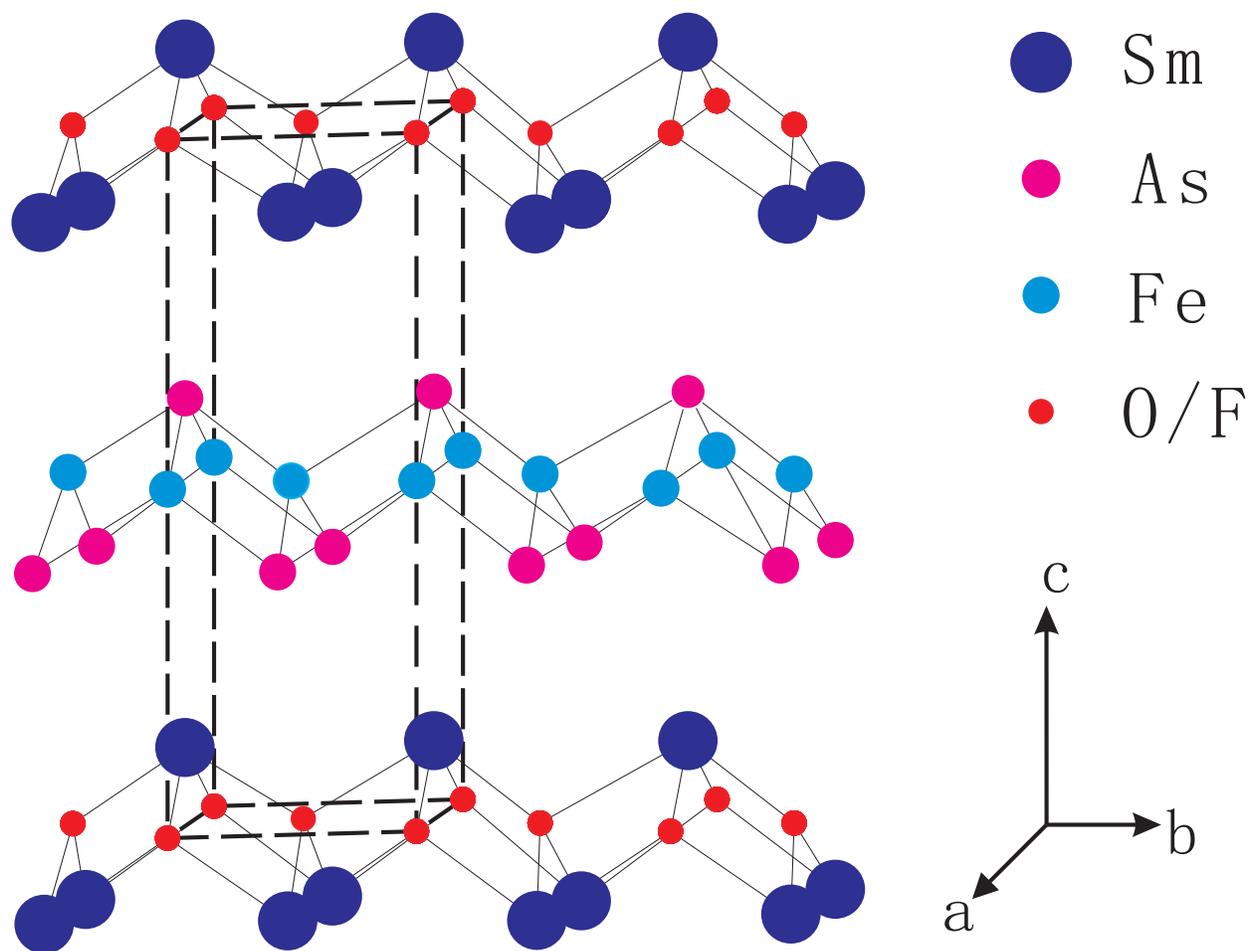


FIG. 1: Structural model of $SmFeAsO_{1-x}F_x$ with the tetragonal ZrCuSiAs type structure.

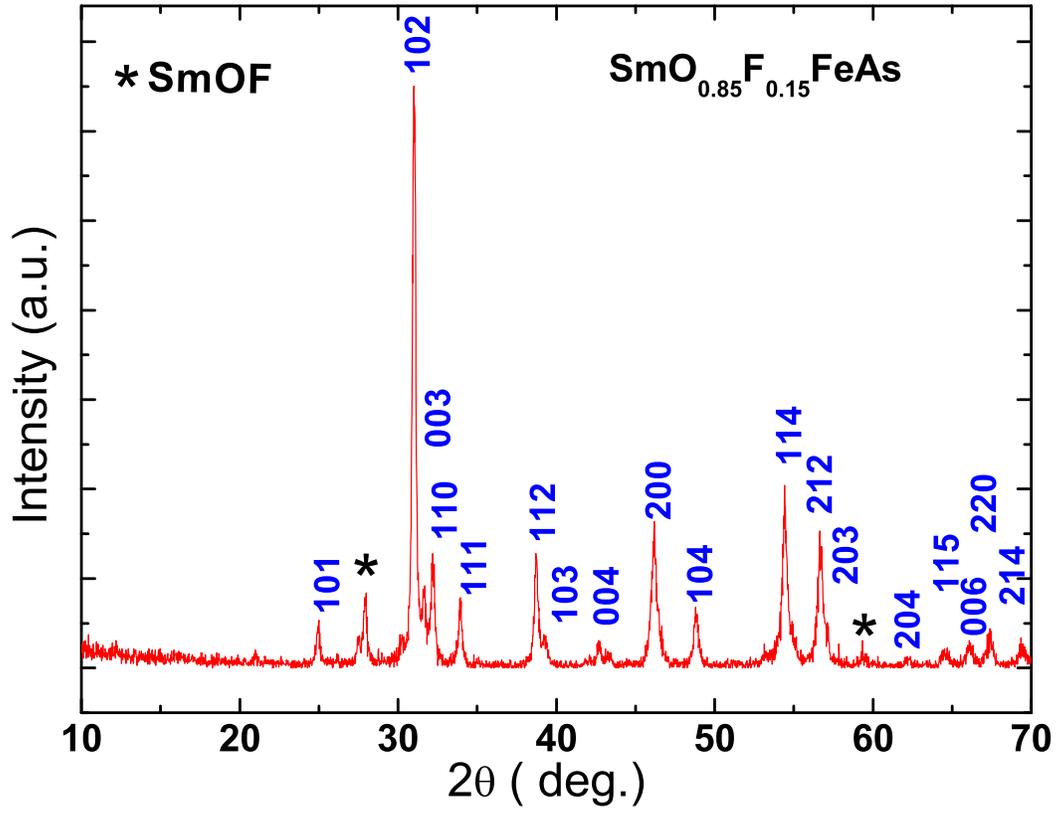


FIG. 2: X-ray diffraction pattern for the sample with nominal composition $SmFeAsO_{1-x}F_x$ ($x=0.15$) annealed at $1160\text{ }^\circ\text{C}$. A tiny impurity phase SmOF is observed.

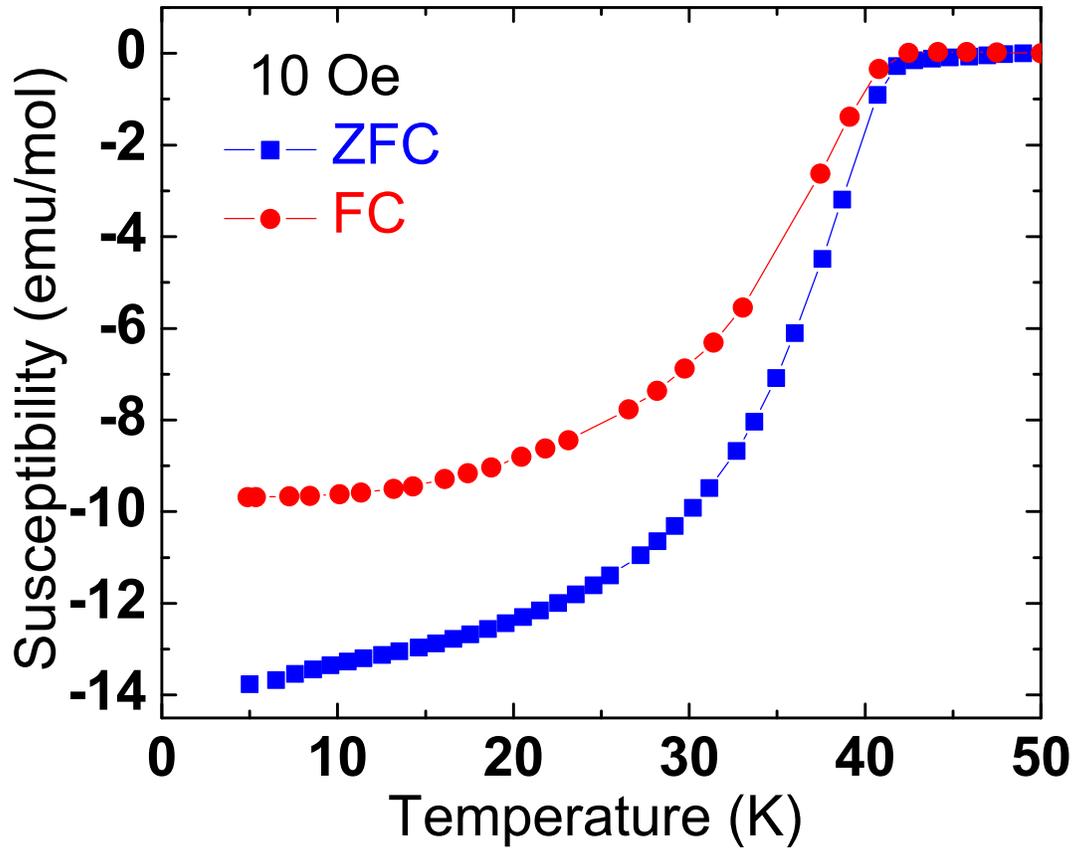


FIG. 3: Temperature dependence of magnetic susceptibility as a function of temperature for the sample annealed at 1160 °C in the zero-field cooled (ZFC) and field-cooled measurements at 10 Oe.

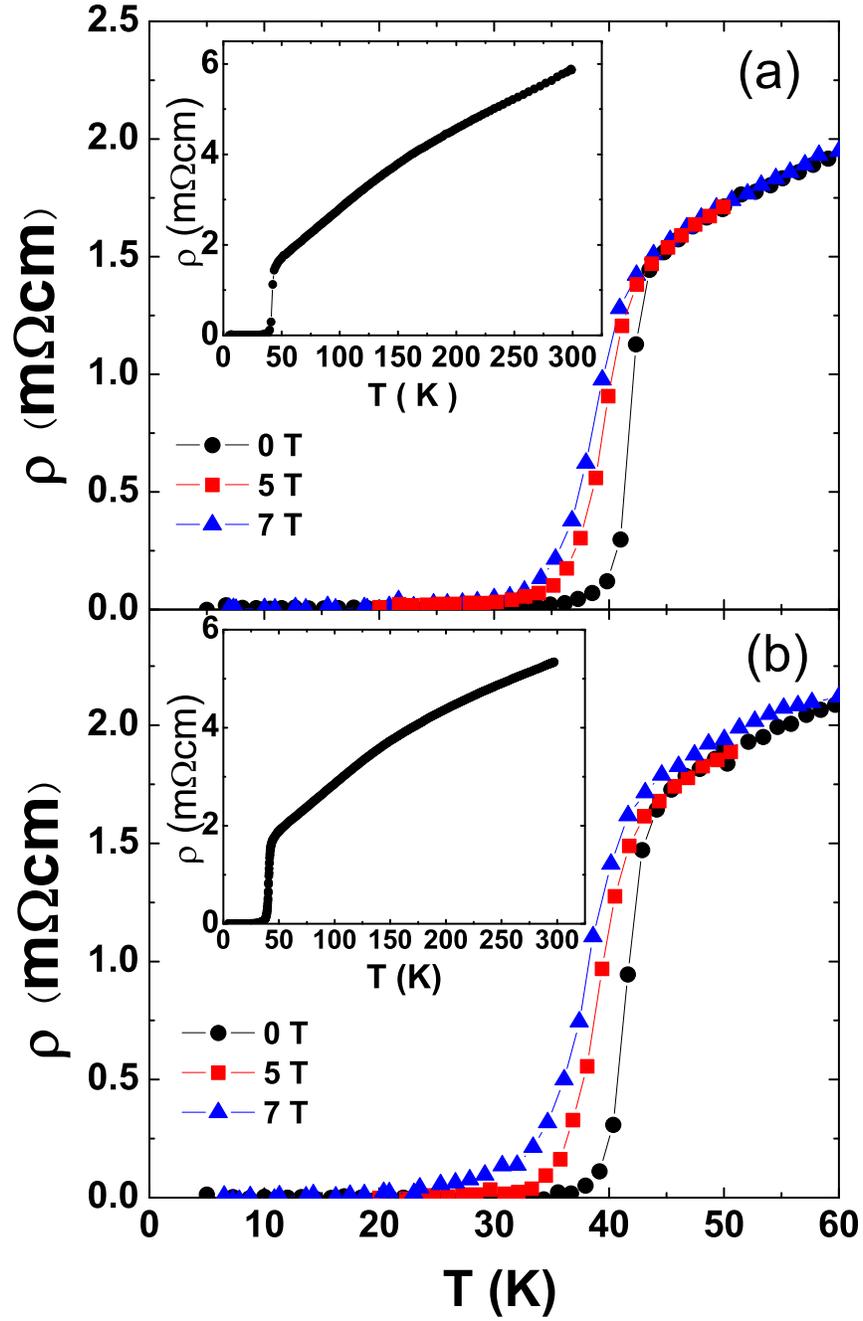


FIG. 4: Temperature dependence of resistivity without magnetic field and under magnetic field of 5 and 7 T for the samples annealed at 1160 °C (a) and 1200 °C (b), respectively. Inset shows the resistivity from 300 K to 5 K.