

In-Field Critical Current of Type-II Superconductors by Strain from Nano-Column Inclusions

J.P. Rodriguez,¹ P.N. Barnes,² and C.V. Varanasi³

¹*Department of Physics and Astronomy,
California State University, Los Angeles, California 90032*

²*Air Force Research Laboratory, Wright-Patterson Air Force Base, Dayton, OH 45433*

³*University of Dayton Research Institute, Dayton, OH 45469*

(Dated: November 1, 2018)

Abstract

A linear elasticity analysis yields that nano-rod inclusions aligned along the c axis of a thin film of $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$, such as BaZrO_3 and BaSnO_3 , squeeze that matrix by pure shear. The sensitivity of the superconducting critical temperature in that material to the latter implies that the phase boundary separating the nano-rod inclusion from the superconductor acts as a collective pinning center for the vortex lattice that appears in external magnetic field. A dominant contribution to the in-field critical current can result. The elasticity analysis also finds that the growth of nano-rod inclusions can be weakly metastable when the inclusion is softer than the matrix.

Introduction. The ongoing development of thin films of superconducting $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ (YBCO) for wire technology has resulted in world-record high critical currents.¹ In external magnetic field, the critical current is considerably enhanced by nano-rod inclusions that are aligned in parallel to the crystalline c axis.^{2,3,4} The enhancement is strongest at orientations of the magnetic field parallel to the c axis. Understanding the fundamental physics behind this effect remains a challenge. It is also unknown what drives the growth of nanorods in the first place in YBCO films.

In this paper, we provide insight into both of these questions by computing the strain field due to nano-rod inclusions that thread a YBCO superconductor along the c axis. The lattice constant of inclusions that optimize the critical current is typically 8% larger than that of the YBCO matrix along the a - b plane. Assuming a coherent phase boundary between the inclusion and a given epitaxial layer of YBCO, a linear elasticity analysis yields that the nanocolumn is compressed axially, while the YBCO matrix is squeezed by pure shear about the nanocolumn. The critical temperature in optimally doped YBCO is known to couple strongly to pure shear in the a - b plane.⁵ In applied magnetic field, we show theoretically how this experimental fact results in substantial collective pinning of the vortex lattice by the phase boundary separating the nano-column inclusion from the YBCO matrix.^{6,7} Also, the elastic energy shows weak metastability at a high density of nanocolumns when the nanocolumn is soft compared to the YBCO layer. We believe that this is what drives the growth of nano-rod inclusions in YBCO films.

Two-Dimensional Elasticity Theory. We shall determine first the elastic strain and the elastic energy cost due to a single nano-rod inclusion that threads a film of YBCO along the c axis. Such nanorods are typically composed either of BaZrO_3 (BZO)^{2,3} or of BaSnO_3 (BSO).⁴ Both are cubic perovskites, with lattice constants (a_{in}) that exceed that of the a - b plane in YBCO, $a_{\text{out}} = 3.86 \text{ \AA}$, by 9% and by 7% respectively.^{2,3,4} Let us temporarily ignore the effect of the lattice mismatch along the c axis by considering only epitaxial layers that are far from any possible partial misfit dislocation, and that present a coherent phase boundary between the inclusion and the YBCO matrix. Such partial misfit dislocations are accompanied by stacking faults,⁸ a topic which will be discussed later in the concluding section. The assumption of a coherent phase boundary is valid for a nano-rod inclusion of diameter less than the distance between possible misfit dislocations,⁸ $a_{\text{Moire}} = (a_{\text{out}}^{-1} - a_{\text{in}}^{-1})^{-1}$. A diameter of 2–3 nm is typical for BZO nanorods,³ which satisfies the bound $a_{\text{Moire}} = 5 \text{ nm}$.

A diameter of 7–8 nm is typical for BSO nanocolumns, on the other hand.⁴ It exceeds $a_{\text{Moire}} = 6$ nm, although not by much.

Consider then a cylindrical nano-column inclusion that presents a coherent phase boundary with a given epitaxial layer of the YBCO matrix. The ideal axial symmetry, assumed here for simplicity, implies a radial displacement field, $\mathbf{u}(\mathbf{r}) = u(r)\hat{\mathbf{r}}$. We then have the boundary condition

$$u_{\text{out}}(r_{\text{out}}) - u_{\text{in}}(r_{\text{in}}) = r_{\text{in}} - r_{\text{out}} \quad (1)$$

between the displacement fields of the the nanocolumn (in) and of the YBCO layer (out) at the phase boundary. The in-plane lattice mismatch that it represents generates strain in both the inclusion and in the YBCO matrix. We shall determine this by a standard elasticity analysis. The elastic energy due to a 2D strain field is given by the integral⁸

$$E_{2\text{D}} = \int' d^2r \left\{ \frac{1}{2}c_{\parallel}(\nabla \cdot \mathbf{u})^2 + \frac{1}{2}c_{\perp} \left[\left(\frac{\partial u_x}{\partial x} - \frac{\partial u_y}{\partial y} \right)^2 + \left(\frac{\partial u_x}{\partial y} + \frac{\partial u_y}{\partial x} \right)^2 \right] \right\} \quad (2)$$

over the corresponding area (prime), which is confined to $r < r_{\text{in}}$ for the nanocolumn and to $r > r_{\text{out}}$ for the YBCO matrix. Here, c_{\parallel} and c_{\perp} are the 2D bulk compression modulus and the 2D shear modulus, respectively. A useful identity for the pure shear component of the elastic energy density is

$$\left(\frac{\partial u_x}{\partial x} - \frac{\partial u_y}{\partial y} \right)^2 + \left(\frac{\partial u_x}{\partial y} + \frac{\partial u_y}{\partial x} \right)^2 = 2(\nabla \mathbf{u})^2 - (\nabla \cdot \mathbf{u})^2 - (\nabla \times \mathbf{u})^2. \quad (3)$$

The strain tensor takes the form $\nabla \mathbf{u} = (du/dr)\hat{\mathbf{r}}\hat{\mathbf{r}} + (u/r)\hat{\phi}\hat{\phi}$ in the present axially symmetric case. It combined with Eq. (3) results in the compact expression $E_{2\text{D}} = \int d^2r \{ \frac{1}{2}c_{\parallel}[r^{-1}d(ru)/dr]^2 + \frac{1}{2}c_{\perp}[r d(r^{-1}u)/dr]^2 \}$ for the elastic energy. Calculus of variations combined with physical considerations then yield a nano-column inclusion squeezed by pure compression and a surrounding YBCO matrix squeezed by pure shear:

$$u_{\parallel}(r) = -A_0 r \quad \text{for } r < r_{\text{in}}, \quad \text{and} \quad u_{\perp}(r) = +B_0 r_{\text{out}}^2 / r \quad \text{for } r > r_{\text{out}}, \quad (4)$$

with corresponding strain tensors

$$\nabla \mathbf{u}_{\parallel} = -A_0 \mathbf{I} \quad \text{and} \quad \nabla \mathbf{u}_{\perp} = B_0 (r_{\text{out}}/r)^2 (\hat{\phi}\hat{\phi} - \hat{\mathbf{r}}\hat{\mathbf{r}}). \quad (5)$$

Above, A_0 and B_0 are unitless constants to be determined below. The total elastic energy (2) generated by the nano-column inclusion is then $E_{2\text{D}}^{(1)} = 2c_{\parallel}^{(\text{in})}\pi r_{\text{in}}^2 A_0^2 + 2c_{\perp}^{(\text{out})}\pi r_{\text{out}}^2 B_0^2$.

Minimizing it with respect to the constants A_0 and B_0 while enforcing the constraint at the boundary (1) yields optimal values $r_{\text{in}}A_0 = (\Delta r)c_{\perp}^{(\text{out})}/(c_{\parallel}^{(\text{in})} + c_{\perp}^{(\text{out})})$ and $r_{\text{out}}B_0 = (\Delta r)c_{\parallel}^{(\text{in})}/(c_{\parallel}^{(\text{in})} + c_{\perp}^{(\text{out})})$. Here $\Delta r = r_{\text{in}} - r_{\text{out}}$. These then yield an elastic energy cost

$$E_{2\text{D}}^{(1)} = 2\pi(\Delta r)^2(c_{\parallel}^{(\text{in})-1} + c_{\perp}^{(\text{out})-1})^{-1} \quad (6)$$

for the nano-column inclusion, which has an equilibrium radius $r_{\text{out}} + u_{\text{out}}(r_{\text{out}})$ given by $r_0 = (c_{\parallel}^{(\text{in})}r_{\text{in}} + c_{\perp}^{(\text{out})}r_{\text{out}})/(c_{\parallel}^{(\text{in})} + c_{\perp}^{(\text{out})})$.

Consider next a field of many cylindrical nano-column inclusions of radius r_0 centered at transverse locations $\{\mathbf{R}_n\}$. Suppose again that they all present a coherent phase boundary with a given epitaxial layer of the YBCO matrix. The displacement field is then a linear superposition of those generated by a single nano-column inclusion (4):

$$\mathbf{u}_{\text{in}}(\mathbf{r}) = \mathbf{u}_{\parallel}(\mathbf{r} - \mathbf{R}_i) + \sum_{j \neq i} \mathbf{u}_{\perp}[(r_{\text{out}}/r_{\text{in}})(\mathbf{r} - \mathbf{R}_i) + \mathbf{R}_i - \mathbf{R}_j] \quad (7)$$

inside the i^{th} nanocolumn, and

$$\mathbf{u}_{\text{out}}(\mathbf{r}) = \sum_j \mathbf{u}_{\perp}(\mathbf{r} - \mathbf{R}_j) \quad (8)$$

inside the YBCO matrix. The pure shear terms that have been added to the pure compression inside of a nanocolumn (7) are required by the coherent phase boundary (1) with the YBCO matrix (8). Observe now, by Eq. (5), that \mathbf{u}_{\parallel} and \mathbf{u}_{\perp} both satisfy the Laplace equation. Inspection of the elastic energy functional (2) combined with the identity (3) then yields that the above superpositions of displacement fields are stationary because $\nabla \cdot \mathbf{u}_{\perp}$, $\nabla \times \mathbf{u}_{\parallel}$ and $\nabla \times \mathbf{u}_{\perp}$ all vanish. Indeed, the elastic energy cost reduces to a sum of surface integrals around the phase boundaries that separate each nanocolumn from the YBCO matrix of the form $E_{2\text{D}} = \sum_i E_{2\text{D}}^{(1)} + \sum_i \sum'_j [e_{i,j,i}(\text{out}) + e_{i,i,j}(\text{out})] + \sum_i \sum'_{j,k} [e_{i,j,k}(\text{in}) + e_{i,j,k}(\text{out})]$, where the indices j and k refer to the terms in the superpositions (7) and (8), and where the index i refers to the phase boundary. The prime notation over the summation symbols indicates that $i \neq j, k$. Each individual contribution $e_{i,j,k}$ is given by a surface integral around the circle S_i of radius r_{out} that is centered at \mathbf{R}_i : $e_{i,j,k}(X) = \text{sgn}(X) c_{\perp}^{(X)} I_{i,j,k}$, with

$$I_{i,j,k} = \oint_{S_i} d\mathbf{a} \cdot [\nabla \mathbf{u}_{\perp}(\mathbf{r} - \mathbf{R}_j)] \cdot \mathbf{u}_{\perp}(\mathbf{r} - \mathbf{R}_k). \quad (9)$$

The sign here is defined by $\text{sgn}(\text{in}) = +1$ and by $\text{sgn}(\text{out}) = -1$. Also, the measure $d\mathbf{a}$ on the circle S_i points radially outward. Substitution of the displacement fields (4) and the

strain fields (5) above yields ultimately that $e_{i,j,i} = 0 = e_{i,i,j}$, and that

$$e_{i,j,k}(X) = \text{sgn}(X)c_{\perp}^{(X)}(2\pi)B_0^2r_{\text{out}}^6\text{Re}[R_{i,j}R_{i,k}e^{i\phi_{j,k}(i)} - r_{\text{out}}^2]^{-2} \quad (10)$$

for $i \neq j, k$. (See Appendix.) Here, $\mathbf{R}_{i,j} = \mathbf{R}_i - \mathbf{R}_j$, and $\phi_{j,k}(i)$ denotes the angle between the vectors $\mathbf{R}_{i,j}$ and $\mathbf{R}_{i,k}$. The 2D elastic energy then is composed of a sum of 1-body ($i = j = k$), 2-body ($j = k$) and 3-body terms ($j \neq k$), $E_{2\text{D}} = \sum_i E_{2\text{D}}^{(1)} + \sum_i \sum'_{j,k} V_{i,j,k}$, with the interaction energy given by

$$V_{i,j,k} = -(2\pi)[c_{\perp}^{(\text{out})} - c_{\perp}^{(\text{in})}]B_0^2r_{\text{out}}^6\text{Re}[R_{i,j}R_{i,k}e^{i\phi_{j,k}(i)} - r_{\text{out}}^2]^{-2}. \quad (11)$$

Notice that $V_{i,j,k}$ changes sign as a function of the relative rigidity between the nano-column inclusion and the YBCO matrix.

The elastic energy will now be obtained by computing subsequent self-energy corrections to the 2-body interaction and to the 1-body line tension. Let's first fix the coordinate for the phase boundary above, \mathbf{R}_i , as well as one of the nanocolumn coordinates above, \mathbf{R}_j . Observe now that the 3-body interaction (11) has zero angle average about the center \mathbf{R}_i over the remaining nanocolumn coordinate \mathbf{R}_k :

$$\int_0^{2\pi} d\phi_{j,k}(i) V_{i,j,k} = 0. \quad (12)$$

This is due simply to the fact that the contour integral $\oint dz z^{-1}(z-w)^{-2}$ around the unit circle, $z = \exp[i\phi_{j,k}(i)]$, vanishes for complex w inside of that circle. Let's assume that each nanocolumn has a hard core of radius $r_1 \sim r_0$. At $R_{i,j} \gg r_1$, we then obtain the estimate $\sum'_k V_{i,j,k} = -\pi r_1^2 n_{\phi} V_{i,j,j}$ for the correction to the 2-body interaction on average over the bulk of the system. Here, n_{ϕ} denotes the density of nanocolumns. The renormalized 2-body interaction that results is then $V_{i,j}^{(2)} = (1 - \pi r_1^2 n_{\phi}) V_{i,j,j}$. Next, assume an effective hard-core of radius $r'_2 \sim r_1$ for the nanocolumn at the coordinate \mathbf{R}_j that remains. We thereby obtain the estimate $\sum'_{j,k} V_{i,j,k} = n_{\phi} \int' d^2 R_{i,j} V_{i,j}^{(2)} = -\pi r_2^2 n_{\phi} (1 - \pi r_1^2 n_{\phi}) E_{2\text{D}}^{(1)}$ for the net self-energy correction to the elastic energy of an isolated nano-column inclusion, with

$$r_2^2 = \frac{1 - c_{\perp}^{(\text{in})}/c_{\perp}^{(\text{out})}}{1 + c_{\perp}^{(\text{out})}/c_{\parallel}^{(\text{in})}} \cdot \frac{r_{\text{out}}^4}{r_2'^2 - r_{\text{out}}^2}. \quad (13)$$

This yields a total elastic energy density

$$E_{2\text{D}}/A = [1 - \pi r_2^2 n_{\phi} (1 - \pi r_1^2 n_{\phi})] n_{\phi} E_{2\text{D}}^{(1)} \quad (14)$$

as a function of the density of nanocolumns. The above third-order polynomial is depicted by Fig. 1. It notably predicts weakly metastable epitaxial growth for relatively soft nanorods within the YBCO matrix, such that $c_{\perp}^{(\text{in})} < c_{\perp}^{(\text{out})}$. This occurs at a density $n_{\phi} = (1 + [1 - (3r_1^2/r_2^2)]^{1/2})/3\pi r_1^2$ of nano-rod inclusions, at large effective crosssections $\pi r_2^2 > 3\pi r_1^2$. The equilibrium density of nano-rod inclusions *cannot* be dilute. In particular, $3\pi r_1^2 n_{\phi}$ must lie somewhere between 1 and 2. Inspection of Eq. (13) indicates that the former condition requires some degree of agglomeration among the nano-column inclusions: $r_{\text{out}} < r'_2 < 2r_{\text{out}}$. This may, however, be an artifact of the previous estimate for the 2-body self-energy correction, which is not accurate at $R_{i,j} \sim r_1$. The total elastic energy density (14) also indicates that relatively hard nano-rod inclusions are not stable because $r_2^2 < 0$, on the other hand (see Fig. 1).

Critical Current by Two-Dimensional Collective Pinning. We shall now determine the critical current of a thin film of superconducting YBCO threaded by nano-rod inclusions along the crystalline c axis and subject to external magnetic field aligned along the same axis. It is important to recall that the critical temperature in an optimally doped YBCO superconductor is primarily sensitive to *shear* strain in the a - b plane.⁵ That fact coupled with the shear strain generated by a nano-column inclusion obtained in the previous section, Eq. (5), results in a potential-energy landscape for vortex lines that can collectively pin the Abrikosov lattice composed of such lines. To show this, let us first assume that vortex lines experience such pinning forces primarily at their cores. The contribution of the core to the vortex line tension is approximated by the fundamental energy scale per unit length $\varepsilon_0 = (\Phi_0/4\pi\lambda_L)^2$, where λ_L denotes the London penetration depth. The temperature dependence shown by the vortex line tension is therefore approximated by $\varepsilon_0(T) = \varepsilon_0(0)[1 - (T/T_{c0})]$ near the mean-field critical temperature T_{c0} . The potential-energy landscape experienced by a vortex line is then given by $\delta\varepsilon_1(\mathbf{r}) = \sum_{\alpha} \sum_{\beta} (\partial\varepsilon_0/\partial T_c)(\partial T_c/\partial \epsilon_{\alpha,\beta})\epsilon_{\alpha,\beta}(\mathbf{r})$, where T_c is the true critical temperature, and where $\epsilon_{\alpha,\beta} = (\partial_{\alpha}u_{\beta} + \partial_{\beta}u_{\alpha})/2$ is the symmetric strain tensor. The pure shear strain (5) generated by an isolated nanocolumn in a YBCO film thereby results in the following d-wave potential-energy landscape for a vortex core given in cylindrical coordinates centered about the nanocolumn:

$$\delta\varepsilon_1(\mathbf{r}) = \varepsilon_p(r_{\text{out}}/r)^2 \cos 2\phi, \quad (15)$$

with $\varepsilon_p = \varepsilon_0(0)(T/T_{c0})T_c^{-1}[(\partial T_c/\partial \epsilon_{bb}) - (\partial T_c/\partial \epsilon_{aa})]B_0$. Here the ratio between T_{c0} and T_c

is assumed to be constant. A rigid vortex line therefore experiences a force field

$$\mathbf{f}_1(\mathbf{r}) = f_p(r_{\text{out}}/r)^3(\hat{\mathbf{r}} \cos 2\phi + \hat{\phi} \sin 2\phi) \quad (16)$$

due to the strain generated by a single nano-column inclusion, where $f_p = 2\varepsilon_p/r_{\text{out}}$ is the maximum force per unit length.

The above pinning/anti-pinning force (16) due to an isolated nano-column inclusion is long range. The presence of an extended field of nanocolumns can cut off that long range, however. In particular, such forces add within the present elastic (8) and linear approximation: $\mathbf{f}(\mathbf{r}) = \sum_i \mathbf{f}_1(\mathbf{r} - \mathbf{R}_i)$. The d-wave nature of each isolated force field (16) implies a null force on average, as well as a characteristic fluctuation of the force over the YBCO matrix: $\bar{\mathbf{f}} = 0$ and $\bar{f}^2 = n_\phi \int' d^2r |\mathbf{f}_1(\mathbf{r})|^2 = \frac{1}{2}(\pi r_{\text{out}}^2 n_\phi) f_p^2$, where the last integral (prime) has been restricted to the YBCO matrix. Matching the fluctuation of the force $\sqrt{\bar{f}^2}$ with the magnitude of an isolated pinning/anti-pinning force $|\mathbf{f}_1(\mathbf{r})|$ yields an effective range for each pinning/anti-pinning center $r_p = (2/\pi n_\phi)^{1/6} r_{\text{out}}^{2/3}$. The two types of regions in the potential energy landscape can be discerned from Fig. 2, where the d-wave potential (15) has been summed numerically over 2744 nanocolumns arranged in a “liquid” fashion.

The d-wave potential (15) that acts on rigid vortex lines in the vicinity of the phase boundaries between the nano-column inclusions and the YBCO matrix has zero angle average. It therefore cannot pin down a vortex line in isolation. Previous work by one of the authors and Maley⁶ implies that it can collectively pin the Abrikosov vortex lattice, however. Theoretical arguments and numerical Monte Carlo simulations indicate, in particular, that a hexatic Bose glass state exists at low temperature if the nano-column inclusions are arranged in parallel, in a “liquid” fashion that shows no voids or clusters.⁷ Such a defective vortex lattice is characterized by a divergent tilt modulus and by isolated lines of edge dislocations that thread it in the direction parallel to the relatively weak correlated pinning/anti-pinning centers. The critical current is then limited by plastic creep of the vortex lattice associated with glide by such edge dislocations. This yields a critical current density⁶ $J_c = j_c + j'_c$ that has a contribution due directly to columnar material defects given by $j_c B/c \sim n_p f_p^2 / c_{66} b$, and that has a relative contribution due to material point defects $j'_c / j_c = \tau_0 / \tau$ given by the ratio between the length scale $\tau_0 = (n'_p / n_p)(f'_0{}^2 / f_p^2 \tau'_p)$ and the film thickness τ . Here n_p and n'_p denotes the density of vortex lines pinned by the nanocolumns and by point defects, respectively. Also, f'_0 denotes the maximum pinning force due to material point

defects, while τ'_p denotes their average separation along an interstitial vortex line. Here also, $c_{66} = (\Phi_0/8\pi\lambda_L)^2 n_B$ is the elastic shear modulus of the pristine vortex lattice at a density n_B of vortex lines⁹ and b denotes the magnitude of the Burgers vector associated with the edge dislocations that thread the vortex lattice. The d-wave nature of the potential energy (15), with zero angle average, also implies that its occupation is purely random. The density of vortex lines that are collectively pinned by the strain-field due to nano-column inclusions is then equal to $n_p = (\sigma_p n_B) n_\phi$, where $\sigma_p = \pi(r_p^2 - r_{\text{out}}^2)$ is the effective crosssectional area of a pinning/anti-pinning center (see Fig. 2). The fact that all interstitial vortex lines are pinned by point defects, or $n_p + n'_p = n_B$, then implies that the critical current density obeys a *pure* inverse-square-root power law with magnetic field, $J_c \propto B^{-1/2}$. Taking values of $\partial T_c / \partial \epsilon_{aa} = 230$ K and $\partial T_c / \partial \epsilon_{bb} = -220$ K for the strain derivatives of T_c in optimally-doped YBCO⁵ can result in a pinning efficiency, $|f_p| \xi / \epsilon_0$, of 93% at liquid nitrogen temperature!

Discussion and Conclusions. We have found that the growth of nano-rod inclusions in YBCO films is very likely driven by weak metastability shown by the elastic energy of epitaxial layers. We also have pointed out how the sensitivity of the critical temperature in optimally-doped YBCO to pure shear strain inside of the a - b plane⁵ results in an effective collective pinning center for the Abrikosov vortex lattice at the phase boundary between the nano-rod inclusion and the YBCO matrix.

The lattice mismatch along the c axis between the nano-rod inclusion and YBCO has so far been neglected, however. YBCO has a unit cell that can be divided into a stack of three (stretched) cubes along the c axis, $AB\bar{A}$, where A and \bar{A} are mirror reflections of each other about the a - b plane, and where each cube has a lattice constant $c_{\text{out}}/3 = 3.9$ Å along that axis. The strain that results at the phase boundary with a BZO nanorod or with a BSO nanocolumn, both of which are cubic with lattice constants $a_{\text{in}} = 4.2$ Å and 4.1 Å, respectively, can be relieved by partial misfit dislocations accompanied by stacking faults in the YBCO matrix:⁸ e.g. $\dots AB\bar{A}\bar{A}\bar{A}AB\bar{A}\dots$. The predicted spacing between such stacking faults, $c_{\text{Moire}} = [(3/c_{\text{out}}) - a_{\text{in}}^{-1}]^{-1}$, is then equal to 5 nm for BZO nanorods and to 8 nm for BSO nanocolumns. We believe that their effect can be incorporated into the previous elasticity analysis by renormalizing the elastic moduli of the YBCO matrix, and hence that our conclusions remain unchanged in their presence.

The authors thank George Levin for discussions. This work was supported in part by the US Air Force Office of Scientific Research under grant no. FA9550-06-1-0479.

APPENDIX: SURFACE INTEGRALS

Equation (9) gives the relevant surface integral that determines the 2-body and 3-body interactions among nano-column inclusions resulting from the long-range strain fields that they generate. Integration by parts combined with $\nabla^2 \mathbf{u}_\perp = 0$ yields that it is symmetric with respect to the latter: $I_{i,j,k} = I_{i,k,j}$. In the case that the nano-column inclusion contained by the surface S_i coincides with one of the individual strain fields, $i = j$, it reduces to the angular integral

$$I_{i,i,k} = \frac{1}{2} r_{\text{out}}^2 B_0^2 \int_0^{2\pi} d\phi \left(\frac{R_{i,k}^2 - r_{\text{out}}^2}{r_{i,k}^2} - 1 \right), \quad (\text{A.1})$$

where $r_{i,k}^2 = r_{\text{out}}^2 + R_{i,k}^2 + 2 r_{\text{out}} R_{i,k} \cos(\phi - \phi_k)$. Here, ϕ_k denotes the orientation of the vector $\mathbf{R}_{i,k} = \mathbf{R}_i - \mathbf{R}_k$. After making the change of variables $z = e^{i\phi}$ and substituting in $\cos(\phi - \phi_k) = (e^{-i\phi_k} z + e^{i\phi_k} z^{-1})/2$, application of Cauchy's residue theorem yields that the integral vanishes: $I_{i,i,k} = 0$.

In the case that neither strain field is generated from the nano-column contained by the surface S_i , $i \neq j$ and $i \neq k$, the surface integral (9) reduces to

$$I_{i,j,k} = \frac{1}{4} r_{\text{out}}^4 B_0^2 \int_0^{2\pi} d\phi \left[\frac{(R_{i,j}^2 - r_{\text{out}}^2)}{r_{i,j}^4} - \frac{1}{r_{i,k}^2} + \frac{R_{j,k}^2}{r_{i,j}^2 r_{i,k}^2} - \frac{(R_{i,j}^2 - r_{\text{out}}^2) R_{j,k}^2}{r_{i,j}^4 r_{i,k}^2} + (j \leftrightarrow k) \right]. \quad (\text{A.2})$$

Repeating the previous steps results in a closed-form expression, but one with a large number of terms. Application of the symbolic manipulation programs available from Stephen Wolfram's *Mathematica* helps reduce it to the relatively simple result found on the right-hand side of Eq. (10).

-
- ¹ S. R. Foltyn, L. Civale, J. L. MacManus-Driscoll, Q. X. Jia, B. Maiorov, H. Wang and M. Maley, *Nature Materials* **6**, 631 (2007).
 - ² J.L. MacManus-Driscoll, S.R. Foltyn, Q.X. Jia, H. Wang, A. Serquis, L. Civale, B. Maiorov, M.E. Hawley, M.P. Maley and D.E. Peterson, *Nature Materials* **3**, 439 (2004).
 - ³ A. Goyal, S. Kang, K.J. Leonard, P.M. Martin, A.A. Gapud, M. Varela, M. Paranthaman, A.O. Ijaduola, E.D. Specht, J.R. Thompson, D.K. Christen, S.J. Pennycook and F.A List, *Supercond. Sci. Technol.* **18**, 1533 (2005).
 - ⁴ C.V. Varanasi, J. Burke, L. Brunke, H. Wang, M. Sumption and P.N. Barnes, *J. Appl. Phys.* **102**, 063909 (2007).

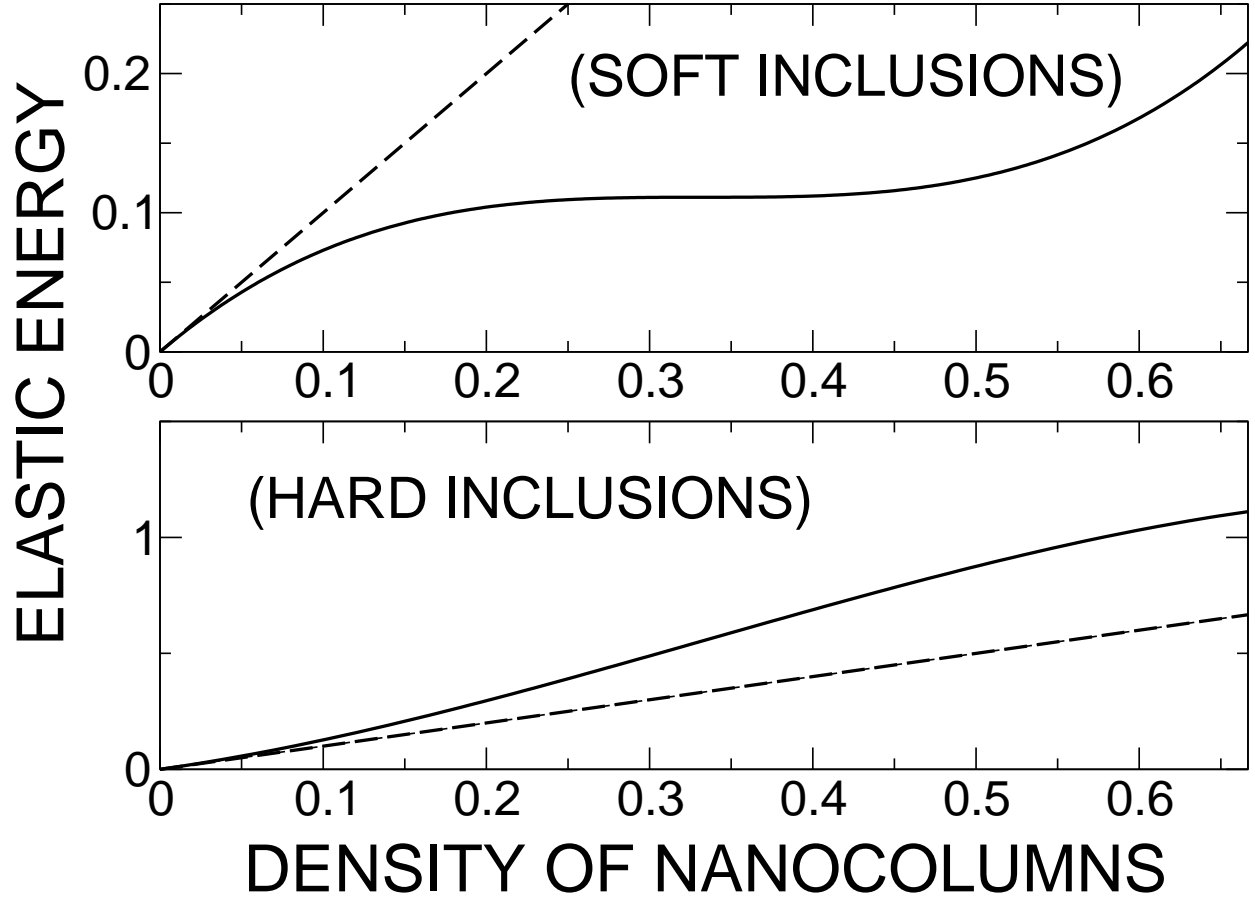


FIG. 1: Plotted is the total elastic energy density (14), in units of $E_{2D}^{(1)}/\pi r_1^2$, versus the density of nano-column inclusions, in units of $1/\pi r_1^2$. The dashed line above corresponds to the elastic energy of isolated nano-column inclusions. The radii in Eq. (14) are set to $r_2^2 = \pm 3r_1^2$ for relatively soft and hard nanocolumns, respectively.

⁵ U. Welp, M. Grimsditch, S. Fleshler, W. Nessler, J. Downey, G.W. Crabtree, and J. Guimpel, Phys. Rev. Lett. **69**, 2130 (1992).

⁶ J.P. Rodriguez and M.P. Maley, Phys. Rev. B **73**, 094502 (2006).

⁷ J.P. Rodriguez, Phys. Rev. B **76**, 224502 (2007).

⁸ D. Hull and D.J. Bacon, *Introduction to Dislocations*, 3rd ed. (Pergamon, Oxford, 1984).

⁹ E.H. Brandt, J. Low Temp. Phys. **26**, 735 (1977).

CHANGE IN VORTEX CORE ENERGY

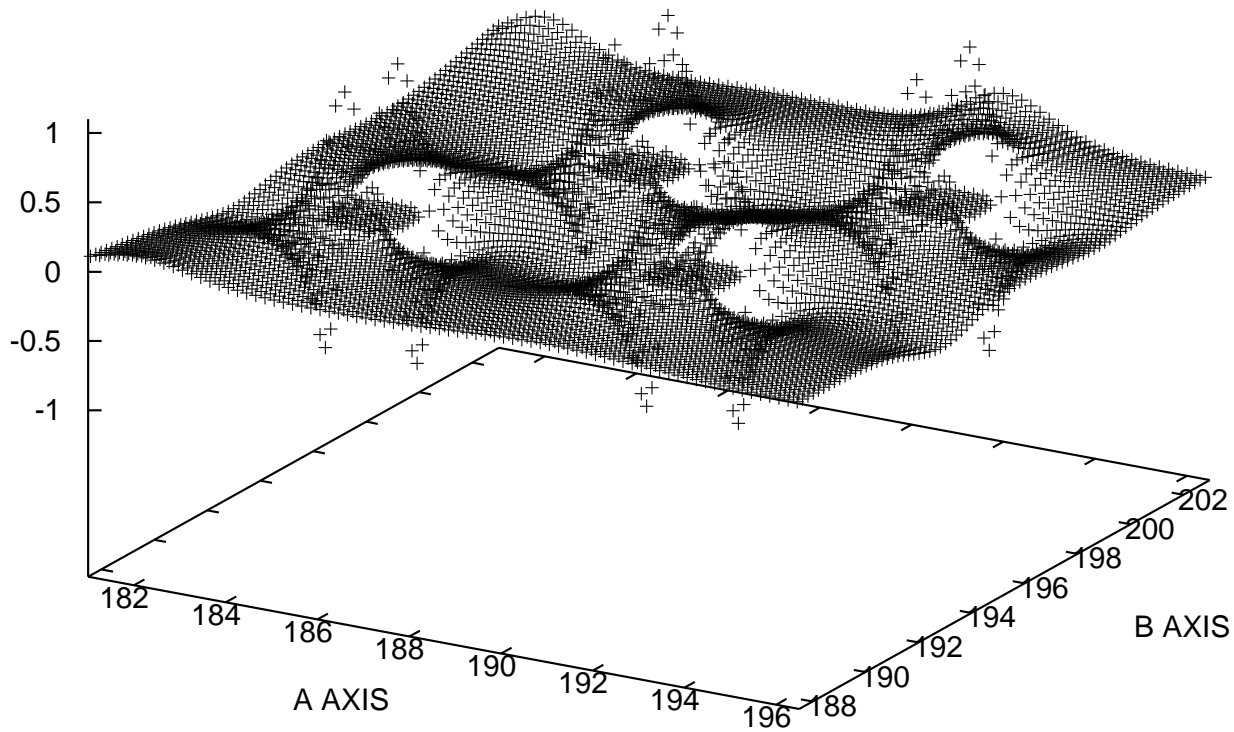


FIG. 2: Displayed is a potential-energy landscape in units of $|\varepsilon_p|$ and of the coherence length for a single vortex line that results from a superposition of 2744 d-wave collective-pinning centers [Eq. (15)] arranged in a “liquid” fashion.