Crystal chemical simulation of superconductors on the basis of oxide and intermetallic layers

L M Volkova

Institute of Chemistry, Far Eastern Branch of the Russian Academy of Sciences 690022 Vladivostok, Russia

E-mail: volkova@ich.dvo.ru

Abstract

Simulation of "hybrid" superconductors of 3d-, 4d- and 5d-transition elements consisting of two different superconducting fragments located between positively charged ions planes – B'O₂ oxide planes and B₂C₂ intermetallic layers – has been performed on the basis of the structure of Sr₂Mn₃As₂O₂ (A₂(B₂C₂)(B'O₂)). The oxide planes are similar to those of CuO₂ in high-temperature superconducting cuprates while the intermetallic layers – to those of Ni₂B₂ in low-temperature superconducting borocarbides RNi₂B₂C and Fe₂As₂ layers in high-temperature superconducting oxypnictides RFeAsO_{1-x}F_x.

1. Introduction

The relation between the temperature of transition into superconducting state and the structural parameters in layered superconductors has been proved experimentally. The T_c change can not be always explained by changing of the charge carriers' concentration. The size effect of A cations located in outer planes of the A2CuO₂ sandwich on T_c has been known since the discovery of high- T_c cuprates [1, 2]. Moreover, it was shown in [3] that not only the size of A cation, but also that of the doping cations (at fixed hole concentration and lattice parameter) affected T_c as well. The sensitivity of superconductivity to the distances from the CuO₂ plane to adjacent A-cations planes $[d(CuO_2-A)]$ was reported in [4-11], while its sensitivity to the distances between A cations and oxygen atoms from the CuO₂ plane [d(A-O)] was found in [12]. $T_{\rm c}$ of the Ln_{1.9}Sr_{0.1}CuO₄ superconductor was doubled (from 25 to 49 K) under effect of strong epitaxial compression, which induced the a

parameter decrease by 0.02 Å and the *c* parameter increase by 0.1 Å [13]. In addition to the size of A cation and its distance to the CuO₂ plane, the charge of this cation also affects T_c . T_c is higher in those optimally doped cuprates (with the same number of CuO₂ planes) where the charge of A cations A is lower. Variation of T_c along with that of the electric field created by the A cations charges was mentioned in [14]. The studies of diborides MgB₂ [15-18] and borocarbides RNi₂B₂C [19-25] showed that T_c of these superconductors, as in case of HTSC cuprates, depended on structural parameters.

We have previously stated [26-31] the correlations between the superconducting transition temperature (T_c) and the relations inside the group of crystallochemical parameters of cationic sublayer for layered superconductors: HTSC on the basis of cuprates, diborides (AB₂) and nickel borocarbides (RNi₂B₂C). These correlations are of similar character for all three classes of compounds, despite the differences in their nature. The correlations enabled us to

conclude that an anisotropic three-dimensional fragment – a sandwich with cationic sublattice of $A_2(Cu)$ in HTSC cuprates, $A_2(B_2)$ in diborides and R(Ni₂) in borocarbides - rather than a separate plane was responsible for emerging of the superconducting phenomenon in layered superconductors. The sandwich internal plane contains square networks of Cu atoms in cuprates and Ni atoms in borocarbides or hexagonal networks of boron atoms in diborides, while the external planes are formed by networks of positively charged ions. The critical structural parameters affecting T_c include the distances between Cu, Ni or B atoms in the sandwich internal plane and those characterizing the space between the internal plane and the A cations plane in this sandwich such as: the interval between these planes surfaces, the degree of heterogeneity of the A cations planes surfaces, and the field formed by A and doping cations charges. We showed that the above parameters, aside from their inherent effect on superconductivity, contained information on the charge carriers' concentration. To attain high transition temperatures, the charges of carriers in the sandwich internal plane and of A ions in the external plane must be of the same sign. It is likely that the T_c could also result from overlapping of the space between the sandwich internal and external planes by the coupling electrons (for example, in borocarbides – by the Ni-B covalent bond electrons) [29]. In the superconducting cuprates the coupling electrons between copper ions and axial oxygen atoms are removed from the CuO₂ plane due to the Jahn-Teller effect while in MgB₂ they are, on the contrary, brought closer to the B2 plane due to substantially ionic character of the Mg-B bond.

The sandwich with a cationic sublattice $R(Fe_2)$ similar to that found in borocarbides RNi_2B_2C (figure 1) can be also discerned in the recently discovered new family of oxypnictides $RFeAsO_{1-x}F_x$ composed of alternating $La_2O_{2-x}F_x$ and Fe_2As_2 layers [32-35] with transition temperatures T_c of 25-28 K, which can be raised up to 55 K by replacing La by Nd, Pr and Sm [36-38],

The objective of the present study is to simulate "hybrid" superconductors containing two different superconducting fragments: oxide planes of CuO_2 -type serving as a basis for high-

temperature superconducting cuprates and intermetallic layers of Ni₂B₂- and Fe₂As₂-type, which participate in formation of superconducting oxypnictides RFeAsO_{1-x}F_x and borocarbides RNi₂B₂C, respectively. An additional requirement in regard to simulation consists in placement of both these fragments between positively charged ions planes to form a superconducting sandwich.

2. Selection and characterization of structural type

The crystal structure of $Sr_2Mn_3As_2O_2$ belonging to the class of oxidpnictides $A_2Mn_3C_2O_2$, where A= Sr, Ba and C = As, Sb, Bi [39], appears to be appropriate for simulation. Let us designate these compounds as $A_2(B_2C_2)(B'O_2)$. The structure of $A_2Mn_3C_2O_2$ compounds is formed by alternating intermetallic layers (B_2C_2) and metalloxide planes MnO_2 (B'O₂). The space between layers is filled by networks of rare earth metal cations. Figure 1 shows the structures formed by B_2C_2 and/or B'O₂ layers.

The intermetallic B_2C_2 layers have been studied as extensively as the metalloxide CuO₂ layers. They belong to different structural types such as ThCr₂Si₂, CaBe₂Ge₂, PbFCl, PbO [40-43] and superconducting phases of LnNi₂B₂C [44] and RFeAsO_{1-x} F_x [32-38] types. The B₂C₂-layer can be represented as built from edge-linked tetrahedral BC_4 (CB₄) or basal edge-linked square pyramids CB₄ (BC₄). Besides, its structure can be considered as a sandwich with inside B₂ square networks and outside C networks with square sides equal to $a\sqrt{2}/2$ and a period, respectively. Interchangeability of metal B and nonmetal C positions in the B₂C₂-layer provides additional possibilities for variation of not only the value, but also of the sign of the layer charge. This layer is capable to sustain significant distortions and exist not only in a tetragonal system, but also, for example, in a rhombic system under a axis compression like in CuTe (a=3,149 Å, b=4,086Å, c=6,946 Å) [45]. Moreover, a remarkable feature of this layer is its stability to extensive variations of atoms sizes and oxidation states as well as the valent electrons concentrations.

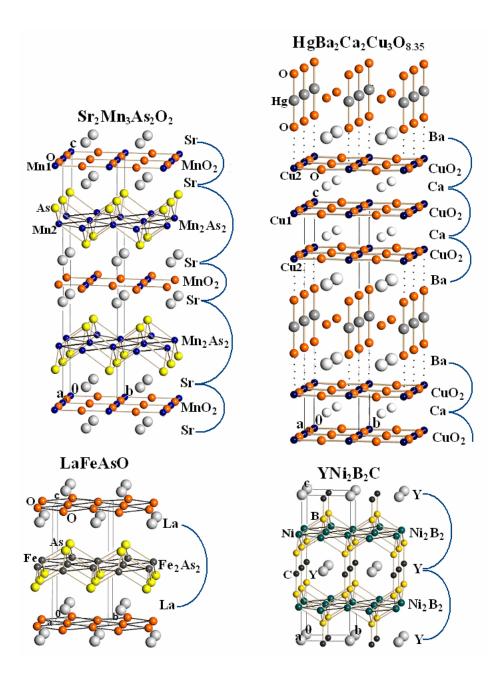


Figure 1. The crystal structures of $Sr_2Mn_3As_2O_2$ and superconductors formed by B_2C_2 and/or B'O₂ layers. The superconducting fragments-sandwiches are shown by semicircles.

The reason of such a stability consists in formation of additional bonds between atoms of the same type (B or C) in flat square networks of both internal and external layers of a B_2C_2 -sandwich and variation of B-C bond lengths. The following examples demonstrate the layer ability to adapt to the compound composition. The distances Cu-Cu, Si-Si and Cu-Si in the Cu₂Si₂-layer are equal to 2.64, 3.73 and 2.52 Å in HfCuSi₂ [45] and 2.97, 4.20 and 2.47 Å in SrCu₂Si₂ [46], respectively. The distances Te-Te

in the Cu₂Te₂-layer are equal to 3.149 and 4.086 Å in the compound CuTe [47] and 4.384 Å in the compound NaCuTe [48], respectively. The shortest distances Cu-Cu in HfCuSi₂ and Te-Te in CuTe are possibly of a binding character, since they are close to Cu-Cu distances in metallic copper (2.56 Å) and regular Te-Te covalent bond lengths (2.69-2.80 Å) [49]. The B₂C₂-layer serves as a buffer to sustain the crystal electroneutrality due to changing the B and C valent states and emerging of the B...B and C...C interactions.

3. Candidate superconductor compounds

The number of representatives of the structural type $Sr_2Mn_3As_2O_2$ must be increased with using transition d-elements such as Cu, Nd, Ta, Re, Ru and Ti. The chemical composition $A_2(B_2C_2)(B'O_2)$ of simulated superconductors shall satisfy the following requirements: B' and B (in some cases only B) shall be transition metals in a mixed-valency state with the intervalent charge transfer energy not higher than for copper ions and have a magnetic moment in one of the valent states.

The B_2C_2 -layers with the structures of ThCr₂Si₂- and CaBe₂Ge₂-types occur for most of 3d, 4d and 5d elements. Aside from similarity of chemical nature and size, d-elements isomorphism in these layers is facilitated by metal and nonmetal atoms locations in some layer planes.

The question on the possibility of formation of flat CuO₂-type layers by these metals remains unanswered. Nevertheless, according to [50], an isomorphic interchangeability of Cu²⁺ by Mn^{2+/3+}, Zn^{2+} , Nb^{4+} , Re^{4+} and Ta^{5+} ions is possible. For the first two Mn ions and, most surprisingly, Zn ions, the compounds $A_2Mn_3Pn_2O_2$ (A = Sr; Pn = P, As, Sb, Bi and A = Ba; Pn = P, As, Sb) [39, 51] and $A_2Zn_3As_2O_2$ (A = Sr, Ba) [52], where Mn and Zn are located in a flat square surrounding by oxygen atoms, have been obtained. Conventionally, a flat coordination is characteristic for Jahn-Teller ions; however, the "forced" coordination phenomenon is known and possibly takes place in $A_2Zn_3As_2O_2$ compounds. It is not also ruled out that coordination of some d-elements is supplemented by two additional oxygen atoms with formation of an octahedron.

There exist some limitations imposed on the $A_2(B_2C_2)(B'O_2)$ compounds composition. In the homologous series of these compounds, just like in the AB_2C_2 (ThCr₂Si₂- and CaBe₂Ge₂-type) compounds series, the value of *a* parameter varies, as a rule, proportionally to variation of A, B and C atoms sizes. Furthermore, in $A_2(B_2C_2)(B'O_2)$ geometrical parameters of the B_2C_2 -layer and A ions sizes are additionally affected by the possibility of varying the B'-O bonds lengths in the oxide layer. For example, substitution of Sr by Ba and As by Sb would result in increasing *a* by approximately 0.1 Å.

Excessive increase of this parameter at substitution of A, B or C by larger ions might result in the B'-O bond rupture and compound destruction. For example, while in the series $A_2Mn_3As_2O_2$ and $A_2Mn_3Sb_2O_2$ the compounds with A = Sr and Ba were obtained, in the series $A_2Mn_3Bi_2O_2$ – only the strontium compounds. This must be also the reason why the authors of [52] could not synthesize the compounds $A_2Zn_3Sb_2O_2$ with antimony along with successful synthesis of $A_2Zn_3As_2O_2$ (A = Sr, Ba) with arsenic.

Let us calculate geometrical parameters of predicted compounds A2(B2C2)(B'O2). The B'-O bonds lengths in the plane $B'O_2$ for B' = Cu [53], Nb [54 - 56], Ta [57 - 59], Re [60], Ru [61] and Ti [62] would be approximately equal to average bond lengths in B'O₆ octahedra of respective elements and fall into the range 1.90-2.00 Å (the limit of stability of B'-O bonds in these elements octahedra is rather wide (1.70-2.30 Å)). Therefore, the elementary unit parameter a and the distances B-B or C-C in the B₂C₂-sandwich internal plane would be in the range 3.80-4.00 Å and 2.76-2.83 Å, respectively. The latter values are close to the metal-metal distances found for metals under study (2.64-2.86 Å) [63], except Cu (d(Cu-Cu) = 2.56 Å).

The stability of the AB'O₂-fragment in the structure of $A_2(B_2C_2)(B'O_2)$ is determined by the value of tolerance factor (*t*), since this fragment has a perovskite-type structure. When the *a* unit parameter is equal to 3.9 ±0.1 Å, the most appropriate ions for A position are Sr, Ca and Na, since for them at *t* in the range of the structure stability (0.8-1) the parameter *a* varies in the ranges 3.62-4.52, 3.39-4.24 and 3.42-4.28 Å, respectively (ionic radii for calculation are taken from [64]).

Using the above considerations and calculated geometrical parameters, we have performed simulation of previously unknown layered compounds $A_2(B_2C_2)(B'O_2)$ with the structure of $Sr_2Mn_3As_2O_2$ -type. Table 1 gives the composition and charge (Q) for the 2A, B'O₂ and B_2C_2 layers of these systems and the B_2C_2 -layer characteristics. Table 1 also includes the type of interaction within the plane and

t	6 (0)		Square	Interaction type
2A	B_2C_2	$B'O_2$	pyramids in	in B_2C_2 -layer
			B ₂ C ₂ -layer	planes
Ca _{2-x} Na _x	B_2C_2	CuO_2	CB_4	BB
	(B = Mn, Fe, Cu)			
4-δ	(C = P, As, Si, Ge)			
	-2	-2+(+δ)		
$Ca_{2-x}Y(Ln)_x$	B_2C_2	CuO_2	CB_4	BB
	(B = Mn, Fe, Cu)			
4+δ	(C = P, As, Si, Ge)			
	-2	-2+(-ð)		
Ca _{2-x} Na _x	B_2C_2	B'O ₂	CB_4	BB
	(B = Ru, Ti)	(B' = Ru, Ti)		
	(C = P, As)			
3-δ	-2	-1+(+δ)		
	(C = Si, Ge)	(B' = Ru, Ti)		
4-δ	-3	-1+(+δ)		
Na _{2-x} Ca _x	B_2C_2	B'O ₂	CB_4	BB
	(B = Ru, Ti)	(B' = Ru, Ti)		
	(C = Si, Ge)			
2+δ	-2	0+(-δ)		
Na _{2-x}	B_2C_2	$B'O_2$	CB_4	BB
	(B = Nb, Ta, Re)	(B' = Nb, Ta, Re)		
	(C = Si, Ge)			
2-δ	-2	0+(+δ)		
Ca _{2-x} Na _x	Cu_2Te_2	CuO ₂	TeCu ₄	TeTe
$4 - (\delta_1 + \delta_2)$	-2+(+δ ₁)	-2+(+δ ₂)		
Y _{2-x} Ca _x	Hg_2Te_2	CuO_2	TeHg ₄	HgHg
$5 - (\delta_1 + \delta_2)$	-3+(+δ ₁)	-2+(+δ ₂)		TeTe
Ca _{2-x} Na _x	In_2Bi_2	CuO_2	BiIn ₄	InIn
4-($\delta_1 + \delta_2$)	$-2+(+\delta_1)$	-2+(+δ ₂)		BiBi
Na _{2-x}	In_2Bi_2	B'O ₂	BiIn ₄	InIn
		(B' = Nb, Ta, Re)		BiBi
2- $(\delta_1 + \delta_2)$	$-2+(+\delta_1)$	$0+(+\delta_2)$		

Table 1. Composition and charge (Q) of layers in compounds A₂(B₂C₂)(B'O₂) & B₂C₂-layer data

distribution of metal (B) and nonmetal (C) atoms on planes (atoms located in the base of CB_4 (BC₄) pyramid form an internal plane while those located in the top – external planes of the B₂C₂layer).

Let us present some arguments in favor of such systems realization.

The system $Ca_{2-x}Na_x(B_2C_2)(CuO_2)$ doped by holes (CuO₂ layer charge is equal to 2+(+ δ)) and the system $Ca_{2-x}Y(Ln)_x(B_2C_2)(CuO_2)$ doped by electrons (CuO₂ layer charge is equal to 2+(- δ)), where B= Mn, Cu, Fe and C = P, As, Si and Ge, are built, according to [50], through substitution of the following elements in Sr₂Mn₃Pn₂O₂ (Pn = P, As, Sb, Bi) [39, 52] by isomorphous elements: Sr by Ca(Na) or Ca(Y, Ln); Mn by Cu and Fe; P by Si; Sb by Ge. The Mn₂Ge₂ layers were found in AMn_2Ge_2 (structural type $ThCr_2Si_2$), where A = Ca, Sr [65].

The possibility of realization of the systems $Ca_{2-x}Na_x(B_2C_2)(B'O_2)$ and $Na_{2-x}Ca_x(B_2C_2)(B'O_2)$, where B and B' = Ru^{3+} - Ru^{4+} and Ti^{3+} - Ti^{4+} and C = P, As, Si and Ge, is based on isomorphism [50] of the elements Mn, Ru and Ti and the existence of the following intermetallic compounds that are isostructural to ThCr₂Si₂: ARu₂P₂, ARu₂As₂ [66], ARu₂Ge₂ [67], where A = Ca, Sr, as well as in ARu₂Si₂, and ARu₂Ge₂ (A = Y, Ln) [68].

Unfortunately, we could not find data for the system $Na_{2-x}(B_2C_2)(B'O_2)$, where B and B' = Nb, Ta, Re, and C = Si, Ge. However, the elements B and B' included into this system are known [50] to be isomorphous to Cu.

The systems Ca_{2-x}Na_x(B₂Te₂)(CuO₂) and Y_{2-x}Ca_x(B₂Te₂)(CuO₂) are capable to exist with the layers B₂Te₂ (B = Cu, Hg), where tellurium atoms are located in external planes while Cu or Hg atoms – in internal planes of this layer. This results from possible isomorphism between Hg, Cu and Fe elements [50], and for the latter two elements such layers were found in the compounds NaCuTe [48], CuTe [47], FeTe_{0.9} and Fe_{1.125}Te [66]. One should mention that the formal valency of mercury in the layer Hg₂Te₂ (d(Hg-Hg) ~2.76 Å) would be less than 1, since in Hg₃AsF₆ [67], where the distance d(Hg-Hg) = 2.64 Å, the Hg valency is equal to 1/3.

Realization of the systems Ca₂ $_{x}Na_{x}(In_{2}Bi_{2})(CuO_{2})$ and $Na_{2-x}(In_2Bi_2)(B'O_2),$ where B' = Nb, Ta, Re, must be also possible. The calculated with using the applied model distances between In atoms (d(In-In)~2.76 Å) located in the internal plane of the In₂Bi₂ layer are close to those found, for example, in InSe (d(In-In) = 2.82 Å) [68]. The distances between bismuth atoms (d(Bi-Bi) ~3.9 Å) located in the external planes of the In₂Bi₂ layer would be much shorter than the Bi van der Waals diameter (4.4 Å) that enables one to suggest the emerging of Bi...Bi interactions.

4. Conclusions

The simulation was performed for new "hybrid" superconductors $A_2(B_2C_2)(B'O_2)$ consisting of two different superconducting fragments: oxide planes B'O₂ and intermetallic layers B_2C_2 located between positively charged ions planes. The crystal structure of $Sr_2Mn_3As_2O_2$ $(Sr_2(Mn_2As_2)(MnO_2))$ related to one of the crystal chemical factors participating in creating conditions for emerging of superconducting state in layered superconductors was used in the simulation. This structure consists of fragments comprising sandwiches I/S/I, in which the internal layer S (B_2C_2 and $B'O_2$) is capable to accumulate transferrable charge carriers at doping other layers in the structure while the external layers I are dielectric planes built from positively charged ions. The possibilities of realization of the $A_2(B_2C_2)(B'O_2)$ system on the basis of B and B' = Cu, Mn, Fe, Nb, Ta, Re, Ru or Ti and C = Si, Ge, P, As, Bi or Te are discussed.

References

- [1] Cava R J 1998 Nature 394 127
- [2] Williams G V M and Tallon J L 1996 Physica C 258 41
- [3] Attfield J P, Kharlanov A L and McAllister J A 1998 Nature 394 157
- [4] Zhang X, Lu W H and Ong C. K 1997 Physica C 289 99
- [5] Volkova L M, Polishchuk S A, Magarill S A and Borisov S V 1989 Sverkhprovodimost: Fiz., Khim., Tekh. 2 127
- [6] Morosin B, Venturing E L, Dunn R G and Newcomer P P 1997 Physica C 288 255
- [7] Nobumasa H, Shimizu K and Kawa T 1990 Physica C 167 515
- [8] Volkova L M, Polishchuk S A, Magarill S A and Borisov S V
- 1991 Sverkhprovodimost: Fiz., Khim., Tekh. 4 155
- [9] Motida K 1991 J. Phys. Soc. Jpn. **60** 3194
- [10] Volkova L M, Polishchuk S A, Magarill S A and Buznik V M 1997 Dokl. Ross. Akad. Nauk 353 200
- [11] Varela M, Arias D, Sefrioui Z, Leon C, Ballesteros C,
- Pennycook S J and Santamaria J 2002 *Phys. Rev. B* 66, 134517 [12] Oshima A and Motida K 2002 *J. Supercond*, **15** 165
- [13] Locquet J-P, Ferret J, Fompeyrine J, Maächler E, Seo J W and Van Tendeloo G 1998 *Nature* **394** 453
- [14] Amelin I I 1994 Sverkhprovodimost: Fiz., Khim., Tekh. 7 788
- [15] Buzea C and Yamashita T 2001 Supercond. <u>Sci</u> and Techn, 14 R115-R146
- [16] Wan X, Dong J, Weng H and Xing D Y 2002 Phys. Rev. B 65 012502
- [17] Neaton J B and Perali A 2001 *Preprint* http://arxiv.org/abs/cond-mat/0104098
- [18] Medvedeva N I, Ivanovskii A L, Medvedeva J E and A J Freeman 2001 Physical Review B 64 20502 (Rapid)
- [19] Tomy C V, Martin J M and Paul D Mc K 1996 Physica B 223&224 116
- [20] Freudenberger J, Kreyssig A, Ritter C, Nenkov K, Drechsler S.-L, Fuchs G, Muller K-H, Loewenhaupt M and Schultz L 1999 Physica C 315 91
- [21] Cho B K, Canfield P C and Jonston D C 1996 Phys. Rev.Lett. 77 163
- [22] Narozhnyi V N, Fuchs G, Freudenberger J, Nenkov K and Müller K-H 2001 Physica C 364-365, 571
- [23] Bitterlich H, Löser W, Behr G, Nenkov K, Fuchs G, Belger A and Schultz L 1998 Physica C 308 243
- [24] Jaencke-Roessler U, Belger A, Zahn G, Wehner B, Paufler P and Bitterlich H 1999 *Physica C* **314** 43
- [25] Eversmann K, Handstein A, Fuchs G, Cao L and Müller K-H 1996 Physica C 266 27
- [26] Volkova L M, Polyshchuk S A, Magarill S A and Sobolev A N 2000 Inorganic Materials 36 919
- [27] Volkova L M, Polyshchuk S A and Herbeck F E 2000 J. Supercond. 13 583
- [28] Volkova L M, Polyshchuk S A, Magarill S A and Herbeck F E 2001 J. Supercond. 14 693 (Preprint http://arxiv.org/abs/condmat/0108295)
- [29] Volkova L M, Polyshchuk S A, Magarill S A and Herbeck F E 2002 J. Supercond. 15 667 (Preprint http://arxiv.org/abs/condmat/0205533)
- [30] Volkova L M, Polyshchuk S A, Magarill S A and Herbeck F E 2003 J. Supercond. 16 939 (Preprint http://arxiv.org/abs/condmat/0212625)
- [31] Volkova L M, Polyshchuk S A and Herbeck F E 2004 Focus on Superconductivity, ed Barry P. Martins (N.Y.: Nova Science Publisher Inc.) p.83 (Preprints http://arxiv.org/abs/cond- mat/0402272 and cond-

mat/0310511) [32] Kamihara Y, Watanabe T, Hirano M and Hosono H 2008

- J. Am. Chem. Soc. 130 3296
- [33] Zhu X, Yang H, Fang L, Mu G and Wen H-H 2008 Preprint http://arxiv.org/abs/0803.1288v1

- [34] Chen G F, Li Z, Li G, Zhou J, Wu D, Dong J, Hu W Z, Zheng P, Chen Z J, Luo J L and Wang N L 2008 Preprint http://arxiv.org/abs/0803.0128v1
- [35] Sefat A S, McGuire M A, Sales B C, Jin R, Hove J Y and Mandrus D 2008 Preprint http://arxiv.org/abs/0803.2528
- [36] Ren Z-A, Yang J, Lu W, Yi W, Shen X-L, Li Z-C, Che G-C, Dong X-L, Sun L-L, Zhou F and Zhao Z-X 2008 Preprint http://arxiv.org/abs/0803.4234)
- [37] Ren Z-A, Yang J, Lu W, Yi W, Che G-C, Dong X-L, Sun L-L and Zhao Z-X. 2008 Preprintt http://arxiv.org/abs/0803.4283
- [38] Ren Z-A, Lu W, Yang J, Yi W, Shen X-L, Li Z-C, Che G-C, Dong X-L, Sun L-L, Zhou F and Zhao Z-X 2008 Preprint http://arxiv.org/abs/0804.2053
- [39] Brechtel E, Cordier G and Schafer H 1979 Z. Naturforsch. B 34 777
- [40] Garnier P, Moreau J and Gavarri J R 1990 Mater. Res. Bull 25 979
- [41] Binnie W P 1956 Acta Crystallogr. 9 686
- [42] Zang H, Wang Y Y, Zhang H, Dravid V P, Marks L D, Han P D, Payne D A, Radaelli P G and Jorgensen J D 1994 Nature 370 352
- [43] Ban Z and Sikirica M 1965 Acta Crystallogr. 18 594
- [44] Siegrist T, Zandbergen H W, Cava R J, Krajewski J J and Peck Ir W F 1994 Nature 367 254
- [45] Andrukhin L S, Lysenko L A, Yarmolyuk Ja P and Gladyshevskii E I 1975 Dopovidi. Acad. Nauk Ukr.RSR A 7 645
- [46] Eisenmann B, May N, Müller W, Schafer H, Weiss A, Winter J and Ziegleder G Z 1970 Naturforsch. B 25 1350
- [47] Baranova R V and Pinsker Z G 1973 Z. Kristallografiya 18 1169
- [48] Sabelsberg G and Schafer H Z. 1978 Naturforsch. B 33 370
- [49] Burns R C, Gillespie W C and Slim D R 1979 Inorg. Chem. 18

3086

- [50] Makarov E S 1973 Atom Isomorphy in Crystals (Moscow: Atomizdat)
- [51] Stetson N T and Kauzlarich S 1991 Inorg. Chem, 30 3969
- [52] Brock S L and Kauzlarich S M 1994 Inorg. Chem. 33 2491
- [53] Sugij N, Yamauchi H and Izumi M 1994 Phys. Rev. B 50 9503
- [54] Andersson S, and Galy J 1969 Acta Crystallogr. Sect. B 25 847
- [55] Schtckel K und Müller-Buschbaum H 1986 Rev. Chimie minerale 23 154
- [56] Wichmann R und Müller-Buschbaum H 1986 Z. Anorg. Allg. Chem. 539 203
- [57] Ishizawa N, Marumo F, Kawamura T and Kimura M 1976 Acta Crystallogr. Sect. B 32 2564
- [58] Shannon J and Katz L 1970 Acta Crystallogr. 26 102
- [59] Marayama N, Sudo E, Kahi K, Tsuzuki A, Kawakami S, Awano M and Torit Y 1988 Jap. J. Appl. Phys. 27 L 1623
- [60] Calvo C, NG H N and Chamberland B L 1978 Inorg. Chem. 17 699
- [61] Maeno Y, Hashimoto H, Yoshida K, Nishizaki S, Fujita T, Bednorz J G and Lichtenberg F 1994 *Nature* **372** 532
- [62] Ruddlesden S N and Popper P 1957 Acta Crystallogr. 10 538
- [63] Wyckoff R W G 1963 *Crystal Structures* vol 1 (New-York London Sydney: John Wiley & Sons)
- [64] Shannon R D and Prewitt C T 1969 Acta Crystallogr. 25 925
- [65] Dorrscheidt W, Neiss N and Schafer H 1976 Z. Naturforsch. B 31 890
- [66] Wenski G and Newis A Z. 1986 Naturforsch. B 41 38
- [67] Schultz J, Williams J W, Miro N D, MacDiarmid A G and Heeger A J 1978 Inorg. Chem. 17 646
- [68] Likforman A, Carré D, Etienne J J and Bachet B 1975 Acta Crystallogr. B 31 1252