

Effect of pressure on the steplike magnetostriction of single crystalline bilayered manganite($\text{La}_{0.4}\text{Pr}_{0.6}$) $_{1.2}\text{Sr}_{1.8}\text{Mn}_2\text{O}_7$

Y.Yamato,¹ M.Matsukawa,^{1,*} T.Kumagai,¹ R.Suryanarayanan,²
S.Nimori,³ M.Apostu,⁴ A.Revcolevschi,² K. Koyama,⁵ and N. Kobayashi⁵

¹*Department of Materials Science and Engineering, Iwate University, Morioka 020-8551, Japan*

²*Laboratoire de Physico-Chimie de L'Etat Solide, CNRS,
UMR8182 Universite Paris-Sud, 91405 Orsay, France*

³*National Institute for Materials Science, Tsukuba 305-0047, Japan*

⁴*Department of Physical, Theoretical and Materials Chemistry,
Faculty of Chemistry, Al. I. Cuza University, Carol I, 700506 Iasi, Romania*

⁵*Institute for Materials Research, Tohoku University, Sendai 980-8577, Japan*

(Dated: November 1, 2018)

We report the effect of pressure on the steplike magnetostriction of single crystalline bilayered manganite($\text{La}_{0.4}\text{Pr}_{0.6}$) $_{1.2}\text{Sr}_{1.8}\text{Mn}_2\text{O}_7$, for our understandings of the ultrasharp nature of the field-induced first-order transition from a paramagnetic insulator to a ferromagnetic metal phase. The application of pressure suppresses a steplike transformation and causes a broad change in the magnetostriction. The injection of an electric current to the crystal also weakens the steplike variation in both the magnetostriction and magnetoresistance. The stabilization of ferromagnetic interaction or the delocalization of charge carriers is promoted with the applied pressure or applied current, resulting in the suppressed steplike behavior. Our findings suggest that the step phenomenon is closely related to the existence of localized carriers such as the short-range charge-orbital ordered clusters.

PACS numbers:

I. INTRODUCTION

Perovskite manganites show a great variety of fascinating properties such as colossal magnetoresistance (CMR) effect and charge-ordered insulating phase¹. The most interesting one is the existence of a phase-separated state, the coexistence of antiferromagnetic charge-orbital ordered (COO) insulating and ferromagnetic (FM) metal regions². Several recent studies on metamagnetic transition in phase-separated manganites have revealed that ultrasharp steps in magnetization curves appear at low temperatures^{3,4,5,6,7,8}. To account for this, a martensitic model due to local strain fields stored in the lattice between competing COO and FM phases with their different unit cells has been proposed though questions have been raised against this model.

For our understanding of the dynamics of a step-like first-order transition from a paramagnetic insulating (PMI) to a ferromagnetic metal (FMM) phase in CMR manganites, we examine the pressure effect on c axis magnetostriction of single crystalline ($\text{La}_{0.4}\text{Pr}_{0.6}$) $_{1.2}\text{Sr}_{1.8}\text{Mn}_2\text{O}_7$.

For the Pr-substituted ($\text{La}_{0.4}\text{Pr}_{0.6}$) $_{1.2}\text{Sr}_{1.8}\text{Mn}_2\text{O}_7$ crystal, a spontaneous ferromagnetic metal phase (originally present with no Pr substitution) disappears at ground state but a field-induced PMI to FMM transformation is observed over a wide range of temperatures^{9,10}. A magnetic (H, T) phase diagram, established from magnetic measurements, is separated into three regions labeled as PMI, FMM, and bistable states, as shown in Fig.1 of ref.¹¹. The proximity of free energies between the PMI and FMM states is of importance to realize the bistable

state where the FMM and PMI states coexist. A stronger field is needed to induce the PMI to FMM transition at low temperatures since the thermal energy is reduced upon lowering temperature.

II. EXPERIMENT

Single crystals of ($\text{La}_{1-z}\text{Pr}_z$) $_{1.2}\text{Sr}_{1.8}\text{Mn}_2\text{O}_7$ ($z=0.6$) were grown by the floating zone method using a mirror furnace. The calculated lattice parameters of the tetragonal crystal structure of the crystals used here were shown in a previous report¹⁰. The dimensions of the $z=0.6$ sample are 3.4×3 mm² in the ab -plane and 1mm along the c -axis. Measurements of magnetostriction along the c -axis were done by means of a conventional strain gauge method at the Tsukuba Magnet Laboratory, the National Institute for Materials Science (NIMS) and at the High Field Laboratory for Superconducting Materials, Institute for Materials Research, Tohoku University. Except for an initial cooled down, the sample was zero-field cooled from 200K down to low temperatures and we then started measuring the isothermal magnetostriction upon increasing (or decreasing) the applied fields, parallel to the c -axis. Next, warming the sample from low temperatures up to 200K in the absence of field and keeping the sample fixed at 200K for 2 hours, the sample was then cooled down to the low T. A typical cooled time is needed for about 2 hours. Checking the stability of sample's temperature, we restart measuring the magnetostriction. For each measurement, we repeated the same procedure. The normal sweep rate was set to be

0.26 T/min. Hydrostatic pressures in the magnetostriction experiment were applied by a clamp-type cell using Fluorinert as a pressure transmitting medium. The pressure was calibrated by the critical temperature of lead. After the magnetostriction measurement under the pressure, we restarted measuring $dL_c(H)$ using the same clamp-type cell but without the applied pressure. Next, we examined the c -axis magnetostriction as a function of the applied current in the ab plane at ambient pressure. Once the sample was removed from the clamp-type cell, it was set in a conventional cryostat for magneto transport measurements. On both ends of the sample the electrodes for injection of the electric current were formed using a gold paste and Cu wires were then attached with silver paste. For magnetoresistance measurements, we carried out the same temperature profile as the magnetostriction experiments.

III. RESULTS AND DISCUSSION

Figure 1 shows the c -axis magnetostriction, $dL_c(H)/L_c(0)$, of $(\text{La}_{0.4}\text{Pr}_{0.6})_{1.2}\text{Sr}_{1.8}\text{Mn}_2\text{O}_7$, both under ambient pressure and a hydrostatic pressure of 0.8 GPa at lower temperatures, where the applied field is parallel to the c -axis ($H\parallel c$). Here, the value of $dL_i(H)$ is defined as $L_i(H) - L_i(0)$. First of all, the steplike lattice transformations appear at 4 K and 6 K at ambient pressure, as shown in Fig.1.

On the other hand, the application of external pressure on the crystal substantially suppresses the steplike transition, causing a broad variation in the magnetostriction. At 4.3 K, the critical field, H_c , is increased from 6.1 T at ambient pressure up to 6.6 T at 0.8 GPa. At 6 K, a huge steplike transition vanishes under the pressure and a continuously smooth variation is observed at high fields, followed by the appearance of a tiny step around 8 T. However, the characteristic field signifying the onset of the field-induced metamagnetic transition, which is not the critical field of the step transitions, is rather lowered at the presence of the applied pressure, as the pressure data measured at high- T in Fig.2.

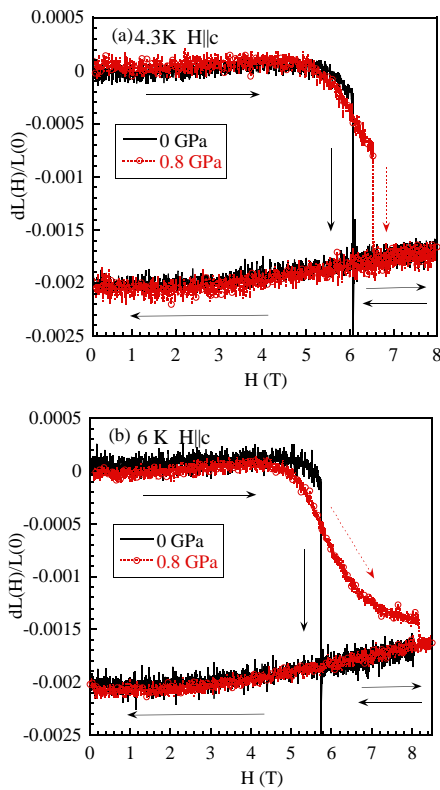


FIG. 1: (color online) the c -axis magnetostriction, $dL_c(H)/L_c(0)$, of $(\text{La}_{0.4}\text{Pr}_{0.6})_{1.2}\text{Sr}_{1.8}\text{Mn}_2\text{O}_7$, both under ambient pressure and a hydrostatic pressure of 0.8 GPa at low temperatures (a) 4K and (b) 6K. The applied field is parallel to the c -axis ($H\parallel c$).

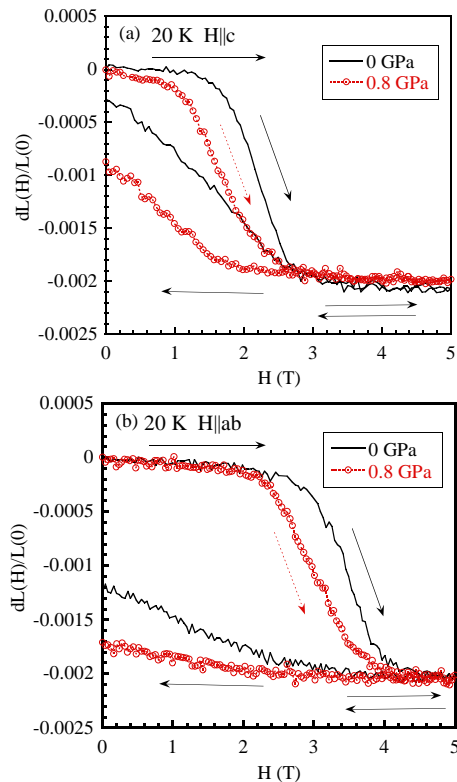


FIG. 2: (color online) the c -axis magnetostriction, $dL_c(H)/L_c(0)$, of $(\text{La}_{0.4}\text{Pr}_{0.6})_{1.2}\text{Sr}_{1.8}\text{Mn}_2\text{O}_7$, both under ambient pressure and a hydrostatic pressure of 0.8 GPa at 20 K. (a) $H\parallel c$ and (b) $H\parallel ab$.

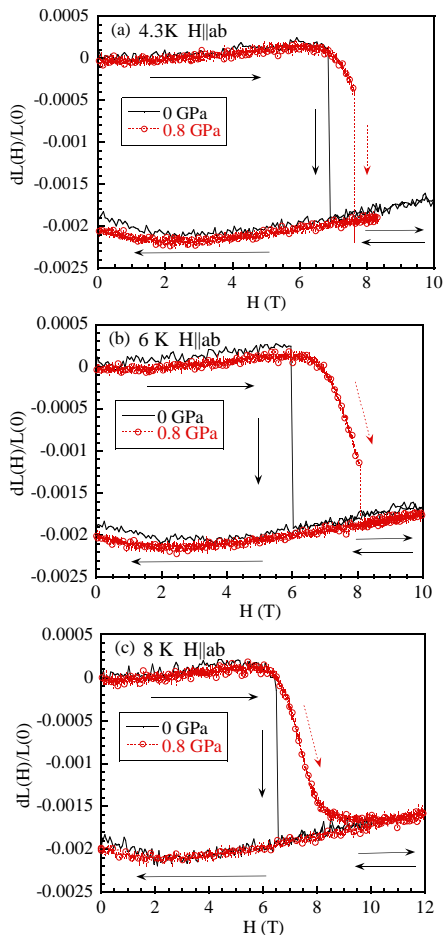


FIG. 3: (color online) the c -axis magnetostriction, $dL_c(H)/L_c(0)$, of $(\text{La}_{0.4}\text{Pr}_{0.6})_{1.2}\text{Sr}_{1.8}\text{Mn}_2\text{O}_7$, both under ambient pressure and a hydrostatic pressure of 0.8 GPa at low temperatures (a) 4K (b) 6K and (c) 8K. The applied field is parallel to the ab -plane ($H||ab$).

When the magnetic field is applied to the ab plane ($H||ab$), we obtain similar results, as shown in Fig.3. These findings are indicative of the occurrence of steplike transformation almost independent of the easy axis of magnetization. The small differences of the higher critical fields in the case of $H||ab$ probably arises from the easy axis of M lying along the c -axis. Under the application of 0.8 GPa, we obtain both $H_c \sim 7.6$ T at 4.3 K and 8.1 T at 6 K accompanied by a degradation of a discontinuous jump, and the disappearance of any steplike profile in $dL_c(H)/L_c(0)$ curve at 8 K.

In our previous paper¹², we have found out that the application of pressure enhances a field-induced ferromagnetic state of Pr-substituted $\text{La}_{1.2}\text{Sr}_{1.8}\text{Mn}_2\text{O}_7$. Our findings are understood from the viewpoint that the double-exchange interaction-driven FM state is strengthened by the applied pressure. For the magnetic field cooled sample, the remarkable step observed in $dL_c(H)/L_c(0)$ is monotonically decreased upon increasing the cooling field

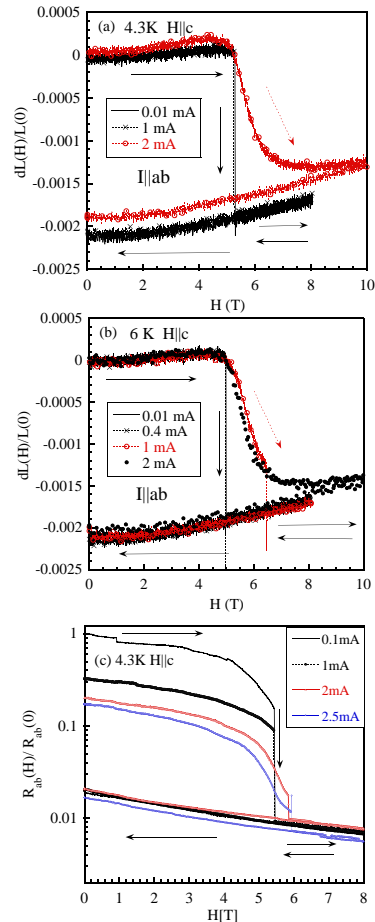


FIG. 4: (color online) the c -axis magnetostriction, $dL_c(H)/L_c(0)$, of $(\text{La}_{0.4}\text{Pr}_{0.6})_{1.2}\text{Sr}_{1.8}\text{Mn}_2\text{O}_7$, under the electric current applied in the ab plane at low temperatures (a) 4K and (b) 6K. The applied field is parallel to the c -axis. (c) the ab plane magnetoresistance R_{ab} of the $z = 0.6$ sample at 4.3K as a function of the applied current from 0.1 up to 2.5 mA. The $R_{ab}(H)$ data are normalized by $R_{ab}(0)$, which is the zero-field resistance at the lowest applied current (0.1 mA). ($H||c$)

from 1 T up to 1.6 T, accompanied by a nonlinear dependence of H_c ¹³. The steplike behavior vanishes when the cooling field exceeds 1.6 T. For each field-cooled run, we expect that the FM region is initially formed within the PMI matrix before the magnetostriction measurements are carried out. A larger volume fraction of the FM phase causes a more suppressed variation in dL . Thus, a pressure-induced suppression in the ultrasharp magnetostriction is a reasonable result since the applied pressure enhances the FM state.

Next, we carry out the magnetostriction measurement under the applied electric current, to examine a relationship between charge transport and steplike lattice deformation appeared in CMR manganites. In the case of ambient pressure, the c axis magnetostriction data at 4.3K

are presented in Fig.4(a) as a function of excited current ($I=0.01, 1$ and 2 mA). Here, the electric current is applied in the ab plane parallel to the MnO_2 double layers. Injection of the electric current over 2 mA exhibits no discontinuous profile in $dL_c(H)/L_c(0)$. We note that the bath temperature is very stable against the applied current up to 2 mA within $\sim 0.5\%$ and Joule heating of the sample affects no contribution to the present behavior.

For comparison, let us now display in Fig.4(c) the ab plane magnetoresistance R_{ab} of the $z = 0.6$ sample as a function of the applied current from 0.1 up to 2.5 mA. First of all, the application of higher current gives rise to a degradation of the magnetoresistive steps observed at lower currents, which is almost consistent with the magnetostriction data shown in Fig.4(a). Next, the zero-field resistance measured at 2 mA shows a substantial drop by $\sim 80\%$, in comparison to $R_{ab}(0)$ at the lowest current (0.1 mA). This result indicates the current-induced destabilization of PMI matrix although the physical role of the application on an electric field is not clear. Similar results are reported in a systematic study on nonlinear transport of a non charge-ordered manganite $\text{Pr}_{0.8}\text{Ca}_{0.2}\text{MnO}_3$, which is not so far from the CO region¹⁴. In a lightly Pr-substituted crystal $(\text{La}_{0.8}\text{Pr}_{0.2})_{1.2}\text{Sr}_{1.8}\text{Mn}_2\text{O}_7$ with $T_c \sim 90\text{K}$, we also have obtained a current-induced remarkable drop in the ab plane resistance at selected temperatures just above T_c . (not shown here) The formation of short-range charge ordering in the paramagnetic phase of an optimally doped parent crystal $\text{La}_{1.2}\text{Sr}_{1.8}\text{Mn}_2\text{O}_7$ has been observed in a previous study¹⁵. Accordingly, we expect that the application of the electric current removes the localizes carriers, such as the COO insulating clusters, from the PMI phase of the Pr-substituted crystal, causing a substantial reduction in the zero-field resistance at higher currents.

Furthermore, neutron scattering measurements on a bilayered manganite $\text{La}_{2-2x}\text{Sr}_{1+2x}\text{Mn}_2\text{O}_7$ ($x = 0.38$) have revealed that the CE-type COO clusters freeze upon decreasing temperature from $T \sim 310\text{K}$, preventing the formation of a long-range COO state¹⁶. The authors have also argued that the PMI state of the crystal with-

out Pr substitution is caused by an orbital frustration and stabilized down to the FMM transition temperature $T_c \sim 114\text{K}$. For the present Pr-substituted sample, one believes that the short-range COO clusters accompanied by the orbital frustration are present within the PMI matrix. As discussed in ref.¹³, we suppose that the orbital frustration has some relationship with the critical instability of the metastable state of the free energy, resulting in the steplike phase transition. The application of hydrostatic pressure stabilizes the ferromagnetic interaction within the paramagnetic matrix and the applied current reinforces an itinerant state of charge carriers within the insulating matrix. In other words, these external variables probably lead to a collapse of the CE-type antiferromagnetic charge-ordered clusters if these type clusters are distributed within the sample. In addition, Mahendiran et al. have claimed that the charge-orbital ordered domains in the Co-doped $\text{Pr}_{0.5}\text{Ca}_{0.5}\text{MnO}_3$ are smaller than the undoped $\text{Pr}_{0.7}\text{Ca}_{0.3}\text{MnO}_3$, suggesting that the onset temperature of the step transitions in the Co-doped compound is higher than that in the undoped one³. We emphasize that the distribution of short-range COO clusters embedded in the matrix provides a significant clue of our understandings of the steplike transformations in CMR manganites. The ultrasharp PMI-FMM transition induced by the magnetic field at low temperatures is in its origin quite different from the standard IM transition associated with the metamagnetic transition at higher T .

In summary, we have demonstrated the influence of pressure on the steplike lattice deformation of single crystalline bilayered manganite $(\text{La}_{0.4}\text{Pr}_{0.6})_{1.2}\text{Sr}_{1.8}\text{Mn}_2\text{O}_7$. The external perturbations such as the application of pressure and electric current give a substantial suppression on the steplike transition, resulting in a broad change in the magnetostriction. It is a future problem to resolve what role the CO clusters within the PMI phase play in the occurrence of the steplike phenomenon observed.

This work was supported by a Grant-in-Aid for Scientific Research from Japan Society of the Promotion of Science.

* Electronic address: matsukawa@iwate-u.ac.jp

¹ *Colossal Magnetoresistive Oxides*, edited by Y.Tokura (Gordon and Breach, New York, 2000).

² *Nanoscale Phase Separation and Colossal Magnetoresistance*, by E.Dagotto (Springer, 2003).

³ R.Mahendiran, A.Maignan, S.Hebert, C.Martin, M.Hervieu, B.Raveau, J.F.Mitchell, and P.Schiffer, Phys.Rev.Lett.89,286602(2002).

⁴ V.Hardy, A.Maignan, S.Hebert, C.Yaicle, C.Martin, M.Hervieu, M.R.Lees, G.Rowlands, D.Mc K. Paul, and B.Raveau, Phys.Rev.B68,220402(R)(2003).

⁵ L.M.Fisher, A.V.Kalinov, I.F.Voloshin, N.A.Babushkina, D.I.Khomskii, Y.Zhang, and T.T.M.Palstra, Phys.Rev.B70,212411(2004).

⁶ L.Ghivelder, R.S.Freitas, M.G.das Virgens, M.A.Continentino, H.Martinho, L.Granja, M.Quintero, G.Leyva, P.Levy, and F.Parisi, Phys.Rev.B69,214414(2004).

⁷ Sunil Nair, A.K.Nigam, A.V.Narlikar, D.Prabhakaran, A.Boothroyd, Phys.Rev.B74,132407(2006).

⁸ Da-qian Liao, Young Sun, Ren-fu Yang, Qing-an Li, and Zhao-hua Cheng, Phys.Rev.B74,174434(2006).

⁹ Y.Moritomo, Y.Maruyama, T.Akimoto, and A.Nakamura, Phys.Rev.B56,R7057(1997).

¹⁰ M.Apostu, R.Suryanarayanan, A.Revcolevschi, H.Ogasawara, M.Matsukawa, M.Yoshizawa, and N.Kobayashi, Phys.Rev.B64,012407(2001).

¹¹ M.Matsukawa, K.Akasaka, H.Noto, R.Suryanarayanan, S.Nimori, M.Apostu, A.Revcolevschi, and N.Kobayashi,

- Phys.Rev.B72,064412(2005).
- ¹² M.Matsukawa,A.Tamura, S.Nimori, R.Suryanarayanan, T.Kumagai,Y. Nakanishi, M.Apostu, A.Revcolevschi, K. Koyama and N.Kobayashi, Phys.Rev.B75,014427(2007).
- ¹³ M.Matsukawa,Y.Yamato,T.Kumagai,A.Tamura, R.Suryanarayanan, S.Nimori, M.Apostu, A.Revcolevschi, K. Koyama and N.Kobayashi, Phys.Rev.Lett. 98,267204(2007).
- ¹⁴ S.Mercone,A. Wahl,Ch. Simon, and C. Martin, Phys.Rev.B61,15269(2000).
- ¹⁵ L.Vasiliu-Doloc, S. Rosenkranz,R. Osborn, S. K. Sinha,J. W. Lynn,J. Mesot,O. H. Seeck,G. Preosti, A. J. Fedro,and J. F. Mitchell, Phys.Rev.Lett.83,4393(1999).
- ¹⁶ D.N.Argyriou,J.W.Lynn,R.Osborn,B.Campbell, J.F.Mitchell,U.Ruett,H.N.Bordallo,A.Wildes,and C.D.Ling, Phys.Rev.Lett.89,036401(2002).