

Glued CaWO_4 Detectors for the CRESST-II Experiment

Michael Kiefer^{*}, Franz Pröbst, Godehard Angloher, Irina Bavykina, Dieter Hauff, Wolfgang Seidel

Max-Planck-Institut für Physik, München, Germany

Received 6 June 2008; revised 15 September 2008; accepted 29 September 2008

Abstract

The Cryogenic Rare Event Search with Superconducting Thermometers Phase II (CRESST-II) at the L.N.G.S in Italy is searching for Dark Matter using low-temperature calorimeters. These detectors allow to discriminate different particles by simultaneous measurement of phonons and scintillation light. The sensors used consist of superconducting tungsten thin-film thermometers, which measure the thermal effect of the phonons created in an attached absorber crystal. It has been observed that the scintillation of the CaWO_4 absorber degrades during the process of depositing the tungsten film. In order to prevent this, a new technique for producing the detectors was investigated. This technique might also be valuable by expanding the range of scintillator materials suitable for producing a Dark Matter detector.

Key words: Dark Matter, WIMP, Solid-state detectors, Low temperature detectors, Scintillation detectors, CaWO_4 , Epoxy, Glue
PACS: 95.35.+d, 29.40.Wk, 07.20.Mc, 29.40.Mc

1. Dark Matter Search with CRESST-II

1.1. Introduction

Since the observations of Zwicky in the 1930's the nature of Dark Matter remains unknown. Experiments like WMAP [1] could only deliver more evidence on its existence but could not clarify its nature. The weakly interacting massive particle (WIMP) is a well-motivated candidate for Dark Matter [2].

1.2. CRESST-II

The CRESST-II experiment aims for direct detection of WIMPs scattering off nuclei in a scintillating absorber crystal [3]. The target material is chosen in order to optimize the cross section for spin-independent coherent WIMP-nucleus scattering, whose cross section scales quadratically with the atomic mass A .

The energy transferred by a scattering is typically only in the order of 10 keV. This, together with an extremely low interaction rate of less than 10 events per kilogram

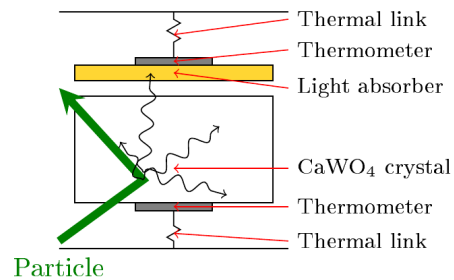


Figure 1. Schematic view of the detector.

of absorber material and year of exposure requires very sensitive detectors, which allow the rejection of background events [2].

In order to reject the background radiation, CRESST-II uses scintillating crystals as target material. A schematic view of the detector can be seen in Figure 1. The energy deposited in a scintillating absorber crystal by a particle interaction excites both phonons and scintillation light. The relative amount of light depends on the nature of the detected particle. As WIMPs, in comparison to highly ionizing particles, cause a relatively low light output, the optimization of detection of the scintillation light is of utmost importance.

The scintillation light is absorbed by a silicon coated sapphire crystal, exciting phonons in the crystal lattice. Each of the two crystals of a detector module, CaWO_4 and sap-

^{*} Corresponding author. Address: Max-Planck-Institut für Physik, Föhringer Ring 6, D-80805 München, Germany. Tel: +49 +89 32354 237, Fax: +49 +89 32354 526

Email address: kiefer@mppmu.mpg.de (Michael Kiefer).

phire, is connected to a superconducting phase transition thermometer for measurement of the phonon signals.

Such a thermometer consists of a thin film of superconducting material (tungsten) which is deposited on the crystal. Phonons are absorbed in the film and increase the temperature of its electron system. The film is thermally stabilized in its phase transition from the superconducting to normal conducting state, therefore its resistance is extremely sensitive to variations in temperature. Phonons that are absorbed in the film increase the temperature of its electron system and thus its resistance. The change in resistance is read out by a sensitive SQUID circuit [3,4,5].

The upcoming EURECA experiment is going to use particle detection and discrimination techniques developed and studied in the CRESST-II experiment [6].

2. Glued Detectors

The idea behind the use of glued detectors is to produce the superconducting phase transition thermometers on small substrates that later on are glued onto the scintillating absorber crystals. This has several advantages:

Light yield: For the evaporation of a tungsten film, the scintillating absorber crystal is heated up. Heat, however, degrades the light output of the scintillator [7], resulting in a decreased particle discrimination capability.

New materials: Other attractive scintillator materials may suffer even more from the W-deposition and etching. Producing the thermometer on a small substrate avoids the exposition of most of the scintillator material to these treatments. In this way, the gluing technique already allowed the use of a ZnWO_4 scintillating absorber crystal in the current run [8].

Mass production: Producing several thermometers at once on a single substrate increases the overall speed of detector production. The substrate can be cut and the thermometers then can be glued onto several absorber crystals. For the upcoming EURECA experiment which aims at increasing the target mass, many more detector modules are needed than the 33 foreseen for CRESST-II.

2.1. Proof-of-principle experiment

For the investigation of glued detectors, a proof-of-principle experiment was performed. This experiment was not shielded from background radiation. In order to cope with the relatively high count rates, a setup smaller than the one used at Gran Sasso was chosen: Instead of a cylindrical crystal of 40 mm height and 40 mm diameter, a cuboid of $20 \times 10 \times 5 \text{ mm}^3$, named C14 was used (see Fig. 2).

The experiment consisted of two parts: First, the whole cuboid CaWO_4 crystal carrying a superconducting phase transition thermometer was exposed to 60 keV-gamma radiation from an ^{241}Am source.

Then, the crystal was cut into two halves, one of them carrying the thermometer. These two halves were glued to-

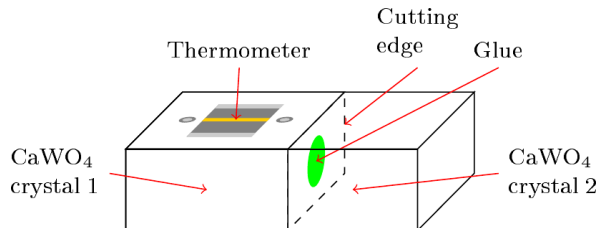


Figure 2. Schematic view of the proof-of-principle experimental setup.

gether with Araldite 2011[®]¹, a two-component epoxy resin. Signals from a 60 keV gamma source were measured, once with the radiation collimated to the half without thermometer and secondly with both halves uniformly irradiated.

2.2. Theoretical model

A theoretical model [9] of the behaviour of a one-crystal-setup with a superconducting phase transition thermometer was extended in order to describe the more complex case of a glued detector.

The detection of phonons works by the following principle: Absorption of radiation in the scintillating absorber crystal creates high-frequency phonons that do not thermalize on the millisecond time scale. The phonons travel through the crystal ballistically before being collected in the thermometer. There, the phonon energy is transferred into the electron system of the superconducting phase transition thermometer, changing its electrical resistance by a measurable amount.

2.2.1. Single absorber crystal

The model makes the following assumptions: The crystal has a volume V_1 and a high-frequency phonon population $N_1(t)$. The transfer of non-thermal phonons into the superconducting phase transition thermometer is described by the transition parameter A_f . The superconducting phase transition thermometer itself has a heat capacity C and is linked with a conductance G_b to a heat bath of constant temperature (see Fig. 3). Neglecting other losses, this means that the phonon population N_1 in the absorber crystal is determined by the deposited energy E , the energy per phonon \mathcal{E} and the rate dN_1/dt at which the phonons flow into the thermometer.

$$\frac{d}{dt}N_1(t) = -A_f \frac{N_1(t)}{V_1}. \quad (1)$$

The phonons enter the thermometer from the absorber crystal and leave through the thermal link. This raises the temperature of the thermometer by an amount of ΔT above its equilibrium temperature:

¹ Araldite is a registered trademark of Huntsman Corporation or an affiliate thereof

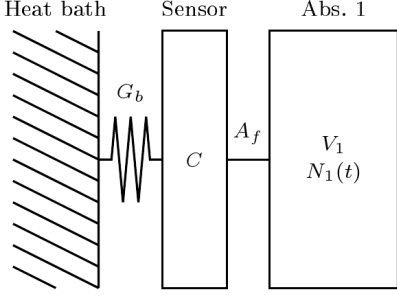


Figure 3. Schematic view of a one-crystal-setup: V_1 , N_1 : Volume and Phonon population in the crystal; A_f : Parameter for transition of phonons between crystal and thermometer; C , G_b : Heat capacity of the thermometer and coupling to the heat bath.

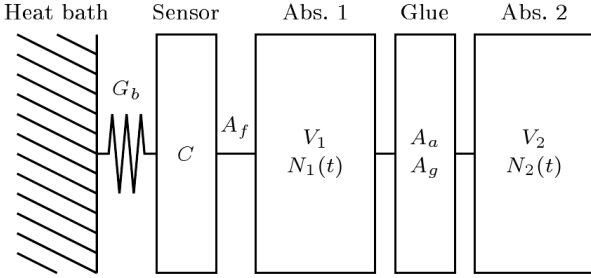


Figure 4. Schematic view of a glued-detector setup: V_x , N_x : Volume and Phonon population in the crystals; A_f , A_g , A_a : Parameter for transition of phonons between absorber crystal 1 and thermometer, transition and absorption through the glue; C , G_b : Heat capacity of the thermometer and coupling to the heat bath.

$$\frac{d}{dt}\Delta T(t)C = -\frac{d}{dt}N_1(t)\mathcal{E} - G_b\Delta T(t) \quad (2)$$

$$= A_f \frac{N_1(t)}{V_1}\mathcal{E} - G_b\Delta T(t) \quad (3)$$

By solving these two differential equations with the initial conditions of $N_1(t=0) = E/\mathcal{E}$ and $\Delta T(t=0) = 0$ one obtains a pulse consisting of two exponentials describing the temperature of the thermometer:

$$\Delta T(t) = \frac{A_f E}{A_f C - G_b V_1} \left(e^{-\frac{G_b}{C}t} - e^{-\frac{A_f}{V_1}t} \right) \quad (4)$$

The quantities G_b/C and A_f/V_1 are considered as the decay time τ_n and the rise time τ_r of the pulse, respectively.

2.2.2. Two absorber crystals

The extension (see Fig. 4) of the model for the glued detector consists of two parts: There is a second absorber crystal which has a volume V_2 and a phonon population $N_2(t)$. It is attached to the first one by a layer of glue. There are possibilities for a phonon in the glue to either pass through or to be absorbed, described by the transition parameter A_g and the absorption parameter A_a . Phonons reflected by the glue do not have to be accounted separately, as they do not affect the balance of the two populations.

Mathematically, this is represented by the following equations:

$$\begin{aligned} \frac{d}{dt}N_1(t) &= -A_f \frac{N_1(t)}{V_1} - A_g \left(\frac{N_1(t)}{V_1} - \frac{N_2(t)}{V_2} \right) \\ &\quad - A_a \frac{N_1(t)}{V_1} \end{aligned} \quad (5)$$

$$\frac{d}{dt}N_2(t) = -A_g \left(\frac{N_2(t)}{V_2} - \frac{N_1(t)}{V_1} \right) - A_a \frac{N_2(t)}{V_2} \quad (6)$$

The left hand side and the first term of the right hand side of Equation (5) are the same as in the one-crystal model (see Equation (1)). Additionally the phonons leaving one crystal and the phonons entering from its counterpart are taken into account by the $A_g(\dots)$ term. The last term treats phonons absorbed by the glue. The second crystal does not carry a thermometer, therefore Equation (6) lacks the term coupling with A_f .

The temperature rise of the thermometer film in the two-crystal case is again described by Equation (3). It makes sense to solve this system of three coupled differential equations for two different cases of initial conditions: If an event is caused by a particle in the first absorber then $N_1(t=0) = E/\mathcal{E}$ and $N_2(t=0) = 0$. Alternatively, if the particle is absorbed in the second crystal then $N_1(t=0) = 0$ and $N_2(t=0) = E/\mathcal{E}$. For both cases, $\Delta T(t=0) = 0$, as in the one-crystal-experiment.

The resulting temperature signals are of the form

$$\begin{aligned} \Delta T(t) &= \\ \alpha_n \left[e^{-\frac{G_b}{C}t} - \left(\frac{\gamma_n}{\phi} \sinh(\phi t) + \cosh(\phi t) \right) e^{-\beta t} \right] \end{aligned} \quad (7)$$

which still has the characteristics of a two-exponential-pulse. The different initial conditions result in different values for the α_n and γ_n . They are, as well as the parameters γ , β and ϕ , functions of the different couplings and volumes:

$$\phi = \frac{\sqrt{([A_f + A_a + A_g]V_2 - [A_a + A_g]V_1)^2 + 4A_g^2V_1V_2}}{2V_1V_2} \quad (8)$$

$$\beta = \frac{(A_f + A_a + A_g)V_2 + (A_a + A_g)V_1}{2V_1V_2} \quad (9)$$

$$\gamma_1 = \frac{(A_f + A_a + A_g)V_2 - (A_a + A_g)V_1}{2V_1V_2} + \frac{A_g^2C}{(G_bV_2 - [A_a + A_g]C)V_1} \quad (10)$$

$$\begin{aligned} \alpha_1 &= A_f E [G_bV_2 - (A_a + A_g)C] \\ &\quad / \{ (G_b^2V_1 - [A_f + A_a + A_g]G_bC)V_2 \\ &\quad + (A_a + A_g)([A_f + A_a] - G_bCV_1) + A_aA_g \} \end{aligned} \quad (11)$$

$$\gamma_2 = \beta - 2\frac{G_b}{C}V_1 \quad (12)$$

$$\begin{aligned} \alpha_2 &= A_f EA_g C \\ &\quad / \{ (G_b^2V_1 - [A_f + A_a + A_g]G_bC)V_2 \\ &\quad + (A_a + A_g)([A_f + A_a] - G_bCV_1) + A_aA_g \} \end{aligned} \quad (13)$$

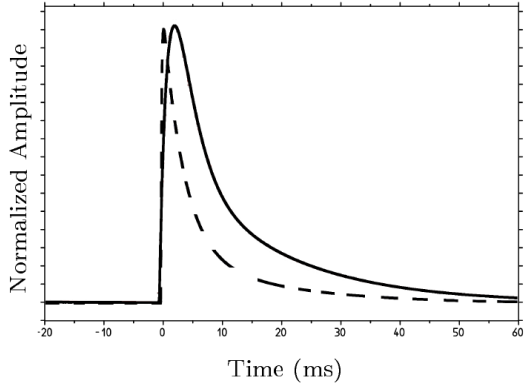


Figure 5. Fit functions for average pulses with fast rise time (dashed), resulting from an event in the thermometer carrier and with slow rise time (normal), resulting from an event in the glued part. Pulse heights are not in scale.

2.3. Results

2.3.1. Pulse shape discrimination

The temperature signal from the thermometer was fitted using the model of the one-crystal-setup (see Equation (4)) for the one-crystal-setup as well as for the glued detector, in order to clean the data from pile-ups. In case of the cut crystal, two distinct classes of pulses (see Fig. 5) have been recorded which differ in rise time by a factor of 10. This is consistent with the results in [10].

Using the information of the collimated and uncollimated measurements, it was possible to attribute the faster pulses to events in the thermometer carrier and the slower pulses to events in the glued part without thermometer.

2.3.2. Spectra

The spectrum which was recorded with the uncut crystal shows two peaks clearly distinguishable from the background, one from the 60 keV-source, the other one corresponding to the escape energy from the tungsten-L-shell at 51 keV (see Fig. 6). Separating the events recorded with the glued detector via their rise times, two spectra from the two absorbers were obtained (see Fig. 7). Both peaks (51 and 60 keV) are still separable in the spectra of the components of the glued detector. The resolution even improved from $\approx 7.5\%$ with the entire crystal to $\approx 5\%$ for each of the halves.

In comparison to the uncut crystal, the threshold for measuring pulses could be reduced due to less noise in the measurement electronics: Therefore the spectrum for the thermometer carrier starts at 5 keV instead of 10 keV. The energy threshold for pulses from the glued-on absorber is increased from 5 keV to 15 keV in comparison to the thermometer carrier. This is due to a calibration effect: Particles of the same energy create lower pulse heights if being absorbed in the glued-on absorber than if being absorbed in the thermometer carrier. Therefore a certain energy band cannot be measured via the glued-on absorber while measurement with the thermometer carrier is still possible.



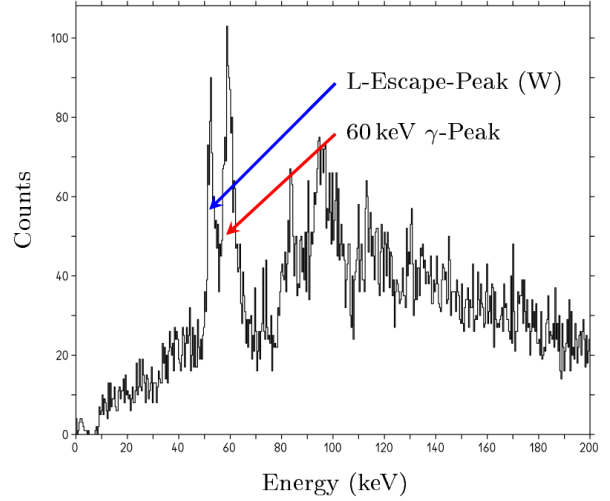


Figure 6. Spectrum taken with the uncut C14 crystal. The resolution is $\approx 7.5\%$ for the 60 keV peak.

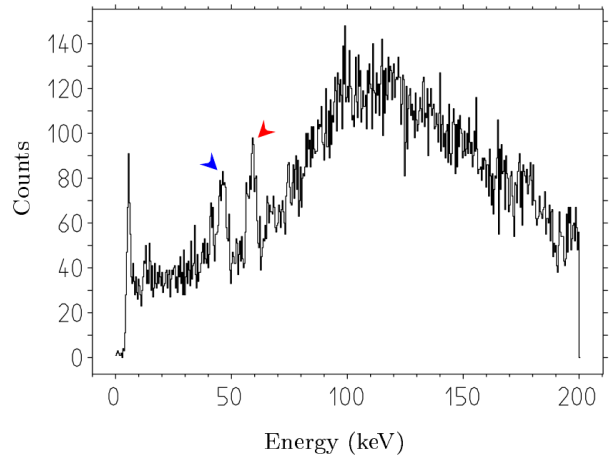

(a) Fast pulses (from thermometer carrier)

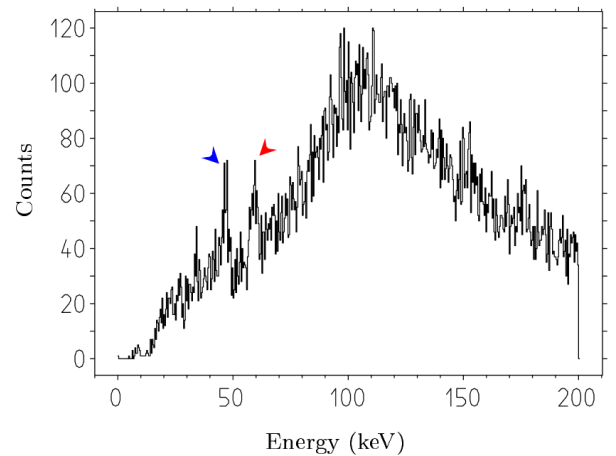

(b) Slow pulses (from glued part)

Figure 7. Comparison of the spectra of pulses originating from the different halves of the crystal. In both crystals, the resolution is $\approx 5\%$ for the 60 keV peak.

A_f	$(5.5772 \pm 0.0093) \cdot 10^{-3} \text{ m}^3 \text{ s}^{-1}$
A_a	$(0.82 \pm 0.34) \cdot 10^{-4} \text{ m}^3 \text{ s}^{-1}$
A_g	$(1.797 \pm 0.090) \cdot 10^{-4} \text{ m}^3 \text{ s}^{-1}$

Table 1
Transition properties of the glue in the proof-of-principle experiment

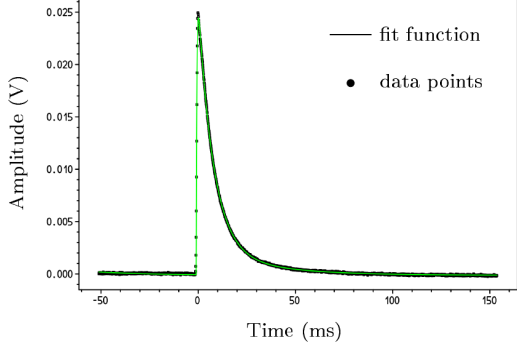


Figure 8. Pulse taken with thermometer carrier WI220. Dots represent data and lines the fitted curves.

2.3.3. Calculation of thermal couplings

The data of a pulse recorded with the one-crystal-setup was fitted to the model of Equation (4). The volume of the crystal was measured and the thermal capacity calculated according to [11] so that the couplings G_b and A_f to the heat bath and the thermometer film could be extracted.

The values of these couplings were assumed to remain unaffected by the cutting of the crystal for the second experiment. Using the parameters obtained from the first experiment, it was possible to fit the pulses of the second experiment with Equation (7) and to extract the couplings A_a and A_g , which are displayed in Table 1.

The amount of phonons that passed through the glue was lower, but still sufficiently high to measure a spectrum. This decrease in phonon signal quality is tolerable in view of an increase of scintillation light.

3. Glued detectors for Gran Sasso

In the present Run 31 of the CRESST-II experiment, three detectors with thermometer carriers and glued-on absorber crystals consisting of CaWO_4 and a fourth glued detector made out of ZnWO_4 are included in the Gran Sasso setup.

3.1. Carrier crystals for Gran Sasso detectors

In order to determine characteristics of the carrier crystals WI220, WI225 and WI228, each of them was used to take a ^{57}Co spectrum before being glued. Figures 8 to 10 show examples of pulses taken with the carrier crystals. Fitting the pulses of the three detectors to the model of Equation (4) resulted in the characteristics shown in Table 2.

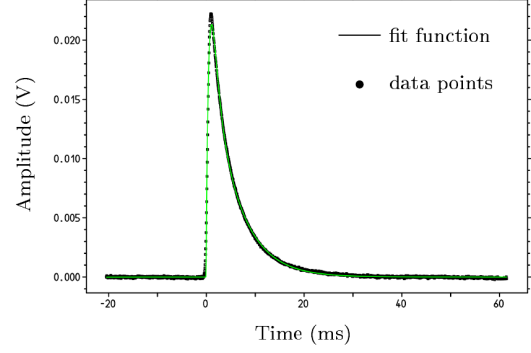


Figure 9. Pulse taken with thermometer carrier WI225. Dots represent data and lines the fitted curves.

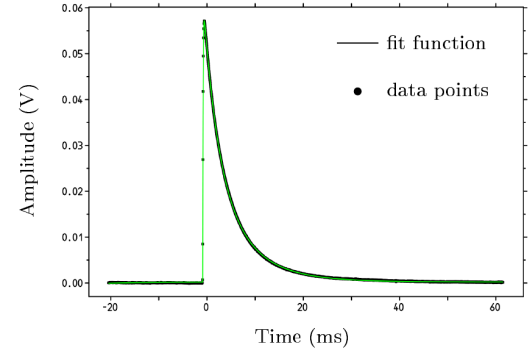


Figure 10. Pulse taken with thermometer carrier WI228. Dots represent data and lines the fitted curves.

	WI220	WI225	WI228
τ_r	$0.3741 \pm 0.0011 \text{ ms}$	$0.7222 \pm 0.0012 \text{ ms}$	$0.0803 \pm 0.0011 \text{ ms}$
τ_n	$7.716 \pm 0.016 \text{ ms}$	$0.8679 \pm 0.0018 \text{ ms}$	$3.1602 \pm 0.0044 \text{ ms}$

Table 2
Characteristics (see Equation (4)) of the pulses measured with the thermometer carrier before gluing.

3.2. Gluing

Following the reference measurement, the thermometer carriers have been glued to cylindrical absorber crystals of 40 mm diameter and height. The masses of the crystals are $\approx 310 \text{ g}$ for CaWO_4 and $\approx 400 \text{ g}$ for ZnWO_4 , respectively.

Two different glues have been used: One detector was glued with Araldite 2011, two others with Epo-Tek 301-2[®]. Both glues have been tested at MPI and it has been observed that Araldite 2011 is itself a scintillator under UV light [12], while Epo-Tek has a lower viscosity. The denser Araldite had to be spread between the two crystals by using a mechanical press while Epo-Tek spreads itself by the weight of the thermometer carrier.

These glued detectors have been installed in the Gran Sasso setup for Run 31 and are currently in use.

² Epo-Tek is a registered trademark of Epoxy Technology, Inc.

4. Conclusion

Detectors with glued thermometers have proven to operate in a stable manner and to deliver pulses which can be used to measure a spectrum. They bring many advantages in terms of fabrication of the detectors without significantly degrading the energy spectrum.

Nevertheless there is a loss of signal quality in the phonon channel. In the case of CRESST, this loss can be accepted, as the increase in scintillation light is expected to improve the discrimination capabilities.

Gluing thermometers onto scintillator crystals may provide a possibility to use scintillator materials which up to now have not been suitable for experiments like CRESST because of difficulties in depositing a thermometer. This might enlarge the choice of scintillating absorber materials for CRESST and the upcoming EURECA experiment.

5. Acknowledgements

I would like to thank the CRESST-group of the Technische Universität München for providing a sample of EpoTek glue.

References

- [1] D. N. Spergel, et al., arXiv (2006) .
URL <http://arxiv.org/abs/astro-ph/0603449v1>
- [2] G. Jungman, M. Kamionkowski, K. Griest, Physics Reports 267 (1996) 195.
- [3] G. Angloher, et al., Astroparticle Physics 23 (2005) 325.
- [4] A. C. S. M. Bento, Aspects of the performance of low temperature calorimeters for x-ray spectroscopy with high definition efficiency, Ph.D. thesis, Lincoln College, Oxford (2004).
- [5] R. F. Lang, arXiv (2008) .
URL <http://arxiv.org/abs/0805.4705>
- [6] H. Kraus, et al., in: J. Phys.: Conf., No. 39, 2006, pp. 139–141.
- [7] J. Ninkovic, et al., Nucl. Instr. and Meth. A 537 (1-2) (2005) 339–343.
- [8] I. Bavykina, et al., these proceedings.
- [9] F. Pröbst, et al., J. of Low Temp. Phys. 100 (1-2) (1995) 69–104.
- [10] J. C. Lanfranchi, et al., Nucl. Instr. and Meth. A (520) (2004) 135–137.
- [11] M. Tinkham, Introduction to Superconductivity, 2nd Edition, McGraw-Hill, 1996.
- [12] K. Schöffner, Private communication (2008).