

Spin Fluctuations and Unconventional Superconductivity in the Fe-based Oxypnictide Superconductor LaFeAsO_{0.7} probed by ⁵⁷Fe-NMR

Nobuyuki Terasaki¹, Hidekazu Mukuda^{1*}, Mitsuharu Yashima¹, Yoshio Kitaoka¹,
Kiichi Miyazawa², Parasharam Shirage², Hijiri Kito², Hiroshi Eisaki², Akira Iyo²

¹Graduate School of Engineering Science, Osaka University, Toyonaka, Osaka 560-8531

²National Institute of Advanced Industrial Science and Technology (AIST), Umezono, Tsukuba 305-8568

We report ⁵⁷Fe-NMR studies on the oxygen-deficient iron (Fe)-based oxypnictide superconductor LaFeAsO_{0.7} ($T_c = 28$ K) enriched by ⁵⁷Fe isotope. In the superconducting state, the spin component of ⁵⁷Fe-Knight shift ^{57}K decreases almost to zero at low temperatures and the nuclear spin-lattice relaxation rate $^{57}(1/T_1)$ exhibits a T^3 -like dependence without the coherence peak just below T_c , which give firm evidence of the unconventional superconducting state formed by spin-singlet Cooper pairing. All these events below T_c are consistently argued in terms of the extended s_{\pm} -wave pairing with a sign reversal of the order parameter among Fermi surfaces. In the normal state, we found the remarkable decrease of $1/T_1T$ upon cooling for both the Fe and As sites, which originates from the decrease of low-energy spectral weight of spin fluctuations over whole \mathbf{q} space upon cooling below room temperature. Such behavior has never been observed for other strongly correlated superconductors where an antiferromagnetic interaction plays a vital role in mediating the Cooper pairing.

KEYWORDS: superconductivity, iron-based oxypnictide, LaFeAsO, NMR

After the discovery of iron (Fe)-based layered oxypnictide superconductor LaFeAs(O_{1-x}F_x),¹ the replacement of La site by other rare earth elements significantly enhances a superconducting transition temperature T_c up to more than 50 K.²⁻⁴ A new route has opened up to deepen understanding of high- T_c superconductivity (SC) phenomena. Mother material LaFeAsO is a semimetal with a stripe antiferromagnetic (AFM) order with $\mathbf{Q} = (0, \pi)$ or $(\pi, 0)$. The crystal structure contains alternate stacking of LaO and FeAs layers along the c -axis. In this structure, the Fe atoms of the FeAs layer are located in a four-fold coordination forming a FeAs₄-tetrahedron. Substitution of oxygen site with fluorine atoms and/or oxygen deficiency at LaO layer causes an exotic SC with a highest T_c besides copper-oxides superconductors.¹⁻⁴ Remarkably, Lee et al. have found that T_c increases up to a highest value of $T_c=54$ K when FeAs₄ tetrahedron is transformed toward a regular one.⁵ Relevant with this fact, we reported that the nuclear quadrupole frequency at the As site relates to T_c for various FeAs-based oxypnictide superconductors, unraveling that T_c is sensitive to the local configuration of FeAs₄ tetrahedron.⁶ The present experimental facts suggest that systematic understanding of local electronic state at the Fe site is quite important to elucidate the origin of SC in the iron-based compounds.

In this letter, we report ⁵⁷Fe-NMR studies on the superconducting and normal-state properties of LaFeAsO_{0.7} with $T_c = 28$ K enriched by ⁵⁷Fe isotope. It is reinforced that the ⁵⁷Fe-NMR- $(1/T_1)$ exhibits a T^3 -like dependence without the coherence peak just below T_c and the spin component of ⁵⁷Fe-Knight shift decreases almost to zero at low temperatures. These results pointing to the unconventional SC with spin-singlet Cooper

pairings are consistent with the theoretical model which proposes that an extended s_{\pm} -wave pairing realizes with a sign reversal of the order parameter among Fermi surfaces. In the normal state, we discuss the characteristics of spin fluctuations in this compound by comparing ⁵⁷Fe- $(1/T_1)$ with the ⁷⁵As- $(1/T_1)$.

The polycrystalline sample of ⁵⁷Fe-enriched LaFeAsO_{0.7} was synthesized via the high-pressure synthesis technique, as described in the elsewhere.³ In particular, starting materials of LaAs, ⁵⁷Fe, ⁵⁷Fe₂O₃ enriched by the ⁵⁷Fe isotope (⁵⁷Fe : nuclear spin $I = 1/2$, $^{57}\gamma_n/2\pi = 1.3757$ MHz/T) were mixed with nominal composition of LaFeAsO_{0.7}. The powder X-ray diffraction measurement indicates that the sample composes of almost a single phase. The superconducting transition temperature T_c was determined to be 28 K by distinct decrease in the dc susceptibility due to the onset of SC diamagnetism. Although the real content of oxygen is unclear, the lattice parameters $a = 4.0226\text{\AA}$ and $c = 8.7065\text{\AA}$ are almost the same as the LaFeAsO_{0.6} with $T_c=28$ K in the previous work,⁶ which indicates that both samples are compatible in their physical properties. The ⁵⁷Fe-NMR measurements were performed in the moderately crushed powder sample, which was oriented along the direction including the ab plane.

Figure 1(a) shows ⁵⁷Fe-NMR spectra obtained by sweeping frequency (f) at magnetic field $H = 11.97$ T at 30 K. When the field is applied parallel to the orientation direction, we observed a single peak, the linewidth of which is as narrow as ~ 20 kHz at 11.97 T, demonstrating that the FeAs layers of this sample are homogeneous irrespective of the oxygen deficiency in the LaO layer. In the field perpendicular to the orientation direction, two horn peaks are observed, which arises from crystals with $\theta = 90^\circ$ and 0° , where θ is the angle between field and

*E-mail address: mukuda@mp.es.osaka-u.ac.jp

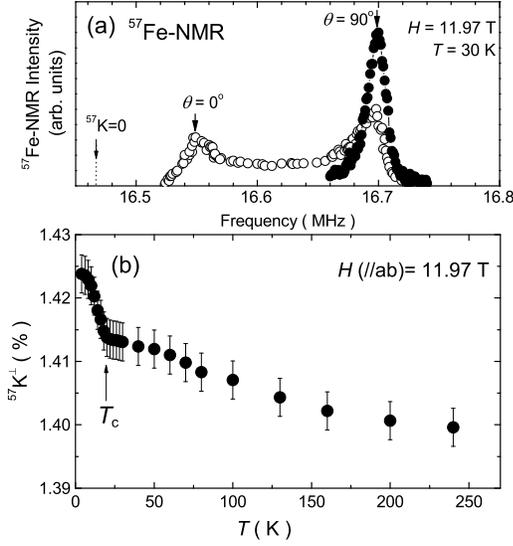


Fig. 1. (a) ^{57}Fe -NMR spectra at $H=11.97$ T and 30 K for $\text{LaFeAsO}_{0.7}$ in the field parallel(\bullet) and perpendicular(\circ) to the orientation direction. (b) The T dependence of $^{57}K^\perp$ at $H=11.97$ T ($T_c(H) \sim 20$ K). It is noteworthy that the T -dependence of $^{57}K^\perp$ is opposite to those of ^{75}As and ^{19}F sites,^{9,11,12} indicating that the hyperfine-coupling constant is negative at Fe site, originating from the inner core-polarization.

c -axis of the crystal. Knight shifts of ^{57}Fe , that is determined by the shift from $f_0 = ^{57}\gamma_n H$ ($^{57}K = 0$), are $^{57}K^\perp \sim 1.413\%$ and $^{57}K^\parallel \sim 0.50\%$ at 30 K for $\theta = 90^\circ$ and 0° , respectively.

The Knight shift comprises generally of the T -independent orbital contribution and T -dependent spin contribution, denoted as $^{57}K_{\text{orb}}$ and $^{57}K_s$, respectively. Here, $^{57}K = ^{57}K_{\text{orb}} + ^{57}K_s$ with $^{57}K_s = ^{57}A_{\text{hf}}^\perp \chi_s$, where $^{57}A_{\text{hf}}^\perp$ is the hyperfine coupling constant and χ_s is the uniform spin susceptibility. Figure 1(b) shows the T dependence of $^{57}K^\perp$ in the field parallel to the ab -plane. It is noteworthy that the T dependence of $^{57}K^\perp$ is opposite to those of ^{75}As and ^{19}F sites,^{9,11,12} indicating that $^{57}A_{\text{hf}}^\perp$ is negative at Fe site, originating from the inner core-polarization. In this compound, $^{57}A_{\text{hf}}^\perp$ at the Fe site is given by $A + 4B$, where A is the on-site negative term dominated by the inner core-polarization, and B is the transferred positive one from the neighbour Fe site through the direct Fe-Fe and/or the indirect Fe-As-Fe bondings. Here, the B composes of B_1 and B_2 derived from the first and second nearest neighbour Fe sites, respectively. In contrast, the $^{75}A_{\text{hf}}^\perp$ at the As site is given by $4C$, where C is the positive term derived from the transferred field(C_{tr}) and diagonal pseudo-dipole field(C_{dip}) induced by one neighboring Fe site. Note that C is deduced to be ~ 6.2 kOe/ μ_B .⁹ Figure 2(a) shows $^{57}K^\perp(T)$ plotted against those of ^{75}As and ^{19}F sites reported by Imai *et al.*,¹² as the T implicit parameter. Their slopes indicate a ratio of hyperfine coupling constants, $^{57}A_{\text{hf}}^\perp / ^{75}A_{\text{hf}}^\perp \simeq -0.38$ and $^{57}A_{\text{hf}}^\perp / ^{19}A_{\text{hf}}^\perp \simeq -4.2$ for $\mathbf{q} = 0$ component. Assuming $A \sim -139$ kOe/ μ_B that is known as the theoretical value of core polariza-

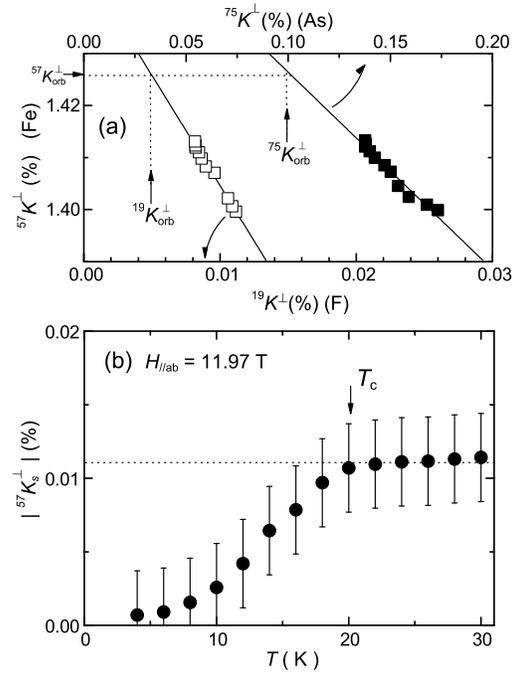


Fig. 2. (a) $^{57}K^\perp(\text{Fe})$ plotted against $^{75}K^\perp(\text{As})$ and $^{19}K^\perp(\text{F})$ reported by Imai *et al.*,¹² the slopes of which gives the ratio of $^{57}A_{\text{hf}}^\perp / ^{75}A_{\text{hf}}^\perp \simeq -0.38$ and $^{57}A_{\text{hf}}^\perp / ^{19}A_{\text{hf}}^\perp \simeq -4.2$. $^{57}K_{\text{orb}}^\perp \sim 1.425\%$ is deduced using the orbital shift of ^{19}F and ^{75}As sites.¹² (b) $|^{57}K_s^\perp|$ evaluated from $|^{57}K^\perp - ^{57}K_{\text{orb}}^\perp|$ decreases to zero in the SC state, which gives firm evidence for spin-singlet Cooper pairing state.

tion field for Fe^{2+} ion,⁷) $B \sim 32.4$ kOe/ μ_B is deduced from $^{57}A_{\text{hf}}^\perp / ^{75}A_{\text{hf}}^\perp = (A + 4B) / (4C) = -0.38$. As shown in Fig. 2(a), $^{57}K_{\text{orb}}^\perp$ was estimated to be 1.425% by assuming the orbital shifts of ^{19}F and ^{75}As sites,¹² which enables us to evaluate $|^{57}K_s^\perp|$ by $|^{57}K^\perp - ^{57}K_{\text{orb}}^\perp|$. Remarkably, the $|^{57}K_s^\perp|$ decreases to almost zero well below T_c , as shown in Fig. 2(b), suggesting possible existence of an isotropic gap in very low temperature regime. This result gives firm evidence of spin-singlet Cooper pairing through the first ^{57}Fe -Knight shift measurement.

The nuclear spin-lattice relaxation rate $^{57}(1/T_1)$ of ^{57}Fe was determined from the recovery curve of ^{57}Fe nuclear magnetization, which is expressed by a simple exponential function as $m(t) \equiv (M(\infty) - M(t)) / M(\infty) = \exp(-t/T_1)$. Here $M(\infty)$ and $M(t)$ are the respective nuclear magnetizations for the thermal equilibrium condition and at a time t after the saturation pulse. Note that $^{57}T_1$ was uniquely determined from a single exponential function of $m(t)$ in the whole T range, suggesting that the normal-state properties are homogeneous and the presence of vortex cores in the SC mixed state under H does not prevent from probing quasiparticle excitations inherent to the novel SC state in $\text{LaFeAsO}_{0.7}$. We measured the $^{57}(1/T_1)$ in the field along the ab -plane, since it was the same with that along the c -axis at 30K.

Figure 3 shows the T dependences of $^{57}(1/T_1)$ at $H = 6.309$ T and 11.97 T in the T range of 4~80 K and 30~240 K, respectively. In the SC state, the ^{57}Fe -NMR

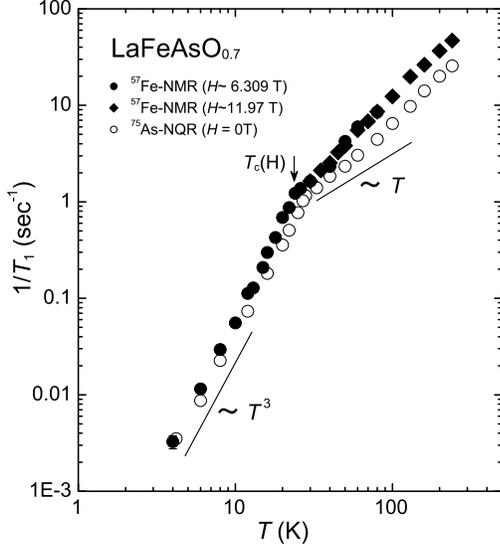


Fig. 3. T dependence of ^{57}Fe -NMR $1/T_1$ at $H = 6.309\text{ T}$ and $H = 11.97\text{ T}$, along with the ^{75}As -NQR $1/T_1$ for $\text{LaFeAsO}_{0.6}$ ($T_c = 28\text{ K}$).⁶⁾ In the SC state, ^{57}Fe - $1/T_1$ follows a T^3 -like dependence upon cooling without the coherence peak just below $T_c(H) = 24\text{ K}$, which resembles the result by ^{75}As -NQR.

$(1/T_1)$ exhibits a T^3 -like dependence without the coherence peak just below $T_c(H) = 24\text{ K}$ at $H = 6.309\text{ T}$, which resembles the previous ^{75}As -NQR $(1/T_1)$ in $\text{LaFeAsO}_{0.6}$.⁶⁾ It is noteworthy that the residual density of states (RDOS) well below T_c was not observed at the Fermi level even for $T/T_c = 0.17$, although RDOS used to be observed in the unconventional superconductors with the line-node gap, easily induced by impurity scatterings especially in a unitarity limit. These features of $1/T_1$ were commonly reported among other Fe-based superconductors.^{6, 8–10)} In contrast, a fully gapped SC state was revealed by the experiments such as ARPES¹³⁾ and magnetic penetration depth.¹⁴⁾ In order to reconcile these issues, the theoretical groups have carried out the calculation of $1/T_1$ on the basis of a nodeless extended s_{\pm} -wave pairing model with a sign reversal of the order parameter between the hole and electron Fermi surfaces.^{15, 16)} In the framework of either a two-band model where the unitarity scattering due to impurities is assumed¹⁷⁾ or a five-band model in a rather clean limit,¹⁸⁾ the experiments are well reproduced by such the calculations. As a matter of fact, the results of $(1/T_1)$ s for ^{57}Fe and ^{75}As in the SC state are consistent with the latter model. This may be because the intrinsic behavior of $1/T_1$ is measured on the highly homogeneous sample, that is guaranteed by the very sharp NMR linewidth with as small as 20 kHz even at 12 T. In this context, our results is consistently argued in terms of the extended s_{\pm} -wave pairing with a sign reversal of the order parameter among Fermi surfaces.

Next we deal with the normal-state properties probed by the $(1/T_1)$ s of both ^{57}Fe and ^{75}As . As shown in Fig. 4, $^{57}(1/T_1 T)$ in the normal state gradually decreases upon cooling down to T_c , resembling that of $^{75}(1/T_1 T)$

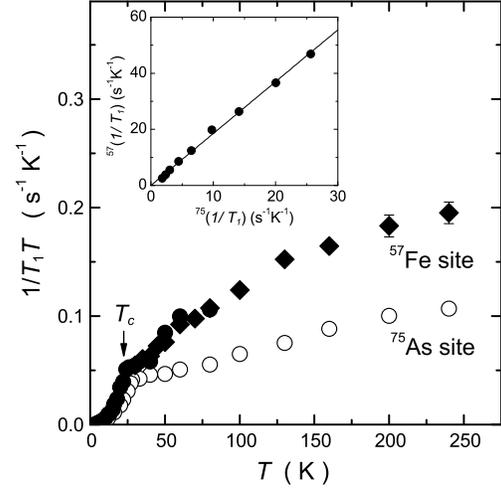


Fig. 4. T dependence of ^{57}Fe - $1/T_1 T$ at $H = 6.309\text{ T}$ (\bullet) and $H = 11.97\text{ T}$ (closed diamond), together with the ^{75}As - $1/T_1 T$ in $\text{LaFeAsO}_{0.6}$ (\circ).⁶⁾ The inset shows the plot of $^{57}(1/T_1 T)$ vs $^{75}(1/T_1 T)$ as the implicit parameter of T between 30 K and 240 K.

at As site. Actually, $^{57}(1/T_1 T)$ at Fe site is well scaled to $^{75}(1/T_1 T)$ at As site⁶⁾ down to 60 K with a ratio of $^{57}(1/T_1 T)/^{75}(1/T_1 T) \simeq 1.85$, as shown in the inset, whereas it deviates slightly from this linear relation in the range of $T = 30\text{ K} - 60\text{ K}$. The respective $1/T_1$ s of ^{57}Fe and ^{75}As are expressed as,

$$^{57,75} \left(\frac{1}{T_1} \right) \sim \sum_{\mathbf{q}} (^{57,75} \gamma_n)^2 |^{57,75} A_{\text{hf}}(\mathbf{q})|^2 \frac{\chi''(\mathbf{q}, \omega_0)}{\omega_0}, \quad (1)$$

$$\begin{aligned} ^{57} A_{\text{hf}}(\mathbf{q}) &= A + 2B_1 [\cos(q_x a) + \cos(q_y a)] \\ &\quad + 4B_2 [\cos(q_x a) \cos(q_y a)], \\ ^{75} A_{\text{hf}}(\mathbf{q}) &= 4C_{\text{tr}} [\cos(q_x a/2) \cos(q_y a/2)] + 4C_{\text{dip}}^{\perp}(\mathbf{q}), \end{aligned} \quad (2)$$

where $A_{\text{hf}}(\mathbf{q})$ is the wave-vector (\mathbf{q})-dependent hyperfine coupling constant, $\chi''(\mathbf{q}, \omega_0)$ is the imaginary part of the dynamical spin susceptibility, a is a distance between Fe atoms, and ω_0 is the NMR/NQR frequency. An anisotropy of $^{57}(1/T_1)$ between the ab -plane and the c -axis is negligibly small for Fe site, which ensures that $\chi''(\mathbf{q}, \omega_0)$ and the hyperfine fields (A and B) are isotropic. Although the anisotropy of $^{75}(1/T_1)$ was observed in other ^{57}As -NMR measurement,⁹⁾ it is predominantly derived from the anisotropy of $C_{\text{dip}}^{\perp}(\mathbf{q})$, which is the inplane component of off-diagonal pseudo-dipole hyperfine field arising from the $\chi''(\mathbf{q}, \omega_0)$ along the c -axis.

Now let us consider three simple cases on the basis of the possible evaluation of hyperfine field. (i) First, we assume a case that spin fluctuations only around $\mathbf{q} = 0$ are predominant. In this case, we would expect a ratio of $^{57}(1/T_1 T)/^{75}(1/T_1 T) \sim 0.005$ by using $(^{57} A_{\text{hf}}^{\perp}/^{75} A_{\text{hf}}^{\perp})^2 = (-0.38)^2$. However, it is three orders of magnitude smaller than the experimental value of 1.85 at $T = 60 \sim 250\text{ K}$, suggesting that the ferromagnetic spin-fluctuation modes around $\mathbf{q} = 0$ are

not predominant in this compound. (ii) Second, we assume the case that the spin fluctuations only around $\mathbf{Q} = (0, \pi/a)$ or $(\pi/a, 0)$ are predominant. It is characteristic that the $|^{57}A_{\text{hf}}(\mathbf{q})|$ at the Fe site becomes large around the boundaries of the first Brillouin zone. For example, $|^{57}A_{\text{hf}}(0, \pi/a)| = |A - 4B_2|$ is roughly evaluated to be $\sim 204 \text{ kOe}/\mu_B$ if B_1 and B_2 were comparable, which are one order of magnitude larger than that of As site. Even though the off-diagonal term $4C_{\text{dip}}^{\perp}(\mathbf{q})$ in eq.(2) is not clear for the paramagnetic state of $\text{LaFeAsO}_{0.7}$, it is tentatively assumed to be $4.3 \text{ kOe}/\mu_B$ obtained for the stripe AFM ordered phase in the orthorhombic BaFe_2As_2 .¹⁹⁾ Then we obtain $^{57}(1/T_1T)^{75}(1/T_1T) \sim 5$, which is the same order of magnitude to the experimental value. (iii) Third, we assume the case that the spin fluctuations only around $\mathbf{Q} = (\pi/a, \pi/a)$ are predominant. In this case, $|^{57}A_{\text{hf}}(\pi/a, \pi/a)|$ becomes largest, whereas $|^{75}A_{\text{hf}}^{\perp}(\pi/a, \pi/a)|$ is expected to be zero. Thus $^{57}(1/T_1T)^{75}(1/T_1T)$ would be the extremely large value, which is inconsistent with the experiment.

Thus far it has been theoretically proposed that the multiple spin-fluctuation modes with $\mathbf{Q} = (\pi/a, 0)$ and $(0, \pi/a)$ arising from the nesting across the disconnected Fermi surfaces would mediate the extended s_{\pm} -wave pairing with a sign reversal of the order parameter.¹⁶⁾ However, in our simple analyses, we could state only that the spin fluctuations at finite wave vectors is more significant than the ferromagnetic spin fluctuations mode in this compound. Nevertheless, it is noteworthy that the $(1/T_1T)$ s for both the Fe and As sites decrease upon cooling, indicating the decrease of low-energy spectral weight of spin fluctuations over whole \mathbf{q} space from the room temperature. In contrast, in the case of the copper-oxide superconductors, $1/T_1T$ s of ^{63}Cu and ^{17}O exhibit a different T dependence, due to the difference in the q -dependence of $^{63,17}A_{\text{hf}}(\mathbf{q})$ and strong AFM spin fluctuations with $\mathbf{Q} = (\pi/a, \pi/a)$.²⁰⁾ The suppression of spin fluctuations over whole \mathbf{q} space upon cooling below room temperature was observed in FeAs-derived high T_c superconductor, which has never been observed for other strongly correlated superconductors where an AFM interaction plays vital role in mediating the Cooper pairing. In this context, it is an open question at the present what type of fluctuations are responsible for a pairing glue taking place a possible extended s_{\pm} -wave pairing.

In summary, the first ^{57}Fe -NMR studies have unraveled the novel SC and normal-state characteristics for the ^{57}Fe -enriched $\text{LaFeAsO}_{0.7}$ with $T_c = 28 \text{ K}$. The measurements of the Knight shift and the T_1 of ^{57}Fe have revealed that the extended s_{\pm} -wave pairing with a sign reversal of the order parameter can be a promising candidate in $\text{LaFeAsO}_{0.7}$ with $T_c = 28 \text{ K}$. This novel SC is theoretically proposed to be realized by the multiple spin-fluctuation modes with $\mathbf{Q} = (\pi/a, 0)$ and $(0, \pi/a)$ arising from the nesting across the disconnected Fermi surfaces. However, in the normal state, we found the remarkable decrease of $1/T_1T$ upon cooling for both the Fe and As sites, indicating the decrease of low-energy spectral weight of spin fluctuations over whole \mathbf{q} space upon cooling below room temperature, which has never

been observed for other strongly correlated superconductors where an AFM interaction plays vital role in mediating the Cooper pairing. Further experiments on T_c -dependences of $1/T_1$ and K at both Fe and As sites by using a single crystal are required to understand the nature of spin fluctuations of this compound.

This work was supported by Grant-in-Aid for Specially promoted Research (20001004) and in part by Global COE Program (Core Research and Engineering of Advanced Materials-Interdisciplinary Education Center for Materials Science), from the Ministry of Education, Culture, Sports, Science and Technology (MEXT), Japan.

- 1) Y. Kamihara, T. Watanabe, M. Hirano, and H. Hosono: J. Am. Chem. Soc. **130** (2008) 3296.
- 2) Z. A. Ren, W. Lu, J. Yang, W. Yi, X. L. Shen, Z. C. Li, G. C. Che, X. L. Dong, L. L. Sun, F. Zhou, and Z. X. Zhao: Chin. Phys. Lett. **25** (2008) 2215.
- 3) H. Kito, H. Eisaki, and A. Iyo: J. Phys. Soc. Jpn. **77** (2008) 063707.
- 4) Z. A. Ren, G. C. Che, X. L. Dong, J. Yang, W. Lu, W. Yi, X. L. Shen, Z. C. Li, L. L. Sun, F. Zhou, and Z. X. Zhao: Europhys. Lett. **83** (2008) 17002.
- 5) C. H. Lee, H. Eisaki, H. Kito, M. T. Fernandez-Diaz, T. Ito, K. Kihou, H. Matsushita, M. Braden, and K. Yamada: J. Phys. Soc. Jpn. **77** (2008) 083704.
- 6) H. Mukuda, N. Terasaki, H. Kinouchi, M. Yashima, Y. Kitaoka, S. Suzuki, S. Miyasaka, S. Tajima, K. Miyazawa, P. M. Shirage, H. Kito, H. Eisaki, and A. Iyo: J. Phys. Soc. Jpn. **77** (2008) 093704.
- 7) A.J.Freeman and R.E. Watson, in *Hyperfine Interactions in Magnetic Materials, Magnetism IIA*, edited by G.T. Rado and S. Suhl Academic, New York, 1965.
- 8) Y. Nakai, K. Ishida, Y. Kamihara, M. Hirano, and H. Hosono: J. Phys. Soc. Jpn. **77** (2008) 073701.
- 9) H.-J. Grafe, D. Paar, G. Lang, N. J. Curro, G. Behr, J. Werner, J. Hamann-Berrero, C. Hess, N. Leps, R. Klingeler, and B. Büchner: Phys. Rev. Lett. **101** (2008) 047003.
- 10) K. Matano, Z. A. Ren, X. L. Dong, L. L. Sun, Z. X. Zhao, and G.-q. Zheng: Europhys. Lett. **83** (2008) 57001.
- 11) K. Ahilan, F. L. Ning, T. Imai, A. S. Sefat, R. Jin, M. A. McGuire, B. C. Sales, and D. Mandrus: Phys. Rev. B **78** (2008) 100501(R).
- 12) T. Imai, K. Ahilan, F.L. Ning, M. A. McGuire, A. S. Sefat, R. Jin, B. C. Sales, D. Mandrus, J. Phys. Soc. Jpn. Suppl.(in press)
- 13) H. Ding, P. Richard, K. Nakayama, K. Sugawara, T. Arakane, Y. Sekiba, A. Takayama, S. Souma, T. Sato, T. Takahashi, Z. Wang, X. Dai, Z. Fang, G. F. Chen, J. L. Luo and N. L. Wang: Europhys. Lett. **83** (2008) 47001.
- 14) K. Hashimoto, T. Shibauchi, T. Kato, K. Ikada, R. Okazaki, H. Shishido, M. Ishikado, H. Kito, A. Iyo, H. Eisaki, S. Shamoto, and Y. Matsuda: arXiv:0806.3149.
- 15) I.I. Mazin, D. J. Singh, M. D. Johannes, and M. H. Du: Phys. Rev. Lett. **101** (2008) 057003.
- 16) K. Kuroki, S. Onari, R. Arita, H. Usui, Y. Tanaka, H. Kontani, and H. Aoki: Phys. Rev. Lett. **101** (2008) 087004.
- 17) A. V. Chubukov, D. Efremov, and I. Eremin: Phys. Rev. B **78** (2008) 134512; D. Parker, O.V. Dolgov, M.M. Korshunov, A.A. Golubov, and I.I. Mazin: Phys. Rev. B **78** (2008) 134524 ; Y. Bang, H.-Y. Choi: Phys. Rev. B **78** (2008) 134523; M. M. Parish, J. Hu, and B. A. Bernevig:arXiv:0807.4572.
- 18) Y. Nagai, N. Hayashi, N. Nakai, H. Nakamura, M. Okumura, and M. Machida: arXiv:0809.1197.
- 19) K. Kitagawa, N. Katayama, K. Ohgushi, M. Yoshida, and M. Takigawa: to be published in J. Phys. Soc. Jpn.
- 20) M. Takigawa, A. P. Reyes, P. C. Hammel, J. D. Thompson, R. H. Heffner, Z. Fisk, and K. C. Ott: Phys. Rev. B **43** (1991) 247.