Letter

Novel critical exponent of magnetization curves near the ferromagnetic quantum phase transitions of $Sr_{1-x}A_xRuO_3$ (A = Ca, La_{0.5}Na_{0.5}, and La)

YUTAKA ITOH*, TAKAO MIZOGUCHI and KAZUYOSHI YOSHIMURA

Department of Chemistry, Graduate School of Science, Kyoto University, Kyoto 606-8502

We report a novel critical exponent $\delta \approx 3/2$ of magnetization curves $M = H^{1/\delta}$ near the ferromagnetic quantum phase transitions of $\mathrm{Sr}_{1-x}\mathrm{A}_x\mathrm{RuO}_3$ (A = Ca, La_{0.5}Na_{0.5}, and La), which the mean field theory of the Ginzburg-Landau-Wilson type fails to reproduce. The effect of dirty ferromagnetic spin fluctuations might be a key.

KEYWORDS: SrRuO₃, ferromagnetic spin fluctuation, quantum critical point, NMR

Itinerant ferromagnetism has been long studied in physics. Modern spin fluctuation theory¹ and the concept of quantum critical point^{2, 3} have developed our understanding the metallic magnetism. However, further ingredients e.g. local criticality, quantum protectorate, and hidden criticality are now required to understand actual experimental results within the present theoretical framework.⁴ The itinerant ferromagnetism has still provided us challenging problems.

SrRuO₃ is a perovskite structure with slightly orthorhombic distortion and an itinerant ferromagnet with the Curie temperature $T_{\rm C} = 160 \text{ K}$.⁵ Ca substitution for Sr ions decreases $T_{\rm C}$ and changes the ferromagnetic state into a paramagnetic one at $x \sim 0.7$ in Sr_{1-x}Ca_xRuO₃.⁶⁻⁹ Although a ferromagnetic-to-antiferromagnetic transition had been thought to occur at $x \sim 0.7$ because of the sign change in the Weiss temperature of Curie-Weiss spin susceptibility, it turned out that CaRuO₃ is a nearly ferromagnetic metal and then the $x \sim 0.7$ transition is a ferromagnetic quantum phase transition.⁸ The Ru⁴⁺ (4d⁴) t_{2g} -band filling should be invariant with the Ca²⁺ substitution for Sr²⁺, so that the chemical pressure may change the band width and then the electron correlation.

La_{0.5}Na_{0.5} and single La ions are known to substitute for Sr ions and to suppress the ferromagnetism.^{6,10–12} For $A^{2+} = La_{0.5}^{3+}Na_{0.5}^+$ and La^{3+} substitution for Sr^{2+} in $Sr_{1-x}A_x RuO_3$ (A = Ca, $La_{0.5}Na_{0.5}$, and La), one may expect charge disordering¹⁰ and electron doping effects on the Ru conduction band, respectively. The critical concentration x_c leading to $T_C = 0$ K is 0.35 for the La substitution.^{11,12} The suppression of T_C is the most steepest for La, secondary for $La_{0.5}Na_{0.5}$ and the slowest for Ca substitution. The electron carrier doping is the most effective to suppress the ferromagnetism.

In this Letter, we report unusual magnetic field dependence of magnetization near the ferromagnetic quantum phase transitions of $\text{Sr}_{1-x}\text{A}_x\text{RuO}_3$ (A = Ca, La_{0.5}Na_{0.5}, and La). We found a novel critical exponent $\delta \approx 3/2$ of magnetization curves $M = H^{1/\delta}$, in contrast to $\delta = 3$ of the mean field theory. The linear relation of Arrott plot breaks down near all the quantum phase transitions for three types of substitution. The dynamic scaling tested by ²³Na NMR suggests the effect of the short mean free path of conduction electrons.

Powder samples of $Sr_{1-x}A_xRuO_3$ were synthesized by a solid state reaction method. $Sr_{1-x}Ca_xRuO_3$ and $Sr_{1-x}La_xRuO_3$: Nominal compositions of $SrCO_3$ (99.99 %), Ru metal (99.99 %), CaCO_3 (99.99 %) or preheated La_2O_3 were mixed, ground, pelletized and fired at 900 °C in 24 hrs. The products were again ground, pelletized and fired at 900 °C in 24 hrs, and finally fired at 1300 °C in 24 hrs and then cooled down to room temperature in a furnace. $Sr_{1-x}(La_{0.5}Na_{0.5})_xRuO_3$: For $0 < x \le 0.5$, nominal $SrCO_3$ (99.99 %), RuO_2 (99.99 %), NaCO_3 (99.99 %) and preheated La_2O_3 were mixed, ground, pelletized

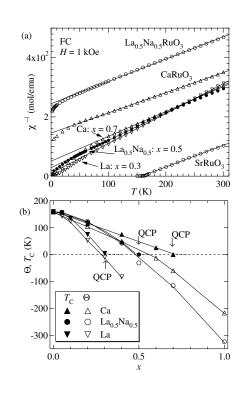


Fig. 1. (a)Inverse magnetic susceptibility χ^{-1} of $\mathrm{Sr}_{1-x} \mathrm{A}_x \mathrm{RuO}_3$ (A = Ca, La_{0.5}Na_{0.5}, and La). Upward triangles, circles and downward triangles are the data for A = Ca, La_{0.5}Na_{0.5}, and La, respectively. The magnetic susceptibility χ is defined by a magnetization M divided by an applied field H = 1 kOe, M/H. The solid lines are the fits by an inverse Curie-Weiss law. (b)Magnetic phase diagram of $\mathrm{Sr}_{1-x} \mathrm{A}_x \mathrm{RuO}_3$. Concentration x dependence of Weiss temperature Θ and Curie temperature T_{C} .

^{*}E-mail: itoh@kuchem.kyoto-u.ac.jp

and fired at 750 °C in 24 hrs. The products were again ground, pelletized and fired at 900 °C in 24 hrs, and finally fired at 1300 °C in 24 hrs. For x = 0.7 and 1.0, the final heat treatment was done at 1100 °C in 24 hrs.¹⁰ Powder X-ray diffraction patterns indicated that all the samples are in a single phase.

Magnetization up to 5 T were measured by a SQUID magnetometer (Quantum Design Co. MPMS). Figure 1 (a) shows inverse magnetic susceptibility χ^{-1} of $\mathrm{Sr}_{1-x}\mathrm{A}_{x}\mathrm{RuO}_{3}$ (A = Ca, La_{0.5}Na_{0.5}, and La) at H = 1kOe. The magnetic susceptibility χ is defined by a magnetization M divided by an applied field H = 1 kOe, M/H. Solid lines are the fits by an inverse Curie-Weiss law. The Curie constants are nearly the same as that of pure SrRuO₃. The Weiss temperature changes from positive to negative values with the A ion substitution.

Figure 1 (b) shows magnetic phase diagram of $Sr_{1-x}A_x RuO_3$. The Weiss temperature Θ and Curie temperature T_C are plotted as a function of concentration x. The critical concentrations x_c of $T_C = 0$ are $\approx 0.7, 0.5$ and 0.3 for A = Ca, La_{0.5}Na_{0.5}, and La, respectively.

Here, we briefly explain the typical magnetization process of a magnetic metal.¹³ Classical free energy of the Ginzburg-Landau-Wilson type is given by,

$$F(M) = -g\mu_{\rm B}HM + \frac{1}{2\chi_s}M^2 + \frac{1}{4}F_1M^4 + \dots$$
 (1)

where χ_s and F_1 are a spin susceptibility and a modemode coupling constant. Up to 4th order expansion, $\partial F/\partial M = 0$ gives a thermal equilibrium state. That is

$$M^2 = a + b\frac{H}{M},\tag{2}$$

where $a=-1/\chi_s F_1$ and $b=g\mu_{\rm B}/F_1$. The plot of M^2 against H/M is shortly called Arrott plot. Since a = 0 at $T = T_{\rm C}$, we obtain

$$M = b^{-1/3} H^{1/3}.$$
 (3)

In general, just at a critical point, we define

$$M \propto H^{1/\delta}$$
. (4)

The mean field theory gives the critical exponent $\delta = 3$.

The left panels in Fig. 2 show magnetization curves (field dependence of magnetization) and the right panels show Arrott plots M^2 against H/M near the ferromagnetic quantum phase transitions of $\operatorname{Sr}_{1-x} \operatorname{A}_x \operatorname{RuO}_3$ with $A = \operatorname{Ca}(x = 0.7)$, $\operatorname{La}_{0.5}\operatorname{Na}_{0.5}(x = 0.5)$, and $\operatorname{La}(x = 0.3)$ from the top to the bottom panels. Obviously, the linearity in the Arrott plots breaks down. The Arrott plots show concave curves. We have observed these behaviors not only at x_c but also around x_c in the individual substitution systems. As to $\operatorname{Sr}_{1-x}\operatorname{Ca}_x\operatorname{RuO}_3$, the concave curved Arrott plots have already been seen up to high magnetic field of H = 44 T.⁹

Figure 3 shows Arrott plots M^2 against H/M of SrRuO₃ and MnSi.¹⁴ The Arrott plots hold relatively well for SrRuO₃. That is, the critical exponent δ near $T_{\rm C} \approx 160$ K is close to the mean field value 3.¹⁵ The Arrott polts of MnSi show convex curves.¹⁶ This is an another breakdown of Arrott plots different from Sr_{1-x}A_xRuO₃ with x_c . The linear relation is seen in the plot of M^4 against H/M.¹⁷

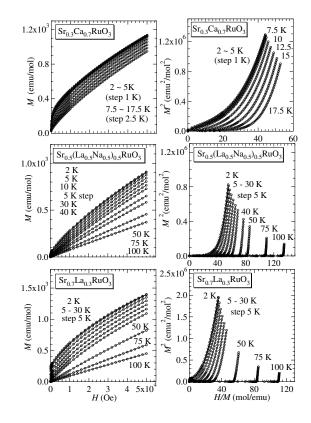


Fig. 2. Field dependence of magnetization M vs H (left panels) and Arrott plots M^2 vs H/M (right panels) near the ferromagnetic quantum phase transitions of $\mathrm{Sr}_{1-x}\mathrm{A}_x\mathrm{RuO}_3$ with $\mathrm{A} = \mathrm{Ca}$ (x = 0.7), $\mathrm{La}_{0.5}\mathrm{Na}_{0.5}$ (x = 0.5), and La (x = 0.3) from the top to the bottom panels. The Arrott plots show concave curves.

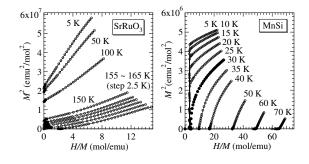


Fig. 3. Arrott plots $M^2 \text{ vs } H/M$ of SrRuO₃ (left panel) and MnSi (right panel). The magnetization curves of MnSi are shown as the known example of the breakdown of the linearity in Arrott plots. The Arrott polts of MnSi show convex curves.

We estimated "b" $\equiv \Delta M^2 / \Delta(H/M)$ as a function of magnetic field H for each Arrott plot. For each substitution system, we observed a crossover from a nearly H-independent "b" for x = 0 at $T_{\rm C}$ to "b" $\propto H$ for x = x_c at low temperatures ($T \ge 2$ K $> T_{\rm C}$). Thus, we found an empirical relation "b" $\propto H$ near the quantum phase transitions, although a and b must not depend on H in eq. (2). This is equivalent to $M \propto H^{2/3}$. The equation of $M = pH^{2/3} + q$ with the T- and x-dependent p and qwas applied to the magnetization around $x = x_c$. The qvanished in $x = x_c$ at low temperatures.

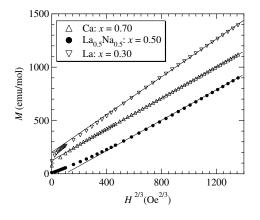


Fig. 4. Magnetization M plotted against $H^{2/3}$ at T = 5 K near the ferromagnetic quantum phase transitions of $\text{Sr}_{1-x}\text{A}_x\text{RuO}_3$ with A = Ca (x = 0.7), $\text{La}_{0.5}\text{Na}_{0.5} (x = 0.5)$, and La (x = 0.3). The straight lines are visual guides.

In Fig. 4, the magnetizations M are plotted against $H^{2/3}$ at T = 5 K near the ferromagnetic quantum phase transitions of $\mathrm{Sr}_{1-x}\mathrm{A}_x\mathrm{RuO}_3$ with A = Ca (x = 0.7), $\mathrm{La}_{0.5}\mathrm{Na}_{0.5}$ (x = 0.5), and La (x = 0.3). The linear relations hold well. The critical exponent of magnetization is $\delta \approx 3/2$ for x_c at lower temperatures. The finite temperature scaling relation could not apply to the $x = x_c$ sample because of $T_{\mathrm{C}} = 0$ K. The test for a scaling relation with respect to $g = (x - x_c)/x_c$ extrapolated toward T = 0 K ¹⁹ remains to be a problem.

MnSi and BaRuO₃²⁰ show the critical exponent $\delta \approx 5$, which can be understood by the effects of thermal ferromagnetic spin fluctuations on the magnetization curves.^{17, 18} The Gaussian fluctuation effects on the magnetization leads to a small $\delta = 7/3 \approx 2.33$,¹⁹ which may apply to BaIrO₃.²¹ The $\delta \approx 1.5$ of Sr_{1-x}A_xRuO₃ smaller than the mean field value $\delta = 3$ could not be reproduced by the higher order terms of magnetization nor by the Gaussian fluctuations. First order like inhomogeneous quantum phase transition^{22, 23} might be associated with the small δ . Some effects on magnetization process via spin fluctuations might affect δ .

In order to study the microscopic spin fluctuation spectrum, we performed ²³Na (nuclear spin I = 3/2 and nuclear gyromagnetic ratio $\gamma_n/2\pi = 11.262 \text{ MHz/T}$) NMR spin-echo measurements for $\text{Sr}_{1-x}(\text{La}_{0.5}\text{Na}_{0.5})_x\text{RuO}_3$ with x = 0.5 and 1.0 at H = 7.48414 T.

²³Na NMR frequency spectra systematically changed with La_{0.5}Na_{0.5} substitution. Figure 5 (a) shows ²³Na Knight shifts against temperature (bottom axis) and against magnetic susceptibility defined by M/H at H= 5 T (top axis) for x = 0.5 and 1.0. The temperature dependent spin part of Knight shift K is proportional to the spin susceptibility χ_s via a hyperfine coupling constant $A_{\rm hf}$, $K_s(T) = A_{\rm hf}\chi_s(T)/N_{\rm A}\mu_{\rm B}$ ($N_{\rm A}$ is the Avogadro number and $\mu_{\rm B}$ is the Bohr magneton). From the $K-\chi$ plots and the linear function fit, $A_{\rm hf}$ was estimated to be $+1.2\pm 0.1$ kOe/ $\mu_{\rm B}$.

Figure 5 (b) shows temperature dependence of ²³Na nuclear spin-lattice relaxation rate $1/T_1$ for x = 0.5 and 1.0 measured by an inversion recovery spin-echo

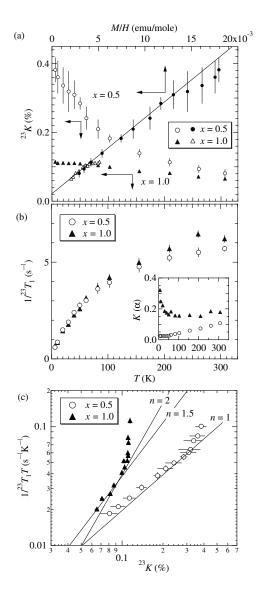


Fig. 5. (a)²³Na Knight shifts plotted against temperature (bottom axis) and against magnetic susceptibility defined by M/Hat H = 5 T (top axis) for $\text{Sr}_{1-x}(\text{La}_{0.5}\text{Na}_{0.5})_x\text{RuO}_3$ with x = 0.5(circles) and 1.0 (triangles). The solid line is a linear function fit to the $K - \chi$ plot. (b)Temperature dependence of ²³Na nuclear spin-lattice relaxation rate $1/T_1$ for $\text{Sr}_{1-x}(\text{La}_{0.5}\text{Na}_{0.5})_x\text{RuO}_3$ with x = 0.5 and 1.0. The inset shows temperature dependence of $K(\alpha)$. (c)Log-log plots of ²³Na nuclear spin-lattice relaxation rate divided by temperature $1/T_1T$ against Knight shift K for $\text{Sr}_{1-x}(\text{La}_{0.5}\text{Na}_{0.5})_x\text{RuO}_3$ with x = 0.5 and 1.0. The solid lines are visual guides for K^n with n = 1, 1.5 and 2

technique. For both x = 0.5 and 1.0, $1/T_1$ shows non-Korringa behavior and levels off at high temperatures. The critical slowing down of $1/T_1 \propto T^{-1/3}$ just at the quantum critical point²⁴ is not observed for x = 0.5. This is consistent with the absence of the critical divergence for the Ca substituted $x \sim 0.7$.^{8,23} No divergence in Fig. 5 (b), however, might be due to the magnetic field ~ 7.5 T.

The inset in Fig. 5 (b) shows temperature dependence of $K(\alpha) = S/T_1TK_s^2$ ($S \equiv \gamma_e \hbar/4\pi k_B \gamma_n$, the electron gyromagnetic ratio γ_e and an exchange enhancement factor α).²⁵ Exchange-enhancement effects deviate the Korringa ratio from that of free electron gas by $K(\alpha)$.²⁵ The ferromagnetic and antiferromagnetic spin fluctuations give $K(\alpha) < 1$ and > 1, respectively. The $K(\alpha) << 1$ in the inset of Fig. 5 (b) evidences that both x = 0.5and 1.0 systems are nearly ferromagnetic metals.

For a nearly ferromagnetic metal, the dynamical spin susceptibility $\chi''(q,\omega)$ with dynamic critical exponent z and magnetic correaltion length ξ is given by a scaling hypothesis,

$$\chi''(q,\omega) = \xi^2 f(\xi q, \xi^z \omega), \tag{5}$$

where f is an appropriate function. One should note z = 3 and 4 in the clean and dirty limits, respectively.^{2,26} This is because in the dirty limit, the quasi-particle life time and the mean free path are short and then the spin fluctuation spectrum is diffusive, that is the characteristic frequency $\Gamma(q) \propto q^2$ (q^4 at $T = T_{\rm C}$), being in contrast to the clean $\Gamma(q) \propto q$ (q^3 at $T = T_{\rm C}$).²⁷ For the nearly ferromagnetic metal in D(= 2 and 3) dimensions, the nuclear spin-lattice relaxation rate divided by temperature $1/T_1T$ is expressed by the static spin susceptibility $\chi_s \propto \xi^2$ and the Knight shift $K_s \propto \chi_s$,

$$\frac{1}{T_1 T} \propto \xi^{2+z-D} \propto K_s^{1+(z-D)/2}.$$
 (6)

This is a consequence from the dynamic scaling law. For a 3D nearly ferromagnetic metal, we obtain $1/T_1T \propto K$ in the clean limit.²⁸ In the dirty limit, we obtain $1/T_1T \propto K^{1.5}$ for z = 4.

In a Lorentzian model, the $\chi''(q, \omega)$ is characterized by the energy width T_0 of spin fluctuations and the spread T_A in the q-space.²⁹ The nuclear spin-lattice relaxation rate $1/T_1$ for the 3D nearly ferromagnetic metal in the clean limit is given by

$$\frac{1}{T_1} = \frac{3\hbar\gamma_{\rm n}^2 A_{\rm hf}^2}{4\pi} \frac{t}{T_{\rm A}y},\tag{7}$$

where the reduced temperature $t = T/T_0$ and the reduced magnetic susceptibility $1/y = (\xi q_B)^2 (q_B \text{ is the effective}$ spherical radius of the Brillouin zone).²⁴ The static spin susceptibility is expressed by $\chi_s/N_A = 1/2T_A y$. The selfconsistent renormalization (SCR) theory reproduces the Curie-Weiss behavior of 1/y as a function of t and the distance y_0 to the quantum critical point.²⁴ At $T \to 0$, $1/T_1 \propto t/T_A y_0$ is Korringa like. At high temperatures $t > y_0 T_0, t/y$ levels off and takes ~ 27.^{24, 28} Thus, we obtain

$$\frac{1}{T_1} \to \frac{81\hbar\gamma_n^2 A_{\rm hf}^2}{4\pi} \frac{1}{T_{\rm A}}.$$
(8)

The temperature dependences of $1/T_1$ in Fig. 5 (b) for A = La_{0.5}Na_{0.5} and the previous ones for A = Ca⁸ are consistent with the SCR results except the critical slowing down toward T = 0 K at the quantum critical point.

Figure 5 (c) shows log-log plots of ²³Na NMR $1/T_1T$ against Knight shift K with temperature as an implicit parameter for x = 0.5 and 1.0. The relation between $1/T_1T$ and K is not a simple $1/T_1T \propto K$. Both x =0.5 and 1.0 systems may be located in the intermediate region between good and bad metals, which might be associated with the small exponent $\delta \approx 3/2$ of magnetization curves. In conclusion, we found a novel small critical exponent $\delta \approx 3/2$ of magnetization curves $M \propto H^{1/\delta}$ near the ferromagnetic quantum phase transitions of $\mathrm{Sr}_{1-x}\mathrm{A}_{x}\mathrm{RuO}_{3}$ (A = Ca, La_{0.5}Na_{0.5}, and La). The ²³Na NMR test for the dynamic scaling law indicated that the dirty ferromagnetic spin fluctuation spectrum might be a key.

We thank H. Ohta, T. Waki, W. Zhang and C. Michioka for their experimental supports and helpful discussions, and S. Miyasaka, M. Hagiwara and I. Terasaki for valuable discussions. This work was supported in part by a Grant-in-Aid for Science Research on Priority Area, "Invention of Anomalous Quantum Materials," from the Ministry of Education, Culture, Sports, Science and Technology of Japan (16076210) and in part by a Grant-in-Aid for Scientific Research from the Japan Society for Promotion of Science (Grant No. 19350030).

- T. Moriya: Spin Fluctuations in Itinerant Electron Magnetism (Springer-Verlag, Berlin 1985).
- 2) J. A. Hertz: Phys. Rev. B 14 (1976) 1165.
- S. Sachdev: Quantum Phase Transitions (Cambridge University Press, New York 1999).
- 4) A. Schofield: Phys. World Aug. (2003) 23.
- J. M. Longo, P. M. Raccah and J. B. Goodenough: J. App. Phys. **39** (1968) 1327.
- 6) A. Kanbayashi: J. Phys. Soc. Jpn. 44 (1978) 108.
- 7) F. Fukunaga and N. Tsuda: J. Phys. Soc. Jpn. 63 (1994) 3798.
- K. Yoshimura, T. Imai, T. Kiyama, K. R. Thurber, A. W. Hunt and K. Kosuge: Phys. Rev. Lett. 83 (1999) 4397.
- 9) T. Kiyama, K. Yoshimura, K. Kosuge, H. Mitamura and T. Goto: J. Phys. Soc. Jpn. 68 (1999) 3372.
- 10) T. He, Q. Huang and R. J. Cava: Phys. Rev. B 63 (2000) 024402.
- R. J. Bouchard and J. F. Weiher: J. Solid State Chem. 4 (1972) 80.
- H. Nakatsugawa, E. Iguchi and Y. Oohara: J. Phys.: Condens. Matter 14 (2002) 415.
- 13) A. Arrott: Phys. Rev. 108 (1957) 1394.
- 14) H. Yasuoka, V. Jaccarino, R. C. Sherwood and J. H. Wernick: J. Phys. Soc. Jpn. 44 (1978) 842. The *MH* curves have been measured for the MnSi sample in this report. We thank Prof. Yasuoka for kind supply of the sample.
- 15) D. Kim, B. L. Zink, F. Hellman, S. McCall, G. Cao and J. E. Crow: Phys. Rev. B 67 (2003) R100406.
- 16) D. Bloch, J. Voiron, V. Jaccarino and J. H. Wernick: Phys. Lett. **51** (1975) 259.
- 17) Y. Takahashi: J. Phys. Soc. Jpn. 55 (1986) 3553.
- 18) Y. Takahashi: J. Phys.: Condens. Matter 13 (2001) 6323.
- M. A. Continentino: Quantum Scaling in Many-Body Systems (World Scientific, Singapore 2001).
- 20) J.-S. Zhou, K. Matsubayashi, Y. Uwatoko, C.-Q. Jin, J.-G. Cheng, J. B. Goodenough, Q. Q. Liu, T. Katsura, A. Shatskiy and E. Ito: Phys. Rev. Lett. **101** (2008) 077206.
- 21) T. Kida, A. Senda, S. Yoshii, M. Hagiwara, T. Takeuchi, T. Nakano and I. Terasaki: in press in Euro. Phys. Lett.
- 22) M. Daniel, J. I. Budnick, W. A. Hines, Y. D. Zhang, W. G. Clark and A. R. Moodenbaugh: J. Phys.: Condens. Matter 12 (2000) 3857.
- 23) Y. J. Uemura et al.: Nature Phys. 31 (2007) 29.
- 24) A. Ishigaki and T. Moriya: J. Phys. Soc. Jpn. 65 (1996) 3402.
- 25) T. Moriya: J. Phys. Soc. Jpn. 18 (1963) 516.
- 26) A. J. Millis: Phys. Rev. B 48 (1993) 7183.
- 27) P. Fulude and A. Luther: Phys. Rev. 170 (1968) 570.
- 28) T. Moriya and K. Ueda: Solid State Commun. 15 (1974) 169.
- 29) Y. Takahashi and T. Moriya: J. Phys. Soc. Jpn. 54 (1985) 1592.