

Scaling behaviors of RESET voltages and currents in unipolar resistance switching

S. B. Lee,¹ S. C. Chae,¹ S. H. Chang,¹ J. S. Lee,² S. Seo,³ B. Kahng,² and T. W.

Noh^{1,a)}

¹*ReCOE & FPRD, Department of Physics and Astronomy, Seoul National University, Seoul 151-747, Korea*

²*Department of Physics and Astronomy, Seoul National University, Seoul 151-747, Korea*

³*Samsung Advanced Institute of Technology, Suwon 440-600, Korea*

^{a)} Author to whom correspondence should be addressed. Electronic mail: twnoh@snu.ac.kr

Unipolar switching phenomena have attracted a great deal of recent attention, but the wide distributions of switching voltages still pose major obstacles for scientific advancement and practical applications. Using NiO capacitors, we investigated the distributions of the RESET voltage and current. We found that they scaled with the resistance value R_o in the low resistance state, and that the scaling exponents varied at $R_o \approx 30 \Omega$. We explain these intriguing scaling behaviors and their crossovers by analogy with percolation theory. We show that the connectivity of conducting filaments plays a crucial role in the RESET process.

Although reversible resistance switching (RS) behavior induced by electric stimulus has been known since the 1960s,¹ interest in these intriguing physical phenomena has been renewed due to the potential applications for nonvolatile resistance random access memory (RRAM). Of particular interest is unipolar RS, in which switching occurs due to two applied voltages of the same polarity. Many consider unipolar RRAM a good candidate for multi-stacked, high density, and nonvolatile memory.² Unfortunately, unipolar RS is usually accompanied by wide distributions of the switching voltages, which make it difficult to fabricate reliable RRAM devices.³ Despite their importance, we have little understanding of the switching voltage distributions.

Unipolar RS is widely accepted to occur because of the formation and rupture of conducting filaments under an electric field.¹ The switching voltage distributions may be closely related to the connection and disconnection of the conducting filaments. To describe collective changes in the conducting filaments' connectivity, we recently developed a new type of percolation model: the random circuit breaker (RCB) network model.⁴ This model was able to successfully explain the reversible dynamic processes observed in the unipolar RS. The resulting percolating cluster was highly directional, unlike the nearly isotropic infinite cluster of classical percolation theory. However, our recent experimental work using third harmonic generation demonstrated that the

connectivity of the conducting filaments in the unipolar RS could be quite similar to that in classical percolating systems.⁵

Here, we investigate how the percolating conducting filaments could become ruptured in one of the resistance switchings, called the RESET. In the unipolar RS, we show that the switching voltage and current scale with the resistance in the low resistance state. Depending on the resistance, there are two scaling regimes. We discuss the crossover between the two regimes in terms of the internal cluster structure of percolating filaments.

We grew a polycrystalline NiO thin film on Pt/Ti/SiO₂/Si substrates using dc magnetron reactive sputtering. Applying photolithographic techniques, we deposited 80-nm-thick Pt top electrodes with an area of $30 \times 30 \mu\text{m}^2$. The detailed fabrication methods for the Pt/NiO/Pt capacitors are described elsewhere.³ Using a semiconductor parameter analyzer (Agilent 4155C; Agilent Technologies, Santa Clara, CA), we measured current–voltage (I – V) curves. To obtain reliable statistics, we obtained 100 I – V curves from seven NiO capacitors.

Figure 1 shows the 100 I – V curves of our NiO capacitors, which were typical unipolar RS. The NiO capacitors were highly insulating in pristine states. When we applied a voltage of approximately 5 V (not shown here), I increased suddenly, causing

a complete dielectric breakdown. To prevent such permanent damage, we kept the current in the NiO capacitor below a compliance level I_{comp} . Immediately after this Forming process, the capacitor entered a low resistance state (LRS). When V was increased above V_R , it changed from the LRS to a high resistance state (HRS). We called this the RESET process. As we increased V again in the HRS and reached V_S , the film changed back into the LRS at a much higher voltage. We called this the SET process. For both Forming and SET processes, we used an I_{comp} of 1 mA.

The wide distributions of V_R and V_S in Fig. 1 are very important. Here, we concentrate on the distribution of V_R during the RESET process. In addition, we also examine the current value I_R during the RESET process. As shown in the inset, we determined the resistance value R_o of the LRS by fitting a linear line to the I - V curve in the small V region.

At first sight, the fluctuations in V_R (Fig. 1) appear so large that it seems impossible to find any simple relation for V_R . However, when we plotted $\log_{10}(V_R)$ vs. $\log_{10}(R_o)$, we found that the V_R data converged to two simple power law dependences. As shown in Fig. 2(a), $V_R \propto R_o^{-0.7 \pm 0.2}$ for $R_o < R_{\text{co}}$, and $V_R \propto R_o^{+0.2 \pm 0.1}$ for $R_o > R_{\text{co}}$, where $R_{\text{co}} \approx 30 \Omega$. Similar scaling behaviors were also found for I_R , as shown in Fig. 2(b): $I_R \propto R_o^{-\alpha}$. The values of exponent α were 1.8 ± 0.2 for $R_o < R_{\text{co}}$ and 0.7 ± 0.1 for $R_o > R_{\text{co}}$.

To obtain a physical picture of each scaling regime, we chose eight points, marked the numerics in Fig. 2(a), and plotted the corresponding I - V curves. As displayed in Fig. 2(c), the I - V curves in the $R_o < R_{co}$ regime show a systematic decrease in V_R (and I_R) with an increase in R_o . Similar behavior was reported in TiO_2 thin films⁶ of 20–30 Ω resistance. However, as shown in Fig. 2(d), in the $R_o > R_{co}$ regime, a systematic increase in V_R (and decrease in I_R) with the increase in R_o occurred. Similar behaviors have been observed in Ti-doped NiO thin films⁷ of 10^2 – 10^4 Ω , and Al_2O_3 thin films⁶ of approximately 100 Ω . Note that we were able to observe both results in our NiO capacitors.

How does the $\log_{10}(V_R)$ and $\log_{10}(I_R)$ data scale with $\log_{10}(R_o)$ in the RESET process? We must pay attention to the electrical breakdown process of semicontinuous metal films, which have been described by classical percolation theories.^{8–10} As with our RESET process, the films were found to experience electrical breakdown at a threshold current I_c , when a hot spot reached the melting temperature of the metallic grains. Yagil, Deutscher, and Bergman found that $I_c \propto R_o^{-\alpha}$ with $\alpha = 1.75 \pm 0.4$ for $R_o < 2$ k Ω and 0.85 ± 0.2 for $R_o > 2$ k Ω .⁹ These scaling behaviors in the two regimes and the values of α were very similar to our observations [Fig. 2(b)].

To obtain further insights, we measured the third harmonic generation response as a

function of R_o . Details of the measurements have been reported elsewhere.^{5,11} The third harmonic signal V_{3f} probes the Joule heating in the percolating cluster in the LRS.^{5,9-11} Figure 3 shows scaling behaviors of the third harmonic coefficient B_{3f} ($\equiv V_{3f}/I^3$), with an applied ac voltage with a peak amplitude value of 0.1 V and a frequency of 10 Hz. As with the V_R and I_R data, $\log_{10}(B_{3f})$ in the LRS scaled with $\log_{10}(R_o)$. It also had two scaling regimes: $B_{3f} \propto R_o^{w+2}$ with $w = 4.7 \pm 0.3$ for $R_o < R_{co}$ and $w = 1.1 \pm 0.2$ for $R_o > R_{co}$.

For an inhomogeneous medium, the current distribution should be highly nonuniform. Moreover, R_o measures the second moments of the current distribution in the network and B_{3f} probes the fourth moments. Thus, B_{3f} can be written as^{5,10,11}

$$\frac{B_{3f}}{R_o^2} \propto \frac{\sum i_b^4}{(\sum i_b^2)^2} \propto R_o^w, \quad (1)$$

where i_b is the current flowing through each conducting filament b . Note that $1/f$ noise measurements also probe the fourth moments, so its scaling behavior can be also written in a form similar to (1). The experimental values of w in the literature vary.¹² For two-dimensional semicontinuous Au films,⁹ reports have indicated that $w \approx 1.65$ for $R_o < 2$ k Ω and $w \approx 0.1$ for $R_o > 2$ k Ω . For sand blasted films,¹² w is reported to vary between 3.4 and 6.

Why are there two scaling regimes? According to classical percolation theory,^{8,10} the

percolating cluster can be viewed as a backbone composed of two groups. In one group, the bonds are in ‘blobs,’ which are multiply connected, but in the other group, the bonds are in ‘links,’ which are singly connected. If any bond in a link is cut, the backbone is split into two parts. The correlation length ξ represents the average distance between the nodes, as shown in Fig. 4(a). The finite size L of the sample can play an important role in determining the effective connectivity between two electrodes. As schematically shown in Fig. 4(b) [and 4(c)], if $\xi < L$ ($\xi > L$), all (some) parts of the infinite metallic cluster should be multiply (singly) connected. The connectivity change will cause changes in current distributions and the w value.^{8,10,13}

The connectivity changes between Figs. 4(b) and (c) can explain why the I – V curves in Figs. 2(c) and (d) behave differently depending on the scaling regime. When $R_o < R_{co}$ (i.e., $\xi < L$), all of the conducting filaments are multiply connected. When the number of the conducting channel decreases, the R_o value increases. Because the current then flows along fewer channels, the Joule heating in each conducting channel increases significantly,^{14,15} resulting in a decrease in I_R and V_R . Our earlier simulations using the RCB network model confirmed this behavior.⁴ When $R_o > R_{co}$ (i.e., $\xi > L$), some parts of the conducting channel become singly connected. In this channel, all of the current should merge. Then, the increase in R_o should be related to the length increase of the

singly connected channel. Thus, I_R should be nearly constant, and V_R should increase. However, due to the Joule heating, I_R could decrease with the R_o value. Our recent simulation using the RCB network model with temperature dissipation effects also supports this argument. Details will be published elsewhere. Therefore, in our NiO capacitors, the scaling regimes of $R_o < R_{co}$ and $R_o > R_{co}$ should correspond to the regimes of $\xi < L$ and $\xi > L$, respectively.

In summary, we investigated the wide distributions of the RESET voltages and currents in NiO films with unipolar resistance switchings. We found that they scaled with the resistance value in the low resistance states. In addition, we found crossover behavior in the scaling. This intriguing behavior could be explained in terms of the connectivity of the percolating cluster.

This work was supported by the Creative Research Initiatives (Functionally Integrated Oxide Heterostructure) of the Ministry of Science and Technology (MOST) and the Korean Science and Engineering Foundation (KOSEF). B. K. and J. S. L were supported by the KOSEF grant funded by the MOST (No.R17-2007-073-01001-0). S. B. L. acknowledges support from a Seoul Science Scholarship.

References

- ¹R. Waser and M. Aono, *Nat. Mater.* **6**, 833 (2007).
- ²M.-J. Lee, Y. Park, D.-S. Suh, E.-H. Lee, S. Seo, D.-C. Kim, R. Jung, B. S. Kang, S.-E. Ahn, C. B. Lee, D. H. Seo, Y.-K. Cha, I.-K. Yoo, J.-S. Kim, and B. H. Park, *Adv. Mater.* **19**, 3919 (2007).
- ³R. Jung, M. J. Lee, S. Seo, D. C. Kim, G.-S. Park, K. Kim, S. E. Ahn, Y. Park, I. K. Yoo, J.-S. Kim, and B. H. Park, *Appl. Phys. Lett.* **91**, 022112 (2007).
- ⁴S. C. Chae, J. S. Lee, S. Kim, S. B. Lee, S. H. Chang, C. Liu, B. Kahng, H. Shin, D.-W. Kim, C. U. Jung, S. Seo, M.-J. Lee, and T. W. Noh, *Adv. Mater.* **20**, 1154 (2008).
- ⁵S. B. Lee, S. C. Chae, S. H. Chang, J. S. Lee, S. Park, Y. Jo, S. Seo, B. Kahng, and T. W. Noh, arXiv:0810.0886.
- ⁶K. M. Kim, B. J. Choi, B. W. Koo, S. Choi, D. S. Jeong, and C. S. Hwang, *Electrochem. Solid-State Lett.* **9**, G343 (2006).
- ⁷S.-E. Ahn, M. J. Lee, Y. Park, B. S. Kang, C. B. Lee, K. H. Kim, S. Seo, D.-S. Suh, D. C. Kim, J. Hur, W. Xianyu, G. Stefanovich, H. Yin, I. K. Yoo, J.-H. Lee, J.-B. Park, I.-G. Baek, and B. H. Park, *Adv. Mater.* **20**, 924 (2008).
- ⁸D. Stauffer and A. Aharony, *Introduction to Percolation Theory*, revised 2nd ed. (Taylor & Francis, London, 1994).

- ⁹Y. Yagil, G. Deutscher, and D. J. Bergman, Phys. Rev. Lett. **69**, 1423 (1992).
- ¹⁰B. K. Chakrabarti and L. G. Benguigui, *Statistical Physics of Fracture and Breakdown in Disordered Systems* (Oxford University Press, Oxford, 1997).
- ¹¹M. A. Dubson, Y. C. Hui, M. B. Weissman, and J. C. Garland, Phys. Rev. B **39**, 6807 (1989).
- ¹²Y. Song, S.-I. Lee, and J. R. Gaines, Phys. Rev. B **46**, 14 (1992).
- ¹³R. Rammal, C. Tannous, and A.-M. S. Tremblay, Phys. Rev. A **31**, 2662 (1985).
- ¹⁴S. H. Chang, S. C. Chae, S. B. Lee, C. Liu, T. W. Noh, J. S. Lee, B. Kahng, J. H. Jang, M. Y. Kim, D.-W. Kim, and C. U. Jung, Appl. Phys. Lett. **92**, 183507 (2008).
- ¹⁵S. H. Chang, J. S. Lee, S. C. Chae, S. B. Lee, C. Liu, B. Kahng, D.-W. Kim, and T. W. Noh, arXiv:0803.4258v1.

Figure captions

FIG. 1. (Color online) One hundred current–voltage (I – V) curves from seven NiO capacitors, which show unipolar resistance switching. The red and blue lines correspond to the RESET and SET processes, respectively. To prevent permanent dielectric breakdown, we used the compliance current I_{comp} ($= 1$ mA). There were wide distributions in the RESET and SET voltages. The inset shows a typical I – V curve near the RESET voltage of the NiO film. R_o is the linear resistance value, obtained from the linear fit to the low V region.

FIG. 2. (Color online) R_o dependences of (a) RESET voltage, V_R , and (b) RESET current, I_R . At R_{co} ($\sim 30 \Omega$), the power law dependences for both V_R and I_R became varied. To clearly demonstrate how the power law varied with R_o , we selected eight data points. The selected I – V curves are in the (c) $R_o < R_{co}$ and (d) $R_o > R_{co}$ regimes.

FIG. 3. (Color online) R_o dependences of the third harmonic coefficient, B_{3f} . Note that R_{co} also separated the power law dependences for B_{3f} .

FIG. 4. (Color online) (a) A schematic of clusters connections in classical percolation

theory. ξ is the coherence length, i.e., the average distance between nodes. Also shown are proposed schematic diagrams for the connectivity of conducting filaments in the regimes of (b) $R_o < R_{co}$ (i.e., $\xi < L$, the sample size) and (c) $R_o > R_{co}$ (i.e., $\xi > L$). The conducting filaments are multiply and singly connected in (b) and (c), respectively.

Figure 1

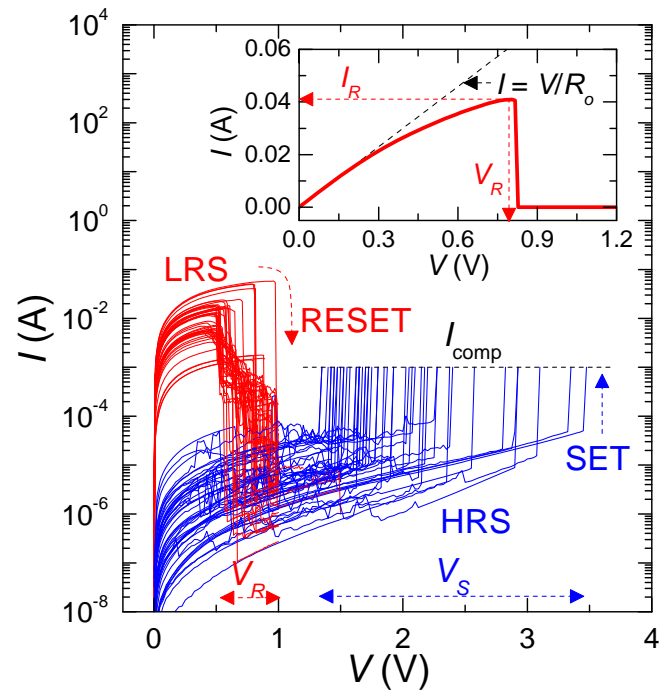


Figure 2

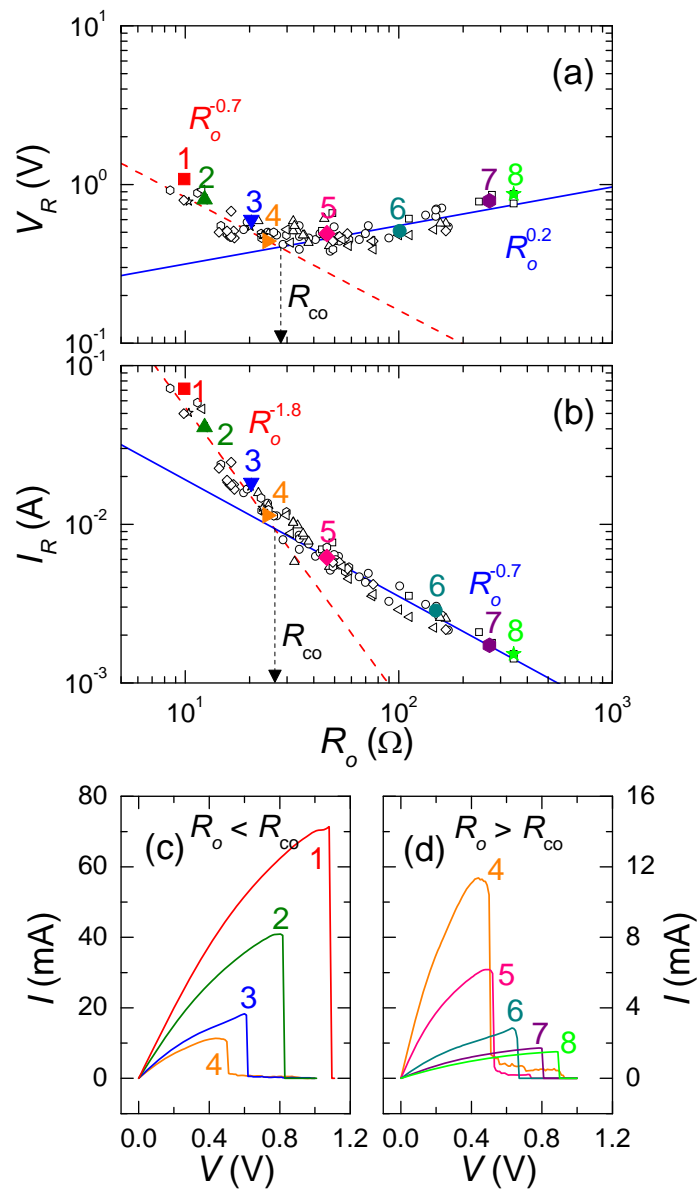


Figure 3

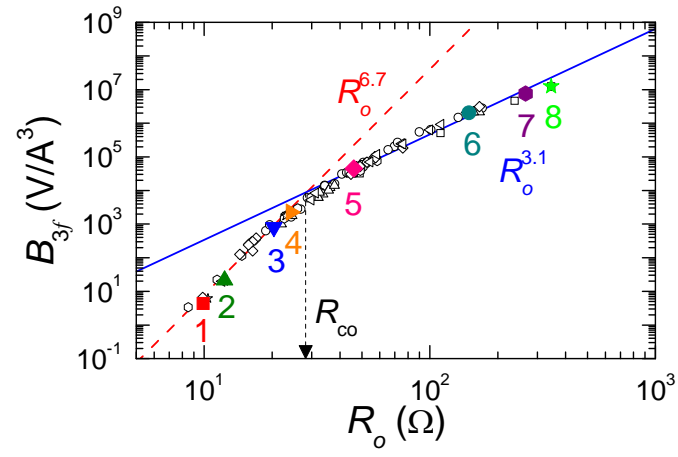


Figure 4

