

Possible superconductivity above 25 K in single crystalline Co-doped BaFe_2As_2 Yasuyuki NAKAJIMA^{1,2*}, Toshihiro TAEN¹, and Tsuyoshi TAMEGAI^{1,2}¹*Department of Applied Physics, The University of Tokyo, 7-3-1 Hongo, Bunkyo-ku, Tokyo 113-8656, Japan*²*JST, Transformative Research-Project on Iron Pnictides (TRIP), 7-3-1 Hongo, Bunkyo-ku, Tokyo 113-8656, Japan*

We present superconducting properties of single crystalline $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$ by measuring magnetization, resistivity, upper critical field, Hall coefficient, and magneto-optical images. The magnetization measurements reveal fish-tail hysteresis loop at high temperatures and relatively high critical current density above $J_c = 10^5$ A/cm² at low temperatures. Upper critical field determined by resistive transition is anisotropic with anisotropic parameter ~ 3.5 . Hall effect measurements indicate that $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$ is a multiband system and the mobility of electron is dominant. The magneto-optical imaging reveals prominent Bean-like penetration of vortices although there is a slight inhomogeneity in a sample. Moreover, we find a distinct superconductivity above 25 K, which leads us to speculate that higher transition temperature can be realized by fine tuning Co-doping level.

KEYWORDS: Iron arsenide, Magneto-optical imaging, Critical current density, Hall coefficient, Upper critical field

Since the discovery of high- T_c iron-based oxypnictide superconductor $\text{LaFeAsO}_{1-x}\text{F}_x$ with $T_c \sim 26$ K,¹ other iron-based superconductors are sought for to obtain higher transition temperature. In rare-earth substituted iron-oxypnictides $R\text{FeAsO}_{1-x}\text{F}_x$ (R = rare earth), the transition temperature has been increased up to 55 K.² In these iron oxypnictides, superconductivity occurs by introducing electrons in the $(\text{FeAs})^-$ layers by substituting F for O. Following these discoveries, oxygen-free iron-arsenide $A\text{Fe}_2\text{As}_2$ (A = Ba, Sr, Ca) is discovered. These materials show superconductivity by substituting alkali metal, such as Na, K and Cs, for A resulting in the introduction of holes in the $(\text{FeAs})^-$ layers.³⁻⁶ In hole-doped oxygen-free iron-arsenides, transition temperature is raised up to ~ 38 K.^{3,4} On the other hand, very recent studies reveal that the electron-doping by substitution of Co or Ni, which have one or two excess d electrons compare to Fe in conducting layers, induces superconductivity in oxygen-free iron-arsenide.^{7,8} In fact, NMR measurements reveal that Co atoms donate electrons without creating localized moments.⁹ Although the highest transition temperature in electron-doped BaFe_2As_2 is reported to be ~ 23 K,¹⁰ which is lower than that in hole-doped BaFe_2As_2 , the fact that the substitution of transition metals leads to occurrence of superconductivity contrasts strongly with a drastic suppression of T_c in cuprates.¹¹ However, the detailed study of the transition temperature as a function of Co-doping is limited.¹⁰ It is an open question whether the highest T_c in electron-doped BaFe_2As_2 is increased further or not.

In this paper, we have prepared the single crystalline sample of $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$ and present its superconducting properties by studying the magnetization, resistivity, upper critical field, Hall coefficient, and magneto-optical images. We address the possibility of further enhancement of transition temperature by fine-tuning Co-doping level.

Single crystalline samples with nominal composition $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$ were grown by FeAs/CoAs self-flux

method. FeAs and CoAs were prepared by placing mixtures of As pieces and Fe/Co powder in a silica tube and reacted at 1065 °C for 10 hours after heating at 700 °C for 6 hours. A mixture with the ratio Ba : FeAs : CoAs = 1 : 4.5 : 0.5 was placed in alumina crucible with quartz fiber as a cup. The whole assembly sealed in a large silica tube, and heated up to 1150°C for 10 hours followed by slow-cooling down to 1090°C at the rate of ~ 1.3 °C/h, after which the silica tube was put into a centrifuge to separate crystals from flux. The typical size of resulting crystals is $\sim 2 \times 2 \times 0.05$ mm³. Magnetization was measured by a commercial SQUID magnetometer (MPMS-XL5, Quantum Design). The resistivity measurements were performed by four-contact method and Hall coefficient were measured by the standard six-wire configuration. The Hall voltage was obtained from the antisymmetric part of the transverse voltage by subtracting the positive and negative magnetic field data. Magneto-optical images were obtained by using the local-field-dependent Faraday effect in the in-plane magne-

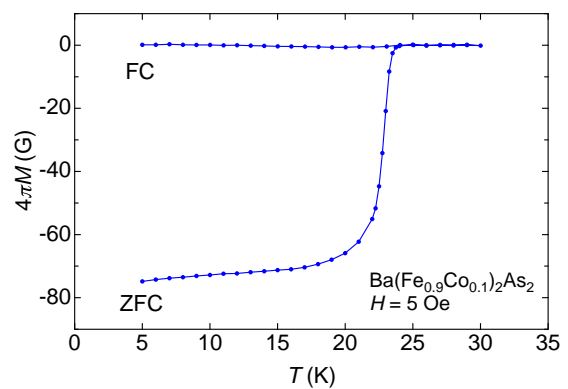


Fig. 1. Temperature dependence of the zero-field-cooled (ZFC) and field-cooled (FC) magnetization at $H = 5$ Oe in $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$.

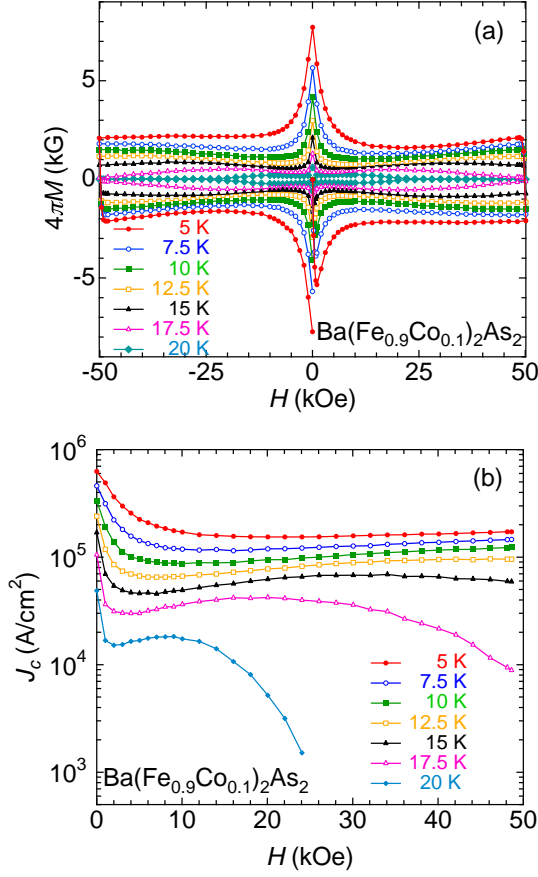


Fig. 2. (a) Field dependence of magnetization in $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$ at 5, 7.5, 10, 12.5, 15, 17.5, and 20 K. (b) Field dependence of critical current density obtained by the data shown in Fig. 2. (a) in $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$ at 5, 7.5, 10, 12.5, 15, 17.5, and 20 K.

tized garnet indicator film and employing a differential method.^{12,13}

Figure 1 shows the temperature dependence of zero-field-cooled (ZFC) and field-cooled (FC) magnetization at 5 Oe. Very sharp transition starting at $T_c \sim 24$ K is observed. It should be noted that this value of T_c is the highest among those reported to date.^{7,9,10,14-17}

Figure 2(a) depicts the magnetization at several temperatures as a function of field. At high temperatures above 15 K, fish-tail magnetization is observed, which is very similar to $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ single crystals.¹⁸ From the magnetization hysteresis loop, we can obtain the critical current density J_c using the Bean model with the assumption of field-independent J_c . According to the Bean model, J_c is given by

$$J_c = 20 \frac{\Delta M}{a(1 - a/3b)}, \quad (1)$$

where ΔM is $M_{\text{down}} - M_{\text{up}}$, M_{up} and M_{down} are the magnetization when sweeping fields up and down, respectively, a and b are sample widths with $a < b$. Figure 2(b) shows the field dependence of J_c obtained by the data shown in Fig. 2(a) using Eq. (1) and effective sample dimension with $a \sim 0.55$ mm and $b \sim 0.63$ mm. At low temperatures, J_c is larger than 10^5 A/cm². This

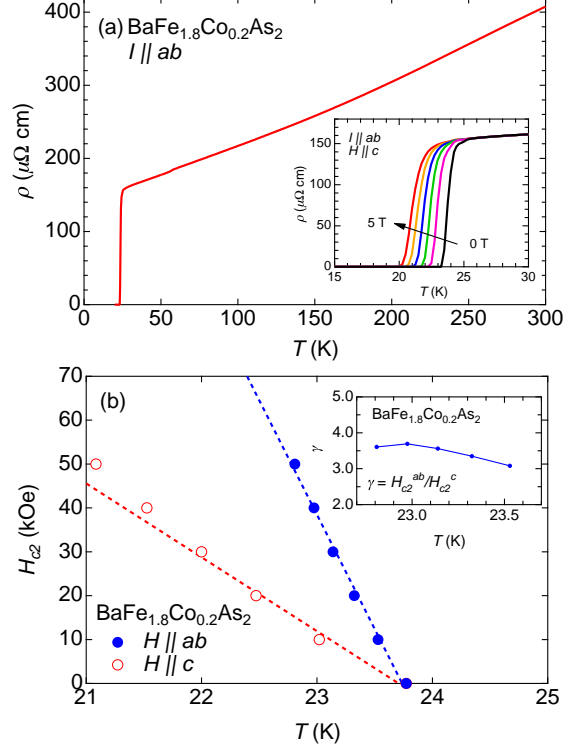


Fig. 3. (a) Temperature dependence of the zero-field resistivity in $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$. Inset: low-temperature in-plane resistivity data at $H = 0, 10, 20, 30, 40,$ and 50 kOe along c -axis. (b) Temperature dependence of upper critical field along ab -plane (●) and c -axis (○) obtained by the midpoint of resistive transition in $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$. Dashed lines are linear fits to the data. Inset: the temperature dependence of anisotropy of the upper critical field along ab - and c -directions $\gamma \equiv H_{c2}^{ab}/H_{c2}^c$.

value is much larger than that reported in Ref. 7 and about twice as large as those reported in Refs. 14 and 15. While the present value of J_c is about one order of magnitude smaller than the typical value for $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ single crystals,¹⁹ it is well within the range for practical applications.

Figure 3 (a) shows temperature dependence of in-plane zero-field resistivity in $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$. With decreasing temperature from 300 K, the resistivity decreases monotonically and then drops suddenly at T_c . There is no anomaly accompanied by a spin-density-wave transition reported in the parent material BaFe_2As_2 ,²⁰ which indicates that the transition is suppressed by Co-doping. The residual resistivity ratio $\rho(300 \text{ K})/\rho(T_c)$ is ~ 2.6 , which is comparative to that reported before.^{7,10,15,17} Inset of Fig.3(a) depicts low-temperature in-plane resistivity data at $H = 0, 10, 20, 30, 40,$ and 50 kOe along c -axis. With increasing fields, T_c decrease and the transition width is broadened only slightly. We plot the upper critical field H_{c2} along ab - and c - directions determined by the midpoint of resistive transition as a function of temperature in Fig. 3(b). The values of slope of H_{c2} along ab - and c -direction at T_c are -52.1 and -16.8 kOe/K, respectively. From the Werthamer-Helfand-Hohenberg theory,²¹ which describes orbital depairing field of conventional dirty type-

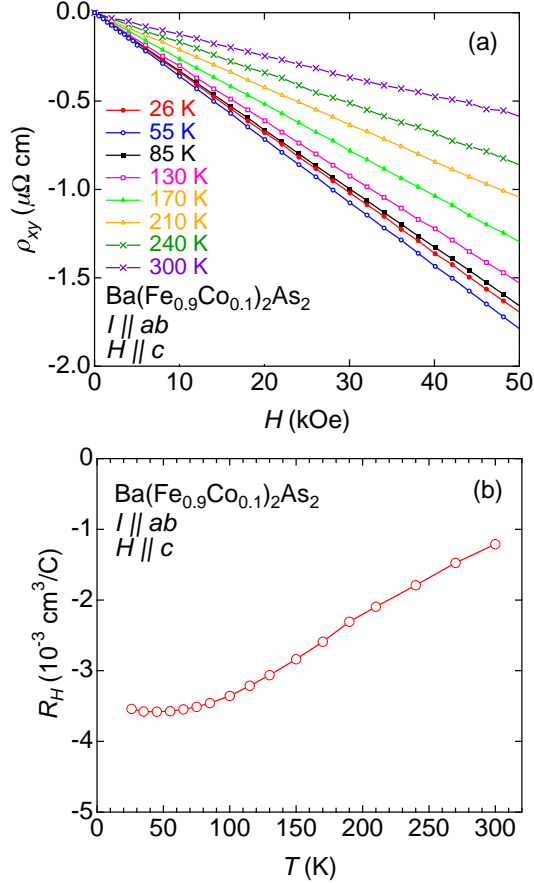


Fig. 4. (a) The Hall resistivity ρ_{xy} as a function of field at several temperatures. (b) Temperature dependence of the Hall coefficient in $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$.

II superconductors, we can obtain the values of $H_{c2}(0) = 0.69T_c[dH_{c2}/dT]|_{T=T_c} \sim 850$ and ~ 280 kOe along ab - and c -direction, respectively. These values are very high and comparative to hole-doped iron-arsenide superconductors $\text{Ba}_{1-x}\text{K}_x\text{Fe}_2\text{As}_2$.²² The inset of Fig. 3(b) shows the anisotropy of the upper critical field $\gamma \equiv H_{c2}^{ab}/H_{c2}^c$. The value of γ is ~ 3 -4 and, slightly increases with decreasing temperature. This value is similar to hole-doped iron arsenide.²³

Hall effect measurements strongly support that electron is introduced by Co-doping and $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$ is multiband system. Figure 4(a) shows the Hall resistivity ρ_{xy} at several temperatures as a function of field. In the present temperature region, ρ_{xy} is negative and shows H -linear dependence. We plot the Hall coefficient R_H in $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$ obtained from ρ_{xy} as a function of temperature in Fig. 4(b). The sign of R_H is negative in the whole temperature range while that in the hole-doped BaFe_2As_2 is positive,²⁴ which is consistent with introduction of electrons by Co-substitution for Fe. The values of R_H decrease with decreasing temperature from 300 K to ~ 60 K and slightly increase after showing a broad minimum at ~ 50 K. The absolute value of R_H just above T_c is three times larger than that at 300 K. In a simple single band system, the Hall coefficient is written as, $R_H = 1/nq$, where q is a charge of a carrier and

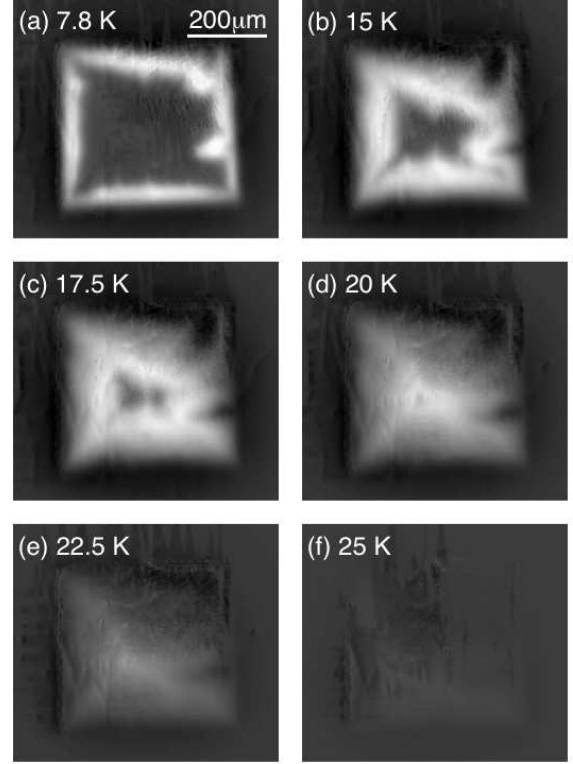


Fig. 5. Magneto-optical imaging of remanent state after applying $H = 690$ Oe in $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$ at (a) 7.8 K, (b) 15 K, (c) 17.5 K, (d) 20 K, (e) 22.5 K, and (f) 25 K.

n is a carrier density. R_H is almost T -independent. By contrast, the Hall coefficient in multiband system, for instance, consisting of electron and hole bands, is given by, $R_H = (n_h\mu_h^2 - n_e\mu_e^2)/(e(n_h\mu_h + n_e\mu_e)^2)$, where n_h (n_e) is a density of holes (electrons) and μ_h (μ_e) is a mobility of holes (electrons). The Hall coefficient in multiband system can be temperature dependent. The obtained results indicate that $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$ is multi-band system similar to the parent material BaFe_2As_2 ²⁵ and mobility of the electron produced by Co-doping becomes dominant with decreasing temperature.

Figure 5 shows magneto-optical images of $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$ in the remanent state at several temperatures after cycling the field up to 690 Oe for five seconds. While the sample for the magneto-optical experiments is different ($0.58 \times 0.45 \times 0.03$ mm³) from that for the magnetization measurements, both crystals show similar properties. The bright region in figures corresponds to the area trapping the vortices. Dark faint zig-zag features originate from in-plane domains of the garnet film and have nothing to do with the flux distribution. At lower temperatures, vortices penetrated from edges of the crystal cannot reach the center due to large shielding current. However, prominent penetrations of vortices are observed near the defects close to the right edge of the sample. The penetrations of vortices develop with increasing temperature. It should be noted that the image at 25 K apparently shows existence of superconductivity in the lower part of the sample. In fact, the zero-field resistivity starts to drop

at ~ 25 K as shown in the inset of Fig. 3(a). The highest transition temperature in $\text{Ba}(\text{Fe}_{1-x}\text{Co}_x)_2\text{As}_2$ reported so far is ~ 23 K.¹⁰ The difference can originate from the difference in Co concentration and/or its distribution. It may be possible to obtain even higher transition temperature in this system by fine-tuning the Co-doping level.

In summary, we have presented a systematic study of magnetization, resistivity, upper critical field, Hall coefficient, and magneto-optical imaging in single crystalline $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$. The magnetization measurements reveal fish-tail hysteresis loop at high temperatures and the relatively high critical current density larger than 10^5 A/cm². Upper critical field obtained by resistive transition is anisotropic. Its anisotropy is about 3.5. Hall effect measurements indicate that $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$ is multiband system and the mobility of electron is dominant. The magneto-optical imaging reveals prominent Bean-like penetrations of vortices although there is slight inhomogeneity in a sample. We also find a distinct superconductivity above 25 K, which leads us to expect that higher transition temperature can be realized by fine-tuning Co-doping.

- 1) Y. Kamihara, T. Watanabe, M. Hirano, and H. Hosono: *J. Am. Chem. Soc.* **130** (2008) 3296.
- 2) Z. A. Ren, W. Lu, J. Yang, W. Yi, X. L. Shen, Z. C. Li, G. C. Che, X. L. Dong, L. L. Sun, F. Zhou, and Z. X. Zhao: *Chin. Phys. Lett.* **25** (2008) 2215.
- 3) M. Rotter, M. Tegel, D. Johrendt: *Phys. Rev. Lett.* **101** (2008) 107006.
- 4) G. F. Chen, Z. Li, G. Li, W. Z. Hu, J. Dong, X. D. Zhang, P. Zheng, N. L. Wang, and J. L. Luo: *Chin. Phys. Lett.* **25** (2008) 3403.
- 5) K. Sasmal, B. Lv, B. Lorenz, A. Guloy, F. Chen, Y. Xue, and C. W. Chu: *Phys. Rev. Lett.* **101** (2008) 107007.
- 6) G. Wu, H. Chen, T. Wu, Y. L. Xie, Y. J. Yan, R. H. Liu, X. F. Wang, J. J. Ying, and X. H. Chen: *J. Phys.: Condens Matter* **20** (2008) 422201.
- 7) A. S. Sefat, R. Jin, M. A. McGuire, B. C. Sales, D. J. Singh, D. Mandrus: *Phys. Rev. Lett.* **101** (2008) 117004.
- 8) L. J. Li, Q. B. Wang, Y. K. Luo, H. Chen, Q. Tao, Y. K. Li, X. Lin, M. He, Z. W. Zhu, G. H. Cao, and Z. A. Xu: arXiv:0809.2009.
- 9) F. L. Ning, K. Ahilan, T. Imai, A. S. Sefat, R. Jin, M. A. McGuire, B. C. Sales, and D. Mandrus: *J. Phys. Soc. Jpn.* **77** (2008) 103705
- 10) N. Ni, M. E. Tillman, J. -Q. Yan, A. Kracher, S. T. Hannahs, S. L. Bud'ko, and P. C. Canfield: arXiv:0811.1767.
- 11) H. Fujishita and M. Sato: *Solid State Commun.* **72** (1989) 529.
- 12) A. Soibel, E. Zeldov, M. Rappaport, Y. Myasoedov, T. Tamegai, S. Ooi, M. Konczykowski, and V. B. Geshkenbein: *Nature* **406** (2000) 282.
- 13) M. Yasugaki, K. Itaka, M. Tokunaga, M. Kameda, and T. Tamegai: *Phys. Rev. B* **65** (2002) 212502.
- 14) A. Yamamoto, J. Jaroszynski, C. Tarantini, L. Balicas, J. Jiang, A. Gurevich, D. C. Larbalestier, R. Jin, A. S. Sefat, M. A. McGuire, B. C. Sales, D. K. Christen, and D. Mandrus: arXiv:0810.0699.
- 15) R. Prozorov, N. Ni, M. A. Tanatar, V. G. Kogan, R. T. Gordon, C. Martin, E. C. Blomberg, P. P. P. Prommapan, J. Q. Yan, S. L. Bud'ko, and P. C. Canfield: arXiv: 0810.1338.
- 16) R. T. Gordon, N. Ni, C. Martin, M. A. Tanatar, M. D. Vannette, H. Kim, G. Samolyuk, J. Schmalian, S. Nandi, A. Kreyssig, A. I. Goldman, J. Q. Yan, S. L. Bud'ko, P. C. Canfield, and R. Prozorov: arXiv: 0810.2295.
- 17) F. Ning, K. Ahilan, T. Imai, A. S. Sefat, R. Jin, M. A. McGuire, B. C. Sales, and D. Mandrus: *J. Phys. Soc. Jpn.* **77** (2008) 103705.
- 18) M. Däumling, J. M. Seuntjens and D. C. Larbalestier: *Nature* **346** (1990) 332.
- 19) T. Tamegai, L. Krusin-Elbaum, L. Civale, P. Santhanam, M. J. Brady, W. T. Masselink, F. Holtzberg, and C. Feild, *Phys. Rev. B* **45** (1992) 8201.
- 20) M. Rotter, M. Tegel, D. Johrendt, I. Schellenberg, W. Hermes, and R. Pöttgen: *Phys. Rev. B* **78** (2008) 020503R.
- 21) N. R. Werthamer, E. Helfand and P. C. Hohenberg: *Phys. Rev.* **147** (1966) 295.
- 22) M. Altarawneh, K. Collar, C. H. Mielke, N. Ni, S. L. Bud'ko, and P. C. Canfield: arXiv:0807.4488.
- 23) N. Ni, S. L. Bud'ko, A. Kreyssig, S. Nandi, G. E. Rustan, A. I. Goldman, S. Gupta, J. D. Corbett, A. Kracher, and P. C. Canfield: *Phys. Rev. B* **78** (2008) 014507.
- 24) G. Wu, R. H. Liu, H. Chen, Y. J. Yan, T. Wu, Y. L. Xie, J. J. Ying, X. F. Wang, D. F. Fang, X. and H. Chen: *Europhys. Lett.* **84** (2008) 27010.
- 25) C. Liu, G. D. Samolyuk, Y. Lee, N. Ni, T. Kondo, A. F. Santander-Syro, S. L. Bud'ko, J. L. McChesney, E. Rotenberg, T. Valla, A. V. Fedorov, P. C. Canfield, B. N. Harmon, and A. Kaminski: arXiv:0806.3453.