

Magnetic Field Induced Coherence-Incoherence Crossover in the Interlayer Conductivity of a Layered Organic Metal

M. V. Kartsovnik¹, P. D. Grigoriev², W. Biberacher¹, and N. D. Kushch³

¹ *Walther-Meißner-Institut, Bayerische Akademie der Wissenschaften, D-85748 Garching, Germany*

² *L. D. Landau Institute for Theoretical Physics,*

Russian Academy of Sciences, 142432 Chernogolovka, Russia and

³ *Institute of Problems of Chemical Physics, Russian Academy of Sciences, 142432 Chernogolovka, Russia*

The angle-dependent interlayer magnetoresistance of the layered organic metal α -(BEDT-TTF)₂KHg(SCN)₄ is found to undergo a dramatic change from the classical conventional behavior at low magnetic fields to an anomalous one at high fields. This field-induced crossover and its dependence on the sample purity and temperature imply the existence of two parallel channels in the interlayer transport: a classical Boltzmann conductivity σ_c and an incoherent channel σ_i . We propose a simple model for σ_i explaining its metallic temperature dependence and low sensitivity to the inplane field component.

Dimensional crossovers and their influence on transport properties and electronic states is a long-standing and still controversial issue in the field of highly anisotropic correlated conductors, such as superconducting cuprates, cobaltates, organics, intercalated compounds, etc. One of the most frequently discussed mechanisms of breaking the interlayer band transport in a layered metal is due to scattering. If the scattering rate τ^{-1} is larger than the interlayer hopping rate, $\tau_h^{-1} \sim t_{\perp}/\hbar$, the quasiparticle momentum and Fermi surface are only defined within conducting layers, i.e. become strictly two-dimensional (2D). Nevertheless, as long as the charge transfer between two adjacent layers is determined by direct one electron tunneling ("weakly incoherent" regime [1]), the interlayer resistivity $\rho_{\perp}(T)$ is predicted to be identical to that in the fully coherent three-dimensional (3D) case [2, 3]. At increasing temperature, the conductivity due to direct tunneling decreases and other conduction mechanisms associated, e.g., with small polarons [4, 5] or resonant impurity tunneling [3, 6] may come into play. This may lead to a crossover from a low-temperature metallic to a high-temperature, seemingly, nonmetallic temperature dependence of ρ_{\perp} . Such a scenario is qualitatively consistent with a nonmonotonic dependence $\rho_{\perp}(T)$ with a maximum at $T_m \sim 100$ K reported for various layered materials [7, 8, 9, 10, 11]. However, it does not explain the fact that the resistivity anisotropy in many of these compounds grows continuously upon cooling deep into the metalliclike regime of $\rho_{\perp}(T)$ [7, 8, 9, 12].

In addition to the latter apparent inconsistency, recent magnetotransport experiments have revealed a low-temperature behavior strongly violating theoretical predictions. The interlayer resistance R_{\perp} of a, presumably, weakly incoherent sample of the organic metal α -(BEDT-TTF)₂KHg(SCN)₄ has been found to be insensitive to a strong magnetic field applied parallel to layers [13]. This is, in particular, reflected in a broad dip in the angular dependence of magnetoresistance which is centered at $\theta = 90^\circ$ and scales with $B_{\perp} = B \cos \theta$, where θ is the

angle between the field and the normal to layers. While a similar dip in the angle-dependent magnetoresistance (AMR) has been observed on a number of other layered materials with different inplane Fermi surface topologies [14, 15, 16, 17], its origin remains unexplained.

For the organic conductor (TMTSF)₂PF₆ characterized by a flat, weakly warped Fermi surface the anomalous dip structure was reported for a field rotation in the plane of the Fermi sheets [14, 18]. It was, however, noticed [18] that the dip develops only at a high enough magnetic field $B > 1$ T; at low fields the curves $R_{\perp}(\theta)$ display a conventional shape with a maximum at the field parallel and a minimum at the field perpendicular to layers. The dramatic change of the AMR behavior was interpreted as a result of a field-induced confinement of conducting electrons. Semiclassically, the excursion of a charge carrier across the layers is restricted by a strong inplane magnetic field B_{\parallel} and limited to within one layer when $B_{\parallel} \geq B_c = 4t_{\perp}/edv_F$, where e is the elementary charge, d is the interlayer period, and v_F is the Fermi velocity. This was suggested to lead to a dimensional crossover and a consequent breakdown of the Fermi-liquid behavior [19]. While the field-induced confinement scenario [19] describes qualitatively a number of features of the magnetoresistance in (TMTSF)₂PF₆, it still does not provide a consistent explanation for the dip around $\theta = 90^\circ$. It remains also unclear why the crossover field increased with temperature in the experiment [18]. Further, as it will be shown below, the crossover between the low-field, conventional and high-field, anomalous AMR can also be observed on a system possessing a cylindrical Fermi surface. It is unclear, to what extent the field-induced confinement can be effective in this case.

Here, we report on the crossover in the shape of the angle-dependent interlayer magnetoresistance of α -(BEDT-TTF)₂KHg(SCN)₄. All the measurements were done under a pressure of ≈ 6 kbar in order to suppress the density-wave formation and stabilize the normal metallic state [20] with a well defined Fermi surface consisting of

a pair of open sheets and a cylinder [21]. We show that the field-induced confinement model [19] is inconsistent with the evolution of the crossover with temperature and sample purity. On the other hand, the observed behavior is strongly suggestive of two parallel contributions to the interlayer conductivity: a classical Boltzmann channel, σ_c , and an anomalous, incoherent channel, σ_i . We propose a possible explanation of the field and temperature dependence of σ_i , without invoking non-Fermi liquid effects.

Figure 1 shows AMR patterns from two samples of α -(BEDT-TTF)₂KHg(SCN)₄ recorded at $T = 1.4$ K, at different field intensities, $B = 0.12, 0.5, 3,$ and 15 T. The transport current is applied perpendicular to the ac plane, that is the plane of conducting layers. Azimuthal angle φ measured between the field projection on the ac plane and the a axis, the latter being perpendicular to the open Fermi sheets, is $\approx 20^\circ$ for both samples. The oscillatory behavior, particularly pronounced at high fields is due to angular magnetoresistance oscillation and Shubnikov-de Haas effects, as described in detail elsewhere [22]. It reveals a high crystal quality of both samples, providing an estimate for the transport scattering time, $\tau_1 \approx \tau_2/3 \sim 5$ ps for samples # 1 and # 2, respectively. In the rest of the paper we focus on the nonoscillating magnetoresistance component.

The low-field curves shown in Fig. 1 have a conventional form for both samples: the AMR is maximum(minimum) at the field directed nearly parallel(perpendicular) to layers. At fields above ~ 1 T, a broad dip around $\theta = \pm 90^\circ$ develops in the AMR of sample #1. Already at $B = 3$ T the magnetoresistance displays an absolute minimum at the field aligned parallel to layers (and perpendicular to the current!). This crossover in the AMR shape is very similar to that reported for (TMTSF)₂PF₆ [18]. Note, however, that in the present case the Fermi surface contains, besides open sheets, a cylindrical part and $\varphi \approx 20^\circ$ corresponds to the field rotating close to the plane perpendicular to the open sheets. Such a geometry is clearly unfavorable for the field-induced confinement scenario [19].

A comparison between the AMR of two samples shown in Fig. 1 reveals yet another disagreement with the field-induced confinement model. While the confinement field B_c is formally independent of the scattering time, the model implies a sufficiently high τ , so that the strong field criterion, $\omega_c \tau > 1$ (ω_c is the characteristic frequency of orbital motion in a magnetic field), is fulfilled. Therefore, the effect should be seen, first of all, in clean samples. By contrast, in our case the crossover is observed in the relatively dirty sample # 1, whereas the cleaner sample # 2 preserves the normal anisotropy up to the highest field applied.

To explain the observed behavior, it is instructive to study the magnetoresistance of sample # 1 as a function of magnetic field, aligned parallel to layers, and its evolu-

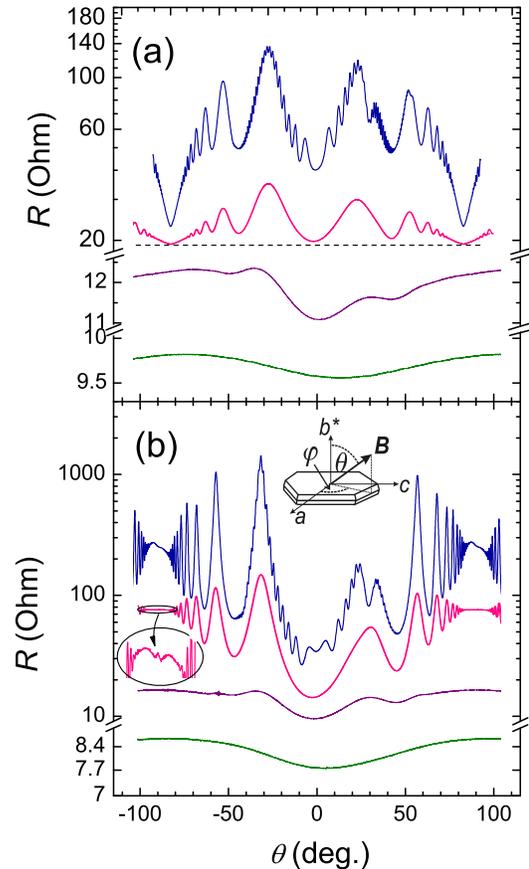


FIG. 1: (color online). Angle-dependent interlayer magnetoresistance of a relatively dirty sample, # 1, of α -(BEDT-TTF)₂KHg(SCN)₄ in the high-pressure metallic state recorded at $T = 1.4$ K, at magnetic fields (bottom to top): 0.12, 0.5, 3, and 15 T; $\varphi \approx 20^\circ$ (b) Same for a very clean sample, # 2. The upper inset illustrates the definition of angles θ and φ ; the lower inset: enlarged fragment of the 3 T curve showing a small "coherence peak".

tion with temperature. The relevant data is shown in Fig. 2 in the form of a Kohler plot. Here, $R_0(T)$ is the zero-field resistance shown in the inset and the normalized field-dependent interlayer conductivity $\sigma(B, T)/\sigma(0, T)$ has been obtained from $R(B)$ measurements, taking into account that $\sigma(B) \propto 1/R(B)$ in our quasi-2D material. According to Kohler's rule, the magnetoresistance or, in our representation, magnetoconductivity at different fields and temperatures should be just a function of $B/R_0(T)$. This rule is strongly violated in Fig. 2: the curves corresponding to different temperatures rapidly diverge from each other, saturating at different levels [23]. On the other hand, the saturation occurs at approximately the same B/R_0 , independent of T .

The described behavior suggests two parallel contributions in the conductivity:

$$\sigma(\mathbf{B}, \tau) = \sigma_c(\mathbf{B}, \tau) + \sigma_i(B_\perp, \tau). \quad (1)$$

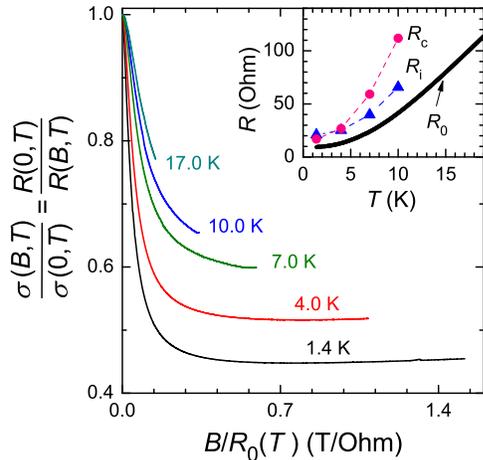


FIG. 2: (color online). Kohler plot of the normalized interlayer conductivity of sample # 1 for the field aligned parallel to conducting layers obtained from field sweeps at different temperatures. Inset: temperature dependence of the zero-field resistance R_0 (thick line) and the resistances of the coherent, $R_c \propto 1/\sigma_c$, (circles) and incoherent, $R_i \propto 1/\sigma_i$, (triangles) channels, see text.

Here, the first term on the right-hand side is the coherent Boltzmann conductivity depending on both the strength and orientation of a magnetic field [24, 25]. In a field parallel to layers it decreases proportional to $(\omega_c\tau)^\alpha$ with $1 \leq \alpha \leq 2$ and, at a high enough field, the second term in Eq. (1) becomes dominant. We associate the latter with incoherent interlayer charge transfer. In agreement with previous observations [13], the incoherent conductivity is insensitive to the inplane magnetic field, however, it does depend on the field component B_\perp perpendicular to layers. This is why the resistance increases, as the field is tilted from the direction parallel to layers [3 T and 15 T curves in Fig. 1(a)]. At high fields, the total conductivity is dominated by σ_i in a large angular interval around $\theta = \pm 90^\circ$, which leads to a scaling behavior of magnetoresistance: $R(B, \theta) = R(B \cos \theta)$ [13].

Evaluating the relative contribution of σ_i to the total zero-field conductivity $\sigma(0, T)$ of sample # 1 from the level, at which the curves in Fig. 2 come to saturation, and using the $R_0(T)$ data plotted in the inset of Fig. 2, one can extract separately the temperature dependences of the classical Boltzmann (empty circles in the inset) and incoherent (filled triangles) channels. Note that even the anomalous, incoherent channel shows a metallic behavior.

The two-channel model provides a natural explanation for the anomalous dip in the AMR found, at certain conditions, on very clean samples of α -(BEDT-TTF)₂KHg(SCN)₄. In such samples, the conductivity is dominated by σ_c as long as the inplane field component parallel to the open Fermi sheets is small. This

is, in particular, reflected in the shape of the small- φ AMR of sample # 2 shown in Fig. 1(b): the angular dependence in the vicinity of $\theta = \pm 90^\circ$ is rather flat and shows a narrow peak, revealing a coherent 3D Fermi surface [24]. When the inplane field component is turned from the a axis to the c axis, which is parallel to the open Fermi sheets, the coherent conductivity rapidly drops down [24]. Under these conditions, the incoherent channel σ_i may become important, which leads to the anomalous dip structure in the b^*c -rotation patterns of the AMR even for relatively clean samples [13]. In the same way can be interpreted the 90° dips observed in the AMR of clean samples of other highly anisotropic compounds, like (TMTSF)₂X with X=PF₆ [26] and ReO₄ [15] or β'' -(BEDT-TTF)₂SF₅CH₂CF₂SO₃ [16].

The proposed model also explains the temperature dependence of the crossover field B_c observed in the experiment on (TMTSF)₂PF₆ [18]. Indeed, while the contribution of the coherent channel decreases with increasing temperature, as seen from Fig. 2, it still remains significant at $T \sim 10$ K. At the same time, the scattering rate, which is proportional to the resistance of the coherent channel, grows by about an order of magnitude between 1.4 and 10 K (see inset in Fig. 2). Therefore, a much higher field is necessary at 10 K for "freezing out" σ_c and making the incoherent channel dominant in the field and angular dependence of magnetoresistance.

Turning to a possible origin of the incoherent conduction channel, its metallic behavior apparently comes into conflict with the existing theories of incoherent interlayer charge transfer (see [3, 4, 5, 6] and references therein) predicting an insulating temperature dependence. In addition, those theories do not account for the significant dependence of σ_i on magnetic field normal to layers. To comply with the experimental observations, we propose to consider elementary events of incoherent interlayer hopping via local centers, such as resonance impurities [3, 6], in combination with diffusive intralayer transfer from one hopping center to another. The essential requirement of our model is that the volume concentration of hopping centers n_i be small, so that the average distance l_i between them along the 2D layers is much larger than the inplane mean free path $l_\tau = v_F\tau$: $l_i = (n_i d)^{-1/2} \gg l_\tau$. This condition, being opposite to the model [3], looks reasonable, since the concentration of resonant impurities (i.e. those impurities which form an electron level with energy close to the Fermi energy) is definitely much lower than the concentration of all kinds of impurities. The current through each hopping center is limited by the resistance R_\perp , which contains two in-series elements:

$$R_\perp = R_{hc} + R_\parallel. \quad (2)$$

The first part, R_{hc} , is the hopping-center resistance itself, which is almost independent of magnetic field and can have a weak nonmetallic temperature dependence

$R_{\text{hc}}(T)$. The second part, R_{\parallel} , is the intralayer resistance, which comes out because the electrons must travel along the conducting layer over a distance $\sim l_i$. In the limit $l_i \gg l_{\tau}$, the 2D intralayer current density $\mathbf{j}(\mathbf{r})$ at each point is proportional to the electric field $\mathbf{E}(\mathbf{r})$ at this point: $j_{\alpha}(\mathbf{r}) = \sigma_{\alpha\beta} d E_{\beta}(\mathbf{r})$, where $\sigma_{\alpha\beta}$ is just the macroscopic 3D inplane conductivity. For simplicity, we consider an isotropic inplane conductivity: $\sigma_{\alpha\beta} = \sigma_{\parallel} \delta_{\alpha\beta}$.

Since the charge density does not change with time, the inplane current must satisfy $\text{div} \mathbf{j}(\mathbf{r}) = 0$ everywhere except the hopping center spots. In the vicinity of each hopping center, the current and electric field are roughly axially symmetric and given by

$$\mathbf{E}(\mathbf{r} - \mathbf{r}_i) = \frac{\mathbf{j}(\mathbf{r} - \mathbf{r}_i)}{\sigma_{\parallel} d} = \frac{I_0}{2\pi\sigma_{\parallel} d} \frac{(\mathbf{r} - \mathbf{r}_i)}{|\mathbf{r} - \mathbf{r}_i|^2}, \quad (3)$$

where I_0 is the current through the hopping center located at point \mathbf{r}_i . R_{\parallel} is determined by the inplane mean voltage drop between two successive hopping centers:

$$I_0 R_{\parallel}(T) \simeq 2 \int_{l_{\tau}}^{l_i} \mathbf{E}(r) dr = \frac{I_0 \ln(l_i/l_{\tau})}{\pi\sigma_{\parallel} d}. \quad (4)$$

As the lower cutoff in the integral (4) we take the mean free path l_{τ} , which neglects the resistance of the ballistic region $|\mathbf{r} - \mathbf{r}_i| < l_{\tau}$ around each impurity. Since the ballistic conductivity is much higher than the diffusive one, this approximation should work well, at least when $\ln(l_i/l_{\tau}) \gtrsim \ln(l_{\tau}/d)$.

The mean voltage drop between two adjacent conducting layers is $E_0 d = I_0 (R_{\text{hc}} + R_{\parallel})$, where E_0 is the external electric field perpendicular to the layers. The total current density in the interlayer direction is $j_t = I_0 n_i d = \sigma_i E_0$, yielding the interlayer conductivity:

$$\sigma_i = \frac{\pi\sigma_{\parallel} n_i d^3}{\pi d \sigma_{\parallel} R_{\text{hc}} + \ln(l_i/l_{\tau})}. \quad (5)$$

The present simple model can be generalized by including the distribution of the hopping centers $n[R_{\text{hc}}(T)]$ and performing integration over $R_{\text{hc}}(T)$. The exact result will depend on the particular physical model of the hopping centers. In the trivial case of short-circuiting the layers (e.g., by dislocations), $R_{\text{hc}} \approx 1/d\sigma_{\parallel}$ and σ_i should be just proportional to the intralayer conductivity. The fact that the temperature dependence of the incoherent channel is considerably weaker than that of the coherent one (inset in Fig. 2), implies that R_{hc} is larger than $1/d\sigma_{\parallel}$ and only slightly varies with (or is independent of) temperature. Such conditions can be fulfilled if the hopping occurs via resonance impurities [3]. Further, both R_{hc} and $1/\sigma_{\parallel}$ are largely insensitive to the inplane magnetic field in the incoherent regime whereas the significant dependence on the out-of-plane field component obviously comes from the intralayer conductivity. Thus, the proposed mechanism is consistent with the main features of the incoherent channel observed in the experiment.

In conclusion, we have shown that the anomalous behavior of the angle-dependent interlayer magnetoresistance in the highly anisotropic layered metal α -(BEDT-TTF)₂KHg(SCN)₄ can be described by parallel contribution of two conduction channels, σ_c and σ_i , providing, respectively, coherent and incoherent interlayer charge transfer. A sufficiently high inplane component of magnetic field changes the proportion of σ_c and σ_i in favor of the latter, thus causing an apparent dimensional crossover. However, by contrast to the field-induced confinement scenario [19], this crossover does not imply a change in the dynamic properties of charge carriers. The proposed model is able to explain not only the observed crossover but also anomalous features found in other layered metals situated in the transient region between the fully coherent and incoherent transport regimes.

The work was supported in part by DFG-RFBR Grant No. 436 RUS 113/926, by MK-4105-2007.2 and RFBR 06-02-16551.

-
- [1] R. H. McKenzie and P. Moses, Phys. Rev. Lett. **81**, 4492 (1998).
 - [2] N. Kumar and A. M. Jayannavar, Phys. Rev. B **45**, 5001 (1992).
 - [3] D. B. Gutman and D. L. Maslov, Phys. Rev. Lett. **99**, 196602 (2007); Phys. Rev. B **77**, 035115 (2008).
 - [4] U. Lundin and R. H. McKenzie, Phys. Rev. B **68**, 081101(R) (2003).
 - [5] A. F. Ho and A. J. Schofield, Phys. Rev. B **71**, 045101 (2005).
 - [6] A. A. Abrikosov, Physica C **317-318**, 154 (1999).
 - [7] A. N. Lavrov, M. Y. Kameneva, and L. P. Kozeeva, Phys. Rev. Lett. **81**, 5636 (1998).
 - [8] C. H. Wang, X. H. Chen, J. L. Luo, G. T. Liu, X. X. Lu, H. T. Zhang, G. Y. Wang, X. G. Luo, and N. L. Wang, Phys. Rev. B **71**, 224515 (2005).
 - [9] L. Buravov, N. Kushch, V. Merzhanov, M. Osherov, A. Khomenko, and E. Yagubskii, J. Phys. I **2**, 1257 (1992).
 - [10] T. Valla, P. D. Johnson, Z. Yusof, B. Wells, Q. Li, S. M. Loureiro, R. J. Cava, M. Mikami, Y. Mori, M. Yoshimura, et al., Nature **417**, 627 (2002).
 - [11] J. G. Analytis, A. Ardavan, S. J. Blundell, R. L. Owen, E. F. Garman, C. Jeynes, and B. J. Powell, Phys. Rev. Lett. **96**, 177002 (2006).
 - [12] V. N. Zverev, A. I. Manakov, S. S. Khasanov, R. P. Shibaeva, N. D. Kushch, A. V. Kazakova, L. I. Buravov, E. B. Yagubskii, and E. Canadell, Phys. Rev. B **74**, 104504 (2006).
 - [13] M. V. Kartsovnik, D. Andres, S. V. Simonov, W. Biberauer, I. Sheikin, N. D. Kushch, and H. Müller, Phys. Rev. Lett. **96**, 166601 (2006).
 - [14] G. M. Danner and P. M. Chaikin, Phys. Rev. Lett. **75**, 4690 (1995).
 - [15] H. Kang, Y. J. Jo, S. Uji, and W. Kang, Phys. Rev. B **68**, 132508 (2003).
 - [16] J. Wosnitzer, J. Hagel, J. S. Qualls, J. S. Brooks, E. Balthes, D. Schweitzer, J. A. Schlueter, U. Geiser,

- J. Mohtasham, R. W. Winter, et al., Phys. Rev. B **65**, 180506(R) (2002).
- [17] M. Kuraguchi, E. Ohmichi, T. Osada, and Y. Shiraki, Synth. Met. **133-134**, 113 (2003).
- [18] E. I. Chashechkina and P. M. Chaikin, Phys. Rev. Lett. **80**, 2181 (1998).
- [19] S. P. Strong, D. G. Clarke, and P. W. Anderson, Phys. Rev. Lett. **73**, 1007 (1994); D. G. Clarke and S. P. Strong, Adv. Phys. **46**, 545 (1997).
- [20] M. V. Kartsovnik, D. Andres, and W. Biberacher, C. R. Chimie **10**, 6 (2007).
- [21] H. Mori, S. Tanaka, M. Oshima, G. Saito, T. Mori, Y. Maruyama, and H. Inokuchi, Bull. Chem. Soc. Jpn. **63**, 2183 (1990).
- [22] D. Andres, M. V. Kartsovnik, W. Biberacher, K. Neumaier, I. Sheikin, and H. Müller, Arxiv:0801.2696; unpublished.
- [23] A careful examination reveals a slight, $\simeq 1\%$, parabolic increase of conductivity at high fields, for $T = 1.4$ and 4 K. We will not consider this small effect here.
- [24] M. V. Kartsovnik, Chem. Rev. **104**, 5737 (2004).
- [25] This term also accounts for the so-called "weakly incoherent" regime [1] when the electron momentum is only defined within layers but is conserved in the elementary event of interlayer tunneling.
- [26] W. Kang, T. Osada, Y. J. Jo, and H. Kang, Phys. Rev. Lett. **99**, 017002 (2007).