

# Evidence for Oxygen Holes due to $d$ - $p$ Rehybridization in Thermoelectric $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$

Y. Ishida,<sup>1</sup> T. Baba,<sup>1</sup> R. Eguchi,<sup>1</sup> M. Matsunami,<sup>1</sup> M. Taguchi,<sup>1</sup> A. Chainani,<sup>1</sup>

Y. Senba,<sup>2</sup> H. Ohashi,<sup>2</sup> Y. Okamoto,<sup>3</sup> H. Takagi,<sup>4</sup> and S. Shin<sup>1,3</sup>

<sup>1</sup>RIKEN SPring-8 Center, Sayo, Sayo, Hyogo 679-5148, Japan

<sup>2</sup>JASRI/SPring-8, Sayo, Sayo, Hyogo 679-5198, Japan

<sup>3</sup>ISSP, University of Tokyo, Kashiwa-no-ha, Kashiwa, Chiba 277-8561, Japan

<sup>4</sup>RIKEN, The Institute for Physical and Chemical Research, Wako, Saitama 351-0198, Japan

(Dated: September 14, 2021)

Soft-x-ray photoemission and absorption spectroscopies are employed to investigate the electronic structures of  $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$ . Similarly to the layered cobaltates such as  $\text{Na}_{1-x}\text{CoO}_2$ , a valence-band satellite feature (VBS) occurs at higher binding energy to the O  $2p$  band. We find that the VBS resonates at the O  $1s$  edge. Additionally, core absorption shows clear  $x$  dependence in the O  $1s$  edge rather than in the Rh  $3p$  edge. These results indicate that the holes in the initial state mainly have O  $2p$  character presumably due to  $d$ - $p$  rehybridizations affected by  $\text{Sr}^{2+}$  vacancy potentials. The resultant inhomogeneous charge texture may have impact on the TE transport properties at low  $x$ .

PACS numbers:

The search for efficient thermoelectric (TE) materials is extensively pursued with the aim at practical applications such as TE batteries and Peltier refrigerators [1]. Since metallic materials had been considered to exhibit poor TE performance [1], it was a surprise that a low-resistive layered cobaltate  $\text{Na}_{1-x}\text{CoO}_2$  ( $x < 0.5$ ) exhibited large TE power ( $Q$ ) at high temperatures [2, 3]. The cobaltates have gained further interest as exhibiting rich phase diagram [4] including superconductivity [5] and 3D magnetism [6, 7]. The largeness of  $Q$  has been discussed from a band-theoretical viewpoint [8, 9, 10, 11] or from a correlated viewpoint [12, 13, 14, 15], or from a viewpoint that there is a coherent-to-incoherent crossover in the low-energy excitations with increasing  $T$  [16, 17]. Furthermore, interesting Na orderings [18, 19] that affect the electronic properties [20, 21, 22] have been reported, but their impact on the TE properties is not clear at present.

From a band-theoretical viewpoint, the valence band of  $\text{NaCoO}_2$  consists of a filled  $t_{2g}$  band positioned just below the chemical potential ( $\mu$ ) and an O  $2p$  band at higher binding energy ( $E_B$ ) as schematically shown in the upper panel of Fig. 1(a). With  $\text{Na}^+$  deintercalation,  $\mu$  is shifted into the  $t_{2g}$  band, and holes of mainly  $t_{2g}$  character are introduced into the triangular lattice of  $\text{Co}^{3+}$  ions. Valence-band spectra of  $\text{Na}_{0.7}\text{CoO}_2$  recorded by photoemission spectroscopy (PES) indeed show the  $t_{2g}$  and the O  $2p$  bands, but in addition, there is a valence-band satellite feature (VBS) at  $E_B \sim 11$  eV [23] as schematically shown in the lower panel of Fig. 1(a). Similar VBSs occur in other layered cobaltates such as  $\text{LiCoO}_2$  [24] and  $\text{Ca}_3\text{Co}_4\text{O}_9$  [9] (VBSs in TE Bi-Sr-Co-O system are obscured by Bi  $6s$  states at  $E_B \sim 11$  eV [25]). Thus, the VBS is a ubiquitous feature in the TE cobaltates, which is missing in the band-theoretical density of states (DOS).

Herein, we investigate element-specific electronic structures of  $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$  [26] using soft-x-ray absorption (XAS) and resonant PES.  $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$  is structurally and electronically analogous to  $\text{Na}_{1-x}\text{CoO}_2$ : hole carriers are introduced into the layered triangular lattice of

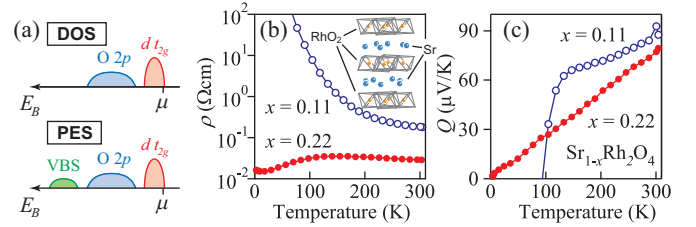


FIG. 1:  $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$ , an analogue of  $\text{Na}_{1-x}\text{CoO}_2$ . (a) Electronic structure. The band theoretical DOSs of the cobaltates and the rhodates exhibit  $t_{2g}$  and O  $2p$  bands, but the valence-band PES spectra additionally exhibit VBSs. Resistivity (b) and TE power (c) of  $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$  as functions of temperature. The crystal structure of  $\text{SrRh}_2\text{O}_4$  is shown in the inset of (b).

low-spin Rh ions (nominally  $t_{2g}^6$ ) through  $\text{Sr}^{2+}$  deintercalation [inset of Fig. 1(b)] to show insulator-to-metal transition at  $x \sim 0.2$  [Fig. 1(b)], and the  $x = 0.22$  sample shows  $Q \sim 70 \mu\text{V/K}$  at 300 K [Fig. 1(c)] [26]. Similarly to the cobaltates [9, 23, 24], we find a VBS in  $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$ . Moreover, the VBS resonates at the O  $1s$  edge followed by O  $1s2p2p$  Auger emissions, providing strong constraints on its origin. We also find clear  $x$  dependence in the O  $1s$  XAS rather than in the Rh  $3p$  XAS. The results indicate that holes in  $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$  have strong O  $2p$  character presumably due to so-called  $d$ - $p$  rehybridizations [27, 28, 29, 30] that redistribute the holes from  $d$  states to  $p$  states beyond a rigid-band-shift picture.

Single-phase well-sintered  $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$  ( $x = 0.11$  and  $0.22$ ) were prepared by a conventional solid state reaction as described elsewhere [26]. The resistivity ( $\rho$ ) and  $Q$  of the samples [Fig. 1(b) and (c), respectively] nicely reproduced those reported previously [26]. XAS and PES were performed at BL17SU of SPring-8 equipped with a VG Scienta SES2002 analyzer [31]. Sample surfaces were obtained by fracturing the samples inside the spec-

trometer under ultrahigh vacuum ( $< 5 \times 10^{-8}$  Pa). XAS spectra were recorded at 300 K in the total electron yield method. PES spectra were recorded at 50 K at  $\sim 250$ -meV energy resolution and  $E_B$  was referenced to  $\mu$  of Au in contact with the sample and the analyzer. PES spectra were normalized to the incident photon flux.

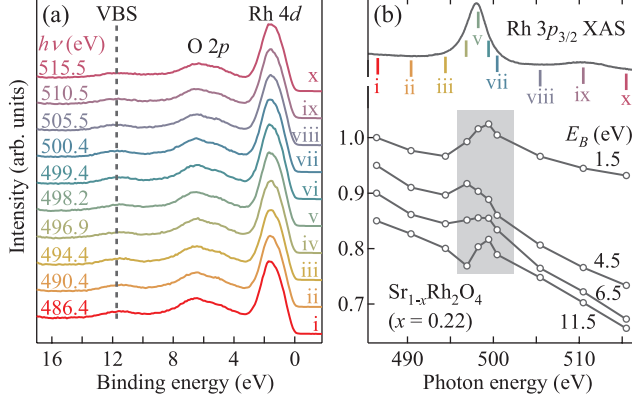


FIG. 2: Rh  $3p$ - $4d$  resonant PES of  $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$  ( $x=0.22$ ). (a) Valence-band spectra recorded across the Rh  $3p_{3/2}$  edge. (b) CIS spectra and Rh  $3p_{3/2}$  XAS. CIS spectra are normalized to the intensity at 486.4 eV and have arbitrary offsets. The labels (i-x) on the spectra in (b) correspond to the photon energies indicated by bars on the Rh  $3p_{3/2}$  XAS in (c).

Figure 2(a) shows valence-band spectra of  $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$  ( $x=0.22$ ) recorded across the Rh  $3p_{3/2}$  edge. We find a VBS at  $E_B \sim 11.7$  eV, a feature missing in the LDA DOS [32], as well as the Rh  $4d$  and the O  $2p$  bands centered at  $E_B \sim 1.5$  and 6 eV, respectively. Figure 2(b) shows constant-initial-state (CIS) spectra at  $E_B = 1.5, 4.5, 6.5,$  and 11.5 eV. One can see resonant enhancement of Rh  $4d$  states at the Rh  $3p_{3/2}$  edge [shaded area in Fig. 2(b)] in all features including the VBS (CIS at  $E_B = 11.5$  eV). This indicates that the Rh  $4d$  weight is spread over a wide energy range and that the VBS has some Rh  $4d$  character. The presence of the Co  $3d$  character in the VBSs of the cobaltates was similarly confirmed through Co  $3d$  resonant PES [9, 23, 24].

Next, we performed resonant PES at the O  $1s$  edge to obtain information about the O  $2p$  states. Figure 3(a) and (b) show, respectively, the valence-band spectra recorded in the vicinity of the O  $1s$  edge and the difference to the off-resonant spectra recorded at  $h\nu = 523.0$  eV. One can see that the VBS resonates at  $h\nu = 527.5$  eV, and subsequently, O  $1s2p2p$  Auger peak emerges from the vicinity of the VBS. The results indicate that the final state of the 11.7-eV VBS is similar to that of the O  $1s2p2p$  Auger emission, namely, the O  $2p$ -two-hole final state [see schematic in Fig. 3(a)]. This interpretation is the same as that of the 6-eV satellite of Ni identified to a Ni  $3d$ -two-hole final state [33]. In order to reach the O  $2p$  two-hole final state by photoemission, the initial state should contain an electronic configuration that has a single hole in the O  $2p$  state. We here-

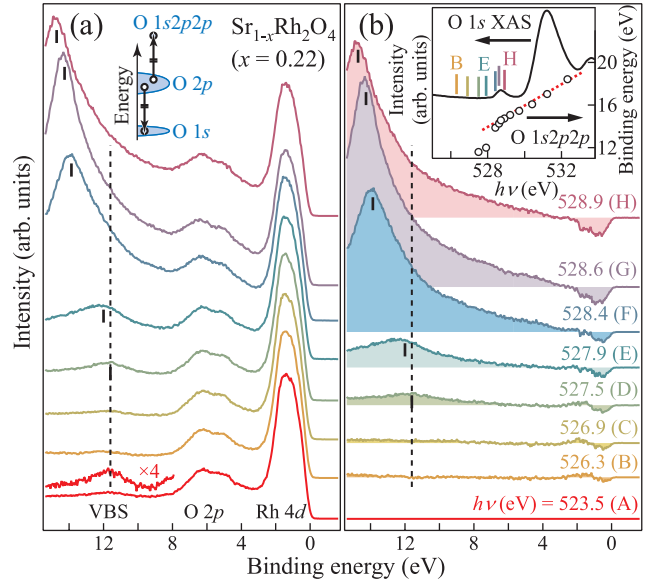


FIG. 3: Valence-band spectra of  $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$  ( $x=0.22$ ) recorded across the O  $1s$  edge. (a) Valence-band spectra recorded in the vicinity of the O  $1s$  edge. Inset shows a schematic of the final state of an O  $1s2p2p$  Auger-electron emission. (b) Difference spectra to the 523.0-eV spectrum. The labels (A-H) on the spectra correspond to the photon energies indicated on the O  $1s$  XAS in the inset in (b). The dotted vertical lines indicate the 11.7-eV VBS, and the bars indicate the O  $1s2p2p$  Auger peaks. The O  $1s2p2p$  Auger peak positions are plotted in the inset in (b), in which the dotted line indicates the constant kinetic energy.

after denote the initial oxygen-hole configuration as  $p_v^5$ . We note that the  $p_v^5$  state is different from the ligand-hole states of the configuration-interaction  $\text{CoO}_6$  cluster-model analyses [34, 35], since the  $p_v^5$  state is considered to be affected by the cation vacancy potentials [36] (discussed later). At  $h\nu \geq 528.7$  eV, the O  $1s2p2p$  Auger peak position is shifted to higher  $E_B$  since the kinetic energy of an O  $1s2p2p$  Auger electron is independent of  $h\nu$  [inset in Fig. 3(c)]. The resonant peak position at  $h\nu = 527.5$  eV slightly deviates from the constant kinetic energy of the normal O  $1s2p2p$  Auger, perhaps since the  $p_v^5$  configuration is mixed to some  $d$ -hole configurations as inferred from the Rh  $4d$  resonant PES [Fig. 2].

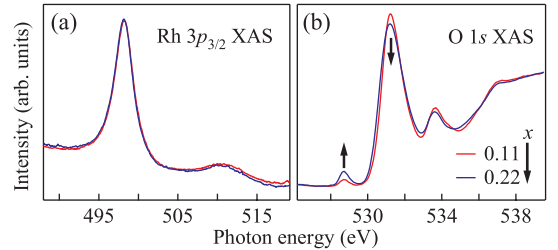


FIG. 4: Rh  $3p_{3/2}$  (a) and O  $1s$  (b) XAS. The arrows in (b) indicate the change with increasing  $x$ .

Evidence for oxygen holes in the initial state is also found in the XAS as shown in Fig. 4. With increasing  $x$ , the height of the prepeak feature in the O 1s XAS at  $h\nu=528.7\text{eV}$  becomes large and that of the main peak at  $h\nu=531.2\text{eV}$  becomes small (for each composition, the line shape at  $h\nu < 533\text{eV}$  was reproducible for 3 fractures). On the other hand, the Rh 3p XAS is hardly changed with  $x$ . Since the O 1s prepeak intensity is almost in proportional to  $x$ , we assign it to Sr-vacancy induced states mainly having O 2p character, so that the prepeak is assigned to  $(1s)^2(2p_v^5) \rightarrow (1s)^1(2p^6)$ . The spectral-weight transfer seen in O 1s XAS is often taken as a signature of strong electron correlation [34]. In the XAS studies of  $(\text{Li}/\text{Na})_{1-x}\text{CoO}_2$  [37, 38, 39], main changes with  $x$  occurred in the O 1s XAS rather than in the Co 2p XAS. Thus, oxygen holes in the initial state are common features in the TE rhodates and cobaltates.

The oxygen holes in  $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$  revealed by resonant PES and XAS at the O 1s edge indicate that the electronic-structure evolution with  $x$  goes beyond a rigid-band-shift picture. Otherwise,  $\mu$  would shift with increasing  $x$  into the Rh 4d band resulting in holes that mainly have Rh 4d character. The spectral weight should therefore be redistributed with increasing  $x$ , most likely due to  $d$ - $p$  rehybridization [27, 28, 29, 30]: as evidenced from the charge densities calculated [40] for  $\text{Li}_{1-x}\text{CoO}_2$  [27, 28] and  $\text{Na}_{1-x}\text{CoO}_2$  [29], the holes introduced via Li/Na deintercalation are not homogeneously distributed in the Co layers but reside at oxygen sites neighboring the Li/Na vacancies, i.e., the cation vacancy potential binds the holes to form the  $p_v^5$  state [28]. The charge density at a Co site was nearly unchanged with increasing  $x$  [27, 28, 29], since the  $t_{2g}$  holes were dressed by  $e_g$  electrons transferred from the O 2p states through the  $d$ - $p$  rehybridization. The essence of the charge rearrangement with doping can be captured in a simple model, namely, transition-metal impurities in semiconductors [30, 41]. The rigidity of the Rh 3p XAS line shape with  $x$  [Fig. 4(a)] is thus considered as a fingerprint that the  $d$ - $p$  rehybridization is self-regulating the local charge density about the Rh site to a nearly constant value.

A striking difference between the O 1s XAS of  $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$  and those of  $(\text{Na}/\text{Li})_{1-x}\text{CoO}_2$  [34, 37, 38, 39] is that the  $x$ -dependent prepeak in the former is well separated from the main peak [Fig. 4(b)], whereas those in the latter are merging into the main peaks. This can be understood that the degree of localization of the  $p_v^5$  state is affected by the strength of the cation vacancy potentials. Since the divalent  $\text{Sr}^{2+}$  vacancy potential is stronger than those of the monovalent  $\text{Li}^+/\text{Na}^+$ , the holes are more strongly bound around the vacancies in the former than in the latter [28]. Hence, the  $p_v^5$  state appears to be more localized in  $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$ , so that the prepeak appears to be a sharp level. The localized character of the  $p_v^5$  state is supported by an  $^{17}\text{O}$  NMR study of  $\text{Na}_{1-x}\text{CoO}_2$  ( $x=0.28$ ), revealing that  $\sim 30\%$  of the oxygen sites carry local magnetic moments [42]. We naturally identify these magnetic oxygens to have the  $p_v^5$

configuration.

It should be noted that a VBS was also observed in stoichiometric  $\text{LiCoO}_2$  having no Li vacancies [24]. Through a configuration-interaction cluster-model analysis, the VBS of  $\text{LiCoO}_2$  was attributed to large  $d$ - $p$  hybridization and orbital degeneracy of the  $d$  states [24]. Thus, the  $d$ - $p$  rehybridization with doping effectively occurs when the parent compound has large  $d$ - $p$  hybridization and orbital degeneracy. Large  $d$ - $p$  hybridization generally occurs in  $t_{2g}$  electron system having unoccupied  $e_g$  orbitals (this includes  $d^0$  insulators [43, 44]). In fact,  $d$ - $p$  rehybridization was reported to occur when carriers are doped into  $\text{SrTiO}_3$ , a nominally  $d^0$  insulator [45]. It is also interesting that a layered  $\text{Cu}_x\text{TiSe}_2$ , which shows TE properties as good as the cobaltates [46], is also considered to exhibit  $d$ - $p$  rehybridization [47]. Here, the hybridization of the Se 4p states into the unoccupied Ti 3d states opens the channel of  $d$ - $p$  rehybridization, and  $\text{Cu}^+$  act as a source of ‘‘occupancy’’ potential. Thus, the TE cobaltates, rhodates, and the intercalated Ti dichalcogenides can be categorized to those exhibiting  $d$ - $p$  rehybridization affected by the cation vacancy/occupancy potentials.

Since the holes in the initial state are not homogeneously distributed in the Rh layers as expected in a rigid-band-shift picture but are further redistributed due to the  $d$ - $p$  rehybridizations and the Sr vacancy potentials, the charge density is considered to be nonperiodic compared to the crystallographic periodicity of  $\text{SrRh}_2\text{O}_4$  (please see the nonperiodic charge densities calculated for  $(\text{Li}/\text{Na})_{1-x}\text{CoO}_2$  [27, 28, 29].) Thus, it would be necessary to realize that the transport is occurring on such an inhomogeneous charge texture with O 2p holes bound to cation vacancies. For example, as was pointed out in [32], the nonmetallic conduction at  $x \lesssim 0.2$  of  $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$  [26] can be viewed as a variable-range hopping, i.e., the low-energy excitations relevant to the transport show weak localizations as they are subject to randomness [48]. The mobility-edge crossing occurring at  $x \sim 0.2$  in  $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$  is reasonably larger than that of  $\text{Na}_{1-x}\text{CoO}_2$  occurring at  $x < 0.1$  [3], since the vacancy potential of  $\text{Sr}^{2+}$  is stronger than that of  $\text{Na}^+$ , although single crystal data will be helpful for further investigations [49]. Another point to be noted is, when a nonmetallic transport is realized by randomness in a spin-orbitally degenerate system such as in  $\text{Fe}_3\text{O}_{4-x}\text{F}_x$  [50], a hump feature occurs at  $T \sim 100\text{K}$  in a  $Q$ - $T$  curve [49, 50, 51]. This feature is very similar to the enhanced  $Q$  at  $\sim 100\text{K}$  in metallic  $\text{Na}_{1-x}\text{CoO}_2$  at low  $x$  [3], which is considered to be on the verge of the metal-nonmetal transition. Further studies are necessary to clarify the relationship between the randomness and the transport properties in the rhodates and the cobaltates particularly at low  $x$ .

In summary, we have performed resonant PES and XAS on  $\text{Sr}_{1-x}\text{Rh}_2\text{O}_4$  and find that the holes have strong O 2p character. The VBS, which commonly occurs in the TE cobaltates, is proven from resonant PES at the O 1s edge to be a fingerprint of the O 2p holes in the

initial state. The results indicate a non-rigid-band evolution of the electronic structure with doping due to the  $d$ - $p$  rehybridization affected by the cation vacancy potentials [27, 28, 29, 30], resulting in an inhomogenous charge texture that may affect the transport properties at low

$x$ .

Y.I. acknowledge A. Mizutani, K. Sugiura, H. Ohta, and I. Matsuda for informative discussion and T. Mizokawa for critical reading of the manuscript.

- 
- [1] G. Mahan, B. Sales, and J. Sharp, *Physics Today* **42** (1997).
- [2] I. Terasaki, Y. Sasago, and K. Uchinokura, *Phys. Rev. B* **56**, R12685 (1997).
- [3] M. Lee *et al.*, *Nat. Mater.* **5**, 537 (2006).
- [4] M. L. Foo, Y. Wang, S. Watauchi, H. W. Zandbergen, T. He, R. J. Cava, and N. P. Ong, *Phys. Rev. Lett.* **92**, 247001 (2004).
- [5] K. Takada, H. Sakurai, E. Takayama-Muromachi, F. Izumi, R. A. Dilanian, and T. Sasaki, *Nature* **422**, 53 (2003).
- [6] J. Sugiyama, J. H. Brewer, E. J. Ansaldo, B. Hitti, M. Mikami, Y. Mori, and T. Sasaki, *Phys. Rev. B* **69**, 214423 (2004).
- [7] S. P. Bayrakci *et al.*, *Phys. Rev. Lett.* **94**, 157205 (2005).
- [8] D. J. Singh, *Phys. Rev. B* **61**, 13397 (2000).
- [9] T. Takeuchi *et al.*, *Phys. Rev. B* **69**, 125410 (2004).
- [10] H. J. Xiang and D. J. Singh, *Phys. Rev. B* **76**, 195111 (2007).
- [11] K. Kuroki and R. Arita, *J. Phys. Soc. Jpn.* **76**, 083707 (2007).
- [12] W. Koshibae, K. Tsutsui, and S. Maekawa, *Phys. Rev. B* **62**, 6869 (2000).
- [13] Y. Wang, N. S. Rogado, R. J. Cava, and N. P. Ong, *Nature* **423**, 425 (2003).
- [14] O. I. Motrunich and P. A. Lee, *Phys. Rev. B* **69**, 214516 (2004).
- [15] J. O. Haerter, M. R. Peterson, and B. S. Shastry, *Phys. Rev. Lett.* **97**, 226402 (2006).
- [16] P. Limelette, S. Hebert, V. Hardy, R. Fresard, C. Simon, and A. Maignan, *Phys. Rev. Lett.* **97**, 046601 (2006).
- [17] Y. Ishida, H. Ohta, A. Fujimori, and H. Hosono, *J. Phys. Soc. Jpn.* **76**, 103709 (2007).
- [18] M. Roger *et al.*, *Nature* **445**, 631 (2007).
- [19] F. C. Chou *et al.*, *Phys. Rev. Lett.* **101**, 127404 (2008).
- [20] C. A. Marianetti and G. Kotliar, *Phys. Rev. Lett.* **98**, 176405 (2007).
- [21] M. Gao, S. Zhou, and Z. Wang, *Phys. Rev. B* **76**, 180402(R) (2007).
- [22] M.-H. Julien *et al.*, *Phys. Rev. Lett.* **100**, 096405 (2008).
- [23] M. Z. Hasan *et al.*, *Phys. Rev. Lett.* **92**, 246402 (2004).
- [24] J. van Elp, J. L. Wieland, H. Eskes, P. Kuiper, and G. A. Sawatzky, *Phys. Rev. B* **44**, 6090 (1991).
- [25] T. Mizokawa, L. H. Tjeng, P. G. Steeneken, N. B. Brookes, I. Tsukada, T. Yamamoto, and K. Uchinokura, *Phys. Rev. B* **64**, 115104 (2001).
- [26] Y. Okamoto, M. Nohara, F. Sakai, and H. Takagi, *J. Phys. Soc. Jpn.* **75**, 023704 (2006).
- [27] C. Wolverton and A. Zunger, *Phys. Rev. Lett.* **81**, 606 (1998).
- [28] C. A. Marianetti, G. Kotliar, and G. Ceder, *Nat. Mater.* **3**, 627 (2004).
- [29] C. A. Marianetti, G. Kotliar, and G. Ceder, *Phys. Rev. Lett.* **92**, 196405 (2004).
- [30] H. Raebiger, S. Lany, and A. Zunger, *Nature* **453**, 763 (2008).
- [31] H. Ohashi *et al.*, *AIP Conf. Proc.* **879**, 523 (2007).
- [32] G. B. Wilson-Short, D. J. Singh, M. Fornari, and M. Snewattana, *Phys. Rev. B* **75**, 035121 (2007).
- [33] C. Guillot *et al.*, *Phys. Rev. Lett.* **39**, 1632 (1977).
- [34] W. B. Wu, D. J. Huang, J. Okamoto, A. Tanaka, H.-J. Lin, F. C. Chou, A. Fujimori, and C. T. Chen, *Phys. Rev. Lett.* **94**, 146402 (2005).
- [35] T. Kroll, A. A. Aligia, and G. A. Sawatzky, *Phys. Rev. B* **74**, 115124 (2006).
- [36] Since the charge densities of  $\text{Li}_{1-x}\text{CoO}_2$  [27, 28] and  $\text{Na}_{1-x}\text{CoO}_2$  [29] are strongly affected by the cation vacancies, it is not *a priori* to adopt the symmetry of a  $\text{CoO}_6$  octahedra [34, 35] to understand the electronic structures of the cobaltates.
- [37] L. A. Montoro, M. Abbate, and J. M. Rosolen, *Electrochem. Solid-State Lett.* **3**, 410 (2000).
- [38] V. R. Galakhov *et al.*, *Phys. Rev. B* **74**, 045120 (2006).
- [39] T. Kroll, M. Knupfer, J. Geck, C. Hess, T. Schwieger, G. Krabbes, C. Sekar, and D. R. Batchelor, *Phys. Rev. B* **74**, 115123 (2006).
- [40] Even though LDA DOS cannot reproduce VBS since LDA does not treat dynamical correlations in the electron removal state [52], charge densities, which are initial-state properties and are considered to be less affected by dynamical correlations, are nicely explained by LDAs.
- [41] F. D. M. Haldane and P. W. Anderson, *Phys. Rev. B* **13**, 2553 (1976).
- [42] F. L. Ning and T. Imai, *Phys. Rev. Lett.* **94**, 227004 (2005).
- [43] K. Okada and A. Kotani, *J. Phys. Soc. Jpn.* **63**, 3176 (1994).
- [44] M. Umeda, Y. Tezuka, S. Shin, and A. Yagishita, *Phys. Rev. B* **53**, 1783 (1996).
- [45] Y. Ishida *et al.*, *Phys. Rev. Lett.* **100**, 056401 (2008).
- [46] G. Wu, H. X. Yang, L. Zhao, X. G. Luo, T. Wu, G. Y. Wang, and X. H. Chen, *Phys. Rev. B* **76**, 024513 (2007).
- [47] C. Umrigar, D. E. Ellis, D. Wang, H. Krakauer, and M. Posternak, *Phys. Rev. B* **26**, 4935 (1982).
- [48] N. F. Mott, *Metal-Insulator Transitions*, 2nd edition (Taylor & Francis, 1990).
- [49] K. Sugiura, H. Ohta, Y. Ishida, R. Huang, T. Saito, Y. Ikuhara, K. Nomura, H. Hosono, and K. Koumoto, *Appl. Phys. Express* **2**, 035503 (2009).
- [50] H. Graener, M. Rosenberg, T. E. Whall, and M. R. B. Jones, *Philos. Mag. B* **40**, 389 (1979).
- [51] I. P. Zvyagin, *The Hopping Thermopower in Hopping Transport in Solids*, edited by M. Pollak and B. Shklovskii, *Modern Problems in Condensed Matter Sciences Vol. 28* (North-Holland, Amsterdam, 1991).
- [52] J. Kunes, V. I. Anisimov, S. L. Skornyakov, A. V. Lukoyanov, and D. Vollhardt, *Phys. Rev. Lett.* **99**, 156404 (2007).