

Origin of Low-Energy Excitations in Charge-Ordered Manganites

E. ZHUKOVA^{1,2}, B. GORSHUNOV^{1,2}, T. ZHANG¹ ^(a), DAN WU¹, A.S. PROKHOROV²,
V.I. TORGASHEV³, E.G. MAKSIMOV⁴ and M. DRESSEL¹ ^(b)

¹ *1. Physikalisches Institut, Universität Stuttgart, Pfaffenwaldring 57, 70550 Stuttgart, Germany*

² *Prokhorov Institute of General Physics, Russian Academy of Sciences, Vavilova Str. 38, 119991 Moscow, Russia*

³ *Faculty of Physics, Southern Federal University, Zorge Str. 5, 344090 Rostov-on-Don, Russia*

⁴ *Lebedev Physics Institute, Russian Academy of Sciences, Leninsky prosp., 53, 119991, Moscow, Russia*

PACS 75.47.Lx – Manganites

PACS 71.45.Lr – Charge-density-wave systems

PACS 73.20.Mf – Collective excitations (including excitons, polarons, plasmons and other charge-density excitations)

PACS 75.50.Tt – Fine-particle systems; nanocrystalline materials

Abstract. - The low-energy excitations in the charge-ordered phase of polycrystalline $\text{La}_{0.25}\text{Ca}_{0.75}\text{MnO}_3$ are explored by frequency-domain terahertz spectroscopy. In the frequency range from 4 cm^{-1} to 700 cm^{-1} (energies 0.4 meV to 90 meV) and at temperatures down to 5 K, we do not detect any feature that can be associated with the collective response of the spatially modulated charge continuum. In the antiferromagnetically ordered phase, broad absorption bands appear in the conductivity and permittivity spectra around 30 cm^{-1} and 100 cm^{-1} which are assigned to former acoustic phonons optically activated due to a fourfold superstructure in the crystal lattice. Our results indicate that characteristic energies of collective excitations of the charge-ordered phase in $\text{La}_{0.25}\text{Ca}_{0.75}\text{MnO}_3$, if any, lie below 1 meV. At our lowest frequencies of only few wavenumbers a strong relaxation is observed above 100 K connected to the formation of the charge-ordered state.

Introduction. – Manganese oxides $R_{1-x}A_x\text{MnO}_3$ (with R being rare earth and A alkaline elements) represent a unique playground for investigating electronic correlation effects in solids because the competing interactions related to charge, spin, orbital and lattice degrees of freedom are of comparable strength, resulting in a rich phase diagram [1–3]. In recent years much effort has been devoted to the intriguing phenomenon of charge ordering (CO), which for $\text{La}_{1-x}\text{Ca}_x\text{MnO}_3$ in the concentrations range $0.5 \leq x \leq 0.85$ takes place at rather high temperatures. Below T_{CO} the system changes also its magnetic properties from a paramagnetic to an antiferromagnetic (AFM) state. It was suggested that the mixed-valence manganese ions dissociate into two subsystems with integer valences, Mn^{3+} and Mn^{4+} which occupy different atomic sites of the lattice, causing spatial stripes of commensurate doping with a period being a multiple of the lattice constant in the a direction [4–6]. Later it was found, however, that the charge modulation does not have full

amplitude and that the wavevector $\mathbf{q} = \mathbf{a}^*(1-x)$ is concentration dependent (\mathbf{a}^* is the reciprocal lattice vector) and not necessarily tied only to atomic sites [7–10].

Recently, it was suggested [11] that the ordering in manganites can be of Fröhlich-Peierls type leading to a charge density wave (CDW) [12]. Several observations seem to support this idea. Fermi-surface nesting [13] was observed, together with transport signatures of a CDW, such as nonlinear dc resistivity and broadband noise [14, 15]. Terahertz and infrared (IR) spectroscopic measurements on $\text{Nd}_{1-x}\text{Sr}_x\text{MnO}_3$, $\text{La}_{1-x}\text{Ca}_x\text{MnO}_3$ and $\text{Pr}_{1-x}\text{Ca}_x\text{MnO}_3$ have revealed resonances in the far-infrared range which are interpreted by the authors as collective modes arising from the CDW condensate [16, 17]. Although the idea seems intriguing [18] and applicable to other charge-ordered systems such as cuprates [19–22] or organics [23], more experiments are needed to verify a CDW state in charge-ordered manganites [24, 25]. Here we present investigations of the low-energy electro-dynamics of $\text{La}_{0.25}\text{Ca}_{0.75}\text{MnO}_3$ which clearly identify the low-frequency excitations simply as former acoustic phonons

^(a)E-mail: zhangtao@issp.ac.cn

^(b)E-mail: dressel@pi1.physik.uni-stuttgart.de

optically activated by folding of the Brillouin zone caused by a superstructure in the crystal lattice.

Experimental. – Polycrystalline samples of $\text{La}_{0.25}\text{Ca}_{0.75}\text{MnO}_3$ were prepared by sol-gel method as described in Ref. [27] where the grain size can be selected by annealing at different temperatures. The average particle diameter was determined by field-emission scanning microscopy and X-ray using Scherrer formula; the structure of the samples was characterized by X-ray diffraction. For the optical measurements, we prepared pellets of 10 mm diameter and thicknesses varying from approximately 0.1 to 0.6 mm. Optical studies were performed in the THz range using a coherent-source spectrometer in a Mach-Zehnder arrangement [28] that allows us to directly measure the complex conductivity $\hat{\sigma}(\nu)$ or complex permittivity $\hat{\epsilon}(\nu)$ at frequencies from $\nu = 1$ up to 50 cm^{-1} , in the temperature interval from 2 to 300 K and in magnetic field up to 8 T. On the same pellets of $\text{La}_{0.25}\text{Ca}_{0.75}\text{MnO}_3$ also the far-infrared reflectivity was measured up to 700 cm^{-1} using a Fourier transform infrared spectrometer in order to obtain the real parts of the conductivity $\sigma(\nu)$ and permittivity $\epsilon'(\nu)$ in a wide frequency interval from 4 up to 700 cm^{-1} .

Results. – In Fig. 1a the conductivity spectra of $\text{La}_{0.25}\text{Ca}_{0.75}\text{MnO}_3$ pellets with grains of 1 micrometer size are plotted for different temperatures. Above the charge-ordering temperature $T_{\text{CO}} \approx 240 \text{ K}$ the conductivity is metal-like, it is almost frequency independent below 30 cm^{-1} , and gradually decreases for higher frequencies. Beyond 200 cm^{-1} phonon features become dominant because incompletely screened by itinerant carriers.

When the sample is cooled below T_{CO} , the conductivity spectra change their character qualitatively, from metallic to dielectric. The values of $\sigma(\nu)$ drop drastically, especially at the lowest frequencies of few wavenumbers. The permittivity $\epsilon'(\nu)$ increases from negative values (at $T = 300 \text{ K}$) up to large positive values; the slope $d\epsilon'/d\nu$ becomes negative (cf. Fig. 3a). As demonstrated in the inset of Fig. 1a, in the range $T_N \approx 140 \text{ K} < T < T_{\text{CO}} \approx 240 \text{ K}$ the conductivity is thermally activated $\sigma(T) \propto \exp\{-E_{\text{act}}/k_B T\}$ with $E_{\text{act}} = 0.13 \text{ eV}$, indicating an energy gap $2\Delta = E_{\text{act}}$ (pseudogap for $T > T_{\text{CO}}$) in the density of states. It is generally accepted that this gap or pseudogap is caused by the long-range charge order below T_{CO} or by correspondent order-parameter fluctuations above T_{CO} [29].

In the AFM phase ($T < T_N$), an absorption band appears in the range 20 to 40 cm^{-1} getting more pronounced as the temperature is lowered. A close inspection of this band reveals two resonances located at frequencies 25 ± 3 and $38 \pm 3 \text{ cm}^{-1}$, which are basically temperature independent. When we reduce the grain size from 1000 to 40 nm, the band gradually disappears, as is demonstrated by Fig. 1b. In addition, a less intense and broader absorption band can be identified in the range $60 - 100 \text{ cm}^{-1}$. It is also more pronounced in the AFM phase, and looses

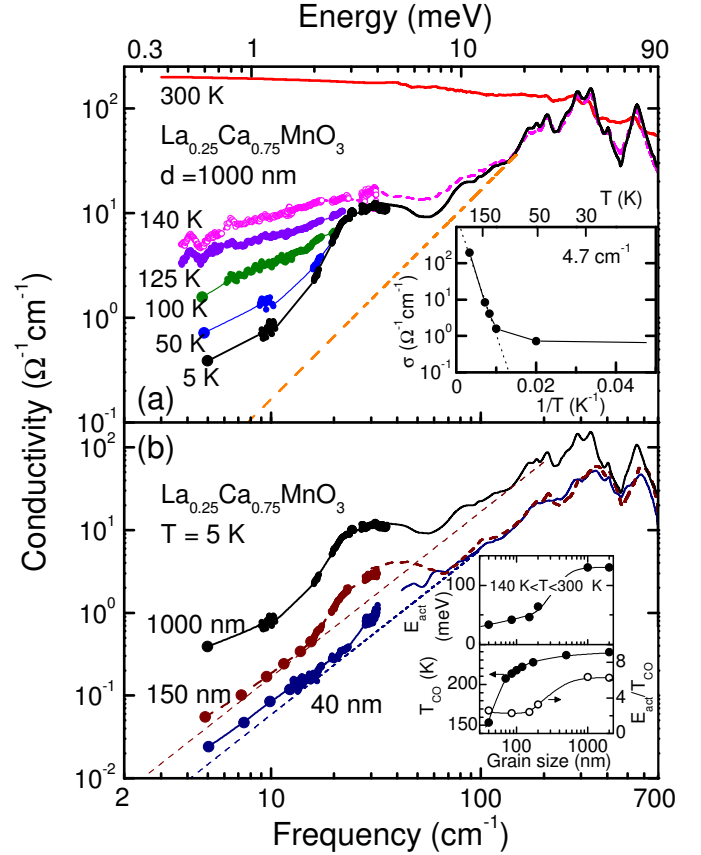


Fig. 1: (Color online) (a) Optical conductivity of $\text{La}_{0.25}\text{Ca}_{0.75}\text{MnO}_3$ plotted in a double-logarithmic fashion for various temperatures as indicated. The symbols correspond to data directly obtained by a Mach-Zehnder interferometer, solid and dashed lines are from reflectivity measurements; the lines below 40 cm^{-1} guide the eye. The thin dotted line represents the ν^2 behavior of the conductivity indicating the low-frequency tail of the lowest infrared phonon. The inset demonstrates in an Arrhenius plot the activated behavior of the low-frequency ($\nu = 4.7 \text{ cm}^{-1}$) conductivity with an activation energy 0.13 eV (dashed line). (b) Comparison of the low-temperature conductivity $\sigma(\nu)$ of $\text{La}_{0.25}\text{Ca}_{0.75}\text{MnO}_3$ samples consisting of different grain sizes, $d = 1000, 150,$ and 40 nm . The dependence of the activation energy E_{act} , the CO transition temperature T_{CO} and correlation strength $2\Delta/T_{\text{CO}}$ on the grain-size is plotted in the inset.

intensity in samples with smaller grains. At our lowest frequencies of only few wavenumbers a strong relaxation is observed above 100 K which vanishes as the temperature decreases $T \rightarrow 0$.

Discussion. – It is generally accepted that the simple picture based on ordering of Mn^{3+} - Mn^{4+} ions is too rough to account for all peculiarities of manganites. To explain the CO state with charge modulation of non-integer amplitude and (in general) incommensurate wavevector $\mathbf{q} = \mathbf{a}^*(1-x)$, a CDW ground state was proposed [14, 15, 24]. Kida *et al.* [16] assigned a low-frequency ($16 - 24 \text{ cm}^{-1}$) absorption peak observed in $\text{Pr}_{0.7}\text{Ca}_{0.3}\text{MnO}_3$ to a collec-

tive excitation (phason) of the CDW state. Along these lines, Nucara *et al.* [17] attributed the asymmetric bands, they recently detected between 15 and 60 cm^{-1} in a series of manganites including $\text{La}_{0.25}\text{Ca}_{0.75}\text{MnO}_3$, to a combination of CDW phason and amplitudon responses, and another peak below 10 cm^{-1} to a pinned CDW-phason.

In contrast to these suggestions and based on our comprehensive spectroscopic investigations of the low-frequency excitations in $\text{La}_{0.25}\text{Ca}_{0.75}\text{MnO}_3$ we show that there are no spectroscopic features at frequencies down to 4 cm^{-1} which could correspond to a collective response of the CO-condensate. We assign the resonance absorptions between 20 and 40 cm^{-1} and around 100 cm^{-1} to acoustic phonons that become optically active after the folding of the Brillouin zone due to evolution of a superstructure in the crystal lattice accompanying the charge and antiferromagnetic orderings. Indeed, X-ray studies of $\text{La}_{0.25}\text{Ca}_{0.75}\text{MnO}_3$ evidence that the orthorhombic unit cell quadruples along the a axis when cooled below T_{CO} [26], meaning that the high-temperature space group Pnma is transformed to $\text{P2}_1/\text{m}$. Consequently, the CO transition has to be described by an order parameter that is transformed according to the $\Sigma_1(\mathbf{q}_x = \mathbf{a}^*/4)$ irreducible representation of the space group Pnma . As a result of the $\text{Pnma} \leftrightarrow \text{P2}_1/\text{m}$ structural phase transition, the phonons with the wavevector $\mathbf{q}_x = \mathbf{a}^*/4$ and $\mathbf{q}_x = \mathbf{a}^*/2$ are folded to the Brillouin zone center (Γ -point) of the monoclinic $\text{P2}_1/\text{m}$ phase. They are split into two types of phonons – symmetric (gerade) and anti-symmetric (ungerade), relative to the center of inversion; in other words, they are split into the (g,u) pairs. The gerade modes (A_g and B_g), become optically Raman-active phonons, while the ungerade modes (A_u and B_u) form polarization waves and become IR-active. In the case of $\text{La}_{0.25}\text{Ca}_{0.75}\text{MnO}_3$ the infrared activity of the corresponding modes is promoted by a dipole moment produced by spatial charge disproportionation which has to include all ions of the new unit cell together with the valence difference on manganese ions.

The described transformation of phonon branches is qualitatively depicted in Fig. 2, in close resemblance with calculations of the phonon frequencies of undoped LaMnO_3 [30]. It now becomes obvious that the absorption band observed in $\text{La}_{0.25}\text{Ca}_{0.75}\text{MnO}_3$ at 20 – 40 cm^{-1} corresponds to the modes with the wave vector $\mathbf{q}_x = \mathbf{a}^*/4$, while the broad set of superimposed bands at frequencies around 100 cm^{-1} is associated with the Brillouin-zone-boundary modes of wave vectors $\mathbf{q}_x = \mathbf{a}^*/4$. Significant broadening of the phonon modes can be connected to the polycrystalline nature of the samples with all three crystallographic directions contributing to the optical response and with phases of other symmetries present below T_N , like a phase with the $3a$ superlattice [26]. The appearance of the broad band at 20 – 40 cm^{-1} only in the AFM phase and not right below T_{CO} agrees well with the temperature evolution of the weight fraction of the new $4a$ phase which starts to increase below T_{CO} but reaches its full strength only below T_N . Note that the magnetic origin

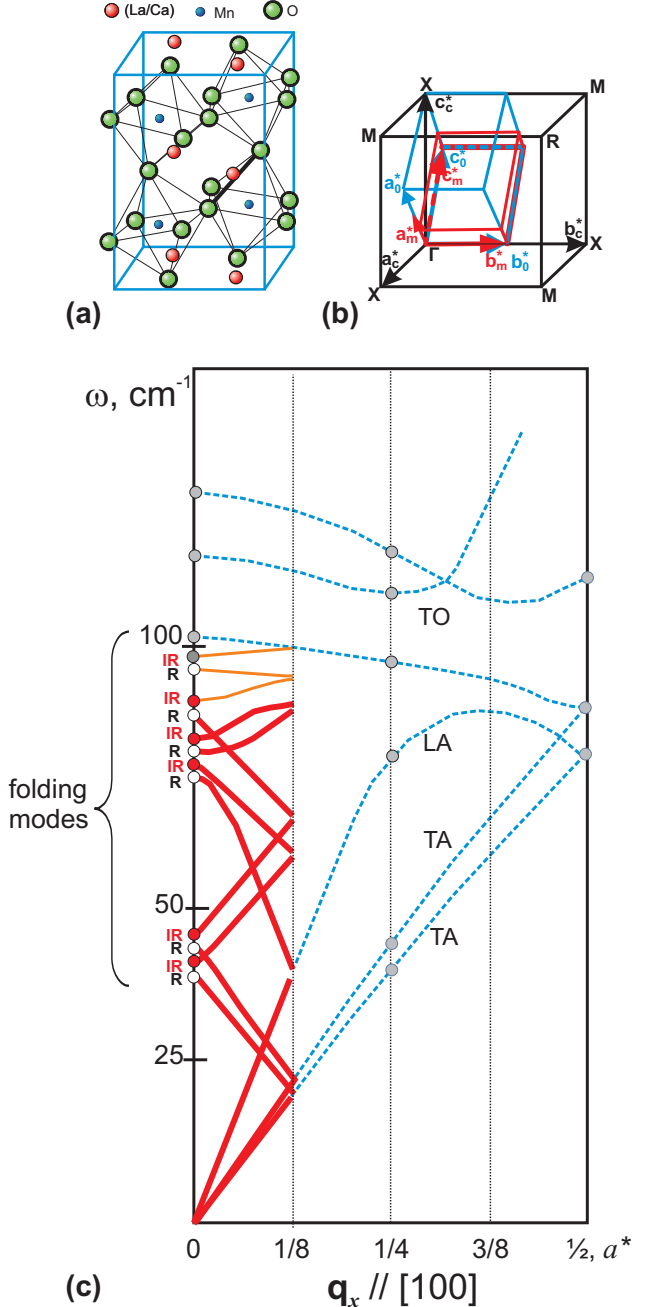


Fig. 2: (Color online) (a) Unit cell of $(\text{La,Ca})\text{MnO}_3$ in the orthorhombic Pnma phase. (b) Transformation of the Brillouin zone of a cubic perovskite-like unit cell at the $\text{Pm}3\text{m} \leftrightarrow \text{Pnma} \leftrightarrow \text{P2}_1/\text{m}$ phase transitions, leading to supercell of $4a^*$. (c) Qualitative scheme demonstrating the folding of the modes at the $\text{Pnma} \leftrightarrow \text{P2}_1/\text{m}$ phase transition. The acoustic phonons with $\mathbf{q}_x = \mathbf{a}^*/4$ and $\mathbf{q}_x = \mathbf{a}^*/2$ (grey dots) in Pnma structure are folded to the center of the monoclinic zone and become Raman- (open dots) and infrared-active (filled dots) optic modes. The band in the frequency range around 20 – 40 cm^{-1} is formed by modes with wavevector $\mathbf{q}_x = \mathbf{a}^*/4$, and the band around 100 cm^{-1} is formed by modes with wave vector $\mathbf{q}_x = \mathbf{a}^*/2$ from the Brillouin zone boundary. Certain contributions to the low-frequency part of the band around 100 cm^{-1} can come from the phonons with the wavevector $\mathbf{q}_x = \mathbf{a}^*/3$ (phase with supercell $3a$ [14]).

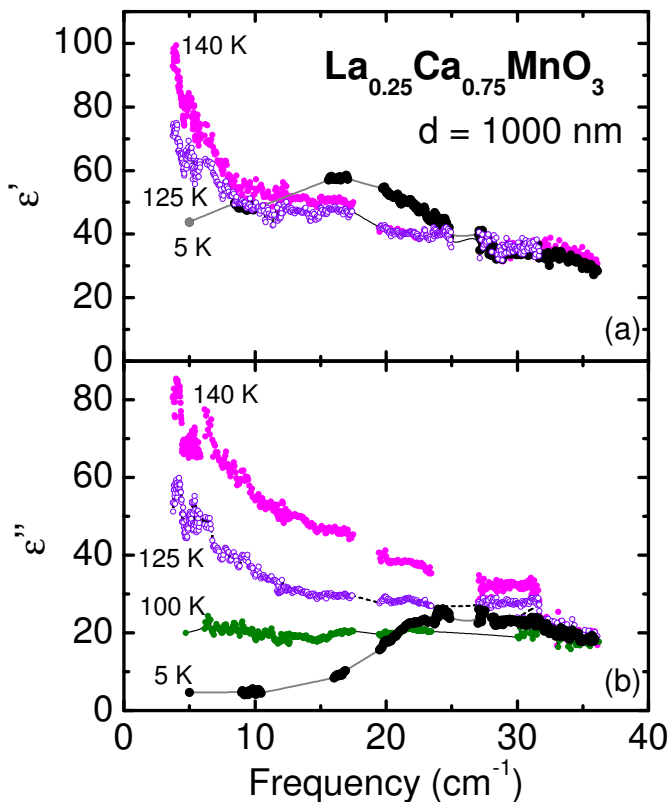


Fig. 3: (Color online) Low-frequency spectra of the (a) real and (b) imaginary parts of the dielectric permittivity, ϵ' and ϵ'' , of $\text{La}_{0.25}\text{Ca}_{0.75}\text{MnO}_3$ directly measured in a Mach-Zehnder geometry at different temperatures as indicated. The lines are guides to the eye.

of the band can definitely be ruled out because the AFM resonance modes are weaker by more than a factor of 100 and their resonance frequencies are strongly temperature dependent [31].

As seen from Fig. 1b, the phonon bands weaken gradually in samples with smaller grain size, indicating a suppression of the $4a$ -superlattice in small nano-crystallites. Reduction of grain sizes causes an intensity decrease, but not a full suppression of the CO gap 2Δ and correlation strength $2\Delta/T_{\text{CO}}$ (inset in Fig. 1b), in accordance with magnetic [32] and optical measurements [29], indicating weak coupling of charge and magnetic order parameters to the lattice. It would be of interest to investigate the low-frequency response and nano-size effects in manganites with other alkali-metal concentrations since x determines the stability of and the balance between the different interactions and also the frequency position of the folded phonon modes, according to the wave-vector of the lattice modulation $\mathbf{q} = \mathbf{a}^*(1-x)$ [8, 9, 33].

In Fig. 3 we present the pronounced relaxational behavior of the real and imaginary parts of the dielectric permittivity, $\hat{\epsilon}(\nu)$ observed at our lowest frequencies. The relaxation becomes weaker as the temperature is lowered and the dc conductivity decreases, indicating a close con-

nection to the itinerant charge carriers. The characteristic frequency $1/(2\pi\epsilon\tau_D)$ (with τ_D the relaxation time), at which the maximum of $\epsilon''(\nu)$ is seen in a simple Debye case [34] has to be located well below our frequency range ($\nu < 4 \text{ cm}^{-1}$). This value is too low for the relaxation to be explained by trivial geometrical localization within the grains: from the metallic strands model the relaxation is expected at 300 cm^{-1} and higher [35]. We thus expect that the observed relaxational dispersion in $\text{La}_{0.25}\text{Ca}_{0.75}\text{MnO}_3$ is intrinsic and linked to the CO process, that might be similar to the “order-disorder” phase transitions, for instance, in ferroelectrics or dipole glasses (relaxors). The dynamics of such systems is commonly described by a relaxational behavior of a certain response function, with a single relaxation time or distribution of those, revealing definite temperature dependences [36]. Alternatively, Efremov *et al.* suggested that in manganites the interplay between charge and magnetism can lead to ferroelectricity with the dipole moments aligned along the diagonal between the a and b axes [37]. The transition to such a ferroelectric phase could also be responsible for the dielectric relaxation observed in $\text{La}_{0.25}\text{Ca}_{0.75}\text{MnO}_3$.

Conclusion. – We have investigated the conductivity and dielectric permittivity of polycrystalline $\text{La}_{0.25}\text{Ca}_{0.75}\text{MnO}_3$ in the frequency range from 4 to 700 cm^{-1} (quantum energies 0.4 to 90 meV) using coherent-source THz spectroscopy, combined with FTIR measurements. In the antiferromagnetically ordered phase at $T < T_N \approx 140 \text{ K}$, a resonance-like absorption bands appear in the spectra at $20 - 40 \text{ cm}^{-1}$ and around 100 cm^{-1} . We show that the bands are not connected to the collective response of the charge-ordered subsystem but are acoustic phonons which gain optical activity when folded to the Brillouin zone center due to a structural phase transition resulting in a fourfold superlattice along the a -direction. With decreasing size of the crystallites, the $4a$ -superlattice and hence the absorption bands are gradually suppressed while the charge and antiferromagnetic orders survive, indicating a weak coupling of the correspondent order parameters to the lattice. Our results evidence that all optically active excitations of the electronically correlated phase in $\text{La}_{0.25}\text{Ca}_{0.75}\text{MnO}_3$ manganite, if any, should have energies smaller than 0.4 meV. Regardless of their microscopic origin – charge-modulated systems that have correlations of the order of 0.1 to 1 eV (as characterized by the charge gap) in general exhibit rather soft excitations observed at microwave-, radio-, and audio-frequencies [12, 22, 38]. At the lowest frequencies $4 - 20 \text{ cm}^{-1}$ a strong relaxation is observed above 100 K in all samples. It may indicate an order-disorder character of the charge-order phase transition in $\text{La}_{0.25}\text{Ca}_{0.75}\text{MnO}_3$.

Acknowledgements. – We acknowledge valuable discussions with P. Arseev, D. Efremov, N. Kovaleva, A. Mukhin, S. Tomić, and V. Travkin. We thank G. Untereiner for technical help. T.Z. and D.W. thank the Alexander von Humboldt. The work was supported by

the Deutsche Forschungsgemeinschaft (DFG) and by the RAS Program for fundamental research “Strongly correlated electrons in solids and solid structures”. Further funding by the scientific programs of the Russian Academy of Sciences and the Russian Foundation for Basic Research (project 08-02-00757a) is acknowledged.

REFERENCES

- [1] *Colossal Magnetoresistance, Charge Ordering and Related Properties of Manganese Oxides*, edited by RAO C.N.R. and RAVEAU B., (World Scientific, Singapore) 1998.
- [2] *Colossal Magnetoresistance Oxides*, edited by TOKURA Y., (Gordon and Breach, London) 1999.
- [3] DAGOTTO E., HOTTA T. and MOREO A., *Phys. Rep.*, **344** (2001) 1.
- [4] GOODENOUGH J., *Phys. Rev.*, **100** (1955) 564.
- [5] CHEN C., CHEONG S.-W. and HWANG H.Y., *J. Appl. Phys.*, **81** (1997) 4326; MORI S., CHEN C.H. and CHEONG S.-W., *Nature*, **392** (1998) 473.
- [6] WANG R., GUI J., ZHU Z. and MOODENBAUGH A.R., *Phys. Rev. B*, **61** (2000) 11946; RADAELLI P.G., COX D.E., CAPONGA L., CHEONG S.-W. and MAREZIO M., *Phys. Rev. B*, **59** (1999) 14440.
- [7] COEY M., *Nature*, **430** (2004) 155.
- [8] BREY L., *Phys. Rev. Lett.*, **92** (2004) 127202.
- [9] LOUDON J. C., COX S., WILLIAMS A. J., ATTFIELD J. P., LITTLEWOOD P. B., MIDGLEY P. A. and MATHUR N.D., *Phys. Rev. Lett.*, **94** (2005) 097202.
- [10] COX S., ROSTEN E., CHAPMAN J.C., KOS S., CALDERON M.J., KANG D.J., LITTLEWOOD P.B., MIDGLEY P.A. and MATHUR N.D., *Phys. Rev. B*, **73** (2006) 132401.
- [11] MILWARD G.C., CALDERON M.J. and LITTLEWOOD P.B., *Nature*, **433** (2005) 607.
- [12] GRÜNER G., *Rev. Mod. Phys.*, **60** (1988) 1129.
- [13] CHUANG Y.-G., GROMKO A. D., DESSAU D. S., KIMURA T. and TOKURA Y., *Science*, **292** (2001) 1509.
- [14] WAHL A., MERCONE S., PAUTRAT A., POLLET M., SIMON CH. and SEDMIDUBSKY D., *Phys. Rev. B*, **68** (2003) 094429.
- [15] COX S., SINGLETON J., McDONALD R. D., MIGLIORI A. and LITTLEWOOD P.B., *Nature Materials*, **7** (2008) 25.
- [16] KIDA N. and TONOUCHI M., *Phys. Rev. B*, **66** (2002) 024401.
- [17] NUCARA A., MASELLI P., CALVANI P., SOPRACASE R., ORTOLANI M., GRUENER G., CESTELLI GUIDI M., SCHADE U. and GARCIA J., *Phys. Rev. Lett.*, **101** (2008) 066407.
- [18] DRESSEL M., DRICHKO N. and KAISER S., *Physica C* (in press) (2009).
- [19] DUMM M., BASOV D. N., KOMIYA S., ABE Y. and ANDO Y., *Phys. Rev. Lett.*, **88** (2002) 147003.
- [20] LUCARELLI A., LUPI S., ORTOLANI M., CALVANI P., MASELLI P., CAPIZZI M., GIURA P., EISAKI H., KIKUGAWA N., FUJITA T., FUJITA M. and YAMADA K., *Phys. Rev. Lett.*, **90** (2003) 037002; ORTOLANI M., CALVANI P., LUPI S., SCHADE U., PERLA A., FUJITA M. and YAMADA K., *Phys. Rev. B*, **73** (2006) 184508.
- [21] LUPI S., NICOLETTI D., LIMAJ O., BALDASSARRE L., ORTOLANI M., ONO S., ANDO Y. and CALVANI P., *Phys. Rev. Lett.*, **102** (2009) 206409.
- [22] VULETIĆ T., KORIN-HAMZIĆ B., IVEK T., TOMIĆ S., GORSHUNOV B., DRESSEL M. and AKIMITSU J., *Phys. Rep.*, **428** (2006) 169.
- [23] DRESSEL M., GRÜNER G., POUGET J. P., BREINING A. and SCHWEITZER D., *J. Phys. I (France)*, **4** (1994) 579; DRESSEL M. AND DRICHKO N., *Chem. Rev.*, **104** (2004) 5689; IVEK T., KORIN-HAMZIĆ B., MILAT O., TOMIĆ S., CLAUSS C., DRICHKO N., GORSHUNOV B., SCHEITZER D. and DRESSEL M., to be published.
- [24] SCHMIDT R., *Phys. Rev. B*, **77** (2008) 205101.
- [25] FISHER B., GENOSSAR J., PATLAGAN L. and REISNER G. M., *J. Magn. Magn. Materials*, in press.
- [26] PISSAS M., MARGIOLAKI I., PRASSIDES K. and SUARD E., *Phys. Rev. B*, **72** (2005) 064426.
- [27] ZHANG T., ZHOU T.F., QIAN T. and LI X.G., *Phys. Rev. B* **76** (2007) 174415.
- [28] GORSHUNOV B. P., VOLKOV A., SPEKTOR I. E., PROKHOROV A. S., MUKHIN A. A., DRESSEL M., UCHIDA S. and LOIDL A., *Int. Journal of Infrared and Millimeter Waves*, **26** (2005) 1217; GORSHUNOV B. P., VOLKOV A. A., PROKHOROV A. S. and SPEKTOR I. E., *Physics of the Solid State*, **50** (2008) 2001.
- [29] KIM K.H., LEE S., NOH T.W. and CHEONG S.-W., *Phys. Rev. Lett.*, **88** (2002) 167204.
- [30] RINI E. G., RAO M. N., CHAPLOT S. L., GAUR N. K. and SINGH R. K., *Phys. Rev. B*, **75** (2007) 214301.
- [31] IVANNIKOV D., BIBERACHER M., KRUG VON NIDDA H.-A., PIMENOV A., LOIDL A., MUKHIN A. A. and BALBASHOV A. M., *Phys. Rev. B*, **65** (2002) 214422.
- [32] ZHANG T. and DRESSEL M., *Phys. Rev. B* **80** (2009) 014435.
- [33] COX S., LOUDON J. C., WILLIAMS A. J., ATTFIELD J. P., SINGLETON J., MIDGLEY P. A. and MATHUR N.D., *Phys. Rev. B* **78** (2008) 035129.
- [34] JONSCHER A.K., *Dielectric relaxation in solids*, (Chelsea Dielectric Press, London) 1983.
- [35] RICE M.J. and BERNASCONI J., *J. Phys. F*, **3** (1973) 55.
- [36] BLINK R. and ZEKS B., *Soft modes in ferroelectrics and antiferroelectrics*, (North-Holland Publishing Company, Amsterdam) 1974.
- [37] EFREMOV D., VAN DEN BRINK J. and KHOMSKII D., *Nature Materials*, **3** (2004) 853.
- [38] LITTLEWOOD P. B., *Phys. Rev. B*, **36** (1987) 3108.