

Direct observation of a nodeless superconducting energy gap in the optical conductivity of iron-pnictides

B. Gorshunov,^{1,2} D. Wu,^{1,*} A. A. Voronkov,² P. Kallina,¹ K. Iida,³
S. Haindl,³ F. Kurth,³ L. Schultz,³ B. Holzapfel,³ and M. Dressel¹

¹*Physikalisches Institut, Universität Stuttgart, Pfaffenwaldring 57, 70550 Stuttgart, Germany*

²*Prokhorov Institute of General Physics, Russian Academy of Sciences, Vavilov str. 38, 119991 Moscow, Russia*

³*IFW Dresden, Institute for Metallic Materials, P. O. Box 270116, 01171 Dresden, Germany*

(Dated: August 17, 2018)

The temperature-dependent optical reflectivity and complex transmissivity of an epitaxially grown $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$ thin film were measured and the optical conductivity and permittivity evaluated over a wide frequency range. The opening of the superconducting gap $2\Delta_0 = 3.7$ meV below $T_c \approx 20$ K is *directly* observed by a completely vanishing optical conductivity. The temperature and frequency dependent electrodynamic properties of $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$ in the superconducting state agree well with the BCS predictions with no nodes in the order parameter. The spectral weight of the condensate 1.94×10^7 cm⁻² corresponds to a London penetration depth $\lambda_L = 3600$ Å.

PACS numbers: 74.25.Gz, 78.20.-e, 74.78.Bz

I. INTRODUCTION

Soon after the discovery of superconductivity in iron-pnictides,¹ the epitaxial growth of LaFeAsO films was reported^{2,3} and superconductivity observed in thin films of Co doped SrFe_2As_2 .^{4,5} By now the homogeneity of the films and the upper critical field have increased to make iron-pnictides interesting for technological applications.^{6,7,8} In particular cobalt-doped BaFe_2As_2 seems to be suitable for producing high-quality thin films which are stable in air,⁸ can be template engineered,⁹ or tuned in T_c by epitaxial growths of strained films.¹⁰

Besides potential applications, thin films are advantageous for investigations of fundamental problems due to their large area, in particular if single crystals of sufficient quality, homogeneity, and size are limited. As far as optical experiments are concerned, only thin films give the opportunity to perform transmission measurements and in this way be much more sensitive to probe the electrodynamic properties of the normal and superconducting states.^{11,12} Issues like the spectral weight distribution, the universal conductivity background, and in particular on the superconducting gaps, on states in the gap, nodes in the order parameter and quasi-particle relaxation are addressed by our optical experiments on $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$ thin films.

II. EXPERIMENTAL DETAILS AND RESULTS

$\text{Ba}(\text{Fe}_{1-x}\text{Co}_x)_2\text{As}_2$ films were deposited on a (001)-orientated $(\text{La,Sr})(\text{Al,Ta})\text{O}_3$ substrate by pulsed laser deposition, where the $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$ target was ablated with 248 nm KrF radiation under UHV conditions.¹⁰ The films grow with a very smooth surface with an rms roughness better than 12 nm, as measured by atomic force microscopy (AFM). The film thickness

was monitored *in situ* by a quartz balance, and finally measured by AFM and ellipsometry to be $d = 90$ nm. The phase purity was checked by X-ray and EDS. Standard four-probe method was utilized to measure the dc resistivity and determine the superconducting transition: from the onset at 22 K with a transition width of 2 K, we have chosen $T_c = 20$ K (inset of Fig. 1).

Using different optical methods, we performed experiments in the frequency range from 4 to 35 000 cm⁻¹ and at various temperatures down to 5 K. In the THz range (4 to 40 cm⁻¹) the complex transmissivity (transmission coefficient amplitude and phase) was measured utilizing a Mach-Zehnder arrangement.¹³ Between 20 and 15 000 cm⁻¹ the reflectivity was investigated by Fourier transform infrared spectroscopy; a gold mirror served as reference. The spectra were extended up to the ultraviolet by room-temperature ellipsometric data (6000 - 35 000 cm⁻¹). In order to determine the properties of the film, we measured the optical parameters of a bare $(\text{La,Sr})(\text{Al,Ta})\text{O}_3$ substrate over the entire frequency and temperature ranges.

In Fig. 1(a) the optical reflectivity is plotted in a wide frequency range for selected temperatures. In particular in the far-infrared range the phonons of the substrate become obvious. For the further analysis we therefore employ a two-layer model that consists of the $(\text{La,Sr})(\text{Al,Ta})\text{O}_3$ substrate with thickness of 1.023 mm and optical parameters determined beforehand, covered by the thin film of $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$. Using Fresnel's equations¹¹ we then can analyze the intrinsic optical properties of the film. In the THz range (4 to 40 cm⁻¹) where data for the transmission and phase shift are available, a corresponding analysis was performed that allowed us to directly determine the values of dielectric permittivity and conductivity, with the experimental uncertainties strongly dependent on the values of $\epsilon(\omega, T)$ and $\sigma(\omega, T)$.¹³ The same model was used to evaluate the optical response of the film at higher frequencies. Even-

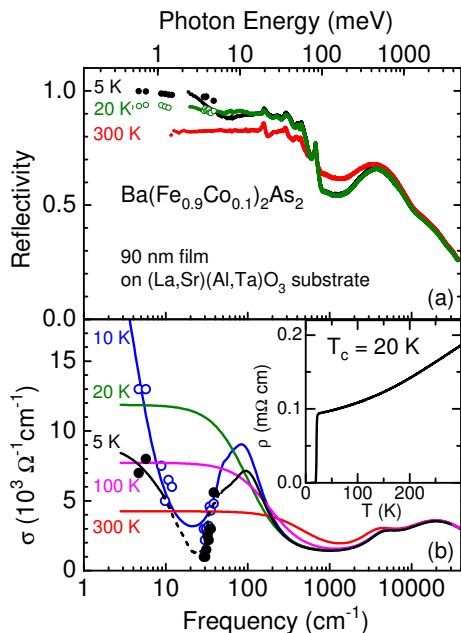


FIG. 1: (Color online) (a) Reflectivity of a 90 nm $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$ film on a 1 mm $(\text{La,Sr})(\text{Al,Ta})\text{O}_3$ substrate measured in a wide frequency range at various temperatures. The dots between 4 and 40 cm^{-1} are calculated from the transmission measurements. (b) Optical conductivity of $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$ obtained from the Drude-Lorentz analysis of the reflection and transmission spectra. The dots are directly calculated from measuring the transmission and phase by a Mach-Zehnder interferometer. The dashed part of the 5 K curve between 10 and 50 cm^{-1} indicates that a simple Lorentz shape does not mimic the superconducting gap properly since $\sigma(\omega)$ basically vanishes abruptly at 30 cm^{-1} . The inset shows the dc resistivity $\rho(T)$ of our sample with $T_c = 20$ K.

tually a self-consistent fit of the conductivity and permittivity spectra at THz frequencies and the reflectivity spectra at higher frequencies yields the overall behavior as presented in Fig. 1(b).

The properties of the $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$ film in the normal state are described by two Drude terms, a narrow σ_N and a broad one σ_B , corresponding to two types of charge carriers as suggested in Ref. 14. In addition, two Lorentz terms account for the interband transitions. In the superconducting state, two additional Drude terms are introduced, one with a tiny scattering rate to model the δ -function (Cooper pair response) obvious in the permittivity spectrum, and another term to describe the quasi-particle contribution to the below-gap conductivity. The optical response at energies around the superconducting gap are mimicked with two Lorentzians since an appropriate expression is missing. The resulting curves $\sigma(\omega, T)$ are plotted in Fig. 1(b) as a function of frequency for selected temperatures.

The most important finding of our investigation is the distinct opening of the superconducting gap which is directly seen in the drop of $\sigma(\omega, T)$ around 30 cm^{-1} upon cooling below T_c , as depicted in Fig. 2(a); for $T = 5$ K

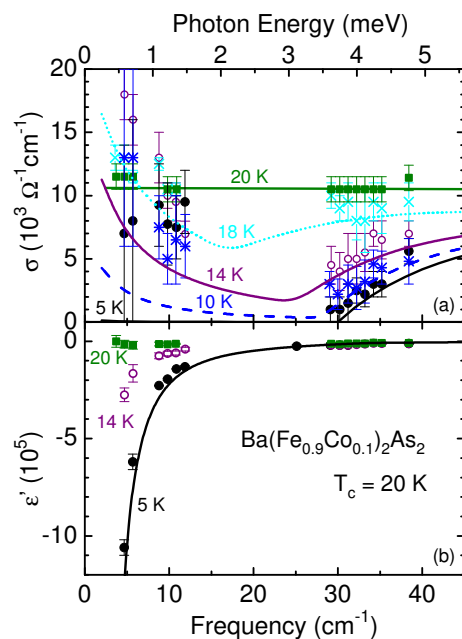


FIG. 2: (Color online) Optical properties of $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$ in the THz range where transmission and phase measurements directly yield the (a) conductivity and (b) permittivity spectra. The lines are calculated from the BCS theory assuming a complete opening of the gap at 30 cm^{-1} over the entire Fermi surface.

the conductivity has completely vanished. The depletion extends up to approximately 200 cm^{-1} . Due to remaining quasi-particles, the conductivity becomes large below 10 cm^{-1} and even exceeds the normal state value. The enormous drop of the low-frequency permittivity $\epsilon'(\omega, T)$ plotted in Fig. 2(b) evidences the inductive response of the superconducting condensate. It should be noted that the overall conductivity of the $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$ film is identical to findings on single crystals^{14,15,16} and thus resembles the intrinsic and general optical behavior of 122 iron-pnictides.

III. ANALYSIS AND DISCUSSION

In the metallic state ($T > 20$ K) the optical conductivity of $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$ has three major components: (i) The infrared peaks at 4400 and 20800 cm^{-1} indicate interband transitions. (ii) The background $\sigma_B \approx 1000$ ($\Omega\text{cm})^{-1}$, which is best seen in the conductivity minimum around 1000 cm^{-1} , is more or less temperature independent; we model it with a Drude term, albeit its roll-off cannot really be determined. (iii) Most important is the narrow Drude component $\sigma_N(\omega)$, which grows and becomes sharper as T decreases. Its spectral weight decreases by 15% when the temperature is reduced from 300 to 20 K. This corresponds to electronic correlation effects previously observed.¹⁷

For $T < T_c$ the THz conductivity dramatically de-

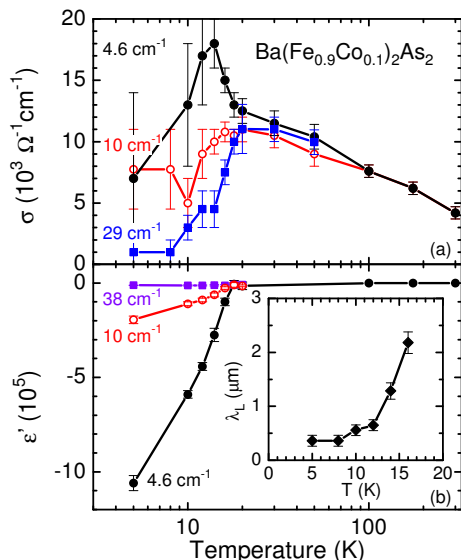


FIG. 3: (Color online) Temperature dependence of the low-frequency (a) optical conductivity $\sigma(\omega, T)$, (b) permittivity $\epsilon(\omega, T)$ and London penetration depth ($\lambda_L(T)$). For the lowest frequencies $\sigma(T)$ clearly exhibits a maximum below T_c .

creases below 100 cm^{-1} due to the opening of the superconducting gap at 30 cm^{-1} , as seen in Fig. 1(b). The directly measured conductivity is displayed in more detail in Fig. 2(a) together with calculations of the BCS-based Mattis-Bardeen model.^{11,18,19} The best description is obtained for $2\Delta_0 = 3.7 \text{ meV}$, corresponding to $2\Delta_0/k_B T_c \approx 2.1$; this value is considerably lower than expected from mean-field theory, but similar to what has been determined from reflection measurements of single crystals.^{14,16} The shape of $\sigma(\omega)$ perfectly agrees with the BCS prediction for a simple s -wave superconductor with no indications of states or nodes in the gap. Previous optical investigations^{20,21} on hole-doped 122 iron-pnictides draw similar conclusions.

Below 10 cm^{-1} a very narrow peak builds up for $T < T_c$ due to the quasi-particle contribution to the conductivity. Its intensity first increases and then diminishes as the quasi-particle number vanishes when $T \rightarrow 0$. In Fig. 3(a) the temperature dependence of $\sigma(\omega, T)$ is plotted for selected frequencies. From room temperature down to $T = 30 \text{ K}$ we find the THz conductivity basically not dependent on frequency, as expected for a normal metal; maybe small indications of fluctuations below 50 K can be identified. In the superconducting state, the conductivity at very low frequency ($\nu = 4.6 \text{ cm}^{-1}$) increases strongly right below T_c , it passes through a maximum σ_{max} around $14 \text{ K} \approx 0.7 T_c$, and then drops rapidly. As the frequency increases, this peak vanishes and only a simple drop of the conductivity is observed for $T < T_c$.

The BCS theory predicts a so-called coherence peak in the electrodynamic absorption of superconductors;^{11,19} it is considered as a hall-mark of singlet superconductivity

and most pronounced in the dirty limit and for s -wave symmetry of the order parameter. In contrast to theory and observations on conventional superconductors,^{22,23} in the present case the quasi-particle peak is larger in amplitude and extends to lower temperatures, as already seen in Fig. 2(a). An even larger peak has been reported²⁴ from microwave experiments on K-doped BaFe_2As_2 and extensively discussed in Ref. 25. It is desired to conduct further experiments on different compositions and films in order to obtain more information on scattering mechanisms, the influence of multiple bands and cross-scattering between the bands.

According to the Ferrell-Glover-Tinkham sum rule^{11,19} the missing area

$$A = \int [\sigma^{(n)}(\omega) - \sigma^{(s)}(\omega)] d\omega \quad (1)$$

between the conductivity in the normal and the superconducting state is collected in the δ -peak of the condensate at $\omega = 0$. It is a measure of the London penetration depth $\lambda_L = c/\sqrt{8A} = (2500 \pm 700) \text{ \AA}$. Alternatively the contribution of the superconducting carriers is probed by the permittivity ϵ' which for low frequencies goes as $1 - \epsilon' \propto (\omega_{ps}/\omega)^2$ in excellent agreement with the experimental results plotted in Fig. 2(b). Its development with temperature is displayed in the inset of Fig. 3(b). For $T \rightarrow 0$ we obtain $\lambda_L = (3600 \pm 500) \text{ \AA}$ in good agreement with the values we obtained for single crystals.^{14,16} The spectral weight $(\omega_{ps}/2\pi c)^2 = (1.94 \pm 0.1) \times 10^7 \text{ cm}^{-2}$ of the superconducting condensate is in excellent agreement with the scaling relation suggested for cuprates.^{26,27,28} We note that taking into account the below-gap contribution to the conductivity due to quasi-particles allows us to obtain more realistic values of the superconducting density compared to reflectivity experiments.

IV. CONCLUSIONS

The comprehensive optical investigation of $\text{Ba}(\text{Fe}_{0.9}\text{Co}_{0.1})_2\text{As}_2$ thin films evidence the complete opening of the superconducting gap at $2\Delta = 3.7 \text{ meV}$, i.e. $2\Delta/k_B T_c = 2.1$. From our complex transmissivity measurements we can rule out nodes in the gap. The frequency and temperature behavior of the complex electrodynamic response corresponds well with the predictions of the BCS theory.

Acknowledgments

Julia Braun helped with the ellipsometric measurements. The work was supported by the RAS Program for fundamental research “Strongly correlated electrons in solids and solid structures”.

-
- * Electronic address: dan.wu@pi1.physik.uni-stuttgart.de
- ¹ Y. Kamihara, T. Watanabe, M. Hirano, and H. Hosono, *J. Am. Chem. Soc.* **130**, 3296 (2008).
 - ² H. Hiramatsu, T. Katase, T. Kamiya, M. Hirano, and H. Hosono, *Appl. Phys. Lett.* **93**, 162504 (2008).
 - ³ E. Backen, S. Haindl, T. Niemeier, R. Hühne, T. Freudenberger, J. Werner, G. Behr, L. Schultz and B. Holzapfel, *Supercond. Sci. Technol.* **21**, 122001 (2008).
 - ⁴ H. Hiramatsu, T. Katase, T. Kamiya, M. Hirano, and H. Hosono, *Appl. Phys. Express* **1**, 101702 (2008).
 - ⁵ B. Maiorov, S. A. Baily, Y. Kohama, H. Hiramatsu, L. Civale, M. Hirano and H. Hosono, *Supercond. Sci. Technol.* **22**, 125011 (2009).
 - ⁶ S. Haindl, M. Kidszun, A. Kauffmann, K. Nenkov, N. Kozlova, J. Freudenberger, T. Thersleff, J. Werner, E. Reich, L. Schultz, and B. Holzapfel, arXiv:0909.2271.
 - ⁷ M. Kidszun, S. Haindl, E. Reich, J. Haenisch, L. Schultz, B. Holzapfel, arXiv:0909.3788.
 - ⁸ T. Katase, H. Hiramatsu, H. Yanagi, T. Kamiya, M. Hirano, and H. Hosono, *Solid State Commun.* **149**, 2121 (2009).
 - ⁹ S. Lee, J. Jiang, C. T. Nelson, C. W. Bark, J. D. Weiss, C. Tarantini, H. W. Jang, C. M. Folkman, S. H. Baek, A. Polyanskii, D. Abraimov, A. Yamamoto, Y. Zhang, X. Q. Pan, E. E. Hellstrom, D. C. Larbalestier, and C. B. Eom, arXiv:0910.0268.
 - ¹⁰ K. Iida, J. Hänsch, R. Hühne, F. Kurth, M. Kidszun, S. Haindl, J. Werner, L. Schultz, and B. Holzapfel, *Appl. Phys. Lett.* **95**, 192501 (2009).
 - ¹¹ M. Dressel and G. Grüner, *Electrodynamics of Solids* (Cambridge University Press, Cambridge, 2002).
 - ¹² M. Dressel, N. Drichko, B. P. Gorshunov, and A. Pimenov, *IEEE J. Sel. Top. Quantum Electron.* **14**, 399 (2008).
 - ¹³ B. Gorshunov, A. Volkov, I. Spektor, A. Prokhorov, A. Mukhin, M. Dressel, S. Uchida, and A. Loidl, *Int. J. Infrared and Millimeter Waves* **26**, 1217 (2005); B. P. Gorshunov, A. A. Volkov, A. S. Prokhorov, I. E. Spektor, *Physics of the Solid State* **50**, 2001 (2008).
 - ¹⁴ D. Wu, N. Barišić, N. Drichko, P. Kallina, A. Faridian, B. Gorshunov, L.J. Li, X. Lin, G.H. Cao, Z.A. Xu, N.L. Wang, and M. Dressel, (unpublished)
 - ¹⁵ N. Barišić, D. Wu, N. Drichko, M. Dressel, L.J. Li, X. Lin, G.H. Cao, and Z.A. Xu, (unpublished)
 - ¹⁶ D. Wu, N. Barišić, B. Gorshunov, N. Drichko, M. Dressel, L.J. Li, X. Lin, G.H. Cao, and Z.A. Xu, (unpublished)
 - ¹⁷ M. M. Qazilbash, J. J. Hamlin, R. E. Baumbach, Lijun Zhang, D. J. Singh, M. B. Maple, and D. N. Basov, *Nature Physics* **5**, 647 (2009).
 - ¹⁸ D. Mattis and J. Bardeen, *Phys. Rev.* **111**, 412 (1958)
 - ¹⁹ M. Tinkham, *Introduction to Superconductivity*, 2nd edition (McGraw-Hill, New York, 1996).
 - ²⁰ G. Li, W. Z. Hu, J. Dong, Z. Li, P. Zheng, G. F. Chen, J. L. Luo, and N. L. Wang, *Phys. Rev. Lett.* **101**, 107004 (2008).
 - ²¹ W. Z. Hu, Q. M. Zhang, and N. L. Wang, *Physica C* **469**, 545 (2009).
 - ²² B. P. Gorshunov, G. V. Kozlov, A. A. Volkov, S. P. Lebedev, I. V. Fedorov, A. M. Prokhorov, V. I. Makhov, J. Schutzmam, and K. F. Renk, *Int. J. Infrared Millimeter Waves* **14**, 683 (1993); B. P. Gorshunov, I. V. Fedorov, G. V. Kozlov, A. A. Volkov, and A. D. Semenov, *Solid State Commun.* **87**, 17 (1993).
 - ²³ K. Steinberg, M. Scheffler, and M. Dressel, *Phys. Rev. B* **77**, 214517 (2008).
 - ²⁴ K. Hashimoto, T. Shibauchi, S. Kasahara, K. Ikada, S. Tonegawa, T. Kato, R. Okazaki, C. J. van der Beek, M. Konczykowski, H. Takeya, K. Hirata, T. Terashima, and Y. Matsuda, *Phys. Rev. Lett.* **102**, 207001 (2009).
 - ²⁵ E. Schachinger and J. P. Carbotte, *Phys. Rev. Lett.* **80**, 174526 (2009).
 - ²⁶ Y.J. Uemura, L.P. Le, G.M. Luke, B.J. Sternlieb, W.D. Wu, J.H. Brewer, T.M. Riseman, C.L. Seaman, M.B. Maple, M. Ishikawa, D.G. Hinks, J.D. Jorgensen, G. Saito, and H. Yamochi, *Phys. Rev. Lett.* **66**, 2665 (1991).
 - ²⁷ C. C. Homes, S. V. Dordevic, M. Strongin, D. A. Bonn, Ruixing Liang, W. N. Hardy, S. Komiyama, Y. Ando, G. Yu, N. Kaneko, X. Zhao, M. Greven, D. N. Basov and T. Timusk, *Nature* **430**, 539 (2004).
 - ²⁸ D. Wu, N. Barišić, N. Drichko, P. Kallina, A. Faridian, B. Gorshunov, M. Dressel, L. J. Li, X. Lin, G. H. Cao, and Z. A. Xu, *Physica C* (2009), doi:10.1016/j.physc.2009.10.142.