

A Theory for the High- T_c Cuprates: Anomalous Normal-State and Spectroscopic Properties, Phase Diagram, and Pairing

J. Ashkenazi*

*Physics Department, University of Miami,
P.O. Box 248046, Coral Gables, FL 33124, U.S.A.*

(Dated: September 30, 2018)

A theory of highly correlated layered superconducting materials is applied for the cuprates. Differently from an independent-electron approximation, their low-energy excitations are approached in terms of auxiliary particles representing combinations of atomic-like electron configurations, where the introduction of a Lagrange Bose field enables treating them as bosons or fermions. The energy spectrum of this field accounts for the tendency of hole-doped cuprates to form stripe-like inhomogeneities. Consequently, it induces a different analytical behavior for auxiliary particles corresponding to “antinodal” and “nodal” electrons, enabling the existence of different pairing temperatures at T^* and T_c . This theory correctly describes the observed phase diagram of the cuprates, including the non-Fermi-liquid to FL crossover in the normal state, the existence of Fermi arcs below T^* and of a “marginal-FL” critical behavior above it. The qualitative anomalous behavior of numerous physical quantities is accounted for, including kink- and waterfall-like spectral features, the drop in the scattering rates below T^* and more radically below T_c , and an effective increase in the density of carriers with T and ω , reflected in transport, optical and other properties. Also is explained the correspondence between T_c , the resonance-mode energy, and the “nodal gap”.

Keywords: superconductivity, cuprates, auxiliary particles, anomalies, pairing

I. INTRODUCTION

High- T_c superconductivity (SC) has been in the forefront of condensed-matter physics research since its discovery in the cuprates over 23 years ago. This system is characterized by anomalous behavior of many of its physical properties [1–11] which led to the suggestion of non-Fermi-liquid (non-FL) models [12–15] for its electronic structure. The recent discovery of high- T_c SC in iron-based compounds (referred to below as FeSCs), provides a new test case for high- T_c theories, especially in view [16] of the striking similarity of their anomalous properties to those of the cuprates.

Recently, a unified theory for the cuprates and the FeSCs has been derived [16] on the basis of common features in their electronic structures, including quasi-two-dimensionality, and the large- U nature of the electron orbitals close to the Fermi level (E_F). Electrons of such orbitals *cannot* be treated through a mean-field independent-particle approach; therefore, their behavior is studied in terms of auxiliary particles, representing combinations of atomic-like electron configurations.

Within this auxiliary-particles method [17], configurations in sites i can be, approximately, treated as bosons or fermions, if each site is mathematically constrained to be occupied by one (and only one) configuration. There is a freedom in choosing configurations of an odd number of electrons as fermions, and of an even number of electrons as bosons, or *vice versa* [16]. The choice here is that configurations corresponding to undoped cuprates

or FeSCs (thus the parent compounds) are bosons.

These auxiliary particles have been treated *beyond* mean-field theory [14]. A grand-canonical Hamiltonian \mathcal{H} has been written down [16], where (in addition to the chemical potential μ) a field of Lagrange multipliers λ_i was introduced ($\lambda \equiv \langle \lambda_i \rangle$) to maintain the above auxiliary-particles’ constraint. This Lagrange field represents an effective fluctuating potential which enables the treatment of the above configurations as bosons or fermions; its effect on them is analogous to the effect of vibrating atoms on electrons, and similarly to lattice dynamics, this is a Bose field [16] (see discussion about it below).

These auxiliary particles are assigned the following *ad hoc* names [16]: (*i*) combinations of boson atomic-like configurations are referred to as “svivons”; their Bose condensation results in static or dynamical inhomogeneities which could be manifested in the existence of a commensurate or an incommensurate resonance mode [16]; (*ii*) combinations of fermion atomic-like configurations are referred to as “quasi-electrons” (QEs); they carry charge $-e$ and are introduced through electron or hole doping (in the second case the configurations correspond to holes of QEs); (*iii*) the Lagrange-field bosons are referred to as “lagrons”, and their coupling to the svivons and QEs provides a dynamical enforcement of the auxiliary-particles’ constraint.

Stripe-like inhomogeneities have been observed [18–22] within the phase diagram of the cuprates. Even though such an inhomogeneous behavior is often dynamical within the SC regime, it is not treated here as a perturbation to a homogeneous state, but as a correction to a static inhomogeneous structure. The application of the constraint, approached here through the Lagrange

*Electronic address: jashkenazi@miami.edu

field, must take into account the existence of these inhomogeneities. This results in a multi-component scenario.

In small- U systems, where low-energy electrons are appropriate quasiparticles (QPs), the FLEX approximation [23] could be applied [24] to derive an effective pairing interaction between them, due to their own spin and charge fluctuations. The low-energy large- U electrons, discussed here, *cannot* be considered as appropriate QPs; but their description in terms of independent auxiliary Fermi and Bose fields provides an intrinsic pairing mechanism through QE-lagron coupling; it can be treated [16] within the Migdal–Eliashberg theory [25–27], similarly to electron-phonon coupling in the case of phonon-induced pairing, but with coupling constants which are so strong that lattice instabilities would have been driven in the electron-phonon case.

In this paper auxiliary particles which are specific for the cuprates are introduced, and their Green’s functions are applied to derive those of the electrons. The detailed QE and electron spectral functions are calculated, with further emphasis on the anomalous low-energy features. The QE, svivon and electron scattering rates are derived in the non-FL regime, and the resulting physical anomalies are discussed. \mathcal{H} is then applied to derive QE and electron pairing which is demonstrated to result in the distinct pseudogap (PG) and SC phases; the associated anomalous physical behavior is discussed. Further calculations on part of these aspects (specifically in the paired states) will appear in separate papers.

II. HAMILTONIAN

Electronic-structure calculations, and a variety of experimental data, indicate that the “universal” (thus *not* characteristic of just specific compounds) low-energy properties of the cuprates are primarily determined by Cu(d) and O(p) orbitals of the CuO₂ planes. Within the LDA, these orbitals generate a multiple-band structure extending over a range of [28] about 9 eV. However, the electronic states at the vicinity of E_F dominantly reside [28–30] in *one* of these bands, of Wannier functions [31] which are centered at the planar Cu atoms, and correspond mainly to σ -antibonding states between Cu($d_{x^2-y^2}$) and O(p_x, p_y) orbitals (though a minor contribution of other orbitals exists as well). Due to this orbital nature of the band, its treatment requires effective transfer (hopping) integrals up to the third-nearest neighbor (see below).

The effective intra-site Coulomb parameter U , for electrons in this band, corresponds to its Wannier functions which are, primarily, combinations of Cu(d) and O(p) functions. Estimates of U must take into account the fact that the d intra-atomic integral U_d is considerably larger than the p integral U_p . In an early derivation of the effective one-band Hamiltonian [32] in hole-doped cuprates, the large- U_d and small- U_p limits have been assumed, resulting in approximately ionic Cu(d) and itinerant O(p)

states. The resulting [32] upper Hubbard band corresponds to Cu⁺¹ ions, and the lower Hubbard band to Cu⁺² ions, part of which are forming singlet states with the doped O(p) holes (known as “Zhang-Rice singlets”).

Consequently, the value of U , derived through this analysis, consists of U_d plus corrections, due to the singlet energy and the difference between the one-electron p and d energies which are considered to be substantially smaller. A more realistic evaluation of U would result in a somewhat smaller value than U_d ; however, since the width of the effective band, within a two-dimensional (2D) Brillouin zone (BZ), is [28–30] about 3 eV, it is appropriate to treat it using a large- U approach.

Within this one-band approach, a 2D square lattice of N sites i is considered (assuming translational symmetry between them); the Cu atoms are located at the lattice points \mathbf{R}_i , generated by the unit vectors $a\hat{x}$ and $a\hat{y}$. An electron of spin σ in site i is created by $d_{i\sigma}^\dagger$ (the two spin states are denoted as $\sigma = \uparrow, \downarrow$, or $\sigma = \pm 1$). The Hamiltonian is expressed as:

$$\mathcal{H}^d \cong \sum_{i\sigma} [(\epsilon^d - \mu)d_{i\sigma}^\dagger d_{i\sigma} + \sum_{j \neq i} t(\mathbf{R}_i - \mathbf{R}_j)d_{i\sigma}^\dagger d_{j\sigma} + \frac{1}{2}Ud_{i,-\sigma}^\dagger d_{i\sigma}^\dagger d_{i\sigma} d_{i,-\sigma}], \quad (1)$$

where the transfer integrals $t(\mathbf{R})$ are considered up to the third-nearest neighbor, and expressed in terms of the parameters t , t' and t'' :

$$\begin{aligned} t(\pm a\hat{x}) &= t(\pm a\hat{y}) = -t, & (2) \\ t(\pm a\hat{x} \pm a\hat{y}) &= -t', & t(\pm 2a\hat{x}) = t(\pm 2a\hat{y}) = -t''. \end{aligned}$$

The present auxiliary-particles approach [16] then becomes the “slave-fermion” method, applied in previous works by the author [33–35]. This approach is *different* from homogeneous RVB models [12, 14, 15] which are also based on auxiliary particles, but generally within the “slave-boson” method, where the fermions are spin-carrying “spinons” and the bosons are charge-carrying “holons”. Within the present approach, the roles of fermions and bosons are switched, and consequently inhomogeneities are inherently introduced through Bose condensation. An electron creation operator is then expressed as [16, 17]:

$$d_{i\sigma}^\dagger = s_{i\sigma}^\dagger h_i + \sigma e_i^\dagger s_{i,-\sigma}, \quad (3)$$

where $s_{i\sigma}^\dagger$, h_i^\dagger and e_i^\dagger create a boson svivon state, and fermion holon and “doublon” states, respectively. The auxiliary-particles’ constraint is expressed as [16, 17]:

$$\sum_{\sigma} s_{i\sigma}^\dagger s_{i\sigma} + h_i^\dagger h_i + e_i^\dagger e_i = 1. \quad (4)$$

For hole-doped cuprates, the effect of the upper-Hubbard-band doublons is ignored in the lowest order, and the creation operator of a fermion QE state is de-

defined as: $q_i^\dagger \equiv h_i$. Eqs. (3,4) are then approximated as:

$$d_{i\sigma}^\dagger \cong s_{i\sigma}^\dagger q_i^\dagger, \quad (5)$$

$$\sum_{\sigma} s_{i\sigma}^\dagger s_{i\sigma} \cong q_i^\dagger q_i. \quad (6)$$

By expressing the electron operators in the rhs of Eq. (1) in terms of the auxiliary-particle operators, through Eq. (5), one gets that the U term in \mathcal{H}^d drops, as is expected far below the upper Hubbard band.

Including in \mathcal{H}^d the effect of doublons, through Eq. (3), within a second-order perturbation expansion, introduces [16] corrections to the transfer integrals, and antiferromagnetic (AF) exchange integrals:

$$\Delta t(\mathbf{R}, \mathbf{R}') \cong -\frac{t(\mathbf{R})t(\mathbf{R}')}{U}, \quad J(\mathbf{R}) \cong \frac{t(\mathbf{R})t(-\mathbf{R})}{U}, \quad (7)$$

for $\mathbf{R} \neq 0$ and $\mathbf{R}' \neq 0$. Considering such integrals only for nearest-neighbor \mathbf{R} and \mathbf{R}' results in their expression in terms of the parameter $J \cong t^2/U$:

$$\Delta t(\pm a\hat{x}, \pm a\hat{x}) = \Delta t(\pm a\hat{y}, \pm a\hat{y}) = \Delta t(\pm a\hat{x}, \pm a\hat{y}) \cong -J, \\ J(\pm a\hat{x}) = J(\pm a\hat{y}) = J. \quad (8)$$

The parameters in Eqs. (2,8) have been determined on the basis of first-principles calculations [28–30, 36, 37]. The set of their values chosen here is: $t = 0.43$ eV, $t' = -0.07$ eV, $t'' = 0.03$ eV, and $J = 0.1$ eV (other sets of values, within the range of the calculated parameters, yield similar results to those below).

Applying the above approximations, and the constraint in Eq. (6) which is approached through a grand-canonical scheme, results in the expression of \mathcal{H}^d in Eq. (1) in terms of \mathcal{H}^a , given by [16]:

$$\mathcal{H}^a = \sum_{ij\sigma} \left\{ \left[\frac{1}{2} \delta_{ij} (\epsilon^d + \lambda - \mu) + (1 - \delta_{ij}) [t(\mathbf{R}_i - \mathbf{R}_j) \right. \right. \\ \left. \left. + \sum_{k \neq i,j} \Delta t(\mathbf{R}_i - \mathbf{R}_k, \mathbf{R}_k - \mathbf{R}_j) s_{k,-\sigma}^\dagger s_{k,-\sigma}] \right] \right. \\ \left. \times s_{i\sigma}^\dagger s_{j\sigma} \right] q_i^\dagger q_j - [\delta_{ij} \lambda + \frac{1}{2} (1 - \delta_{ij}) J(\mathbf{R}_i - \mathbf{R}_j) \\ \times s_{j,-\sigma}^\dagger s_{j,-\sigma}] s_{i\sigma}^\dagger s_{i\sigma} \left. \right\} + \Delta \mathcal{H}, \quad (9)$$

where the mean value λ of the constraint Lagrange multipliers λ_i is treated similarly to the chemical potential μ , while $\lambda_i - \lambda$ fluctuations are treated through:

$$\Delta \mathcal{H} = \sum_i (\lambda_i - \lambda) [q_i^\dagger q_i - \sum_{\sigma} s_{i\sigma}^\dagger s_{i\sigma}]. \quad (10)$$

\mathcal{H}^a describes an auxiliary system of fermions and bosons, behaving according to the laws of physics, but it is relevant for the real physical system only under the set of values of time-dependent λ_i for which the constraint is maintained. Assuming lattice translational symmetry, let $\lambda(\mathbf{k})$, $q^\dagger(\mathbf{k})$ and $s_{\sigma}^\dagger(\mathbf{k})$ be, respectively, the Fourier transforms of λ_i , q_i^\dagger and $s_{i\sigma}^\dagger$ to the wave vector (\mathbf{k}) representation, determined within the lattice BZ.

By Eq. (10), nonzero $\lambda_i - \lambda$ introduce hybridization between QE and between svivon states, and the time derivatives of λ_i induce transitions between such states. Consequently, the Lagrangian of the auxiliary system depends both on $\lambda(\mathbf{k})$, playing the role of generalized coordinates, and on their time derivatives $\dot{\lambda}(\mathbf{k})$ which must *not* vanish (for $\mathbf{k} \neq 0$) in order to prevent constraint-violating fluctuations. This dependence could be applied [38] to derive the conjugate momenta $p^\lambda(\mathbf{k})$ of $\lambda(\mathbf{k})$, and the dependence of \mathcal{H}^a on them, reflecting the effect of $\dot{\lambda}(\mathbf{k})$.

Since $\lambda(\mathbf{k})$ and $p^\lambda(\mathbf{k})$ are coordinates and momenta in a physical-like quantum system, there exist coefficients $\gamma(\mathbf{k})$ for which one can express (for $\mathbf{k} \neq 0$), in a similar manner as in lattice dynamics [39] (units where $\hbar = 1$ are used):

$$\lambda(\mathbf{k}) = \gamma(\mathbf{k}) [l(\mathbf{k}) + l^\dagger(-\mathbf{k})], \\ p^\lambda(\mathbf{k}) = \frac{1}{2i\gamma(\mathbf{k})} [l(-\mathbf{k}) - l^\dagger(\mathbf{k})], \quad (11)$$

where $l^\dagger(\mathbf{k})$ are the creation operators of boson lagron states within the BZ (omitting the $\mathbf{k} = 0$ point which corresponds to λ in Eq. (9)). Thus, one could express $\Delta \mathcal{H}$ in Eq. (10) as:

$$\Delta \mathcal{H} = \sum_{\mathbf{k}, \mathbf{q} \neq 0} \gamma(\mathbf{q}) [l(\mathbf{q}) + l^\dagger(-\mathbf{q})] \\ \times [q^\dagger(\mathbf{k}) q(\mathbf{k} + \mathbf{q}) - \sum_{\sigma} s_{\sigma}^\dagger(\mathbf{k}) s_{\sigma}(\mathbf{k} + \mathbf{q})]. \quad (12)$$

The coupling of QEs and svivons to lagrons, through $\Delta \mathcal{H}$ in Eq. (12), introduces an implicit dependence of the auxiliary system on $\lambda(\mathbf{k})$ and $p^\lambda(\mathbf{k})$, due to the modifications introduced to the QE and svivon spectra. The effect of $\lambda(\mathbf{k})$ is manifested in the real parts of their induced self-energies [39, 40], and that of $p^\lambda(\mathbf{k})$ in the corresponding imaginary parts. These effects on the QE and svivon spectra introduce modifications in the Helmholtz free energy \mathcal{F}^a of the auxiliary system which could be expressed in terms of an effective lagron Hamiltonian \mathcal{H}^λ , depending on $\lambda(\mathbf{k})$ and $p^\lambda(\mathbf{k})$.

The effect of the magnitudes and rates of the $\lambda_i - \lambda$ fluctuations on \mathcal{F}^a could be generally treated within a second-order perturbation expansion. Since a constrained minimum of \mathcal{F}^a cannot be lower than the unconstrained one, the contribution of each of these time-dependent Lagrange multipliers to \mathcal{H}^λ must not be negative. Thus, in analogy to the harmonic approximation in lattice dynamics [31, 39], the dependence of \mathcal{H}^λ on $\lambda(\mathbf{k})$ and $p^\lambda(\mathbf{k})$ has a positive definite quadratic form. Consequently, by applying the canonical transformation:

$$\tilde{\lambda}(\mathbf{k}) = \cos(\xi_{\mathbf{k}}^\lambda) \lambda(\mathbf{k}) + \sin(\xi_{\mathbf{k}}^\lambda) p^\lambda(\mathbf{k}), \\ \tilde{p}^\lambda(\mathbf{k}) = \cos(\xi_{\mathbf{k}}^\lambda) p^\lambda(\mathbf{k}) - \sin(\xi_{\mathbf{k}}^\lambda) \lambda(\mathbf{k}), \quad (13)$$

an appropriate choice of $\xi_{\mathbf{k}}^\lambda$ results in an expression of the form:

$$\mathcal{H}^\lambda \cong \frac{1}{2} \sum_{\mathbf{k} \neq 0} [A^\lambda(\mathbf{k}) \tilde{\lambda}^\dagger(\mathbf{k}) \tilde{\lambda}(\mathbf{k}) + B^\lambda(\mathbf{k}) \tilde{p}^{\lambda\dagger}(\mathbf{k}) \tilde{p}^\lambda(\mathbf{k})], \quad (14)$$

where the coefficients $A^\lambda(\mathbf{k})$ and $B^\lambda(\mathbf{k})$ are positive. Expressing $\tilde{\lambda}(\mathbf{k})$ and $\tilde{p}^\lambda(\mathbf{k})$ through Eqs. (11,13) yields:

$$\mathcal{H}^\lambda \cong \sum_{\mathbf{k} \neq 0} \omega^\lambda(\mathbf{k}) [l^\dagger(\mathbf{k})l(\mathbf{k}) + \frac{1}{2}], \quad \text{where} \quad (15)$$

$$\omega^\lambda(\mathbf{k}) = \left\{ [\sin^2(\xi_{\mathbf{k}}^\lambda) A^\lambda(\mathbf{k}) + \cos^2(\xi_{\mathbf{k}}^\lambda) B^\lambda(\mathbf{k})] \right. \\ \left. \times [\cos^2(\xi_{\mathbf{k}}^\lambda) A^\lambda(\mathbf{k}) + \sin^2(\xi_{\mathbf{k}}^\lambda) B^\lambda(\mathbf{k})] \right\}^{\frac{1}{2}}, \quad (16)$$

$$|\gamma(\mathbf{k})|^2 = \frac{1}{2} \left\{ \frac{\sin^2(\xi_{\mathbf{k}}^\lambda) A^\lambda(\mathbf{k}) + \cos^2(\xi_{\mathbf{k}}^\lambda) B^\lambda(\mathbf{k})}{\cos^2(\xi_{\mathbf{k}}^\lambda) A^\lambda(\mathbf{k}) + \sin^2(\xi_{\mathbf{k}}^\lambda) B^\lambda(\mathbf{k})} \right\}^{\frac{1}{2}}.$$

The derivation of \mathcal{H}^λ from \mathcal{H}^a is conceptually analogous to the derivation of a phonon Hamiltonian from the Hamiltonian of electrons and nuclei in a crystal. In the same manner that the auxiliary system represents the real physical system only under the correct lagron spectrum and coupling constants, a system of electrons coupled to phonons in a crystal precisely represents the physical system only under the correct phonon spectrum and coupling constants.

The evaluation of the lagron energies $\omega^\lambda(\mathbf{k})$ in Eq. (15) could be carried out self-consistently, on the basis of \mathcal{H}^a in Eq. (9), applying diagrammatic techniques [39, 40] (this introduces lagron linewidths, ignored in Eq. (15)). The coefficients $\gamma(\mathbf{k})$, appearing in Eq. (11), should be chosen such that Eq. (16) is satisfied, and the svivon and QE spectra, obtained on the basis of Eq. (9), maintain the constraint in Eq. (6).

These conditions are approached by checking trial $\omega^\lambda(\mathbf{k})$ spectra, determined on the basis of physical considerations (see below), and looking for the coefficients $\gamma(\mathbf{k})$ for which these spectra are obtained self-consistently. Convergence is reached when the lagron spectrum and $\gamma(\mathbf{k})$ satisfy Eq. (16), and determine QE and svivon spectra which maintain the constraint; it is checked through specific relations between these spectra, expressed through the ‘‘constraint susceptibility’’ [16] (see below). It turns out that the derivation of the major features of the lagron, QE and svivon spectra could be performed without an elaborate point by point self-consistent calculation.

III. GREEN’S FUNCTIONS

The elements of the ‘‘normal’’ svivon and QE Green’s-function [39, 40] matrices $\underline{\mathcal{G}}^s$ and $\underline{\mathcal{G}}^q$ are based, in the site representation, on expectation values of the form $\langle s_{i\sigma} s_{j\sigma}^\dagger \rangle$ and $\langle q_i q_j^\dagger \rangle$, respectively. The Bose condensation of svivons, and the pairing of QEs introduce ‘‘anomalous’’ [40] svivon and QE Green’s-function matrices $\underline{\mathcal{F}}^s$ and $\underline{\mathcal{F}}^q$ based, in the site representation, on expectation values of the form $\langle s_{i\uparrow} s_{j\downarrow} \rangle$ and $\langle q_i q_j \rangle$, respectively.

The above Green’s-function matrices are presented diagrammatically as the propagators shown in Fig. 1(a); in the \mathbf{k} and Matsubara representations [39, 40] they are diagonal and expressed, at temperature T , as functions

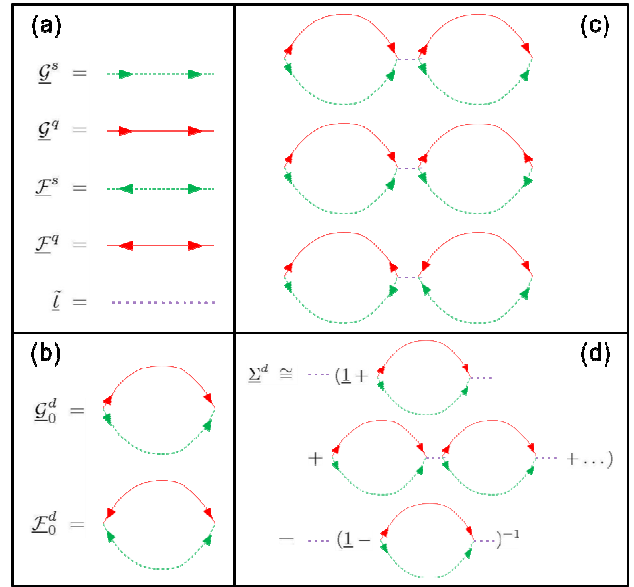


FIG. 1: (a) Propagator diagrams of the normal and anomalous svivon and QE Green’s-function matrices $\underline{\mathcal{G}}^s$, $\underline{\mathcal{G}}^q$, $\underline{\mathcal{F}}^s$, $\underline{\mathcal{F}}^q$, and of the renormalized transfer matrix \tilde{l} (see discussion in the text); (b) bubble diagrams of the zeroth-order normal and anomalous electron Green’s-function matrices $\underline{\mathcal{G}}_0^d$ and $\underline{\mathcal{F}}_0^d$; (c) diagrams of typical first-order corrections to $\underline{\mathcal{G}}_0^d$ and $\underline{\mathcal{F}}_0^d$; (d) diagrammatical presentation of the geometrical-series sum determining the self-energy correction $\underline{\Sigma}^d$ to $\underline{\mathcal{G}}_0^d$ for [41] $T > T_p^q$.

of $\omega_\nu = \nu \pi k_B T$, where k_B is the Boltzmann constant, and ν is an integer which is even for bosons and odd for fermions. The dependence of the Green’s functions on $i\omega_\nu$ is analytically continued [39, 40] to the complex z plane, including the $\pm i0^+$ vicinity of the real ω -axis (where 0^+ is an infinitesimally small positive number).

The normal and anomalous electron Green’s-function matrices $\underline{\mathcal{G}}^d$ and $\underline{\mathcal{F}}^d$ are also diagonal in the \mathbf{k} representation. By Eq. (5), the elements of $\underline{\mathcal{G}}^d$ (far below the upper Hubbard band) are based, in the site representation, on expectation values of the form $\langle q_i s_{i\sigma} s_{j\sigma}^\dagger q_j^\dagger \rangle$, and of $\underline{\mathcal{F}}^d$ on expectation values of the form $\langle q_i s_{i\uparrow} q_j s_{j\downarrow} \rangle$. Thus the zeroth-order (in t/U) normal electron Green’s-function matrices $\underline{\mathcal{G}}_0^d$ correspond, in the site representation, to bubble diagrams formed by $\underline{\mathcal{G}}^s$ and $\underline{\mathcal{G}}^q$, and the anomalous matrices $\underline{\mathcal{F}}_0^d$ to bubble diagrams formed by $\underline{\mathcal{F}}^s$ and $\underline{\mathcal{F}}^q$, as is presented diagrammatically in Fig. 1(b). In the \mathbf{k} and Matsubara representations, $\underline{\mathcal{G}}_0^d$ and $\underline{\mathcal{F}}_0^d$ become convolutions of such bubble diagrams (see below).

The relevant term for single-electron excitations in \mathcal{H}^a

in Eq. (9) could be expressed (using Eqs. (5,6)) as:

$$\begin{aligned} \mathcal{H}_e^a &= \sum_{ij\sigma} \tilde{t}_{ij} s_{i\sigma}^\dagger q_i^\dagger s_{j\sigma} q_j, \quad \text{where} \\ \tilde{t}_{ij} &\cong \delta_{ij}(\epsilon^d + \lambda - \mu) + (1 - \delta_{ij})[t(\mathbf{R}_i - \mathbf{R}_j) \\ &\quad + \sum_{k \neq i,j} n_{ijk}^s \Delta t(\mathbf{R}_i - \mathbf{R}_k, \mathbf{R}_k - \mathbf{R}_j)], \end{aligned} \quad (17)$$

where n_{ijk}^s is the conditioned expectation value $\langle s_{k,-\sigma}^\dagger s_{k,-\sigma} \rangle$ when there is a σ electron in site i and no electron in site j , or *vice versa*.

The elements \tilde{t}_{ij} in Eq. (17) introduce a matrix \tilde{t} which is diagonal in the \mathbf{k} representation, and its eigenvalues correspond (considerably below the upper Hubbard band) to an LDA-like band structure, within the one-orbital model. This matrix is also presented diagrammatically in Fig. 1(a). The dominant corrections to $\underline{\mathcal{G}}^d$ and $\underline{\mathcal{F}}^d$, beyond $\underline{\mathcal{G}}_0^d$ and $\underline{\mathcal{F}}_0^d$, are introduced through \mathcal{H}_e^a in Eq. (17); first-order corrections of this type are presented, diagrammatically, in Fig. 1(c).

At T above the QE pairing temperature [41] T_p^q one has $\underline{\mathcal{F}}^q = \underline{\mathcal{F}}^d = \underline{0}$ (though $\underline{\mathcal{F}}^s \neq \underline{0}$). Similarly to the summation of bubble diagrams within the RPA [39, 40], the self-energy correction to $\underline{\mathcal{G}}_0^d$ (due to multiple QE-svicon scattering) could then be evaluated, through Eq. (17), as a sum of a geometrical series, presented diagrammatically in Fig. 1(d), yielding:

$$\underline{\Sigma}^d \cong \tilde{t} \sum_{n=0}^{\infty} (\underline{\mathcal{G}}_0^d \tilde{t})^n = \tilde{t} (\underline{1} - \underline{\mathcal{G}}_0^d \tilde{t})^{-1}. \quad (18)$$

Using Dyson's equation [39, 40], $(\underline{\mathcal{G}}^d)^{-1} = (\underline{\mathcal{G}}_0^d)^{-1} - \underline{\Sigma}^d$, one can express $\underline{\mathcal{G}}^d$ as:

$$\underline{\mathcal{G}}^d \cong (\underline{1} - \underline{\mathcal{G}}_0^d \tilde{t}) (\underline{1} - 2\underline{\mathcal{G}}_0^d \tilde{t})^{-1} \underline{\mathcal{G}}_0^d. \quad (19)$$

The consequence of Eq. (19) is that there are two types of poles in the z -dependent $\underline{\mathcal{G}}^d$. One type, contributed by the $\underline{\mathcal{G}}_0^d$ term, consists of a non-FL distribution of convoluted QE-svicon poles; the other type is of poles contributed by the multiple-scattering $(\underline{1} - 2\underline{\mathcal{G}}_0^d \tilde{t})^{-1}$ term, and it is consistent with electron poles within FL theory.

Since the evaluation of physical properties can be expressed in terms of the electron Green's functions, and their poles, these properties are characterized by FL-like and/or non-FL features due to the different types of poles in $\underline{\mathcal{G}}^d$. The phase diagram of the cuprates [42] indicates a non-FL to FL crossover in the normal-state behavior of the cuprates between the underdoped and the overdoped regimes [1, 11]. In heavily overdoped cuprates, a crossover is expected to a regime where the large- U approach, applied here, stops being valid, and there is no SC state.

IV. SPECTRAL FUNCTIONS

A. Lagrons

Low-energy (soft) lagron modes play a significant role in the lagron spectrum. In the phonon case, the emergence of a soft mode requires (when it is not at the close vicinity of $\mathbf{k} = 0$) a considerable self-energy correction, through electron-phonon coupling, in order to lower the "bare" phonon energy; by the Kramers-Kronig relation [39, 40] between the imaginary and real parts of the phonon self-energy, such an energy lowering means that the soft phonon mode has a considerable linewidth.

On the other hand, in the lagron case, the entire mode energy $\omega^\lambda(\mathbf{q})$ consists of a self-energy correction, due to its coupling to QEs and svivons, through $\Delta\mathcal{H}$ in Eq. (12). Thus, the Kramers-Kronig relation of the lagron self-energy implies that both the energy and the linewidth of a lagron mode could be extremely close to zero. Applying this relation, and Eq. (14), indicates that $A^\lambda(\mathbf{q})$ and $B^\lambda(\mathbf{q})$ almost vanish at this point, $\mathbf{q} = \mathbf{Q}_m$, of the lagron energy minimum, and have the same type of dependence on $\mathbf{q} - \mathbf{Q}_m$ within a BZ range of $\mathbf{q} \simeq \mathbf{Q}_m$.

Consequently, by Eq. (16), $\omega^\lambda(\mathbf{q})$ also has this type of dependence on $\mathbf{q} - \mathbf{Q}_m$, within this BZ range, and $|\gamma(\mathbf{q})|^2$ is fairly independent of \mathbf{q} there. This behavior of $\gamma(\mathbf{q})$ is very different from the \mathbf{k} dependence of the coupling constants between electrons and acoustic phonons in metals which vanish [31, 39] for $\mathbf{k} \rightarrow 0$. As will be discussed further below, the \mathbf{q} dependence of $\omega^\lambda(\mathbf{q})$ which is consistent with the physics of the cuprates is the one yielding a Bose-condensation-type behavior. For their 2D BZ, this corresponds to $\omega^\lambda(\mathbf{q}) \propto |\mathbf{q} - \mathbf{Q}_m|$, for $\mathbf{q} \simeq \mathbf{Q}_m$; the apparent singularity of $\omega^\lambda(\mathbf{q})$ at $\mathbf{q} = \mathbf{Q}_m$ is a self-consistent consequence of the macroscopic value of $\langle l^\dagger(\mathbf{Q}_m) l(\mathbf{Q}_m) \rangle$.

By Eq. (11), the \mathbf{Q}_m points of the lagron spectrum correspond to particularly large values of $\lambda(\mathbf{q})$ and $p^\lambda(\mathbf{q})$, for $\mathbf{q} \cong \mathbf{Q}_m$. This is typical of wave vectors corresponding to major spin and charge fluctuations, where an inhomogeneous enforcement of the auxiliary-particles' constraint is essential. Theoretical studies [43-45], based on Hamiltonians like \mathcal{H}^d in Eq. (1), predict that the interplay between the effects of electron hopping and AF exchange is likely to drive the formation of stripe-like inhomogeneities (studied in previous works by the author [34, 35]). Thus the physics of the cuprates is consistent with \mathbf{Q}_m points which correspond to the wave vectors of the striped structures.

In agreement with the above theoretical predictions, the hole-doped cuprates are characterized by dynamical or static stripe-like inhomogeneities [18-22]; in SC stoichiometries, they correspond to stripes directed along the a - or the b -axis; however, an intrinsic mechanism (of a nature discussed below) introduces long-range symmetry between stripe segments directed along these axes, resulting in a checkerboard-like structure [21, 22]. Consequently, the lagron spectrum corresponding to such a structure is of the type presented in Fig. 2.

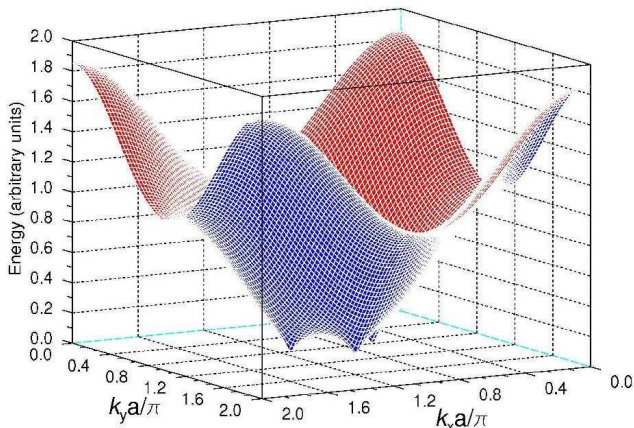


FIG. 2: A typical lagron spectrum in hole-doped cuprates; the minima correspond to degenerate striped structures [18–22].

Thus, the lagron energy band, $\omega^\lambda(\mathbf{q})$, is characterized by V-shape minima:

$$\begin{aligned} \omega^\lambda(\mathbf{Q}_m) &= k_B T / \mathcal{O}(N), \quad \text{at} \\ \mathbf{Q}_m &= \mathbf{Q} + \delta\mathbf{q}_m, \quad \text{for } m = 1, 2, 3 \text{ or } 4, \end{aligned} \quad (20)$$

where $\mathbf{Q} = (\pi/a)(\hat{x} + \hat{y})$ is the wave vector of the AF order in the parent compounds; $\delta\mathbf{q}_m = \pm\delta q\hat{x}$ or $\pm\delta q\hat{y}$ are modulations around \mathbf{Q} , indicative of the striped structures [18–22] (typically, $\delta q \cong \pi/4a$). The lagron spectrum presented in Fig. 2 corresponds to degenerate states of stripes directed along the a and b axes, and of different phases of the spin periodicity (see below). The four lagron energy minima, and the symmetry of the system, determine the main features of the spectrum, and as was discussed above, the linewidths are generally larger at higher energies. The high-energy extent of this spectrum is somewhat higher than that of the svivon spectrum [16], and is thus expected to be ~ 0.3 – 0.4 eV.

The existence of four equivalent lagron minima in points \mathbf{Q}_m in Eq. (20) results in a combination state of four Bose condensates of the lagron field [46], each consisting of a striped structure of the symmetry corresponding to one of the \mathbf{Q}_m wave vectors. In SC stoichiometries, such a combination state is energetically favorable, for $T \rightarrow 0$, on one of the symmetry-broken condensates (corresponding to a long-range striped structure) since it is the one which yields pairing (see below). Similarly to phonons which are Goldstone bosons [47] associated with spontaneous breakdown of lattice translational symmetry, the lagrons are Goldstone bosons associated with the breakdown of the symmetries of the long-range striped structures, corresponding to each of the combined condensates.

The svivon and QE spectra are evaluated through a self-consistent second-order diagrammatic expansion, where a mean-field treatment of \mathcal{H}^a in Eq. (9) is applied at the zeroth order. The expansion is carried out on two Hamiltonian terms; one of them is the svivon-lagron and QE-lagron coupling term $\Delta\mathcal{H}$ in Eq. (12). The treat-

ment of the analogous electron-phonon coupling term in phonon-mediated SCs is based on the fact that the ratio between phonon and electron energies is very small; consequently, by Migdal’s theorem [25], “vertex corrections” beyond a second-order diagrammatic expansion are negligible due to a small integration phase space.

Concerning the treatment of $\Delta\mathcal{H}$, as can be viewed in Fig. 2, the lagron spectrum consists of two regimes; a low-energy one around point \mathbf{Q} (including the points \mathbf{Q}_m defined in Eq. (20)), and a high-energy regime in the rest of the BZ. As is discussed below, the peculiar behavior (including pairing) introduced by $\Delta\mathcal{H}$ is primarily due to lagrons of the low-energy regime, for which Migdal’s theorem applies. Vertex corrections due to lagrons of the high-energy regime may be not negligible, but they are regular and could be approximated as renormalization effects within the second-order diagrammatic expansion.

B. Svivons

In the parent compounds, the lagron spectrum includes one V-shape minimum at $\mathbf{q} = \mathbf{Q}$, corresponding to a condensate (see above), and the Bose condensation of the svivon field [46] is manifested in long-range AF order [33]. Within such a svivon condensate which corresponds to a combination of Néel states, shifted from each other by $a\hat{x}$, the expectation value $n^s \equiv \langle s_{i\sigma}^\dagger s_{i\sigma} \rangle$ is site- and spin-independent (and equals 0.5 for zero doping).

The svivon band is then characterized [33] by V-shape minima of energy $k_B T / \mathcal{O}(N)$ at the points $\pm\mathbf{k}_0 \equiv \pm\mathbf{Q}/2$. There are four inequivalent values of \mathbf{k}_0 , introducing a broken symmetry:

$$\mathbf{k}_0 \equiv \frac{\mathbf{Q}}{2} = \pm \frac{\pi}{2a}(\hat{x} + \hat{y}) \quad \text{or} \quad \pm \frac{\pi}{2a}(\hat{x} - \hat{y}). \quad (21)$$

They correspond to two degenerate condensates of rectangular symmetry, with axes along the $\hat{x} + \hat{y}$ and $\hat{x} - \hat{y}$ directions. Within the grand-canonical scheme, the svivon minima at $\pm\mathbf{k}_0$ in the AF condensates are self-consistently formed due to [33] large values of both

$$\begin{aligned} n^s(\mathbf{k}) &\equiv \langle s_\sigma^\dagger(\mathbf{k}) s_\sigma(\mathbf{k}) \rangle, \quad \text{and} \quad m^s(\mathbf{k}) \equiv \langle s_\uparrow(\mathbf{k}) s_\downarrow(-\mathbf{k}) \rangle \\ (\text{note that } n^s &= \frac{1}{N} \sum_{\mathbf{k}} n^s(\mathbf{k})), \end{aligned} \quad (22)$$

around the minima (becoming $\mathcal{O}(N)$ at $\mathbf{k} = \pm\mathbf{k}_0$).

In SC stoichiometries, the minimum of the lagron spectrum at point \mathbf{Q} splits into the four \mathbf{Q}_m points, introduced in Eq. (20), and shown in Fig. 2. As was mentioned above, this spectrum corresponds to a combination of four condensates, in which AF order is replaced by striped structures, corresponding to svivon condensates [46] of energy minima which are shifted [16] from $\pm\mathbf{k}_0$ (see discussion below).

The svivon minimal energies, within their condensates, are then [16] *not* as close to zero as $k_B T / \mathcal{O}(N)$ (and the

shape of the minima becomes parabolic close to the bottom), since they are evaluated on the basis of a lower-free-energy state (due to coupling to the QEs) which is a combination of the condensates (and thus it consists of fluctuating striped structures); but one still has (within each condensate) $m^s(\mathbf{k}) \neq 0$ which are large, together with $n^s(\mathbf{k})$, around the energy minima (though not as large as $\mathcal{O}(N)$ —see below).

Note that $\lambda(\mathbf{q})$ and $p^\lambda(\mathbf{q})$ in Eq. (11) scale with $l(\pm\mathbf{q})$ and $l^\dagger(\pm\mathbf{q})$ which behave like $\langle l^\dagger(\pm\mathbf{q})l(\pm\mathbf{q}) \rangle^{\frac{1}{2}}$ for $\mathbf{q} \cong \mathbf{Q}_m$, while $n^s(\mathbf{k})$ and $m^s(\mathbf{k})$ are determined through Eq. (22). Thus, the fact that the svivon energy minima do not get too close to zero enables such a lagron spectrum (thus with the V-shape energy minima specified in Eq. (20)) to yield values of $\lambda(\mathbf{q})$ and $p^\lambda(\mathbf{q})$ which have appropriate values to maintain the constraint [46] within the $\mathbf{q} \simeq \mathbf{Q}_m$ ranges.

Bose-condensed systems are characterized by nonzero expectation values of the field operators [39, 40]. Treating the (combined) svivon condensates adiabatically, one can express, through Eq. (22), $m^s(\mathbf{k}) = \langle s_\uparrow(\mathbf{k}) \rangle \langle s_\downarrow(-\mathbf{k}) \rangle$; these $\langle s_\uparrow(\mathbf{k}) \rangle$ and $\langle s_\downarrow(-\mathbf{k}) \rangle$ have the same magnitude, but different phases due to the different sites where the contribution to $\sigma = \uparrow$ and $\sigma = \downarrow$ svivons is maximal, and their phases fluctuate in a correlated manner. Terms including such expectation values in the final result of a calculation, do not vanish due to phase fluctuations only if they appear as products of the form $\langle s_\uparrow(\mathbf{k}) \rangle \langle s_\downarrow(-\mathbf{k}) \rangle$ (which are expressed as $m^s(\mathbf{k})$).

The second Hamiltonian term, treated through a self-consistent second-order diagrammatic expansion, accounts for the coupling between QEs and svivon fluctuations which are expressed through terms of the form $s_\sigma(\mathbf{k}) - \langle s_\sigma(\mathbf{k}) \rangle$. It is obtained by expanding \mathcal{H}^a , in the rhs of Eq. (9), in such fluctuations (when the svivon operators there are expressed in the \mathbf{k} representation), and treating them as a perturbation. This Hamiltonian term could be approximated as (see Eq. (17)):

$$\mathcal{H}' \cong \frac{1}{N} \sum_{\mathbf{k}\mathbf{k}'\mathbf{k}''\sigma} \{ \tilde{t}(\mathbf{k}' + \mathbf{k}'') \langle s_\sigma^\dagger(\mathbf{k}' + \mathbf{k}'' - \mathbf{k}) \rangle q^\dagger(\mathbf{k}) \times q(\mathbf{k}') [s_\sigma^\dagger(\mathbf{k}'') - \langle s_\sigma(\mathbf{k}'') \rangle] + h.c. \}, \quad (23)$$

where $\tilde{t}(\mathbf{k})$ is the Fourier transform of $\tilde{t}(\mathbf{R})$ which is, approximately, defined similarly to $t(\mathbf{R})$ in Eq. (2), modifying t' and t'' (due to the Δt terms in Eq. (8)) to $\tilde{t}' \cong t' + 2n^s J$ and $\tilde{t}'' \cong t'' + n^s J$, respectively (while t remains unchanged).

Following the standard treatment of Bose-condensed systems [39, 40], the (Bogoliubov) boson creation operator of an excited svivon state of wave vector \mathbf{k} and spin σ is derived as [33] a combination of $s_\sigma^\dagger(\mathbf{k})$ and $s_{-\sigma}(-\mathbf{k})$. A 2×2 energy plus self-energy matrix is derived within the basis created by the spinor operator $(s_\uparrow^\dagger(\mathbf{k}), s_\downarrow(-\mathbf{k}))$. It is expressed as

$$\underline{\epsilon}_0^s(\mathbf{k}) + \underline{\Sigma}^s(\mathbf{k}, z) = [\epsilon_0^s(\mathbf{k}) + \Sigma^s(\mathbf{k}, z)] \underline{1} + \Re \Phi^s(\mathbf{k}, z) \underline{\tau}_1 + \Im \Phi^s(\mathbf{k}, z) \underline{\tau}_2, \quad (24)$$

where $\underline{1}$, $\underline{\tau}_1$ and $\underline{\tau}_2$ are the unity and Pauli matrices, and z are “complex energies” [39, 40]. The diagonal terms in the rhs of Eq. (24) include $\epsilon_0^s(\mathbf{k})$, derived within the mean-field approximation, and $\Sigma^s(\mathbf{k}, z)$, derived through the diagrammatic expansion. The non-diagonal terms, $\Phi^s(\mathbf{k}, z)$ and $\Phi^s(\mathbf{k}, z)^*$, are derived through *both* the mean-field and the diagrammatic calculations; they exist due to the nonzero values of $m^s(\mathbf{k}')$.

Two degenerate Bogoliubov svivon states, corresponding to $(\mathbf{k} \uparrow)$ and $(-\mathbf{k} \downarrow)$, are derived as a function of z , and their boson annihilation operators are denoted by $\tilde{s}_\uparrow(\mathbf{k}, z)$ and $\tilde{s}_\downarrow(-\mathbf{k}, z)$, respectively; $s_\uparrow(\mathbf{k})$ and $s_\downarrow(-\mathbf{k})$ are then expressed as [33]:

$$s_\sigma(\sigma\mathbf{k}) = \exp(i\phi_{\mathbf{k}}^s(z)/2) [\cosh(\xi_{\mathbf{k}}^s(z)) \tilde{s}_\sigma(\sigma\mathbf{k}, z) + \sinh(\xi_{\mathbf{k}}^s(z)) \tilde{s}_{-\sigma}^\dagger(-\sigma\mathbf{k}, z)], \quad (25)$$

where the coefficients $\xi_{\mathbf{k}}^s(z)$ and $\phi_{\mathbf{k}}^s(z)$ are determined by the requirement that the matrix $\underline{\epsilon}_0^s(\mathbf{k}) + \underline{\Sigma}^s(\mathbf{k}, z)$ in Eq. (24) is diagonalized under the transformation to these Bogoliubov states. This transformation diagonalizes Dyson's equation [39, 40], yielding the poles of the diagonalized svivon Green's function $\tilde{\mathcal{G}}^s(\mathbf{k}, z)$ at:

$$z = \tilde{\epsilon}_0^s(\mathbf{k}) + \tilde{\Sigma}^s(\mathbf{k}, z), \text{ where } \Im \tilde{\Sigma}^s(\mathbf{k}, z) = \cosh(2\xi_{\mathbf{k}}^s(z)) \Im \Sigma^s(\mathbf{k}, z),$$

$$\tilde{\epsilon}_0^s(\mathbf{k}) + \Re \tilde{\Sigma}^s(\mathbf{k}, z) \equiv E^s(\mathbf{k}, z) = \text{sign}[\epsilon_0^s(\mathbf{k}) + \Re \Sigma^s(\mathbf{k}, z)] \sqrt{[\epsilon_0^s(\mathbf{k}) + \Re \Sigma^s(\mathbf{k}, z)]^2 - |\cos(\psi_{\mathbf{k}}^s(z) - \phi_{\mathbf{k}}^s(z)) \Phi^s(\mathbf{k}, z)|^2},$$

$$\Phi^s(\mathbf{k}, z) = |\Phi^s(\mathbf{k}, z)| \exp(i\psi_{\mathbf{k}}^s(z)), \text{ and } |\cos(\psi_{\mathbf{k}}^s(z) - \phi_{\mathbf{k}}^s(z))| = \min \left[1, \left| \frac{\epsilon_0^s(\mathbf{k}) + \Re \Sigma^s(\mathbf{k}, z)}{\Phi^s(\mathbf{k}, z)} \right| \right]. \quad (26)$$

The coefficients $\xi_{\mathbf{k}}^s(z)$ are obtained through:

$$\cosh(2\xi_{\mathbf{k}}^s(z)) = \frac{\epsilon_0^s(\mathbf{k}) + \Re \Sigma^s(\mathbf{k}, z)}{E^s(\mathbf{k}, z)}, \quad (27)$$

$$\sinh(2\xi_{\mathbf{k}}^s(z)) = -\frac{\cos(\psi_{\mathbf{k}}^s(z) - \phi_{\mathbf{k}}^s(z)) |\Phi^s(\mathbf{k}, z)|}{E^s(\mathbf{k}, z)}.$$

The svivon spectral functions are obtained through:

$$A^s(\mathbf{k}, \omega) \equiv \Im \tilde{\mathcal{G}}^s(\mathbf{k}, \omega - i0^+)/\pi$$

$$= \frac{\Gamma^s(\mathbf{k}, \omega)/2\pi}{[\omega - E^s(\mathbf{k}, \omega)]^2 + [\frac{1}{2}\Gamma^s(\mathbf{k}, \omega)]^2}, \quad (28)$$

where $\Gamma^s(\mathbf{k}, \omega) \equiv 2\Im\tilde{\Sigma}^s(\mathbf{k}, \omega - i0^+)$. $\tilde{\mathcal{G}}^s(\mathbf{k}, z)$ has positive- and negative-energy poles [16] (see below); $\Gamma^s(\mathbf{k}, \omega)$ and $A^s(\mathbf{k}, \omega)$ are positive for $\omega > 0$ and negative for $\omega < 0$, and the ω -integral of A^s (including the contributions of the different poles) is normalized to one.

The values of $n^s(\mathbf{k})$ and $m^s(\mathbf{k})$ in Eq. (22) are obtained through [33]:

$$\begin{aligned} n^s(\mathbf{k}) &= \int d\omega \cosh(2\xi_{\mathbf{k}}^s(\omega)) A^s(\mathbf{k}, \omega) [b_T(\omega) + \tfrac{1}{2}] - \tfrac{1}{2}, \\ m^s(\mathbf{k}) &= \int d\omega \sinh(2\xi_{\mathbf{k}}^s(\omega)) A^s(\mathbf{k}, \omega) [b_T(\omega) + \tfrac{1}{2}] \\ &\quad \times \exp(i\phi_{\mathbf{k}}^s(\omega)), \end{aligned} \quad (29)$$

where $b_T(\omega) \equiv 1/[\exp(\omega/k_B T) - 1]$ is the Bose distribution function; one has $b_T(\omega) + \frac{1}{2} \cong \frac{1}{2}\text{sign}(\omega)$ in the high- $|\omega|/k_B T$ limit.

A lagron spectrum of the type presented in Fig. 2 determines eight degenerate svivon condensates with energy minima at the points:

$$\pm \frac{\mathbf{Q}_m}{2} = \pm \left(\mathbf{k}_0 + \frac{\delta\mathbf{q}_m}{2} \right), \quad (30)$$

for each of the four values of m in Eq. (20), and the two possibilities for $\pm\mathbf{k}_0$ in Eq. (21). Lagrons at the $\pm\mathbf{Q}_m$ points (of the energies in Eq. (20)) induce symmetric positive- and (lower weight) negative-energy svivon spectral branches [16], corresponding to the splitting of the Green's functions poles, due to the inhomogeneities. The phases $\psi_{\mathbf{k}}^s(\omega)$ and $\phi_{\mathbf{k}}^s(\omega)$ then satisfy:

$$\begin{aligned} \psi_{-\mathbf{k}}^s(\omega) &= \psi_{\mathbf{k}}^s(-\omega) = \psi_{\mathbf{k}}^s(\omega) + \pi, \\ \phi_{-\mathbf{k}}^s(\omega) &= \phi_{\mathbf{k}}^s(-\omega) = \phi_{\mathbf{k}}^s(\omega). \end{aligned} \quad (31)$$

Thus, by Eqs. (26,31), the svivon condensation order parameter $\Phi^s(\mathbf{k}, \omega)$ reverses its sign upon the sign reversal of either \mathbf{k} or ω .

The effects of entropy at high T , and of pairing at low T (see below), drive the system to a combination state of the eight broken-symmetry condensates, specified in Eq. (30), at high T , and of four of them, corresponding to one of the two possibilities for $\pm\mathbf{k}_0$ in Eq. (21), at low T . Such combinations reflect fluctuations between the condensates. Consequently, the planar symmetry of the system remains square at high T , while at low T it is broken to a rectangular symmetry with axes along the $\hat{x} + \hat{y}$ and $\hat{x} - \hat{y}$ directions, in agreement with experiment. Svivon spectral functions in the SC state have been presented elsewhere [16].

C. Unpaired QEs and electrons

1. General features

The QE spectrum is evaluated treating fluctuations between the combined svivon condensates adiabatically. Thus, in analogy to the effect of lattice dynamics on

single-electron states in a crystal, the contribution of coupling to the different svivon condensates to the QE states is averaged out, and $\underline{\mathcal{G}}^q$ remains diagonal in the \mathbf{k} representation (corresponding to the lattice plus a superstructure determined by \mathbf{Q} —see below), though scattering is introduced. This conclusion remains approximately correct also under the random long-range distribution of static inhomogeneities, observed in a certain range of the phase diagram [21, 22], since the variation that they introduce to the charge distribution, and thus to the effective potential of the QEs, is rather small and insufficient to introduce Anderson localization.

Since, by Eqs. (21,30), the points $\pm\mathbf{Q}_m/2$, of the svivon energy minima within their condensates [16], are symmetrical around $\pm\mathbf{k}_0 \equiv \pm\mathbf{Q}/2$, the averaged svivon spectral contribution to the QE states is symmetrical around these points as well; consequently, it is invariant [16] under a \mathbf{k} -shift of \mathbf{Q} (note that $2\mathbf{Q}$ is reciprocal-lattice vector), and thus it corresponds to an effective AF order. The symmetry of the electron spectrum is the same as that of the convoluted QE-svivon spectrum (see Eqs. (5,19)). Thus, since the electron spectrum is invariant under a \mathbf{k} -shift of $2\mathbf{Q}$, the QE spectrum must also be invariant under a \mathbf{k} -shift of \mathbf{Q} .

By introducing appropriate phase factors to the QE and svivon states, their \mathbf{k} values can be shifted by \mathbf{k}_0 or $-\mathbf{k}_0$, so that corresponding QE and electron bands appear in the same BZ areas. Thus, by Eq. (30), a shift of $-\mathbf{k}_0$ in the svivon \mathbf{k} values results in the shift of the energy minima in their condensates from $\pm\mathbf{Q}_m/2$ to $\delta\mathbf{q}_m/2$ and $\mathbf{Q} - \delta\mathbf{q}_m/2$.

The evaluated QE spectral functions $A^q(\mathbf{k}, \omega)$ for hole-doped cuprates, corresponding to $n^s = 0.42$ (thus close to “optimal stoichiometry”), at $k_B T = 0.01$ eV, within the “hump phase” [42], are presented in Fig. 3(a-c). The calculation is based on a typical svivon spectrum, where the averaged svivon-condensate spectra [16] have broad energy minima which are approximately linear in T in this phase (see below).

The determination of the svivon and QE linewidths is discussed below, and they are, approximately, consistent (within the hump phase) with the marginal-Fermi-liquid (MFL) phenomenology [13]. The fact that the QE spectrum is invariant under a \mathbf{k} -shift of \mathbf{Q} , is reflected in the existence of *equivalent* “main” and “shadow” QE bands obtained from each other by a \mathbf{Q} shift.

As was discussed above, the QE spectrum has a mean-field “bare-band” part, $\epsilon_0^q(\mathbf{k})$, and a “dressed” part, introduced by self-energy corrections $\Sigma^q = \Sigma_s^q + \Sigma_\lambda^q$, due to coupling to svivon fluctuations (through \mathcal{H}') and to lagrons (through $\Delta\mathcal{H}$), respectively. The QE spectral functions are obtained through:

$$\begin{aligned} A^q(\mathbf{k}, \omega) &\equiv \Im\mathcal{G}^q(\mathbf{k}, \omega - i0^+)/\pi \\ &= \frac{\Gamma^q(\mathbf{k}, \omega)/2\pi}{[\omega - \epsilon_0^q(\mathbf{k}) - \Re\Sigma^q(\mathbf{k}, \omega)]^2 + [\Gamma^q(\mathbf{k}, \omega)/2]^2}, \end{aligned} \quad (32)$$

where $\Gamma^q(\mathbf{k}, \omega) \equiv 2\Im\Sigma^q(\mathbf{k}, \omega - i0^+)$. The effect of inhomogeneity is that the QE Green's function $\mathcal{G}^q(\mathbf{k}, z)$ has more

than one pole (see below). The ω -integral of $A^q(\mathbf{k}, \omega)$, including the contributions of the different poles, is normalized to one.

The effect of the nearest-neighbor transfer integral t on $\epsilon_0^q(\mathbf{k})$ drops out (due to opposite-sign contributions of svivon states shifted by \mathbf{Q}). The effects of t' and t'' (see Eq. (2)) on $\epsilon_0^q(\mathbf{k})$ are renormalized, due to svivon and Δt terms in Eqs. (8,9), and they could be, approximately, replaced by $\tilde{t}' = 2n^s(t' + 4n^s J)$ and $\tilde{t}'' = 2n^s(t'' + 2n^s J)$, respectively. The n^s factors here are derived from the summation of expectation values of products of svivon operators which could be expressed both in terms of the $n^s(\mathbf{k})$ and of the $m^s(\mathbf{k})$ factors (which have a major contribution at the vicinity of the svivon energy minima), and applying Eqs. (22), (27) and (29).

The independence of $\epsilon_0^q(\mathbf{k})$ on t reflects the fact that a QE represents [16] an approximate electron for which the creation operator of its svivon component, through Eq. (5), is replaced by its expectation value. Since averaging the svivon spectrum over its degenerate condensates corresponds to an effective AF order (see above), the dependence of the QE spectrum on nearest-neighbor hopping processes (which disturb this order) must involve svivon fluctuations, through \mathcal{H}' in Eq. (23). Thus, the effect of t on it is introduced by the self-energy term:

$$\begin{aligned} \Sigma_s^q(\mathbf{k}, z) &\cong \frac{2}{N^2} \sum_{\mathbf{k}'\mathbf{k}''} \int d\omega^q A^q(\mathbf{k}', \omega^q) \left\{ |\tilde{t}(\mathbf{k}' + \mathbf{k}'')|^2 \right. \\ &\times |m^s(\mathbf{k}' + \mathbf{k}'' - \mathbf{k})| \left\{ \int d\omega^s A^s(\mathbf{k}'', \omega^s) \right. \\ &\times \left\{ \cosh^2(\xi_{\mathbf{k}}^s(\omega^s)) \left[\frac{b_T(\omega^s) + f_T(-\omega^q)}{z - \omega^s - \omega^q} \right] \right. \\ &+ \left. \sinh^2(\xi_{\mathbf{k}}^s(\omega^s)) \left[\frac{b_T(\omega^s) + f_T(\omega^q)}{z + \omega^s - \omega^q} \right] \right\} \\ &- \left. \frac{|m^s(\mathbf{k}'')|}{z - \omega^q} \right\} + |\tilde{t}(\mathbf{k} + \mathbf{k}'')|^2 |m^s(\mathbf{k} + \mathbf{k}'' - \mathbf{k}')| \\ &\times \left\{ \int d\omega^s A^s(\mathbf{k}'', \omega^s) \left\{ \cosh^2(\xi_{\mathbf{k}}^s(\omega^s)) \right. \right. \\ &\times \left. \left[\frac{b_T(\omega^s) + f_T(\omega^q)}{z + \omega^s - \omega^q} \right] + \sinh^2(\xi_{\mathbf{k}}^s(\omega^s)) \right. \\ &\times \left. \left. \left[\frac{b_T(\omega^s) + f_T(-\omega^q)}{z - \omega^s - \omega^q} \right] \right\} - \frac{|m^s(\mathbf{k}'')|}{z - \omega^q} \right\} \left. \right\}, \end{aligned} \quad (33)$$

where $f_T(\omega) \equiv 1/[\exp(\omega/k_B T) + 1]$ is the Fermi distribution function.

By Eq. (29), the magnitudes of the $|m^s(\mathbf{k}'')|$ terms in the rhs of Eq. (33), and of the integrated terms that they are subtracted from, differ (in the vicinity of the svivon energy minima, where the major contribution to the \mathbf{k}'' summation comes from) mainly because of their different energy denominators. When the signs of the denominators of these terms are opposite, they *both* contribute to “pushing” the QE energies towards zero. Consequently, the Σ_s^q -induced self-consistent renormalization of the QE energies is a shift towards zero which becomes larger closer to zero.

This results in BZ areas of “flat” QE bands which would have been at energies of the $k_B T$ scale, if it were not for the effect of QE-lagron coupling (introducing to them the structure discussed below). The transition between these low-energy areas and the higher-energy BZ areas is through an almost discontinuous wide-energy zone, as is viewed in Fig. 3(a-b). This peculiar spectral structure reflects the distinction between strongly renormalized low-energy QEs which are subject to hopping processes maintaining the stripe-like inhomogeneities, and high-energy QEs which are not; it is primarily determined by the contribution of the hopping parameter t to \mathcal{H}' in Eq. (23).

The corresponding electron spectral functions $A^d(\mathbf{k}, \omega) \equiv \Im \mathcal{G}^d(\mathbf{k}, \omega - i0^+)/\pi$, obtained on the basis of Eq. (19), are presented in Fig. 3(d-f). The high weight of the svivon poles around their minimal energies [16] results in band-like features in the electron spectrum which follow the QE band (see below).

The effect of the multiple-scattering FL-like electron poles in Eq. (19) is the removal of the equivalence between the main and the shadow electron bands, as is observed in experiment [48, 49]. However, non-FL behavior associated with the QE Fermi surface (FS) in Fig. 3(c) persists, contributing the hole and electron pocket-like features appearing in Fig. 3(f), and detected in experimental data [50] mainly in the underdoped regime. The existence of such FS pockets has also been confirmed in the observation of quantum oscillations [51, 52]. On the other hand, the FL-like contribution to the normal-state electron spectrum is dominant in the overdoped regime, where quantum oscillations typical of a large FS have been observed [53].

The low-energy flat QE bands, and the almost discontinuous transition from them to the high-QE-energy BZ areas are modified in the electron spectrum (see Fig. 3(d-e)) to low-energy kinks followed by “waterfalls”, in agreement with experiment [54, 55]. As was discussed above, this spectral anomaly results from the renormalization of the QEs, such that their low-energy excitations maintain the stripe-like inhomogeneities.

2. Low-energy range

The self-energy term, introduced by QE-lagron coupling through $\Delta \mathcal{H}$ in Eq. (12) is expressed (for un-paired QEs) as:

$$\begin{aligned} \Sigma_\lambda^q(\mathbf{k}, z) &\cong \frac{1}{N} \sum_{\mathbf{q}} \int d\omega^q A^q(\mathbf{k} - \mathbf{q}, \omega^q) \\ &\times F_T(\mathbf{q}, \omega^q, z), \quad \text{where} \quad (34) \\ F_T(\mathbf{q}, \omega^q, z) &= |\gamma(\mathbf{q})|^2 \left[\frac{b_T(\omega^\lambda(\mathbf{q})) + f_T(-\omega^q)}{z - \omega^\lambda(\mathbf{q}) - \omega^q} \right. \\ &\quad \left. + \frac{b_T(\omega^\lambda(\mathbf{q})) + f_T(\omega^q)}{z + \omega^\lambda(\mathbf{q}) - \omega^q} \right]. \end{aligned}$$

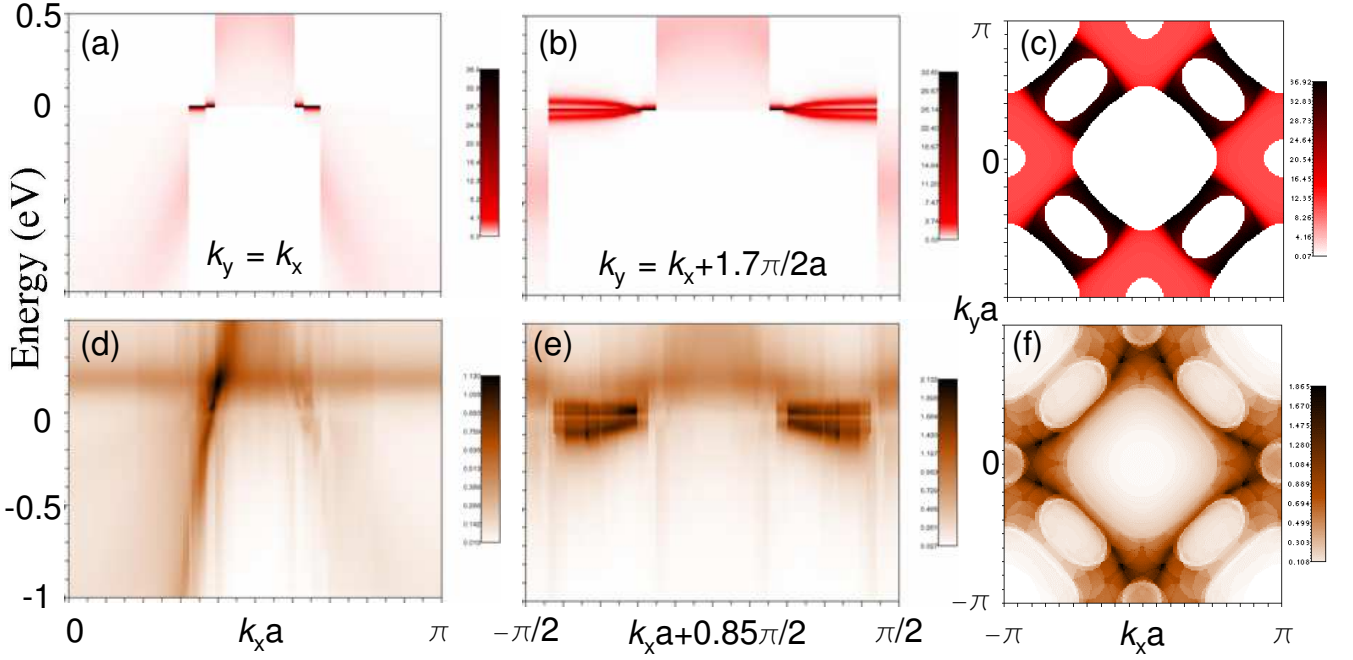


FIG. 3: The QE (a-c) and electron (d-f) spectral functions in optimally hole-doped cuprates along a “line of nodes” (a,d), along a parallel line (b,e) shifted by $0.425\pi(\hat{y} - \hat{x})$, and on the “Fermi surface” (c,f), determined at $\omega = -0.1k_B T$.

Within the low-QE-energy BZ areas, the ω -dependence of Σ_s^q is weak, and its imaginary part is relatively small. Consequently ϵ_0^q could be renormalized there to include the effect of Σ_s^q , and the anomalous behavior of $A^q(\mathbf{k}, \omega)$ is obtained approximating Σ^q in Eq. (32) by the QE-lagron term Σ_λ^q in Eq. (34).

As is viewed in Fig. 2, one could specify the lagrons according to five ranges in the BZ: (1) those at the four energy minima points \mathbf{Q}_m in Eq. (20), referred to as “ \mathbf{Q}_m lagrons”; (2) those at the lagron “extended saddle point” (ESP) around point \mathbf{Q} , referred to as “ \mathbf{Q} -ESP lagrons” which introduce an energy scale $\sim\omega^\lambda(\mathbf{Q})$; (3) those of energies $\lesssim\omega^\lambda(\mathbf{Q})$, around the \mathbf{Q}_m points, referred to as “ \mathbf{Q}_m -vicinity lagrons”; (4) those around the high-energy saddle points at $(\pi/a)\hat{x}$ and $(\pi/a)\hat{y}$, referred to as “high-energy SP lagrons”; (5) those within the rest of the lagron spectrum, referred to as “continuum lagrons” which occupy most of their phase space.

Analogous expressions to Eq. (34), where A^q , ω^q and $f_T(\pm\omega^q)$ are replaced by A^s , ω^s and $-b_T(\pm\omega^s)$ (and \cosh^2 and \sinh^2 factors are introduced—see below), are obtained for the contribution of $\Delta\mathcal{H}$ in Eq. (12) to the sivon self-energy terms, appearing in Eq. (24). The \mathbf{Q} -ESP lagrons then help stabilize high-spectral-weight sivon states somewhat below $\omega^\lambda(\mathbf{Q})$ in the SC state. Consequently [16], the resonance-mode energy E_{res} is somewhat above $\omega^\lambda(\mathbf{Q})$ [56].

The spectral functions of low-energy QEs, coupled to each other through \mathbf{Q}_m lagrons, split (due to the large values of the Bose functions in Eq. (34)—see Eq. (20) and the discussion above) into positive- and negative-energy peaks, referred to as “humpons”; such a splitting is expected due to the spin-density waves (SDW) associated

with the stripe-like inhomogeneities which are generated by the lagron spectrum in Fig. 2.

As was discussed above, within some range of temperatures, free energy (where the effects of both energy and entropy are accounted for) is minimized for a phase of fluctuating inhomogeneities. For unpaired QEs, a third QE spectral peak appears in this phase, between the positive- and negative-energy humpons (as is sketched in Fig. 4(a)), and it is referred to as a “stripon”; it represents low-energy charge carriers due to the fluctuating charged stripes.

A stripon at point \mathbf{k} is associated with the pole of $\mathcal{G}^q(\mathbf{k}, z)$ which corresponds to lattice periodicity, while the humpons result from poles corresponding to the inhomogeneities. The energies $\sim\omega_H$ of the humpon peaks correspond to the energy associated with the inhomogeneities, and could be as high as $\sim J$. As is discussed below, the stripon peak is sharper than the humpon peaks for $k_B T \ll \omega_H$, and its width increases with T .

The $\gamma(\mathbf{q})$ coefficients in Eq. (12) remain finite for $\mathbf{q} \rightarrow \mathbf{Q}_m$ (see Eq. (16) and the above discussion) and their values there, as well as the values of $\omega^\lambda(\mathbf{Q}_m)$ in Eq. (20), are self-consistently determined to yield such humpon energies due to coupling to lagrons, and specifically those around the \mathbf{Q}_m points, through Eq. (34). The contribution of the \mathbf{Q} -ESP lagrons results in $\omega_H > \sim\omega^\lambda(\mathbf{Q})$.

Within the low-QE-energy BZ areas there are “nodal areas”, close to the lines of nodes $y = \pm x$, and “antinodal areas”, close to circles of radii of about $(\pi/4a) - (\pi/3a)$ around the $(\pi/a)\hat{x}$ and $(\pi/a)\hat{y}$ points. As can be seen in Fig. 3(c), a difference between the QEs in the antinodal and nodal areas is that the first, but *not* the latter (if they are close enough to the lines of nodes), can be coupled to

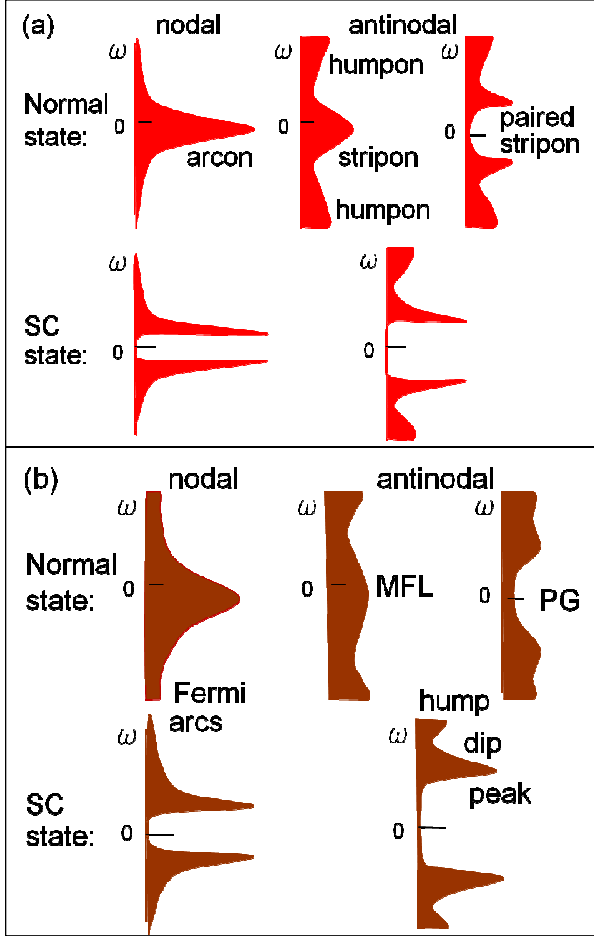


FIG. 4: Typical low-energy QE (a) and electron (b) spectral functions in the normal and SC states, in nodal (arcon, Fermi arcs) and antinodal (humpon, stripon, peak, dip, hump) points in hole-doped cuprates. Their structures are presented in the MFL, PG, and SC states (see discussion in the text).

other low-energy QEs through (up to four) \mathbf{Q}_m lagrons (see Eq. (20)).

Consequently, the spectral functions of unpaired QEs within the nodal areas (referred to as “arcons”) are characterized by a simple peak (due to one- \mathcal{G}^q pole per \mathbf{k} point), of the $k_B T$ energy scale, as is sketched in Fig. 4(a). On the other hand, the spectral functions of QEs within the antinodal areas are characterized by the above humpon–stripon–humpon structure. As will be discussed below, these spectral features of the QEs (specified as arcons, stripons and humpons) are associated with different physical features in the cuprates.

Thus a two-component scenario is described here, concerning the symmetries of the low-energy QEs in the nodal and antinodal areas, due to the different number of poles in $\mathcal{G}^q(\mathbf{k}, z)$ they correspond to. An increase in T results in an increase in the spectral weight within the stripons peaks in the antinodal areas (on the expense of those within the humpon peaks), and in the shift of the

borderline between the nodal and antinodal areas (concerning the symmetry of the QEs) towards the antinodal ones. When $k_B T$ crosses ω_H , a crossover occurs from the above inhomogeneity-derived two-component scenario to a homogeneous one, where all the low-energy QEs correspond to one- \mathcal{G}^q pole per \mathbf{k} point.

For $k_B T \ll \omega_H$, the arcon and stripon peaks at different \mathbf{k} points can be treated as an almost flat band. The energy center of this band is close to the centers of most of the peaks, determined through (see Eq. (32)) the relation: $\omega = \epsilon_0^q(\mathbf{k}) + \Re \Sigma^q(\mathbf{k}, \omega)$. The T dependence of the band center approximately corresponds to that of the effective QE chemical potential $\mu - \lambda$ (see Eq. (9)); thus [34], this T dependence scales with $k_B T$, if the band is not half filled and its width is not larger than $\sim k_B T$, and it is weaker, otherwise.

The above low-energy spectral features of the QEs are consistent with the nodal–antinodal dichotomy occurring in the cuprates. Furthermore, they provide convenient QPs to study, discuss, and analyze (see below) their peculiar low-energy spectrum and its consequences on the derivation of their anomalous physical properties.

3. QE scattering rates

The scattering rates $\Gamma^q(\mathbf{k}, \omega) \equiv 2\Im \Sigma^q(\mathbf{k}, \omega - i0^+)$ of unpaired low-energy QEs can be expressed, on the basis of Eq. (34), as:

$$\begin{aligned} \Gamma^q(\mathbf{k}, \omega) \cong & \frac{2\pi}{N} \sum_{\mathbf{q}} |\gamma(\mathbf{q})|^2 \{ A^q(\mathbf{k} - \mathbf{q}, \omega - \omega^\lambda(\mathbf{q})) \\ & \times [b_T(\omega^\lambda(\mathbf{q})) + f_T(\omega^\lambda(\mathbf{q}) - \omega)] \\ & + A^q(\mathbf{k} - \mathbf{q}, \omega + \omega^\lambda(\mathbf{q})) \\ & \times [b_T(\omega^\lambda(\mathbf{q})) + f_T(\omega^\lambda(\mathbf{q}) + \omega)] \}, \end{aligned} \quad (35)$$

where an approximately \mathbf{q} -independent $|\gamma(\mathbf{q})|^2$ could be assumed (see Eq. (16) and the above discussion).

Eq. (35) is applied to study the behavior of Γ^q , specifically in the low- and high- $|\omega|/k_B T$ limits. As can be viewed in Fig. 3(a-b), the $\mathbf{k} - \mathbf{q}$ points where A^q contributes to Eq. (35), for $|\omega| \lesssim 0.3$ eV, consist mainly of those within the low-QE-energy BZ areas, shown in Fig. 3(c). The ω dependencies of $A^q(\mathbf{k}, \omega)$ within the low-energy arcon and stripon peaks, the mid-energy humpon peaks, and the high-energy areas, are specified in terms of canonical functions $A_{\text{le}}^q(\omega)$, $A_{\text{me}}^q(\omega)$ and $A_{\text{he}}^q(\omega)$, respectively.

The energies at the maxima of $A_{\text{he}}^q(\omega)$ are generally too high to have a significant contribution to Γ^q , through Eqs. (32,35), within the ranges of T and ω studied here. The humpon peaks (characterized by A_{me}^q) exist within the low-energy antinodal areas in the $k_B T \ll \omega_H$ regime, and if also $|\omega| \ll \omega_H$, their role is negligible, similarly to that of A_{he}^q ; for $|\omega| \gtrsim \omega_H$, they are approached as a case of A_{le}^q . In the $k_B T \gtrsim \omega_H$ regime the humpon and

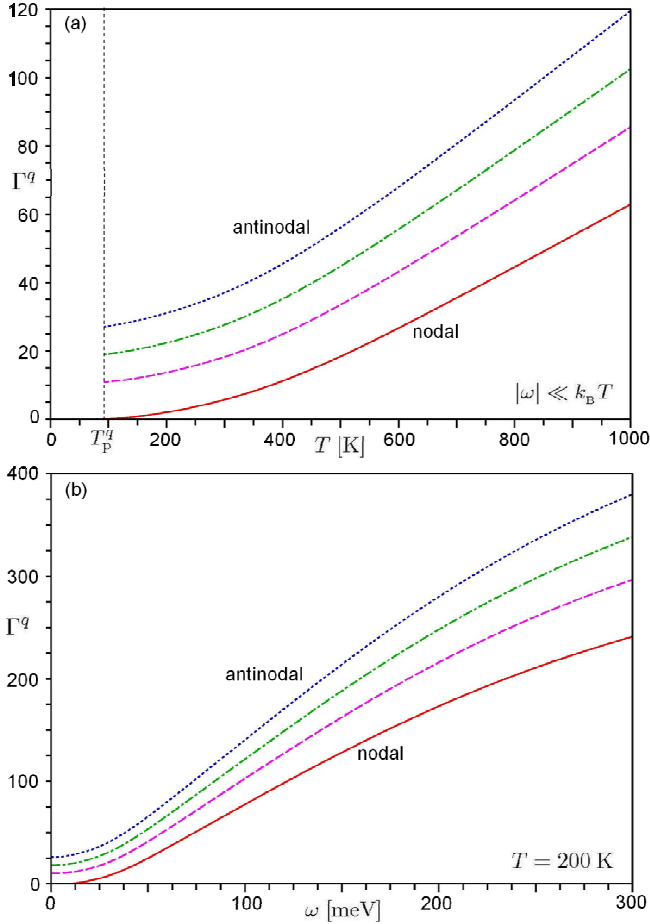


FIG. 5: Typical results (in arbitrary units) for the QE scattering rates Γ^q , at [41] $T > T_p^q$, in \mathbf{k} points ranging between the lines of nodes and the antinodal BZ areas, as (a) a function of T for $|\omega| < k_B T_p^q$, and (b) a function of ω , for $k_B T < \Gamma_{0a}^q$ (see discussion in the text).

stripon peaks are merged into an arcon peak which is again approached as a case of A_{le}^q .

The evaluation of $\Gamma^q(\mathbf{k}, \omega)$ is detailed in Appendix A; typical results are presented in Figs. 5(a-b), as functions

of T and ω , in the low $|\omega|/k_B T$ limit, and at T above [41] T_p^q and below Γ_{0a}^q/k_B (see Appendix A) and $\omega^\lambda(\mathbf{Q})/k_B$, respectively; these results include \mathbf{k} points ranging between the nodal and antinodal BZ areas. Approximate linear dependencies of $\Gamma^q(\mathbf{k}, \omega)$ on T and on ω are found in the low- and high- $|\omega|/k_B T$ limits, respectively, above a \mathbf{k} -dependent low-energy scale $\omega_L(\mathbf{k})$. The high- $|\omega|$ extent of this linear dependence is limited by the high-energy extent of the lagron spectrum in Fig. 2 (which could exceed ~ 0.3 eV), and the high- T extent is limited by the phase stability. The contribution of humpons to Γ^q results in the increase of the slopes of the Γ^q vs $k_B T$ and $|\omega|$ curves when their increasing values approach ω_H .

For $k_B T \& |\omega| \ll \omega_L(\mathbf{k})$, $\Gamma^q(\mathbf{k}, \omega)$ can be approximated as $\Gamma_0^q(\mathbf{k})$ (determined in Eq. (A3)) which is close zero on the lines of nodes, and to Γ_{0a}^q in the antinodal areas. As is discussed in Appendix A, the value of $\omega_L(\mathbf{k})$ is close to Γ_{0a}^q in the antinodal areas, and is somewhat smaller than [56] $\omega^\lambda(\mathbf{Q}) \simeq \frac{3}{4}E_{res}$ on the lines of nodes; $\omega^\lambda(\mathbf{Q})$ is smaller than Γ_{0a}^q in the heavily underdoped regime, and their values cross each other when the doping level is increased.

4. Svivon scattering rates

The svivon scattering rates Γ^s include a term Γ_λ^s , due to their coupling to lagrons through $\Delta\mathcal{H}$ in Eq. (12), yielding an analogous expression to that for Γ^q in Eq. (35). However, also a term Γ_q^s , due to svivon-QE coupling, through \mathcal{H}' in Eq. (23), has a low-energy contribution to Γ^s which becomes significant above [41] T_p^q . Since $A^s(\mathbf{k}, \omega)$ includes symmetric positive- and negative-energy branches (of different weights), and the sign of $\Gamma^s(\mathbf{k}, \omega)$ is that of ω , one has (differently from QEs—see Eq. (A3)):

$$\Gamma^s(\mathbf{k}, \omega \rightarrow 0) = 0. \quad (36)$$

Using Eqs. (22), (23) and (26), one can express Γ^s (for unpaired QEs) as:

$$\begin{aligned} \Gamma^s(\mathbf{k}, \omega) &= \Gamma_q^s(\mathbf{k}, \omega) + \Gamma_\lambda^s(\mathbf{k}, \omega), \quad \text{where} \\ \Gamma_q^s(\mathbf{k}, \omega) &\cong \frac{2\pi \cosh(2\xi_{\mathbf{k}}^s(\omega))}{N^2} \sum_{\mathbf{k}'\mathbf{k}''} |\tilde{t}(\mathbf{k} + \mathbf{k}'')|^2 |m^s(\mathbf{k} + \mathbf{k}'' - \mathbf{k}')| \int d\omega' A^q(\mathbf{k}', \omega') A^q(\mathbf{k}'', \omega' - \omega) [f_T(\omega' - \omega) - f_T(\omega')], \\ \Gamma_\lambda^s(\mathbf{k}, \omega) &\cong \frac{2\pi \cosh(2\xi_{\mathbf{k}}^s(\omega))}{N} \sum_{\mathbf{q}} |\gamma(\mathbf{q})|^2 \{ A^s(\mathbf{k} - \mathbf{q}, \omega - \omega^\lambda(\mathbf{q})) \cosh^2(\xi_{\mathbf{k}-\mathbf{q}}^s(\omega - \omega^\lambda(\mathbf{q}))) [b_T(\omega^\lambda(\mathbf{q})) - b_T(\omega^\lambda(\mathbf{q}) - \omega)] \\ &\quad + A^s(\mathbf{k} - \mathbf{q}, \omega + \omega^\lambda(\mathbf{q})) \cosh^2(\xi_{\mathbf{k}-\mathbf{q}}^s(\omega + \omega^\lambda(\mathbf{q}))) [b_T(\omega^\lambda(\mathbf{q})) - b_T(\omega^\lambda(\mathbf{q}) + \omega)] \} \\ &\quad + A^s(\mathbf{k} - \mathbf{q}, \omega^\lambda(\mathbf{q}) - \omega) \sinh^2(\xi_{\mathbf{k}-\mathbf{q}}^s(\omega^\lambda(\mathbf{q}) - \omega)) [b_T(\omega^\lambda(\mathbf{q}) - \omega) - b_T(\omega^\lambda(\mathbf{q}))] \\ &\quad + A^s(\mathbf{k} - \mathbf{q}, -\omega - \omega^\lambda(\mathbf{q})) \sinh^2(\xi_{\mathbf{k}-\mathbf{q}}^s(-\omega - \omega^\lambda(\mathbf{q}))) [b_T(\omega^\lambda(\mathbf{q}) + \omega) - b_T(\omega^\lambda(\mathbf{q}))] \}. \end{aligned} \quad (37)$$

Let $\bar{\epsilon}^s(\mathbf{k})$ be the positive svivon energies [16] (within their condensates) at the maxima of $A^s(\mathbf{k}, \omega)$ ($-\bar{\epsilon}^s(\mathbf{k})$

are the lower-weight negative energies—see above); let

$\bar{\epsilon}_{\min}^s = \bar{\epsilon}^s(\mathbf{k}_{\min})$ be the minimum of $\bar{\epsilon}^s(\mathbf{k})$ (within each condensate there are two \mathbf{k}_{\min} points, separated from each other by a \mathbf{Q}_m vector). Above [41] T_p^q , the T dependence of $\bar{\epsilon}^s(\mathbf{k})$ is determined by the variation of λ in Eq. (9) to maintain a T -independent n^s through Eqs. (22, 29). By Eq. (26), this results in the approximate scaling:

$$\bar{\epsilon}^s(\mathbf{k}) \propto \sqrt{(c^s|\mathbf{k} - \mathbf{k}_{\min}|)^2 + (T - T_0)^2}, \quad (38)$$

for $|\mathbf{k} - \mathbf{k}_{\min}| < k_{\max}$,

where c^s and T_0 are constants (one has $T_0 < T_p^q$, and it could be in principle either positive or negative—see below), and k_{\max} represents the radius of an approximate circle around \mathbf{k}_{\min} , in the BZ, where there is a noticeable effect of Φ^s on $\bar{\epsilon}^s(\mathbf{k})$.

By Eq. (38), $\bar{\epsilon}_{\min}^s$ approximately scales with $T - T_0$, such that it remains sufficiently larger than $k_B T$ (as [16] below T_p^q) that $b_T(|\omega|)$ is relatively small (though not negligible), within the range where $\mathbf{k} \simeq \mathbf{k}_{\min}$, and $|A^s(\mathbf{k}, \omega)|$ is significant. On the other hand, Eq. (38) yields that the effect of T on $\bar{\epsilon}^s(\mathbf{k}) \gg \bar{\epsilon}_{\min}^s$ is through a minor additional term scaling, approximately, with $(T - T_0)^2$, and in such \mathbf{k} points one has $b_T(|\omega|) \ll 1$ within the ω range where $|A^s(\mathbf{k}, \omega)|$ has a considerable magnitude.

When T is increased, the minima of $\bar{\epsilon}^s(\mathbf{k})$ around $\bar{\epsilon}_{\min}^s$ become broader and flatter, and since $|T_0/T|$ is decreased, the ratio $\bar{\epsilon}_{\min}^s/T$ changes as is necessary in order to maintain a constant n^s , through Eqs. (22, 29) (under the opposing effects of T on it through the minima and $\cosh(2\xi_{\mathbf{k}}^s(\omega))$ —see below—as well as the effect of the linewidth of $\bar{\epsilon}^s(\mathbf{k})$, for $\mathbf{k} \simeq \mathbf{k}_{\min}$).

By Eqs. (26), (27) and (38), the $\cosh(2\xi_{\mathbf{k}}^s(\omega))$ factors, appearing in Eq. (37), can be approximated as:

$$\cosh(2\xi_{\mathbf{k}}^s(\omega)) \simeq \sqrt{\frac{(c^s k_{\max})^2 + (T - T_0)^2}{(c^s|\mathbf{k} - \mathbf{k}_{\min}|)^2 + (T - T_0)^2}}, \quad (39)$$

for $|\mathbf{k} - \mathbf{k}_{\min}| < k_{\max}$, and $|\omega| \lesssim \bar{\epsilon}^s(\mathbf{k})$.

These factors are largest in \mathbf{k} points at the low-svicon-energy (LE) BZ areas, close to the \mathbf{k}_{\min} points, where $\Gamma^s(\mathbf{k}, \omega)$ is significant in the $|\omega| \lesssim \bar{\epsilon}_{\min}^s$ range, and by Eq. (39) they, approximately, scale there with $1/(T - T_0)$, for $|\omega| \lesssim \bar{\epsilon}^s(\mathbf{k})$. On the other hand, in \mathbf{k} points at the mid-svicon-energy (ME) BZ areas, where $\Gamma^s(\mathbf{k}, \omega)$ is significant in the $\sim \bar{\epsilon}_{\min}^s < |\omega| < \sim 2J$ range, and Eq. (39) is still valid, it yields a weak T dependence for the $\cosh(2\xi_{\mathbf{k}}^s(\omega))$ factors, through a term $\propto (T - T_0)^2$. The $\cosh(2\xi_{\mathbf{k}}^s(\omega)) \cong 1$ limit specifies \mathbf{k} points at high-svicon-energy (HE) BZ areas, where the effect of condensation is missing and Eqs. (38, 39) are invalid; $\Gamma^s(\mathbf{k}, \omega)$ is significant there in the high- ω and $-T$ limits. At the LE and ME areas one has $\cosh(2\xi_{\mathbf{k}}^s(\omega)) \cong 1$ for $|\omega| \gg \bar{\epsilon}^s(\mathbf{k})$.

Thus, one could classify the svicon spectrum within the BZ according to LE, ME and HE areas, and crossover areas which could be, approximately, split between them. Since the minima of $\bar{\epsilon}^s(\mathbf{k})$ around $\bar{\epsilon}_{\min}^s$ become broader and flatter when T is increased, the LE areas are growing

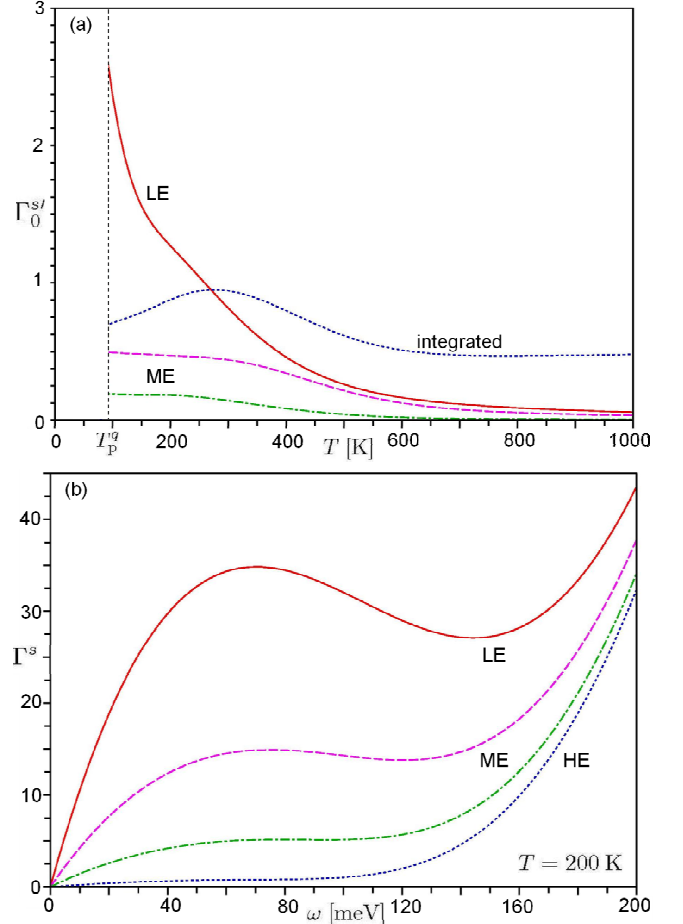


FIG. 6: Typical results (in arbitrary units), at [41] $T > T_p^q$, for (a) the T dependence of the ω derivative $\Gamma_0^{s'}$ of the svicon scattering rates Γ^s at $\omega = 0$, in LE and ME svicon \mathbf{k} points (see discussion in the text) and of its \mathbf{k} -integrated value, and for (b) the ω dependence of Γ^s , in LE, ME and HE svicon \mathbf{k} points.

with T on the expense of the ME areas. By Eq. (38), the size of the LE areas scales with $(T - T_0)^2$, and thus the size of the ME areas is decreased by a relatively minor term (for $k_B T \ll \sim J$) which scales with $(T - T_0)^2$.

The evaluation of $\Gamma^s(\mathbf{k}, \omega)$ is detailed in Appendix B. In the $|\omega| \ll \bar{\epsilon}_{\min}^s$ regime, one has $\Gamma^s(\mathbf{k}, \omega) \propto \omega$ for [41] $T > T_p^q$ (which is enabled by Eq. (36)). This results, through Eq. (B1), in the existence of low-energy tails in $A^s(\mathbf{k}, \omega)$, and thus in the disappearance of the spin gap and the sharp resonance mode, existing [16] at $T < T_p^q$, in agreement with experiment.

Typical results for the T dependence of $\Gamma_0^{s'}(\mathbf{k}) \equiv \lim_{\omega \rightarrow 0} [\Gamma^s(\mathbf{k}, \omega)/\omega]$ in the LE and ME areas are presented in Fig. 6(a). For $k_B T \ll \Gamma_{0a}^q$ (see Eq. (A3)), $\Gamma_0^{s'}$ is characterized by scaling with $1/(T - T_0)$ in the LE areas, and by a constant plus a minor term $\propto (T - T_0)^2$ in the ME areas (it practically vanishes in the HE areas). For $k_B T \gg \Gamma_{0a}^q$, $\Gamma_0^{s'}$ is characterized by scaling with $1/[(T - T_0)^2(1 - T_0/T)]$ in the LE areas, with $1/[(T - T_0)(1 - T_0/T)]$ in the neighboring ME areas (which

turn into LE areas at higher T —see Fig. 6(a)), and with $1/T^2$ in higher-energy ME areas. A typical T dependence of the \mathbf{k} -integrated $\Gamma_0^s(\mathbf{k})$ is also presented in Fig. 6(a); it is characterized by some linear increase with T at low $T > T_p^q$, followed by a decrease around $k_B T \simeq \Gamma_{0a}^q$, and a weak dependence at higher T .

Typical results for $\Gamma^s(\mathbf{k}, \omega)$, as a function of ω (at constant $T > T_p^q$), within the LE, ME and HE areas, are presented in Fig. 6(b). They are characterized (see Appendix B) by scaling with ω for $|\omega| < \sim \bar{\epsilon}^s(\mathbf{k})$ (which is somewhat larger than $k_B T$ in the LE areas), with a slope which is approximately $\propto 1/\bar{\epsilon}^s(\mathbf{k})$, for low $\bar{\epsilon}^s(\mathbf{k})$, and is smaller for high $\bar{\epsilon}^s(\mathbf{k})$; in the case that $\bar{\epsilon}^s(\mathbf{k}) < \sim J$, this is followed by a decrease in the $|\Gamma^s|$ vs $|\omega|$ slope at $|\omega| \simeq \bar{\epsilon}^s(\mathbf{k})$, and for small $\bar{\epsilon}^s(\mathbf{k})$, also by a wide maximum of $|\Gamma^s|$, centered somewhat above $|\omega| \simeq \bar{\epsilon}^s(\mathbf{k})$, and its decrease above it; the $|\Gamma^s|$ vs $|\omega|$ slope rises at $\bar{\epsilon}^s(\mathbf{k}) \simeq J$, and an approximately linear increase of $|\Gamma^s|$ with $|\omega|$ is maintained at higher $|\omega|$ values, up to about the high-energy limits of the lagron spectrum (see Fig. 2).

5. Non-FL electron scattering rates

Let $\epsilon_p^q(\mathbf{k}) + \frac{1}{2}i\Gamma_p^q(\mathbf{k})$ and $\epsilon_p^s(\mathbf{k}) + \frac{1}{2}i\Gamma_p^s(\mathbf{k})$ be the poles of $\underline{\mathcal{G}}^q$ and $\underline{\mathcal{G}}^s$, respectively; they have weight factors $w_p^q(\mathbf{k})$ and $w_p^s(\mathbf{k})$ normalized as: $\sum_p w_p^q(\mathbf{k}) = \sum_p w_p^s(\mathbf{k}) = 1$. $\Gamma_p^q(\mathbf{k})$ and $\Gamma_p^s(\mathbf{k})$ are related to the scattering rates $\Gamma^q(\mathbf{k}, \omega)$ and $\Gamma^s(\mathbf{k}, \omega)$, analyzed above, through the Kramers–Kronig relation [39, 40]:

$$\int \frac{d\omega |\Gamma(\mathbf{k}, \omega)| / 2\pi}{(\omega - \epsilon_p(\mathbf{k}))^2 + (\Gamma_p(\mathbf{k})/2)^2} = 1. \quad (40)$$

This indicates that the dependence of $\Gamma_p^q(\mathbf{k})$ on T and $\epsilon_p^q(\mathbf{k})$ is close to that of $\Gamma^q(\mathbf{k}, \omega)$ on T and $\omega \simeq \epsilon_p^q(\mathbf{k})$.

The elements of the approximate electron Green’s-function matrix $\underline{\mathcal{G}}_0^d$ (see Eq. (19)), represented by the bubble diagrams in Fig. 1(b), could be expressed as [39, 40]:

$$\begin{aligned} \mathcal{G}_0^d(\mathbf{k}, z) &= \sum_{pp'\mathbf{k}'} w_{p'}^s(\mathbf{k}') w_p^q(\mathbf{k} - \mathbf{k}') \text{sign}(\epsilon_{p'}^s(\mathbf{k}')) \\ &\times \left\{ \cosh^2(\xi_{\mathbf{k}'}^s(\epsilon_{p'}^s(\mathbf{k}') + \frac{1}{2}i|\Gamma_{p'}^s(\mathbf{k}')|)) \frac{[b_T(\epsilon_{p'}^s(\mathbf{k}') + \frac{1}{2}i|\Gamma_{p'}^s(\mathbf{k}')|) + f_T(-\epsilon_p^q(\mathbf{k} - \mathbf{k}') - \frac{1}{2}i\Gamma_p^q(\mathbf{k} - \mathbf{k}'))]}{[z - (\epsilon_p^q(\mathbf{k} - \mathbf{k}') + \epsilon_{p'}^s(\mathbf{k}')) - \frac{1}{2}i(\Gamma_p^q(\mathbf{k} - \mathbf{k}') + |\Gamma_{p'}^s(\mathbf{k}')|)]} \right. \\ &\left. + \sinh^2(\xi_{\mathbf{k}'}^s(\epsilon_{p'}^s(\mathbf{k}') - \frac{1}{2}i|\Gamma_{p'}^s(\mathbf{k}')|)) \frac{[b_T(\epsilon_{p'}^s(\mathbf{k}') - \frac{1}{2}i|\Gamma_{p'}^s(\mathbf{k}')|) + f_T(\epsilon_p^q(\mathbf{k} - \mathbf{k}') + \frac{1}{2}i\Gamma_p^q(\mathbf{k} - \mathbf{k}'))]}{[z - (\epsilon_p^q(\mathbf{k} - \mathbf{k}') - \epsilon_{p'}^s(\mathbf{k}')) - \frac{1}{2}i(\Gamma_p^q(\mathbf{k} - \mathbf{k}') + |\Gamma_{p'}^s(\mathbf{k}')|)]} \right\}, \quad (41) \\ A_0^d(\mathbf{k}, \omega) &\equiv \Im \mathcal{G}_0^d(\mathbf{k}, \omega - i0^+) / \pi \cong \frac{1}{N} \sum_{\mathbf{k}'} \int d\omega' A^s(\mathbf{k}', \omega') \{ A^q(\mathbf{k} - \mathbf{k}', \omega - \omega') \cosh^2(\xi_{\mathbf{k}'}^s(\omega')) \\ &\times [b_T(\omega') + f_T(\omega' - \omega)] + A^q(\mathbf{k} - \mathbf{k}', \omega + \omega') \sinh^2(\xi_{\mathbf{k}'}^s(\omega')) [b_T(\omega') + f_T(\omega' + \omega)] \}. \quad (42) \end{aligned}$$

Since the svivons are in a combination state of degenerate condensates (corresponding to the different \mathbf{Q}_m points), the \mathbf{k}' summation in Eq. (42) includes the averaging of the $A^s(\mathbf{k}', \omega') \cosh^2(\xi_{\mathbf{k}'}^s(\omega'))$ and $A^s(\mathbf{k}', \omega') \sinh^2(\xi_{\mathbf{k}'}^s(\omega'))$ terms over these condensates.

In the non-FL regime, where major features of the physics of the cuprates are described correctly replacing $\underline{\mathcal{G}}^d$ in Eq. (19) by $\underline{\mathcal{G}}_0^d$, the evaluation of these features is approached approximating the electron spectral functions $A^d(\mathbf{k}, \omega) \equiv \Im \mathcal{G}^d(\mathbf{k}, \omega - i0^+) / \pi$ by $A_0^d(\mathbf{k}, \omega)$ in Eq. (42). Note that the ω -integral of $A_0^d(\mathbf{k}, \omega)$, given in Eq. (42), is short of one *exactly* by the contribution of the electron states of the upper Hubbard band, created by the second term in the rhs of Eq. (3), ignored in Eq. (5).

The evaluation of $A_0^d(\mathbf{k}, \omega)$ is detailed in Appendix C, and it is found to be, approximately, expressed as a sum of two terms, presented in Eq. (C1). One term, $A_{0c}^d(\mathbf{k}, \omega)$, represents a convolution of QE and modified svivon spectral functions, where the low-energy ($< k_B T$) tails of A^s have been truncated (see Eq. (B1) and Fig. 6(b)).

The other term, $A_{0b}^d(\mathbf{k}, \omega)$, represents anomalous effective electron bands, generated by the QE spectral functions and the truncated A^s tails.

As was discussed above, the QE spectral functions are specified as low-energy (LE), mid-energy (ME) and high-energy (HE) types of functions: $A_{le}^q(\omega)$, $A_{me}^q(\omega)$ and $A_{he}^q(\omega)$, respectively; consequently, the A_{0b}^d electron bands corresponding to them are referred to as LE, ME and HE bands. The LE A_{0b}^d band, due to the arcon and stripon peaks, is flat and extends over the low-QE-energy BZ areas (see Fig. 3(c,f)). The ME A_{0b}^d band, due to the humpons, merges with the LE band at high T (see above), and has a similar role to that of the HE A_{0b}^d band at low T .

In the low $|\omega|/k_B T$ limit, A_0^d is dominated (through Eq. (C1)) by the LE A_{0b}^d band [58], and the physical properties based on it reflect its anomalous features; thus, as is explained in Appendix C, the linewidth of this effective band increases linearly with T , and the spectral weight $W^d(\mathbf{k})$ within it depends on T (especially in the

antinodal areas), increasing with it at low $T > T_p^q$, and saturating at $k_B T \gtrsim \omega_H$; the band linewidth plays the role of the electron scattering rates $\Gamma^d(\mathbf{k}, \omega)$ in physical properties derived from it. Typical results for these effective Γ^d and W^d , as functions of T (for $\omega \rightarrow 0$), in \mathbf{k} points ranging between the nodal and antinodal BZ areas, are presented in Figs. 7(a-b).

On the other hand, in the high- $|\omega|/k_B T$ limit A_0^d is dominated by A_{0c}^d (based on a convolution of QE and modified svivon spectral functions) [58] plus a minor contribution of the ME and HE A_{0b}^d bands; when T is increased, the spectral weight within them is decreased by the same amount that it is increased within the LE A_{0b}^d band (see Fig. 7(b)). Physical properties could then often be formulated in terms of QE and svivon contributions, where one of them may be dominant.

Thus, the electron scattering rates $\Gamma^d(\mathbf{k}, \omega)$ measured in the high- $|\omega|/k_B T$ limit, in various physical properties, are obtained as convoluted combinations of those of the QEs and svivons, as is implied from Eqs. (40, 41); due to the \cosh^2 and \sinh^2 factors in Eq. (41), the major svivon contribution comes (see Eq. (39)) from LE and ME BZ areas at energies ranging between $k_B T$ and somewhat above $\bar{\epsilon}^s(\mathbf{k})$, where a maximum or a plateau appears in the Γ^s curves in Fig. 6(b). Consequently (see Figs. 5(b) and 6(b)), when $T > T_p^q$, $\Gamma^d(\mathbf{k}, \omega)$ are approximately linear in ω , for $k_B T < |\omega| \lesssim 0.3$ eV.

Typical results for Γ^d (at T above [41] T_p^q and below Γ_{0a}^q/k_B and $\omega^\lambda(\mathbf{Q})/k_B$), as a function of ω , in \mathbf{k} points ranging between the nodal and antinodal BZ areas, are presented in Fig. 7(c). The evaluation of these results is based on precise Fermi and Bose distribution functions, and not on their asymptotic values assumed in Eq. (C1); thus, they reflect a smooth crossover between the high- and the low- $(|\omega|/k_B T)$ behaviors, around $|\omega| \simeq k_B T$, manifested in lower slopes of the Γ^d *vs.* $|\omega|$ curves for $|\omega| \rightarrow 0$.

Similarly, due to large \cosh^2 and \sinh^2 factors, svivons of the LE and ME areas also have a major contribution to A_{0c}^d in Eq. (C1). Consequently, the convoluted QE-svivon states at energies $k_B T < |\omega| \lesssim 0.3$ eV have a band-like behavior of linewidth which approximately increases linearly with $|\omega|$, as can be seen in Fig. 3(d-e) [58].

The linear dependence of the linewidths on ω is in agreement with ARPES results [57, 59]; furthermore, the measured zero-energy-interpolated linewidths are closest to zero along the line of nodes and largest in the antinodal direction, in agreement with the results obtained here for $\Gamma_0^q(\mathbf{k})$ in nodal and antinodal points (see Eq. (A3) and the discussion in Appendix A). This linear dependence is found here both for the main and the shadow bands, as has been observed by ARPES [48]. Note, however, that A_0^d misses the effect of the multiple-scattering FL-like electron poles in Eq. (19), which contribute only to the main bands (see Fig. 3(d)).

Thus, in the regime where the contribution of the non-FL $A_0^d(\mathbf{k}, \omega)$ to $A^d(\mathbf{k}, \omega)$ provides a good approximation for the evaluation of the effective $\Gamma^d(\mathbf{k}, \omega)$ in various ex-

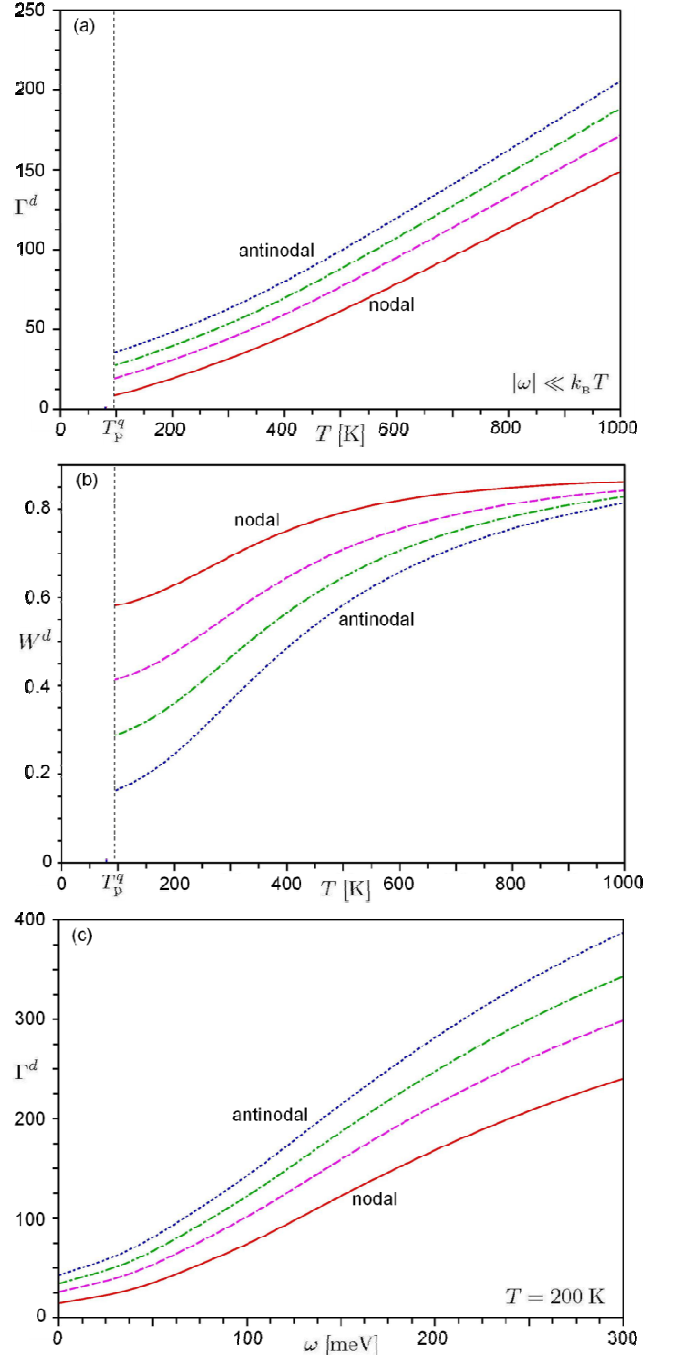


FIG. 7: Typical results (in arbitrary units), within the non-FL regime (corresponding to the Γ^q and Γ^s results presented in Figs. 5 and 6), for the T dependence of (a) the electron scattering rates Γ^d , (b) the spectral weights W^d within effective LE electron band (see discussion in the text), and (c) for the ω dependence of Γ^d .

periments, the measured Γ^d are expected to be characterized by a linear dependence on T in the low- $|\omega|/k_B T$ limit, and by a linear dependence on ω in the high- $|\omega|/k_B T$ limit. Such a behavior corresponds to the MFL phenomenology [13], and thus, the hump phase [42] is referred to here as the MFL phase.

The linear dependence of the Γ^d on T or ω , down to their lowest value within the MFL phase, has been attributed to quantum criticality [59, 60]. In the present work a different, though not contradictory, approach is applied, and the linear dependence on T or ω results from the role of the Bose svivon field which has linear low-energy spectral tails, down to $\omega = 0$, due to Eq. (36). This linear dependence, and the switching in the roles of $k_B T$ and $|\omega|$ between the low- and high- $|\omega|/k_B T$ limits, result here from the behavior of terms like $-|\omega|b_T(-|\omega|)$ in these limits.

The effect of convolution with svivons on the low-energy QE spectral peaks, including the different contributions to A_0^d , is sketched in Fig. 4(b). The traces of the arcon and stripon peaks are considerably broadened in the MFL phase [58]; however, since the evaluation of physical quantities in the low $|\omega|/k_B T$ limit is dominated by the LE A_{0b}^d part of A_0^d , for which the broadening of the QE peaks is $\sim 2k_B T$ (see Appendix C), these quantities are sensitive to the sharpness of these peaks.

6. Anomalous physical properties

The T dependencies of the transport properties of the cuprates, whose anomalous behavior has been associated with non-FL behavior from the start, are the consequence of the unconventional T behavior of the effective scattering rates and spectral weight corresponding to the LE A_{0b}^d band. The T dependence of the electrical resistivity in the cuprates [1] follows in the MFL phase that of the evaluated effective Γ^d , presented in Fig. 7(a).

The effect of transfer of spectral weight from the A_{0c}^d and ME A_{0b}^d bands to the LE A_{0b}^d band, when T rises, is reflected in Hall-effect and thermoelectric power (TEP) results which are dominantly determined by the latter. This transfer occurs at both positive and negative energies of magnitude $\sim k_B T$; thus, it should be reflected in such measurements as an effective increase in the density of carriers, subject to the question whether the occupation of the LE A_{0b}^d band passes through half filling.

In conventional bands both the Hall number (n_H), and the TEP (S), are negative when the band is almost empty, and positive when it is almost full; the analytical periodic behavior of such bands over the *entire* BZ generally results [31] in a coincidence between their signs. As was discussed above, the LE A_{0b}^d band is not conventional, and consists of the arcon-stripon contribution $A_{le}^q(\omega)$ to the QE spectral functions (see Figs. 3,4), and the low-energy tails of the svivon spectral functions (see Fig. 6). Thus, it occupies only a *part* of the BZ, and a careful analysis should be made on the origin of the signs of n_H and S , derived from it.

The sign of S is [61] that of the average energy (relative to the chemical potential) within the range of the band close to the FS, introduced through $\omega df_T(\omega)/d\omega$. Since the LE A_{0b}^d band lies almost entirely within this range, the TEP derived from it could be either positive

or negative, depending on the band occupation, and thus on stoichiometry.

On the other hand, the sign of n_H is [61] opposite from that of the averaged second derivatives of the band dispersion curve over the FS (where $-df_T(\omega)/d\omega$ contributes). Since the LE A_{0b}^d band extends only over the arcon-stripon QE BZ areas, shown in Fig. 3(a-c), where the sign of the second derivatives of the band dispersion curve is dominantly negative, the sign of n_H is expected to be positive, independently of the occupation of the band (and thus of stoichiometry); the fact that this low-energy band is flat results in small dispersion derivatives, but also in a nonzero $-df_T(\omega)/d\omega$ factor over a range of the BZ, and the contradicting effects introduced to the expression [61] for n_H compensate for each other. And indeed, for hole-doped cuprates, studied here, n_H is found to be positive in the MFL phase, and its T dependence follows [2, 3] that of $W^d(\mathbf{k})$, presented in Fig. 7(b).

The T dependence of the TEP in YBCO has been analyzed [4] in terms of a “narrow-band model”, under which $|S|$ is larger than typical metallic values, and increases with T up to its saturation value (when $k_B T$ exceeds the bandwidth), thus [4]: $S_{\text{sat}} = (k_B/e) \ln[x/(1-x)]$; here x is the fractional band occupation (thus $x = 0$ when the band is empty of electrons, and $x = 1$ when it is full) within the measured stoichiometry.

For hole-doped cuprates of an electronic structure similar to the one presented in Fig. 3, the TEP does not saturate with T , and has an almost universal dependence on T and the doping level [5]. Thus, in the underdoped and lightly overdoped regimes, S increases with T at low T , reaching a positive maximum, and then decreases with T , having an almost linear dependence on it at high T ; at the optimal stoichiometry, S crosses zero at $T \cong 300$ K which has been applied [5] to determine the doping level in cuprates. In the heavily overdoped regime, S is negative and decreases monotonously with T , consistently with an FL state with a band which is less than half filled (as is expected in this regime).

The LE A_{0b}^d band is a narrow one (being based on the almost dispersionless stripons and arcons); however, since its linewidth increases linearly with T , the TEP saturation temperature [4] cannot be reached. Furthermore, the asymmetry of the QE and electronic spectra, presented in Fig. 3, with respect to the inversion of the sign of the energy, results in a temperature-induced transfer of spectral weight to the LE A_{0b}^d band (from the A_{0c}^d and ME A_{0b}^d bands) which is larger for negative than for positive energies. Consequently, the fractional occupation x of this band decreases when T is increased.

Thus, in the underdoped and lightly overdoped regimes, the LE A_{0b}^d band is more than half filled at low T , resulting in positive S (within the MFL phase) which first increases with T to approach its saturation value, but the decrease in x with T results also in a decrease in this saturation value [4], and thus in S (after it reaches its maximal value). Consequently, a “universal” behavior of S is obtained for cuprates of the same type of electronic

structure as in Fig. 3, in agreement with experiment [5]. The value $S = 0$, at $T \cong 300$ K, at optimal stoichiometry, implies that the LE A_{0b}^d band is then half filled.

The existence of a universal behavior in the cuprates has been observed [9] in various physical quantities, determined by the LE A_{0b}^d band. This behavior is expressed through the scaling of their T -dependencies in a typical energy corresponding to spectrum of the low-energy QEs. These quantities include, in addition to the TEP, the planar and c -axis resistivities, the Hall coefficient, the uniform magnetic susceptibility, and the spin-lattice relaxation rate.

Linearity of the electron scattering rates in ω , for $|\omega| \lesssim 0.3$ eV (similarly to ones shown in Fig. 7(c)), within the MFL phase, has been observed in optical results [60, 62]. In different hole-doped cuprates, the optical conductivity $\sigma^d(\omega)$ consists in this phase [10] of a low-energy Drude term, and a higher-energy “mid-IR” term, where the effective density of carriers within the Drude term is 4–5 times smaller than those integrated up to above the mid-IR energy (a behavior referred to as “Tanner’s law”).

Within the present approach, the electron spectral functions are approximated by $A_0^d(\mathbf{k}, \omega)$ in Eq. (42), including both the A_{0b}^d and A_{0c}^d terms in Eq. (C1) [58]. At low ω , the QE contribution to A_0^d includes only the stripions and arcons peaks, resulting in the Drude term in $\sigma^d(\omega)$. The mid-IR term in $\sigma^d(\omega)$ is introduced due to the growing role (in A_0^d) of humpons at higher energies, and of the almost detached higher-energy QEs (see Fig. 3(a-b)) at further higher energies. Thus the increase in the effective number of carriers with energy, expressed by Tanner’s law [10], reflects the difference between the occupied QE spectral weight residing within their low-energy peaks, and that residing within their entire spectrum.

D. Paired QEs and electrons

1. Formulation and general features

QE pairing is approached adapting of the Migdal–Eliashberg theory [27] for the present case. Nambu spinors ($q^\dagger(\mathbf{k})$, $q(-\mathbf{k})$) are considered as creation operators (the \mathbf{k} values here are within a half of the BZ, but since there is a freedom in choosing this half, the derived expressions are valid within the entire BZ). Self-energy 2×2 matrices are derived, and expressed (in terms of the Pauli matrices \mathcal{I}_1 , \mathcal{I}_2 and \mathcal{I}_3) through:

$$\underline{\epsilon}_0^q(\mathbf{k}) + \underline{\Sigma}^q(\mathbf{k}, z) = [\epsilon_0^q(\mathbf{k}) + \Sigma^q(\mathbf{k}, z)]\mathcal{I}_3 + \Re\Phi^q(\mathbf{k}, z)\mathcal{I}_1 + \Im\Phi^q(\mathbf{k}, z)\mathcal{I}_2. \quad (43)$$

The diagonalization of $\underline{\epsilon}_0^q(\mathbf{k}) + \underline{\Sigma}^q(\mathbf{k}, z)$ yields QE Bogoliubov states annihilated by $q_+(\mathbf{k}, z)$ and $q_-(\mathbf{k}, z)$, corresponding to positive and negative energies, respectively; the transformation between them and the

unpaired-state QE operators is expressed as:

$$\begin{aligned} q(\mathbf{k}) &= \exp(i\phi_{\mathbf{k}}^q(z)/2)[\cos(\xi_{\mathbf{k}}^q(z))q_+(\mathbf{k}, z) \\ &\quad - \sin(\xi_{\mathbf{k}}^q(z))q_-(\mathbf{k}, z)], \\ q^\dagger(-\mathbf{k}) &= \exp(-i\phi_{\mathbf{k}}^q(z)/2)[\sin(\xi_{\mathbf{k}}^q(z))q_+(\mathbf{k}, z) \\ &\quad + \cos(\xi_{\mathbf{k}}^q(z))q_-(\mathbf{k}, z)]. \end{aligned} \quad (44)$$

This transformation diagonalizes Dyson’s equation [39, 40], yielding the poles of the diagonalized QE Green’s function $\mathcal{G}_\pm^q(\mathbf{k}, z)$ at:

$$\begin{aligned} z &= \pm\epsilon_0^q(\mathbf{k}) + \Sigma_\pm^q(\mathbf{k}, z) \\ &\equiv \pm E^q(\mathbf{k}, z) + i\Im\Sigma_\pm^q(\mathbf{k}, z), \text{ where} \\ \Im\Sigma_\pm^q(\mathbf{k}, z) &= \pm \cos(2\xi_{\mathbf{k}}^q(z))\Im\Sigma^q(\mathbf{k}, z), \\ E^q(\mathbf{k}, z) &= \sqrt{[\epsilon_0^q(\mathbf{k}) + \Re\Sigma^q(\mathbf{k}, z)]^2 + [\bar{\Phi}^q(\mathbf{k}, z)]^2}, \\ \Phi^q(\mathbf{k}, z) &= |\Phi^q(\mathbf{k}, z)| \exp(i\psi_{\mathbf{k}}^q(z)), \\ \phi_{\mathbf{k}}^q(z) &= \psi_{\mathbf{k}}^q(z) \text{ or } \psi_{\mathbf{k}}^q(z) + \pi, \text{ and} \\ \bar{\Phi}^q(\mathbf{k}, z) &\equiv \cos(\psi_{\mathbf{k}}^q(z) - \phi_{\mathbf{k}}^q(z))|\Phi^q(\mathbf{k}, z)| = \pm|\Phi^q(\mathbf{k}, z)|. \end{aligned} \quad (45)$$

The coefficients $\xi_{\mathbf{k}}^q(z)$ are obtained through:

$$\begin{aligned} \cos(2\xi_{\mathbf{k}}^q(z)) &= \frac{\epsilon_0^q(\mathbf{k}) + \Re\Sigma^q(\mathbf{k}, z)}{E^q(\mathbf{k}, z)}, \\ \sin(2\xi_{\mathbf{k}}^q(z)) &= \frac{\bar{\Phi}^q(\mathbf{k}, z)}{E^q(\mathbf{k}, z)}. \end{aligned} \quad (46)$$

The spectral functions of the QE Bogoliubov states are obtained through:

$$\begin{aligned} A_\pm^q(\mathbf{k}, \omega) &\equiv \Im\mathcal{G}_\pm^q(\mathbf{k}, \omega - i0^+)/\pi \\ &= \frac{\Gamma_\pm^q(\mathbf{k}, \omega)/2\pi}{[\omega \mp E^q(\mathbf{k}, \omega)]^2 + [\frac{1}{2}\Gamma_\pm^q(\mathbf{k}, \omega)]^2}, \end{aligned} \quad (47)$$

where $\Gamma_\pm^q(\mathbf{k}, \omega) \equiv 2\Im\Sigma_\pm^q(\mathbf{k}, \omega - i0^+) \geq 0$, and thus $A_\pm^q \geq 0$ (note that $\cos(2\xi_{\mathbf{k}}^q(\omega))$ is positive within the $\omega > 0$ range of A_+^q , and negative within the $\omega < 0$ range of A_-^q —see Eqs. (45,46)).

The self-energy terms Σ^q and Φ^q are primarily determined, at low energies, by QE-lagron coupling, through $\Delta\mathcal{H}$ in Eq. (12). Their self-consistent expressions are derived similarly to the unpaired case in Eq. (34), yielding:

$$\begin{aligned} \Sigma^q(\mathbf{k}, z) &\cong \frac{1}{N} \sum_{\mathbf{q}} \int d\omega^q [\cos^2(\xi_{\mathbf{k}-\mathbf{q}}^q(\omega^q)) \\ &\quad \times A_+^q(\mathbf{k} - \mathbf{q}, \omega^q) + \sin^2(\xi_{\mathbf{k}-\mathbf{q}}^q(\omega^q)) \\ &\quad \times A_-^q(\mathbf{k} - \mathbf{q}, \omega^q)] F_T(\mathbf{q}, \omega^q, z), \\ \Phi^q(\mathbf{k}, z) &\cong \frac{1}{2N} \sum_{\mathbf{q}} \int d\omega^q \sin(2\xi_{\mathbf{k}-\mathbf{q}}^q(\omega^q)) \\ &\quad \times \exp(i\phi_{\mathbf{k}-\mathbf{q}}^q(\omega^q)) [A_+^q(\mathbf{k} - \mathbf{q}, \omega^q) \\ &\quad - A_-^q(\mathbf{k} - \mathbf{q}, \omega^q)] F_T(\mathbf{q}, \omega^q, z). \end{aligned} \quad (48)$$

$\Im\Sigma^q(\mathbf{k}, \omega - i0^+)$ is obtained by expressing $(\omega - i0^+ \mp \omega^\lambda(\mathbf{q}) - \omega^q)^{-1}$ in $F_T(\mathbf{q}, \omega^q, \omega - i0^+)$, in Eqs. (34, 48), as

[39, 40] $\pi i \delta((\omega \mp \omega^\lambda(\mathbf{q}) - \omega^q))$; such an expression could not be applied to obtain $\Im\Phi^q(\mathbf{k}, \omega - i0^+)$, because of the $\exp(i\phi_{\mathbf{k}-\mathbf{q}}^q(\omega^q))$ phase factors in the rhs of Eq. (48), but it could still be applied to obtain a term $i\hat{\Phi}^q(\mathbf{k}, \omega - i0^+)$ in $\Phi^q(\mathbf{k}, \omega - i0^+)$. Due to the f_T and b_T factors in Eq. (34), QEs and svivons at energies ω^q and $\omega^\lambda(\mathbf{q})$ contribute to $\Im\Sigma^q(\mathbf{k}, \omega - i0^+)$ and $\hat{\Phi}^q(\mathbf{k}, \omega - i0^+)$ at $\omega = \omega^q \pm \omega^\lambda(\mathbf{q})$ when $\omega^\lambda(\mathbf{q}) \ll k_B T$, and at $\omega = \omega^q + \text{sign}(\omega^q)\omega^\lambda(\mathbf{q})$ when $\omega^\lambda(\mathbf{q}) \gg k_B T$.

The most significant low-energy contribution to Σ^q and Φ^q in Eq. (48) is from \mathbf{q} points corresponding to \mathbf{Q}_m and \mathbf{Q}_m -vicinity lagrons (see above); an additional significant contribution comes from \mathbf{Q} -ESP lagrons. Thus, by Fig. 2, a QE spectral peak around the energy ω^q , located at $\sim \mathbf{k} - \mathbf{Q}_m$, contributes (due to \mathbf{Q}_m and \mathbf{Q}_m -vicinity lagrons) peaks to $\Im\Sigma^q(\mathbf{k}, \omega - i0^+)$ and $\hat{\Phi}^q(\mathbf{k}, \omega - i0^+)$ at $\omega \simeq \omega^q$, with asymmetry towards larger $|\omega^q|$; if such a QE peak is located at $\sim \mathbf{k} - \mathbf{Q}$, it contributes to them (due to \mathbf{Q} -ESP lagrons) peaks at $\omega \simeq \omega^q + \text{sign}(\omega^q)\omega^\lambda(\mathbf{Q})$, if $k_B T \ll \omega^\lambda(\mathbf{Q})$, and at $\omega \simeq \omega^q \pm \omega^\lambda(\mathbf{Q})$, if $k_B T \gg \omega^\lambda(\mathbf{Q})$.

$\Re\Sigma^q$ and Φ^q could be expressed through the Kramers–Kronig relations [39, 40]:

$$\begin{aligned}\Re\Sigma^q(\mathbf{k}, \omega) &= \wp \int \frac{d\omega' \Im\Sigma^q(\mathbf{k}, \omega' - i0^+)}{\pi(\omega - \omega')}, \\ \Phi^q(\mathbf{k}, \omega - i0^+) &= \wp \int \frac{d\omega' \hat{\Phi}^q(\mathbf{k}, \omega' - i0^+)}{\pi(\omega - \omega')} \\ &\quad + i\hat{\Phi}^q(\mathbf{k}, \omega - i0^+).\end{aligned}\quad (49)$$

The effect of peaks in $\Im\Sigma^q(\mathbf{k}, \omega - i0^+)$ (which is always positive) on $\Re\Sigma^q$, in Eq. (49), is to “push” the peaks in $A_\pm^q(\mathbf{k}, \omega)$ away from them, through Eqs. (45, 47). As was discussed above, the location of peaks in $\hat{\Phi}^q(\mathbf{k}, \omega - i0^+)$ (and in $\Im\Sigma^q(\mathbf{k}, \omega - i0^+)$) is close to $\mathbf{k} - \mathbf{Q}$, and symmetrically around it. Consequently, in order to stabilize pairing, one should choose (see Eqs. (45), (46) and (48)):

$$\begin{aligned}\phi_{\mathbf{k}}^q(\omega) &= \psi_{\mathbf{k}}^q(\omega), \text{ getting} \\ \phi_{\mathbf{k}+\mathbf{Q}}^q(\omega) &= \phi_{\mathbf{k}}^q(\omega) + \pi, \text{ and introduce} \\ \tilde{\Phi}^q(\mathbf{k}, \omega) &= |\Phi^q(\mathbf{k}, \omega)| \cos \phi_{\mathbf{k}}^q(\omega), \text{ where} \\ \text{sign}[\tilde{\Phi}^q(\mathbf{k}, \omega)] &\text{ is independent of } \omega.\end{aligned}\quad (50)$$

$\tilde{\Phi}^q(\mathbf{k}, \omega)$ plays the role of the pairing order parameter; by Eq. (50) it reverses its sign when \mathbf{k} is shifted by \mathbf{Q} , resulting to an approximate $d_{x^2-y^2}$ pairing symmetry. For the choices in Eq. (50) one gets that the effect of the peaks in $\hat{\Phi}^q(\mathbf{k}, \omega - i0^+)$ on Φ^q in Eq. (49) is to “push” (through Eqs. (45, 47)) the peaks in $A_\pm^q(\mathbf{k}, \omega)$ away from them, if they are at energies of the opposite sign, and to “pull” these peaks towards them, if they are at energies of the same sign.

Such a scenario could result in a pairing gap, where in addition to the humpons, the stripon and arcon peaks (which are not on the lines of nodes) are split into positive- and negative-energy peaks. As was discussed above, the locations (at low T) of the centers of the peaks

in $\Im\Sigma^q(\mathbf{k}, \omega - i0^+)$ and $\hat{\Phi}^q(\mathbf{k}, \omega - i0^+)$ are at higher values of $|\omega|$ than those of such split peaks in $A_\pm^q(\mathbf{k} - \mathbf{q}, \omega)$, where $\mathbf{q} = \mathbf{Q}$ or \mathbf{Q}_m .

By the symmetry of the QE spectrum under a shift in \mathbf{Q} , a split peak in $A_+^q(\mathbf{k}, \omega)$ or $A_-^q(\mathbf{k}, \omega)$ is pushed, on the average, away from zero by the opposite-energy-sign peaks in $\Im\Sigma^q(\mathbf{k}, \omega - i0^+)$, and towards zero by the same-energy-sign peaks in it, and this is insufficient to stabilize the gap, unless the symmetry between the degenerate lagron and svivon condensates (see Fig. 2, Eq. (20), and the above discussion) is broken, and a *static* striped structure sets in.

The *additional* effect of peaks in $\hat{\Phi}^q(\mathbf{k}, \omega - i0^+)$, at *both* positive and negative energies, is to push this split peak, on the average, *away* from zero. Thus, a gap is stabilized, under a certain temperature (in a state of combined lagron and svivon condensates corresponding to fluctuating inhomogeneities), by breaking symmetry through the introduction of a nonzero $\tilde{\Phi}^q$. A quantitative calculation on this pairing scenario will be published in a separate paper.

Nonzero $\hat{\Phi}^q$ results in a nonzero anomalous QE Green’s function matrix $\underline{\mathcal{F}}^q$ (see above), and consequently in a nonzero anomalous electron Green’s function matrix $\underline{\mathcal{F}}^d$. The expression for its zeroth-order term $\underline{\mathcal{F}}_0^d$, in terms of $\underline{\mathcal{F}}^s$ and $\underline{\mathcal{F}}^q$, is presented diagrammatically in Fig. 1(b). Within the \mathbf{k} representation, the expression for $\mathcal{F}_0^d(\mathbf{k}, z)$ is similar to the expression for $\mathcal{G}_0^d(\mathbf{k}, z)$ in Eq. (41); the $\cosh^2(\xi_{\mathbf{k}}^s)$ and $\sinh^2(\xi_{\mathbf{k}}^s)$ factors there are replaced by $\sinh(2\xi_{\mathbf{k}}^s)/2$, and additional factors are included (for both \mathcal{F}_0^d and \mathcal{G}_0^d) due to QE pairing; thus, $\mathcal{G}_0^q(\mathbf{k}, z)$ and $\mathcal{F}_0^q(\mathbf{k}, z)$ are expressed in terms of the diagonalized $\mathcal{G}_\pm^q(\mathbf{k}, z)$, and have their poles specified in Eq. (45).

As will be detailed elsewhere, the electron spectrum is determined through the diagonalization of 2×2 matrices whose diagonal terms are determined by $\mathcal{G}^d(\mathbf{k}, z)^{-1}$, and non-diagonal terms by $\mathcal{F}^d(\mathbf{k}, z)^{-1}$ and $[\mathcal{F}^d(\mathbf{k}, z)^{-1}]^*$. The evaluation of the approximate electron spectral functions $A_0^d(\mathbf{k}, \omega)$ in a paired state is analogous to their evaluation, through Eqs. (42, C1), in the unpaired case; but the $\cosh^2(\xi_{\mathbf{k}}^s)$ and $\sinh^2(\xi_{\mathbf{k}}^s)$ factors there are modified, and expansion coefficients due to the pairing diagonalization procedures are included. The obtained electron spectrum is characterized by a pairing gap of the same symmetry as that of $\hat{\Phi}^q$; the opposite signs of $\hat{\Phi}^q$ around the lines of modes result in a zero electron pairing gap on these lines, and in its continuous variation around them, due to QE-svivon convolution.

2. Pseudogap phase

As was discussed above, the number of poles in $\mathcal{G}^q(\mathbf{k}, z)$ is different for QEs in nodal and antinodal \mathbf{k} points. Thus these two types of low-energy QEs correspond to different symmetries, and it is analytically possible to have $\tilde{\Phi}^q \neq 0$ for only one of them (corresponding to a specific

area within the QE BZ). Since (as was discussed above with respect to humpon–humpon splitting) \mathbf{Q}_m lagrons contribute significantly (through Eq. (48)) to QE pairing in antinodal points, and less (if at all) in nodal points, it is likely that there exists a temperature range $T_c < T < T^*$, where $\tilde{\Phi}^q \neq 0$ in the antinodal, but *not* in the nodal QE BZ areas. The symmetry of a state within this T range is *different* from the symmetries of the states where $\tilde{\Phi}^q \neq 0$ for either almost all the low-energy QEs, or almost none of them.

Scattering between the $\tilde{\Phi}^q \neq 0$ antinodal, and the $\tilde{\Phi}^q = 0$ nodal QEs prevents the existence of supercurrent in such a partial-pairing state, and it corresponds to the PG phase of the cuprates [42]. From a comparison between the expressions for Σ^q and Φ^q in Eq. (48), and the above discussion, one concludes that T^* could not exceed a maximal value which is somewhat smaller than $\sim \omega_H/k_B$ (where the effect of the inhomogeneities disappears). Consequently, $k_B T^*$ could be, at the most, close to $\sim J$ (see discussion above), in agreement with the values of T^* observed in the phase diagram [42].

The stripon peaks split in this phase into positive- and negative-energy peaks, as is sketched in Fig. 4(a). The contribution of \mathbf{Q} -ESP lagrons to Σ^q and Φ^q in Eq. (48), and the fact that $|\Re \Sigma^q| > |\Phi^q|$ within the higher-weight Bogoliubov band, results in an energy separation [56] $> \omega^\lambda(\mathbf{Q}) \simeq \frac{3}{4} E_{\text{res}}$ between same-energy-sign stripon and humpon peaks.

There exists a low- T regime within the PG phase where the inhomogeneities become static (resulting in an energy gain), and they are observed as a glassy structure [21, 22]; this regime is characterized by a lower minimum $\bar{\epsilon}_{\text{min}}^s$ of the svivon dispersion curves, and a higher spectral weight in the humpon peaks (which, as was discussed above, correspond to the inhomogeneities), on the expense of that in the split stripon peaks. In order for a static inhomogeneous structure to coexist with pairing, it should not break the symmetry between the four \mathbf{Q}_m points in Eq. (20) and Fig. 2, and $\bar{\epsilon}_{\text{min}}^s$ should not be too close to zero; this requires the effect of coupling to the lattice, manifested in the existence of local distortions.

The static inhomogeneities are obtained through two types of combinations of striped condensates, corresponding to different \mathbf{Q}_m points; one type is of the different phases of the SDWs introduced by the stripes, resulting in static charge-density waves [22] (CDWs) of wave vectors $2\delta\mathbf{q}_m$ (while the spins are fluctuating); the other type is of the different directions (thus a and b) of the stripes, resulting in a checkerboard-like structure [21] of short stripe segments of $\sim 4a$ periodicity, along the two directions (similarly to a structure predicted earlier [35]). Longer unidirectional stripes can be obtained [18, 19] when the resulting energy gain is larger than that due to pairing which is suppressed altogether, as probably occurs in “1/8 doping anomalies” and below the minimal SC doping level.

The above derivation of the low- ω QE and svivon scattering rates in the MFL phase required the existence of

low- ω QE (particularly stripon) spectral weight, as occurs [41] for $T > T_p^q$. Consequently, the opening of a partial QE gap in the PG phase results in a substantial reduction in Γ^q and $|\Gamma^s|$, for $|\omega|$ below the gap energy, but not above it, in agreement with experiment [1, 6].

However, since the gap is partial, the low- ω scattering features, including the low-energy svivon spectral tails, existing for $T > T^*$, partially persist for $T_c < T < T^*$. Consequently, the electron spectral functions in the PG phase include, as in the MFL phase (see Eq. (C1)), an effective LE band part $A_{0b}^d(\mathbf{k}, \omega)$ which consists here of the low-energy part of the Fermi arcs around the lines of nodes, and a convoluted QE-svivon part $A_{0c}^d(\mathbf{k}, \omega)$. The contribution of arcons to A_{0c}^d forms the extension of the Fermi arcs to higher energies, and the contribution of stripsons to it is modified by pairing (see above), reflecting the existence of the pseudogap. The association of the latter electron states with Bogoliubov states, due to pairing, is supported by experiment [63, 64]. Also the existence of Fermi arcs which are *distinct* from Fermi pockets (see above) has been established by experiment [65]. These two features in A^d in the PG phase are sketched in Fig. 4(b).

A decrease in T , within the PG phase, results in the transition of the spectral functions of low-energy QEs from a structure of $\tilde{\Phi}^q = 0$ arcons to that of $\tilde{\Phi}^q \neq 0$ stripsons and humpons. It is associated with the growing effect of the inhomogeneities at lower T , within the PG phase, discussed above. Since all the arcons are coupled to stripon–humpons through lagrons, the transition of unpaired arcons into paired stripon–humpons would include at $T = 0$ *all* the arcons (except for those on the lines of nodes, where $\tilde{\Phi}^q = 0$ by symmetry) if the arcons remained unpaired.

The signature of such a transition on the electron spectrum is the observed reduction of the Fermi arcs with decreasing T , within the PG phase, and indeed, the extrapolation of their reduction to $T = 0$ results in the points on the lines of nodes [66]. Such a low- T “ d -wave nodal liquid” has been observed [67] in the regime where the PG state persists down to $T \rightarrow 0$.

3. Superconducting phase

SC occurs when $\tilde{\Phi}^q \neq 0$ for the nodal arcons (except for those on the lines of nodes), in addition to the antinodal stripsons and humpons. Thus the arcon peaks split below T_c into positive- and negative-energy peaks, as is sketched in Fig. 4(a). Since their coupling to other QEs through \mathbf{Q}_m lagrons is weak, or absent, the *additional* pairing necessary for SC to set in is induced primarily through \mathbf{Q} -ESP lagrons.

As was discussed above, the lagron energy involved in such pairing is $\sim \omega^\lambda(\mathbf{Q})$ which could be treated analogously to the dominant boson energy [68] $k_B \bar{\Omega}$ in electron-phonon systems. A coupling parameter $\bar{\lambda}$ is obtained by approximating Eq. (48) similarly to the treatment of such

systems [68], resulting in values as large as $\bar{\lambda} \simeq 3$. The dependence of $\bar{\lambda}$ on the doping level is *weak* since, below T_c , $\bar{\Phi}^q \neq 0$ *both* for the nodal and the antinodal QEs.

Estimating T_c on the basis of an expression (for electron-phonon systems) which is valid within the *entire* coupling regime [68]: $T_c \simeq 0.25\tilde{\Omega}/[\exp(2/\bar{\lambda}) - 1]^{1/2}$, results in an approximate scaling $\omega^\lambda(\mathbf{Q})/k_B T_c \simeq 3.9$, and thus [56] $E_{\text{res}}/k_B T_c \simeq 5.2$, in agreement with experiment [69]. This explains the enhancement of T_c compared to conventional electron-phonon SCs, where such large $\bar{\lambda}$ values would result in lattice instabilities.

The crucial role played by lagrons at the \mathbf{Q}_m points and their vicinity (where $\omega^\lambda(\mathbf{q}) \propto |\mathbf{q} - \mathbf{Q}_m|$) in the pairing of stripons is not comparable to the minor role played by low-energy acoustic phonons in conventional SCs; while the coupling constants between electrons and acoustic phonons vanish [31, 39] for $\mathbf{q} \rightarrow 0$, the coupling constants $\gamma(\mathbf{q})$ between QEs and lagrons remain constant for $\mathbf{q} \rightarrow \mathbf{Q}_m$ (see Eq. (16) and the above discussion).

High-energy lagrons also play some role in pairing, and specifically the high-energy SP lagrons (see Fig. 2). An optical analysis, in an attempt to determine the energy spectrum of the bosons involved in pairing in the cuprates, reveals [70] significant contributions of bosons at low energies, at energies [56] $\sim \omega^\lambda(\mathbf{Q}) \simeq \frac{3}{4}E_{\text{res}}$, and at energies $\sim 0.2\text{--}0.3$ eV which are consistent with those of high-energy SP lagrons.

The opening of an SC gap prevents the above derivation of QE and svivon scattering rates, depending on the condition $T > T_p^q$ (which is only partially fulfilled in the PG phase). This results in a drastic reduction in Γ^q and $|\Gamma^s|$, for $|\omega|$ below the gap energy, but not above it. Consequently, the split stripon and arcon peaks are sharp below T_c , while the humpon peaks remain wide (see Fig. 4(a)).

Also the low-energy svivon spectral tails disappear below T_c , and thus the electron spectral functions $A^d(\mathbf{k}, \omega)$, can then be approximated through a modification (see above) of the convoluted QE-svivon term $A_{0c}^d(\mathbf{k}, \omega)$ in Eq. (C1) *alone*. The resulting radical reduction (for $T < T_c$) in the electron scattering rates, for $|\omega|$ below the gap energy, is observed in optical [6] and microwave [7] results.

An aspect of Tanner’s law [10], discussed above, is that the optically determined SC-state superfluid density corresponds to the density of carriers determined by the normal-state Drude term, and misses the contribution of the mid-IR term. This observation is consistent with the present prediction that both the Drude and the superfluid density are determined by the contribution of stripons and arcons to A_0^d .

The traces of the arcon and stripon gaps on A^d , sketched in Fig. 4(b), are often referred to as nodal and antinodal gaps, respectively. The antinodal gap-edge structure includes the (stripon-derived) peak and (humpon-derived) hump (see Fig. 4(b)). The nodal gap has been found [71, 72] to scale with $\sim 5k_B T_c$, consistently [68] with the ratio between the pairing gap and T_c for the

large coupling parameters $\bar{\lambda}$ in this case (see above).

Since Eq. (48) couples between the nodal and antinodal pairing order parameters, the opening of a nodal gap below T_c modifies the antinodal gap (which opens below T^*) in a manner observed [73, 74] as an apparent onset (below T_c) of a “second energy gap”, superimposed on the pseudogap; however, it is clear that the antinodal gap is “smoothly connected” to the nodal gap [75].

In the underdoped regime, most of the antinodal (but not nodal) Cooper pairs are formed at $T_c < T < T^*$; this is consistent with the observation [76] that in this regime only a small density of additional antinodal (but not nodal) pairs are formed at $T < T_c$. Since the superfluid density consists of pairs formed both at $T < T_c$ and at $T_c < T < T^*$, it does not coincide with the density of the additional pairs formed at $T < T_c$ [76].

The svivon energy minima are lower below T_c than their values ($\bar{\epsilon}_{\text{min}}^s$) above it, and since the low-energy svivon spectral tails existing above T_c (see Fig. 6 and Appendix B) have disappeared, a spin gap opens up. This results [16] in the existence of a *sharp* resonance mode below T_c . Since (see above) the energy separation between the stripon and humpon peaks [56] $> \omega^\lambda(\mathbf{Q}) \simeq \frac{3}{4}E_{\text{res}}$, the reduction in the width of the stripon peak results in the appearance of a dip between the peak and the hump (see Fig. 4(b)), at $\sim E_{\text{res}}$ above the peak, in agreement with experiment [8, 77]. This structure is manifested as a T -dependent “antinodal kink” in the electron dispersion curves [78].

The balance between energy gains due to pairing and inhomogeneity, discussed above with respect to the PG phase, is relevant also for the SC state, especially in the underdoped regime. The fact that the lattice is involved in the establishment of the static checkerboard-like [21] structure (see above) is supported by the observation of an unconventional isotope effect within this regime [79]. It is viewed *not only* in T_c , but also in properties like the magnetic penetration depth, in T^* , and in the onset temperatures of spin-glass and AF ordering in adjacent inhomogeneous regimes of the phase diagram [79].

Since the local lattice distortions have a non-linear negative effect on the pairing energy, a heterogeneous nanoscale structure sets in [80], including regions of varying strengths of the effects of pairing and inhomogeneity. Regions of a stronger pairing effect are characterized by a larger spectral weight within the peak (on the expense of that within the hump), and a weaker checkerboard-like structure. Since the static inhomogeneities have only a minor effect on the nodal gap, this heterogeneous structure has almost no effect on it (it has a significant effect on the antinodal gap), in agreement with experiment [80].

V. CONSTRAINT SUSCEPTIBILITY

The spectrum $\omega^\lambda(\mathbf{q})$ of the lagrons, and the constants $\gamma(\mathbf{q})$ of their coupling to QEs and svivons, have to be determined through the condition that the resulting QE

and svivon spectra satisfy, in every site, the auxiliary-particles' constraint in Eq. (6). This condition can be expressed as a requirement [16] that two-site correlation functions of the svivon operators in the lhs of Eq. (6) is equal to that defined, similarly, through the QE operators in the rhs of Eq. (6); thus:

$$\sum_{\sigma\sigma'} \langle s_{i\sigma}^\dagger s_{i\sigma} s_{j\sigma'}^\dagger s_{j\sigma'} \rangle \cong \langle q_i^\dagger q_i q_j^\dagger q_j \rangle. \quad (51)$$

The terms in the lhs and the rhs of Eq. (51) introduce a susceptibility-like function, referred to as the constraint-susceptibility [16] (χ_c^s or χ_c^q); it should be the same (thus $\chi_c^s = \chi_c^q$), whether it is evaluated on the basis of the svivon spectrum (thus χ_c^s), or the QE spectrum (thus χ_c^q), through the lhs or the rhs of Eq. (51), respectively. Vertex corrections to χ_c^s and χ_c^q , due to $\Delta\mathcal{H}$ in Eq. (12) and \mathcal{H}' in Eq. (23), do not vary them qualitatively.

A major feature of $\Im\chi_c^s(\mathbf{q}, \omega - i0^+)$, in the SC state, is [16] the existence, around $\mathbf{q} = 0$, of a sharp low-energy peak at $\omega \simeq E_{\text{res}}$, and a higher-energy tail, extending up to $\sim J$; the $\chi_c^q = \chi_c^s$ equality implies that such a peak structure must be also a major feature of $\Im\chi_c^q(\mathbf{q}, \omega - i0^+)$ in the SC state; it can be, approximately, evaluated through [39, 40] (see Eqs. (44), (45), (47) and (51)):

$$\begin{aligned} \chi_c^q(\mathbf{q}, z) \cong & \frac{1}{N} \sum_{\mathbf{k}} \int d\omega_1 \int d\omega_2 \left\{ [\cos^2(\xi_{\mathbf{k}}^q(\omega_1)) A_+^q(\mathbf{k}, \omega_1) \right. \\ & + \sin^2(\xi_{\mathbf{k}}^q(\omega_1)) A_-^q(\mathbf{k}, \omega_1)] [\cos^2(\xi_{\mathbf{k}-\mathbf{q}}^q(\omega_2)) \\ & \times A_+^q(\mathbf{k}-\mathbf{q}, \omega_2) + \sin^2(\xi_{\mathbf{k}-\mathbf{q}}^q(\omega_2)) \\ & \times A_-^q(\mathbf{k}-\mathbf{q}, \omega_2)] + \frac{1}{4} \sin^2(2\xi_{\mathbf{k}}^q(\omega_1)) \\ & \times \sin(2\xi_{\mathbf{k}-\mathbf{q}}^q(\omega_2)) \cos[\phi_{\mathbf{k}}^q(\omega_1) - \phi_{\mathbf{k}-\mathbf{q}}^q(\omega_2)] \\ & \times [A_+^q(\mathbf{k}, \omega_1) - A_-^q(\mathbf{k}, \omega_1)] [A_+^q(\mathbf{k}-\mathbf{q}, \omega_2) \\ & \left. - A_-^q(\mathbf{k}-\mathbf{q}, \omega_2)] \right\} \frac{f_T(\omega_2) - f_T(\omega_1)}{z + \omega_2 - \omega_1}. \quad (52) \end{aligned}$$

The structure of a peak in $\Im\chi_c^q(\mathbf{q} = 0, \omega - i0^+)$, obtained through Eq. (52), represents an average on the same- \mathbf{k} -point transitions between negative- and positive-energy QE spectral features (thus on the two sides of the SC gap, as is sketched in Fig. 4(a)). These features consist of single sharp arcon peaks in the nodal areas, and of separate stripon and (broad) humpon peaks in the antinodal areas.

Thus, an equality between $\Im\chi_c^q$ and $\Im\chi_c^s$, at $\mathbf{q} = 0$ in the SC state, means that the sharp low-energy peak corresponds to averaged same- \mathbf{k} transitions between the positive- and negative-energy arcon peaks, while the higher-energy tail corresponds to averaged same- \mathbf{k} transitions between the positive- and negative-energy stripon-humpon spectral features. The proximity of the low-energy peak to E_{res} , and of the extent of the higher-energy tail to $\sim J$, is consistent with the above-mentioned values of the SC nodal gap [68], and the humpon energies, respectively. This demonstrates the qualitative self-consistency of the theoretical approach, the lagron spectrum, and the spectral functions presented here.

The constraint-susceptibility analysis demonstrates that the connection between features (such as typical energies) of the QE and lagron spectra, derived here, is closely related to the auxiliary-particles' constraint. This results in similarities between spectroscopic features derived here and in models where electrons are coupled to spin fluctuations. However, since such models do not correspond to the large- U case (studied here), a quantitative analysis based on them [81] does not yield a realistic spectrum of the relevant spin fluctuations.

VI. CONCLUSIONS

In conclusion, a theory for highly correlated layered SCs, where the low-energy excitations are approached in terms of combinations of atomic-like electron configurations, rather than approximately independent electrons, has been shown to resolve qualitative mysteries of the cuprates. A Lagrange Bose field which accounts for the tendency of the doped system to form stripe-like inhomogeneities, enables treating these configurations as bosons or fermions.

The addressed anomalous properties of the hole-doped cuprates include the observed phase diagram, non-FL to FL crossover, the existence of MFL critical behavior and a PG phase with Fermi arcs, kink- and waterfall-like spectral features, the drop in the scattering rates in the PG phase, and further in the SC phase, an effective increase in the density of carriers with T and ω , the correspondence between T_c , E_{res} , and the SC nodal gap, *etc.*

Electron-lattice coupling is not included in the Hamiltonian treated here; however, such coupling is necessary to explain the establishment of static inhomogeneous structures within the PG and SC states. This coupling is expected to be strong for the derived low-energy spectral peaks, introducing phonon anomalies at comparable energies, an anomalous isotope effect [79], *etc.*

The electronic structure of the FeSCs differs from that of the cuprates. However, the similarity between their anomalous properties [16], and the fact that a formally common many-body Hamiltonian could be worked out [16] for both systems, implies that part of the conclusions drawn above about the physics of the cuprates, apply also for the FeSCs, with some modification. Further details of the theory, and a comparison between its consequences for the cuprates and the FeSCs, will appear in forthcoming papers.

Acknowledgments

The author acknowledges the encouragement of Davor Pavuna, and constructive discussions with him. He also benefited from stimulating discussions with Stewart Barnes, Antonio Bianconi, Annette Bussmann-Holder, Neil Johnson, Hugo Keller, Dirk Manske, Alex Müller, David Tanner, Dirk van der Marel, Carolyne Van Vliet,

and other colleagues and members of the high- T_c community.

Appendix A: Evaluation of the QE Scattering Rates

The behavior of Γ^q is determined at \mathbf{k} points within the low-energy nodal and antinodal areas, and the adjacent high-energy areas; it could be expressed as a sum of two terms:

$$\Gamma^q(\mathbf{k}, \omega) = \Gamma_1^q(\mathbf{k}, \omega) + \Gamma_2^q(\mathbf{k}, \omega), \quad (\text{A1})$$

corresponding to the contributions of the \mathbf{Q}_m lagrons (Γ_1^q), and of the other lagrons (Γ_2^q), to the \mathbf{q} summation in Eq. (35).

By Eqs. (20, 35), $\Gamma_1^q(\mathbf{k}, \omega)$ in Eq. (A1) can be approximately expressed as:

$$\Gamma_1^q(\mathbf{k}, \omega) \propto \sum_{m=1}^4 A^q(\mathbf{k} - \mathbf{Q}_m, \omega), \quad (\text{A2})$$

where the combination in the rhs is of terms specified as $A_{\text{le}}^q(\omega)$, $A_{\text{me}}^q(\omega)$ and $A_{\text{he}}^q(\omega)$ (see above), consisting of the arcon, stripon and humpon peaks, shown in Fig. 4(a), and the higher-energy spectrum, shown in Fig. 3(a-b); terms scaling with them contribute, through Eq. (A2), to low- $|\omega|$ Γ^q within the antinodal areas, and partially within the nodal areas (not too close to the lines of nodes) and the adjacent high-energy areas. $A_{\text{le}}^q(\omega \rightarrow 0)$ (and its contribution to $\Gamma_1^q(\omega \rightarrow 0)$) decreases when T increases (see below), and $\lim_{T \rightarrow 0} A_{\text{le}}^q(\omega \rightarrow 0)$ does not vanish (for unpaired QEs). Consequently, in \mathbf{k} points within the above areas there exists a nonzero limit:

$$\Gamma_0^q(\mathbf{k}) \equiv \lim_{T \rightarrow 0} \Gamma_1^q(\mathbf{k}, \omega \rightarrow 0). \quad (\text{A3})$$

By Eq. (32), and the lack of contributions due to Γ_2^q (see below), $\Gamma_0^q(\mathbf{k})$ determine the zero- T limit of the widths of the stripon and arcon peaks which are, consequently, ~ 0 close to the lines of nodes. Let Γ_{0a}^q be a typical value of $\Gamma_0^q(\mathbf{k})$ in the antinodal areas; since it is determined by the coupling of QEs, through Eqs. (35, A3), to \mathbf{Q}_m lagrons, while ω_{H} is determined by their coupling, through Eq. (34), to *both* \mathbf{Q}_m and other lagrons (see below), Γ_{0a}^q is few times smaller than ω_{H} .

A \mathbf{k} -dependent low-energy scale $\omega_{\text{L}}(\mathbf{k})$ exists which is close to Γ_{0a}^q in the antinodal areas; for $k_{\text{B}}T$ & $|\omega| \ll \omega_{\text{L}}(\mathbf{k})$, $A^q(\mathbf{k}, \omega)$ is dominated by the contribution of $\Gamma_0^q(\mathbf{k})$ to Eq. (32), and it is almost independent of T and ω within this range. For $k_{\text{B}}T \gg \omega_{\text{L}}(\mathbf{k})$, the T - and ω -dependencies of the stripon/arcon peak center (discussed above), and of Γ^q , largely determine the behavior of $A_{\text{le}}^q(\omega)$, through Eq. (32). Its low- ω T -dependence is determined by the broadening of the peak (through Γ^q) which, self-consistently, scales with T (see below), resulting in an approximate scaling of the low- ω A_{le}^q with $1/T$.

$\Gamma_2^q(\mathbf{k}, \omega)$ in Eq. (A1) includes the part in the rhs of Eq. (35) where only the four \mathbf{Q}_m points in Eq. (20) are

omitted from the sum over \mathbf{q} . This summation requires a 2D integration which could be carried out by dividing the BZ into a mesh based on \mathbf{q}_{\parallel} and \mathbf{q}_{\perp} lines, directed along lagron-energy gradients, and perpendicular to them, respectively.

As can be viewed in Figs. 2 and 3(c), for a sufficiently fine mesh, each BZ section (specified as s) within it could be approximated as a circular segment where $\omega^\lambda(\mathbf{q})$ is linear in \mathbf{q}_{\parallel} , and $A^q(\mathbf{k} - \mathbf{q}, \omega \mp \omega^\lambda(\mathbf{q}))$ in Eq. (35) could be expressed as $A_s^q(\omega \mp \omega^\lambda(\mathbf{q}))$, where A_s^q is of the form of either A_{le}^q or A_{me}^q or A_{he}^q . Consequently, the \mathbf{q} integral over the circular segment s is, approximately, proportional to an integral on $d\omega^\lambda$, where the integrand is multiplied by $(\omega^\lambda - \omega_{0s}^{\lambda q})$, between positive limits $\omega_{ns}^{\lambda q}$ and $\omega_{xs}^{\lambda q}$ ($\omega_{0s}^{\lambda q}$ is a constant).

Fig. 2 indicates that $\omega_{0s}^{\lambda q} = \omega_{ns}^{\lambda q} = 0$ within four circular BZ sections around the V-shape lagron energy minima at the \mathbf{Q}_m points, and that $|\omega_{0s}^{\lambda q}|$ are large in integration sections corresponding to \mathbf{Q} -ESP lagrons (where $\omega^\lambda \simeq \omega^\lambda(\mathbf{Q})$) and to high-energy SP lagrons.

The major features of $\Gamma_2^q(\mathbf{k}, \omega)$, in the low- and high- $|\omega|/k_{\text{B}}T$ limits, are obtained when the following approximations are applied within each of the above $d\omega^\lambda$ integration ranges: (a) the asymptotic behavior of $b_T(\omega^\lambda)$, for $\omega^\lambda \ll k_{\text{B}}T$ and $\omega^\lambda \gg k_{\text{B}}T$, (thus $b_T(\omega^\lambda) \cong k_{\text{B}}T/\omega^\lambda$, for $\omega^\lambda \ll k_{\text{B}}T$, and $b_T(\omega^\lambda) \cong 0$, for $\omega^\lambda \gg k_{\text{B}}T$) is extended to $\omega^\lambda < k_{\text{B}}T$ and $\omega^\lambda > k_{\text{B}}T$, respectively; (b) the low- T limit of $f_T(\omega')$ (thus $f_T(\omega') \cong 1$, for $\omega' < 0$, and $f_T(\omega') \cong 0$, for $\omega' > 0$) is applied for $f_T(\omega^\lambda \mp \omega)$. This yields, through Eq. (35):

$$\begin{aligned} \Gamma_2^q(\mathbf{k}, \omega) &= \sum_s [\Gamma_{Ts}^q(\mathbf{k}, \omega) + \Gamma_{\omega s}^q(\mathbf{k}, \omega)], \quad \text{where} \\ \Gamma_{Ts}^q(\mathbf{k}, \omega) &\propto k_{\text{B}}T \int_{\omega_{Tns}^{\lambda q}}^{\omega_{Txs}^{\lambda q}} d\omega^\lambda (1 - \omega_{0s}^{\lambda q}/\omega^\lambda) [A_s^q(\omega - \omega^\lambda) \\ &\quad + A_s^q(\omega + \omega^\lambda)], \quad (\text{A4}) \\ \Gamma_{\omega s}^q(\mathbf{k}, \omega) &\propto \int_{\omega_{\omega ns}^{\lambda q}}^{\omega_{\omega xs}^{\lambda q}} d\omega^\lambda (\omega^\lambda - \omega_{0s}^{\lambda q}) A_s^q(\omega - \omega^\lambda \text{sign}(\omega)), \\ \omega_{Tns}^{\lambda q} &= \min(k_{\text{B}}T, \omega_{ns}^{\lambda q}), \quad \omega_{Txs}^{\lambda q} = \min(k_{\text{B}}T, \omega_{xs}^{\lambda q}), \\ \omega_{\omega ns}^{\lambda q} &= \min(|\omega|, \omega_{ns}^{\lambda q}), \quad \omega_{\omega xs}^{\lambda q} = \min(|\omega|, \omega_{xs}^{\lambda q}). \end{aligned}$$

By the results presented in Figs. 2 and 3(a-c), one could evaluate the contributions $\delta\Gamma_2^q$ to Γ^q , within the different BZ areas, due to terms including different forms of A_s^q in Eq. (A4). The T - and ω -dependencies of these $\delta\Gamma_2^q$ terms depend on those of A_s^q , on the integration limits in Eq. (A4), and on the number of nonzero integrals there. Within the antinodal areas, significant values of $\delta\Gamma_2^q$ are obtained through Eq. (A4) for $\omega \rightarrow 0$, while close to the lines of nodes (where $\Gamma_0^q(\mathbf{k})$ to Eq. (A3) is negligible) they contribute significantly only when $|\omega|$ exceeds an energy which is somewhat smaller than $\omega^\lambda(\mathbf{Q})$. Thus, this energy determines the low-energy scale $\omega_{\text{L}}(\mathbf{k})$ (see above) around the lines of nodes.

As was discussed above, for $k_{\text{B}}T$ & $|\omega| \ll \omega_{\text{L}}(\mathbf{k}')$, A_{le}^q in this \mathbf{k}' point is approximately independent of T and

ω , within the low- ω^λ integration sections in Eq. (A4), resulting in weak T and ω dependencies of the corresponding $\delta\Gamma_2^q$. For $k_B T \gg \omega_L(\mathbf{k}')$ and $|\omega| \ll k_B T$, since A_{le}^q , self-consistently, scales as $1/T$ (see above), $\delta\Gamma_2^q$ approximately scales with T by Eq. (A4). For $|\omega| \gg \omega_L(\mathbf{k}')$ and $k_B T \ll |\omega|$, A_{le}^q can be approximated in Eq. (A4) by a δ -function around the energy of the corresponding arcon or stripon peak, resulting in $\delta\Gamma_2^q$ which is linear in ω . The high- $|\omega|$ extent of this term is limited by the high-energy extent of the lagron spectrum in Fig. 2, and the high- T extent is limited by the phase stability.

When $k_B T$ or $|\omega|$ exceeds ω_H , A_{me}^q (due to the humpons—see above) behaves similarly to A_{le}^q , and the $\delta\Gamma_2^q$ term it contributes also has, in this range, a linear dependence on T in the low- $|\omega|$ limit, and a linear dependence on ω , in the low- T limit. This results in an increase in the slope of the Γ^q vs T ($|\omega|$) curve as the increasing $k_B T$ ($|\omega|$) approaches ω_H . A similar slope increase, due to A_{he}^q , is expected when their high-energy maxima are approached, *as long as* they do not exceed the high-energy extent of the lagron spectrum. However, since (see Fig. 3(a-b)) there is an apparent discontinuity between the QE low- and high-energy BZ areas, where the energies at the maxima of A_{he}^q mostly exceed those of the lagron spectrum, the derived contribution of A_{he}^q to Γ^q is minute.

Appendix B: Evaluation of the svivon Scattering Rates

The $\cosh^2(\xi_{\mathbf{k}}^s(\omega'))$ and $\sinh^2(\xi_{\mathbf{k}}^s(\omega'))$ factors, appearing in the expression for Γ_λ^s in Eq. (37), are close to $\cosh(2\xi_{\mathbf{k}}^s(\omega'))$ within the LE and ME svivon BZ areas, where the major contribution to the expression comes from; thus their T and ω dependencies there are close to those of $\cosh(2\xi_{\mathbf{k}}^s(\omega'))$, derived above through Eq. (39). The effect of their $\propto 1/(T - T_0)$ behavior within the LE areas is considered *together with* the size $\propto (T - T_0)^2$ of these areas, resulting in an approximate scaling with $(T - T_0)$. The associated decrease in the size of the ME areas introduces in these areas a minor $\propto (T - T_0)^2$ term, as in $\cosh(2\xi_{\mathbf{k}}^s(\omega'))$.

The values of $n^s(\mathbf{k})$ are determined through Eq. (29), and their variation with T takes place mainly in the LE BZ areas. However, since n^s is T independent, one gets through Eq. (22) that the T variation is minor for the averaged values of $n^s(\mathbf{k})$ over the LE areas and the crossover areas between them and the ME areas. This applies also for the T dependence of the $|m^s(\mathbf{k}')|$ factors, appearing in the expression for Γ_q^s in Eq. (37), due to the proximity in the LE areas between the expressions for $n^s(\mathbf{k})$ and $m^s(\mathbf{k})$ in Eq. (29).

$\Gamma_q^s(\mathbf{k}, \omega)$ represents the scattering of a svivon into a particle-hole QE pair, while its spin is condensed; at low T and ω , it is determined by the stripon and arcon A_{le}^q spectral functions. In the $k_B T \ll |\omega| \ll \Gamma_{0a}^q$ regime (see Eq. (A3) and the discussion in Appendix A), A_{le}^q

is, approximately, constant within the integration range in Eq. (37); in the LE areas, this results in Γ_q^s which approximately scales with $\omega/(T - T_0)$, for $|\omega| \lesssim \bar{\epsilon}_{\min}^s$, its magnitude passes through a maximum at higher $|\omega|$ values, and crosses over to scaling with ω in the $|\omega| \gg \bar{\epsilon}_{\min}^s$ limit, if it could be reached in this regime; as was discussed above, in processes where Γ_q^s is integrated over a part of the BZ, the contribution of the LE areas to it scales with $\omega(T - T_0)$, for $|\omega| \lesssim \bar{\epsilon}_{\min}^s$; $|\Gamma_q^s|$ is smaller, in this regime, in the ME areas (and much smaller in the HE areas), and approximately scales there with ω , plus a minor term $\propto \omega(T - T_0)^2$ (and it may pass through a maximum).

When $k_B T \gg \Gamma_{0a}^q$ & $|\omega|$, the T -scaled broadening of $A_{le}^q(\omega)$ (see Appendix A) results in a $1/T^2$ -scaled decrease of the above values of Γ_q^s with T . For $|\omega| \gg \Gamma_{0a}^q$ & $k_B T$, the contribution of particle-hole QE pairs, based on A_{le}^q , to Γ_q^s is vanishing, resulting in its sharp decrease; a high- ω contribution to Γ_q^s due to humpons and high-energy QEs is small compared to Γ_λ^s , for such values of ω .

The major physical effect of Γ_q^s is the introduction, *right above* [41] T_p^q , of a width $|\Gamma^s|$ to the svivon states around their energy minima which extends to exceedingly low (nonzero) energies $|\omega|$. The corresponding spectral functions, obtained through Eq. (28), can be approximately expressed as:

$$\begin{aligned} A^s(\mathbf{k}, \omega) &\simeq \frac{\Gamma^s(\mathbf{k}, \omega)/2\pi}{[\omega - \bar{\epsilon}^s(\mathbf{k})]^2 + [\frac{1}{2}\Gamma^s(\mathbf{k}, \omega)]^2} \\ &\simeq \frac{\Gamma^s(\mathbf{k}, \omega)}{2\pi[\bar{\epsilon}^s(\mathbf{k})]^2}, \text{ for } |\omega| \ll \bar{\epsilon}^s(\mathbf{k}). \end{aligned} \quad (\text{B1})$$

The ω scaling of Γ_q^s , at low ω and T , results in an ω -independent product $A^s(\mathbf{k}, \omega)b_T(\omega)$ in the low- ω limit.

Similarly to Γ^q in Eq. (A1), Γ_λ^s could be expressed as a sum of two terms:

$$\Gamma_\lambda^s(\mathbf{k}, \omega) = \Gamma_1^s(\mathbf{k}, \omega) + \Gamma_2^s(\mathbf{k}, \omega), \quad (\text{B2})$$

corresponding to the contributions of the \mathbf{Q}_m lagrons (Γ_1^s), and of the other lagrons (Γ_2^s), to the \mathbf{q} summation in Eq. (37). As in the case of Γ_1^q in Eq. (A2), Γ_1^s can be approximately expressed as:

$$\begin{aligned} \Gamma_1^s(\mathbf{k}, \omega) &\propto \cosh(2\xi_{\mathbf{k}}^s(\omega)) \\ &\times \sum_{m=1}^4 [A^s(\mathbf{k} - \mathbf{Q}_m, \omega) \cosh^2(\xi_{\mathbf{k} - \mathbf{Q}_m}^s(\omega)) \\ &\quad - A^s(\mathbf{k} - \mathbf{Q}_m, -\omega) \sinh^2(\xi_{\mathbf{k} - \mathbf{Q}_m}^s(-\omega))]. \end{aligned} \quad (\text{B3})$$

Thus, $|\Gamma_1^s(\mathbf{k}, \omega)|$ has maxima combined of the maxima of $A^s(\mathbf{k} - \mathbf{Q}_m, |\omega|)$ at $|\omega| \cong \bar{\epsilon}^s(\mathbf{k} - \mathbf{Q}_m)$, for the four \mathbf{Q}_m points, and decreases to zero at higher energies. Within a svivon condensate, $\bar{\epsilon}^s(\mathbf{k} - \mathbf{Q}_m) \simeq \bar{\epsilon}^s(\mathbf{k})$ for one of the \mathbf{Q}_m points, and $|\Gamma_1^s(\mathbf{k}, \omega)|$ is largest when both \mathbf{k} and $\mathbf{k} - \mathbf{Q}_m$ are at the LE areas. In the low $\omega/k_B T$ limit, Γ_1^s is negligible (see Eqs. (B1, B3)) compared to Γ_q^s and Γ_2^s (see below).

An expression for $\Gamma_2^s(\mathbf{k}, \omega)$ is derived analogously to the one for $\Gamma_2^q(\mathbf{k}, \omega)$ in Eq. (A4). The \mathbf{q} summation in Eq. (37) is, similarly, carried out by using a BZ mesh based on circular segments s , where the $A^s(\mathbf{k} - \mathbf{q}, \omega \mp \omega^\lambda(\mathbf{q})) \cosh^2(\xi_{\mathbf{k}-\mathbf{q}}^s(\omega \mp \omega^\lambda(\mathbf{q}))$ and $A^s(\mathbf{k} - \mathbf{q}, -\omega \pm \omega^\lambda(\mathbf{q})) \sinh^2(\xi_{\mathbf{k}-\mathbf{q}}^s(-\omega \pm \omega^\lambda(\mathbf{q}))$ terms in Eq. (37) are expressed as $A_s^s(\omega \mp \omega^\lambda(\mathbf{q})) \cosh^2(\xi_s^s(\omega \mp \omega^\lambda(\mathbf{q}))$ and $A_s^s(-\omega \pm \omega^\lambda(\mathbf{q})) \sinh^2(\xi_s^s(-\omega \pm \omega^\lambda(\mathbf{q}))$, respectively.

As in the case of Γ_2^q , the \mathbf{q} integral over section s is, approximately, proportional to an integral on $d\omega^\lambda$, where the integrand is multiplied by $(\omega^\lambda - \omega_{0s}^{\lambda s})$, between positive limits $\omega_{ns}^{\lambda s}$ and $\omega_{xs}^{\lambda s}$; again, one has $\omega_{0s}^{\lambda s} = \omega_{ns}^{\lambda s} = 0$ within four circular BZ sections around the V-shape lagron energy minima at the \mathbf{Q}_m points, and $|\omega_{0s}^{\lambda s}|$ are large in integration sections corresponding to \mathbf{Q} -ESP and high-energy SP lagrons.

Similarly to the evaluation of Γ_2^q in Appendix A, the $b_T(\omega')$ functions in Eq. (37) (where ω' is either ω^λ or $\omega^\lambda \mp \omega$) are approximated through their asymptotic behaviors: (a) $b_T(\omega') \cong k_B T / \omega$, for $|\omega'| \ll k_B T$; (b) $b_T(\omega') \cong -1$, for $\omega' \ll -k_B T$; (c) $b_T(\omega') \cong 0$, for $\omega' \gg k_B T$. In order to obtain the major features of $\Gamma_2^s(\mathbf{k}, \omega)$ in the low- and high- $|\omega|/k_B T$ limits, it is formulated in term of expressions where the asymptotic behavior of b_T in (a) is extended to $|\omega'| < k_B T$, and its behaviors in (b) and (c) are extended to $\omega' < -k_B T$ and $\omega' > k_B T$, respectively. Furthermore, when both $0 < \omega^\lambda < k_B T$ and $0 < \omega^\lambda \mp \omega < k_B T$, the differences $b_T(\omega^\lambda) - b_T(\omega^\lambda \mp \omega)$ are approximated (through derivation) as $\mp \omega k_B T / [\omega^\lambda \mp \omega/2]^2$. Consequently, one gets through Eq. (37):

$$\Gamma_2^s(\mathbf{k}, \omega) = \cosh(2\xi_{\mathbf{k}}^s(\omega)) \sum_s [\Gamma_{T_s}^s(\mathbf{k}, \omega) + \Gamma_{\tau_s}^s(\mathbf{k}, \omega) + \Gamma_{\omega_s}^s(\mathbf{k}, \omega)], \quad \text{where}$$

$$\Gamma_{T_s}^s(\mathbf{k}, \omega) \propto k_B T \left\{ \int_{\omega_{1ns}^{\lambda s}}^{\omega_{1xs}^{\lambda s}} d\omega^\lambda (1 - \omega_{0s}^{\lambda s} / \omega^\lambda) [A_s^s(\omega - \omega^\lambda \text{sign}(\omega)) \cosh^2(\xi_s^s(\omega - \omega^\lambda \text{sign}(\omega))) - A_s^s(\omega^\lambda \text{sign}(\omega) - \omega) \sinh^2(\xi_s^s(\omega^\lambda \text{sign}(\omega) - \omega))] - \left[\int_{\omega_{2ns}^{\lambda s}}^{\omega_{2xs}^{\lambda s}} + \int_{\omega_{3ns}^{\lambda s}}^{\omega_{3xs}^{\lambda s}} \right] d\omega^\lambda \left[\frac{\omega^\lambda - \omega_{0s}^{\lambda s}}{\omega^\lambda - |\omega|} \right] [A_s^s(\omega - \omega^\lambda \text{sign}(\omega)) \cosh^2(\xi_s^s(\omega - \omega^\lambda \text{sign}(\omega))) - A_s^s(\omega^\lambda \text{sign}(\omega) - \omega) \sinh^2(\xi_s^s(\omega^\lambda \text{sign}(\omega) - \omega))] + \int_{\omega_{4ns}^{\lambda s}}^{\omega_{4xs}^{\lambda s}} d\omega^\lambda (1 - \omega_{0s}^{\lambda s} / \omega^\lambda) [A_s^s(\omega + \omega^\lambda \text{sign}(\omega)) \cosh^2(\xi_s^s(\omega + \omega^\lambda \text{sign}(\omega))) - A_s^s(-\omega^\lambda \text{sign}(\omega) - \omega) \sinh^2(\xi_s^s(-\omega^\lambda \text{sign}(\omega) - \omega))] \right\}$$

$$\Gamma_{\tau_s}^s(\mathbf{k}, \omega) \propto |\omega| k_B T \left\{ - \int_{\omega_{5ns}^{\lambda s}}^{\omega_{5xs}^{\lambda s}} d\omega^\lambda \frac{(\omega^\lambda - \omega_{0s}^{\lambda s})}{(\omega^\lambda - |\omega|/2)^2} [A_s^s(\omega - \omega^\lambda \text{sign}(\omega)) \cosh^2(\xi_s^s(\omega - \omega^\lambda \text{sign}(\omega))) - A_s^s(\omega^\lambda \text{sign}(\omega) - \omega) \sinh^2(\xi_s^s(\omega^\lambda \text{sign}(\omega) - \omega))] + \int_{\omega_{6ns}^{\lambda s}}^{\omega_{6xs}^{\lambda s}} d\omega^\lambda \frac{(\omega^\lambda - \omega_{0s}^{\lambda s})}{(\omega^\lambda + |\omega|/2)^2} [A_s^s(\omega + \omega^\lambda \text{sign}(\omega)) \cosh^2(\xi_s^s(\omega + \omega^\lambda \text{sign}(\omega))) - A_s^s(-\omega^\lambda \text{sign}(\omega) - \omega) \sinh^2(\xi_s^s(-\omega^\lambda \text{sign}(\omega) - \omega))] \right\}, \quad (\text{B4})$$

$$\Gamma_{\omega_s}^s(\mathbf{k}, \omega) \propto \int_{\omega_{7ns}^{\lambda s}}^{\omega_{7xs}^{\lambda s}} d\omega^\lambda (\omega^\lambda - \omega_{0s}^{\lambda s}) [A_s^s(\omega - \omega^\lambda \text{sign}(\omega)) \cosh^2(\xi_s^s(\omega - \omega^\lambda \text{sign}(\omega))) - A_s^s(\omega^\lambda \text{sign}(\omega) - \omega) \sinh^2(\xi_s^s(\omega^\lambda \text{sign}(\omega) - \omega))], \quad \text{and}$$

$$\omega_{T1} = \min(|\omega|, k_B T), \quad \omega_{T2} = \max(0, |\omega| - k_B T), \quad \omega_{ans}^{\lambda s} = \min(\omega_{T2}, \omega_{xs}^{\lambda s}), \quad \omega_{bns}^{\lambda s} = \max(\omega_{ans}^{\lambda s}, \omega_{ns}^{\lambda s}),$$

$$\omega_{T3} = \max(|\omega|, k_B T), \quad \omega_{cns}^{\lambda s} = \min(\omega_{T3}, \omega_{xs}^{\lambda s}), \quad \omega_{dns}^{\lambda s} = \max(\omega_{cns}^{\lambda s}, \omega_{ns}^{\lambda s}),$$

$$\omega_{T4} = |\omega| + k_B T, \quad \omega_{T5} = \max(0, k_B T - |\omega|), \quad \omega_{ens}^{\lambda s} = \min(\omega_{T5}, \omega_{xs}^{\lambda s}), \quad \omega_{fns}^{\lambda s} = \max(\omega_{ens}^{\lambda s}, \omega_{ns}^{\lambda s}),$$

$$\omega_{gns}^{\lambda s} = \min(\omega_{T1}, \omega_{xs}^{\lambda s}), \quad \omega_{hns}^{\lambda s} = \max(\omega_{gns}^{\lambda s}, \omega_{ns}^{\lambda s}), \quad \omega_{1ns}^{\lambda s} = \min(\omega_{T1}, \omega_{ns}^{\lambda s}), \quad \omega_{1xs}^{\lambda s} = \min(\omega_{T1}, \omega_{xs}^{\lambda s}),$$

$$\omega_{2ns}^{\lambda s} = \min(|\omega|, \omega_{bns}^{\lambda s}), \quad \omega_{2xs}^{\lambda s} = \min(|\omega|, \omega_{xs}^{\lambda s}), \quad \omega_{3ns}^{\lambda s} = \min(\omega_{T4}, \omega_{dns}^{\lambda s}), \quad \omega_{3xs}^{\lambda s} = \min(\omega_{T4}, \omega_{xs}^{\lambda s}),$$

$$\omega_{4ns}^{\lambda s} = \min(k_B T, \omega_{fns}^{\lambda s}), \quad \omega_{4xs}^{\lambda s} = \min(k_B T, \omega_{xs}^{\lambda s}), \quad \omega_{5ns}^{\lambda s} = \min(k_B T, \omega_{hns}^{\lambda s}), \quad \omega_{5xs}^{\lambda s} = \min(k_B T, \omega_{xs}^{\lambda s}),$$

$$\omega_{6ns}^{\lambda s} = \min(\omega_{T5}, \omega_{ns}^{\lambda s}), \quad \omega_{6xs}^{\lambda s} = \min(\omega_{T5}, \omega_{xs}^{\lambda s}), \quad \omega_{7ns}^{\lambda s} = \min(\omega_{T2}, \omega_{ns}^{\lambda s}), \quad \omega_{7xs}^{\lambda s} = \min(\omega_{T2}, \omega_{xs}^{\lambda s}).$$

The dominant contribution to Γ_2^s , in the low $|\omega|/k_B T$ limit, is of the $\Gamma_{\tau_s}^s$ terms in Eq. (B4). By Fig. 2, their integration ranges which contribute significantly to $\Gamma_2^s(\mathbf{k}, \omega)$ are, for $k_B T < \sim \omega^\lambda(\mathbf{Q})$, within the cone-like areas around those \mathbf{Q}_m points where $\mathbf{k} - \mathbf{Q}_m$ is within the LE areas; the shape of the integration ranges is modified when $k_B T$ exceeds $\sim \omega^\lambda(\mathbf{Q})$.

As was mentioned above, at a point \mathbf{k}' within the LE areas, $A^s(\mathbf{k}', \omega')$ is not small in the range $\omega' \simeq k_B T$, due to the effect of Γ_q^s at $T > T_p^q$; by Eq. (38), its T dependence could then be approximated (within the range where it is significant) in terms of a scaling factor α^s between ω' and $(T - T_0)$ which yields, taking into account normalization:

$$\begin{aligned} & (T' - T_0)A^s(\mathbf{k}', \omega' = \pm \alpha^s(T' - T_0)) @ T = T' \\ & \cong (T'' - T_0)A^s(\mathbf{k}', \omega' = \pm \alpha^s(T'' - T_0)) @ T = T'', \\ & \text{for } \mathbf{k}' \in \text{the LE areas.} \end{aligned} \quad (\text{B5})$$

Since the \cosh^2 and \sinh^2 factors in the expression for $\Gamma_{\tau_s}^s$, in Eq. (B4), approximately scale in the LE areas with $1/(T - T_0)$, they introduce a $1/(T - T_0)$ factor to the integrals within these areas. Furthermore, since the size of the LE areas scales with $(T - T_0)^2$, and $(T - T_0)A^s(\mathbf{k}', \omega^\lambda)$ has a scaling dependence on $\omega^\lambda/(T - T_0)$ (see Eq. (B5)), one could, approximately, replace the variable ω^λ in these integrals by $\omega^\lambda/(T - T_0)$, in the low $|\omega|/k_B T$ limit at least for $k_B T < \sim \omega^\lambda(\mathbf{Q})$.

This results in $\Gamma_2^s(\mathbf{k}, \omega)$ which approximately scales, in the low $|\omega|/k_B T$ limit, with $\omega/[(T - T_0)^2(1 - T_0/T)]$, if \mathbf{k} is within the LE areas, and with $\omega/[(T - T_0)(1 - T_0/T)]$, if it is within the part of ME areas where there exists a \mathbf{Q}_m point for which $\mathbf{k} - \mathbf{Q}_m$ is within the LE areas (which applies when $k_B T < \sim \omega^\lambda(\mathbf{Q})$). Thus, the ω dependence of $\Gamma_2^s(\mathbf{k}, \omega)$ in the low $|\omega|/k_B T$ limit is similar to that of $\Gamma_q^s(\mathbf{k}, \omega)$ (see above) in the $k_B T \ll \Gamma_{0a}^q$ regime, but it decreases faster with T there; however, this behavior of Γ_2^s persists in the $k_B T \gg \Gamma_{0a}^q$ regime, where Γ_q^s decreases faster with T , and it is somewhat modified when $k_B T$ exceeds $\sim \omega^\lambda(\mathbf{Q})$.

Similarly to Γ_q^s above, an integration on the low- $(|\omega|/k_B T)$ Γ_2^s , over a part of the BZ, results in a contribution of the LE areas which, approximately, scales with $\omega/(1 - T_0/T)$; for $k_B T > \sim \omega^\lambda(\mathbf{Q})$ this contribution persists as the dominant part of the \mathbf{k} -integrated low- $(|\omega|/k_B T)$ Γ^s , and it approximately scales with ω .

In the high- $|\omega|/k_B T$ limit, Γ_2^s is determined by the $\Gamma_{\omega_s}^s$ terms in Eq. (B4). The A^s functions in the integrals there can then be approximated by δ -functions around the corresponding $\pm \bar{\epsilon}^s(\mathbf{k}')$, resulting in factors $|\omega| - \bar{\epsilon}^s(\mathbf{k}') - \omega_{0s}^{\lambda s}$ (thus depending linearly on ω), for $|\omega| > \bar{\epsilon}^s(\mathbf{k}')$; however, there are also multiplicative factors of $\cosh^2(\xi_{\mathbf{k}'}^s(\bar{\epsilon}^s(\mathbf{k}')))$ or $\sinh^2(\xi_{\mathbf{k}'}^s(\bar{\epsilon}^s(\mathbf{k}')))$ and of $\cosh(2\xi_{\mathbf{k}'}^s(\omega))$ which has an opposite ω -dependence for $|\omega| < \sim J$.

Appendix C: Evaluation of the Electron Spectral Functions

By Eq. (42), $A_0^d(\mathbf{k}, \omega)$ is a convolution of QE and svivon spectral functions, weighted by the $b_T(\omega') + f_T(\omega' \mp \omega)$ factors. In order to study the effect of these factors, let us approximate them through their low- and high- $|\omega'|/k_B T$ asymptotic behaviors; thus they are expressed as: (a) $b_T(\omega') + f_T(\omega' \mp \omega) \cong k_B T/\omega'$, for $|\omega'| < k_B T$; (b) $b_T(\omega') + f_T(\omega' \mp \omega) \cong 0$, for $|\omega'|$ & $|\omega' \mp \omega| > k_B T$ and $\text{sign}(\omega') = \text{sign}(\omega' \mp \omega)$; (c) $b_T(\omega') + f_T(\omega' \mp \omega) \cong \omega'/|\omega'|$, for $|\omega'|$ & $|\omega' \mp \omega| > k_B T$ and $\text{sign}(\omega') \neq \text{sign}(\omega' \mp \omega)$; (d) $b_T(\omega') + f_T(\omega' \mp \omega) \cong \omega'/2|\omega'|$, for $|\omega'| > k_B T$ and $|\omega' \mp \omega| < k_B T$. Eq. (42) is then approximated as:

$$\begin{aligned} A_0^d(\mathbf{k}, \omega) &= A_{0b}^d(\mathbf{k}, \omega) + A_{0c}^d(\mathbf{k}, \omega), \quad \text{where} \\ A_{0b}^d(\mathbf{k}, \omega) &\cong \frac{k_B T}{N} \sum_{\mathbf{k}'} \int_{-k_B T}^{k_B T} \frac{d\omega'}{\omega'} A^s(\mathbf{k}', \omega') \\ &\quad \times [A^q(\mathbf{k} - \mathbf{k}', \omega - \omega') \cosh^2(\xi_{\mathbf{k}'}^s(\omega')) \\ &\quad + A^q(\mathbf{k} - \mathbf{k}', \omega + \omega') \sinh^2(\xi_{\mathbf{k}'}^s(\omega'))], \\ A_{0c}^d(\mathbf{k}, \omega) &\cong \frac{1}{N} \sum_{\mathbf{k}'} \left\{ \int_{k_B T}^{|\omega| + k_B T} d\omega' A^s(\mathbf{k}', \omega') \right. \\ &\quad \times [1 - \frac{1}{2}\theta(k_B T - |\omega| + \omega')] \\ &\quad \times [\theta(\omega)A^q(\mathbf{k} - \mathbf{k}', \omega - \omega') \cosh^2(\xi_{\mathbf{k}'}^s(\omega')) \\ &\quad + \theta(-\omega)A^q(\mathbf{k} - \mathbf{k}', \omega + \omega') \sinh^2(\xi_{\mathbf{k}'}^s(\omega'))] \\ &\quad - \int_{-|\omega| - k_B T}^{-k_B T} d\omega' A^s(\mathbf{k}', \omega') \\ &\quad \times [1 - \frac{1}{2}\theta(k_B T - |\omega| - \omega')] \\ &\quad \times [\theta(-\omega)A^q(\mathbf{k} - \mathbf{k}', \omega - \omega') \cosh^2(\xi_{\mathbf{k}'}^s(\omega')) \\ &\quad \left. + \theta(\omega)A^q(\mathbf{k} - \mathbf{k}', \omega + \omega') \sinh^2(\xi_{\mathbf{k}'}^s(\omega')) \right\}. \end{aligned} \quad (\text{C1})$$

$A_{0c}^d(\mathbf{k}, \omega)$ in Eq. (C1) represents a convolution of QE and modified svivon spectral functions, where the low-energy ($|\omega'| < k_B T$) tails of A^s have been truncated (see Eq. (B1) and Fig. 6(b)), while $A_{0b}^d(\mathbf{k}, \omega)$ is generated by these A^s tails and QE spectral functions. Since the QE spectrum (see Fig. 3(a-c)) includes almost dispersionless low-energy peaks extending over ranges of the BZ, the effect of the $A^q(\mathbf{k} - \mathbf{k}', \omega \mp \omega')$ terms in the expression for A_{0b}^d is to introduce their low-energy peaks which are modified (due to the \mathbf{k}' summation and ω' integration) to increase the peak widths by $\sim 2k_B T$; this results in an effective low-energy (LE) electron band of a linewidth which depends linearly on T , for $T > T_p^q$.

The contribution of svivons to the \mathbf{k}' summation (including averaging over the svivon condensates) in the expression for A_{0b}^d in Eq. (C1) is determined by that of the LE svivons, plus some contribution of ME svivons. For LE svivons, the \cosh^2 and \sinh^2 factors in this expression approximately scale with $1/(T - T_0)$ (see Eq. (39)), and the T dependence of the $A^s(\mathbf{k}', \omega')$ terms there is approximated through the scaling relation specified in Eq. (B5),

introducing a factor of $1/(T - T_0)$, and replacing the integration variable ω' by $x = \omega'/k_B(T - T_0)$ (with integration limits $\pm T/(T - T_0)$). For ME svivons the \cosh^2 , \sinh^2 and A^s factors have a weak T dependence.

As was discussed above, the size of the BZ areas of LE svivons scales with $(T - T_0)^2$ (on the expense of areas of the ME svivons). The expression for $A_{0b}^d(\mathbf{k}, \omega)$ in Eq. (C1) introduces, for \mathbf{k}' points corresponding to LE svivons, a BZ section (of the same size) of $\mathbf{k} - \mathbf{k}'$ points of QEs, out of which only its subsection of low-energy QEs contributes to the LE A_{0b}^d effective band. The size of this subsection approximately scales with $(T - T_0)^{\alpha^q(\mathbf{k})}$, where the T -dependent exponent $\alpha^q(\mathbf{k}) \geq 0$ is generally ≤ 2 . Consequently, the \mathbf{k}' summation over LE svivons in Eq. (C1) introduces a factor of $(T - T_0)^{\alpha^q(\mathbf{k})}$ to their contribution to the LE $A_{0b}^d(\mathbf{k}, \omega)$.

At low $T > T_p^q$, these low-QE-energy $\mathbf{k} - \mathbf{k}'$ points are shifted from the electron \mathbf{k} point (choosing the QE BZ as in Fig. 3(a-c)) by $\sim (\delta\mathbf{q}_m/2)$ and $\sim (\mathbf{Q}_m - \delta\mathbf{q}_m/2)$, for the four values of m (see Eq. (20)). As can be viewed in Fig. 3(c), $\alpha^q(\mathbf{k})$ is close to 2 for antinodal \mathbf{k} points, within this temperature regime, and one can then also assume that $k_B T \ll \Gamma_0^q(\mathbf{k})$, where the T dependence of the stripon A^q is weak (see Eq. (A3) and discussion in Ap-

pendix A). Thus, one gets by Eq. (C1) and the above discussion that the antinodal LE $A_{0b}^d(\mathbf{k}, \omega)$ approximately scales with T around its maximum; since the width of the effective electron band, it represents, is characterized by a constant plus a linear T term, this implies that for antinodal electrons at low $T > T_p^q$, the spectral weight within the LE effective band anomalously increases with T . There is some increase with T , in this regime, also in the spectral weight within the nodal LE effective band, mainly due to the contribution of ME svivons.

On the other hand, for antinodal and nodal \mathbf{k} points in the $k_B T \gg \Gamma_0^q(\mathbf{k})$ regime (in the nodal case this corresponds to $T > T_p^q$), $\alpha^q(\mathbf{k})$ is close to 1 (see Fig. 3(c)), and A^q in Eq. (C1) scales with $1/T$ (see discussion in Appendix A). This results in LE $A_{0b}^d(\mathbf{k}, \omega)$ which approximately scales with $1/T$ around its maximum; thus since the linewidth of the effective band it represents scales with T , one gets that the spectral weight within this band is approximately T independent for $k_B T \gg \Gamma_0^q(\mathbf{k})$. Note, however, that when $k_B T$ approaches ω_H , the humpons merge with the stripions in the antinodal BZ areas, resulting in a further increase in the spectral weight within the effective LE electron band there, saturating at $k_B T \gtrsim \omega_H$.

-
- [1] H. Takagi, B. Batlogg, H. L. Kao, J. Kwo, R. J. Cava, J. J. Krajewski, and W. F. Peck, Jr., *Phys. Rev. Lett.* **69**, 2975 (1992).
- [2] Y. Kubo and T. Manako, *Physica C* **197**, 378 (1992).
- [3] H. Y. Hwang, B. Batlogg, H. Takagi, H. L. Kao, J. Kwo, R. J. Cava, J. J. Krajewski, and W. F. Peck, Jr., *Phys. Rev. Lett.* **72**, 2636 (1994).
- [4] B. Fisher, J. Genossar, I. O. Lelong, A. Kessel, and J. Ashkenazi, *J. Supercond.* **1**, 53 (1988); J. Genossar, B. Fisher, I. O. Lelong, J. Ashkenazi, and L. Patlagan, *Physica C* **157**, 320 (1989).
- [5] S. Tanaka, M. Sera, M. Sato, and H. Fujishita, *J. Phys. Soc. Japan* **61**, 1271 (1992); K. Matsuura, T. Wada, Y. Yaegashi, S. Tajima, and H. Yamauchi, *Phys. Rev. B* **46**, 11923 (1992); S. D. Obertelli, J. R. Cooper, and J. L. Tallon, *Phys. Rev. B* **46**, 14928 (1992); C. K. Subramaniam, A. B. Kaiser, H. J. Trodahl, A. Mawdsley, and R. G. Buckley, *Physica C* **203**, 298 (1992).
- [6] A. V. Puchkov, D. N. Basov, and T. Timusk, *J. Phys.: Condens. Matter*, **8**, 10049 (1996).
- [7] D. A. Bonn, Ruixing Liang, T. M. Riseman, D. J. Baar, D. C. Morgan, Kuan Zhang, P. Dosanjh, T. L. Duty, A. MacFarlane, G. D. Morris, J. H. Brewer, W. N. Hardy, C. Kallin and A. J. Berlinsky, *Phys. Rev. B* **47**, 11314 (1993).
- [8] J. F. Zasadzinski, L. Ozyuzer, N. Miyakawa, K. E. Gray, D. G. Hinks, and C. Kendziora, *Phys. Rev. Lett.* **87**, 067005 (2001).
- [9] H. G. Luo, Y. H. Su, and T. Xiang, *Phys. Rev. B* **77**, 014529 (2008).
- [10] D. B. Tanner, H. L. Liu, M. A. Quijada, A. M. Zibold, H. Berger, R. J. Kelley, M. Onellion, F. C. Chou, D. C. Johnston, J. P. Rice, D. M. Ginsberg, and J. T. Markert, *Physica B* **244**, 1 (1998).
- [11] G. S. Boebinger, Yoichi Ando, A. Passner, T. Kimura, M. Okuya, J. Shimoyama, K. Kishio, K. Tamasaku, N. Ichikawa, and S. Uchida, *Phys. Rev. Lett.* **77**, 5417 (1996).
- [12] P. W. Anderson, *Phys. Rev. Lett.* **64**, 1839 (1990).
- [13] C. M. Varma, P. B. Littlewood, S. Schmitt-Rink, E. Abrahams and A. E. Ruckenstein, *Phys. Rev. Lett.* **63**, 1996 (1989).
- [14] Patrick A. Lee, *Rep. Prog. Phys.* **71**, 012501 (2008).
- [15] Karyn Le Hur, T. Maurice Rice, *Annals of Physics* **324**, 1452 (2009).
- [16] J. Ashkenazi, *J. Supercond. Nov. Magn.* **22**, 3 (2009), arXiv:0809.4237.
- [17] S. E. Barnes, *Adv. Phys.* **30**, 801 (1981).
- [18] J. M. Tranquada, J. D. Axe, N. Ichikawa, Y. Nakamura, S. Uchida, and B. Nachumi, *Phys. Rev. B* **54**, 7489 (1996); J. M. Tranquada, J. D. Axe, N. Ichikawa, A. R. Moodenbaugh, Y. Nakamura, and S. Uchida, *Phys. Rev. Lett.* **78**, 338 (1997).
- [19] K. Yamada, C. H. Lee, K. Kurahashi, J. Wada, S. Wakimoto, S. Ueki, H. Kimura, Y. Endoh, S. Hosoya, G. Shirane, R. J. Birgeneau, M. Greven, M. A. Kastner, and Y. J. Kim, *Phys. Rev. B* **57**, 6165 (1998).
- [20] C. Howald, H. Eisaki, N. Kaneko, M. Greven, and A. Kapitulnik, *Phys. Rev. B* **67**, 014533 (2003); A. Fang, C. Howald, N. Kaneko, M. Greven, and A. Kapitulnik, *Phys. Rev. B* **70**, 214514 (2004).
- [21] T. Hanaguri, C. Lupien, Y. Kohsaka, D.-H. Lee, M. Azuma, M. Takano, H. Takagi, and J. C. Davis, *Nature* **430**, 1001 (2004); Y. Kohsaka, C. Taylor, K. Fujita, A. Schmidt, C. Lupien, T. Hanaguri, M. Azuma,

- M. Takano, H. Eisaki, H. Takagi, S. Uchida, and J. C. Davis, *Science* **315**, 1380 (2007).
- [22] W. D. Wise, M. C. Boyer, Kamallesh Chatterjee, Takeshi Kondo, T. Takeuchi, H. Ikuta, Yayu Wang and E. W. Hudson, *Nature Physics* **4**, 696 (2008).
- [23] N. E. Bickers, D. J. Scalapino and S. R. White, *Phys. Rev. Lett.* **62**, 961 (1989).
- [24] D. Manske, I. Eremin, and K. H. Bennemann, *Phys. Rev. B* **67**, 134520 (2003).
- [25] A. B. Migdal, *Soviet Phys.—JETP* **7**, 996 (1958).
- [26] G. M. Eliashberg, *Soviet Phys.—JETP* **11**, 966 (1960).
- [27] D. J. Scalapino, J. R. Schrieffer, and J. W. Wilkins, *Phys. Rev.* **148**, 263 (1966).
- [28] O. K. Andersen, A. I. Liechtenstein, O. Jepsen and F. Paulsen, *J. Phys. Chem. Solids*, **56**, 1573 (1995).
- [29] E. Pavarini, I. Dasgupta, T. Saha-Dasgupta, O. Jepsen, and O. K. Andersen, *Phys. Rev. Lett.* **87**, 047003 (2001).
- [30] R. S. Markiewicz, S. Sahrakorpi, M. Lindroos, Hsin Lin, and A. Bansil, *Phys. Rev. B* **72**, 054519 (2005).
- [31] Neil W. Ashcroft and N. David Mermin, *Solid State Physics* (Saunders College, Philadelphia, 1976).
- [32] F. C. Zhang and T. M. Rice, *Phys. Rev. B* **37**, 3759 (1987).
- [33] J. Ashkenazi, *J. Supercond.* **7**, 719 (1994).
- [34] J. Ashkenazi, *J. Phys. Chem. Solids*, **63**, 2333 (2002).
- [35] J. Ashkenazi, *J. Phys. Chem. Solids*, **65**, 1461 (2004); in *New Challenges in Superconductivity: Experimental Advances and Emerging Theories*, edited by J. Ashkenazi, M. V. Eremin, J. L. Cohn, I. Eremin, D. Manske, D. Pavuna, and F. Zuo (Springer, 2005), p. 187.
- [36] V. I. Anisimov, M. A. Korotin, I. A. Nekrasov, Z. V. Pchelkina, and S. Sorella, *Phys. Rev. B* **66**, 100502 (2002).
- [37] Xiangang Wan, Thomas A. Maier, and Sergej Y. Savrasov, *Phys. Rev. B* **79**, 155114 (2009).
- [38] Herbert Goldstein, *Classical Mechanics*, Third Edition (Addison-Wesley, New York, 1980).
- [39] Carolyne M. Van Vliet, *Equilibrium and Non-equilibrium Statistical Mechanics*, (World Scientific, 2008).
- [40] Gerald D. Mahan, *Many-Particle Physics*, Third Edition (Kluwer Academics / Plenum Publishers, New York, 2000).
- [41] For simplicity, one QE pairing temperature T_p^q is mentioned, though as is discussed in the text, pairing of “antinodal” QEs occurs in the PG phase, and it is extended to “nodal” QEs (except for those on the lines of nodes) in the SC state.
- [42] T. Honma, and P. H. Hor, *Phys. Rev. B* **77**, 184520 (2008).
- [43] J. Zaanen, and O. Gunnarsson, *Phys. Rev. B* **40**, 7391 (1989).
- [44] K. Machida, *Physica C* **158**, 192 (1989).
- [45] V. J. Emery, and S. A. Kivelson, *Physica C* **209**, 597 (1993).
- [46] The formation of an AF or a striped structure requires the Bose condensation of *both* the svivon and the lagron fields; the first one is necessary in order to obtain large values for the spin occupation and correlation parameters $n^s(\mathbf{k})$ and $m^s(\mathbf{k})$ (see Eq. (22)), at the relevant \mathbf{k} vectors; the latter is needed in order to have, at the corresponding \mathbf{q} vectors, sufficiently large lagron coordinates and momenta $\lambda(\mathbf{q})$ and $p^\lambda(\mathbf{q})$ (see Eq. (11)) to maintain the auxiliary-particles’ constraint.
- [47] Jeffrey Goldstone, Abdus Salam, and Steven Weinberg, *Phys. Rev.* **127**, 965 (1962).
- [48] K. Nakayama, T. Sato, T. Dobashi, K. Terashima, S. Souma, H. Matsui, T. Takahashi, J. C. Campuzano, K. Kudo, T. Sasaki, N. Kobayashi, T. Kondo, T. Takeuchi, K. Kadowaki, M. Kofu, and K. Hirota, *Phys. Rev. B* **74**, 054505 (2006).
- [49] A. D. Palczewski, T. Kondo, R. Khasanov, N. N. Kolesnikov, A. V. Timonina, E. Rotenberg, T. Ohta, A. Bendounan, Y. Sassa, A. Fedorov, S. Pailhis, A. F. Santander-Syro, J. Chang, M. Shi, J. Mesot, H. M. Fretwell, and A. Kaminski, *Phys. Rev. B* **78**, 054523 (2008).
- [50] J. Chang, Y. Sassa, S. Guerrero, M. Mansson, M. Shi, S. Pailhes, A. Bendounan, R. Mottl, T. Claesson, O. Tjernberg, L. Patthey, M. Ido, N. Momono, M. Oda, C. Mudry, J. Mesot, *New J. Phys.* **10**, 103016 (2008).
- [51] Nicolas Doiron-Leyraud, Cyril Proust, David LeBoeuf, Julien Levallois, Jean-Baptiste Bonnemaïson, Ruixing Liang, D. A. Bonn, W. N. Hardy, Louis Taillefer, *Nature* **447**, 565 (2007).
- [52] E. A. Yelland, J. Singleton, C. H. Mielke, N. Harrison, F. F. Balakirev, B. Dabrowski, and J. R. Cooper, *Phys. Rev. Lett.* **100**, 047003 (2008).
- [53] B. Vignolle, A. Carrington, R. A. Cooper, M. M. J. French, A. P. Mackenzie, C. Jaudet, D. Vignolles, Cyril Proust, N. E. Hussey, *Nature* **455**, 952 (2008).
- [54] B. P. Xie, K. Yang, D. W. Shen, J. F. Zhao, H. W. Ou, J. Wei, S. Y. Gu, M. Arita, S. Qiao, H. Namatame, M. Taniguchi, N. Kaneko, H. Eisaki, K. D. Tsuei, C. M. Cheng, I. Vobornik, J. Fujii, G. Rossi, Z. Q. Yang, and D. L. Feng, *Phys. Rev. Lett.* **98**, 147001 (2007).
- [55] W. Meevasana, F. Baumberger, K. Tanaka, F. Schmitt, W. R. Dunkel, D. H. Lu, S.-K. Mo, H. Eisaki, and Z.-X. Shen, *Phys. Rev. B* **77**, 104506 (2008).
- [56] A typical correspondence between $\omega^\lambda(\mathbf{Q})$ and the resonance-mode energy E_{res} is given by [16]: $\omega^\lambda(\mathbf{Q}) \simeq \frac{3}{4}E_{\text{res}}$.
- [57] J. Chang, M. Shi, S. Pailhis, M. Mensson, T. Claesson, O. Tjernberg, A. Bendounan, Y. Sassa, L. Patthey, N. Momono, M. Oda, M. Ido, S. Guerrero, C. Mudry, and J. Mesot, *Phys. Rev. B* **78**, 205103 (2008).
- [58] There is a smooth transition between the low- and high- $|\omega|/k_B T$ regimes, and *no separate* contributions of A_{0b}^d and A_{0c}^d could be detected in $A^d(\mathbf{k}, \omega)$ through this range.
- [59] T. Valla, A. V. Fedorov, P. D. Johnson, B. O. Wells, S. L. Hulbert, Q. Li, G. D. Gu, and N. Koshizuka, *Science* **285**, 2110 (1999).
- [60] D. van der Marel, H. J. A. Molegraaf, J. Zaanen, Z. Nussinov, F. Carbone, A. Damascelli, H. Eisaki, M. Greven, P. H. Kes, M. Li, *Nature* **425**, 271 (2003).
- [61] S. Bar-Ad, B. Fisher, J. Ashkenazi, and J. Genossar, *Physica C* **156**, 741 (1988).
- [62] J. Hwang, T. Timusk, A. V. Puchkov, N. L. Wang, G. D. Gu, C. C. Homes, J. J. Tu, and H. Eisaki, *Phys. Rev. B* **69**, 094520 (2004).
- [63] A. Kanigel, U. Chatterjee, M. Randeria, M. R. Norman, G. Koren, K. Kadowaki, and J. C. Campuzano, *Phys. Rev. Lett.* **101**, 137002 (2008).
- [64] H.-B. Yang, J. D. Rameau, P. D. Johnson, T. Valla, A. Tsvelik and G. D. Gu, *Nature* **456**, 77 (2008).
- [65] Jianqiao Meng, Guodong Liu, Wentao Zhang, Lin Zhao, Haiyun Liu, Xiaowen Jia, Daixiang Mu, Shanyu Liu, Xiaoli Dong, Jun Zhang, Wei Lu, Guiling Wang, Yong

- Zhou, Yong Zhu, Xiaoyang Wang, Zuyan Xu, Chuangtian Chen, and X. J. Zhou, *Nature* **462**, 335 (2009).
- [66] A. Kanigel, M. R. Norman, M. Randeria, U. Chatterjee, S. Souma, A. Kaminski, H. M. Fretwell, S. Rosenkranz, M. Shi, T. Sato, T. Takahashi, Z. Z. Li, H. Raffy, K. Kadowaki, D. Hinks, L. Ozyuzer, J. C. Campuzano, *Nature Physics* **2**, 447 (2006).
- [67] U. Chatterjee, M. Shi, D. Ai, J. Zhao, A. Kanigel, S. Rosenkranz, H. Raffy, Z. Z. Li, K. Kadowaki, D. G. Hinks, Z. J. Xu, J. S. Wen, G. Gu, C. T. Lin, H. Claus, M. R. Norman, M. Randeria, and J. C. Campuzano, arXiv:0910.1648.
- [68] V. Z. Kresin, and S. A. Wolf, *Rev. Mod. Phys.* **81**, 481 (2009).
- [69] Ph. Bourges, B. Keimer, S. Pailhès, L. P. Regnault, Y. Sidis, and C. Ulrich, arXiv:cond-mat/0211227; Y. Sidis, S. Pailhès, B. Keimer, P. Bourges, C. Ulrich, and L. P. Regnault, *Phys. Stat. Sol. (b)* **241**, 1204 (2004)
- [70] E. van Heumen, E. Muhlethaler, A. B. Kuzmenko, H. Eisaki, W. Meevasana, M. Greven, and D. van der Marel, *Phys. Rev. B* **79**, 184512 (2009).
- [71] M. Le Tacon, A. Sacuto, A. Georges, G. Kotliar, Y. Gallais, D. Colson, and A. Forget, *Nature Physics* **2**, 537 (2006); W. Guyard, A. Sacuto, M. Cazayous, Y. Gallais, M. Le Tacon, D. Colson, and A. Forget, *Phys. Rev. Lett.* **101**, 097003 (2008).
- [72] S. Hufner, M. A. Hossain, A. Damascelli, and G. A. Sawatzky, *Rep. Prog. Phys.* **71**, 062501 (2008).
- [73] W. S. Lee, I. M. Vishik, K. Tanaka, D. H. Lu, T. Sasagawa, N. Nagaosa, T. P. Devereaux, Z. Hussain, Z.-X. Shen, *Nature* **450**, 81 (2007).
- [74] Takeshi Kondo, Rustem Khasanov, Tsunehiro Takeuchi, Jvrg Schmalian, Adam Kaminski, *Nature* **457**, 296 (20079).
- [75] K. Nakayama, T. Sato, Y. Sekiba, K. Terashima, P. Richard, T. Takahashi, K. Kudo, N. Okumura, T. Sasaki, and N. Kobayashi, *Phys. Rev. Lett.* **102**, 227006 (2009).
- [76] S. Blanc, Y. Gallais, A. Sacuto, M. Cazayous, M. A. Miasson, G. D. Gu, J. S. Wen, and Z. J. Xu, *Phys. Rev. B* **80**, 140502 (2009).
- [77] N. Jenkins, Y. Fasano, C. Berthod, I. Maggio-Aprile, A. Piriou, E. Giannini, B. W. Hoogenboom, C. Hess, T. Cren, O. Fischer, *Phys. Rev. Lett.* **103**, 227001 (2009).
- [78] T. Sato, H. Matsui, T. Takahashi, H. Ding, H.-B. Yang, S.-C. Wang, T. Fujii, T. Watanabe, A. Matsuda, T. Terashima, and K. Kadowaki, *Phys. Rev. Lett.* **91**, 157003 (2003).
- [79] R. Khasanov, A. Shengelaya, D. Di Castro, E. Morenzoni, A. Maisuradze, I. M. Savić, K. Conder, E. Pomjakushina, A. Bussmann-Holder, and H. Keller, *Phys. Rev. Lett.* **101**, 077001 (2008); Hugo Keller and Annette Bussmann-Holder, *Advances in Condensed Matter Physics* (Hindawi Publishing Corporation, 2010), doi: 10.1155/2010/393526.
- [80] K. McElroy, D.-H. Lee, J. E. Hoffman, K. M. Lang, J. Lee, E. W. Hudson, H. Eisaki, S. Uchida, and J. C. Davis, *Phys. Rev. Lett.* **94**, 197005 (2005).
- [81] E. Schachinger and J. P. Carbotte, *Phys. Rev. B* **80**, 094521 (2009).