

First-principles simulations on the structural and energetic properties of domains in $\text{PbTiO}_3/\text{SrTiO}_3$ superlattices

Pablo Aguado-Puente¹ and Javier Junquera¹

¹ *Departamento de Ciencias de la Tierra y Física de la Materia Condensada,
Universidad de Cantabria, Cantabria Campus Internacional,
Avenida de los Castros s/n, 39005 Santander, Spain*

(Dated: November 20, 2018)

We report first-principles calculations, within the density functional theory, on the structural and energetic properties of 180° stripe domains in $(\text{PbTiO}_3)_n/(\text{SrTiO}_3)_n$ superlattices. For the explored periodicities ($n=3$ and 6) we find that the polydomain structures compete in energy with the monodomain phases. Our results suggest the progressive transition, as a function of n , from a strong to a weak electrostatic coupling regime between the SrTiO_3 and PbTiO_3 layers. Structurally, they display continuous rotation of polarization connecting 180° domains. A large offset between $[100]$ atomic rows across the domain wall and huge strain gradients are observed. The domain wall energy is very isotropic, depending very weakly on the stripe orientation.

PACS numbers: 77.55.Px, 77.80-e, 77.80.Dj, 77.84.Cg, 31.15.A-

I. INTRODUCTION

The growth of superlattices composed of thin layers of ABO_3 perovskites with different physical properties has become one of the most promising paths to exploit the coupling between instabilities in order to engineer new functionalities in these heterostructures.¹⁻³ For a long time the focus was on the electrostatic coupling between the layers of the superlattice,^{4,5} and the interplay with the epitaxial strain.⁶ More recently, after the discovery of the appearance of a polarization from the coupling of two rotational modes in ultra-short period $\text{PbTiO}_3/\text{SrTiO}_3$ superlattices,⁷ the interest has evolved to include also the interaction between ferroelectric (FE) and antiferrodistortive (AFD) modes in perovskite related layered compounds.⁸⁻¹⁰

At the same time, polarization domains in ferroelectric thin films are being subject of numerous investigations due to the recent finding of their intrinsic functional properties. One of the most remarkable is the conductivity at domain walls within an otherwise insulating material.^{11,12} The great activity in the research of polydomain phases in ferroelectric thin films has also demonstrated that the domain structure in these systems, with rotation of the polarization^{13,14} or the formation of flux-closure structures in thin films,¹⁵⁻²⁰ and vortex structures in nano-sized ferroelectrics,^{21,22} probably differs significantly from the typically assumed picture of alternating regions where the polarization points along opposite directions with sharp domain walls (DW).

In the particular case of $\text{PbTiO}_3/\text{SrTiO}_3$ interfaces, pioneer works were devoted to the identification of 180° stripe domains in PbTiO_3 *thin films* grown on thick SrTiO_3 (001) substrates. The domain structures were characterized both in reciprocal space (strong satellites around PbTiO_3 Bragg peaks in synchrotron x-ray scattering measurements),²³⁻²⁵ and in real space (images recorded by atomic force microscopy).²⁶ Only lately,

the attention has turned to the study of the domain structures in $\text{PbTiO}_3/\text{SrTiO}_3$ *superlattices*. Zubko and coworkers²⁷ have recently focused on the dependence of their structural and dielectric properties as a function of the volume fraction of PbTiO_3 , the electrodes, and the applied electric fields. While the results of the superlattices asymmetrically sandwiched between Nb-doped SrTiO_3 (bottom) and gold (top) electrodes were consistent with a monodomain configuration,²⁸ those corresponding to the use of symmetrically coated SrRuO_3 electrodes (both top and bottom) suggested a polydomain phase with DW motion, which dynamics might be quite different than the conventional one.²⁹ Furthermore, through a combination of x-ray diffraction, transmission electron microscopy, and ultra-high resolution electron energy loss spectroscopy (EELS), Zubko *et al.*^{30,31} have also recently showed the progressive transition between two different regimes, controlled by the thickness of the individual SrTiO_3 and PbTiO_3 layers. In the first regime, present for sufficiently thin paraelectric layers, SrTiO_3 and PbTiO_3 are strongly electrostatically *coupled*: a uniform monodomain polarization is adopted throughout the thickness of the superlattice to minimize the depolarizing field. In the second regime, when the paraelectric layer thickness is increased, SrTiO_3 and PbTiO_3 are *decoupled*: the polarization is confined within the FE PbTiO_3 layers forming domains. EELS measurements revealed the presence of broad interfacial layers with reduced tetragonality and polarization extending over 5-6 unit cells (u.c.) into the PbTiO_3 layers. Strikingly, in the electrostatic decoupled regime, the domain structure was found to be coherent over several tens of superlattice repetitions. These works pointed out the suitability of this system for the study of domains in ultra-thin ferroelectric films, given the behavior of the ferroelectric layers as quasi-independent films, while the thickness of the whole system prevents the charge leakage when electric fields are applied.²⁷ They also constitute a good example of how to tune the functional properties with respect to dif-

ferent factors, such as the electrical boundary conditions or the periodicity of the superlattice.

On the other hand, the theoretical studies of $\text{PbTiO}_3/\text{SrTiO}_3$ superlattices have focused, so far, on three different aspects of the monodomain configurations: (i) the analysis of the structural, electronic and ferroelectric properties of both the pristine^{28,32,33} and disordered^{32,33} (including the presence of cation intermixing or defects) interfaces, (ii) the study of the coupling between the AFD instabilities and the FE polarization, compatible with an improper ferroelectric behaviour,⁷ or (iii) the influence of strain on the previous coupling.⁸

In this work we perform first-principles calculations on polydomain phases of $(\text{PbTiO}_3)_n/(\text{SrTiO}_3)_n [(n | n)]$ superlattices, with periodicities of $n = 3$ and 6. Our goal is to gain further insight on the polarization and oxygen octahedra rotation profiles. Besides, we compare the differences in energies between relevant phases. The influence of the periodicity, orientation, energy of the DWs, and the mixed FE-AFD-strain coupling present in these superlattices⁸ are carefully considered. We also analyze the strain fields induced by the domain structure and their role in the inter-layer coupling.

The rest of the paper is organized as follows: the method on which the simulations are based is described in Sec. II. In Sec. III A we compare the energy of the different competing phases (monodomain versus polydomain) to ascertain their relative stability. The atomic structure of the domains is analyzed in Sec. III B. Finally, the polarization profiles and strain fields are discussed in Sec. III C.

II. METHODS

The simulations have been carried out within the local density approximation (LDA) to the density functional theory (DFT) using the SIESTA code.³⁴ The rest of the technical parameters remain the same as in Ref. 8.

In this work we have performed simulations of $(n | n)$ superlattices, by means of a supercell approach. Two values of n have been considered, $n = 3$ and 6, aiming to sample superlattices within the two distinct regimes experimentally observed: strong (for $n \lesssim 4$) and weak (for $n \gtrsim 4$) electrostatic coupling between the SrTiO_3 and PbTiO_3 layers.

As the starting point, an ideal structure was defined stacking along the $[001]$ direction n unit cells of SrTiO_3 and n unit cells of PbTiO_3 . The in-plane lattice constant was fixed to the theoretical LDA value of SrTiO_3 (3.874 Å). First, mirror symmetry planes were imposed at the central atomic layers of PbTiO_3 and SrTiO_3 , and an initial atomic relaxation was performed in order to find a reference paraelectric ground-state. Then, the reference structure was replicated N_x times along the $[100]$ direction and N_y times along the $[010]$ direction. Due to the periodic boundary conditions used in the simulations, N_x determines the domain periodicity, while N_y allows

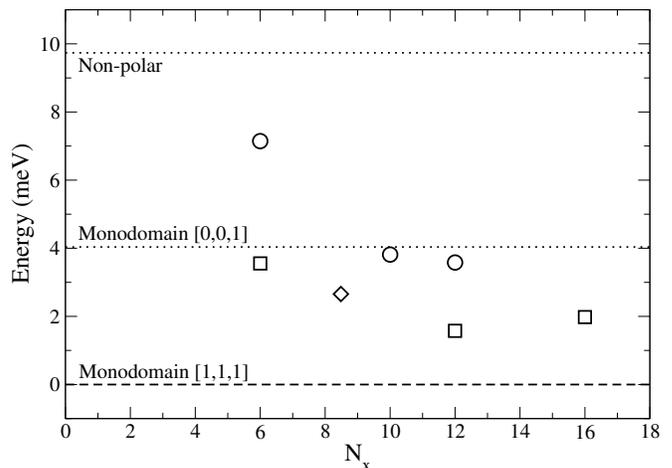


FIG. 1: Differences in energies between polydomain, monodomain and non-polar configurations in $(3|3)$ $\text{PbTiO}_3/\text{SrTiO}_3$ superlattices, as a function of the domain period N_x . Total energies of supercells are given per 5-atom perovskite unit cell. Circles represent the configurations where the AFD modes are not allowed ($N_y = 1$), while squares represent configuration with condensed AFD modes ($N_y = 2$). Diamond indicates a configuration where the DW lies along the $\langle 110 \rangle$ direction, also allowing for the condensation of AFD modes. The monodomain phases have been labeled as in Ref. 8. In the non-polar configuration, the AFD distortions have been considered. All energies are given with respect to the most stable monodomain configuration.

to switch on ($N_y = 2$) and off ($N_y = 1$) the AFD instabilities. Following the recipe given in Ref. 16, a percentage of the bulk soft mode distortion was superimposed on the PbTiO_3 layers, so the polarization points upwards in half of the superlattice and downwards in the other half. For $N_y = 2$ superlattices, small rotations were induced by hand following a $a^0a^0c^-$ pattern in Glazer notation. Finally, an extra atomic relaxation of the full heterostructure was carried out, until the maximum value of the Hellman-Feynman forces and the zz stress tensor component fell below $0.01 \text{ eV}/\text{Å}$ and $0.0001 \text{ eV}/\text{Å}^3$ respectively [except for the $(3 | 3)$ superlattice with $N_x = 16$ and $N_y = 2$ (960 atoms in the simulation box) and for the $(6 | 6)$ superlattice with $N_x = 12$ and $N_y = 1$ (720 atoms), which were relaxed down to a maximum force of $0.05 \text{ eV}/\text{Å}$].

To establish the notation, we will call the plane parallel to the interface the (x, y) plane, whereas the perpendicular direction will be referred to as the z -axis.

III. RESULTS

A. Energetics.

For the $(3 | 3)$ superlattices we have performed simulations of the different competing phases in order to de-

termine their relative stability. The energies of the polydomain, monodomain and non-polar configurations as a function of the domain periodicity are shown in Fig. 1. For these superlattices, the balance between the electrostatic energy (which tends to reduce the domain period), and the DW energy density (which tends to increase it) results in an optimum periodicity of the domain structure, Λ , of about 12 unit cells (46.5 Å) (the energy for N_x equal 12 and 16 might be considered as equivalent within the accuracy of our simulations).

The most stable phase found in our simulations, however, corresponds to a monodomain structure, with the polarization in the PbTiO_3 layer pointing close to the perovskite unit cell diagonal (configuration labeled as [111] in Ref. 8 and Fig. 1). This result is consistent with the upturn in the domain periodicity observed by Zubko and coworkers,³¹ suggesting that for $n < 4$ the superlattices enter into the strong coupling regime. Nevertheless, the energy difference between the monodomain and the most stable polydomain configuration is very small (of the order of 1.6 meV/5-atom-perovskite-unit-cell, well below the thermal energy at room temperature), suggesting a close competition between them for small values of n . A small change on any external condition (growth temperature, or how fast the system is cooled, etc.) might help the system to overcome potential energy barriers, activate transitions between them and could, eventually, stabilize a metastable domain structure. This fact might explain why both, polydomain and monodomain samples, have been observed experimentally.²⁷

For a given domain periodicity, the energy is systematically lowered if the rotation of the oxygen octahedra are allowed, with reductions ranging between 3.6 meV per 5-atom perovskite unit cell (for $N_x = 6$) to 2.0 meV (for $N_x = 12$). This highlights the importance of the FE-AFD coupling in these heterostructures. The coupling is also noticeable when the pattern of the oxygen octahedra in the polydomain phases are compared with those of monodomain configuration. We see in Fig. 2 that at the center of the domains (i. e. mid-distance between two DW, see column of atoms embodied by a bracket in Fig. 4) where the polarization is purely out-of-plane, P_z , the rotations along an in-plane axis (tiltings) essentially vanish, resembling the case of the [001] monodomain phase reported in Ref. 8. Regarding the rotations around the z -axis, the larger P_z in the PbTiO_3 layer in polydomain phases penalizes the AFD modes and the rotation angles are smaller. The FE-AFD coupling also affects the magnitude of the polarization, resulting in a slight reduction of P_z when condensation of AFD modes is allowed (see Table I).

We also find that the effect of the DW orientation is small: a change in the orientation of the DW from $\langle 100 \rangle$ to $\langle 110 \rangle$ does not affect significantly the energy of the superlattice. This points to a rather isotropic DW structure, with the energy of the domains depending very weakly on the stripe orientation, in good agreement

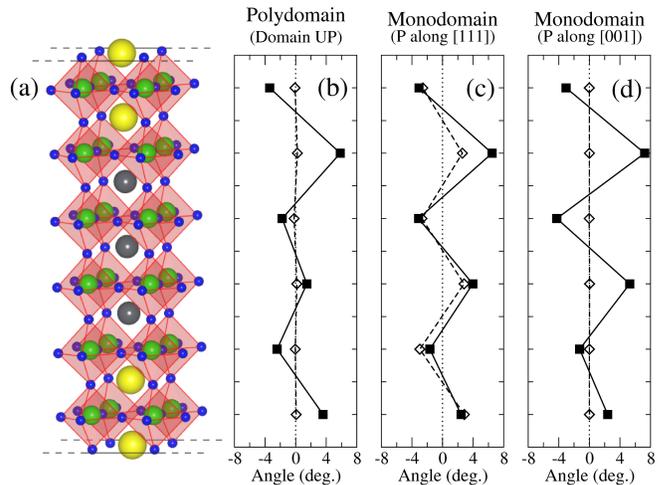


FIG. 2: (Color online) (a) Schematic representation of the center of a domain in a (3|3) $\text{PbTiO}_3/\text{SrTiO}_3$ superlattice (see region embodied by a bracket in Fig. 4). Atoms are represented by balls: Sr in yellow, Ti in green, O in blue, and Pb in grey. In panels (b)-(d) we represent the amplitude of the rotations (squares) and tiltings (diamonds) of each TiO_6 octahedra: (b) at the center of a domain in the polydomain configuration with $N_x = 12$, (c) in the ground state monodomain phase (with polarization in the PbTiO_3 layer pointing close to the perovskite unit cell diagonal, see Ref. 8), and (d) in a monodomain phase with polarization lying along [001].

TABLE I: Out-of-plane polarization, P_z , at the center of the domains in $\text{PbTiO}_3/\text{SrTiO}_3$ superlattices with $N_x = 12$ u.c. P_z^{PTO} (P_z^{STO}) stands for the polarization at the central perovskite unit cell within the PbTiO_3 (SrTiO_3) layer. Values in parenthesis correspond to the root mean square polarization, averaged along the [100] direction. Units in $\mu\text{C}/\text{cm}^2$.

$(n n)$	N_x	N_y	P_z^{PTO}	P_z^{STO}
(3 3)	12	1	65 (56)	31 (26)
(3 3)	12	2	60 (53)	29 (24)
(6 6)	12	1	75 (70)	21 (17)

with experimental results,²⁷ phenomenological Landau-Ginzburg-Devonshire theory,³⁵ and model Hamiltonian¹⁵ simulations.

For the (6 | 6) superlattices only one domain periodicity was simulated due to the scaling of the system size. For the same reason, in this case rotations of the oxygen octahedra were not allowed in the calculations of the polydomain phases. In view of the results for the (3 | 3) superlattice, the presence of the octahedra rotations results in a decrease of the energies of polydomains structures and a small reduction of the polarization at the center of the domains. We chose $N_x = 12$ u.c. ($\Lambda = 46.5$ Å), close to the experimental value of $\Lambda = 55$ Å.³⁰ These polydomain phase were found to lie 3.8 meV/5-atom-

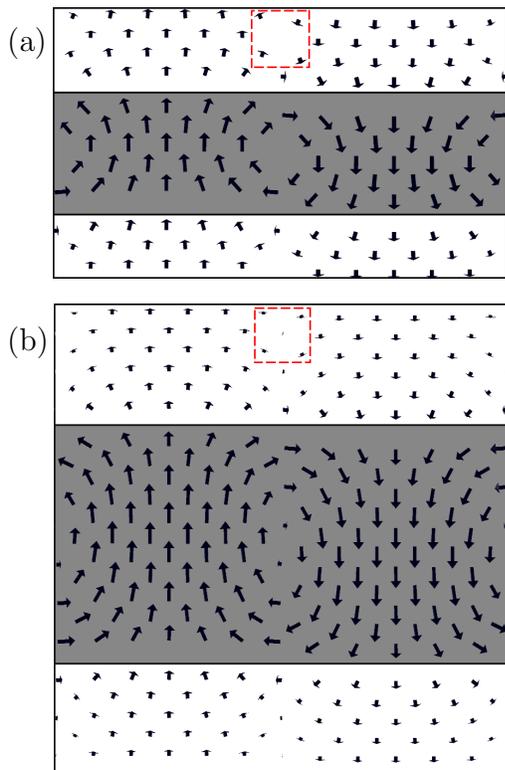


FIG. 3: (Color online) Local polarization profile of polydomain structures in $(\text{PbTiO}_3)_n/(\text{SrTiO}_3)_n$ superlattices with (a) $n = 3$ and (b) $n = 6$. The PbTiO_3 and SrTiO_3 are depicted as gray and white regions respectively. Red dashed squares in the SrTiO_3 layers mark the position where antivortices are formed.

perovskite-unit-cell *below* the most stable monodomain phase without AFD distortions.

The change in the most stable phase [from monodomain in the $(3 | 3)$ to polydomain in the $(6 | 6)$] indicates a crossover between the weak and strong electrostatic coupling regimes described in the Introduction. Experimentally this transition was inferred to occur gradually, with a minimum of the domains size observed at $n \simeq 4$ (Ref. 31). In related $\text{KTaO}_3/\text{KNbO}_3$ superlattices, the critical periodicity for the crossover ranges between $7 \leq n \leq 15$ (experiments from Ref. 36), and $12 \leq n \leq 24$ (shell models simulations from Ref. 37).

B. Atomic structure of the domains.

Figure 3 shows the local polarization profile of the most stable polydomain configurations found for the $(3 | 3)$ and $(6 | 6)$ superlattices (both with a domain periodicity of $N_x = 12$ u.c.). Similar patterns are obtained for other domain sizes. In order to be able to make quantitative comparisons, from now on only simulations where oxygen octahedra were *not* allowed are discussed. The local polarization is obtained calculating the polarization of a

unit cell centered on every cation of the system (except at the interfaces where no “bulk-like” unit cell can be chosen) and using the displacement of the atoms with respect to the ideal phase and the bulk Born effective charges of the corresponding material, either PbTiO_3 or SrTiO_3 , depending on the layer the cation belongs to.

Near the DWs the local polarization pattern clearly displays a continuous polarization rotation within 3 u.c. around the DW, connecting two 180° domains.

As suggested by the experimental results exposed in Ref. 31, the examination of Fig. 3 reveals that the actual domain structure in this kind of systems is often an intermediate case between 180° domains and the closure domains commonly found in ferromagnets, displaying rotation of the polarization upon approaching the DWs^{14,38} (although the length scale over which the polarization rotation takes place is only a few unit cells in the case of ferroelectrics, in contrast with the several nanometers or even microns typical of ferromagnets). However, we have to keep in mind that in ideal closure domains, the divergence of the polarization vanishes everywhere and, therefore, the depolarizing field is perfectly screened. In our simulations, the polarization of the SrTiO_3 indicates the presence of a residual depolarizing field and thus, strictly speaking, our domains do not constitute perfect domains of closure.

Our results also support the robustness of the rotation of polarization and the formation of vortices in ferroelectric nanostructures suggested by previous theoretical studies. These geometries have been predicted to exist independently of (i) the used methodology (including first-principles,^{16,39} model hamiltonians,^{40–42} phase field models,⁴³ and phenomenological Devonshire-Ginzburg-Landau theories^{35,44}), and/or (ii) the electrostatic boundary conditions (with metallic^{16,45} or semiconducting electrodes,^{41,44} or even in free standing slabs.^{39,42})

It is remarkable to see that the polarization rotation in the $\text{PbTiO}_3/\text{SrTiO}_3$ superlattices is mostly due to large in-plane displacement of the Pb atoms at the PbO layers in the vicinity of the interface. This contrasts with the predicted domains in $\text{BaTiO}_3/\text{SrRuO}_3$ capacitors,¹⁶ where the in-plane polarization is due to the displacements of the Sr atoms in the first layer of the electrode. Here, the Pb atoms move of the order of 0.2 Å, a displacement large enough to be detectable with the recently developed atomic-resolution aberration-corrected transmission electron microscopy. Using this technique, polarization rotation at DWs have been experimentally observed in ferroelectric thin films with thicknesses of a few tens of unit cells.^{19,20} However the high quality level achieved during the last years in the growth of short-period superlattices, together with the large in-plane displacements predicted, make this kind of system particularly suited for the observation of the formation of vortices at domain walls in ultrathin films, comparable in size to the simulated systems listed above.

Interestingly, within the SrTiO_3 layer and close to the

DW we do observe the formation of antivortices; a local polarization pattern where two dipoles point face to face and two tail to tail (see red dashed squares in Fig. 3. These antivortices have also been recently predicted to form in epitaxial BiFeO₃ films.⁴⁶)

C. Polarization profiles and strain field

Within a polydomain configuration, there is no need anymore to keep constant the normal component of the polarization at the interface, P_z , since the electric fields that arise from its discontinuity are efficiently screened by the presence of domains. As a consequence P_z , that in the monodomain configuration is continuous throughout the superlattice, in the polydomain case is very inhomogeneous with polarization mismatches at the center of the domains of $34 \mu\text{C}/\text{cm}^2$ and $54 \mu\text{C}/\text{cm}^2$ for the (3 | 3) and (6 | 6) superlattice respectively (see Table I).

The layer-by-layer polarization of Fig. 5(a) and 5(c) shows that, within SrTiO₃, it converges to a rather homogeneous well defined value, that at the center of the domain decreases from $31 \mu\text{C}/\text{cm}^2$ (for $n = 3$) to $21 \mu\text{C}/\text{cm}^2$ (for $n = 6$). On the contrary, the PbTiO₃ layer displays a smooth variation of the polarization, with a progressive reduction spanning over a length of three unit cells into the PbTiO₃ layers from the interface. The great reduction of the polarization of the SrTiO₃ layer upon a increase in n , together with the out-of-plane polarization at the center of the PbTiO₃ layer rapidly approaching the bulk value ($83 \mu\text{C}/\text{cm}^2$), again supports the gradual electrostatic decoupling of the ferroelectric layer.³¹

In Fig. 5 we also plot the variation of the local tetragonality across the superlattice, calculated for the same perovskite unit cell surrounding each cation. The layer-by-layer tetragonality *averaged* along the [100] direction, plotted as black squares in Fig. 5(b) and (d), displays a variation that is well correlated with that of the polarization: an almost constant value inside the SrTiO₃ layer and a smooth increase from the interfaces towards the center of the PbTiO₃. The polarization of the SrTiO₃ layer induces a slight tetragonality of this material. This reduction of symmetry with respect to the cubic unit cell of bulk SrTiO₃ is consistent with the decrease of the t_{2g} - e_g splitting observed in the EELS spectra of this system by Zubko and coworkers.³¹

Besides, in Fig. 5(b) and (d) we show the layer-by-layer tetragonality across the superlattice at the center of a domain with the polarization pointing *up*. Strikingly, and contrary to the polarization, the variation of the local tetragonality as we move across the superlattice is very asymmetric. The tetragonality reaches its maximum value in the PbTiO₃ layer at the bottom interface with respect to the polarization direction, and gradually reduces its magnitude as we move towards the top interface. In the SrTiO₃ layer, the strain gradient is smaller and, forced by the imposed periodic boundary conditions, it has opposite sign.

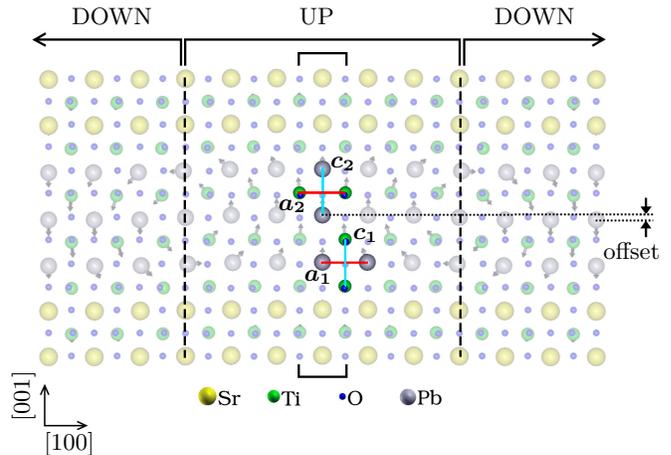


FIG. 4: (Color online) Schematic view of the (3 | 3) superlattice with $N_x = 12$ and $N_y = 1$ indicating how local values of the magnitudes plotted in Fig. 5 and 7 are defined. Red (blue) lines represent local values of in-plane, a , (out-of-plane, c) lattice constants, measured from the in-plane (out-of-plane) distance between equivalent cations of the same chemical specie in consecutive unit cells along the x (z) direction. Magnitudes with subscript 1 (2) indicate unit cells centered on a [001] AO (TiO₂) atomic plane. Local polarization is marked with arrows. Black dotted lines indicate the offset between [100] atomic rows to the left and right of the domain walls, defined as the relative vertical shift of A-cations in a given atomic plane. Bracket at the bottom of the up domain indicates the position of its center, where the values plotted as empty symbols in Fig. 5 and 7 are obtained. Finally, domain walls are represented by dashed lines.

The analysis of the polarization and tetragonality profiles reveals that the formation of domains in the superlattices is associated with complex distortions. The characteristics of the strain field in this system can be explained as a combination of different effects.

On the one hand, in PbTiO₃ the off-center displacements of both the Pb and Ti cations contribute to the polarization. Therefore the Pb atoms displace along z in opposite direction in the up and down domains. This gives rise to an *offset* between [100] atomic rows to the left and right of the DW [see Fig. 6(a)]. A sizable offset of 0.6 \AA was already predicted by Meyer and Vanderbilt in 180° stripe domains in bulk PbTiO₃.⁴⁷ As in Ref. 47, for the PbTiO₃/SrTiO₃ superlattices we quantify this offset for a given layer as the difference in the z -coordinate of a equivalent A-cation at the center of opposite domains (see Fig. 4). The layer by layer offset, shown in Fig. 7(a) and (c), amounts up to almost 0.5 (0.45) \AA at the middle of the PbTiO₃ layer in the (6 | 6) [(3 | 3)] superlattice. Although the offset of opposite domains is partially accommodated by the interfaces – which reflects in the increase (decrease) of the tetragonality at the bottom (top) interface in Fig. 5(b) and (d) –, it still propagates into the SrTiO₃, amounting a sizable $\sim 0.1 \text{ \AA}$.

On the other hand, in thin films the polarization in PbTiO₃ rotates at the DW. Indeed, as pointed out above, our simulations show that large in-plane displacements of

- 589 (2007)
- ⁷ E. Bousquet, M. Dawber, N. Stucki, C. Lichtensteiger, P. Hermet, S. Gariglio, J. M. Triscone, and Ph. Ghosez, *Nature* **452**, 732 (2008)
 - ⁸ P. Aguado-Puente, P. García-Fernández, and J. Junquera, *Phys. Rev. Lett.* **107**, 217601 (2011)
 - ⁹ N. A. Benedek and C. J. Fennie, *Phys. Rev. Lett.* **106**, 107204 (2011)
 - ¹⁰ J. M. Rondinelli and N. A. Spaldin, *Adv. Mater.* **23**, 3363 (2011)
 - ¹¹ J. Seidel, L. W. Martin, Q. He, Q. Zhan, Y. H. Chu, A. Rother, M. E. Hawkrigde, P. Maksymovych, P. Yu, M. Gajek, N. Balke, S. V. Kalinin, S. Gemming, F. Wang, G. Catalan, J. F. Scott, N. A. Spaldin, J. Orenstein, and R. Ramesh, *Nat. Mater.* **8**, 229 (2009)
 - ¹² J. Guyonnet, I. Gaponenko, S. Gariglio, and P. Paruch, *Adv. Mater.* **23**, 5377 (2011)
 - ¹³ G. Catalan, A. Janssens, G. Rispens, S. Csiszar, O. Seeck, G. Rijnders, D. H. A. Blank, and B. Noheda, *Phys. Rev. Lett.* **96**, 127602 (2006)
 - ¹⁴ D. Lee, R. K. Behera, P. Wu, H. Xu, Y. L. Li, S. B. Sinnott, S. R. Phillpot, L. Q. Chen, and V. Gopalan, *Phys. Rev. B* **80**, 060102 (2009)
 - ¹⁵ B.-K. Lai, I. Ponomareva, I. A. Kornev, L. Bellaiche, and G. J. Salamo, *Phys. Rev. B* **75**, 085412 (2007)
 - ¹⁶ P. Aguado-Puente and J. Junquera, *Phys. Rev. Lett.* **100**, 177601 (2008)
 - ¹⁷ S. Prosandeev, S. Lisenkov, and L. Bellaiche, *Phys. Rev. Lett.* **105**, 147603 (2010)
 - ¹⁸ Y. Ivry, D. P. Chu, J. F. Scott, and C. Durkan, *Phys. Rev. Lett.* **104**, 207602 (2010)
 - ¹⁹ C.-L. Jia, K. W. Urban, M. Alexe, D. Hesse, and I. Vrejoiu, *Science* **331**, 1420 (2011)
 - ²⁰ C. T. Nelson, B. Wincheser, Y. Zhang, S.-J. Kim, A. Melville, C. Adamo, C. M. Folkman, S. H. Baik, C. B. Eom, D. G. Schlom, L.-Q. Chen, and X. Pan, *Nano Lett.*, **11**, 828 (2011)
 - ²¹ I. I. Naumov, L. Bellaiche, and H. X. Fu, *Nature* **432**, 737 (2004)
 - ²² S. Prosandeev, I. Ponomareva, I. Naumov, I. Kornev, and L. Bellaiche, *J. Phys.: Condens. Matter* **20**, 193201 (2008)
 - ²³ S. K. Streiffer, J. A. Eastman, D. D. Fong, C. Thompson, A. Munkholm, M. V. Ramana Murty, O. Auciello, G. R. Bai, and G. B. Stephenson, *Phys. Rev. Lett.* **89**, 067601 (2002)
 - ²⁴ G. B. Stephenson, D. D. Fong, M. V. R. Murty, S. K. Streiffer, J. A. Eastman, O. Auciello, P. H. Fuoss, A. Munkholm, M. E. M. Aanerud, and C. Thompson, *Physica B* **336**, 81 (2003)
 - ²⁵ D. D. Fong, G. B. Stephenson, S. K. Streiffer, J. A. Eastman, O. Auciello, P. H. Fuoss, and C. Thomson, *Science* **304**, 1650 (2004)
 - ²⁶ C. Thompson, D. D. Fong, R. V. Wang, F. Jiang, S. K. Streiffer, K. Latifi, J. A. Eastman, P. H. Fuoss, and G. B. Stephenson, *Appl. Phys. Lett.* **93**, 182901 (2008)
 - ²⁷ P. Zubko, N. Stucki, C. Lichtensteiger, and J.-M. Triscone, *Phys. Rev. Lett.* **104**, 187601 (2010)
 - ²⁸ M. Dawber, C. Lichtensteiger, M. Cantoni, M. Veithen, Ph. Ghosez, K. Johnston, K. M. Rabe, and J. M. Triscone, *Phys. Rev. Lett.* **95**, 177601 (2005)
 - ²⁹ J. Y. Jo, P. Chen, R. J. Sichel, S. J. Callori, J. Sinsheimer, E. M. Dufresne, M. Dawber, and P. G. Evans, *Phys. Rev. Lett.* **107**, 055501 (2011)
 - ³⁰ A. Torres-Pardo, A. Gloter, P. Zubko, N. Jecklin, C. Lichtensteiger, C. Colliex, J.-M. Triscone, and O. Stéphan, *Phys. Rev. B* **84**, 220102 (2011)
 - ³¹ P. Zubko, N. Jecklin, A. Torres-Pardo, P. Aguado-Puente, A. Gloter, C. Lichtensteiger, J. Junquera, O. Stéphan, and J.-M. Triscone, submitted(2012)
 - ³² V. R. Cooper, K. Johnston, and K. M. Rabe, *Phys. Rev. B* **76**, 020103(R) (2007)
 - ³³ M. Gu, J. Wang, Q. Y. Xie, and X. S. Wu, *Physical Review B* **82**, 134102 (2010)
 - ³⁴ J. M. Soler, E. Artacho, J. D. Gale, A. García, J. Junquera, P. Ordejón, and D. Sánchez-Portal, *J. Phys.: Condens. Matter* **14**, 2745 (2002)
 - ³⁵ A. M. Bratkovsky and A. P. Levanyuk, *Phys. Rev. B* **84**, 045401 (2011)
 - ³⁶ E. D. Specht, H. M. Christen, D. P. Norton, and L. A. Boatner, *Phys. Rev. Lett.* **80**, 4317 (1998)
 - ³⁷ M. Sepliarsky, S. R. Phillpot, D. Wolf, M. G. Stachiotti, and R. L. Migoni, *Phys. Rev. B* **64**, 060101(R) (2001)
 - ³⁸ C. Kittel, *Phys. Rev.* **70**, 965 (1946)
 - ³⁹ T. Shimada, S. Tomoda, and T. Kitamura, *Phys. Rev. B* **81**, 144116 (2010)
 - ⁴⁰ B.-K. Lai, I. Ponomareva, I. I. Naumov, I. A. Kornev, H. Fu, L. Bellaiche, and G. J. Salamo, *Phys. Rev. Lett.* **96**, 137602 (2006)
 - ⁴¹ S. Prosandeev and L. Bellaiche, *Phys. Rev. B* **75**, 172109 (2007)
 - ⁴² D. Sichuga and L. Bellaiche, *Phys. Rev. Lett.* **106**, 196102 (2011)
 - ⁴³ J. Slutsker, A. Artemev, and A. Roytburd, *Phys. Rev Lett.* **100**, 087602 (2008)
 - ⁴⁴ G. B. Stephenson and K. R. Elder, *J. Appl. Phys* **100**, 051601 (2006)
 - ⁴⁵ C. Lichtensteiger, P. Zubko, M. Stengel, P. Aguado-Puente, J. M. Triscone, Ph. Ghosez, and J. Junquera, in *Oxide ultrathin films: science and technology*, edited by G. Pacchioni and S. Valeri (John Wiley & Sons, 2011)
 - ⁴⁶ S. Prosandeev, I. A. Kornev, and L. Bellaiche, *Phys. Rev. Lett.* **107**, 117602 (2011)
 - ⁴⁷ B. Meyer and D. Vanderbilt, *Phys. Rev. B* **65**, 104111 (2002)
 - ⁴⁸ P. Zubko, G. Catalan, P. R. L. Welche, A. Buckley, and J. F. Scott, *Phys. Rev. Lett.* **99**, 167601 (2007)
 - ⁴⁹ L. E. Cross, *J. Mater. Sci.* **41**, 53 (2006)
 - ⁵⁰ J. Hong, G. Catalan, J. F. Scott, and E. Artacho, *J. Phys.: Condens. Matter* **22**, 112201 (2010)
 - ⁵¹ G. Catalan, A. Lubk, A. H. G. Vlooswijk, E. Snoeck, C. Magen, A. Janssens, G. Rispens, G. Rijnders, D. H. A. Blank, and B. Noheda, *Nat. Mater.* **10**, 963 (2011)
 - ⁵² D. Lee, A. Yoon, S. Y. Jang, J.-G. Yoon, J.-S. Chung, M. Kim, J. F. Scott, and T. W. Noh, *Phys. Rev. Lett.* **107**, 057602 (2011)
 - ⁵³ J. Hong and D. Vanderbilt, *Phys. Rev. B* **84**, 180101(R) (2011)
 - ⁵⁴ E. V. Bursian and O. I. Zaikovskii, *Sov. Phys. - Solid. State* **10**, 1121 (1968)
 - ⁵⁵ E. V. Bursian, *Ferroelectrics* **307**, 177 (2004)