

# Emergent heavy fermion behavior at the Wigner-Mott transition

Jaime Merino,<sup>1</sup> Arnaud Ralko,<sup>2</sup> and Simone Fratini<sup>2</sup>

<sup>1</sup>*Departamento de Física Teórica de la Materia Condensada,  
Condensed Matter Physics Center (IFIMAC) and Instituto Nicolás Cabrera,  
Universidad Autónoma de Madrid, Madrid 28049, Spain*

<sup>2</sup>*Institut Néel-CNRS and Université Joseph Fourier,  
Boîte Postale 166, F-38042 Grenoble Cedex 9, France*

(Dated: September 30, 2018)

We study charge ordering driven by Coulomb interactions on triangular lattices relevant to the Wigner-Mott transition in two dimensions. Dynamical mean-field theory reveals a pinball liquid phase whose low energy properties are captured by the periodic Anderson model. Strong quasiparticle renormalization is predicted at the onset of Kondo antiferromagnetic coupling between localized electrons (pins) and itinerant carriers (balls). Non-Fermi liquid behavior can occur in such charge ordered systems due to spin-flip scattering of itinerant electrons off the pins in analogy with heavy fermion compounds.

PACS numbers: 71.10.Hf, 71.10.Fd, 74.40.Kb, 74.70.Kn

The interplay between charge ordering (CO) and the Mott metal-insulator transition (MIT) is an important open problem in correlated materials, whose manifestations are common in narrow-band systems such as the transition metal oxides [1] (cuprates, manganites, nickelates, cobaltates), low-dimensional organic conductors [2] as well as transition-metal dichalcogenides [3]. On one hand, charge ordering phenomena are favored by the presence of electronic correlations, as these slow down the electronic motion and reduce the tendency to charge delocalization. Conversely, the reconstruction of the electronic spectrum upon entering a phase with broken symmetry can enhance the effects of correlations, extending the realm of Mott physics away from the usual integer fillings [2, 4–11]. An illustration of this phenomenon is realized in the dichalcogenide compound 1T-TaS<sub>2</sub> [3, 12, 13], where nominally weak electronic correlations are so effectively enhanced upon formation of a charge density wave that they can trigger a Mott metal-insulator transition.

A fundamental relation between charge ordering and the Mott metal-insulator transition has also been pointed out recently in the different context of the two-dimensional electron gas (2DEG), leading to the concept of Wigner-Mott transition [6–9]. Close to the Wigner crystal phase induced by the long ranged Coulomb repulsion at low density, the electrons form an effectively narrow-band system at half-filling (one electron per site of the Wigner crystal [14]), whose physical properties therefore resemble those of a Mott insulator. Correspondingly, it has been shown that the melting of the Wigner crystal shares several common features with the Mott transition [6, 7, 15].

In the present Letter, we explore the interplay of charge order and correlations starting from the extended Hubbard model on the triangular lattice, which frustrates the insulating CO found in bipartite lattices. Based on DMFT calculations at  $T = 0$  we find that the

nearest-neighbor Coulomb repulsion stabilizes a charge ordered metallic phase over a broad range of concentrations. In this phase, termed *pinball liquid* and sketched in Fig. 1, quasi-localized electrons (pins) coexist with itinerant electrons (balls), whose dynamics become heavily renormalized for sufficiently large carrier concentration. The origin of this renormalization is elucidated via a mapping to a periodic Anderson model (PAM): tuning the hybridization between the two species reveals an antiferromagnetic coupling leading to Kondo screening of the localized moments. Although our calculations are limited to the zero temperature case, the strong analogies with heavy fermions indicate that non-Fermi liquid behavior can arise in correlated CO systems on frustrated lattices in a broad temperature range above the Kondo breakdown temperature scale.

*Model.* The reference model to study the interplay between charge ordering and electronic correlations is the Extended Hubbard Model (EHM):

$$H = -t \sum_{\langle ij \rangle \sigma} (c_{i\sigma}^\dagger c_{j\sigma} + h.c.) + U \sum_i n_{i\uparrow} n_{i\downarrow} + V \sum_{\langle ij \rangle} n_i n_j. \quad (1)$$

which describes electrons moving on a lattice with transfer integral  $t$  and interacting via both on-site ( $U$ ) and nearest-neighbor Coulomb interactions ( $V$ ). We set the energy scale  $t = 1$ . Studies of the EHM have mostly focused on bipartite lattices [2, 4, 5, 7–9] (the Bethe lattice, or the square lattice in two-dimensions), as these can naturally accommodate for charge ordering at a commensurate occupation of one charge per two lattice sites, corresponding to one quarter band filling. There are important cases however where the relevant lattice geometry is non-bipartite, adding frustration to the already rich phenomenology of correlated CO. A notable example is the two-dimensional Wigner crystal itself, where charges arrange on a triangular pattern in order to minimize their electrostatic energy. How the analogy be-

tween the Wigner crystal transition and the Mott MIT is modified when one considers the appropriate triangular geometry [14] remains an open question, that was not addressed in Refs. [6, 7]. A second example is the family of two-dimensional organic conductors  $\theta$ -ET<sub>2</sub> [16, 17], where the molecular lattice is triangular and the band filling is fixed by charge transfer to one hole per two molecular sites. In this framework, the EHM has been studied intensively to address the phenomenon of charge ordering, and fundamental differences between the square and triangular lattice have emerged. Most prominently, for isotropic  $V$ , on the triangular lattice, geometrical frustration prevents the two-fold CO characteristic of bipartite lattices, and a three-fold CO is realized instead (cf. Fig. 1b) [10, 11, 18, 19].

*DMFT solution.* We solve the model Eq. (1) using dynamical mean field theory (DMFT). In its simplest form, this method maps a single-band Hubbard model onto an Anderson quantum impurity model in an effective metallic bath that is determined self-consistently. Allowing for charge ordering [4] with  $N$ -fold symmetry breaking implies solving  $N$  interconnected (through hopping amplitudes) impurity models, one for each sublattice. Calling  $G_{\alpha,\sigma}^0(i\omega_n)$  the Green's function of the  $\alpha$ -th electronic bath and  $G_{\alpha,\sigma}^{And}(i\omega_n)$  that of the corresponding impurity problem, a local self-energy is extracted from the solution of the Anderson model for each sublattice  $\alpha$  via  $\Sigma_{\alpha,\sigma}(i\omega_n) = G_{\alpha,\sigma}^0(i\omega_n)^{-1} - G_{\alpha,\sigma}^{And}(i\omega_n)^{-1}$ . The lattice Green's function within the dynamical mean-field approximation then reads  $\mathbf{G}_\sigma(\mathbf{k}, i\omega_n) = [(i\omega_n + \mu)\mathbf{I} - \mathbf{E}_H - \mathbf{t}(\mathbf{k}) - \Sigma_\sigma(i\omega_n)]^{-1}$ , where bold letters indicate  $N \times N$  matrices in sublattice space,  $\mathbf{I}$  is the identity matrix and  $\mathbf{t}(k)$  is the Bloch matrix connecting the different sublattices. Matsubara frequencies,  $\omega_n = (2n + 1)\pi/\beta$ , with  $\beta = 200$  are used. Specializing to the three-fold order realized on the triangular lattice, the matrix elements between sublattices  $\alpha = A, B, C$  are  $t_{AB}(k) = t_{BC}(k) = \phi_k$ ,  $t_{AC}(k) = \phi_k^*$ , having defined  $\phi_k = \sum_i e^{i\delta_i \cdot k}$  and  $\delta_i$  ( $i = 1, 3$ ) the vectors connecting an  $A$  site to its three  $B$  neighbors (see Fig. 1-b).  $\mathbf{E}_H$  is a diagonal matrix whose elements  $E_{H,\alpha} = 3 \sum_{\gamma \neq \alpha} V \langle n_\gamma \rangle$  are, for each  $\alpha$ , the mean-field electrostatic potentials of charges on the nearest-neighboring sites. The problem is solved self-consistently by imposing the condition  $(1/N_s) \sum_{\mathbf{k}} G_{\alpha\alpha,\sigma}(\mathbf{k}, i\omega_n) = G_{\alpha,\sigma}^{And}(i\omega_n)$ , with  $N_s$  the total number of lattice sites. We use Lanczos diagonalization as a problem solver, taking 10 auxiliary sites for each impurity problem. The spectral density for electrons on the  $\alpha$ -sublattice is obtained as  $A_{\alpha,\sigma}(\omega) = -\text{Im} G_{\alpha\alpha,\sigma}(\omega)/\pi$ . We restrict our analysis to solutions where the  $B$  and  $C$  sublattices are equivalent. Practical calculations for a density  $n$  of holes are performed by taking  $n$  electrons per site and changing the sign of  $t$  in Eq. (1).

*The pinball liquid.* Fig. 1-a shows the phase diagram of the EHM obtained from DMFT on the triangular lattice at  $n = 1/2$  (quarter filling), which basically agrees

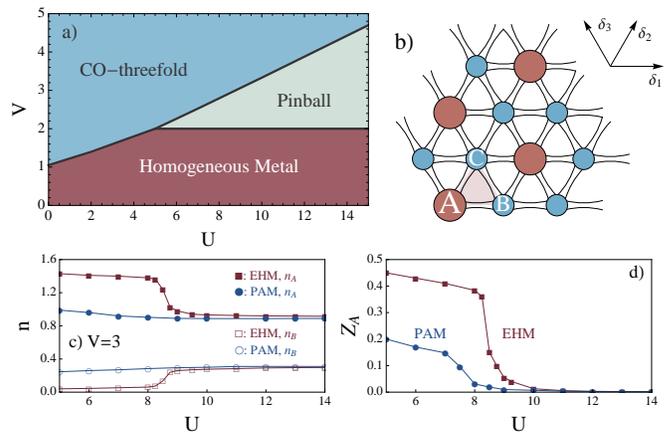


FIG. 1: (Color online) Pinball liquid phase on the triangular lattice from DMFT. (a) The  $U$ - $V$  phase diagram of the EHM on the triangular lattice at quarter filling. (b) Sketch of the pinball phase with pins on the  $A$  sublattice (red, large disks) and balls (blue, small) on the  $B$ - $C$  sublattice. The shaded area is the unit cell. (c) and (d) are the charge occupations and quasiparticle weight  $Z_A$  as a function of  $U$ . Dashed lines are obtained from the PAM Eq. (3).

with previous results obtained from exact diagonalization (ED) on small clusters [10, 11]. In the weakly correlated limit,  $U \rightarrow 0$ , a transition from a homogeneous metal (HM) to a metallic CO state is realized upon increasing the intersite repulsion  $V$ , similar to what is found on bipartite lattices [5, 7-9]. In contrast, the charge ordered insulator obtained on bipartite lattices in the large  $U$  region is replaced here by a metallic CO, termed the *pinball liquid* [18, 19], extending up to increasingly large values of  $V$ . In such phase, quasi-localized charges (*pins*) coexist with a low density of itinerant carriers (*balls*) flowing in the honeycomb lattice formed by interstitial sites (see Fig. 1-b). At large  $V$  and small  $U$ , the full CO in the three-fold geometry corresponds to a density  $n_A \rightarrow 3/2$  on the charge-rich sites and  $n_B \rightarrow 0$  on the charge-poor sites. Increasing  $U$  tends to suppress the double occupancy and eventually when  $U \gtrsim 3V$ , the local Coulomb energy cost is suppressed by leaving only one charge per  $A$  site (a pin,  $n_A \simeq 1$ ). The excess charge density is then transferred to the charge-poor sites (balls,  $n_B \simeq 1/4$ ). The transition is sharp, as shown in Fig. 1-c, and it can be anticipated that the two species behave very differently; pins form an almost half-filled system with a marked Mott behavior due to strong onsite Coulomb interactions, in opposition to the balls which, owing to their low concentration, are in principle protected from them. We note here that the stability of the pinball phase is not limited to the case  $n = 1/2$  described here, but actually extends to the entire range  $1/3 < n < 2/3$  [20].

The quasiparticle weight of the correlated pins, defined as  $Z_A = [1 - \partial \text{Im} \Sigma_A(\omega) / \partial \omega]_{\omega=0}^{-1}$  (depicted in Fig. 1-d) is large in the conventional CO phase at low  $U$ , and

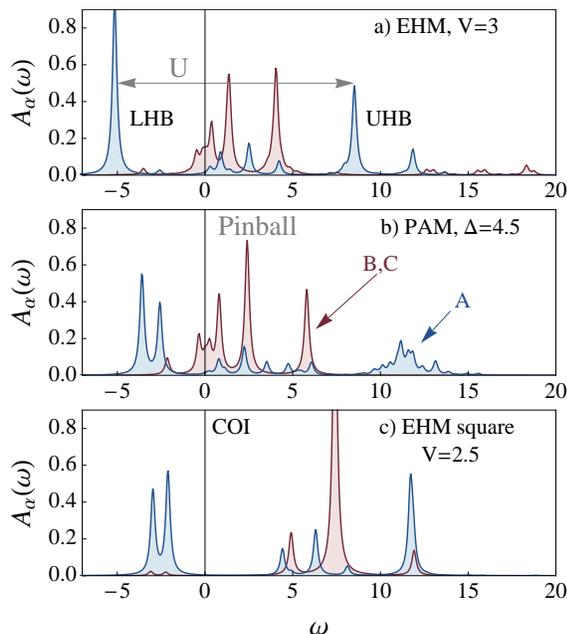


FIG. 2: (Color online) Metallic behavior of the pinball liquid vs. square lattice charge ordered insulator. Spectral functions  $A_A(\omega)$  and  $A_B(\omega)$  projected on the charge rich and charge poor sublattices, for  $U = 12$  in the EHM on the triangular lattice at  $V = 3$  (a) and on the square lattice at  $V = 2.5$  in the COI phase (c). (b) Same quantities for the PAM at the corresponding value  $\Delta = 4.5t$ . The vertical lines denote the Fermi energy.

drops drastically upon entering the pinball liquid (here at  $U = 8.5t$ ). As mentioned above, this occurs when the  $A$ -sublattice concentration spontaneously adjusts to  $n_A \simeq 1$  (Fig. 1-c). Within the accuracy of our method, a small non-vanishing quasiparticle weight persists at all  $U$ , indicating that the pins do not undergo a full Mott transition, but remain in a strongly correlated Fermi liquid state up to  $U \rightarrow \infty$ . We believe that this originates from the fact that the filling of the correlated hybrid band is never exactly integer. This contrasts with the situation encountered on bipartite lattices [9], where the electron concentration in the correlated band is automatically fixed to half-filling once that the Fermi energy falls inside the gap, resulting in a true Mott transition for  $U \gtrsim W$  and  $V \gtrsim 2$ .

The sublattice spectral densities  $A_\alpha(\omega)$  within the charge ordered pinball phase, illustrated in Fig. 2-a for  $U = 12$  and  $V = 3$  for the EHM, confirm this picture. The system is metallic, as testified by the strong spectral weight crossing the Fermi level, which primarily originates from the ball sublattice (B,C sites). The  $A$ -sublattice instead shows typical features of strongly correlated systems with a spectral weight mostly located in two separate regions away from the Fermi level – the lower and upper Hubbard bands separated by an energy  $U$  – and a weak quasiparticle residue at the Fermi energy,

quantified by  $Z_A$ . The spectrum of the charge ordered insulator (COI) phase on the square lattice is shown in Fig. 2-c for comparison.

*Periodic Anderson model and Emergent heavy fermions.* To get further insight into the effects of electronic correlations we now map the problem into a periodic Anderson model (PAM). This is achieved by introducing creation operators  $a_i^+$ ,  $b_i^+$  and  $c_i^+$  respectively on the  $A$ ,  $B$  and  $C$  sublattices and diagonalizing the bands of the honeycomb lattice formed by  $B$  and  $C$  sites (tight-binding on graphene). Rewriting  $\phi_k = \sum_i e^{i\delta_i \cdot k}$  as  $E_k e^{i\theta_k}$ , we can define  $B$ - $C$  subspace spinor operators  $\gamma_{k,\pm}^\pm = (e^{-i\theta_k/2}, \pm e^{i\theta_k/2})/\sqrt{2}$ , whose energies are  $\epsilon_{k,\pm} = \pm E_k$  (the origin is fixed at the Dirac point). Dropping the Coulomb interaction on the conduction bands leads to

$$H_{\text{PAM}} = \sum_{i\sigma} \epsilon_A a_{i\sigma}^\dagger a_{i\sigma} + \sum_{k\sigma\alpha} \epsilon_{k,\alpha} \gamma_{k\alpha}^\dagger \gamma_{k\alpha\sigma} \quad (2)$$

$$+ \sum_{ik,\alpha} (V_{k,\alpha} e^{ikR_i} a_{i\sigma}^\dagger \gamma_{k\alpha\sigma} + h.c.) + U \sum_i a_{i\uparrow}^\dagger a_{i\uparrow} a_{i\downarrow}^\dagger a_{i\downarrow}$$

where the hybridization between the conduction bands and the localized level is determined by  $V_{k,-} = -\sqrt{2}E_k \sin(3\theta_k/2)$  and  $V_{k,+} = \sqrt{2}E_k \cos(3\theta_k/2)$ . The energy of the localized level is set by the charge transfer gap,  $\epsilon_A = -\Delta$ , which originates from the electrostatic interaction between charges on different sublattices. The pinball phase studied in the preceding paragraphs corresponds to  $\Delta = 3V/2$  and is therefore in the charge transfer regime  $U \gg \Delta$  (because  $U > 3V \gg 3V/2$ , cf. Fig. 1-a). The quantities  $n_\alpha$ ,  $Z_A$  and  $A_\alpha(\omega)$  calculated in the PAM are compared with the EHM results in Figs. 1-(c,d) and 2-(a,b) showing a consistent agreement in the pinball liquid phase.

The nature of the coupling between pins and balls is now conveniently analyzed based on the low energy effective PAM varying the number of electrons per unit cell  $n_{\text{cell}} \in [0, 3]$  ( $n_{\text{cell}} = 3n$ ) for a fixed  $\Delta = 4.5$ . This interval includes the region of stability of the pinball in the original EHM [20], i.e.  $1 < n_{\text{cell}} < 2$ . The density of states (DOS) of  $H_{\text{PAM}}$  in the non-interacting limit  $U = 0$  is shown in Fig. 3-a. Hybridization broadens the localized pin level at  $\epsilon_A = -\Delta$  (vertical line in Fig. 3-a) into a dispersive band, and also affects the dispersion of the conduction bands, that is no longer symmetric around the Dirac point  $\omega = 0$ . Because  $\epsilon_A < 0$ , pins are populated first and  $n_A \simeq n_{\text{cell}}$  until  $n_{\text{cell}} = 1$  as seen in  $n_\alpha$  depicted in Fig. 3-b. For  $n_{\text{cell}} > 1$ , the  $A$  sublattice is filled with  $\simeq 1$  electron per site (the maximum allowed by the large  $U$ ) and the remaining electrons move to the conduction band. Correspondingly, the Fermi energy moves from the bottom of the  $(-)$  band to the Dirac point, reached at  $n_{\text{cell}} = 3$ . Interestingly,  $Z_A$  (blue squares in Fig. 3-b) is strongly suppressed in the whole pinball phase (hatched region in Fig. 3-b). Following Refs. [25, 26], we define

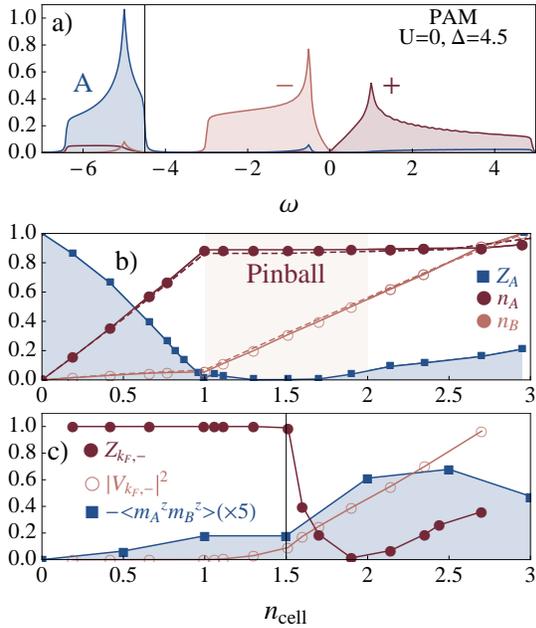


FIG. 3: (Color online) Strong quasiparticle renormalization in pinball liquid phase and antiferromagnetic Kondo correlations. (a) DOS of the noninteracting PAM ( $U = 0$ ) (3) for  $\Delta = 4.5$ . Different colors correspond to projection on the non-hybridized bands: pins (blue),  $-$  (orange) and  $+$  (red). (b) A/B sublattice densities (full lines=DMFT, dashed=ED) and pin quasiparticle weight (DMFT) as a function of the filling  $n_{\text{cell}}$  (c) hybridization, quasiparticle renormalization (DMFT) and magnetic correlations (ED).

the effective self-energy for conduction electrons as

$$\Sigma_{k,\pm}(i\omega_n) = \frac{|V_{k,\pm}|^2}{i\omega_n + \mu - \epsilon_A - \Sigma_A(i\omega_n) - \frac{|V_{k,\pm}|^2}{i\omega_n + \mu - E_k}} \quad (3)$$

which accounts for hybridization as well as indirect interaction effects arising via the Coulomb repulsion of localized charges. Based on Eq. (3), we evaluate the quasiparticle renormalization  $Z_{k,\pm} = [1 - \partial \text{Im}(\Sigma_{k,\pm}) / \partial \omega]_{\omega=0}^{-1}$  of the balls. Note that  $V_{k,-}$  vanishes for wavevectors  $k$  forming an angle  $\pi/6$  [ $\pi/3$ ] with the x-axis, leading to *cold spots* where conduction and localized electrons are perfectly decoupled and  $Z_{k,-} = 1$  identically. In Fig. 3-c we report instead  $Z_{k,-}$  in the directions of maximum hybridization on the Fermi surface (*hot spots*), for which a sharp drop is found at  $n_{\text{cell}} = 3/2$ . This is attributed to an increase in the hybridization with the correlated pins occurring around this filling (see also  $|V_{k,-}|^2$ ). On the same figure is also reported the inter-species magnetic correlation  $\langle m_z^A m_z^B \rangle = \langle (n_{A\uparrow} - n_{A\downarrow})(n_{B\uparrow} - n_{B\downarrow}) \rangle$  calculated by ED on a 12-site cluster (we use ED because inter-site correlations cannot be addressed in the single site DMFT scheme). As shown in Fig. 3-c, the strong renormalization of the metal is accompanied by a buildup of anti-ferromagnetic correlations, corresponding to a screening of the localized moments by the con-

duction electrons. From our data we conclude that pins and balls are nearly decoupled for  $n_{\text{cell}} \leq 3/2$ , while a strong Kondo coupling between the two fluids, responsible for strong renormalization of the conduction electrons, is present at larger concentrations.

*Wigner crystal in the 2DEG.* According to the lattice analogy proposed in Refs. [6, 7, 14], the existence of pronounced short range order close to the MIT enables a mapping of the continuous 2DEG to our model  $H_{\text{PAM}}$  at  $n_{\text{cell}} = 1$ . We can then associate  $\Delta \propto r_s$  [14], where  $r_s$  is the ratio of Coulomb to kinetic energy in the electron gas. The case  $\Delta = 4.5$  analyzed in Fig. 3-b then corresponds, for  $n_{\text{cell}} = 1$ , to a 2DEG well into the Wigner crystal phase: the system is insulating, as both  $Z_A$  and the DOS at the Fermi energy (not shown) vanish at this point. Following Ref. [14] the quantum melting of the Wigner crystal upon reducing  $r_s$  can be identified with a closing of the gap between the pin and  $(-)$  bands (Fig. 3-a) occurring below a critical  $\Delta_c$ . From our DMFT results, this happens at  $\Delta_c \simeq 3.7$  for  $U = 12$ . Although a detailed study of the MIT of the 2DEG is beyond the scope of this work, we note that a metallic state can also be achieved at  $\Delta > \Delta_c$ , by doping away from  $n_{\text{cell}} = 1$ . The resulting metal is very different when doping holes into the pin band ( $n_{\text{cell}} = 1 + \delta$  with  $\delta < 0$ , leading to  $Z_A \propto |\delta|$ , cf. Fig. 3-b) or electrons into the conduction band ( $\delta > 0$ , with  $Z_A$  jumping sharply to a small but finite value). The latter situation actually corresponds to the self-doping instability proposed in Ref. [6]. If this scenario were realized, the metal on the verge of Wigner crystallization would actually be a pinball liquid itself, indicating an appealing connection between the physics of the 2DEG and the emergence of heavy fermion behavior.

*Concluding remarks.* The combination of electronic correlations and geometrical frustration on charge ordered triangular lattices leads to an exotic pinball liquid state in which localized and itinerant electrons coexist. Based on the close analogies with heavy fermion systems, pointed out via an explicit mapping of the electronic problem onto the periodic Anderson model, non-Fermi liquid behavior should occur in such phase as a consequence of the scattering of the itinerant electrons off the localized moments of the pins. On the experimental side, this behavior would be consistent with the anomalous metallic phases of the family of organic conductors  $\theta$ -(BEDT-TTF) $_2$ X which display violation of the Mott-Ioffe-Regel limit in the resistivity, absence of Drude peak in the optical conductivity [22, 23] and non-monotonic  $1/T_1$ -NMR relaxation rates [28] close to charge ordering. The scenario proposed here for emergent heavy fermion behavior could also be of relevance to other correlated materials exhibiting charge ordering on triangular lattices such as transition-metal dichalcogenides [3, 12, 13], AgNiO $_2$  [29] and  $^3\text{He}$  bilayers [30], as well as to the interaction-driven MIT in the 2DEG [9].

### Acknowledgments.

J.M. acknowledges financial support from MINECO (MAT2011-22491, MAT2012-37263-C02-01). This work is supported by the French National Research Agency through Grant No. ANR-12-JS04-0003-01 SUBRIS-SYME.

- 
- [1] M. Imada, A. Fujimori, Y. Tohura, Rev. Mod. Phys. **70**, 10391263 (1998).
- [2] H. Seo, J. Merino, H. Yoshioka and M. Ogata, J. Phys. Soc. Jpn. **75** 051009 (2010).
- [3] P. Fazekas and E. Tosatti, Philos. Mag. B **39**, 229 (1979).
- [4] R. Pietig, R. Bulla, and S. Blawid, Phys. Rev. Lett. **82**, 4046 (1999).
- [5] J. Merino, Phys. Rev. Lett. **99**, 036404 (2007).
- [6] S. Pankov and V. Dobrosavljevic, Phys. Rev. B **77**, 085104 (2008).
- [7] A. Camjayi, K. Haule, V. Dobrosavljevic, and G. Kotliar, Nat. Phys. **4**, 932 (2008).
- [8] C. Li and Z. Wang, Phys. Rev. B **80**, 125130 (2009)
- [9] A. Amaricci, *et. al.*, Phys. Rev. B **82**, 155102 (2010).
- [10] L. Cano-Cortés, J. Merino, S. Fratini, Phys. Rev. Lett. **105**, 036405 (2010).
- [11] L. Cano-Cortés, A. Ralko, C. Fevrier, J. Merino and S. Fratini, Phys. Rev. B **84**, 155115 (2011).
- [12] L. Perfetti, *et al.*, Phys. Rev. Lett. **97**, 067402 (2006).
- [13] B. Sipos, *et al.*, Nat. Mater. **7**, 960 (2008).
- [14] Z. Lenac and M. Sunjic, Phys. Rev. B **52**, 11238 (1995).
- [15] M. M. Radonjić, D. Tanasković, V. Dobrosavljević, K. Haule, and G. Kotliar, Phys. Rev. B **85**, 085133 (2012).
- [16] H. Kino and H. Fukuyama, J. Phys. Soc. Jpn. **65**, 2158 (1996).
- [17] H. Mori, S. Tanaka, and T. Mori, Phys. Rev. B **57**, 12023 (1998).
- [18] M. Kaneko and M. Ogata, J. Phys. Soc. Jpn. **75** 014710 (2006).
- [19] C. Hotta and N. Furukawa, Phys. Rev. B **74**, 193107 (2006).
- [20] C. Hotta and N. Furukawa, J. Phys.: Cond. Matter **19**, 145242 (2007).
- [21] B. Spivak and S. Kivelson, Phys. Rev. B **70**, 155114 (2004).
- [22] K. Takenaka *et al.*, Phys. Rev. Lett. **95**, 227801 (2005).
- [23] H. Tajima, S. Kyoden, H. Mori, and S. Tanaka, Phys. Rev. B **62**, 9378 (2000).
- [24] X. Waintal, Phys. Rev. B **73**, 075417 (2006).
- [25] A. C. Hewson, *The Kondo Problem to Heavy Fermions*, (Cambridge University Press, Cambridge, England, 1993).
- [26] A. Amaricci, *et. al.*, Phys. Rev. B **85**, 05110 (2012).
- [27] P. Gegenwart, Q. Si, and F. Steglich, Nat. Phys. **4**, 186 (2008).
- [28] M. Hirata, K. Miyagawa, K. Kanoda and M. Tamura, Phys. Rev. B **85**, 195146 (2012).
- [29] E. Wawrzyńska, *et. al.*, Phys. Rev. Lett. **99**, 157204 (2007).
- [30] M. Neumann, J. Nyéki, B. Cowan and J. Saunders, Science **317**, 1356 (2007).