

Superconductivity at 43 K induced by isovalent doping of 112-type iron arsenide $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$

Kazutaka Kudo,^{1,2, a)} Tasuku Mizukami,¹ Yutaka Kitahama,¹ Daisuke Mitsuoka,¹ Keita Iba,¹ Kazunori Fujimura,¹ Naoki Nishimoto,¹ Yuji Hiraoka,^{1,2} and Minoru Nohara^{1,2}

¹⁾Department of Physics, Okayama University, Okayama 700-8530, Japan

²⁾Research Center of New Functional Materials for Energy Production, Storage and Transport, Okayama University, Okayama 700-8530, Japan

(Dated: 1 February 2017)

The effects of isovalent doping on the superconducting transition temperature T_c in novel 112-type iron arsenide $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$ were studied by conducting measurements of electrical resistivity ρ and magnetization M . P or Sb doping strongly enhances T_c : P-doped $\text{Ca}_{0.84}\text{La}_{0.16}\text{FeAs}_2$ and Sb-doped $\text{Ca}_{0.85}\text{La}_{0.15}\text{FeAs}_2$ exhibited T_c of 41 and 43 K, respectively, while $\text{Ca}_{0.85}\text{La}_{0.15}\text{FeAs}_2$ without P/Sb exhibited $T_c = 35$ K. These observations will give a hint for further enhancing T_c of rare-earth doped Ca-Fe-As systems.

The discovery of iron-based superconductors has stimulated the development of novel superconducting materials^{1–3} such as *RE*FeAs (1111 type),⁴ *A*Fe₂As₂ (122 type),⁵ *A*FeAs (111 type),⁶ FeSe (11 type),⁷ and compounds with perovskite-type and/or rocksalt-type spacer layers.^{8–12} Here, *RE*, *AE*, and *A* correspond to rare-earth, alkali-earth, and alkali elements, respectively. For this class of materials, the maximum superconducting transition temperature T_c is 55 K.¹³ In order to achieve further enhancement of T_c , however, novel iron-based superconducting materials are required.

Very recently, Katayama *et al.* reported the novel 112-type iron-based superconductor $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$.¹⁴ This compound crystallizes in the monoclinic structure with the space group $P2_1$ (No. 4) and consists of alternately stacked Fe₂As₂ and arsenic zigzag bond layers. The T_c was reported to be 34 K for $x = 0.16$. Though pure CaFeAs₂ was not obtained, Katayama *et al.* found that a small amount of La for Ca stabilizes the 112 phase. The most notable feature of this compound is the existence of arsenic zigzag bond layers. The chemical formula can be written as $(\text{Ca}_{1-x}^{2+}\text{La}_x^{3+})(\text{Fe}_2^{2+}\text{As}_2^{3-})_{1/2}\text{As}^- \cdot xe^-$ with an excess charge of xe^- injected into the Fe₂²⁺As₂³⁻ layers. Thus, the arsenic zigzag bond layers are considered to be composed of As⁻ ions with $4p^4$ configuration as found in *RET*As₂ ($T = \text{Ag}, \text{Au}$).^{15,16} Note that the structure of $\text{Ca}_{10}(\text{T}'_4\text{As}_8)(\text{Fe}_2\text{As}_2)_5$ with $\text{T}'_4\text{As}_8$ layers ($\text{T}' = \text{Pt},^{17–20} \text{Pd},^{21} \text{Ir}^{22}$) can be classified as a derivative of the 112-type structure. The As⁻ zigzag bond layers can be transformed to $\text{T}'_4\text{As}_8$ layers if 1/5 of the As is substituted with T' , two interstitial T' atoms are added, and $(\text{As}_2)^{4-}$ dimers are formed due to the breakdown of the zigzag chains caused by the injection of additional electrons from T' .

First-principle band calculations demonstrated the presence of almost cylindrical Fermi surfaces in $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$,¹⁴ which is favorable for high T_c in iron-based superconductors.^{23,24} This suggests that the

112-type iron-based superconductors have the potential to exhibit higher T_c . Interestingly, Katayama *et al.*¹⁴ suggested that the trace superconductivity of $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$ could be $T_c = 45$ K. In this Letter, we report the emergence of bulk superconductivity at 43 K induced by the isovalent doping of $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$. We find that T_c was drastically enhanced by tiny amounts of P or Sb doping.

Single crystals of $\text{Ca}_{1-x}\text{La}_x\text{Fe}(\text{As}_{1-y}\text{Pn}_y)_2$ ($\text{Pn} = \text{P}$ and Sb) were grown by a heating mixture of Ca, La, FeAs, As, P, and Sb powders. A stoichiometric amount of the mixture was placed in an aluminum crucible and sealed in an evacuated quartz tube. The preparation was carried out in a globe box filled with argon gas. The ampules were heated at 700°C for 3h, heated to 1100°C at a rate of 46°C/h, and cooled to 1050°C at a rate of 1.25°C/h, followed by furnace cooling. The obtained samples were characterized by powder x-ray diffraction (XRD), performed using a Rigaku RINT-TTR III x-ray diffractometer with $\text{CuK}\alpha$ radiation. The $\text{Ca}_{1-x}\text{La}_x\text{Fe}(\text{As}_{1-y}\text{Pn}_y)_2$ was obtained together with a powder mixture of LaAs, FeAs, FeAs₂, and CaFe₂As₂. We separated plate-like single crystals of the present system from the mixture with typical dimensions of $0.4 \times 0.4 \times 0.01$ mm³. The La content, x , was analyzed by energy-dispersive x-ray spectrometry (EDS). The synthesis for nominal $x = 0.07$ – 0.50 yielded samples with $x = 0.15$ – 0.25 . On the other hand, the P and Sb contents could not be determined because the nominal amounts of P ($y = 0.005$) and Sb ($y = 0.01$) are very small. In the remainder of this work, we assume nominal y . Electrical resistivity ρ_{ab} (parallel to the *ab*-plane) measurements were carried out by a standard DC four-terminal method in a Quantum Design PPMS. The magnetization M was measured using a Quantum Design MPMS.

We demonstrate the bulk superconductivity at 35 K and the trace superconductivity at 45 K in $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$ by the temperature dependence of the magnetization M and the electrical resistivity ρ_{ab} shown in Figs. 1(a) and 2(a), respectively. The electrical resistivity ρ_{ab} of $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$ with a composition of $x = 0.15$ exhibits a sharp drop below 40 K, and zero resistiv-

^{a)}Electronic mail: kudo@science.okayama-u.ac.jp

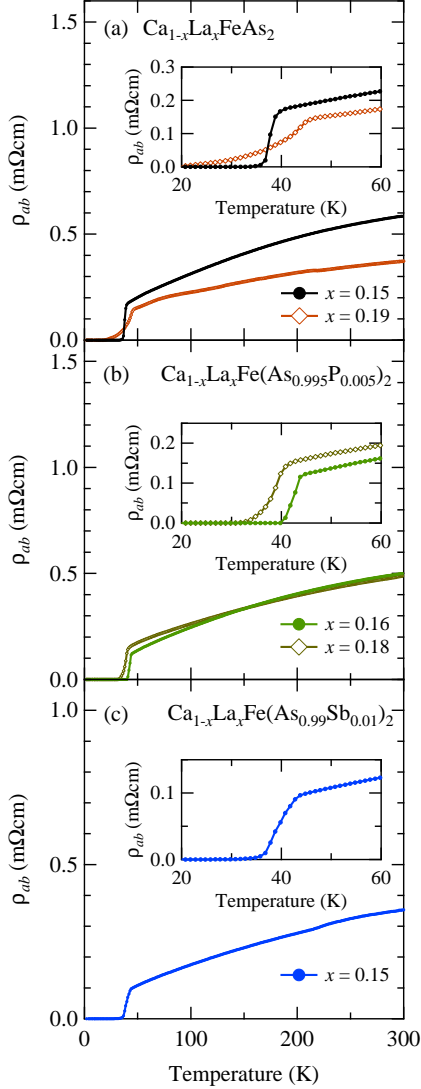


FIG. 1. Temperature dependence of the electrical resistivity parallel to the ab -plane, ρ_{ab} , for $\text{Ca}_{1-x}\text{La}_x\text{Fe}(\text{As}_{1-y}\text{Pn}_y)_2$ ($\text{Pn} = \text{P}$ and Sb). The insets show magnified view in the vicinity of the superconducting transition.

ity is observed at 35 K. As shown in Fig. 2(a), the diamagnetic behavior below $T_c = 35$ K clearly supports the emergence of bulk superconductivity. On the other hand, ρ_{ab} of $x = 0.19$ exhibits the onset of superconductivity at 45 K, as shown in Fig. 1(a), but no diamagnetic signal is observed at ~ 45 K, as shown in Fig. 2(a). We found that tiny amounts of isovalent doping converts this trace superconductivity into bulk superconductivity. As shown in Fig. 1(b), the P-doped $\text{Ca}_{1-x}\text{La}_x\text{Fe}(\text{As}_{0.995}\text{P}_{0.005})_2$ shows the onset of superconductivity at 44 K and zero resistivity at 40 K for $x = 0.16$. Evidence for bulk superconductivity is found in the magnetization M , which clearly shows diamagnetic behavior below $T_c = 41$ K, as

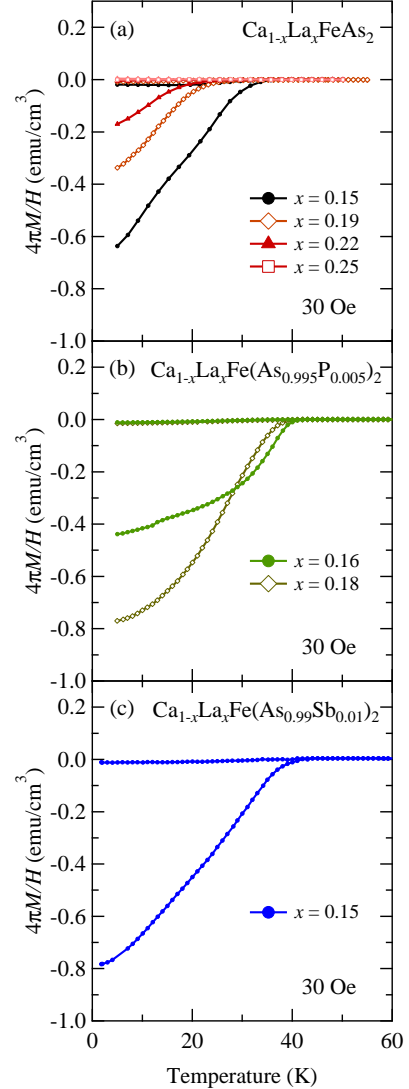


FIG. 2. Temperature dependence of the magnetization M measured at a magnetic field H of 30 Oe for $\text{Ca}_{1-x}\text{La}_x\text{Fe}(\text{As}_{1-y}\text{Pn}_y)_2$ ($\text{Pn} = \text{P}$ and Sb) under zero-field and field cooling conditions.

shown in Fig. 2(b). The shielding volume fraction at 5 K corresponds to 44% for perfect diamagnetism, supporting the emergence of bulk superconductivity. In a composition of $x = 0.18$, though the T_c of 39 K is somewhat smaller than that of $x = 0.16$, the shielding volume fraction exhibits a high value of 77%. Moreover, the Sb-doped $\text{Ca}_{1-x}\text{La}_x\text{Fe}(\text{As}_{0.99}\text{Sb}_{0.01})_2$ also exhibits the onset of superconductivity and zero resistivity at high temperatures such as 44 K and 35 K, respectively, for $x = 0.15$ (Fig. 1(c)). In this case, the bulk superconductivity is further supported by diamagnetic behavior below $T_c = 43$ K, as shown in Fig. 2(c). The shielding volume fraction at 1.8 K corresponds to 78% for perfect diamagnetism.

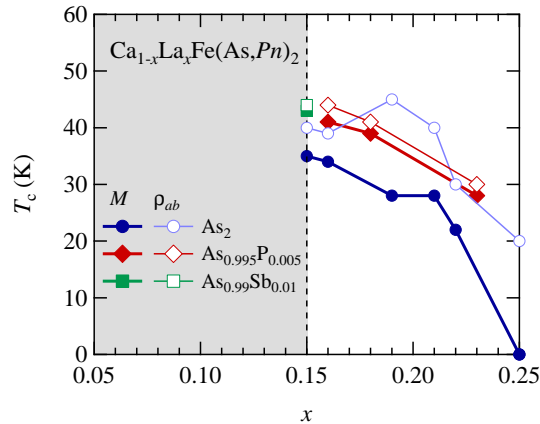


FIG. 3. The x dependence of the superconducting transition temperature T_c below which the magnetization shows diamagnetic signal and the resistivity starts to drop in $\text{Ca}_{1-x}\text{La}_x\text{Fe}(\text{As}_{1-y}\text{Pn}_y)_2$ ($Pn = \text{P}$ and Sb).

The emergence of bulk superconductivity induced by isovalent P doping has also been reported in the 122-type iron-based superconductor. The electrical resistivity of the La-doped $\text{Ca}_{1-x}\text{La}_x\text{Fe}_2\text{As}_2$ exhibited a superconducting transition at high temperatures such as ~ 40 – 43 K, but no visible diamagnetic signal was observed above 40 K.^{25,26} In contrast, the additional P co-doping induced bulk superconductivity at 45 K in $\text{Ca}_{1-x}\text{La}_x\text{Fe}_2(\text{As}_{1-y}\text{P}_y)_2$.²⁷ In the case of La and P co-doped CaFe_2As_2 , it has been suggested that independent tuning of the concentration of charge carriers and the cell volume optimizes the superconductivity. In the present case, further study of the crystal structure will provide useful information on the P or Sb doping effect to realize high T_c .

Figure 3 shows the x dependence of T_c derived from the magnetization and the onset T_c derived from the electrical resistivity. It seems that the resistive-onset T_c determines the upper limit of superconducting transition. In $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$ without P/Sb doping, the T_c determined from magnetization is considerably lower than the resistive-onset T_c . On the other hand, in the case of additional P or Sb doping, these T_c values almost coincide with each other. Moreover, the magnetic T_c almost reaches the maximum value of the resistive T_c (45 K) observed in $\text{Ca}_{1-x}\text{La}_x\text{Fe}_2\text{As}_2$ ($x = 0.19$), suggesting that the tiny amount of isovalent doping has drawn the potential high T_c phase in this x range. It is noted that if we can reduce x , the T_c would increase because T_c of $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$ tends to increase with decreasing x . We should develop chemical methods to do so.

In summary, we report bulk superconductivity at 43 K induced by isovalent doping of $\text{Ca}_{1-x}\text{La}_x\text{FeAs}_2$. We found that tiny amounts of isovalent P or Sb doping drastically enhanced T_c : P-doped $\text{Ca}_{0.84}\text{La}_{0.16}\text{FeAs}_2$ and Sb-

doped $\text{Ca}_{0.85}\text{La}_{0.15}\text{FeAs}_2$ exhibit T_c of 41 and 43 K, respectively. The structural analysis of the present system will provide useful information on the factor for enhancing T_c in terms of tiny amounts of isovalent doping.

ACKNOWLEDGMENTS

The authors are grateful to N. Katayama and H. Sawa for valuable discussions. Part of this work was performed at the Advanced Science Research Center at Okayama University. This work was partially supported by a Grant-in-Aid for Scientific Research (C) (25400372) from the Japan Society of the Promotion of Science (JSPS) and the Funding Program for World-Leading Innovative R&D on Science and Technology (FIRST Program) from JSPS.

- ¹K. Ishida, Y. Nakai, and H. Hosono, *J. Phys. Soc. Jpn.* **78**, 062001 (2009).
- ²J. Paglione and R. L. Greene, *Nat. Phys.* **6**, 645 (2010).
- ³D. C. Johnston, *Adv. Phys.* **59**, 803 (2010).
- ⁴Y. Kamihara, T. Watanabe, M. Hirano, and H. Hosono, *J. Am. Chem. Soc.* **130**, 3296 (2008).
- ⁵M. Rotter, M. Tegel, and D. Johrendt, *Phys. Rev. Lett.* **101**, 107006 (2008).
- ⁶J. H. Tapp, Z. Tang, B. Lv, K. Sasmal, B. Lorenz, P. C. W. Chu, and A. M. Guloy, *Phys. Rev. B* **78**, 060505(R) (2008).
- ⁷F.-C. Hsu, J.-Y. Luo, K.-W. Yeh, T.-K. Chen, T.-W. Huang, P. M. Wu, Y.-C. Lee, Y.-L. Huang, Y.-Y. Chu, D.-C. Yan, and M.-K. Wu, *Proc. Natl. Acad. Sci. U.S.A.* **105**, 14262 (2008).
- ⁸X. Zhu, F. Han, G. Mu, B. Zeng, P. Cheng, B. Shen, and H.-H. Wen, *Phys. Rev. B* **79**, 024516 (2009).
- ⁹N. Kawaguchi, H. Ogino, Y. Shimizu, K. Kishio, and J. Shimoyama, *Appl. Phys. Express* **3**, 063102 (2010).
- ¹⁰X. Zhu, F. Han, G. Mu, P. Cheng, B. Shen, B. Zeng, and H.-H. Wen, *Phys. Rev. B* **79**, 220512(R) (2009).
- ¹¹H. Ogino, K. Machida, A. Yamamoto, K. Kishio, J. Shimoyama, T. Tohei, and Y. Ikuhara, *Supercond. Sci. Technol.* **23**, 115005 (2010).
- ¹²P. M. Shirage, K. Kihou, C.-H. Lee, H. Kito, H. Eisaki, and A. Iyo, *Appl. Phys. Lett.* **97**, 172506 (2010).
- ¹³Z.-A. Ren, W. Lu, J. Yang, W. Yi, X.-L. Shen, Z.-C. Li, G.-C. Che, X.-L. Dong, L.-L. Sun, F. Zhou, and Z.-X. Zhao, *Chin. Phys. Lett.* **25**, 2215 (2008).
- ¹⁴N. Katayama, K. Kudo, S. Onari, T. Mizukami, K. Sugawara, Y. Sugiyama, Y. Kitahama, K. Iba, K. Fujimura, N. Nishimoto, M. Nohara, and H. Sawa, *J. Phys. Soc. Jpn.*, in press.
- ¹⁵M. Brylak, M. H. Möller, and W. Jeitschko, *J. Solid State Chem.* **115**, 305 (1995).
- ¹⁶D. Rutzinger, C. Bartsch, M. Doerr, H. Rosner, V. Neu, Th. Doert, and M. Ruck, *J. Solid State Chem.* **183**, 510 (2010).
- ¹⁷S. Kakiya, K. Kudo, Y. Nishikubo, K. Oku, E. Nishibori, H. Sawa, T. Yamamoto, T. Nozaka, and M. Nohara, *J. Phys. Soc. Jpn.* **80**, 093704 (2011).
- ¹⁸N. Ni, J. M. Allred, B. C. Chan, and R. J. Cava, *Proc. Natl. Acad. Sci. U.S.A.* **108**, E1019 (2011).
- ¹⁹C. Löhnert, T. Stürzer, M. Tegel, R. Frankovsky, G. Friederichs, and D. Johrendt, *Angew. Chem. Int. Ed.* **50**, 9195 (2011).
- ²⁰M. Nohara, S. Kakiya, K. Kudo, Y. Oshiro, S. Araki, T. C. Kobayashi, K. Oku, E. Nishibori, and H. Sawa, *Solid State Commun.* **152**, 635 (2012).
- ²¹C. Hieke, J. Lippmann, T. Stürzer, G. Friederichs, F. Nitsche, F. Winter, R. Pöttgen, and D. Johrendt, *Phil. Mag.* **93**, 3680 (2013).
- ²²K. Kudo, D. Mitsuoka, M. Takasuga, Y. Sugiyama, K. Sugawara,

- N. Katayama, H. Sawa, H. S. Kubo, K. Takamori, M. Ichioka, T. Fujii, T. Mizokawa, and M. Nohara, *Sci. Rep.* **3**, 3101 (2013).
- ²³D. J. Singh and M.-H. Du, *Phys. Rev. Lett.* **100**, 237003 (2008).
- ²⁴I. A. Nekrasov, Z. V. Pchelkina, and M. V. Sadovskii, *JETP Lett.* **88**, 679 (2008).
- ²⁵S. R. Saha, N. P. Butch, T. Drye, J. Magill, S. Ziemak, K. Kirshenbaum, P. Y. Zavalij, J. W. Lynn, and J. Paglione, *Phys. Rev. B* **85**, 024525 (2012).
- ²⁶Z. S. Gao, Y. P. Qi, L. Wang, D. L. Wang, X. P. Zhang, C. Yao, C. L. Wang, and Y. W. Ma, *EPL* **95**, 67002 (2011).
- ²⁷K. Kudo, K. Iba, M. Takasuga, Y. Kitahama, J. Matsumura, M. Danura, Y. Nogami, and M. Nohara, *Sci. Rep.* **3**, 1478 (2013).