

INVESTIGATION OF THE SERS SPECTRA OF COPPER PHTHALOCIANINE ADSORBED ON GALLIUM PHOSPHIDE SUBSTRATES

A.M. Polubotko* V.P. Chelibanov**

*A.F. Ioffe Physico-Technical Institute Russian Academy of Sciences, Politechnicheskaya 26,

194021 Saint Petersburg, Russia Tel: (812) 274-77-29, Fax: (812) 297-10-17 E-mail:

alex.marina@mail.ioffe.ru

**State University of Information Technologies, Mechanics and Optics, Kronverkskii 49, 197101

Saint Petersburg, RUSSIA, E-mail: Chelibanov@gmail.com

Abstract

The SERS spectra of the phthalocyanine molecule, adsorbed on the gallium phosphide substrate are investigated. It is demonstrated that there appear strong lines, which are forbidden in usual Raman scattering. Analysis of the spectra indicates that these lines are associated with a strong quadrupole light-molecule interaction and also by a strong enhancement of the tangential components of the electric field on the surface. As it was demonstrated earlier, the last effect is characteristic for SERS on semiconductor and dielectric substrates, where there is the enhancement not only of the normal, but of the tangential components of the electric field on the surface.

Investigation of the SERS phenomenon on semiconductor and dielectric substrates is of a great interest both from the theoretical and experimental points of view. In [1] it was demonstrated that the reason of SERS in this case is the surface roughness. The enhancement arises in small regions of the surface with a very large curvature. As it was demonstrated in our work [1], the enhancement in SERS on semiconductor and dielectric substrates is weaker than on

metals with the same value of the modulus of the dielectric constant. This result is associated with the fact that semiconductors and dielectrics are transparent in principle for the electromagnetic field in a wide range of frequencies in contrast with metals, which “expel” the field. Therefore the systems with the semiconductor and dielectric substrates possess by a “smaller heterogeneity” of the medium, that results in a weaker enhancement of the field and its derivatives. However, in accordance with theoretical and experimental results [1], in contrast with the metal, there is the enhancement not only of the normal, but also of the tangential component of the electric field at the surface, that results in some peculiarities of the SERS spectra. We investigated the SERS spectra of the copper phthalocyanine molecule (Figure 1), adsorbed on the gallium phosphide substrate, published in [2].

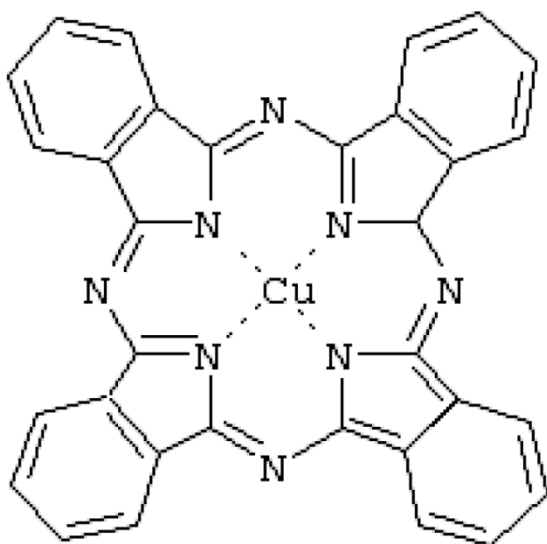


Figure 1. The Copper phthalocyanine molecule

As it is well known copper phthalocyanine belongs to the D_{4h} symmetry group. The SERS spectra of this molecule, adsorbed on the particles of GaP with a mean sizes $d=106, 60, \text{ и } 40$ nm in the interval of the wavenumbers $500-1700 \text{ cm}^{-1}$ are shown on the Figure 2.

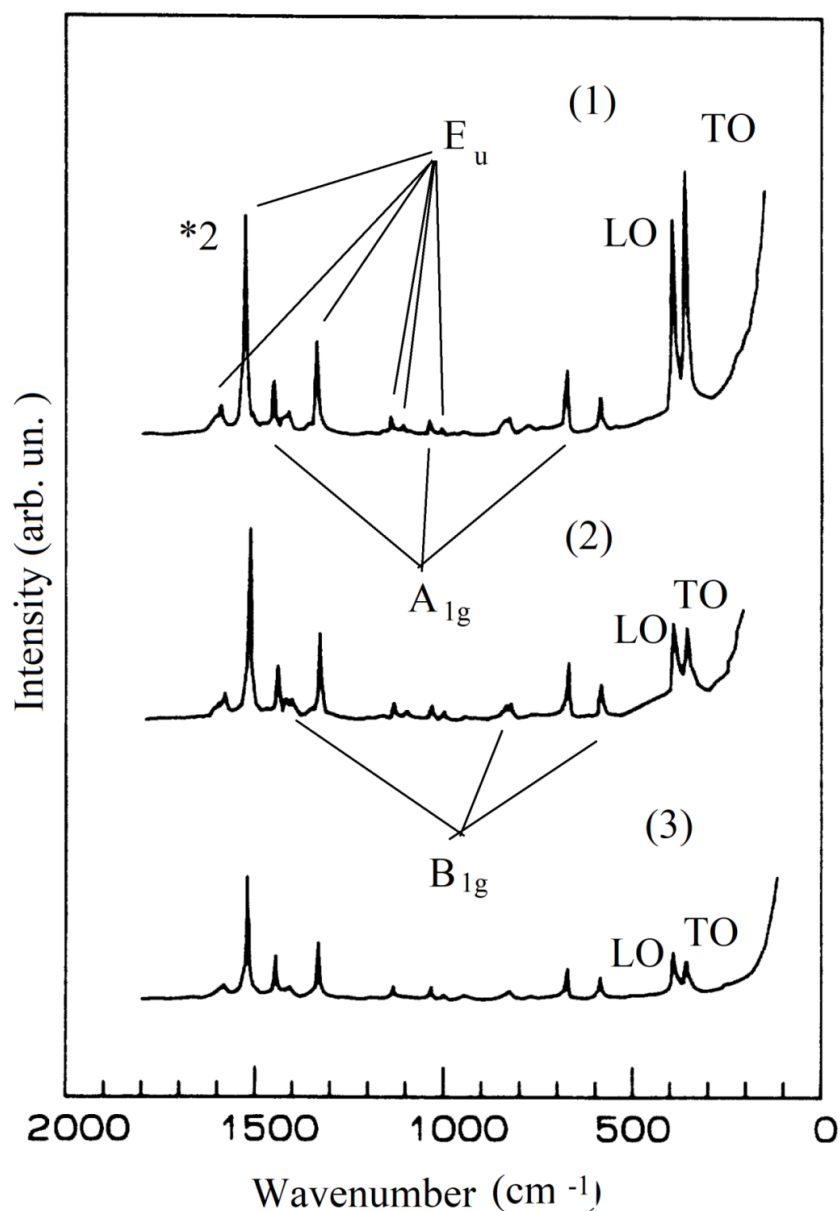


Figure 2. The SERS spectra of the phthalocyanine molecule, adsorbed on the gallium phosphide substrate. (1) – the mean size of the particles 106 nm, the enhancement coefficient 700; (2) – the mean size of the particles 60 nm, the enhancement coefficient 300; (3) – the mean size of the particles 40 nm, the enhancement coefficient 200. LO and TO designate the lines, which belong to the longitudinal and transverse phonons of the substrate.

It is necessary to note that the spectra were taken for the wavelength of the incident radiation 514.5 nm. The enhancement coefficients were approximately 700, 300 and 200 respectively for the particles with the mean sizes $d=106$, 60, and 40 nm. In accordance with our ideas the phthalocyanine molecule adsorbs parallel to the surface of nano particles. From Table 1 one can see, that there are sufficiently intense lines, caused by the vibrations with A_{1g} and B_{1g}

Table 1. Assignment of the lines of the copper phthalocyanine molecule, adsorbed on the gallium phosphide substrate.

Wavenumbers cm^{-1}	Irreducible representations
580 m	B_{1g}
680 m	A_{1g}
830 vw	B_{1g}
950 vw	A_{2u}
1000 vw	E_u
1030 vw	A_{1g}
1096 vw	E_u
1121 vw	E_u
1327 s	E_u
1400 vw	B_{1g}
1440 m	A_{1g}
1511 s	E_u
1580 w	E_u

irreducible representations and the wavenumbers 680, 1030, 1440 cm^{-1} and 580, 1030, 1400 cm^{-1} respectively, characteristic for the usual Raman scattering. However there appear strong forbidden lines with the irreducible representation E_u , caused by the vibrations transforming as the components of the dipole moments (d_x, d_y) with the wavenumbers 1000, 1096, 1121, 1327, 1511 и 1580 cm^{-1} and also a very weak line with the irreducible representation A_{2u} , caused by the vibration, transforming as the dipole moment d_z , which is perpendicular to the surface, with the wavenumber 950 cm^{-1} . Appearance of the forbidden lines with the irreducible representation E_u is in conformity with our SERS theory on semiconductor and dielectric substrates [1], when there is the enhancement not only of the normal, but of the tangential components of the electric field. In accordance with our SERS theory [3], the scattering can occur via various dipole and quadrupole moments $d_x, d_y, d_z, Q_{xx}, Q_{yy}, Q_{zz}$, or via various

linear combinations of the above quadrupole moments, transforming after the unit irreducible representation for the molecules, with sufficiently high symmetry. For the copper phthalocyanine molecule these combinations are $Q_1 = Q_{xx} + Q_{yy}$ and $Q_2 = Q_{zz}$, which one names as main quadrupole moments Q_{main} . The scattering diagram for SERS is shown on the Figure 3. Here we do not repeat our reasoning, which one can find in our works and in the monograph [3] in particular. It is necessary only to indicate that the scattering contributions via dipole and main quadrupole moments Q_1 and Q_2 , which we designate as $(d - Q_{main})$, define appearance of forbidden lines. Therefore their appearance, and also appearance of a weak line with the irreducible representation A_{2u} indicate the appearance of a sufficiently strong quadrupole light-molecule interaction, which arises in the system with a semiconductor substrate in this case. One should note that in [4], we reported appearance of forbidden lines on the hydroquinone molecule,

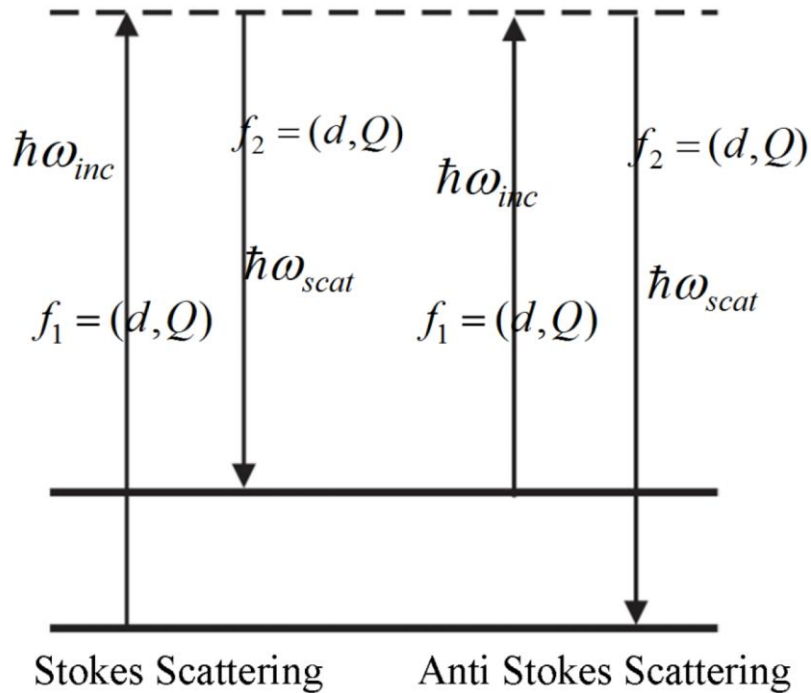


Figure 3. The scattering diagram for SERS. The scattering can occur via various combinations of the dipole and the main quadrupole moments d and Q . Here f_1 and f_2 designate the dipole and main quadrupole moments, ω_{inc} and ω_{scat} are the frequencies of the incident and the scattered fields.

adsorbed on the TiO_2 substrate. However the forbidden lines with the irreducible representation E_u have significantly higher intensity in our case, which is even more than the intensities of allowed lines with the irreducible representations A_{1g} and B_{1g} , in contrast to the system with hydroquinone, where they are very weak. One of the reasons of this “anomaly” is the fact that the copper phthalocyanine molecule is significantly larger than hydroquinone while the quadrupole interaction increases with the increase of the size of the molecules.

References:

1. Polubotko A.M., Chelibanov V.P. //Optics and spectroscopy, 2017, V. 122, № 6, P. 980.
2. Hayashi S., Koh R., Ichiyama Y., Yamamoto K.// Physical Review Letters, 1988, V. 60, No 11, P. 1085.
3. Polubotko A. M. The Dipole Quadrupole Theory of Surface Enhanced Raman Scattering, Nova Science Publishing Inc. 2009, New York.
4. Polubotko A.M. Chelibanov V.P.//Optics and spectroscopy, 2018, V. 124, № 1, P. 68.