Heavy-electron quantum criticality and single-particle spectroscopy

Stefan Kirchner*

Zhejiang Institute of Modern Physics, Zhejiang University, Hangzhou, Zhejiang 310058, China and Zhejiang Province Key Laboratory of Quantum Technology and Device, Zhejiang University, Hangzhou 310027, China

Silke Paschen

Institute of Solid State Physics, Vienna University of Technology, Wiedner Hauptstrasse 8-10, 1040 Vienna, Austria

Qiuyun Chen

Science and Technology on Surface Physics and Chemistry Laboratory, Mianyang 621908, China

Steffen Wirth

Max Planck Institute for Chemical Physics of Solids, 01187 Dresden, Germany

Donglai Feng

State Key Laboratory of Surface Physics, and Department of Physics, Fudan University, Shanghai 200433, China and Hefei National Laboratory for Physical Science at Microscale, CAS Center for Excellence in Quantum Information and Quantum Physics, and Department of Physics, University of Science and Technology of China, Hefei 230026, China

Joe D. Thompson

Los Alamos National laboratory, Los Alamos, New Mexico 87545, USA

Qimiao Si

Department of Physics and Astronomy and Center for Quantum Materials, Rice University, Houston, Texas 77005, USA

(Dated: March 12, 2020)

Angle-resolved photoemission spectroscopy (ARPES) and scanning tunneling microscopy (STM) have become indispensable tools in the study of correlated quantum materials. Both probe complementary aspects of the single-particle excitation spectrum. Taken together, ARPES and STM have the potential to explore properties of the electronic Green's function, a central object of many-body theory. This review explicates this potential with a focus on heavy-electron quantum criticality, especially the role of Kondo destruction. A discussion on how to probe the Kondo destruction effect across the quantum-critical point using ARPES and STM measurements is presented. Particular emphasis is placed on the question of how to distinguish between the signatures of the initial onset of hybridization-gap formation, which is the "high-energy" physics to be expected in all heavy-electron systems, and those of Kondo destruction, which characterizes the low-energy physics and, hence, the nature of quantum criticality. Recent progress and possible challenges in the experimental investigations are surveyed,

the STM and ARPES spectra for several quantum-critical heavy-electron compounds are compared, and the prospects for further advances are outlined.

CONTENTS

Ι.	Introduction	2			
II.	Quantum Criticality A. High-energy excitations, temperature evolution, and	3			
	mass enhancement	5			
	B. Isothermal evolution at low temperatures	6			
	C. Further considerations	6			
	D. Summary of Sec. II	6			
III.	ARPES, STM, and the Single-particle Green's Function	6			
	A. The single-particle Green's function	7			
	B. ARPES and STM	7			
	C. Probing quantum criticality in the Kondo lattice	8			
	D. Summary of Sec. III	9			
IV.	Quantum Criticality in YbRh ₂ Si ₂	10			
	Summary of Sec. IV	11			
V.	The Cerium-based 115 Family: Photoemission versus				
	Tunneling Spectroscopy	11			
	A. CeIrIn ₅	11			
	B. CeCoIn ₅	12			
	C. CeRhIn ₅	14			
	D. Further considerations	15			
	E. Summary of Sec. V	16			
VI.	Progress, Challenges, and Prospects				
	A. High-energy Kondo features	16			
	B. Isothermal evolution at low temperatures	17			
	C. Outlook	17			
VII.	Conclusion	19			
	Acknowledgements	19			
	References	20			

I. INTRODUCTION


A major objective of quantum materials research is to link observable properties to the nature of quantum mechanical many-body ground state properties and to the characteristics of the excitation spectrum above the ground state. In particular, it aims at understanding and predicting the emergence of novel phases in terms of a minimal set of variables, most notably symmetries and broken symmetries of the ground state and the ensuing classification of the excitation spectrum. The typical energy window commonly involved in the materials of interest can cover a wide range, from a few percent of a meV to several eV. A well-known example is the high-temperature superconductors, which have stimulated research since their discovery more than 30 years ago.

The quest for a unified understanding of different classes of quantum materials has led to the notion of quantum-critical points (QCPs) as an economic and powerful way of organizing their phase diagrams (Coleman and Schofield, 2005; Kirchner et al., 2013; Sachdev, 1999; Si and Steglich, 2010). Such continuous zerotemperature phase transitions not only separate different ground states but also give rise to a characteristic behavior; this is the quantum-critical fan, which can extend to comparatively large energies and temperatures. cf. Fig. 1. Within this fan, universal scaling behavior is expected up to some material-specific high-energy cutoff. Among the material classes that are currently attracting particular interest are the cuprates, iron prictides, pyrochlore iridates, transition metal dichalcogenides, and heavy-electron compounds. An underlying theme of most if not all of these materials classes is the tendency of their charge carriers to localize in response to the large effective Coulomb repulsion experienced by the itinerant degrees of freedom. The tendency toward localization gives rise to the bad-metal behavior of these materials.

In heavy-electron compounds, which most commonly are based on Ce, Yb, and U, the primary degree of freedom is the f electron. In the lanthanide-based materials, the 4f electron is localized close to the ionic core as a result of atomic physics and thus has a characteristic energy of the order eV. For the same reason, the wave-function overlap between the 4f orbitals and the band (or c) electrons, i.e., the hybridization, is typically small. As a result, the 4f electron appears localized at high temperatures or energies in the entire range of phase space as long as the valency of the lanthanide ion remains near its localized limit. In this regime each 4f electron contributes an amount $\sim \ln N_f$ to the entropy, where N_f is the angular momentum degeneracy. N_f is affected by spin-orbit coupling and the crystal electric fields but as long as $N_f > 1$, the spin entropy remains macroscopically large.

Similar arguments in principle apply to actinide-based heavy-electron compounds (Fisk et al., 1985). In contrast to their 4f counterparts, 5f orbitals are substantially less localized. As a result, the associated heavyelectron bands are more dispersive, f-c hybridization is stronger and crystal electric fields are less well defined. Collectively, these properties frequently lead to more complex behaviors compared to Ce- or Yb-based intermetallics (Lawrence et al., 2011), and so we use the lanthanide-based heavy-electron materials as exemplary of the essential physics. As temperature is lowered and the ground state is approached, the spin entropy associated with the localized 4f (5f) electron needs to be quenched. Evidently, the system possesses several options for releasing this entropy, which lead to different ground states. At zero temperature, the system can tran-

^{*} stefan.kirchner@correlated-matter.com

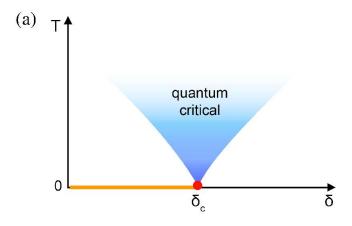

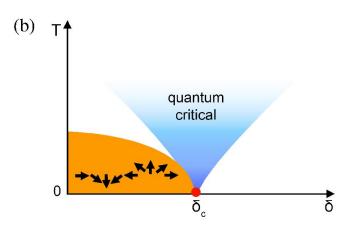


FIG. 1 The quantum critical fan. (a) A continuous quantum phase transition occurs at zero temperature for a critical value (δ_c) of a nonthermal tuning parameter δ . It separates the distinct behaviors of the ground state wavefunction, i.e., being ordered for $\delta < \delta_c$ (the orange line) and disordered for $\delta > \delta_c$. At nonzero temperatures vestiges of the quantum phase transition lead to distinctive scaling behavior in a quantum-critical fan that spreads out of the quantum-critical point and extends up to a problem specific cutoff temperature. Unlike the scaling behavior, the existence of a fan of quantumcritical behavior is generic, independent of the nature of the criticality. (b) Frequently, quantum phase transitions occur as order is suppressed and the transition temperature $T_c(\delta)$ of a classical phase transition vanishes, i.e., $T_c(\delta \to \delta_c) \longrightarrow 0$. In heavy-electron materials, the most common types of quantum criticality separate antiferromagnetic and paramagnetic phases. Shown here is a type of antiferromagnetic order, indicated by the variation of the magnetic moment density over one wavelength. This Colloquium explores the potential of single-particle spectroscopies to distinguish different types of quantum criticality.

sition from one ground state to another upon changing coupling constants in the Hamiltonian. At values of these coupling constants where the ground state energy is non-analytic, the system undergoes a quantum phase transition. Experiments, however, are performed at nonzero temperatures. The challenge then is how to distinguish the approach to different ground states with only a lim-

ited, intermediate temperature window accessible to experiment. This task is made even more difficult given that high-energy properties are largely insensitive to the changes in the coupling constants that take a system through different ground states.

The primary tools for exposing the underlying physics that accompanies the entropy release as the temperature or energy is lowered include spectroscopic methods that can trace excitations over some energy range of interest. For example, spin excitations can be probed with the help of inelastic neutron scattering. Among the various spectroscopic techniques, angle-resolved photoemission spectroscopy (ARPES) and scanning tunneling microscopy or spectroscopy (STM) stand out as these allow one to most directly trace properties of the single-particle Green's function, the basic building block in almost every many-body theory.

We survey and compare recent ARPES and STM experiments performed on quantum-critical heavy-electron compounds that are located close to ground state instabilites at the border of magnetism. In particular, we focus on how critical Kondo destruction (Coleman et al., 2001; Si et al., 2001), i.e., the breakdown of Kondo entanglement at zero temperature right at the onset of magnetism, is reflected in ARPES and STM data at elevated temperatures.

This Colloquium is organized as follows. After a brief introduction of quantum criticality in heavy-electron systems, we recapitulate the relation between APRES and STM measurements and their link with the single-particle Green's function. We then discuss recent STM measurements on YbRh₂Si₂, a heavy-electron antiferromagnet that features a Kondo destruction QCP as a function of the applied magnetic field, before turning to high-resolution ARPES measurements on the cerium-115 family that consists of CeMIn₅ (M=Co,Rh,Ir). We close with an outlook on current challenges and future directions. To facilitate reading, each section (II-V) ends with a brief summary of the salient points discussed in the section.

II. QUANTUM CRITICALITY

Quantum phase transitions occur at zero temperature and like their finite temperature counterparts, they can be either first order or continuous (Gegenwart et al., 2008; v. Löhneysen et al., 2007; Sachdev, 1999; Si and Steglich, 2010). In contrast to the finite temperature case where thermal fluctuations drive the transition, quantum fluctuations, encoded already at the Hamiltonian level, are responsible for the occurrence of a quantum phase transition. A classical transition can be accessed by varying the temperature through a threshold value T_c , while the zero-temperature transition is approached by tuning a nonthermal control parameter, denoted δ in Fig. 1,


to its critical value (δ_c). If the transition is continuous, characteristic, critical scaling ensues in its vicinity which reflects the singular correlations of the ground state wavefunction at δ_c . At nonzero temperatures, this singular behavior leads to the quantum-critical fan in which characteristic behavior is observed in various quantities below a system-specific cutoff energy: see Fig. 1.

In stoichiometric heavy-electron compounds containing Ce or Yb elements, 4f electrons in a partially filled 4f shell are strongly correlated, provided the Ce or Yb ions possess a valence close to +III. The spin-orbit interaction and the crystal electric field generated by the ligands surrounding the Ce or Yb ion in the crystalline environment reduce the degeneracy of the 4f shell. Most commonly, the lowest lying atomic 4f levels correspond to a Kramers doublet. As a result, the 4f electrons behave as a lattice of effective spin-1/2 local moments. This leads to an effective description in terms of the Kondo lattice Hamiltonian:

$$H_{KL} = H_0 + \sum_{ij} I_{ij} \mathbf{S}_i \cdot \mathbf{S}_j + \sum_i J_K \mathbf{S}_i \cdot \mathbf{s}_i^c, \qquad (1)$$

where $H_0 = \sum_{\mathbf{k},\sigma} \varepsilon_{\mathbf{k}} c_{\mathbf{k}\sigma}^{\dagger} c_{\mathbf{k}\sigma}$ describes the conduction electrons with dispersion $\varepsilon_{\mathbf{k}}$. The Ruderman-Kittel-Kasuya-Yosida (RKKY) interaction I_{ij} acting between the local moments \mathbf{S} at site i and j and the Kondo coupling J_K (between the local moments and the conduction electron spin density \mathbf{s}^c) typically are antiferromagnetic, i.e., $I_{ij} > 0$, $J_K > 0$. The competition between these two types of interactions lies at the heart of the microscopic physics for heavy-electron systems (Doniach, 1977).

In the heavy-electron compounds described by the Kondo lattice Hamiltonian, Eq. (1), a QCP may arise from tuning the ratio of RKKY to Kondo interactions, which is parametrized by the nonthermal control paramater $\delta \equiv T_K^0/I$. Here, the Kondo scale (for the $N_f = 2$ case) is $T_K^0 \approx \rho_0^{-1} \exp\left(-1/\rho_0 J_K\right)$, with ρ_0 being the density of states of the conduction electrons at the Fermi energy, whereas I parametrizes the RKKY interaction. This RKKY exchange interaction between the localized moments is mediated by the conduction electron spin density. It is perturbatively generated from the Kondo coupling term $\sim J_K$, resulting in $I_{ij}(J_K)$. In Eq. (1), we added I_{ij} as an independent exchange interaction to facilitate the discussion of the phase diagram, because tuning the ratio between the explicit I_{ij} and J_K is more convenient. It accesses the quantum phase transition that otherwise would have been induced in the tuning of δ through the variation of the ratio of J_K to the conduction electron bandwidth $2D \sim 1/\rho_0$. Formally, one may think of Eq.(1) as arising from a more complete starting Hamiltonian through the process of integrating out additional conduction electron degrees of freedom; this procedure results in the explicit I_{ij} term in the effective Hamiltonian of Eq.(1). One needs to be sure that there is no double counting of the explicit and generated con-

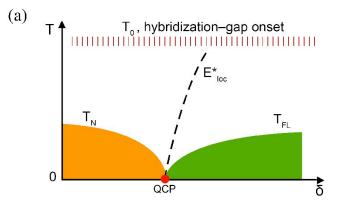

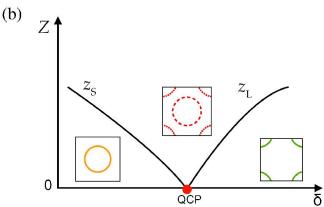


FIG. 2 Basic concepts of Kondo destruction quantum criticality. (a) Local quantum criticality with Kondo destruction under the variation of the control parameter δ . Here T_0 is a high-energy scale that describes the initial onset of dynamical Kondo correlations and that smoothly evolves across the QCP δ_c . This high-energy scale is reflected in the onset of hybridization-gap formation. The low-energy physics is described in terms of T_N and $T_{\rm FL}$, which are, respectively, the temperatures for the Néel transition and the crossover into the paramagnetic Fermi liquid state. This phase diagram also involves the Kondo destruction energy scale E_{loc}^* , which characterizes the Kondo destruction. The E_{loc}^* line divides the phase diagram in terms of the flow of the system toward either the Kondo screened or the Kondo destruction ground state. In the conventional model of spin-density wave quantum criticality, the line E_{loc}^* extrapolates to zero temperature in the ordered phase so that the Fermi surface already is large before reaching the QCP with increasing δ and evolves smoothly across the QCP (Coleman et al., 2001; Si et al., 2001). Adapted from Ref. (Stockert et al., 2012). (b): The small (left) and large (right) Fermi surfaces and the associated quasiparticle weights z_S and z_L that are discussed in Sec. III. The fluctuating Fermi surfaces (middle) are associated with the QCP. Adapted from (Pfau et al., 2012).

tributions to I_{ij} , and this can be consistently done in practice. For a technical discussion of this point see (Si et al., 2005).

On the paramagnetic side, the ground state is characterized by the amplitude of the *static* Kondo singlets that are formed between the local moments and conduction

electron spins (Hewson, 1993). For a Kondo destruction QCP, this static Kondo singlet amplitude is continuously suppressed when the system approaches the QCP from the paramagnetic side (Si *et al.*, 2014, 2001; Zhu *et al.*, 2003).

As illustrated in Fig. 2(a), the Kondo destruction energy scale E^*_{loc} goes to zero as the control parameter δ approaches the QCP at δ_c from the paramagnetic side, and the antiferromagnetic order sets in when δ goes across δ_c . The Kondo destruction goes beyond the Landau framework of quantum criticality. The latter is based on order-parameter fluctuations, which in the present context of antiferromagnetic heavy-electron systems is referred to as a spin-density-wave (SDW) QCP (Hertz, 1976; Millis, 1993; Moriya, 1985). It arises when E^*_{loc} stays nonzero when decreasing δ to δ_c and approaches zero only inside the ordered regime at $\delta < \delta_c$. In this case, the asymptotic quantum-critical behavior at energies below $E^*_{loc}(\delta_c)$ is the same as in the type of phase diagram shown in Fig. 1(b), where E^*_{loc} is not part of the critical physics.

The Kondo destruction gives rise to a dynamical spin susceptibility which displays unusual scaling at the QCP (Si et al., 2014, 2001). This includes a fractional exponent (Glossop and Ingersent, 2007; Grempel and Si, 2003; Zhu et al., 2003, 2007) in the singular dependence on frequency (ω) and temperature (T), and ω/T scaling. These features have in fact been observed by inelastic neutron scattering measurements on the 5f electron system UCu_{5-x}Pd_x (Aronson et al., 1995) and the 4f electron-based metal CeCu_{6-x}Au_x (Schröder et al., 2000).

For $\text{CeCu}_{6-x}\text{Au}_x$ at its critical doping $x_c \approx 0.1$, the exponent in the ω/T scaling analysis (Schröder *et al.*, 2000) was found to be $\alpha = 0.75(5)$, which compares well with the value $\alpha = 0.72\text{-}0.78$ calculated at the Kondo destruction QCP (Glossop and Ingersent, 2007; Grempel and Si, 2003; Zhu *et al.*, 2003, 2007). In the case of a standard SDW QCP, no such ω/T scaling is expected as this QCP is described by a Ginzburg-Landau functional above its upper critical dimension (Hertz, 1976; Millis, 1993; Moriya, 1985).

In the single-particle excitations, the collapse of E_{loc}^* implies a sudden reconstruction of the Fermi surface across the QCP. To contrast this picture with the more traditional scenario of an SDW transition (Hertz, 1976; Millis, 1993; Moriya, 1985), where critical fluctuations are tied to nesting properties of the Fermi surface, we refer to quantum criticality exhibiting critical Kondo destruction as local quantum criticality (Coleman et al., 2001; Pépin, 2007; Senthil et al., 2004; Si et al., 2001). At zero temperature:

• For $\delta > \delta_c$, the Fermi surface is large and is given by the combination of the 4f and conduction electrons. A nonzero amplitude of the static Kondo singlet specifies a *Kondo screened* ground state.

Here, Kondo resonances appear in the excitation spectrum, reflecting the entanglement between the 4f moments and the conduction electrons in the ground state. The Kondo effect is responsible for the large mass enhancement and a small quasiparticle weight z_L : see Fig. 2(b). There is a small gap for the single-particle excitations at the wavevectors where the small Fermi surface would have resided.

- For $\delta < \delta_c$, the Fermi surface is small as determined by the conduction electrons alone. This is because, when the amplitude of the static Kondo singlet vanishes, there is no longer a well-defined Kondo resonance. We refer to this state as a Kondo destruction ground state.
- At the QCP, single-particle excitations are gapless and have a non-Fermi-liquid form, at both small and large Fermi surfaces.

A. High-energy excitations, temperature evolution, and mass enhancement

Figure 2(a) also contains a high-energy scale T_0 which describes the initial onset of dynamical Kondo correlations. This scale is generally affected by the presence of higher crystal electric field doublets (or quartets) that together form the 4f multiplet (Chen et al., 2017; Cornut and Coqblin, 1972; Kroha et al., 2003; Pal et al., 2019). It is important to note that this scale smoothly evolves across the QCP at δ_c . The development of the hybridization gap is associated with the initial onset of dynamical Kondo correlations, as illustrated in Fig. 3, and will appear on both sides of δ_c .

For $\delta > \delta_c$, the temperature evolution of the physical properties reflects the flow of the system toward the Kondo screened ground state. For instance, the initial onset of dynamical Kondo correlations results in the Kondo screened ground state; the single-particle excitations develop into fully coherent heavy quasiparticles at the large Fermi surface as the temperature is lowered below $T_{\rm FL}$, the crossover temperature into the paramagnetic Fermi liquid state.

For $\delta < \delta_c$, the initial onset of dynamical Kondo correlations still takes place, even though it does *not*, in the end, lead to a well-defined Kondo resonance and the Kondo-singlet amplitude vanishes in the ground state. Still, as the temperature is further lowered, vestiges of the Kondo effect will be observed at any nonzero temperature. In particular, the effective mass is a dynamical quantity, measuring the dispersion of the Landau quasiparticles, and is enhanced through the dynamical Kondo effect; further discussions of this point have been given by (Cai *et al.*, 2019; Si *et al.*, 2014).

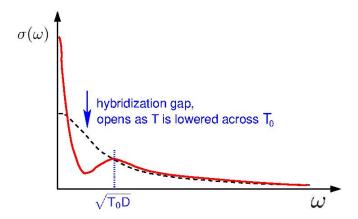


FIG. 3 Sketch of the optical conductivity $\sigma(\omega)$ for temperatures well above (dashed black line) and well below (continuous red line) the crossover temperature scale T_0 . Here the lowering of temperature through T_0 is accompanied by the onset of the hybridization gap. The characteristic frequency scale for the hybridization gap is $\sqrt{T_0D}$ (vertical dotted blue line), where D is an energy scale of the order of the conduction electron bandwidth. At low energies, i.e., for $\omega \ll T_0$ and $T \ll T_0$, and sufficiently far away from quantum criticality (i.e. $\delta < \delta_c$ or $\delta > \delta_c$), a pronounced Drude peak reflects the mass enhancement in the Fermi liquid regimes that surround the QCP in the phase diagram: see Fig. 2(a). The behavior of $\sigma(\omega)$ at high energies, including the hybridization gap, is a generic feature of heavy-electron systems and is seen throughout the high-energy part of the phase diagram of Fig. 2(a).

B. Isothermal evolution at low temperatures

The distinction between the two sides of δ_c can be sharply made at low temperatures, where well-defined quasiparticles reside at the small Fermi surface for $\delta < \delta_c$ and at the large Fermi surface for $\delta > \delta_c$. At zero temperature, a sudden reconstruction of the Fermi surface appears as δ passes through δ_c . At nonzero but low temperatures, this becomes a crossover. The crossover width increases with increasing temperature. When the crossover width becomes large, the difference between the two sides becomes ambiguous. We illustrate this point next, especially through the experiments carried out on YbRh₂Si₂.

C. Further considerations

In the Kondo destruction description, the *static* Kondo effect is suppressed in the antiferromagnetic phase at $\delta < \delta_c$. However, dynamical Kondo singlet correlations remain at nonzero frequencies in this regime. They lead to the development of 4f-electron spectral weight near the Fermi energy, which we refer to as Kondo resonance-like features. The dynamical Kondo effect [see Ref. (Cai et al., 2019)] as well as earlier discussions by (Si et al., 2014; Zhu et al., 2003) still produces a large mass en-

hancement and a small quasiparticle weight z_S : see Fig. 2(b). There is a small gap for the single-particle excitations at the wavevectors where the large Fermi surface would have developed.

The inelastic neutron scattering result on $\text{CeCu}_{6-x}\text{Au}_x$ $(x_c \approx 0.1)$ (Schröder et~al.,~2000) has been confirmed by the recent inelastic neutron scattering measurements (Poudel et~al.,~2019) in $\text{CeCu}_{6-x}\text{Ag}_x$ $(x_c \approx 0.2)$. When analyzing the data in terms of the one-component form, as arising in the Kondo destruction description, Ref. Poudel et~al.,~2019 found a similar form of ω/T scaling with a similar value for the critical exponent $\alpha = 0.73(1)$. Ref. Poudel et~al.,~2019 also analyzed the data in terms of a multicomponent spin fluctuation spectrum with one of the weaker components conforming to the expectation of an SDW QCP. However, thermodynamic singularities have provided evidence for the one-component description (Grube et~al.,~2017).

D. Summary of Sec. II

For heavy-electron metals, the Landau form of quantum criticality corresponds to an SDW QCP. A new type of quantum criticality has been advanced in the form of a Kondo destruction (local) QCP. It goes beyond the Landau framework in that the critical destruction of Kondo entanglement characterizes the physics beyond the slow fluctuations of the magnetic order parameter. The Kondo destruction is characterized by a new energy scale E^*_{loc} vanishing at the QCP as illustrated in Fig. 2(a); a sudden reconstruction from large to small Fermi surface as the system is tuned from the paramagnetic side through the QCP, along with a vanishing quasiparticle weight on approach of the QCP from both sides, as illustrated in Fig. 2(b).

III. ARPES, STM, AND THE SINGLE-PARTICLE GREEN'S FUNCTION

The unusual ω/T scaling of the dynamical spin susceptibility sets apart the QCP featuring critical Kondo destruction from the more traditional QCP based on the Landau framework of order-parameter fluctuations. It means that the dynamical susceptibility $\chi(\omega,T)$, in the regime where the critical singularities dominate, can be scaled to depend on ω or T only through the combination ω/T . Such scaling has been observed in $\text{CeCu}_{6-x}\text{Au}_x$ at its antiferromagnetic QCP (Schröder et al., 1998) and indicated for YbRh₂Si₂ (Friedemann et al., 2010). Recent measurements of the optical conductivity in thin films of YbRh₂Si₂ have demonstrated a singular response in the charge sector with an ω/T scaling (Prochaska et al., 2020). A scaling form of this kind for both the optical conductivity and dynamical spin susceptibility is strongly

suggestive of the presence of ω/T scaling in the single-particle excitations encoded in the single-particle Green's function.

A. The single-particle Green's function

This Green function can quite generally be cast into the form

$$G(\omega, \mathbf{k}, T) = \frac{1}{\omega - \varepsilon_{\mathbf{k}} - \Sigma(\omega, \mathbf{k}, T)},$$
 (2)

where $\varepsilon_{\mathbf{k}}$ is the bare electron dispersion and the proper self-energy $\Sigma(\omega, \mathbf{k}, T)$ encodes the effects of electron-electron interaction. In a Fermi liquid, this function can be decomposed into two parts,

$$G(\omega, \mathbf{k}, T) = G_{\text{coh}}(\omega, \mathbf{k}, T) + G_{\text{incoh}}(\omega, \mathbf{k}, T), \quad (3)$$

where the incoherent part is nonsingular close to the Fermi surface while the coherent part G_{coh} near E_F describes the quasiparticle contribution and assumes the form

$$G_{\text{coh}}(\omega, \mathbf{k}, T) = \frac{z}{\omega - v_F(k - k_F) + i\Gamma(\omega, T)}, \quad (4)$$

where z is the quasiparticle weight and v_F is the Fermi velocity. The lifetime of a quasiparticle is given by the inverse of the decay rate Γ . The amplitude of the static Kondo screening previously discussed is related to a pole in the self-energy, which in the Fermi liquid regime can at sufficiently low ω and T be written as

$$\Sigma(\omega, \mathbf{k}, T) = \frac{a}{\omega - b} + \delta \Sigma(\omega, \mathbf{k}, T), \tag{5}$$

where a and b are parameters that capture the strength of Kondo screening and the energy of the Kondo resonance, respectively. The pole in Σ shifts the Fermi momentum from its initial, "small" value to a new, "large" value as long as $a \neq 0$. In the SDW QCP case, $a \neq 0$ on either side of the critical point. For the local QCP, by contrast, Kondo screening is critically destroyed; correspondingly, on the antiferromagnetic side, a = 0 and the Fermi surface is small.

The Hall effect turns out to be a particularly useful quantity in this context as it is a measure of the carrier density on either side of the QCP. This is a consequence of the Fermi liquid nature of the two phases separated by the QCP, in which the Hall coefficient is completely determined by the renormalized dispersion of the single-particle excitations, to the leading order of elastic scattering (quenched disorder) when it is nearly isotropic. In other words, here, the Hall coefficient is independent of the quasiparticle weight z or any Landau parameters, regardless of the strength of electron-electron (and electron-phonon) interactions. This can be seen through

the kinetic equations of a Fermi liquid or using the Kubo formalism (Betbeder-Matibet and Nozières, 1966; Kohno and Yamada, 1988) and related Feynman diagrammatic means (Khodas and Finkel'stein, 2003).

The dynamical spin susceptibility $\chi(\omega, \mathbf{k}, T)$ and also the optical conductivity $\sigma(\omega, T)$ can be written as convolutions of the Green's function with itself and specific vertex functions. On the other hand, ARPES and STM measurements depend directly on $G(\omega, \mathbf{k}, T)$. Single-particle spectroscopies are thus, at least in principle, particularly useful in distinguishing between the two types of quantum criticality.

B. ARPES and STM

ARPES and STM measurements probe the singleparticle spectrum and thus give access to the spectral function $A(E, \mathbf{k}) = -(1/\pi) \text{Im} G(\omega = E + i0^+, \mathbf{k}, T)$. Although the single-particle Green's function appears in the theoretical description of ARPES and STM, both spectroscopic techniques are complementary. While ARPES directly probes the single-particle excitations as a function of energy and momentum, STM measures a conductance that is local in real space. Both methods are surface sensitive, albeit to different degrees. Furthermore, through variation of the photon energy, the bulk sensitivity of ARPES can be enhanced. By construction, ARPES probes only the occupied part of the single-particle excitation spectrum, which, especially at low temperatures, leads to a sharp cutoff at the Fermi energy (Hüfner, 2003). ARPES therefore measures only part of the full spectral function, i.e., the imaginary part of the retarded Green's function below the Fermi energy. A sketch of the spectral function of a Fermi liquid is shown in Fig. 4 (a). It consists of contributions from the quasiparticle pole and an incoherent background. The quasiparticle pole contributes a factor z to the total area beneath the spectral function, while the incoherent background contributes 1-z times the total area. z is commonly called the wave-function renormalization factor and it is inversely proportional to the quasiparticle mass in a Fermi liquid. The evolution of z with tuning parameter is plotted schematically in Fig. 2(b) where we see that zvanishes at a local QCP. The position of the quasiparticle pole as a function of momentum defines the disperion. Per se, ARPES is not able to distinguish between the quasiparticle peak and the incoherent part of the spectral function. Provided the energy and momentum resolution is not a limiting factor, however, the characteristic broadening $\delta \epsilon$ of the quasiparticle peak in energy ($\sim |E_{\mathbf{k}} - E_F|^2$, where $E_{\mathbf{k}}$ is the quasiparticle energy) and with temperature ($\sim T^2$) should be discernible in the momentum-distribution curves provided by ARPES. The weight of the quasiparticle peak, in principle, could also be extracted based on the total incoherent part. However, since ARPES probes only occupied states, the complete spectral function is inaccessible. Although inverse photoemission is in principle able to probe states above the Fermi energy, it is limited by rather poor energy resolution.

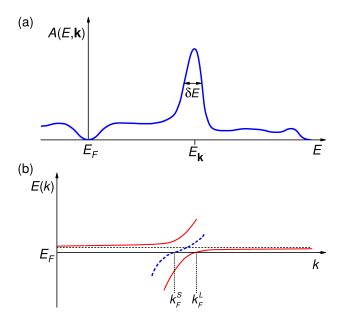


FIG. 4 Electronic characteristics of the Fermi liquid state of a Kondo lattice. (a) Spectral density of a Fermi liquid: The quasiparticle pole at ϵ_k has a characteristic width $\delta\epsilon$ that increases with the distance from the Fermi energy E_F as $\delta E \sim |E_{\bf k}-E_F|^2$. A similar broadening occurs due to finite-temperature effects. The incoherent part of $A(E,{\bf k})$ vanishes at E_F . (b) Quasiparticle dispersion in the Fermi liquid to either side of the QCP: k_F^L and k_F^S refer to large and small Fermi surfaces, respectively. Across a Kondo destruction QCP, the one-electron spectrum is gapless at k_F^L and develops a small gap at k_F^S for $\delta > \delta_c$, and the converse is valid for $\delta < \delta_c$. The flattening of the dispersion near k_F^S for $\delta < \delta_c$ (dashed blue curve) reflects the effective mass enhancement due to the dynamical Kondo effect.

In general, when interpreting ARPES spectra, one needs to keep in mind that in order to relate the photoemission intensity to the spectral function, the one-electron dipole matrix element enters, which generally is unknown. In addition, k_z broadening can be important, where k_z is the component of the electron momentum perpendicular to the surface and depends on the photon energy (Strocov, 2003; Wadati $et\ al.$, 2006).

STM, on the other hand, measures a local-in-real-space conductance. In the linear-response regime, the current-voltage characteristics are related to the local density of states (DOS) of the material under investigation (Bardeen, 1961; Tersoff and Hamann, 1985). Therefore, at low bias voltage and temperature, the spatially resolved spectral density can be obtained. As the applied bias voltage shifts the chemical potential at which the local density of states is probed, STM is, unlike ARPES,

not confined to only occupied states. It is, however, important to realize that the assumption that the spectral function is independent of the bias voltage has to break down at some sample-dependent value of the bias voltage beyond which the tunneling current can no longer be related to the local density of states. Moreover, the properties of the STM tip, e.g., its DOS, may affect the results.

C. Probing quantum criticality in the Kondo lattice

One of the strongest diagnostic tools to distinguish the local QCP from the SDW QCP is Hall conductivity measurements, as the local QCP manifests itself by a jump of the Hall coefficient across the QCP. This is a consequence of the Hall coefficient being inversely proportional to the carrier density (in the isotropic case or, in general, the curvatures of the quasiparticle dispersion on the Fermi surface) while being independent of the quasiparticle weight z in a Fermi liquid. The continuous nature of the local QCP is ensured by the vanishing of the quasiparticle weight from either side of the transition. For an SDW QCP, on the other hand, z will remain nonzero (except at isolated points on the Fermi surface) as δ is tuned through δ_c .

In a Kondo lattice at sufficiently high temperatures, where in first approximation the effect of the RKKY interaction can be ignored, the single-impurity Anderson model is expected to capture the overall physical behavior. This model is given by

$$H_{\text{AND}} = \sum_{\sigma} \varepsilon f_{\sigma}^{\dagger} f_{\sigma} + \sum_{\mathbf{k}, \sigma} \varepsilon_{\mathbf{k}} c_{\mathbf{k}, \sigma}^{\dagger} c_{\mathbf{k}, \sigma}$$

$$+ \frac{U}{2} \sum_{\sigma \neq \sigma'} f_{\sigma'}^{\dagger} f_{\sigma'}^{\dagger} f_{\sigma'} f_{\sigma} + \sum_{\mathbf{k}, \sigma} \left(V_{\mathbf{k}} f_{\sigma}^{\dagger} c_{\mathbf{k}, \sigma} + \text{h.c.} \right)$$
(6)

where f_{σ}^{\dagger} (f_{σ}) is the set of local 4f electron creation (destruction) operators of spin projection σ . The conduction electron operators are c_{σ}^{\dagger} and c_{σ} . The band structure of the conduction electrons is encoded in $\varepsilon_{\mathbf{k}}$, and the matrix element $V_{\mathbf{k}}$ that mixes 4f and c electrons is referred to as the hybridization. [For the case of the periodic Anderson model in the local-moment limit, with the 4f electron occupancy being close to unity, it reduces to the Kondolattice model given in Eq. (1) when the charge degrees of freedom of the 4f electrons are projected out (Schrieffer and Wolff, 1966; Zamani $et\ al.$, 2016a).]

STM spectra of single-site Kondo problems possess the structure of Fano resonances (Fano, 1961) and depend on the ratio of tunneling into the Kondo impurity vs tunneling into the embedding host. This ratio is encoded in the so-called Fano parameter. Rigorous derivations of the tunneling current and the form of the Fano parameter are given in (Plihal and Gradzuk, 2001; Schiller and Hershfield, 2000; Újsághy et al., 2000). If tunneling occurs predominantly into the conduction band the

measured local DOS features the suppression of conduction electron states near the Fermi energy as the Kondo effect develops. The first scanning tunneling studies of dense Kondo systems appeared about a decade ago (Aynajian et al., 2010; Ernst et al., 2010; Schmidt et al., 2010). The pronounced variation of STM spectra with the type of surface for Kondo lattice compounds is largely due to variations in the Fano parameter (see e.g., Fig. 10 for tunneling into differently terminated surfaces). This has been explicitly demonstrated based on mean field and dynamical mean field theory approximations for the Kondo lattice (Benlagra et al., 2011; Figgins and Morr, 2010; Maltseva et al., 2009; Wölfle et al., 2010). At sufficiently high temperatures, however, STM spectra in the vicinity of each Ce moment are expected to be similar to those for the single-ion Kondo case. Kondo screening is a predominantly local phenomenon and thus its onset and evolution are easily probed in real space, i.e., via STM. For a study of the single-particle Green's function in the paramagnetic Fermi liquid regime of the Kondo lattice far away from any QCP, in the context of photoemission, see Refs. (Costi and Manini, 2002; Reinert et al., 2001). ARPES measurements at similar temperatures. around and above the energy scale T_0 , provide the band structure $\varepsilon_{\mathbf{k}}$ of the occupied conduction electron states. A flat band near the 4f electron atomic level ε [see Eq. (6), which is far from the Fermi energy, and the formation of a flat band near the Fermi energy induced by the Kondo effect at each Ce moment reflect the 4f electron spectral weight. This can be enhanced using resonant ARPES, (Chen *et al.*, 2017).

At sufficiently low temperatures, in the Fermi liquid regime to either side of the QCP at δ_c [Fig. 2(a)], the band structure near the Fermi energy is shown in Fig. 4(b). For $\delta < \delta_c$, the small Fermi surface prevails and the band structure is that of the blue dashed line crossing the Fermi energy E_F at k_F^S . Still, incoherent spectral weight, a vestige of incomplete Kondo screening, develops but is ultimately gapped near k_F^L . For $\delta > \delta_c$, the Fermi surface incorporates the 4f moments and the Fermi wavevector changes from k_F^S at high temperatures (without the 4f moments) to k_F^L at low temperatures. On this side of the QCP, any spectral weight near k_F^S is due to incoherent single-particle excitations and is ultimately gapped. In other words, for $\delta > \delta_c$ in the Fermi liquid regime the spectral weight near the dashed blue line of Fig. 4(b) has developed a small gap at k_F^S . This should in principle be directly detectable via ARPES, provided the energy and momentum resolution are sufficiently high, and low enough temperatures can be reached.

On the other hand, the change k_F^S to k_F^L has only indirect vestiges in real space as the Fermi liquid is a momentum-space concept. The ensuing difficulties when tracing single-particle excitations in real space can already be read off from Fig. 4(b): The Fermi liquid is described by a low-energy effective theory and is valid

only in the vicinity of k_F . [The spectral function is a more general concept but it only assumes a form as illustrated in Fig. 4(a) in the Fermi liquid regime.] Fourier transforming the momentum-resolved spectral function to real space necessarily will sum up spectral weight outside of the Fermi liquid regime, where the characteristic form of broadening that identifies the quasiparticle peak is no longer valid.

One possible way forward is to perform quasiparticle interference (QPI) experiments to map out the band structure near the Fermi energy (Derry et al., 2015; Yazdani et al., 2016). We return to this possibility in Sec. VI. Another possible way is to perform isothermal STM measurements at low temperatures through the phase diagram connecting $\delta < \delta_c$ with $\delta > \delta_c$. While this by itself does not provide any direct information on the size of the Fermi surface, it was recently demonstrated that such a measurement is able to pick up the critical slowing down at the Kondo destruction energy scale (Seiro et al., 2018), as discussed in the next section (see Sec. IV).

D. Summary of Sec. III

The nature of quantum criticality in heavy-electron metals is manifested in the evolution of the single-particle excitations across the QCP. It is natural to probe this behavior using the ARPES and STM spectroscopies, given that they are an established means of studying single-particle excitations in metals. However, this task is challenging, mostly because heavy-electron systems have the distinction that the required energy scale is very low.

For ARPES, this requirement poses a challenge to access the quantum-critical behavior as is the limitation that even the state-of-the-art setups cannot yet reach temperatures below about 1 K. Still, ARPES should be informative in elucidating (i) the onset of a hybridization gap, which represents the high-energy physics for the quantum criticality of heavy-electron metals [see Fig. 2(a)]; and (ii) the evolution of the dynamical Kondo effect as temperature is lowered toward either the antiferromagnetic or paramagnetic ground state or the quantum-critical regime.

STM spectroscopy has superb energy resolution and can reach low temperatures, but more demanding setups (such as those suited for QPI) are needed to access the information in the momentum space. Still, STM probes the single-particle physics in a way that is complementary to ARPES. In addition, it provides a promising means to probe the isothermal evolution of single-particle excitations at low temperatures across the Kondo destruction energy scale.

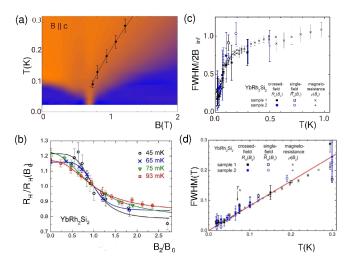


FIG. 5 Quantum criticality in YbRh₂Si₂. (a) The temperature vs field phase diagram of YbRh₂Si₂ The blue regions mark Fermi liquid behavior, i.e., $\rho(T) - \rho(0) \sim T^2$, while orange indicates the quantum-critical area of the phase diagram where $\rho(T) - \rho(0) \sim T^x$, with $x \approx 1$. The continuous line in the quantum-critical region is the E^* line as derived from thermodynamic and transport properties (Friedemann $et\ al.,\ 2010;$ Gegenwart $et\ al.,\ 2007;$ Paschen $et\ al.,\ 2004).$ Adapted from (Custers et al., 2003). (b) Normalized Hall coefficient across the critical field for different temperatures. The inverse of R_H is a measure of the carrier density. The lower T, the sharper is the crossover. At T=0 and $B=B_c$, a jump of R_H corresponds to the sudden localization of 4felectrons as B is taken trough B_c from above. From (Paschen et al., 2004). (c) Comparison between the isothermal magnetotransport crossover width and the crossover field as specified by the ratio of the FWHM/2 to the crossover inflection field B_{inf} . FWHM denotes the full width at half maximum. From (Paschen et al., 2016). (d) The "sharpness" of the crossover: The FWHM vanishes in a linear-in-T fashion indicating a jump of R_H at B_c in the zero-temperature limit. From (Friedemann et al., 2010).

IV. QUANTUM CRITICALITY IN YbRh₂Si₂

YbRh₂Si₂ is a prototype system for local quantum criticality as illustrated by its temperature (T)-magnetic field (B) phase diagram: see Fig. 5(a). Here the Fermi surface jump and the Kondo destruction energy scale have been extensively studied through magnetotransport and thermodynamic measurements. At a given temperature, the isothermal Hall coefficient [Fig. 5(b)] and other transport and thermodynamic quantities display a rapid crossover (Friedemann et al., 2010; Gegenwart et al., 2007; Paschen et al., 2004).

From these measurements, a $E^*(B)$ line is thus specified in the phase diagram. This line relates to each T a B^* scale: $B^*(T) \geq B_c$ with $B^*(T=0) = B_c$. The full-width at half-maximum (FWHM) of the crossover [Fig. 5(b)] extrapolates to zero in the zero-temperature limit [Fig. 5(d)], which implicates a jump of the Fermi surface across the QCP. It follows that, in the low-

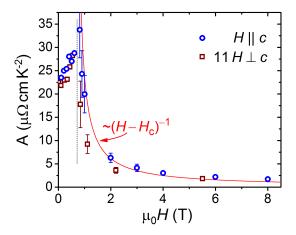



FIG. 6 Divergence of the T^2 coefficient A of the resistivity at the QCP in YbRh₂Si₂. Through the Kadowaki-Woods relation, this implies that the effective mass diverges on approach to the critical field $B_c = \mu_0 H_c$ from either side of the QCP. Data for $H \perp c$ have been scaled by a factor of 11. Adapted from Ref. (Gegenwart *et al.*, 2002).

temperature limit, at $B < B_c$, the Fermi surface is small.

On the non-magnetic side, $B > B_c$, the mass enhancement diverges as B approaches B_c from above. This has been established by measurements of both the T-linear specific-heat coefficient γ , which is proportional to the effective mass m^* , and the T^2 coefficient A of the resistivity, which was found to obey the Kadowaki-Woods relation (Tsujii $et\ al.$, 2005). The divergence of A is shown in Fig. 6.

For $B < B_c$, the mass enhancement is also large. This is compatible with the large C/T measured in the antiferromagnetic state, although to reliably extract γ is a challenge because of the interference of the large specificheat feature at the magnetic transition temperature T_N . The mass enhancement can be more reliably extracted from the A coefficient, because the effect of the magnetic transition at T_N on the resistivity is relatively minor. The evolution of the A coefficient with B is consistent with the destruction of the Kondo effect as the QCP is approached from the nonmagnetic side as well as the dynamical Kondo effect inside the antiferromagnetic phase.

The effect of increasing temperature on the Hall crossover can be quantified in terms of the ratio of the crossover width to the crossover magnetic field. For $T \gtrsim 0.5$ K, the ratio quickly increases toward unity as shown in Fig. 5(c). This implies that, for such temperatures, YbRh₂Si₂ falls in the quantum-critical fluctuation regime already for zero magnetic field. Thus, the single-particle spectral weight will be significant at both the small and large Fermi surfaces. In this temperature range, significant spectral weight is thus to be expected at the large Fermi surface. The ARPES measurements in YbRh₂Si₂, which have been reported for T > 1K (Kummer et al., 2015), are consistent with this prediction

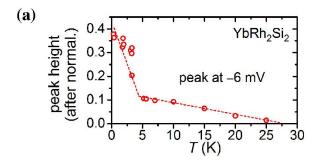

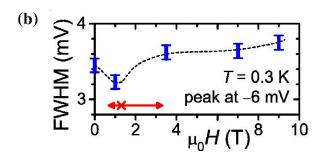


FIG. 7 STM spectroscopy of the lattice Kondo feature at 6meV in YbRh₂Si₂. (a) The temperature evolution of the peak height of the -6meV peak. A strong increase in the peak height is observed below 5K. (b) The FWHM of the -6meV peak across the critical field at the base temperature T=0.3K. Note that at this temperature all field values place the system within the quantum-critical fan. The decrease of the peak width near $B^*=\mu_0 H^*(T=0.3~{\rm K})$ is consistent with a critical slowing down at quantum criticality. From (Seiro et al., 2018).

(Paschen et al., 2016).

The temperature evolution of the single-particle excitations in YbRh₂Si₂ has been studied by STM measurements, which were first carried out down to 4.6 K by (Ernst et al., 2011) and were recently extended down to 0.3K (Seiro et al., 2018). The lattice Kondo effect has been identified with the feature at a particular bias, -6meV. The initial onset of this feature takes place near 25K, which corresponds to $T_0^{\rm en}$, an estimate of T_0 based on the spin entropy S and defined through $S(T_0^{\rm en}/2) = 0.4R \ln 2$, where R is the ideal gas constant: see Table I. At B = 0, the measurements down to T = 0.3K show an increase in the spectral weight: see Fig. 7(a). This is compatible with the dynamical Kondo effect at nonzero temperatures.

The STM experiments have also determined the isothermal B dependence of the peak width at the lowest measured temperature $T=0.3\mathrm{K}$. It shows a minimum near $B^*(T=0.3\mathrm{K})$ as shown in Fig. 7(b). This observation is consistent with a critical slowing down associated with the Kondo destruction energy scale that was implicated by magnetotransport and thermodynamic measurements (Friedemann et al., 2010; Gegenwart et al., 2007; Paschen et al., 2004). As such, it represents the

most direct evidence so far for the Kondo destruction quantum criticality based on a single-particle measurement in $YbRh_2Si_2$.

Summary of Sec. IV

We now summarize the salient results on YbRh₂Si₂ discussed in this section.

High-energy features: STM experiments for YbRh₂Si₂ at B=0 clearly observe the initial onset of dynamical Kondo correlations around T_0 , a comparatively high temperature, as expected for any Kondo lattice system regardless of the nature (Kondo screened or Kondo destruction) of its ground state. This is consistent with the observation of a hybridization gap in the optical spectrum (Kimura et al., 2006). As temperature is further lowered below T_0 , 4f electron spectral weight is expected to develop, and this has also been clearly observed.

Low-energy isotherms: STM experiments for YbRh₂Si₂ have been carried out as a function of magnetic field at T=0.3K. The Kondo lattice spectral peak shows a critical slowing-down feature at B^* , the Kondo destruction scale previously determined from magnetotransport and thermodynamic measurements. As such, the STM results are consistent with local quantum criticality.

V. THE CERIUM-BASED 115 FAMILY: PHOTOEMISSION VERSUS TUNNELING SPECTROSCOPY

The cerium-based 115 family is comprised of compounds $CeMIn_5$ where M = Co, Rh, or Ir. These compounds are stoichiometric and can be grown in a very clean form. All three compounds crystallize in the HoCoGa₅ structure type and thus possess tetragonal unit cells. Because of their proximity to quantum criticality, they have contributed considerably to a global understanding of quantum-critical heavy-electron materials (Park and Thompson, 2009; Si, 2006). While CeCoIn₅ and CeIrIn₅ under ambient conditions are lowtemperature superconductors, CeRhIn₅ is an antiferromagnet (Movshovich et al., 2001; Petrovic et al., 2001b). In addition, substituted variants, e.g., by Cd substitution on the In site or by substitution of Ce, have also been investigated; for a review, see (Thompson and Fisk, 2012).

A. CelrIn₅

CeIrIn₅ at ambient pressure is a heavy-electron superconductor with a transition temperature $T_c = 0.40$ K (Petrovic *et al.*, 2001a). After almost two decades of

study, the origin of superconductivity remains controversial, although there is growing support for a magnetically driven mechanism (Chen et~al.,~2015). In spite of this controversy, superconductivity in CeIrIn₅ has attracted recent attention because of its unusual strain tunability (Bachmann et~al.,~2019).

In contrast to CeCoIn_5 or even CeRhIn_5 , CeIrIn_5 has been comparatively less studied by STM and ARPES. Early ARPES studies led to different conclusions concerning the formation of 4f-derived flat bands (Fujimori et al., 2006, 2003). More recently, a high-resolution ARPES study by (Chen et al., 2018a) mapped out the full bandstructure of CeIrIn_5 . Interestingly, this study was able to resolve the complete fine structure of both the $4f_{5/2}^1$ and $4f_{7/2}^1$ peaks in the measured energy-distribution curves (EDCs) and momentum-distribution curves, which may be a reflection of the comparatively stronger 4f-c hybridization than in CeCoIn_5 (Chen et al., 2018a).


To the best of our knowledge, no scanning tunneling spectroscopy of $CeIrIn_5$ is available, apart from an STM investigation that focused on the structural properties of $CeIrIn_5$ surfaces (Ernst *et al.*, 2010; Wirth *et al.*, 2014). Our main focus in this section is therefore on $CeCoIn_5$ and $CeRhIn_5$.

B. CeCoIn₅

CeCoIn₅ has attracted interest not only for its comparatively high superconducting transition temperature $T_c \sim 2.3 \mathrm{K}$ but also for an overall phenomenology that resembles that of the underdoped cuprates.

The strong interest in CeCoIn₅ includes early photoemission studies which, however, have led to contradictory results concerning the localized versus itinerant nature of the 4f electrons (Koitzsch et al., 2008, 2013, 2009). Optical conductivity measurements of CeCoIn₅ show the existence of a hybridization gap at high energies which starts forming at comparatively high temperatures (Burch et al., 2007; Singley et al., 2002) and recent STM studies of CeCoIn₅ are in line with these findings (Allan et al., 2013; Aynajian et al., 2012; Zhou et al., 2013). de Haas-van Alphen (dHvA) studies performed at low temperatures indicate that the Fermi surface of CeCoIn₅ includes the 4f electrons and that therefore the Fermi surface of CeCoIn₅ is large (Settai et al., 2001; Shishido et al., 2002). This conclusion is further corroborated by band-structure calculations that treat the 4f electrons as fully itinerant (Haule et al., 2010).

CeCoIn₅ under ambient conditions is believed to be located close to an antiferromagnetic QCP of the SDW type and can be tuned to a quantum phase transition by applying a magnetic field (Ronning *et al.*, 2005; Singh *et al.*, 2007; Zaum *et al.*, 2011). The STM study by (Aynajian *et al.*, 2012) also reported an interesting energy-






FIG. 8 Temperature dependence of the resistivity ρ of CeCoIn₅. (a) $\rho(T)$ in the temperature range from 2.2 to 300K. ρ has a smooth maximum around $T_{\rm coh} \approx 40{\rm K}$; this temperature for the resistivity maximum is commonly referred to as the coherence temperature, which is a manifestation of T_0 defined earlier. (b) ρ (black continuous line) and the magnetic resistivity ρ_m (red continuous line) in a semilog plot for temperatures from 2 to 200K. $\rho_m(T)$ is defined as the difference between the resistivity of CeCoIn₅ and that of its nonmagnetic reference compound LaCoIn₅ at temperature T. The dashed line represents a linear law fit to $\rho_m(T)$ and shows that $\rho_m(T)$ is linear in T from T_c to approximately 20K.

over-temperature (ω/T) scaling of the local conductance of CeCoIn₅ which sets in around 60K. It is worth recalling that STM probes the single-particle response while the dynamical spin susceptibility measures the magnetic fluctuation spectrum. As ω/T scaling is not expected in the dynamical spin susceptibility at a QCP of the SDW type, the observation of dynamical scaling in the local conductance suggests that the SDW nature applies, at least at ambient conditions, only at asymptotically low energies. In any case, the observation of ω/T scaling does appear to be in line with the linear-in-temperature behavior of the resistivity below 20K (Petrovic et al., 2001b) as shown in Fig. 8. Further support in favor of such an ω/T scaling in CeCoIn₅ for the single-particle excitations near the Γ point has come from a recent high-resolution ARPES study (Chen et al., 2017).

The ARPES study by (Chen et al., 2017) reported the first 3D Fermi surface mapping of CeCoIn₅ and provided a measurement of the full band structure of this heavy-electron system. Because of the large temperature range of the study from 14 to 310K, Chen et al. were able to demonstrate that the formation of the 4f-derived flat band sets in at temperatures far above the coherence temperature. This finding is significant, although not entirely unexpected. It demonstrates not only the slow evolution of the Kondo screening process but also the likely role of a Kondo effect on the excited crystal field levels (Chen et al., 2017; Pal et al., 2019). These results contrast with a temperature-independent Fermi surface in YbRh₂Si₂ that was inferred from the stateof-the-art ARPES measurements in a temperature window from 1 to 100K (Kummer et al., 2015). An earlier laser-based ARPES study of YbRh₂Si₂ reported a Tdependent bandstructure below 100 K (Mo et al., 2012). In this regard, we note that (Chen et al., 2017) suggested that ARPES at temperatures larger than 100 K may be

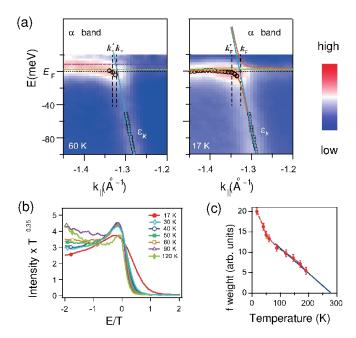


FIG. 9 ARPES view of the 4f electron weight near the Fermi energy in CeCoIn₅. (a) Evidence for the initial development of hybridization between 4f and conduction band α at T=60 and T=17K after dividing the EDCs by the Fermi-Dirac function. (b) ω/T scaling of the EDCs near the Γ point in an intermediate temperature range and energy range around the Fermi energy E_F . (c) Background subtracted 4f electron spectral weight transfer near the Γ point vs temperature. The EDCs have been integrated over an energy window from -40 to 2meV. (From (Chen et al., 2017)).

required in YbRh₂Si₂ due to the large effect of the crystal field levels. This is consistent with $T_0^{\rm hyb} \approx 160 {\rm K}$ in this compound; see Table I.

High-resolution ARPES results on CeCoIn₅ that are largely compatible with those of Chen et al. (Chen et al., 2017) have also been reported by Jang et al. (Jang et al., 2017). Although ARPES measurements on heavyelectron compounds have been a major experimental achievement, care has to be taken when extrapolating to the high-temperature region where the 4f electrons have to be localized across the phase diagram, as previously argued. In Fig. 9(a) we reproduced the EDCs from (Chen et al., 2017) for the α band, one of three bands that are part of the high-temperature Fermi surface, in the vicinity of its Fermi crossing for both T = 60 and T = 17K. The data have been divided by the Fermi-Dirac function to access the region (slightly) above the Fermi energy. The dashed lines in Fig. 9(a) indicate the positions of maxima of the main and the first excited crystal electric field-related Kondo resonancelike features, both of which are taken to be dispersionless. Here k_F is the Fermi momentum of the conduction electrons without 4f participation, i.e., at high temperatures.

In Fig. 9(c), the building up of spectral weight near the Fermi energy is shown as a function of temperature. This

is calculated by integrating the EDCs near the Fermi energy, i.e., from -40 to 2meV, and after subtracting a flat, temperature-independent overall background. It is worth recalling that the majority of the Kondo resonancelike features of a cerium-based system is located above the Fermi energy, a region which is, especially at low T, inaccessible to ARPES.

It is instructive to analyze the high-resolution ARPES data of Chen et al. for the temperature-dependent band structure of CeCoIn₅ in light of the expectation that the Fermi surface of this compound should contain the 4f electrons at sufficiently low temperatures. In other words, in terms of Fig. 2, CeCoIn₅ is located on the $\delta > \delta_c$ side of the $E^*_{\rm loc}$ line. Note, however, that Fig. 2 presents one type of specific cut through the global heavy-electron phase diagram (Si, 2006) ; its variant, with $E^*_{\rm loc}$ at δ_c being small but nonzero, is believed to describe CeCoIn₅.

The continuous red line in the right-hand panel of Fig. 9(a) is a fit of the data to the mean field expression for the single level, single band Anderson lattice model. The circles in Fig. 9(a) are obtained from the maximum in the EDCs and interpreted as the dispersion of the quasiparticle band. This leads to the value of k_F' , where k_F' is the projected zero-temperature Fermi momentum. Such a fit should not be taken too literally. As previously mentioned, mean field approaches may in principle be suitable to address the conduction bands at comparatively high energies and temperatures or the low-energy behavior on either the small or the large Fermi volume side in a limited energy range. They do, however, generically fail to describe the crossover from the high- to the lowenergy or temperature behavior. In addition, there is the general difficulty of constructing the correct mean field theory. The effective model for a system like CeCoIn₅ should not be the single level, single band Anderson lattice model. Nonetheless, the mean field construction provides an estimate for the change in the Fermi wave vector from its high-temperature value k_F to k'_F . If $k'_F = k_F$, the 4f electrons remain localized and do not contribute to the Fermi volume. As discussed and also briefly mentioned in (Chen et al., 2018b), if the Fermi surface of CeCoIn₅ expands from k_F to k_F' as the zero-temperature limit is approached, the bandstructure in the vicinity of E_F should resemble that sketched in Fig. 4(a) and the spectral weight close to k_F needs to vanish as $T \to 0$ so that the incoherent spectral weight at the Fermi energy is gapped out. The detection of such a, possibly very small, gap is challenging in view of the limited energy resolution and k_z broadening effects of ARPES experiments as discussed in Sec. III. Note that, although it is expected that $k_F' \neq k_F$ in CeCoIn₅, results shown in Fig. 9(a) are indicative of a spectral weight increase near and at k_F as the temperature is lowered from T=60to T = 17K. Most likely, this is more than just a reflection of the limited energy resolution of the measurement, and instead indicates that the single-particle excitations

are not of the Fermi liquid form depicted in Fig. 4(a). This is also corroborated by the strange metal behavior, encoded in an approximately linear-in-temperature dependence of the resistivity over a wide temperature window above the superconducting transition temperature $(T_c \sim 2.3 \text{K})$ (Petrovic et al., 2001b). In Fig. 8, the temperature dependence of the resistivity ρ of CeCoIn₅ is shown together with the magnetic resistivity, i.e., the difference between the resistivities of CeCoIn₅ and its nonmagnetic reference compound LaCoIn₅.

The ARPES study of (Chen et al., 2017) also indicated the presence of ω/T scaling in the EDCs near the Γ point in an intermediate temperature range. This is reproduced in Fig. 9(c). Already at around 90K, the EDCs multiplied by $T^{x_{EDC}}$ (with $x_{EDC} \approx 0.36$) collapse on a function depending only on ω/T . This, however, should not be interpreted as reflecting an ω/T scaling of all single-particle excitations, which would imply a strict linear-in-T behavior of the resistivity. Indeed, this scaling seems to be confined to the vicinity of the Γ point and is absent in the angle-integrated EDCs. Moreover, this peculiar scaling exists only in an intermediate T range and fails below 20K, as shown in Fig. 9(c). This conclusion appears to be compatible with the findings reported in (Aynajian et al., 2012), taking into account that tunneling into states with small lattice momenta is favored over tunneling into large-momentum states (Huang et al., 2015; da Silva Neto et al., 2013; Tersoff and Hamann, 1985). This demonstrates that ARPES and STM indeed provide information on the single-particle Green's function that can be directly compared to each other. It is, however, noteworthy that the temperature exponents accompanying this ω/T scaling in the intermediate temperature range from 20 to around 70K differ somewhat depending on the measurement technique. While the STM-derived exponent is $x_{STM} \approx 0.53$, the best fit of the ARPES data was obtained for $x_{EDC} \approx 0.36$. The difference between the ARPES and STM results is most

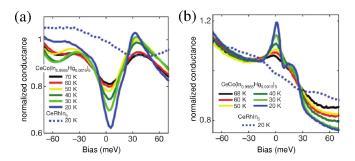


FIG. 10 Tunneling spectroscopy of CeCoIn₅ and CeRhIn₅: local conductance vs applied bias voltage for different temperatures on (a) Ce-terminated surfaces and (b) Co-(respectively, Rh-) terminated surfaces. The peak-dip-peak structure in conductance of CeCoIn₅ (a) is typical of a hybridization gap that is not obvious in CeRhIn₅, even at the lowest temperature. From (Aynajian $et\ al.$, 2012).

likely due to the dependence of the STM current on the degree of tunneling into 4f and c electron states. This dependence is encoded in the Fano parameter.

STM studies on CeCoIn₅ (and to a much lesser extent on CeRhIn₅ and CeIrIn₅) have been performed by several groups (Allan et al., 2013; Aynajian et al., 2012, 2014; Ernst et al., 2010; Haze et al., 2018; Zhou et al., 2013). In Figs. 10(a) and (b), results are shown for the local tunneling conductance of CeCoIn₅ very lightly doped with mercury (Hg) as well as CeRhIn₅ at different temperatures and on two different surfaces (Aynajian et al., 2012). The Hg-doping induced disorder in CeCoIn₅ generates impurity scattering at the dopant sites which in turn can be systematically used to obtain lattice momentum-resolved information of the local DOS through QPI (Derry et al., 2015). This use of QPI to extract the band structure near E_F in the low-temperature limit, however, also has potential shortcomings that were already alluded to in Sec. III.

C. CeRhIn₅

CeRhIn₅ is an antiferromagnet with a Néel temperature of $T_N=3.8\mathrm{K}$ at ambient pressure and has predominantly localized moments (Hegger et~al.,~2000). Under pressure, T_N can be suppressed to zero, thus tuning the system to a QCP at a critical pressure p_c . de Haasvan Alphen studies of CeRhIn₅ across the QCP display a clear jump of the dHvA frequencies at p_c , see Fig. 11(a), which implies that the Fermi surface changes discontinuously at the QCP (Shishido et~al.,~2005). This compound therefore likely hosts a Kondo destruction QCP at $\delta_c=p_c$ (δ was defined in Sec. II). This conclusion is further corroborated by an effective mass that tends to diverge on approach to p_c ; see Fig. 11(b). The latter re-

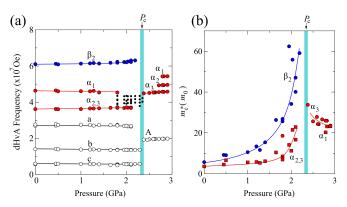


FIG. 11 de Haas-van Alphen measurements on CeRhIn₅. (a) Jump of the dHvA frequencies at p_c indicating a reconstruction of the Fermi surface as the QCP is crossed. (b) Diverging effective mass upon approaching p_c from above and below. Adapted from (Shishido *et al.*, 2005)

flects the vanishing of the wave-function renormalization factor z, depicted in Fig. 2(b), as the QCP is reached from either above or below p_c . In addition, transport measurements provide evidence for the Kondo destruction QCP (Park et al., 2006, 2008). These low-energy quantum-critical features are accompanied by experiments measuring high-energy properties. The optical conductivity of CeRhIn₅ was reported in (Mena et al., 2005) and shows the formation of a weak hybridization gap at high frequencies as temperature is lowered below the crossover scale T_0 .

Despite evidence for the existence of a QCP featuring critical reconstruction of the Fermi surface in CeRhIn₅ under pressure, APRES and STM investigations of this compound are comparatively rare. This is largely due to difficulties in preparing a suitable surface and to the present impossibility of making these measurements under applied pressure. Early nonresonant ARPES investigations of CeRhIn₅ reported that the 4f electrons in this compound are predominantly itinerant (Moore $et\ al.$, 2002), whereas a second nonresonant ARPES study argued that the 4f electrons are nearly localized (Fujimori $et\ al.$, 2003).

Scanning tunneling spectroscopy data on Ce- and Rhterminated surfaces of CeRhIn₅ show no clearly discernible Fano resonances, at least at around 20K (Aynajian et al., 2012), see Fig. 10(a) and (b). Interestingly, these results seem incompatible with high-resolution resonant ARPES data which point to the development of the 4f-electron spectral weight near the Fermi energy, although the weight transfer is much weaker than in CeCoIn₅; see Fig. 12 (Chen et al., 2018b). The spectral weight transfer depicted in Fig. 12 for the three bands crossing the Fermi surface also shows that, in the temperature range studied, spectral weight transfer occurs mainly near the γ band crossing. The difference between the ARPES measurements of (Chen et al., 2018b) and

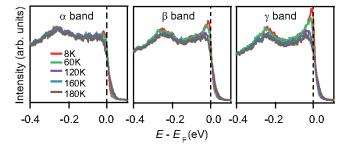


FIG. 12 EDCs of CeRhIn₅ vs temperature. The energy-distribution curves show the evolution of spectral weight with temperature near the Fermi energy E_F for the three bands that cross E_F , labeled α , β , and γ . Data were taken along the ΓM direction at $k_{\parallel} = -0.57 \mathring{A}^{-1}$ (α band), $k_{\parallel} = -0.3 \mathring{A}^{-1}$ (β band), and $k_{\parallel} = -0.124 \mathring{A}^{-1}$ (γ band) and with an uncertainty of $\delta k_{\parallel} \sim 0.03 \mathring{A}^{-1}$ for each of the three k_{\parallel} values. From (Chen et al., 2018b).

the STM investigation of (Aynajian et al., 2012) is likely due to the increased surface sensitivity of STM. One possibility is that the Kondo temperature at the surface is reduced due to the reduced hybridization; a second is that the cleaving process to obtain suitable surfaces appears to be more problematic for CeRhIn₅ and CeIrIn₅ than for CeCoIn₅. In fact, recent STM results (Haze et al., 2019) on epitaxially grown CeRhIn₅ with well-defined surfaces are very much in line with the ARPES measurements of (Chen et al., 2018b). As in the case of the STM images of YbRh₂Si₂ [see Fig. 7(a)], these data are consistent with the dynamical Kondo effect taking place near the small Fermi surface.

D. Further considerations

We now turn to several additional points that cut across specific Ce-115 families. First, the connection between the different Ce-115 families deserves further stud-As already discussed, isothermal dHvA measurements in CeRhIn₅ provide evidence for a sudden Fermi surface reconstruction at p_c . Intriguingly, frequencies of dominant α orbits at $p > p_c$ for CeRhIn₅ are very similar to those found for the large Fermi surface of $CeCoIn_5$ at atmospheric pressure (Shishido et al., 2005). No Fermisurface reconstruction was found in CeCoIn₅. It is possible that a sudden Fermi-surface reconstruction can still be found in CeCoIn₅ under a new tuning parameter, such as negative pressure. But it may also be that such an effect simply does not exist in CeCoIn₅, reflecting its inherent difference from CeRhIn₅. For example, the 4f-chybridization is much larger in CeCoIn₅ than in CeRhIn₅, as evident in their STM spectra; see Fig. 10. As argued recently, this difference in overall hybridization can be traced to an anisotropic spatial extent of their 4f orbitals that is set by details of the crystal electric field wavefunction (Sundermann et al., 2019; Willers et al., 2015).

Second, an alternative explanation for the jump of the dHvA measurements across p_c in CeRhIn₅ was proposed by (Watanabe and Miyake, 2010). It was suggested that the 4f-valence fluctuations lead to a rapid valence change near p_c and a strongly first order antiferromagnetic transition. The latter implies a large jump of the order parameter and, thus a large reconstruction of the Fermi surface. So far, however, all experimental evidence points to a continuous transition at p_c . In addition, canonical valence-fluctuating systems such as CeSn₃ (CePd₃) have specific-heat coefficients of 53 (37) mJ/(mol K²), and effective Kondo temperatures of 770 (1120) K (Lawrence et al., 1981). In those cases, the 4f-occupancy n_f will be far from 1 or 0 and, consequently, the entropy in the valence-fluctuation sector, which one can estimate by $R \left[n_f \ln n_f^{-1} + (1 - n_f) \ln (1 - n_f)^{-1} \right]$, will be a sizable fraction of $R \ln 2$. By contrast, in the quantumcritical regime of CeRhIn₅, the specific-heat coefficient is very large [$\gamma \approx 1.25 \text{ J/(mol K}^2)$] (Park and Thompson, 2009), implying that n_f is exceedingly close to 1. Thus, the valence-fluctuation sector will have a small entropy compared to the nearly $R \ln 2$ entropy in the spin sector and can hardly be the main driver of the critical fluctuations. In other words, the quantum criticality should primarily be driven by physics of the Kondo limit (Park et al., 2006, 2008). Similar arguments apply to CeCoIn₅, CeIrIn₅, YbRh₂Si₂, and CeCu_{5.9}Au_{0.1}.

E. Summary of Sec. V

We close this section by summarizing the status of ARPES and STM investigations in cerium-based 115 systems as discussed in this section.

By and large, the existing STM and ARPES results on the cerium-based 115 family are consistent with each other, given the requirements of surface quality and the associated difficulties. The recent high-resolution ARPES investigation of these 115 materials also shows that none of the three compounds follows the low-temperature band-structure expectations of a fully-coherent heavy-electron Fermi liquid, encoded in Fig. 4(a). This is in line with other measurements, in particular transport measurements, which suggest that none is in a Fermi liquid regime in the range where the ARPES measurements were made. Further, the limited energy resolution of state-of-the-art ARPES is still pos-

VI. PROGRESS, CHALLENGES, AND PROSPECTS

A. High-energy Kondo features

We have stressed that the initial onset of dynamical Kondo correlations or hybridization is expected, at the T_0 scale of Fig. 2, for all heavy-electron systems regardless of the nature of their ground states. This scale is evident in YbRh₂Si₂ by STM and optical conductivity [Fig. 13(b)]. Similarly, the formation of a hybridization gap was manifested in CeRhIn₅ by optical conductivity measurements (Mena et al., 2005), reproduced in Fig. 13(a), and, recently, by STM measurements (Haze et al., 2019). Also for CeCu₆, which is near a QCP that is accessed by introducing Au substitution for Cu, a hybridization gap has been observed in the optical conductivity, see Fig. 13(c) (Marabelli and Wachter, 1990). This captures the high-energy T_0 scale for the onset of hybridization-gap formation [Fig. 2(a)] and indeed evolves smoothly across the critical substitution $x_c = 0.1$ based on photoemission measurements (Klein et al., 2008). The T_0 scale is also evidenced by recent time-resolved measurements in the critical substitution range (Pal et al., 2019; Wetli et al., 2018). Here, a terahertz irradiation pumps the system ing a major challenge in the heavy-electron materials class in which the associated energy scales are typically very small.

High-energy features: Existing ARPES and STM investigations of the 115 members show the initial onset of dynamical Kondo correlations around the T_0 temperature scale [Fig. 2(a)] and the concomitant onset of hybridization-gap formation. This is in line with optical conductivity measurements on these compounds (Chen and Wang, 2016). Comparing ARPES and STM data for the same compound gives complementary results that are compatible with each other, and provide evidence for the existence of the hybridization-gap onset scale T_0 .

Low-energy features: Neither in $CeCoIn_5$ nor in $CeRhIn_5$ has ARPES been able to confirm unambiguously the existence of either k_F^L or k_F^S . While this may not be surprising due to the limited energy and momentum resolution currently available to ARPES, this finding is also compatible with the absence of Fermi liquid signatures in the investigated temperature range in these compounds; in this range, Fermi liquid signatures are absent as well in transport and thermodynamic properties. Isothermal measurements of dHvA have shown a sudden reconstruction of the Fermi surface across the pressure-induced QCP in $CeRhIn_5$, which provides strong evidence for a Kondo destruction QCP.

and disturbs the correlations between the local moments and conduction electrons. We can expect the underlying Kondo coupling to produce an initial echo at a time corresponding to $\hbar/(k_BT_0)$. Such a finite timescale is indeed observed both away from and at the QCP. Note that the Fermi liquid scale of CeCu₆ is 0.2K (see Table I), which is not accessible by current experiments done at temperatures above 1.5K. Nonetheless, it is conceivable that future experiments may probe not only the echo effect at $\hbar/(k_BT_0)$, but also the response in the scaling time regime much beyond $\hbar/(k_BT_0)$.

Table I compiles high-temperature and Fermi liquid energy scales of the heavy-electron compounds discussed in this Colloquium. This table lists both $T_0^{\rm hyb}$, the initial onset of the hybridization gap, and $T_0^{\rm en}$, based on the spin entropy S. These two high-energy scales can differ by as much as an order of magnitude, which is not too surprising given that the crossover of Kondo lattice systems from the high-temperature incoherent regime toward the low-temperature coherent, quantum critical, or ordered regime is rather broad. This crossover can be made even broader when the excited crystal field levels are involved. In practice, we propose to use

$$T_0 = \sqrt{T_0^{\text{hyb}} T_0^{\text{en}}} \tag{7}$$

as a measure of the crossover Kondo scale. Defined in

	$T_{ ext{FL}}(ext{K})$	$T_0^{\mathrm{hyb}}(\mathrm{K})$	$T_0^{\mathrm{en}}(\mathrm{K})$	Reference
YbRh ₂ Si ₂	0.07	~ 160	≈ 24	(Gegenwart et al., 2006; Kimura et al., 2006; Trovarelli et al., 2000)
$YbRh_2Si_2$	< 0.008 (LMT)	~ 160	≈ 24	(Gegenwart et al., 2006; Kimura et al., 2006; Taupin et al., 2015)
$(B=B_c, B c)$				
$YbRh_2Si_2$	0.135	~ 160	≈ 24	(Gegenwart et al., 2002, 2006; Kimura et al., 2006)
(B=2T, B c)				
$CeCoIn_5$	0.14	$\gtrsim 100$	≈ 25	(Mena et al., 2005; Paglione et al., 2007; Petrovic et al., 2001b)
	(B=6T)			
$CeRhIn_5$	< 0.15	$\gtrsim 60^{(\dagger)}$	≈ 10	(Chen et al., 2018b; Park et al., 2008; Park and Thompson, 2009)
	$p_c = 2.35 \text{GPa}, \mu_0 \text{H} = 10 \text{T}$			
$CeCu_6$	0.2	$\gtrsim 40$	≈ 4	(Amato et al., 1987; Fischer et al., 1987; Marabelli and Wachter, 1990)
$CeCu_{6-x}Au_x (x_c = 0.1)$	$< 0.02 \; (LMT)$	$\gtrsim 40$	≈ 4	(Fischer et al., 1987; Löhneysen et al., 1994; Marabelli and Wachter, 1990)

TABLE I Characteristic high- and low-temperature scales for several heavy-electron compounds located in the vicinity of quantum criticality. Here $T_{\rm FL}$ is a temperature scale below which the Landau Fermi liquid T^2 resistivity is observed. $T_0^{\rm hyb}$ is a "high temperature" estimate for the onset of the hybridization gap and is estimated from the optical conductivity $\sigma(\omega,T)$ (Figs. 3 and 13) with the exception of CeRhIn₅, where existing $\sigma(\omega,T)$ data indicate only that $8K < T_0^{\rm hyb} < 300K$ (Mena et al., 2005). $T_0^{\rm en}$ is a "low-temperature" estimate of T_0 based on the spin entropy S, using a procedure for the single-impurity Kondo model with constant conduction electron density of states (for which $T_0 = T_0^{\rm en} = T_K^0$): $S(T_0^{\rm en}/2) = 0.4R \ln 2 \approx 0.277R$, where R = 8314.5 mJ/(mol K) is the ideal gas constant. LMT designates the lowest measured temperature for the electrical resistivity ρ .

For YbRh₂Si₂ at the critical field, $T_{\rm FL}$ has been estimated from $\rho(T)$ and using the result that $\rho(T) \sim T$ down to the LMT of 8mK (Taupin *et al.*, 2015), making the listed value to be an upper bound. The hybridization gap onset in $\sigma(\omega)$ is assumed to be the same for $0 \le B \le 2$ T. Similarly, changes of $T_0^{\rm en}$ are assumed to be small for fields $0 \le B \le 2$ T, where the specific heat at around 20K is only weakly field dependent for $B \le 2T$ (Gegenwart *et al.*, 2006).

For CeRhIn₅, the QCP is located at $p_c = 2.35$ GPa and H_c with $\mu_0 H_c \lesssim 10$ T (Park et al., 2008).

^(†)This value for T_0^{hyb} has been estimated from the ARPES data of (Chen *et al.*, 2018b) for ambient conditions; see also Fig. 12. For $\text{CeCu}_{6-x}\text{Au}_{0.1}$, $\rho(T)$ is linear in T down to the LMT of 20mK; hence, the listed value is also an upper bound. The estimate of T_0^{hyb} in $\text{CeCu}_{6-x}\text{Au}_{0.1}$ is supported by the specific heat data of (Löhneysen *et al.*, 1994).

The references in this table are arranged such that in each row the first reference provides T_{FL} , the second contains estimates for T_0^{hyb} and the third provides results on the low-temperature (spin) entropy.

this way, we can infer from Table I that T_0 is $\sim 62 \mathrm{K}$ in YbRh₂Si₂, $\sim 50 \mathrm{K}$ in CeCoIn₅, $\gtrsim 25 \mathrm{K}$ in CeRhIn₅, and $\gtrsim 13 \mathrm{K}$ in CeCu₆.

B. Isothermal evolution at low temperatures

We discussed in Sec. II that, to assess the nature of quantum criticality (Kondo destruction versus SDW), the isothermal evolution of quasiparticle spectral weight at low temperatures is particularly informative. In YbRh₂Si₂, this was done through STM measurements as a function of magnetic field at T=0.3 K, and the results (Seiro et al., 2018) support the Kondo-destruction scale that had been inferred from magnetotransport and thermodynamic measurements (Friedemann et al., 2010; Gegenwart et al., 2007; Paschen et al., 2004). Further STM measurements at lower temperatures will clearly be instructive. Whether related STM studies can be carried out in 115 systems is at the present time unclear, because the QCP is realized at a relatively large pressure (CeRhIn₅) or possibly at negative pressure (CeCoIn₅ and

CeIrIn₅) (Pham *et al.*, 2006; Sidorov *et al.*, 2002). In these latter two cases, applying uniaxial tension might open the possibility of both ARPES and STM studies in a regime that would access their respective QCP. Similar isothermal studies by ARPES appear to be difficult, due to the low temperature that is needed, and also because ARPES cannot be performed in the presence of a magnetic field.

C. Outlook

As previously discussed (see Sec. III), STM is a real space probe and thus generally lacks momentum resolution. It is, however, possible to extract information on the band structure near the Fermi energy using Friedel oscillations that occur near defects (Petersen et al., 2000, 1998). Since STM is a surface probe, QPI provides only a projected band structure. Furthermore, the standard approach which is based on Born scattering is known to be insufficient in many cases (Toldin et al., 2013). This limitation notwithstanding, it will be instructive to ob-

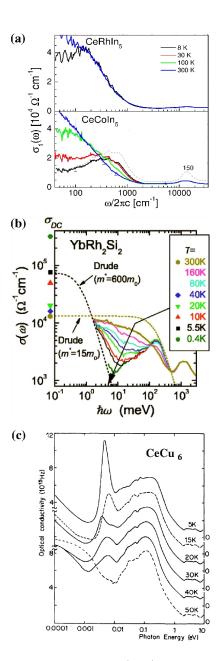


FIG. 13 Optical conductivity $\sigma(\omega, T)$ and evolution of the hybridization gap. (a) Although the hybridization gap in CeRhIn₅ (top) is overall less pronounced than that in the optical conductivity of CeCoIn₅ (bottom), the overall features for both compounds are in accordance with general expectations (see Fig. 3): at the highest measured T a broad Drude peak exists out of which a hybridization gap develops below $\sqrt{T_0D}$ as T is lowered. Adapted from (Mena et al., 2005). (b) The hybridization gap in YbRh₂Si₂ evolves over a large T region, starting well above 100K. As the data are taken at zero external field, the system is located on the $\delta < \delta_c$ side (see Sec. II) and a Drude peak is therefore expected in $\sigma(\omega, T)$ at small ω and sufficiently low T. From (Kimura et al., 2006). (c) In CeCu₆ the optical conductivity develops a hybridization gap at around $\hbar\omega \approx 1 \text{meV}$ below 50K which is flanked toward higher energies by a pronounced peak. From (Marabelli and Wachter, 1990).

tain band structure information through Fourier transform STM on either side of the QCP to interpret QPI spectra in the quantum-critical fan of the QCP.

Critical Kondo destruction is accompanied by a particular kind of ω/T scaling. Recently, this type of scaling was demonstrated for the optical conductivity of YbRh₂Si₂ thin films grown by molecular beam epitaxy, studied by time-domain THz-transmisson spectroscopy (Prochaska et al., 2020). This result would be surprising from the perspective of an SDW QCP, where only the spin dynamics is expected to be critical. However, it is in line with critical Kondo destruction (Prochaska et al., 2020). Because the magnetic quantum phase transition is accompanied by the transition from a phase with asymptotically decoupled local-moment and conduction electron degrees of freedom to one in which the entangling of the two turns the 4f local moments into composite quasiparticles, it is natural that both the single-particle and charge dynamics are critical. Indeed, calculations at the Kondo destruction QCP in various large-N limits (Cai et al., 2020; Kirchner et al., 2005; Komijani and Coleman, 2019; Zhu et al., 2004) and, more recently, in the physical N=2 case (Cai et al., 2020) have shown such a singular charge dynamics. Intriguingly, this type of charge dynamical scaling in models of the Kondo limit smoothly connects to the ω/T scaling for the charge dynamics in the beyond-Landau-type quantum criticality in the mixed-valence regime (Pixley et al., 2012).

Epitaxial thin films of members of the 115 family and CeIn₃ have been available for some time (Shishido et al., 2010) but STM measurements on these films of CeCoIn₅ and CeRhIn₅ have been reported only very recently (Haze et al., 2019, 2018). The observed onset of the hybridization gap in the STM spectrum demonstrates the high-energy T_0 scale which, as we have emphasized, is consistent with a Kondo destruction ground state in CeRhIn₅. It will be interesting to see whether a lattice mismatch between substrate and thin film might be used as a substitute for pressure tuning and to establish the range of ω/T scaling both within the general phase diagram and with respect to the type of correlator, i.e., single-particle excitations, two-particle correlators like the density-density, spin-spin, or current-current correlation functions, and their n-point (n > 4) counterparts.

We also briefly discussed in Sec. III that the underlying assumption in the interpretation of STM spectra in terms of the equilibrium local DOS is less justified at higher voltages. This may be particularly pertinent near the QCP, where the temperature of the measurement itself is expected to set the only relevant scale (Kirchner and Si, 2009). It would be interesting to explore the scaling of spectral density with bias voltage in the nonequilibrium regime which could be yet another way of unraveling the properties of the underlying QCP (Ribeiro et al., 2015; Zamani et al., 2016b).

We have so far focused on YbRh₂Si₂ and Ce-115 compounds. It will be instructive to carry out measurements of single-particle properties in other candidate heavy-electron materials for Kondo destruction (Gegenwart et al., 2008; Kirchner et al., 2013; Si and Paschen, 2013; Stewart, 2001). A case in point is CeNiAsO, a heavy-electron relative of the high- T_c Fe-based oxypnictides. Here the recent neutron scattering experiments provide evidence for a local-moment antiferromagnetic order, whose ordering wave vector is determined by the RKKY interaction mediated by the conduction electron states near the small Fermi surface (i.e., the Fermi surface of the conduction electrons alone, with the 4f electrons localized) (Wu et al., 2019), and transport measurements have suggested the possibility of a Kondo destruction QCP induced by either pressure or P-for-As doping (Luo et al., 2014).

More broadly, there is the question of where to look for new examples of Kondo destruction criticality. If the f-chybridization is too strong, magnetic order would more likely be of the SDW type that, when tuned to T=0, would result in a conventional QCP. Thus, weaker hybridization is expected to be a more favorable setting to access a possible Kondo destruction QCP. Alternatively, a low carrier density gives a small Fermi surface in a Kondo lattice and delays the full development of a Kondo singlet state with decreasing temperature. $CeNi_2As_{2-\delta}$ appears to be an example of such a case with evidence of Kondo-destruction quantum criticality (Luo et al., 2015). Finally, in the absence of tuning hybridization or carrier density, increasing frustration, whether through crystal structure or reduced dimensionality, offers an exciting opportunity for discovering new examples (Fritsch et al., 2014; Si, 2006; Tokiwa et al., 2015; Zhao et al., 2019).

VII. CONCLUSION

We have reviewed and compared recent ARPES and STM investigations on heavy-electron materials close to magnetic instabilities with a focus on Kondo destruction quantum criticality. Real-space and momentumspace spectroscopies combine the power of both methods (Crepaldi et al., 2013; Nicoara et al., 2006) which has proven to be useful in the study of complex materials such as the cuprate high-temperature superconductors (Markiewicz, 2004; Shen and Davis, 2008) and the Kondo insulator SmB₆ (Matt et al., 2018). In the context of cerium- and ytterbium-based rare earth intermetallics as well as actinide-based compounds, such a combination seems particularly promising given that much of the excitement and interest generated by these materials derives from the interplay of local and itinerant degrees of freedom. While Kondo screening is primarily a local phenomenon, a possible Fermi-volume increase is best addressed in momentum space. Method-specific

constraints, limited energy resolution and the need for very low temperatures in order to resolve a Fermi momentum change across a Kondo destruction quantum-critical point pose unique challenges to both ARPES and STM investigations.

On the other hand, combining ARPES and STM results with other measurements, like resistivity and magnetotransport measurements, neutron scattering and optical conductivity investigations, can provide a consistent picture of Kondo destruction quantum criticality that emerges as a function of some nonthermal tuning parameter and enables one to locate a specific compound in the general phase diagram of heavy-electron materials. This appears particularly relevant in the present context in order to aide a separation of bulk and surface contributions as both ARPES and STM are primarily surface sensitive. The change in symmetry and c-f hybridization that typically occurs at surfaces can in Kondo systems substantially modify low-energy scales as compared to their bulk value.

We have emphasized the distinction between the spectroscopic properties that reflect the high-energy Kondo physics, such as the formation of the hybridization gap, and those that are capable of probing the nature of quantum criticality, such as low-temperature isothermal measurements across the quantum-critical point. The latter has become possible in the STM measurements of YbRh₂Si₂, which corroborates the Kondo destruction energy scale that had been extracted by isothermal magnetotransport and thermodynamic measurements. In CeRhIn₅, strong evidence for Kondo destruction in the one-electron excitation spectrum has been provided by quantum oscillation measurements across the critical pressure. It will certainly be instructive to explore further signatures of beyond-Landau quantum criticality in these and other heavy-electron systems.

Acknowledgements

We are grateful to the late Elihu Abrahams, Jim Allen, Pegor Aynajian, Ang Cai, Kai Grube, Nigel Hussey, Kevin Ingersent, Johann Kroha, Hilbert von Löhneysen, Yuji Matsuda, Emilian Nica, Jed H. Pixley, Pedro Ribeiro, Rong Yu, Zuo-Dong Yu, Farzaneh Zamani, and Gertrud Zwicknagl for useful discussions. Part of these discussions took place at the 2018 Hangzhou Workshop on Quantum Matter and we thank all participants of the workshop. This work was in part supported by the National Key R&D Program of the MOST of China, Grant No. 2016YFA0300200 (S.K., Q.C., and D.F.), the National Science Foundation of China, No. 11774307 (S.K.), and No. 11874330 (Q.C.), and the Science Challenge Project, Grant No. TZ2016004 (D.F.). The work in Vienna was supported by the FWF (Project No. P 29296-N27) and the European Microkelvin Platform (H2020 Project No. 824109). The work at Los Alamos was performed under the auspices of the U.S. Department of Energy, Division of Materials Sciences and Engineering. The work at Rice was in part supported by the NSF (DMR-1920740) and the Robert A. Welch Foundation (C-1411). S.K. acknowledges support by MOST of Taiwan, Grant No. 108-2811-M-009-500 and hospitality of NCTU, Hsinchu. Donglai Feng is supported by the Anhui Initiative in Quantum Information Technologies. Q.S. acknowledges the hospitality and the support by a Ulam Scholarship from the Center for Nonlinear Studies at Los Alamos National Laboratory and the hospitality of the Aspen Center for Physics (NSF, PHY-1607611).

REFERENCES

- Allan, M. P., F. Massee, D. K. Morr, J. V. Dyke, A. W. Rost, A. P. Mackenzie, C. Petrovic, and J. C. Davis (2013), Nat. Phys. 9, 468.
- Amato, A., D. Jaccard, J. Flouquet, F. Lapierre, J. L. Tholence, R. A. Fisher, S. E. Lacy, J. A. Olsen, and N. E. Phillips (1987), J. Low Temp. Phys. 68, 371.
- Aronson, M. C., R. Osborn, R. A. Robinson, J. W. Lynn, R. Chau, C. L. Seaman, and M. B. Maple (1995), Phys. Rev. Lett. **75**, 725.
- Aynajian, P., E. H. da Silva Neto, A. Gyenis, R. E. Baumbach, J. D. Thompson, Z. Fisk, E. D. Bauer, and A. Yazdani (2012), Nature 486, 201.
- Aynajian, P., E. H. da Silva Neto, C. V. Parkera, Y. Huangb, A. Pasupathy, J. Mydosh, and A. Yazdani (2010), Proc. Natl. Acad. Sci. 107, 10383.
- Aynajian, P., E. H. da Silva Neto, B. B. Zhou, S. Misra, R. E. Baumbach, Z. Fisk, J. Mydosh, J. D. Thompson, E. D. Bauer, and A. Yazdani (2014), J. Phys. Soc. Jpn. 83, 061008.
- Bachmann, M. D., G. M. Ferguson, F. Theuss, T. Meng,
 C. Putzke, T. Helm, K. R. Shirer, Y.-S. Li, K. A. Modic,
 M. Nicklas, M. König, D. Low, S. Ghosh, A. P. Mackenzie,
 F. Arnold, E. Hassinger, R. D. McDonald, L. E. Winter,
 E. D. Bauer, F. Ronning, B. J. Ramshaw, K. C. Nowack,
 and P. J. W. Moll (2019), Science 366, 221.
- Bardeen, J. (1961), Phys. Rev. Lett. 6, 57.
- Benlagra, A., T. Pruschke, and M. Vojta (2011), Phys. Rev. B **84**, 195141.
- Betbeder-Matibet, O., and P. Nozières (1966), Ann. Physics 37, 17.
- Burch, K. S., S. V. Dordevic, F. P. Mena, A. B. Kuzmenko, D. van der Marel, J. L. Sarrao, J. R. Jeffries, E. D. Bauer, M. B. Maple, and D. N. Basov (2007), Phys. Rev. B 75, 054523.
- Cai, A., H. Hu, K. Ingersent, S. Paschen, and Q. Si (2019), "Dynamical Kondo effect and Kondo destruction in effective models for quantum-critical heavy fermion metals," ArXiv:1904.11471.
- Cai, A., Z. Yu, H. Hu, S. Kirchner, and Q. Si (2020), Phys. Rev. Lett. 124, 02705.
- Chen, Q. Y., C. H. P. Wen, Q. Yao, K. Huang, Z. F. Ding, L. Shu, X. H. Niu, Y. Zhang, X. C. Lai, Y. B. Huang, G. B. Zhang, S. Kirchner, and D. L. Feng (2018a), Phys. Rev. B 97, 075149.

- Chen, Q. Y., D. F. Xu, X. H. Niu, J. Jiang, R. Peng, H. C. Xu, C. H. P. Wen, Z. F. Ding, K. Huang, L. Shu, Y. J. Zhang, H. Lee, V. N. Strocov, M. Shi, F. Bisti, T. Schmitt, Y. B. Huang, P. Dudin, X. C. Lai, S. Kirchner, H. Q. Yuan, and D. L. Feng (2017), Phys. Rev. B 96, 045107.
- Chen, Q. Y., D. F. Xu, X. H. Niu, R. Peng, H. C. Xu, C. H. P.
 Wen, X. Liu, L. Shu, S. Y. Tan, X. C. Lai, Y. J. Zhang,
 H. Lee, V. N. Strocov, F. Bisti, P. Dudin, J.-X. Zhu, H. Q.
 Yuan, S. Kirchner, and D. L. Feng (2018b), Phys. Rev.
 Lett. 120, 066403.
- Chen, R. Y., and N. L. Wang (2016), Rep. Prog. Phys. 79, 064502.
- Chen, Y., W. B. Jiang, C. Y. Guo, F. Ronning, E. D. Bauer, T. Park, H. Q. Yuan, Z. Fisk, J. D. Thompson, and X. Lu (2015), Phys. Rev. Lett. 114, 146403.
- Coleman, P., C. Pépin, Q. Si, and R. Ramazashvili (2001), J. Phys. Condens. Matter 13, R723.
- Coleman, P., and A. J. Schofield (2005), Nature 433, 226.
- Cornut, B., and B. Coqblin (1972), Phys. Rev. B 5, 4541.
- Costi, T. A., and N. Manini (2002), J. Low Temp. Phys. **126**, 835
- Crepaldi, A., S. Pons, E. Frantzeskakis, F. Calleja, M. Etzkorn, A. P. Seitsonen, K. Kern, H. Brune, and M. Grioni (2013), Phys. Rev. B 87, 115138.
- Custers, J., P. Gegenwart, H. Wilhelm, K. Neumaier, Y. Tokiwa, O. Trovarelli, C. Geibel, F. Steglich, C. Pépin, and P. Coleman (2003), Nature 424, 524.
- Derry, P. G., A. K. Mitchell, and D. E. Logan (2015), Phys. Rev. B 92, 035126.
- Doniach, S. (1977), Physica B+C **91**, 231.
- Ernst, S., S. Kirchner, C. Krellner, C. Geibel, G. Zwicknagl, F. Steglich, and S. Wirth (2011), Nature 474, 362.
- Ernst, S., S. Wirth, F. Steglich, Z. Fisk, J. L. Sarrao, and J. D. Thompson (2010), Phys. Status Solidi B **247**, 624.
- Fano, U. (1961), Phys. Rev. **124**, 1866.
- Figgins, J., and D. K. Morr (2010), Phys. Rev. Lett. **104**, 187202.
- Fischer, H. E., E. T. Swartz, R. O. Pohl, B. A. Jones, J. W. Wilkins, and Z. Fisk (1987), Phys. Rev. B **36**, 5330.
- Fisk, Z., J. L. Smith, H. R. Ott, and B. Batlogg (1985), J. Magn. Magn. Mater 52, 79.
- Friedemann, S., N. Oeschler, C. Krellner, C. Geibel, F. Steglich, S. Paschen, S. Kirchner, and Q. Si (2010), Proc. Natl. Acad. Sci. USA 107, 14547.
- Fritsch, V., N. Bagrets, G. Goll, W. Kittler, M. J. Wolf, K. Grube, C.-L. Huang, and H. v. Löhneysen (2014), Phys. Rev. B 89, 054416.
- Fujimori, S.-i., A. Fujimori, K. Shimada, T. Narimura, K. Kobayashi, H. Namatame, M. Taniguchi, H. Harima, H. Shishido, S. Ikeda, D. Aoki, Y. Tokiwa, Y. Haga, and Y. Ōnuki (2006), Phys. Rev. B 73, 224517.
- Fujimori, S.-I., T. Okane, J.Okamoto, K. Mamiya, and Y. Muramatsu (2003), Phys. Rev. B 67, 144507.
- Gegenwart, P., J. Custers, C. Geibel, K. Neumaier, T. Tayama, K. Tenya, O. Trovarelli, and F. Steglich (2002), Phys. Rev. Lett. 89, 056402.
- Gegenwart, P., Q. Si, and F. Steglich (2008), Nat. Phys. 4, 186.
- Gegenwart, P., Y. Tokiwa, T. Westerkamp, F. Weickert, J. Custers, J. Ferstl, C. Krellner, C. Geibel, P. Kerschl, K.-H.Müller, and F. Steglich (2006), New J. Phys. 8, 171.
- Gegenwart, P., T. Westerkamp, C. Krellner, Y. Tokiwa, S. Paschen, C. Geibel, F. Steglich, E. Abrahams, and Q. Si (2007), Science 315, 969.

- Glossop, M., and K. Ingersent (2007), Phys. Rev. Lett. 99, 227203.
- Grempel, D. R., and Q. Si (2003), Phys. Rev. Lett. **91**, 026401.
- Grube, K., S. Zaum, O. Stockert, Q. Si, and H. v. Löhneysen (2017), Nat. Phys. 13, 742.
- Haule, K., C.-H. Yee, and K. Kim (2010), Phys. Rev. B 81, 195107.
- Haze, M., R. Peters, Y. Torii, T. Suematsu, D. S. M. Naritsuka, Y. Kasahara, T. Shibauchi, T. Terashima, and Y. Matsuda (2019), J. Phys. Soc. Jpn. 88, 014706.
- Haze, M., Y. Torii, R. Peters, S. Kasahara, Y. Kasahara, T. Shibauchi, T. Terashima, and Y. Matsuda (2018), J. Phys. Soc. Jpn. 87, 034702.
- Hegger, H., C. Petrovic, E. G. Moshopoulou, M. F. Hundley, J. L. Sarrao, Z. Fisk, and J. D. Thompson (2000), Phys. Rev. Lett. 84, 4986.
- Hertz, J. (1976), Phys. Rev. B 14, 1165.
- Hewson, A. C. (1993), The Kondo Problem to Heavy Fermions (Cambridge University Press, Cambridge).
- Huang, D., C.-L. Song, T. A. Webb, S. Fang, C.-Z. Chang, J. S. Moodera, E. Kaxiras, and J. E. Hoffman (2015), Phys. Rev. Lett. 115, 017002.
- Hüfner, S. (2003), Photoelectron Spectroscopy (Springer-Verlag Berlin Heidelberg).
- Jang, S., J. D. Denlinger, J. W. Allen, V. S. Zapf, M. B. Maple, J. N. Kim, B. G. Jang, and J. H. Shim (2017), "Evolution of the Kondo lattice electronic structure above the transport coherence temperature," ArXiv:1704.08247.
- Khodas, M., and A. M. Finkel'stein (2003), Phys. Rev. B 68, 155114.
- Kimura, S., J. Sichelschmidt, J. Ferstl, C. Krellner, C. Geibel, and F. Steglich (2006), Phys. Rev. B 74, 132408.
- Kirchner, S., and Q. Si (2009), Phys. Rev. Lett. 103, 206401.
 Kirchner, S., O. Stockert, S. Wirth, and (Eds.) (2013),
 "'Quantum Criticality and Novel Phases'," Phys. status solidi, vol. 250, special issue (3).
- Kirchner, S., L. Zhu, Q. Si, and D. Natelson (2005), Proc. Natl. Acad. Sci. USA 102, 18824.
- Klein, M., A. Nuber, F. Reinert, J. Kroha, O. Stockert, and H. v. Löhneysen (2008), Phys. Rev. Lett. 101, 266404.
- Kohno, H., and K. Yamada (1988), Prog. Theor. Phys. **80**, 623.
- Koitzsch, A., S. V. Borisenko, D. Inosov, J. Geck, V. B. Zabolotnyy, H. Shiozawa, M. Knupfer, J. Fink, B. Büchner, E. D. Bauer, J. L. Sarrao, and R. Follath (2008), Phys. Rev. B 77, 155128.
- Koitzsch, A., T. K. Kim, U. Treske, M. Knupfer, B. Büchner, M. Richter, I. Opahle, R. Follath, E. D. Bauer, and J. L. Sarrao (2013), Phys. Rev. B 88, 035124.
- Koitzsch, A., I. Opahle, S. Elgazzar, S. V. Borisenko, J. Geck, V. B. Zabolotnyy, D. Inosov, H. Shiozawa, M. Richter, M. Knupfer, J. Fink, B. Büchner, E. D. Bauer, J. L. Sarrao, and R. Follath (2009), Phys. Rev. B 79, 075104.
- Komijani, Y., and P. Coleman (2019), Phys. Rev. Lett. 122, 217001.
- Kroha, J., S. Kirchner, G. Sellier, P. Wölfle, D. Ehm, F. Reinert, S. Hüfner, and C. Geibel (2003), Physica E 18, 69.
- Kummer, K., S. Patil, A. Chikina, M. Güttler, M. Höppner,
 A. Generalov, S. Danzenbächer, S. Seiro, A. Hannaske,
 C. Krellner, Y. Kucherenko, M. Shi, M. Radovic, E. Rienks,
 G. Zwicknagl, K. Matho, J. W. Allen, C. Laubschat,
 C. Geibel, and D. V. Vyalikh (2015), Phys. Rev. X 5, 011028.

- Lawrence, J. M., P. S. Riseborough, and R. D. Parks (1981), Reports on Progress in Physics 44, 1.
- Lawrence, J. M., C. H. Wang, A. D. Christianson, and E. D. Bauer (2011), J. Phys. Condens. Matter 23, 094210.
- v. Löhneysen, H., A. Rosch, M. Vojta, and P. Wölfle (2007), Rev. Mod. Phys. **79**, 1015.
- Löhneysen, H. v., T. Pietrus, G. Portisch, H. G. Schlager, A. Schröder, M. Sieck, and T. Trappmann (1994), Phys. Rev. Lett. 72, 3262.
- Luo, Y., L. Pourovskii, S. E. Rowley, Y. Li, C. Feng, A. Georges, J. Dai, G. Cao, Z. Xu, Q. Si, and N. P. Ong (2014), Nat. Mater. 13, 777.
- Luo, Y., F. Ronning, N. Wakeham, X. Lu, T. Park, Z.-A. Xu, and J. D. Thompson (2015), Proc. Natl. Acad. Sci. USA 112, 13520.
- Maltseva, M., M. Dzero, and P. Coleman (2009), Phys. Rev. Lett. 103, 206402.
- Marabelli, F., and P. Wachter (1990), Phys. Rev. B **42**, 3307. Markiewicz, R. S. (2004), Phys. Rev. B **69**, 214517.
- Matt, C. E., H. Pirie, A. Soumyanarayanan, M. M, Yee, Y. He, D. T. Larson, W. S. Paz, J. Palacios, M. Hamidian, and J. E. Hoffman (2018), "Consistency between ARPES and STM measurements on SmB₆," accepted for publication in Phys. Rev. B and ArXiv:1810.13442.
- Mena, F. P., D. van der Marel, and J. L. Sarrao (2005), Phys. Rev. B 72, 045119.
- Millis, A. J. (1993), Phys. Rev. B 48, 7183.
- Mo, S.-K., W. S. Lee, F. Schmitt, Y. L. Chen, D. H. Lu, C. Capan, D. J. Kim, Z. Fisk, C.-Q. Zhang, Z. Hussain, and Z.-X. Shen (2012), Phys. Rev. B 85, 241103(R).
- Moore, D. P., T. Durakiewicz, J. J. Joyce, A. J. Arko, L. A. Moralesa, J. L. Sarrao, P. G. Pagliuso, J. M. Wills, and C. G. Olson (2002), Physica B **312-313**, 134.
- Moriya, T. (1985), Spin Fluctuations in Itinerant Electron Magnetism (Springer, Berlin).
- Movshovich, R., M. Jaime, J. D. Thompson, C. Petrovic, Z. Fisk, P. G. Pagliuso, and J. L. Sarrao (2001), Phys. Rev. Lett. 86, 5152.
- Nicoara, N., E. Román, J. M. Gómez-Rodriguez, J. A. Martin-Gago, and J. Méndez (2006), Organic Electr. 7, 287.
- Paglione, J., T. A. Sayles, P.-C. Ho, J. R. Jeffries, and M. B. Maple (2007), Nat. Phys. 3, 703.
- Pal, S., C. Wetli, F. Zamani, O. Stockert, H. v. Löhneysen, M. Fiebig, and J. Kroha (2019), Phys. Rev. Lett. 122, 096401.
- Park, T., F. Ronning, H. Q. Yuan, M. B. Salamon, R. Movshovich, J. L. Sarrao, and J. D. Thompson (2006), Nature 440, 65.
- Park, T., V. A. Sidorov, F. Ronning, J.-X. Zhu, Y. Tokiwa, H. Lee, E. D. Bauer, R. Movshovich, J. L. Sarrao, and J. D. Thompson (2008), Nature 456, 366.
- Park, T., and J. D. Thompson (2009), New. J. Phys. 11, 055062.
- Paschen, S., S. Friedemann, S. Wirth, F. Steglich, S. Kirchner, and Q. Si (2016), J. Magn. Magn. Mater. 400, 17.
- Paschen, S., T. Lühmann, S. Wirth, P. Gegenwart, O. Trovarelli, C. Geibel, F. Steglich, P. Coleman, and Q. Si (2004), Nature 432, 881.
- Pépin, C. (2007), Phys. Rev. Lett. 98, 206401.
- Petersen, L., P. Hofmann, E. Plummer, and F. Besenbacher (2000), J. Electron Spectros. and Relat. Phenom. **109**, 97.
- Petersen, L., P. T. Sprunger, P. Hofmann, E. Lægsgaard, B. G. Briner, M. Doering, H.-P. Rust, A. M. Bradshaw,

- F. Besenbacher, and E. W. Plummer (1998), Phys. Rev. B 57, 6858(R).
- Petrovic, C., R. Movshovich, M. Jaime, P. G. Pagliuso, M. F. Hundley, J. L. Sarrao, Z. Fisk, and J. D. Thompson (2001a), Europhys. Lett. **53**, 354.
- Petrovic, C., P. G. Pagliuso, M. F. Hundley, R. Movshovich, J. L. Sarrao, J. D. Thompson, Z. Fisk, and P. Monthoux (2001b), J. Phys. Condens. Matter 13, L337.
- Pfau, H., S. Hartmann, U. Stockert, P. Sun, S. Lausberg, M. Brando, S. Friedemann, C. Krellner, C. Geibel, S. Wirth, S. Kirchner, E. Abrahams, Q. Si, and F. Steglich (2012), Nature 484, 493.
- Pham, L. D., T. Park, S. Maquilon, J. D. Thompson, and Z. Fisk (2006), Phys. Rev. Lett. 97, 056404.
- Pixley, J. H., S. Kirchner, K. Ingersent, and Q. Si (2012), Phys. Rev. Lett. 109, 086403.
- Plihal, M., and J. W. Gradzuk (2001), Phys. Rev. B 63, 085404.
- Poudel, L., J. M. Lawrence, L. S. Wu, G. Ehlers, Y. Qiu, A. F. May, F. Ronning, M. D. Lumsden, D. Mandrus, and A. D. Christianson (2019), npj Quantum Materials 4, 52.
- Prochaska, L., X. Li, D. C. MacFarland, A. M. Andrews, M. Bonta, E. F. Bianco, S. Yazdi, W. Schrenk, H. Detz, A. Limbeck, Q. Si, E. Ringe, G. Strasser, J. Kono, and S. Paschen (2020), Science 367, 285.
- Reinert, F., D. Ehm, S. Schmidt, G. Nicolay, S. Hüfner, J. Kroha, O. Trovarelli, and C. Geibel (2001), Phys. Rev. Lett. 87, 106401.
- Ribeiro, P., F. Zamani, and S. Kirchner (2015), Phys. Rev. Lett. **115**, 220602.
- Ronning, F., C. Capan, A. Bianchi, R. Movshovich, A. Lacerda, M. F. Hundley, J. D. Thompson, P. G. Pagliuso, and J. L. Sarrao (2005), Phys. Rev. B 71, 104528.
- Sachdev, S. (1999), Quantum Phase Transitions (Cambridge University Press, Cambridge).
- Schiller, A., and S. Hershfield (2000), Phys. Rev. B 61, 9036.
 Schmidt, A. R., M. H. Hamidian, P. Wahl, F. Meier, A. V. Balatsky, J. D. Garrett, T. J. Williams, G. M. Luke, and J. C. Davis (2010), Nature 465, 570.
- Schrieffer, J. R., and P. A. Wolff (1966), Phys. Rev. **149**, 491
- Schröder, A., G. Aeppli, E. Bucher, R. Ramazashvili, and P. Coleman (1998), Phys. Rev. Lett. 80, 5623.
- Schröder, A., G. Aeppli, R. Coldea, M. Adams, O. Stockert, H. v. Löhneysen, E. Bucher, R. Ramazashvili, and P. Coleman (2000), Nature 407, 351.
- Seiro, S., L. Jiao, S. Kirchner, S. Hartmann, S. Friedemann, C. Krellner, C. Geibel, Q. Si, F. Steglich, and S. Wirth (2018), Nat. Commun. 9, 3324.
- Senthil, T., M. Vojta, and S. Sachdev (2004), Phys. Rev. B 69, 035111.
- Settai, R., H. Shishido, S. Ikeda, Y. Murakawa, M. Nakashima, D. Aoki, Y. Haga, H. Harima, and Y. Onuki (2001), J. Phys. Condens. Matter 13, L627.
- Shen, K. M., and J. S. Davis (2008), Materials Today 11, 14.
 Shishido, H., R. Settai, D. Aoki, S. Ikeda, H. Nakawaki,
 N. Nakamura, T. Iizuka, Y. Inada, K. Sugiyama,
 T. Takeuchi, K. Kindo, T. C. Kobayashi, Y. Haga,
 H. Harima, Y. Aoki, T. Namiki, H. Sato, and Y. Ōnuki
 (2002), J. Phys. Soc. Jpn. 71, 162.
- Shishido, H., R. Settai, H. Harima, and Y. Ōnuki (2005), J. Phys. Soc. Jpn. 74, 1103.
- Shishido, H., T. Shibauchi, K. Yasu, T. Kato, H. Kontani, T. Terashima, and Y. Matsuda (2010), Science **327**, 980.

- Si, Q. (2006), Physica B: Condens. Matter 378-380, 23.
- Si, Q., and S. Paschen (2013), Phys. Status Solidi B 250, 425.
- Si, Q., J. H. Pixley, E. Nica, S. J. Yamamoto, P. Goswami, R. Yu, and S. Kirchner (2014), J. Phys. Soc. Jpn. 83, 061005.
- Si, Q., S. Rabello, K. Ingersent, and J. Smith (2001), Nature **413**, 804.
- Si, Q., and F. Steglich (2010), Science **329**, 1161.
- Si, Q., J.-X. Zhu, and D. R. Grempel (2005), J. Phys. Condens. Matter 17, R1025.
- Sidorov, V. A., M. Nicklas, P. G. Pagliuso, J. L. Sarrao, Y. Bang, A. V. Balatsky, and J. D. Thompson (2002), Phys. Rev. Lett. 89, 157004.
- da Silva Neto, E. H., P. Aynajian, R. E. Baumbach, E. D. Bauer, J. Mydosh, S. Ono, and A. Yazdani (2013), Phys. Rev. B 87, 161117.
- Singh, S., C. Capan, M. Nicklas, M. Rams, A. Gladun, H. Lee, J. F. DiTusa, Z. Fisk, F. Steglich, and S. Wirth (2007), Phys. Rev. Lett. 98, 057001.
- Singley, E. J., D. N. Basov, E. D. Bauer, and M. B. Maple (2002), Phys. Rev. B **65**, 161101(R).
- Stewart, G. R. (2001), Rev. Mod. Phys. 73, 797.
- Stockert, O., S. Kirchner, F. Steglich, and Q. Si (2012), J. Phys. Soc. Jpn. 81, 011001.
- Strocov, V. (2003), J. Electron Spectrosc. Relat. Phenom. 130, 65.
- Sundermann, M., A. Amorese, F. Strigari, B. Leedahl, L. H. Tjeng, M. W. Haverkort, H. Gretarsson, H. Yavaş, M. M. Sala, E. D. Bauer, P. F. S. Rosa, J. D. Thompson, and A. Severing (2019), Phys. Rev. B 99, 235143.
- Taupin, M., G. Knebel, T. D. Matsuda, G. Lapertot, Y. Machida, K. Izawa, J.-P. Brison, and J. Flouquet (2015), Phys. Rev. Lett. 115, 046402.
- Tersoff, J., and D. R. Hamann (1985), Phys. Rev. B 31, 805.Thompson, J. D., and Z. Fisk (2012), J. Phys. Soc. Jpn. 81, 011002
- Tokiwa, Y., C. Stingl, M.-S. Kim, T. Takabatake, and P. Gegenwart (2015), Science Adv. 1.
- Toldin, F. P., J. Figgins, S. Kirchner, and D. K. Morr (2013), Phys. Rev. B 88, 081101(R).
- Trovarelli, O., C. Geibel, S. Mederle, C. Langhammer, F. M. Grosche, P. Gegenwart, M. Lang, G. Sparn, and F. Steglich (2000), Phys. Rev. Lett. 85, 626.
- Tsujii, N., H. Kontani, and K. Yoshimura (2005), Phys. Rev. Lett. 94, 057201.
- Újsághy, O., J. Kroha, L. Szunyogh, and A. Zawadowski (2000), Phys. Rev. Lett. 85, 2557.
- Wadati, H., T. Yoshida, A. Chikamatsu, H. Kumigashira, M. Oshima, H. Eisaki, Z.-X. Shen, T. Mizokawa, and A. Fujimori (2006), Phase Transitions 79, 617.
- Watanabe, S., and K. Miyake (2010), J. Phys. Soc. Jpn. **79**, 033707.
- Wetli, C., S. Pal, J. Kroha, K. Kliemt, C. Krellner, O. Stockert, H. v. Löhneysen, and M. Fiebig (2018), Nat. Phys. 14, 1103.
- Willers, T., F. Strigari, Z. Hu, V. Sessi, N. B. Brookes, E. D. Bauer, J. L. Sarrao, J. D. Thompson, A. Tanaka, S. Wirth, L. H. Tjeng, and A. Severing (2015), Proc. Natl. Acad. Sci. USA 112, 2384.
- Wirth, S., Y. Prots, M. Wedel, S. Ernst, S. Kirchner, Z. Fisk, J. D. Thompson, F. Steglich, and Y. Grin (2014), J. Phys. Soc. Jpn. 83, 061009.

- Wölfle, P., Y. Dubi, and A. V. Balatsky (2010), Phys. Rev. Lett. 105, 246401.
- Wu, S., W. A. Phelan, L. Liu, J. R. Morey, J. A. Tutmaher,
 J. C. Neuefeind, A. Huq, M. B. Stone, M. Feygenson, D. W.
 Tam, B. A. Frandsen, B. Trump, C. Wan, S. R. Dunsiger,
 T. M. McQueen, Y. J. Uemura, and C. L. Broholm (2019),
 Phys. Rev. Lett. 122, 197203.
- Yazdani, A., E. H. da Silva Neto, and P. Aynajian (2016), Annual Review of Condensed Matter Physics 7, 11.
- Zamani, F., P. Ribeiro, and S. Kirchner (2016a), New J. Phys. 18, 063024.
- Zamani, F., P. Ribeiro, and S. Kirchner (2016b), J. Magn. Magn. 400, 7.
- Zaum, S., K. Grube, R. Schäfer, E. D. Bauer, J. D. Thompson, and H. v. Löhneysen (2011), Phys. Rev. Lett. 106,

- 087003.
- Zhao, H., J. Zhang, M. Lyu, S. Bachus, Y. Tokiwa, P. Gegenwart, S. Zhang, J. Cheng, Y.-f. Yang, G. Chen, Y. Isikawa, Q. Si, F. Steglich, and P. Sun (2019), Nat. Phys. 15, 1261.
- Zhou, B. B., S. Misra, E. H. da Silva Neto, P. Aynajian, R. E. Baumbach, J. D. Thompson, E. D. Bauer, and A. Yazdani (2013), Nat. Phys. 9, 474.
- Zhu, J.-X., D. R. Grempel, and Q. Si (2003), Phys. Rev. Lett. **91**, 156404.
- Zhu, J.-X., S. Kirchner, R. Bulla, and Q. Si (2007), Phys. Rev. Lett. 99, 227204.
- Zhu, L., S. Kirchner, Q. Si, and A. Georges (2004), Phys. Rev. Lett. 93, 267201.