

Turbulence-assisted formation of bacterial cellulose

Sung-Ha Hong, Jia Yang, Mahdi Davoodianidalik, Horst Punzmann, Michael Shats and Hua Xia^{1, a)}
Research School of Physics, The Australian National University, Canberra ACT 2601, Australia

(Dated: 26 March 2025)

Bacterial cellulose is an important class of biomaterials which can be grown in well-controlled laboratory and industrial conditions. The cellulose structure is affected by several biological, chemical and environmental factors, including hydrodynamic flows in bacterial suspensions. Turbulent flows leading to random motion of fluid elements may affect the structure of the extracellular polymeric matrix produced by bacteria. Here we show that two-dimensional turbulence at the air-liquid interface generates chaotic rotation at a well-defined scale and random persistent stretching of the fluid elements. This leads to a remarkable change in the structure of the bacterial cellulose morphology and to the formation of spherical cellulose beads whose size is controlled by the turbulence forcing scale. In addition, turbulence affects the cellulose microstructure, including the porosity of the material, by random but persistent stretching of the fluid elements. The results offer new approaches to engineering of the bacterial cellulose structure by controlling turbulence parameters.

I. INTRODUCTION

Bacterial biofilms represent the most abundant form of life on Earth¹. Microorganisms form extracellular polymeric matrices in a fluid environment, typically at the liquid-air, liquid-liquid and liquid-solid interfaces. Some of the biofilms, such as the bacterial cellulose (BC)^{2,3}, are valuable biomaterials with great industrial and medical potential^{4–6}. The BC is produced by various bacteria, for example, by the genera *Acetobacter*, *Acanthamoeba*, and *Achromobacter*, at the liquid-air interface in a variety of forms, such as cellulose sheets⁷, or spherical cellulose beads (SCB)⁸. The SCB is a desired cellulose form in many applications^{9–11}. Spherical beads make perfect delivery vehicles for many functional materials, such as graphene, magnetic and conducting metal particles and other chemical compounds which can be encapsulated into BC spheres^{12,13}.

An attractive feature of the BC is the possibility to create cellulose with a desired fibre structure at both macroscopic and nanoscopic scales in the process of the material formation, rather than using post-production treatment methods. Along with chemical and biological processes which affect the biofilm development, hydrodynamic flows in bacterial suspensions are also capable of shaping biofilms¹⁴. It has been recently demonstrated that when suspensions of *E. coli* are perturbed by surface waves, patterned biofilms at the liquid-solid interface are developed¹⁵.

Surface waves can form ordered patterns, but they can also lead to the generation of turbulent flows at the air-liquid interfaces^{16–18}. Such flows were shown to be very similar to quasi-two-dimensional (2D) turbulence which can be generated in laboratory^{19–21}. Turbulence greatly enhances particle dispersion^{22–24}. Thus, it can significantly affect the growth of the extracellular polymeric matrix during the biofilm development and can change

the resulting structure of the cellulose. Since the wave-driven fluid motion decays in the bulk of the liquid^{25,26}, turbulent motion is the strongest in a relatively thin layer (a fraction of the wavelength) near the liquid-air interface. The BC produced at the air-liquid interfaces is particularly suitable to test this idea. Since the microorganisms forming the BC typically are not motile, flows in bacterial suspensions should not be affected by the motion of bacteria, as it occurs in suspensions of fast swimming micro-swimmers which can generate turbulence themselves²⁷.

Turbulence is a strongly non-equilibrium state of a flow characterised by broad kinetic energy spectra and enhanced dispersion of fluid particles²⁸. Finite-size particles in turbulence experience random walk while they are also exposed to random torques causing rotational diffusion²⁹. At small scales, the rotational diffusion coefficient associated with the Brownian motion strongly decays with the increase of the particle size d : $D_{rot} \propto T/(\mu d^3)$ (where μ and T are the fluid viscosity and its temperature) and it is negligibly small in the millimetre range of scales³⁰. However, in 2D turbulence, the particle dispersion is governed by the scale comparable to the agitation (forcing) scale^{31–33}. Therefore, this scale may affect the characteristic scale of the bacterial fibre structure. In addition, turbulent flows generate stretching of the fluid elements which can also affect the formation of the bacterial cellulose.

Here we study the BC development by *Gluconacetobacter xylinus*³⁴ at the liquid-air interface in a turbulent quasi-2D flow. We show that turbulence indeed generates chaotic rotation in a fluid. The angular velocity of turbulent rotation is the strongest at the scale just below the forcing scale of turbulence, while above this scale it decays exponentially. Such turbulent rotation leads to a dramatic effect on the formation of the *G. xylinus* BC near the liquid surface. While in non-perturbed liquid, microorganisms form continuous sheets of the BC, in turbulent flows they form spherical beads whose size is proportional to the forcing scale of turbulence. Turbulence also effects the microscopic structure of the BC,

^{a)} Electronic mail: hua.xia@anu.edu.au

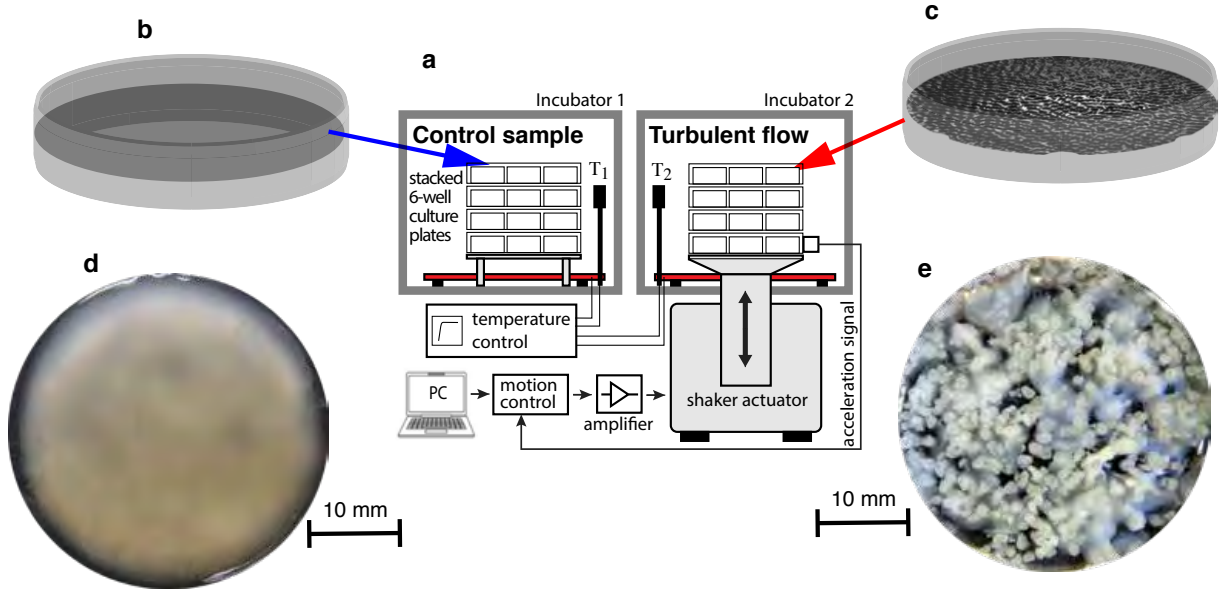


FIG. 1. (a) Schematic of the experimental setup. Bacterial suspensions of *G. xylinus* are placed inside temperature controlled incubators 1 and 2. Incubator 1 houses control (non-vibrated) samples with a non-perturbed air-liquid interface (b). Samples in the Incubator 2 are vertically vibrated at the prescribed frequency and acceleration. (c) The Faraday waves on the surface of the suspension generate turbulent flows. (d) The bacterial cellulose is developed in the control incubator in the form of a cellulose sheet. (e) In the suspension exposed to turbulence, cellulose develops in the form of spherical beads.

namely, the biofilm porosity due to chaotic stretching of bacterial suspensions.

II. RESULTS

A. Bacterial cellulose formation in quasi-2D turbulence

Effects of turbulence on the formation of the BC are studied in bacterial suspension of *G. xylinus*. Turbulence is generated using parametrically excited waves (Faraday waves) in vertically shaken containers (Fig. 1a and Methods). Here vertical acceleration is characterised by a supercriticality parameter $\alpha = (a - a_{th})/a_{th}$, where a is the amplitude of the sinusoidal acceleration of the container and a_{th} is the threshold acceleration for the parametric generation of the Faraday waves. Characteristics of the surface flow generated by such waves closely resemble 2D turbulence statistics generated using other methods, for example electromagnetically driven turbulence in layers of electrolytes^{16–21}. By changing the vertical acceleration of the container, one can control the kinetic energy of turbulence, while the frequency of the vibration controls the energy injection scale L_f (related to the Faraday wavelength λ)^{17,18}. Here the kinetic energy of the horizontal fluid motion (per unit mass) is characterised by the mean-squared fluctuating velocity at the fluid surface, $\langle u^2 \rangle$, which in these experiments is changed in the range of $\langle u^2 \rangle = (0.5\text{--}20) \times 10^{-4} \text{ m}^2 \text{ s}^{-2}$. This energy is proportional to the supercriticality parameter α (see Methods), which ranges from 0.1 to 3 in these experi-

ments. The forcing scale of turbulence is varied between 2 and 5 mm which corresponds to the oscillation frequencies of $f = (45 - 150) \text{ Hz}$. Bacterial suspensions of *G. xylinus* are exposed to turbulent flows for 72 hours (see Methods).

We observe the formation of two forms of the bacterial cellulose. Flat cellulose sheets, or pellicles, are formed at the surface of the suspension in the control samples (no vibration) and at lower turbulence energies, at $\alpha < 0.6$, Fig. 1d. When α (and the level of turbulent velocity fluctuations) is increased, spherical beads of cellulose embedded within the biofilm develop in the suspension, Fig. 1e. The diameter of the spherical beads is reduced with the reduction in the turbulence forcing scale (increase in the vibration frequency). Figs. 2a,b illustrate SCBs formed at the frequencies of $f = 60 \text{ Hz}$ and 120 Hz respectively with a supercriticality of $\alpha = 1.5$. The scanning electron microscopy (SEM) images illustrate the beads in Fig. 2c,d. The probability density functions of the bead sizes for these two cases are shown in Fig. 2e. Peaks of the PDFs at $d_b \approx 0.95 \text{ mm}$ (120 Hz) and $d_b \approx 1.3 \text{ mm}$ (60 Hz) correspond to the turbulence forcing scales of $L_f = 2.5$ and 4.4 mm . In the next section we discuss how the turbulence forcing scale can affect the bead size.

In addition to changing the macroscopic morphology of the cellulose, turbulence also substantially modifies microscopic structure of the cellulose fibres. The fibre structure of the cellulose formed in the presence of turbulent flows is rarefied, as seen in the SEM images of Figs. 3a-d. The analysis of the planar SEM images shows that the size and the area of the pores in cellulose, as well

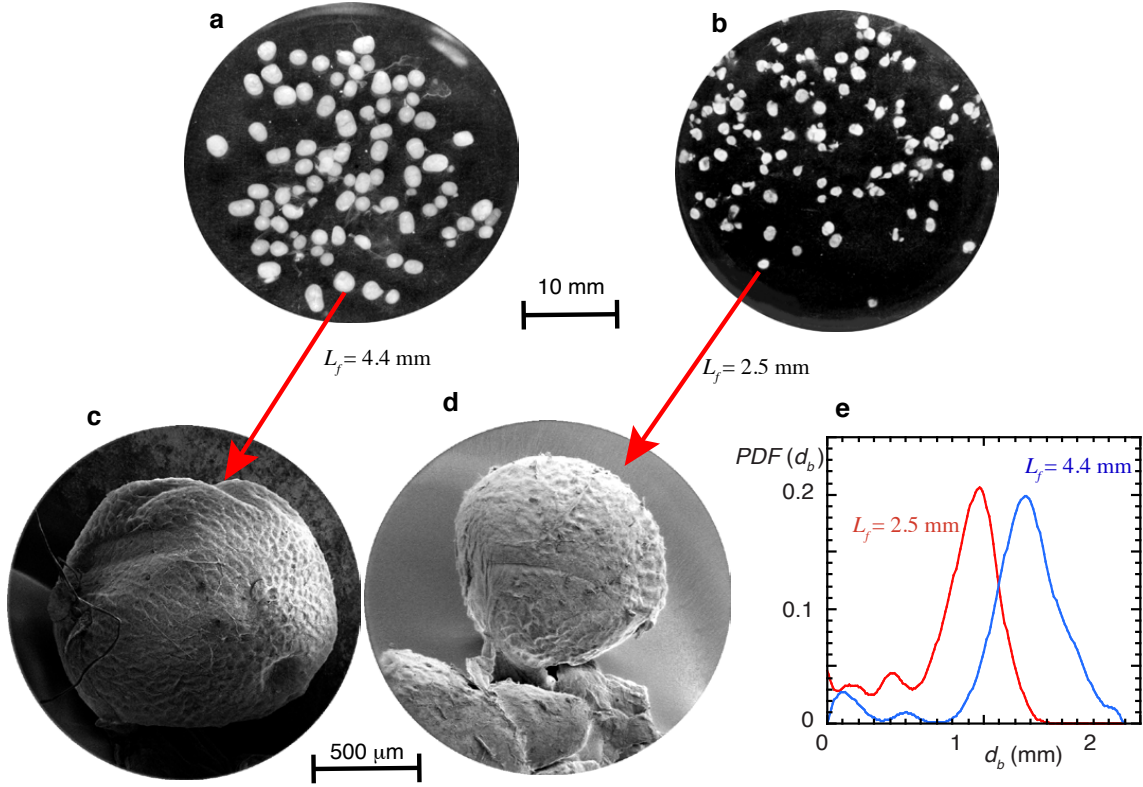


FIG. 2. Spherical cellulose beads formed in turbulent flows forced at the scale (a,c) $L_f = 4.4$ mm ($f_s = 60$ Hz), and (b,d) $L_f = 2.5$ mm ($f_s = 120$ Hz). (c,d) Cellulose bead images using SEM. (e) Probability density functions of the bacterial cellulose beads formed at different L_f .

as their probability distributions change in turbulent environment, Fig. 3e. In the samples formed in unperturbed bacterial suspensions (control samples), the PDF of the pore diameters A decays exponentially as $\text{PDF}(A) \propto \exp(-A/A_1)$, where $A_1 \approx 0.03$ μm . In the samples formed in turbulence, these PDFs are much broader, and the pore diameter distribution follows an exponential scaling, $\text{PDF}(A) \propto \exp(-A/A_2)$, where $A_2 \approx 0.06$ μm .

Changes in the microscopic structure of the BC are not correlated with the forcing scale of turbulence: similar PDFs of the pore size are observed in turbulence excited at $L_f = 5$ mm ($f = 45$ Hz) and $L_f = 2.2$ mm ($f = 150$ Hz), Fig. 3e. The effect of turbulence on the fibre structure does not have a threshold in the turbulence intensity, in contrast to the formation of the cellulose beads. The microscopic structure in turbulence changes regardless of its macroscopic shape, both in the flat sheets, and in the spherical cellulose beads.

To understand the effects of turbulence on the cellulose formation, we study two processes which can lead to (1) the formation of spherical beads, and (2) the changes in the microscopic structure of the cellulose fibres, namely (1) turbulent rotation and (2) stretching of fluid elements in turbulent flows.

B. Turbulent rotation and stretching in quasi-2D turbulence

It is recognised that the BC formation in agitated or shaken culture methods can lead to the production of different particle sizes and various shapes (spherical, ellipsoidal, fibrous suspensions etc.)³⁶. The relationship between the flow conditions and the resulting shape of the BC particles however is not established. The wave-driven turbulence provides an opportunity to study the BC development under well-controlled conditions since the statistical characteristics of such flows can be accurately characterised by a few key parameters: turbulence forcing scale, and the turbulence kinetic energy which is proportional to the supercriticality α (see above)^{31,33}. These parameters control the diffusive motion of fluid particles at the liquid surface^{37–39}. In addition to displacement of particles in turbulence from their initial position in a random-walk fashion, turbulent flows also lead to random rotation of finite size objects due to the generation of turbulent torque⁴⁰. Such torque can lead to bending of the BC fibres and to the changes in the macroscopic structure of the cellulose. In quasi-2D turbulence, it is expected that the rotation is small at the scales smaller than the forcing scale since the flow consists of coherent bundles of fluid particles^{39,41}. However, if a particle is exposed to the forces produced by several

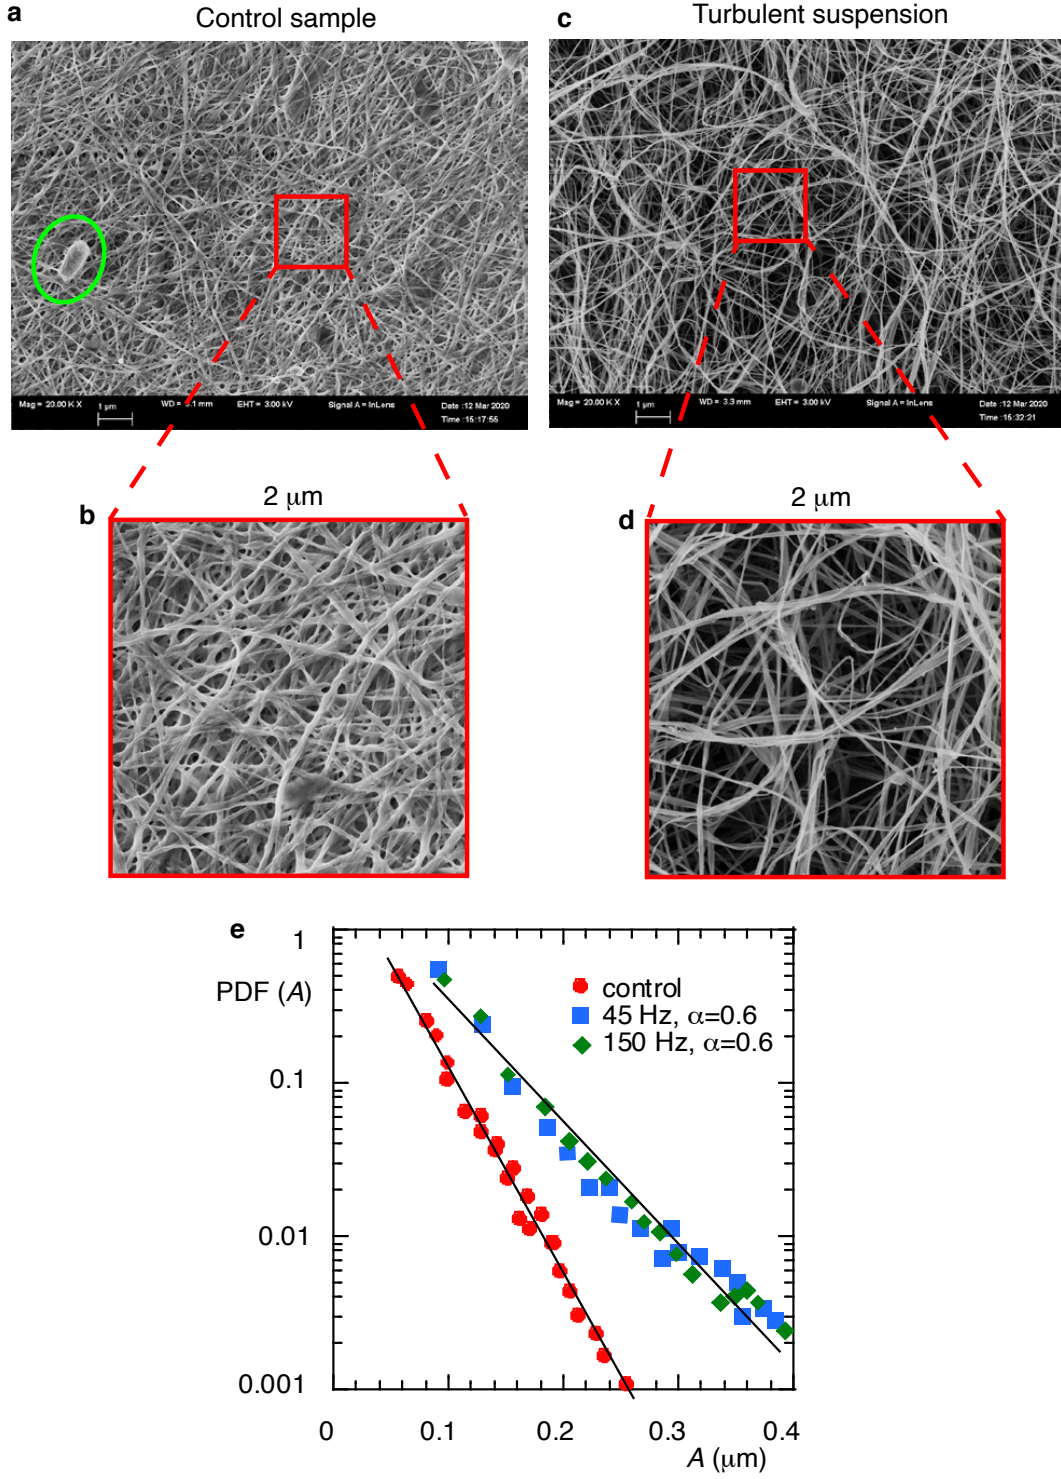


FIG. 3. Microscopic structure of the bacterial cellulose (SEM). (a,b) Cellulose structure of the control (non-shaken) samples. (c,d) Structure of the cellulose formed in the turbulent bacterial suspension at the excitation frequency $f = 45$ Hz ($L_f = 5$ mm) and acceleration $a = 0.5g$ ($\alpha = 0.6$). (e) Probability density functions of the cellulose pore diameter A in control samples (red circles) and in the samples vibrated at $f = 45$ Hz (blue squares) and $f = 150$ Hz (green diamonds) at the supercriticality parameter $\alpha = 0.6$. A green circle in (a) highlights a *G. xylinus* microorganism.

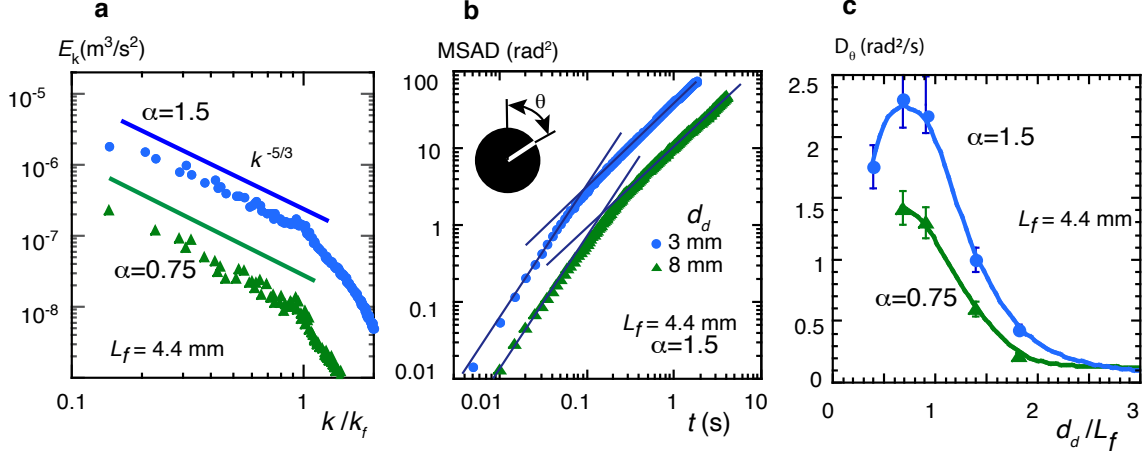


FIG. 4. Turbulent rotation and angular displacement characteristics in 2D turbulence. (a) Kinetic energy spectra on the surface of the liquid at two levels of the vertical acceleration $\alpha = 0.75$ (green triangles) and $\alpha = 1.5$ (blue circles). (b) Mean squared angular displacement of the circular disks versus time: disk diameters $d_d = 3$ mm (blue circles) and 8 mm (green triangles). The forcing scale of turbulence is $L_f = 4.4$ mm, supercriticality $\alpha = 1.5$. At short times, $\text{MSAD} \propto t^2$, indicating the ballistic regime. At longer times, $\text{MSAD} = D_\theta t$, indicating diffusive regime. (c) The rotational diffusion coefficients versus the ratio d_d/L_f of the disk diameter over turbulence forcing scale. These are measured at two levels of the supercriticality $\alpha = 0.75$ (green triangles) and $\alpha = 1.5$ (blue circles).

of such bundles, one can expect that turbulent torques will lead to measurable fluctuations in the particle angular velocities. The rotational diffusivity in such flows has not been studied before.

Similarly to random translation of particles, the rotational diffusivity can be characterised by the mean square angular displacement (MSAD) $\delta\theta^2(t) = \sum_0^t |\Delta\theta(t)|^2$, where $\Delta\theta(t) = \theta(t + \Delta t) - \theta(t)$. The MSAD can be tracked in time by following the orientational dynamics of the disks floating on the surface of the liquid (pictured in the inset of Fig. 4(b), see Methods). No mean rotation is observed, as expected in an isotropic turbulent flow. In wave-driven, quasi-2D turbulence, kinetic energy spectra are determined by the inverse energy cascade range ($E_k \propto k^{-5/3}$ at $k \leq k_f$) and the forward enstrophy cascade ($E_k \propto k^{-3}$ at $k \geq k_f$)⁴². Figure 4a shows the measured spectra in these experiments. The MSAD corresponding to these spectra show that turbulent rotation of the disks is described by the ballistic rotation regime at short times, and diffusive rotation at longer times, Fig. 4b:

$$\langle \delta\theta^2 \rangle \approx V_\theta^2 t^2, \quad t \ll T_\theta \quad (1)$$

$$\langle \delta\theta^2 \rangle \approx D_\theta t, \quad t \gg T_\theta \quad (2)$$

Here T_θ is the autocorrelation time of the angular velocity $T_\theta = 1/\langle \tilde{\omega}^2 \rangle \int_0^\infty \langle \omega(t_0 + t)\omega(t_0) \rangle dt$, where $\omega = d\theta/dt$ is the angular velocity of the disks, and $\langle \tilde{\omega}^2 \rangle$ is its variance.

For the cellulose formation occurring on the time scales of hours, we are interested in the long-time behaviour. We measure the rotational diffusion coefficient D_θ at different ratios of the disk diameter d_d to the forcing scale L_f . This coefficient, shown in Fig. 4c, is peaked at $d_d/L_f < 1$ and it decays exponentially at larger d_d/L_f .

This behaviour is also observed in a different type of quasi-2D turbulence, which is driven electromagnetically. The rate of diffusion is proportional to the turbulence kinetic energy: the increase in the variance of the turbulent velocity fluctuations $\langle u^2 \rangle$ leads to the increase in D_θ , Fig. 4c. Such turbulent torques may lead to random bending of the BC fibres resulting in the formation of the BC beads whose size is correlated with the turbulence forcing scale L_f .

To understand how turbulence can affect the microscopic structure of the BC, we study the stretching of the fluid parcels^{43,44}. Two adjacent fluid particles remain close to each other for a long time as they move within a coherent bundle. Occasionally these bundles split leading to the stretching of the fluid parcels. Extreme stretching events have been found in numerical simulations of 3D turbulence^{45–47}. However turbulent stretching has not been studied in 2D turbulence and it is not clear how the probability of stretching events depends on the turbulence parameters.

Stretching can be characterised by the relative separation of a pair of initially adjacent particles at times t_0 and $(t_0 + \tau)$: $R(t_0 + \tau)/R(t_0)$, (Fig. 5a). The logarithm of stretching normalised by time τ gives the value of the finite-time Lyapunov exponent $\Lambda(t, \mathbf{x}) = (1/\tau) \ln[R(t_0 + \tau)/R(t_0)]$ which characterises the rate of local deformation of an infinitesimal fluid element⁴⁸. Here $\mathbf{x}$ is the initial position of the pair of particles.

Trajectories of the fluid particles are determined using simulated trajectories derived from experimentally measured velocity fields (see Methods). The finite-time Lyapunov exponent field $\Lambda(\tau, \mathbf{x})$ gives the spatial distribution of the stretching rates for a particular integration

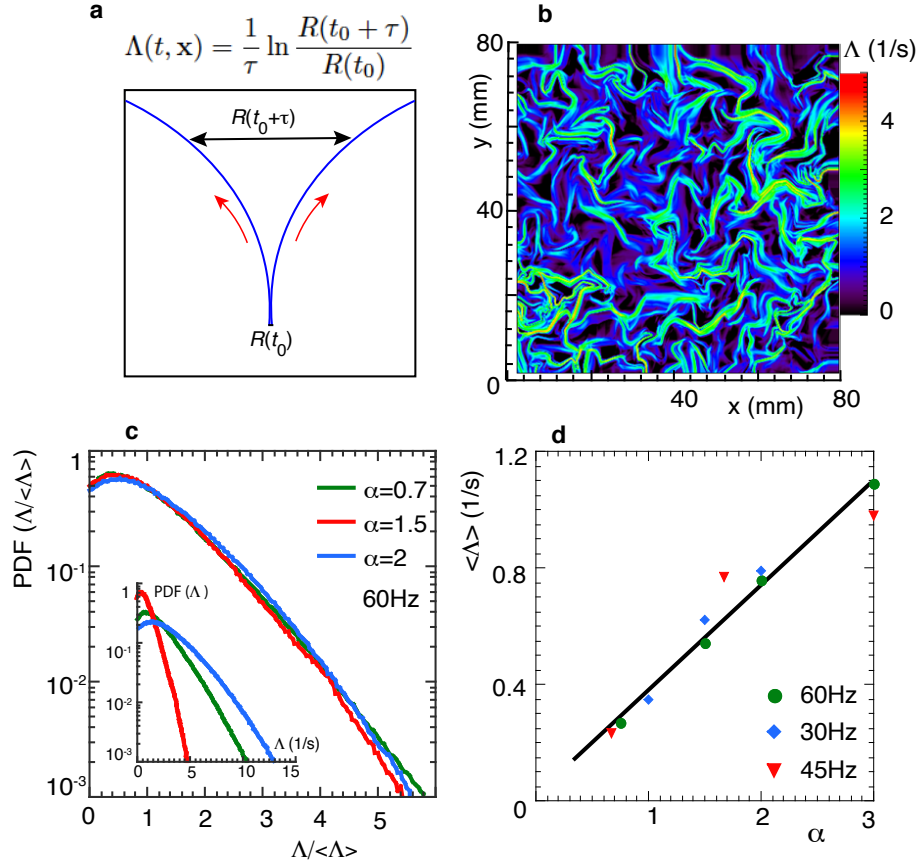


FIG. 5. Turbulent stretching of fluid parcels. (a) Schematic of the fluid particle separation. (b) Finite-time Lyapunov exponents Λ on the turbulent surface computed over time $\tau = 0.6T_L$. (c) Probability density functions of $\Lambda / \langle \Lambda \rangle$ (where $\langle \Lambda \rangle$ is the spatially averaged quantity) at three different vertical accelerations $\alpha = 0.7, 1.5$ and 2 and the frequency of $f = 60$ Hz. The inset shows the PDFs of non-normalised Λ . (d) Spatially averaged value of the Lyapunov exponents versus the supercriticality parameter α at different excitation frequencies: $f = 30$ Hz (blue diamonds), $f = 45$ Hz (red triangles), and $f = 60$ Hz (green circles).

time τ . Of a particular interest here, is the probability of strong stretching events occurring on the time scale comparable to the Lagrangian velocity correlation time $T_L = 1 / \langle \tilde{u}^2 \rangle \int_0^\infty \langle \mathbf{u}(t_0 + t) \mathbf{u}(t_0) \rangle dt$, where $\mathbf{u}$ is the fluid velocity along the Lagrangian trajectory, $\langle \tilde{u}^2 \rangle$ is its variance, and the angular brackets denote the ensemble averaging. Such short-time Lyapunov exponents have not been studied in 2D turbulence before.

Figure 5b shows a snapshot of the stretching field computed for $\tau = 0.6T_L$. The ridges of high values of Λ constantly move and reconnect (see Supplementary Video 1), such that over time, all points on the liquid surface experience many stretching events. The probability density functions of Λ are illustrated in the inset of Fig. 5c for three values of vertical accelerations which correspond to the supercriticality parameter α from 0.7 to 2 . However, if Λ is normalised by its spatially averaged value $\langle \Lambda \rangle$, the PDFs measured at different energies collapse onto a single function, Fig. 5c. The PDF of the Lyapunov exponent can be fitted with a Weibull distribution, $f(x) = (k/\beta)(x/\beta)^{(k-1)}e^{-(x/\beta)^k}$, where $k = 1.35$

is the shape parameter and $\beta = 1.3$ is the scale parameter. The Weibull distribution is related to a number of other probability distributions, in particular, it interpolates between the exponential distribution ($k = 1$) and the Rayleigh distribution ($k = 2$).

The collapse of the PDFs of the average-normalised finite-time Lyapunov exponents to this universal form is due to the fact that the spatially averaged Lyapunov exponents $\langle \Lambda \rangle$ increase approximately linearly with the increase in the supercriticality α of the wave-driven turbulence, Fig. 5d. This trend is independent of the turbulence forcing scale (vibration frequency), and correlates with the insensitivity of the PDF of the cellulose pore area to the forcing scale (Fig. 3e).

III. DISCUSSION AND CONCLUSIONS

Turbulence generated by parametrically excited waves in vertically shaken containers (Faraday waves) affects the formation of bacterial cellulose by *Gluconacetobacter*

xylinus microorganisms. Changes in the millimetre-range morphology of the biofilm are found in the samples exposed to quasi-2D turbulence: above some threshold turbulence energy corresponding to the supercriticality parameter of $\alpha = 1.5$ we observe the formation of spherical cellulose beads (Fig. 1). The size of the beads changes with the change in the turbulence forcing scale, L_f , determined by the frequency of the Faraday waves. The higher the frequency, the smaller the beads (Fig. 2). It is hypothesised that the turbulence-induced torque manifested as chaotic rotation of fluid elements, leads to the bending of the cellulose fibres. Such a rotation is studied by analysing the rotation of the circular disks at the liquid surface. It is found that the maximum in the rotational diffusion coefficient corresponds to the ratio of the disk diameter over the forcing scale of $d_d/L_f \approx 0.7$. For larger disks (or smaller L_f), D_θ decreases exponentially. The characteristic size of the cellulose beads d_b normalised by L_f is in the range $d_b/L_f = 0.3 - 0.4$, Fig. 2e. Turbulent rotation results from the interaction between meandering coherent bundles of fluid particles^{31,39,41} whose widths is about L_f , therefore the fibre clusters whose size is much less than L_f do not experience strong torque. Thus it seems reasonable that the formation of the beads occurs on the scales of the order of L_f .

The microscopic structure of the cellulose is also affected by turbulence: cellulose exposed to turbulent flows is rarified in comparison with the control samples, Fig. 3. We attribute this effect to the stretching of fluid elements by turbulence. Stretching is evaluated by measuring turbulent velocity fluctuations and by computing trajectories of the fluid particles. The separation of initially close particles is characterised by the finite-time Lyapunov exponents Λ . Spatially averaged $\langle \Lambda \rangle$ monotonically increases with the increase in the supercriticality α (Fig. 5d), while the probability density functions show exponential tails at larger stretching events (Fig. 5c). The mean stretching rate also appears to be independent on the forcing scale of turbulence. This behaviour correlates with exponential distribution of pore size in bacterial cellulose (Fig. 3e), which is also insensitive to the turbulence forcing scale. Thus turbulent stretching is found to be a plausible mechanism responsible for the modification of the BC microstructure at small scales.

Summarising, we investigate two fundamental processes in wave-driven turbulence, turbulent rotation and stretching. It is shown that turbulence can be used as a tool to produce biofilms with remarkably different macro- and microscopic structures. The results offer new methods which allow to engineer bacterial cellulose properties (e.g. porosity, water holding capacity, etc.) by employing well-controlled wave-driven turbulence.

IV. METHODS

Turbulent flow generation

Faraday waves are generated on the surface of a liq-

uid which is vertically vibrated at the frequency f_s with sinusoidal acceleration a above a parametric excitation threshold (a_{th}) ³⁵, at a supercriticality parameter $\alpha = (a - a_{th})/a_{th} \geq 1$. The flow generated on the surface at high α exactly reproduces the statistics of 2D turbulence^{16,17,32}. In the experiments, turbulence kinetic energy is proportional to the supercriticality parameter³³. The kinetic energy spectrum has a form $E_k = C\epsilon^{2/3}k^{-5/3}$ in the inverse energy cascade range. The energy injection rate (equal to the dissipation rate) $\epsilon = (E(k)/C)^{3/2}k^{5/3}$ where $C = 6$ is the Kolmogorov constant and it increases with the increase in α as $\epsilon \sim \alpha^3$. The forcing scale of the flow is half the wavelength of the Faraday waves, $L_f = 1/2\lambda$. The experiments are conducted at $f_s = (30 - 150)$ Hz, $\alpha = (0.1 - 2)$, and $L_f = (2 - 13)$ mm.

Floating disks of various sizes d_d (normalised size d_d/L_f ranging from 0.4 to 7) are used to study the rotational torque in the flow. A white stripe is marked on each disk to track its orientation θ ($\theta \in [-90^\circ, +90^\circ]$). The angular velocities V_θ are calculated based on the angular displacements between two adjacent image frames and averaged over three points in time. The statistics of the disk rotation is captured along the disk trajectories in turbulence. To minimise the disturbance to the flow, only one disk on the surface is used in each measurement. More than 600 independent realisations (movies) are recorded in every experiment to achieve statistical convergence.

The velocity field is measured using a particle image velocimetry technique. To determine the FTLE field from the measured velocity fields, we simulate the particle trajectories by integrating the velocity field from $t = t_0$ and determine how much initially adjacent particles are separated during the finite integration time τ using a 4th order Runge-Kutta integration method. The FTLE field gives the spatial distribution of the stretching rate within a flow for the integration time τ . The mean FTLE is obtained by spatially averaging over the fluid surface characterizing the mean stretching rate of the fluid parcels.

Bacterial culture

The culture media of *G. xylinus* (ATCC 700178) is prepared by adding 20 g of glucose, 5 g of peptone, 5 g of yeast extract, 2.7 g of Na_2HPO_4 and 1.5g of citric acid in 1.0L of distilled water.

72 hour culture. To prepare the 72 hour culture, one 100 μ L frozen stock (stored in $-80^\circ C$) is transferred into a 1.5 mL Eppendorf tube and centrifuged at 12,000 rpm for 5 minutes to remove Dimethyl sulfoxide (used for the frozen stock). The pellet is collected and resuspended in 5mL of fresh media, incubated for 72 hours at $26^\circ C$ in a stationary condition.

To collect the bacteria from the 72 hour culture, we grind the cellulose formed at the 72 hour culture and collect the solution. The culture solution is also centrifuged at 12,000 rpm for 5 minutes to form the pellet. The pellet is then resuspending in 1 mL fresh media.

Cellulose formation in turbulent flows. Six-well microplates containing 8 ml of culture media are inoculated with 20 μ l of 72 hour culture solution of *G. xylinus* as described above. The microplates are vibrated for 72 hours at 26°C. The control samples are incubated for 72 hours in a non-vibrated incubator. The layer thickness of the culture media is kept at $h = 8$ mm in all the experiments.

Harvested bacterial cellulose is immersed in ethanol. Subsequently it is transferred to 0.1 M NaOH and boiled for 40 min at 90 °C. It is then neutralised in deionised water for 24 hours.

Sample preparation for SEM. The fibrous structure of the cellulose is fixed using chemical fixative glutaraldehyde. The samples are washed in deionised water to remove fixatives, then dehydrated using critical-point drying. After that, samples are mounted on the studs and sputter-coated with a thin layer of evaporated gold for the SEM analysis.

The software imageJ (particle analysis) is used to analyse the fibre structure, such as the pore area, pore diameter, and the pore size distribution.

ACKNOWLEDGMENTS

This work was supported by the Australian Research Council Discovery Projects and Linkage Projects funding schemes (DP160100863, DP190100406 and LP160100477). H.X. acknowledges support from the Australian Research Council's Future Fellowship (FT140100067). The authors acknowledge the technical assistance of Centre for Advanced Microscopy (ANU) and the Australian National Fabrication Facility (ACT node).

Author contributions:

H.X. and M.S. designed the project. S.H.H. and M.D. conducted the cellulose formation experiments. J. Y. conducted the rotational diffusion experiments. H.P. designed the experimental setup. J.Y. and H.X. analysed the experimental data. H.X. and M.S. wrote the paper. All authors reviewed the paper.

¹Hall-Stoodley, L., Costerton J.W. & Stoodley, P. Bacterial biofilms: from the natural environment to infectious diseases. *Nat. Rev. Microbiol.* **2**, 95-108 (2004).

²Jonas, R. & Farah, L. F. Production and application of microbial cellulose. *Polym. Degrad. Stabil.* **59**, 101-106 (1998).

³Campano, C. et al. Enhancement of the fermentation process and properties of bacterial cellulose: a review. *Cellulose* **23**, 57-91 (2016).

⁴Nguyen, P.Q. et al. Engineered Living Materials: Prospects and Challenges for Using Biological Systems to Direct the Assembly of Smart Materials. *Adv. Mater.* **30**, 1704847 (2018).

⁵Svensson, A., Nicklasson, F., Harrah, T., Panilaitis, B., Kaplan, D.L., Brittberg, M. & Gatenholm, P. Bacterial cellulose as a potential scaffold for tissue engineering of cartilage, *Biomaterials* **26**, 419 (2005).

⁶Kucinska-Lipka, J., Gubanska, I. & Janik, H.Z. Bacterial cellulose in the field of wound healing and regenerative medicine of skin: recent trends and future perspectives. *Polym. Bull.* **72**, 2399-2419 (2015).

⁷Yamanaka, S. et al. The structure and mechanical properties of sheets prepared from bacterial cellulose. *J. Mater. Sci.* **24**, 3141 (1989).

⁸Y. Hu, J.M. Catchmark and E.A. Vogler. Factors impacting the formation of sphere-like bacterial cellulose particles and their biocompatibility for human osteoblast growth. *Biomacromolecules*, **14**, 3444 (2013).

⁹Gemeiner, P., Benes, M.J. & Stamberg, J. Bead cellulose and its use in biochemistry and biotechnology. *Chem. Papers.* **43**, 805-848 (1989).

¹⁰Petersen, N. & Gatenholm, P. Bacterial cellulose-based materials and medical devices: current state and perspectives. *Appl. Microbiol. Biotechnol.* **91**, 1277-86 (2011).

¹¹Picheth, G.F. et al. Bacterial cellulose in biomedical applications: A review. *Inter. J. Bio. Macromolecules.* **104**, 97-106 (2017).

¹²Iguchi M., Yamanaka S. & Budhiono A. Bacterial cellulose: a masterpiece of nature's arts. *J. Mater. Sci.* **35**, 261-270 (2000).

¹³Drozd, r. et al. Functionalized magnetic bacterial cellulose beads as carrier for Lecitase ultra immobilization. *Appl. Biochem. Biotechnol.* **187**, 176-193(2019).

¹⁴Kannan, A. et al. Dynamic switching enables efficient bacterial colonization in flow. *Proc. Natl. Acad. Sci. U.S.A.* **115**, 5438-5443 (2018).

¹⁵Hong, S-H. et al. Surface waves control bacterial attachment and formation of biofilms in thin layers. *Sci. Adv.* **6**, eaaz9386(2020).

¹⁶von Kameke, A., Huhn, F., Fernández-García, G., Muñuzuri, A. P. & Pérez-Muñuzuri, V. Double cascade turbulence and Richardson dispersion in a horizontal fluid flow induced by Faraday waves. *Phys. Rev. Lett.* **107**, 074502 (2011).

¹⁷Francois N., Xia H., Punzmann H. & Shats M. Inverse energy cascade and emergence of large coherent vortices in turbulence driven by Faraday waves, *Phys. Rev. Lett.* **110**, 194501 (2013).

¹⁸Francois N., Xia H., Punzmann H., Ramsden S. & Shats M., Three-dimensional fluid motion in Faraday waves: Creation of vorticity and generation of two-dimensional turbulence, *Phys. Rev. X* **4**, 021021 (2014).

¹⁹Paret, J. & Tabeling, P. Experimental observation of the two-dimensional inverse energy cascade. *Phys. Rev. Lett.* **79**, 4162 (1997).

²⁰Xia, H., Punzmann, H., Falkovich, G. & Shats, M. Turbulence-condensate interaction in two dimensions. *Phys. Rev. Lett.* **101**, 194504 (2008).

²¹Xia, H., Byrne, D., Falkovich, G. & Shats, M. Upscale energy transfer in thick turbulent fluid layers. *Nat. Phys.* **7**, 321 (2011).

²²Bodenschatz, E., Malinowski, S.P., Shaw, R.A. & Stratmann, F. Can we understand clouds without turbulence? *Science* **327**, 970-971 (2010).

²³Barkley, D. et al. The rise of fully turbulent flow. *Nature* **526**, 550-553 (2015).

²⁴Sreenivasan, K.R. Turbulent mixing: a perspective. *PNAS*, **10**, 116 (2019).

²⁵Falkovich, G. Fluid mechanics. Cambridge University Press. ISBN-10: 1107129567 (2018).

²⁶Colombi, R., Schluter, M. & von Kameke, A. Measurements of sub-surface velocity fields in quasi-2D Faraday flow. arXiv: 1911.11208v3 (2020).

²⁷Dunkel, J., Heidenreich, S., Drescher, K., Wensink, H.H., Bar, M., & Goldstein, R.E., Fluid dynamics of bacterial turbulence. *Phys. Rev. Lett.* **110**, 228102 (2013).

²⁸Toschi, F. & Sega, M. (Ed.). Flowing matter. Springer, (2019).

²⁹Zeff, B.W. et al. Measuring intense rotation and dissipation in turbulent flows. *Nature*, **42**, 146(2003).

³⁰Berg, H. C. Random Walks in Biology. Princeton University Press, Princeton, NJ. 1983.

³¹Xia H., Francois N., Punzmann H. & Shats M. Lagrangian scale of particle dispersion in turbulence, *Nat. Commun.* **4**, 2013 (2013).

³²Xia H., Francois N., Punzmann H. & Shats M. Taylor particle dispersion during transition to fully developed two-dimensional turbulence, *Phys. Rev. Lett.* **112**, 104501 (2014).

- ³³Xia, H. et al. Tunable diffusion in wave-driven two-dimensional turbulence. *J. Fluid Mech.* **865**, 811 (2019).
- ³⁴Brown, A.J. On an acetic ferment which forms cellulose. *J. Chem. Soc.* **49**, 432(1886)
- ³⁵Faraday, M. On a peculiar class of acoustical figures; and on certain forms assumed by a group of particles upon vibrating elastic surfaces. *Philos. T. R. Soc. A* **121** 299-318(1831).
- ³⁶Wang, J., Tavakoli, J. & Tang, Y. Bacterial cellulose production, properties and applications with different culture methods: A review. *Carbohydr. Polym* **219**, 63-76 (2019).
- ³⁷Yang, J., Davoodianidalik, M., Xia, H., Punzmann H., Shats, M. and Francois, N. Passive swimming in hydrodynamic turbulence at a fluid surface. *Phys. Rev. Fluids*, **4**, 104608 (2019).
- ³⁸Yang, J., Francois, N., Punzmann, H., Shats, M. & Xia, H. Diffusion of ellipsoids in laboratory two-dimensional turbulent flow. *Phys. Fluids*, **31**, 085116 (2019)
- ³⁹Xia, H., Francois, N., Faber, B., Punzmann, H. & Shats, M. Local anisotropy of laboratory two-dimensional turbulence affects pair dispersion. *Phys. Fluids* **31**, 025111(2019).
- ⁴⁰Zimmermann, R., Gasteuil, Y., Bourgoin, M., Volk, R., Pumir, A., Pinton, J-F. Rotational intermittency and turbulence induced lift experienced by large particles in a turbulent flow. *Phys. Rev. Lett.* **106**, 154501(2011).
- ⁴¹Francois, N., Xia, H., Punzmann, H. & Shats, M. Rectification of chaotic fluid motion in two-dimensional turbulence. *Phys. Rev. Fluids* **3**, 124602 (2018).
- ⁴²Kraichnan, R. Inertial ranges in two-dimensional turbulence. *Phys. Fluids* **10**, 1417 (1967).
- ⁴³Aref, H. Stirring by chaotic advection. *J. Fluid Mech.* **143**, 1-21 (1984)
- ⁴⁴Ottino, J.M. The kinematics of mixing: stretching, chaos and transport (Cambridge University Press, Cambridge, 1989).
- ⁴⁵Scatamacchia, R., Biferale, L. & Toschi, F. Extreme events in the dispersions of two neighbouring particles under the influence of fluid turbulence. *Phys. Rev. Lett.* **109**, 144501 (2012).
- ⁴⁶Goto, S. & Vassilicos, J.C. Particle pair diffusion and persistent streamline topology in two-dimensional turbulence. *New J. Phys.* **6**, 65 (2004).
- ⁴⁷Rossi, L., Vassilicos, J.C. & Hardalupas, Y. Electromagnetically controlled multi-scale flows, *J. Fluid Mech.* **558**, 207-242 (2006).
- ⁴⁸Boffetta, G. et al. Detecting barriers to transport: a review of different techniques. *Physica D*, **159**, 58-70 (2001).