

# Quantum Kinetics of the Magneto–Photo–Galvanic Effect

Dieter Hornung<sup>1</sup> and Ralph von Baltz<sup>2</sup>

<sup>1</sup>*University of Applied Sciences, 66117 Saarbrücken, Germany and*

<sup>2</sup>*Institute for Theory of Condensed Matter, Faculty of Physics,  
Karlsruhe Institute of Technology (KIT), 76131 Karlsruhe, Germany*

(Dated: April 29, 2021)

Using the Keldysh–technique we derive a set of quasiclassical equations for Bloch–electrons in noncentrosymmetric crystals upon excitation with quasimonochromatic radiation in the presence of external electrical and magnetic fields. These equations are analog to the Semiconductor–Bloch–Equations for the dynamics of electrons including the photogalvanic effect (PGE) in particular the shift–mechanism. The shift PGE has been recently identified as showing promise for the development of new photovoltaic materials. In addition, our theory may be useful to investigate the interplay between breaking time–reversal symmetry and topological properties as well as the analysis of recent local excitation experiments in nano–photonics. Explicit results for the photogalvanic tensors are presented for linear and circular polarized light and a magnetic field. In addition, we disprove existing statements, that the shift–photogalvanic effect does not contribute to the photo–Hall current.

PACS numbers: 72.10Bg, 72.40+w, 77.84.-s

Keywords: photogalvanic effect, bulk photovoltaic effect, nonlinear transport, magnetic field, Berry–connection, quasi–classical approximation.

## I. INTRODUCTION

In noncentrosymmetric crystals a direct current can be induced upon the absorption of light under homogeneous conditions. This phenomenon was discovered more than 50 years ago and it was termed bulk photovoltaic effect (BPVE) or photogalvanic effect (PGE), cf. Sturman and Fridkin’s book<sup>1</sup>. By two major discoveries the PGE recently gained an unprecedented boost: The discovery of ferroelectric perovskite materials<sup>2</sup> in 2009 as potentially relevant solar cell materials and the discovery of Weyl–semimetals in 2015 with topological protected states<sup>3</sup>. The underlying physics is intimately connected with the so–called shift–mechanism (as described later). The aim of this paper is to work out a semiclassical theory for the PGE which is suited for numerical investigations including external electrical and magnetic fields.

The PGE depends on the properties of the material, applied fields as well as on the properties of the absorbed light. In first order in the light intensity and in an external magnetic field with induction  $\mathbf{B}$ , symmetry requires the following representation for the radiation–induced direct current (no static electrical field, neglecting photon momentum)

$$j_\alpha = I (P_{\alpha\mu\nu}^S(\omega) + R_{\alpha\beta\mu\nu}^S(\omega) B_\beta) \operatorname{Re}(e_\mu^* e_\nu) + I (P_{\alpha\mu\nu}^A(\omega) + R_{\alpha\beta\mu\nu}^A(\omega) B_\beta) \operatorname{Im}(e_\mu^* e_\nu). \quad (1)$$

Symbols have the following meaning:  $I$  (local) intensity,  $\omega$  frequency,  $e_\mu$  (cartesian) components of the (complex) unit polarization vector  $\mathbf{e}$  of the light. Indices  $\alpha, \beta, \mu, \nu \in \{x, y, z\}$  indicate cartesian components, an asterisk indicates complex conjugation.  $\mathbf{P}^S, \mathbf{P}^A$  denote polar tensors of rank three whereas  $\mathbf{R}^S, \mathbf{R}^A$  are of rank four with axial symmetry. Superscripts S, A specify symmetry and antisymmetry with respect to polarization indices  $\mu, \nu$  and their contributions are usually termed as

“linear” and “circular”, respectively<sup>4</sup>.  $\mathbf{P}^S$  is analogous to the piezotensor whereas  $\mathbf{P}^A$  is equivalent to the (rank two axial) gyrotensor in gyrotropic media, and  $\mathbf{R}^A$  is equivalent to a polar tensor of rank three, see Birss<sup>5</sup>.

In the spirit of nonlinear optics<sup>6</sup>, the PG–current results from a quadratic term in the current–field relation. Standard second order quantum mechanical response theory<sup>7</sup> revealed two different origins of the PGE: a “ballistic” (kinetic) and a “shift” mechanism. The ballistic PGE results from asymmetric optical transitions in cooperation with impurities or phonon scattering which is described by the diagonal matrix elements of the density operator (with respect to a Bloch–basis). The shift PGE, on the other hand, is a band–structure property and results from the nondiagonal elements. It is intimately related to the Bloch–representation of the position operator<sup>8</sup> which leads to a shift of Bloch wave–packets in real space upon optical transitions<sup>9–11</sup>. The circular PGE ( $\mathbf{P}^A$ –term) is invariant under time–reversal as opposed to the linear PGE ( $\mathbf{P}^S$ –term), an external magnetic field breaks time–reversal explicitly.

For linear polarized light, the shift–current contribution can be represented as ( $\mathbf{P}^S$ –term, reformulation of Eq. (19) of Ref.<sup>9</sup>)

$$\mathbf{j}_{\text{PG}} = \frac{I}{\hbar\omega} \frac{e^3}{4\pi^2 \omega m_0^2 \epsilon_0 c \eta} \int (f_{v,0} - f_{c,0}) \times |\langle c, \mathbf{k} | \mathbf{e} \cdot \mathbf{p} | v, \mathbf{k} \rangle|^2 \mathbf{s}_{cv}(\mathbf{e}, \mathbf{k}) \times \delta(E_c(\mathbf{k}) - E_v(\mathbf{k}) - \hbar\omega) d^3k, \quad (2)$$

$$\mathbf{s}_{cv}(\mathbf{e}, \mathbf{k}) = \mathbf{X}_{vv}(\mathbf{k}) - \mathbf{X}_{cc}(\mathbf{k}) + \nabla_{\mathbf{k}} \Phi_{cv}(\mathbf{e}, \mathbf{k}), \quad (3)$$

$$\mathbf{X}_{mn}(\mathbf{k}) = \int i u_{m\mathbf{k}}^*(\mathbf{r}) \nabla_{\mathbf{k}} u_{n\mathbf{k}}(\mathbf{r}) d^3r, \quad (4)$$

where  $\Phi_{cv}(\mathbf{e}, \mathbf{k})$  is defined via the expression

$$\langle c, \mathbf{k} | \mathbf{e} \cdot \mathbf{p} | v, \mathbf{k} \rangle = i |\langle c, \mathbf{k} | \mathbf{e} \cdot \mathbf{p} | v, \mathbf{k} \rangle| e^{i \Phi_{cv}(\mathbf{e}, \mathbf{k})}. \quad (5)$$

$|n, \mathbf{k}\rangle$  denotes the Bloch-states of (conduction/valence) bands<sup>12</sup>  $n = c, v$  at wave vector  $\mathbf{k}$ ,  $E_n(\mathbf{k})$  is the band-energy, and  $u_{n\mathbf{k}}(\mathbf{r}) = \langle \mathbf{r} | n, \mathbf{k} \rangle$  is the lattice-periodic part of the Bloch-function  $\langle \mathbf{r} | n, \mathbf{k} \rangle$ .  $f_{n,0}(\mathbf{k})$  is the equilibrium Fermi-function,  $m_0$  is the free-electron mass,  $e$  the elementary charge.  $\mathbf{e}$  (real) denotes the polarization vector and  $I$  is the local intensity of the radiation at frequency  $\omega$ .  $\eta$  is the refractive index of the material and integrals over  $r$  and  $k$  extend over the crystal unit-cell and the Brillouin-zone, respectively. Note, the shift current does not depend on the carrier mobility.

By construction, the shift vector  $\mathbf{s}_{cv}(\mathbf{e}, \mathbf{k})$  is invariant with respect to phase transformations of the Bloch states, however, it depends on the polarization of the light, therefore, it is not a genuine property of the material (by contrast to  $\mathbf{P}^S$ ). Second order Quantum response theory was fully exploited by Sipe<sup>13</sup> and collaborators who developed a nowadays widely used approach to study nonlinear optical phenomena on a microscopic level, such as second order harmonic generation and the shift PGE. Results (3)–(5) are valid for linear polarization only and they are implicitly contained in Ref.<sup>13</sup>(Eq. (58) and below, linear polarization of arbitrary direction). The shift distance is comparable to the crystal unit cell<sup>14,17</sup> and may be even larger, e.g. CdSe: 0.4 nm, GaP: 0.9 nm.

Up to 2006 (to the best of our knowledge) there was only but one bandstructure evaluation<sup>14</sup> of Eq. (2) which was performed for n-doped GaP. This material has been used as a fast and robust IR monitor<sup>15</sup>. First principles band structure calculations have been performed by Nastos and Sipe<sup>16,17</sup> for GaAs and GaP below and above the band gap and for CdSe and CdS. Young and Rappe<sup>18</sup> confirmed the shift mechanism as given by Eqs. (2–4) for some “old materials” like BaTiO<sub>3</sub>, KNbO<sub>3</sub> and claimed its key role for the large efficiency of the new ferroelectrics for solar energy conversion up to 23%, see e.g. Refs.<sup>20–25</sup>. Recent numerical studies have discovered new groups of promising materials with large shift contributions up to 20 times than previously known<sup>30</sup>, e.g. the quasi two-dimensional systems GeS<sup>31</sup>, MoS<sub>2</sub><sup>32</sup>, chiral materials<sup>33</sup> or using strain-engineering<sup>34</sup>.

It became obvious that the shift vector Eq. (3) is a Berry-connection which provides a sensitive tool to analyse the topological nature of quantum states in the recently discovered Weyl semimetals, see e.g. Refs.<sup>26–29</sup>. A recent revisit for the second-order optical response by Holder et al.<sup>37</sup> identified three different mechanisms to generate a dc-current: the Berry curvature, a term closely related to the quantum metric, and the diabatic motion. Berry-connections have been also recognized as relevant ingredients for the quasiclassical dynamics of Bloch electrons<sup>35</sup> and the anomalous Hall effect<sup>36</sup>. Other interesting phenomena and applications with relation to the shift mechanism are, e.g. (i) FIR detectors in the form of semiconductor heterostructures<sup>38</sup>, (ii) the shift vector as the geometrical origin of beam shifts<sup>39</sup>, (iii) nanotubes<sup>40</sup>, or (iv) twisted graphene bilayers<sup>41</sup>.

By using the Keldysh-technique we derive a set of

quasiclassical equations for the PGE (Sect. II) upon (inhomogeneous) excitation and including external electrical and magnetic fields. Our theory relies on the assumptions: (i) electron Bloch-states are a relevant basis, (ii) scattering and recombination are treated on a phenomenological level, (iii) electron-hole Coulomb-interaction is neglected. Explicit results for the PG-tensors are worked out in Sect. III. Sect. IV gives a summary and discussion whereas Appendices A – C contain technical details and an application to GaP.

## II. QUANTUM KINETICS

The quantum kinetic theory of the PGE is based on a hermitian matrix function  $\mathbf{f}$  with elements  $f_{mn}(\mathbf{k}, \mathbf{R}, T)$  which describes the single-particle states of the crystal,  $m, n$  denote band-indices. The arguments of  $\mathbf{f}$  are - besides the wave vector  $\mathbf{k}$  - the position vector  $\mathbf{R}$  and the time  $T$ . This theory is a generalization of the classical Boltzmann description, it includes, however, diagonal (local electron concentrations) as well as nondiagonal (nondissipative, coherent) contributions of the density-operator.

The basic equations for  $\mathbf{f}$  are derived by using the Keldysh-technique as formulated by Rammer and Smith<sup>43</sup>. This technique provides a consistent way to construct a quasiclassical description at finite temperatures, it uses solely gauge invariant quantities, external fields can be easily included, and applications are much simpler to work out than a full quantum mechanical treatment as in Eqs. (2–4).

### A. Keldysh formulation

It is algebraically favorable to use a representation in which all Keldysh-matrices have the Jordan normal form (Ref.<sup>43</sup>, Sec.IIB). For example the Green-function  $\hat{\mathbf{G}}$  reads

$$\hat{\mathbf{G}} = \begin{bmatrix} G^R & G^K \\ 0 & G^A \end{bmatrix}.$$

$G^R, G^A$  denote the usual retarded and advanced Green-functions and  $G^K$  is the Keldysh-function which plays a crucial role within this formulation

$$\begin{aligned} G^R(\mathbf{R}, T; \mathbf{r}, t) &= +\theta(t)\{G^>(\mathbf{R}, T; \mathbf{r}, t) - G^<(\mathbf{R}, T; \mathbf{r}, t)\}, \\ G^A(\mathbf{R}, T; \mathbf{r}, t) &= -\theta(-t)\{G^>(\mathbf{R}, T; \mathbf{r}, t) - G^<(\mathbf{R}, T; \mathbf{r}, t)\}, \\ G^K(\mathbf{R}, T; \mathbf{r}, t) &= G^>(\mathbf{R}, T; \mathbf{r}, t) + G^<(\mathbf{R}, T; \mathbf{r}, t). \end{aligned}$$

All these functions are special combinations of the Kadanoff-Baym functions  $G^<, G^>$  (Ref.<sup>43</sup>, Sec.IIA,IIB)

$$G^<(\mathbf{R}, T; \mathbf{r}, t) = +i\langle\langle \psi^+(\mathbf{r}_2, t_2) \psi(\mathbf{r}_1, t_1) \rangle\rangle, \quad (6)$$

$$G^>(\mathbf{R}, T; \mathbf{r}, t) = -i\langle\langle \psi(\mathbf{r}_1, t_1) \psi^+(\mathbf{r}_2, t_2) \rangle\rangle. \quad (7)$$

$\psi(\mathbf{r}_1, t_1)$ ,  $\psi^+(\mathbf{r}_2, t_2)$  are the electron field-operators in the Heisenberg-picture.  $\mathbf{R} = (\mathbf{r}_1 + \mathbf{r}_2)/2$ ,  $T = (t_1 + t_2)/2$

denote a ‘‘center-of-mass’’ coordinate and a ‘‘mean’’ time, respectively. In addition relative variables  $\mathbf{r} = \mathbf{r}_1 - \mathbf{r}_2$ ,  $t = t_1 - t_2$  will be needed.  $\langle\langle \dots \rangle\rangle$  corresponds to the grand-canonical ensemble average (at finite temperatures).

Our starting point is – as layed out by Sipe and Shkreptii<sup>13</sup> – an independent particle description with the Hamiltonian

$$H(\mathbf{r}, \mathbf{p}, t) = \frac{(\mathbf{p} - q\mathbf{A})^2}{2m_0} + V(\mathbf{r}) + q\Phi. \quad (8)$$

$\mathbf{p}$  denotes the canonical momentum,  $V(\mathbf{r})$  is the periodic crystal-potential, and  $m_0, q$  are the mass and charge ( $q = -e$ ) of the electrons.  $\mathbf{A} = \mathbf{A}(\mathbf{r}, t)$ ,  $\Phi = \Phi(\mathbf{r}, t)$  are the vector and scalar potentials of the radiation and external (classical) electromagnetic field,  $\mathbf{A} = \mathbf{A}_{rad} + \mathbf{A}_{cl}$ ,  $div\mathbf{A} = 0$ . In the following, we assume that the energies  $E_n(\mathbf{k})$  and Bloch-states  $|n, \mathbf{k}\rangle$  of the electrons are known from a bandstructure calculation ( $\mathbf{A} = \Phi = 0$ ).

The photogalvanic effect is independent of photon-momentum, see Eq. (1), therefore the magnetic field of the radiation can be neglected, i.e.  $\mathbf{A}_{rad}(\mathbf{r}, t)$  can be approximated by a position-independent field (equivalent to the electrical dipole approximation),  $\mathbf{A}_{rad}(t)$ ,  $\Phi_{rad} = 0$ . Regrouping the remaining terms in Eq. (8), we obtain

$$H(\mathbf{r}, \mathbf{p}, t) = H_{cl}(\mathbf{r}, \mathbf{p}, t) + H_{int}(\mathbf{r}, \mathbf{p}, t), \quad (9)$$

$$H_{cl}(\mathbf{r}, \mathbf{p}, t) = \frac{(\mathbf{p} - q\mathbf{A}_{cl})^2}{2m_0} + V(\mathbf{r}) + q\Phi_{cl}, \quad (10)$$

$$H_{int}(\mathbf{r}, \mathbf{p}, t) = -\frac{q}{m_0}(\mathbf{p} - q\mathbf{A}_{cl}(\mathbf{r}, t))\mathbf{A}_{rad}(t). \quad (11)$$

Radiation will be treated in terms of a photon-propagator, additionally  $\mathbf{A}_{cl}$  enters as vertex operator.

In thermal equilibrium ( $\mathbf{A} = \Phi = 0$ ) the Green-functions Eqs. (6,7) can be represented in terms of Bloch-

functions of Eq. (8) ( $\mathbf{A} = \Phi = 0$ ),

$$\hat{\mathbf{G}}_0(\mathbf{R}; \mathbf{r}, t) = \sum_{n, \mathbf{k}} \langle \mathbf{R} + \frac{\mathbf{r}}{2} | n, \mathbf{k} \rangle \hat{\mathbf{g}}_{n,0}(\mathbf{k}, t) \langle n, \mathbf{k} | \mathbf{R} - \frac{\mathbf{r}}{2} \rangle \quad (12)$$

where

$$\hat{\mathbf{g}}_{n,0} = \begin{bmatrix} -i\theta(t) e^{-iE_n t} & -i(1 - 2f_{n,0}(\mathbf{k})) e^{-iE_n t} \\ 0 & i\theta(-t) e^{-iE_n t} \end{bmatrix}. \quad (13)$$

$f_{n,0}(\mathbf{k})$  denotes the Fermi-function. Here, and in the following units are used where  $\hbar = 1$ .

The radiation field will be treated as an external quasi-classical field with no internal dynamics, i.e. there exists only a contribution to the Keldysh-component of the photon Green-function  $\hat{\mathbf{D}}$ ,

$$D_{\mu\nu}^K(t) = -i \frac{I}{\omega^2 \epsilon_0 c \eta} (e_\mu e_\nu^* e^{-i\omega t} + cc), \quad (14)$$

$cc$  means complex conjugate, for a derivation see App. A.

The equation of motion for  $\hat{\mathbf{G}}$  is identical with the Dyson-equation

$$\hat{\mathbf{G}}_0^{-1} \otimes \hat{\mathbf{G}} = \delta(\mathbf{r})\delta(t)\hat{\mathbf{1}} + \hat{\Sigma} \otimes \hat{\mathbf{G}}, \quad (15)$$

$$\hat{\mathbf{G}}_0^{-1} = (i\partial_{t_1} - H_{cl}(\mathbf{r}_1, \mathbf{p}_1, t_1)) \hat{\mathbf{1}}. \quad (16)$$

$\otimes$  means matrix-multiplication,  $H_{cl}$  stands for Eq. (10), and  $\hat{\Sigma}$  denotes the electron-photon self-energy which is calculated using  $\hat{\mathbf{D}}$  from Eq. (14) with  $-\frac{q}{m_0}(\mathbf{p} - q\mathbf{A}_{cl})$  as the vertex-operator (Ref.<sup>43</sup>, Sec.IIC).

## B. Kinetic equations

In order to set up a quasiclassical description the following (standard) approximation for the Green-function with inclusion of the external electromagnetic field is made, Baym<sup>44</sup> (p. 74)

$$\hat{\mathbf{G}}(\mathbf{R}, T; \mathbf{r}, t) = \sum_{n, n', \mathbf{k}} \langle \mathbf{R} + \frac{\mathbf{r}}{2} | n, \mathbf{k} \rangle \hat{\mathbf{g}}_{nn'}(\mathbf{R}, T; \mathbf{k}, t) \langle n', \mathbf{k} | \mathbf{R} - \frac{\mathbf{r}}{2} \rangle e^{iq[\mathbf{r}\mathbf{A}_{cl}(\mathbf{R}, T) - t\Phi_{cl}(\mathbf{R}, T)]} \quad (17)$$

where

$$\hat{\mathbf{g}}_{nn'}(\mathbf{R}, T; \mathbf{k}, t) = \begin{bmatrix} g_{nn'}^R & g_{nn'}^K \\ 0 & g_{nn'}^A \end{bmatrix}.$$

Here,  $I(\mathbf{R}, T)$ ,  $\mathbf{A}_{cl}(\mathbf{R}, T)$  ( $\mathbf{B} = \nabla \times \mathbf{A}_{cl}(\mathbf{R}, T)$ ) and  $\Phi_{cl}(\mathbf{R}, T)$  ( $\mathbf{E} = -\partial_T \mathbf{A}_{cl}(\mathbf{R}, T) - \nabla \Phi_{cl}(\mathbf{R}, T)$ ) denote classical macroscopic fields which are assumed constant on atomic scales so that Bloch-functions are still a suitable basis and will be only noticeable in  $\hat{\mathbf{g}}_{nn'}$ . The phase factor  $e^{iq\mathbf{r}\mathbf{A}_{cl}(\mathbf{R}, T)}$  takes into account the phase shift induced by a vector potential  $\mathbf{A}_{cl}$  along the direct path of the particle from  $\mathbf{r}_2$  to  $\mathbf{r}_1$  and reduces the contribution of the diamagnetic part  $q\mathbf{A}_{cl}$  in the vertex operator

$-\frac{q}{m_0}(\mathbf{p} - q\mathbf{A}_{cl})$ . Likewise,  $e^{-iq\mathbf{r}\mathbf{A}_{cl}(\mathbf{R}, T)}$  collects the local shifts of the energy levels due to an electrical potential  $\Phi_{cl}(\mathbf{R}, T)$ .

Observable quantities such as the charge current density  $\mathbf{j}_q$  are calculated with the aid of the Keldysh-component  $\langle G^K(\mathbf{R}, t; \mathbf{r}, t) \rangle$ , averaged over the volume of an elementary cell, of Eq. (17) to

$$\mathbf{j}_q(\mathbf{R}, T) = -i \frac{q}{m_0} \left( \frac{1}{i} \nabla_{\mathbf{r}} - q\mathbf{A}_{cl} \right) \langle G^K(\mathbf{R}, T; \mathbf{r}, t) \rangle |_{\mathbf{r}=0, t=0}$$

where the spin factor of two is already included here. Using the definition  $f_{nn'}(\mathbf{R}, T; \mathbf{k}) = \frac{1}{2i} g_{nn'}^K(\mathbf{R}, T; \mathbf{k}, t=0)$ ,

the charge current density becomes in terms of  $\mathbf{f}$

$$\mathbf{j}_q(\mathbf{R}, T) = \frac{2q}{m_0 V} \sum_{n, n', \mathbf{k}} f_{nn'}(\mathbf{R}, T, \mathbf{k}) \langle n', \mathbf{k} | \mathbf{p} | n, \mathbf{k} \rangle. \quad (18)$$

$V$  is the volume of the crystal.

We are looking for the current-contribution which is linear in the intensity (quadratic in the E-field), therefore, only the "turtle" photon self-energy diagram is needed. For the Feynman-rules see Ref.<sup>43</sup> (Eqs. (2.39-2.43)). Moreover, only the antihermitian parts of the self-energies  $\hat{\Sigma}$  (photons and phonons), will be taken into account, because these describe irreversible processes

that occur in consequence of the absorption processes. Hermitian parts of  $\hat{\Sigma}$ , on the contrary, describe band-renormalization effects which can be safely neglected<sup>45</sup>.

The basic equations for  $f_{nn'}$  are obtained from the Dyson-equation by subtracting its adjoint, [ $\dots = \dots$ ], and performing the integral transformation (Ref.<sup>43</sup>, Sec.IIE):

$$-\frac{1}{2} \int d^3 R \int d^3 r \langle n, \mathbf{k} | \mathbf{R} + \frac{\mathbf{r}}{2} \rangle \langle \mathbf{R} - \frac{\mathbf{r}}{2} | n', \mathbf{k} \rangle \times e^{-iq[\mathbf{r} \mathbf{A}_{el}(\mathbf{R}, T) - t \Phi_{el}(\mathbf{R}, T)]} [\dots = \dots].$$

$\mathbf{R}$ - and  $\mathbf{r}$ -integrations extend over a unit-cell and the whole crystal, respectively. Eventually, the relative time  $t$  is set equal to zero. As the result, we obtain:

---

Diagonal elements  $f_n = f_{nn}$ :

$$(\partial_T + q\mathbf{E} \cdot \nabla_{\mathbf{k}}) f_n(\mathbf{R}, T; \mathbf{k}) + \nabla_{\mathbf{R}} \cdot \mathbf{j}_n(\mathbf{R}, T; \mathbf{k}) + q\mathbf{B} \cdot (\nabla_{\mathbf{k}} \times \mathbf{j}_n(\mathbf{R}, T; \mathbf{k})) = G_n^{(0)}(\mathbf{R}, T; \mathbf{k}) + \delta G_n^{(\mathbf{B})}(\mathbf{R}, T; \mathbf{k}) + I_{n, pn} + I_{n, r}. \quad (19)$$

This is a modified Boltzmann equation for the distribution function  $f_n$  of band  $n$ . The total particle current density  $\mathbf{j}_n(\mathbf{R}, T; \mathbf{k})$  in the drift- and acceleration terms act as driving terms

$$\mathbf{j}_n(\mathbf{R}, T; \mathbf{k}) = \frac{1}{2m_0} \sum_{n'} (\langle n, \mathbf{k} | \mathbf{p} | n', \mathbf{k} \rangle f_{n'n}(\mathbf{R}, T; \mathbf{k}) + hc) = \mathbf{v}_n(\mathbf{k}) f_n(\mathbf{R}, T; \mathbf{k}) + \mathbf{j}_n^{ND}(\mathbf{R}, T; \mathbf{k}), \quad (20)$$

where  $hc$  means hermitian conjugate.  $G_n^{(0)}$ ,  $\delta G_n^{(\mathbf{B})}$ ,  $I_{n, pn}$  and  $I_{n, r}$  will be defined below.

In Eq. (20), the particle current density is decomposed in terms of a kinetic and a "nondiagonal" contribution  $\mathbf{j}_n^{ND}$  (see Eq. (26) below). The latter corresponds to the particle shift-current density of the state  $\mathbf{k}$  in the band  $n$  and is only different from zero if absorption of radiation causes an interband transition.

Nondiagonal elements  $f_{nn'}$  ( $n \neq n'$ ):

$$i(E_n(\mathbf{k}) - E_{n'}(\mathbf{k})) f_{nn'}(\mathbf{R}, T; \mathbf{k}) = G_{nn'}^{(0)}(\mathbf{R}, T; \mathbf{k}) + \delta G_{nn'}^{(\mathbf{B})}(\mathbf{R}, T; \mathbf{k}) + \delta G_{nn'}^{(\mathbf{E})}(\mathbf{R}, T; \mathbf{k}). \quad (21)$$

These elements are determined by a comparatively simple equation, because there is a dominant term ( $i(E_n - E_{n'}) f_{nn'}$ ) on the left side of this equation, against which all others ( $\partial_T f_{nn'}$ ,  $q\mathbf{E} \cdot \nabla_{\mathbf{k}} f_{nn'}$ , etc.), can safely be neglected. In order to get a closed set of equations, the particle current density  $\mathbf{j}_n$  and the generation matrix  $G_{nn'}$  have still to be specified.

The generation matrix  $G_{nn'}(\mathbf{R}, T; \mathbf{k})$  consists of the exclusively intensity-dependent part  $G_{nn'}^{(0)}$  with diagonal elements  $G_n^{(0)} = G_{nn}^{(0)}$  and the parts  $\delta G_{nn'}^{(\mathbf{B})}$  and  $\delta G_{nn'}^{(\mathbf{E})}$  which depend linearly on  $\mathbf{B}$  and  $\mathbf{E}$ , respectively. The latter parts stem from the phase factor in Eq. (17) and their diagonal elements  $\delta G_n^{(\mathbf{B})}$ ,  $\delta G_n^{(\mathbf{E})}$  are all equal to zero (dependence on  $(\mathbf{R}, T; \mathbf{k})$  suppressed). In addition, there is a contribution  $\delta G_n^{(\mathbf{B}, dia)}$  from the diamagnetic part of

---

the vertex operator to Eq. (19) which is exploited in Appendix B.

$I_{n, pn}$  describes the momentum relaxation (e.g. by phonon collisions) and  $I_{n, r}$  describes thermalization and recombination. As  $G_{nn'}$  is a hermitian matrix, it is conveniently written in the form

$$G_{nn'}(\mathbf{k}) = \bar{G}_{nn'}(\mathbf{k}) + hc. \quad (22)$$

There are three contributions to the generation rate  $G_{nn'}$

$$\begin{aligned} \bar{G}_{nn'}^{(0)}(\mathbf{R}, T; \mathbf{k}) = I(\mathbf{R}, T) \frac{\pi q^2}{2\omega^2 m_0^2 \epsilon_0 c \eta} \sum_{\substack{n_1 \\ \Omega = \pm\omega}} (f_{n_1, 0}(\mathbf{k}) - f_{n', 0}(\mathbf{k})) \delta(E_{n_1}(\mathbf{k}) - E_{n'}(\mathbf{k}) - \Omega) \times \\ \langle n, \mathbf{k} | p_\mu | n_1, \mathbf{k} \rangle \langle n_1, \mathbf{k} | p_\nu | n', \mathbf{k} \rangle e_{\mu, \Omega}^* e_{\nu, \Omega}, \end{aligned} \quad (23)$$

$$\begin{aligned} \delta \bar{G}_{nn'}^{(\mathbf{B})}(\mathbf{R}, T; \mathbf{k}) &= I(\mathbf{R}, T) \frac{\pi q^3}{4\omega^2 m_0^2 \epsilon_0 c \eta} \sum_{\substack{n_1, n_2 \\ \Omega = \pm\omega}} \left\{ [\nabla_{\mathbf{Q}_1} \times \nabla_{\mathbf{Q}_2}]_{\beta} [(f_{n_2,0}(\mathbf{k} + \mathbf{Q}_2) - f_{n_1,0}(\mathbf{k} + \mathbf{Q}_1)) \times \right. \\ &\quad \left. \delta(E_{n_2}(\mathbf{k} + \mathbf{Q}_2) - E_{n_1}(\mathbf{k} + \mathbf{Q}_1) - \Omega) \times \right. \\ &\quad \left. (n, \mathbf{k} | p_{\mu} + k_{\mu} | n_1, \mathbf{k} + \mathbf{Q}_1) (n_1, \mathbf{k} + \mathbf{Q}_1 | p_{\nu} + k_{\nu} | n_2, \mathbf{k} + \mathbf{Q}_2) (n_2, \mathbf{k} + \mathbf{Q}_2 | n', \mathbf{k}) (1 - \delta_{n,n'}) \right\} B_{\beta} \frac{1}{i} e_{\mu, \Omega}^* e_{\nu, \Omega}, \quad (24) \end{aligned}$$

$$\begin{aligned} \delta \bar{G}_{nn'}^{(\mathbf{E})}(\mathbf{R}, T; \mathbf{k}) &= I(\mathbf{R}, T) \frac{\pi q^3}{4\omega^2 m_0^2 \epsilon_0 c \eta} \sum_{\substack{n_1 \\ \Omega = \pm\omega}} \left\{ \nabla_{\mathbf{Q}, \alpha} [(f_{n',0}(\mathbf{k} + \mathbf{Q}) - f_{n_1,0}(\mathbf{k} + \mathbf{Q})) \times \right. \\ &\quad \left. \partial_{\Omega} \delta(E_{n_1}(\mathbf{k} + \mathbf{Q}) - E_{n'}(\mathbf{k} + \mathbf{Q}) + \Omega) \times \right. \\ &\quad \left. (n, \mathbf{k} | p_{\mu} + k_{\mu} | n_1, \mathbf{k} + \mathbf{Q}) (n_1, \mathbf{k} + \mathbf{Q} | p_{\nu} + k_{\nu} | n', \mathbf{k}) \right\} E_{\alpha} \frac{1}{i} e_{\mu, \Omega}^* e_{\nu, \Omega}. \quad (25) \end{aligned}$$

After differentiation, the vectors  $\mathbf{Q}$ ,  $\mathbf{Q}_1$  and  $\mathbf{Q}_2$  have to be set to zero. The expressions  $(n_1, \mathbf{k}_1 | \dots | n_2, \mathbf{k}_2)$  are matrix elements, which are calculated with respect to the lattice periodic parts of the Bloch-functions,  $e_{\mu, \omega} = e_{\mu}$  and  $e_{\mu, -\omega} = e_{\mu}^*$  are the components of the complex-valued polarization vector.

$\mathbf{j}_n^{ND}$  is obtained from Eq. (20) with  $\bar{G}_{nn'}^{(0)}$  from Eq. (23):

$$j_{n,\alpha}^{ND}(\mathbf{R}, T; \mathbf{k}) = \frac{1}{m_0} \sum_{m \neq n} \text{Im} \left( \frac{\langle n, \mathbf{k} | p_{\alpha} | m, \mathbf{k} \rangle \bar{G}_{mn}^{(0)}(\mathbf{R}, T; \mathbf{k}) + \bar{G}_{nm}^{(0)*}(\mathbf{R}, T; \mathbf{k}) \langle m, \mathbf{k} | p_{\alpha} | n, \mathbf{k} \rangle^*}{E_m - E_n} \right) \quad (26)$$

$$= I(\mathbf{R}, T) \frac{\pi e^2}{2\omega^2 m_0^3 \epsilon_0 c \eta} \sum_{\substack{m \neq n, n_1 \\ \Omega = \pm\omega}} [(f_{n_1,0} - f_{n,0}) \delta(E_{n_1} - E_n - \Omega) + (f_{n_1,0} - f_{m,0}) \delta(E_{n_1} - E_m - \Omega)] \quad (27)$$

$$\times \left[ \text{Im} \left( \frac{\langle n, \mathbf{k} | p_{\alpha} | m, \mathbf{k} \rangle \langle m, \mathbf{k} | p_{\mu} | n_1, \mathbf{k} \rangle \langle n_1, \mathbf{k} | p_{\nu} | n, \mathbf{k} \rangle}{E_m - E_n} \right) \text{Re}(e_{\mu, \Omega}^* e_{\nu, \Omega}) + \right. \quad (28)$$

$$\left. \text{Re} \left( \frac{\langle n, \mathbf{k} | p_{\alpha} | m, \mathbf{k} \rangle \langle m, \mathbf{k} | p_{\mu} | n_1, \mathbf{k} \rangle \langle n_1, \mathbf{k} | p_{\nu} | n, \mathbf{k} \rangle}{E_m - E_n} \right) \text{Im}(e_{\mu, \Omega}^* e_{\nu, \Omega}) \right]. \quad (29)$$

The term (28) is an even function of  $\mathbf{k}$  that contributes to  $\mathbf{P}^S$ , Eq. (32), whereas the odd term (29) does not.

### III. DERIVATION OF THE PG-TENSORS

As an application of the kinetic theory we verify the result Eq. (2) for  $\mathbf{P}^S$ , and give the representations of the other PG-tensors  $\mathbf{P}^A$ ,  $\mathbf{R}^S$  and  $\mathbf{R}^A$  as defined by Eq. (1). The following assumptions are made: (i) no

external electrical field, (ii) external magnetic field  $\mathbf{B}$  as well as the (monochromatic) radiation intensity  $I$  is constant in space and time so that  $f_{nn'}$  does not depend on  $(\mathbf{R}, T)$ . Under these assumptions the kinetic equations (19-21) become

$$n = n' : \quad q \mathbf{B} \cdot (\nabla_{\mathbf{k}} \times \mathbf{j}_n(\mathbf{k})) = G_n^{(0)}(\mathbf{k}) - \frac{f_n(\mathbf{k}) - \langle f_n(\mathbf{k}) \rangle_E}{\tau_n} + I_{n,r}, \quad (30)$$

$$n \neq n' : \quad i (E_n(\mathbf{k}) - E_{n'}(\mathbf{k})) f_{nn'}(\mathbf{k}) = G_{nn'}^{(0)}(\mathbf{k}) + \delta G_{nn'}^{(\mathbf{B})}(\mathbf{k}). \quad (31)$$

In addition, Eqs. (20) and (26–29) will be needed.

To simplify matters, the collision operator  $I_{n,pn}$  was replaced within a relaxation time approximation.  $\langle f_n(\mathbf{k}) \rangle_E$  denotes the average of the distribution function over a surface of constant energy and  $\tau_n$  is the relaxation time for each band  $n$ , numerical values are taken from experiment. The operator  $I_{n,r}$  which ensures thermalization and recombination is assumed to be only energy-

dependent. Obviously, the PG-current solely stems from  $f_{nn'}(\mathbf{k})$ -terms which are asymmetric with respect to  $\mathbf{k}$ ,  $\delta f_{nn'}(\mathbf{k}) = -\delta f_{nn'}^*(-\mathbf{k})$ , which in turn originate from generation terms with  $\delta G_n(\mathbf{k}) = -\delta G_n(-\mathbf{k})$  and  $\delta G_{nn'}(\mathbf{k}) = \delta G_{nn'}^*(-\mathbf{k})$ . Therefore, only such terms will be considered when deriving representations for the tensors.

### A. Tensor $\mathbf{P}^S$

Linearly polarized light and  $\mathbf{B} = 0$  is implied in Eqs. (30,31). The relevant contributions of the state function are:

$$\begin{aligned} n = n' : \quad & \delta f_n = 0, \\ n \neq n' : \quad & \delta f_{nn'} = \frac{G_{nn'}^{(0)}(\mathbf{k})}{i(E_n(\mathbf{k}) - E_{n'}(\mathbf{k}))}. \end{aligned}$$

The corresponding PG-current density  $\mathbf{j}_{\text{PG}}$  is determined

from Eq. (26) by summation over all states (including the spin factor of two)

$$\mathbf{j}_{\text{PG}} = \frac{2q}{V} \sum_{n,\mathbf{k}} \mathbf{j}_n^{ND}(\mathbf{k}),$$

which is performed along the route described in Refs.<sup>9,11</sup>. As a result, we obtain<sup>12</sup>:

$$\begin{aligned} P_{\alpha\mu\nu}^S = & \frac{e^3}{4\pi^2 \omega^2 m_0^2 \epsilon_0 c \eta} \int_{1.BZ} d^3k (f_{v,0} - f_{c,0}) \delta(E_c(\mathbf{k}) - E_v(\mathbf{k}) - \omega) \times \\ & \left\{ \frac{1}{2} \text{Im}[(\nabla_{\mathbf{k},\alpha} \langle c, \mathbf{k} | p_\nu | v, \mathbf{k} \rangle) \langle v, \mathbf{k} | p_\mu | c, \mathbf{k} \rangle - \langle c, \mathbf{k} | p_\nu | v, \mathbf{k} \rangle (\nabla_{\mathbf{k},\alpha} \langle v, \mathbf{k} | p_\mu | c, \mathbf{k} \rangle)] \right. \\ & \left. + \text{Re}[\langle c, \mathbf{k} | p_\nu | v, \mathbf{k} \rangle \langle v, \mathbf{k} | p_\mu | c, \mathbf{k} \rangle [X_{vv,\alpha} - X_{cc,\alpha}]] \right\}. \end{aligned} \quad (32)$$

Equation (32) is identical with Eq. (2) as can be checked by decomposing  $\mathbf{e} \cdot \mathbf{p}$  into components.

### B. Tensor $\mathbf{P}^A$

Circular polarized light and  $\mathbf{B} = 0$  is implied in Eqs. (30,31). The relevant contribution of the state function to determine  $\mathbf{P}^A$  is:

$$n = n' : \quad \delta f_n = \tau_n \delta G_n^{(0)}(\mathbf{k}), \quad (33)$$

$$n \neq n' : \quad \delta f_{nn'} = 0. \quad (34)$$

$\delta G_n^{(0)}(\mathbf{k})$  is the part of the generation rate  $G_n^{(0)}(\mathbf{k})$  as given by Eqs. (22,23),

$$\begin{aligned} \delta G_n^{(0)}(\mathbf{k}) = & I \frac{\pi q^2}{\omega^2 m_0^2 \epsilon_0 c \eta} \sum_{\substack{n' \\ \Omega = \pm\omega}} (f_{n,0}(\mathbf{k}) - f_{n',0}(\mathbf{k})) \delta(E_{n'}(\mathbf{k}) - E_n(\mathbf{k}) - \Omega) \\ & \times \text{Im}(\langle n, \mathbf{k} | p_\mu | n', \mathbf{k} \rangle \langle n', \mathbf{k} | p_\nu | n, \mathbf{k} \rangle) \text{Im}(e_{\mu,\Omega}^* e_{\nu,\Omega}). \end{aligned} \quad (35)$$

Insertion of Eq. (33) and Eq. (35) into Eq. (18) leads to

$$j_\alpha^{circ} = \frac{2q}{V} \sum_{\substack{n=v,c \\ \mathbf{k}}} v_{n,\alpha}(\mathbf{k}) \delta f_n(\mathbf{k}), \quad (36)$$

and the tensor element  $P_{\alpha\mu\nu}^A$  reads:

$$\begin{aligned} P_{\alpha\mu\nu}^A = & \frac{e^3}{4\pi^2 \omega^2 m_0^2 \epsilon_0 c \eta} \sum_{\substack{n',n \\ \Omega = \pm\omega}} \int_{1.BZ} d^3k (f_{n',0}(\mathbf{k}) - f_{n,0}(\mathbf{k})) \delta(E_{n'}(\mathbf{k}) - E_n(\mathbf{k}) - \Omega) \times \\ & \tau_n v_{n,\alpha}(\mathbf{k}) (\delta_{v,n} + \delta_{c,n}) \text{Im}(\langle n, \mathbf{k} | p_\mu | n', \mathbf{k} \rangle \langle n', \mathbf{k} | p_\nu | n, \mathbf{k} \rangle) \text{sign}(\Omega). \end{aligned} \quad (37)$$

Performing the sums over  $\Omega$ ,  $n$  and  $n'$ , we obtain<sup>12</sup>:

$$\begin{aligned} P_{\alpha\mu\nu}^A = & \frac{e^3}{4\pi^2 \omega^2 m_0^2 \epsilon_0 c \eta} \int_{1.BZ} d^3k (f_{v,0}(\mathbf{k}) - f_{c,0}(\mathbf{k})) \delta(E_c(\mathbf{k}) - E_v(\mathbf{k}) - \omega) \times \\ & (\tau_c v_{c,\alpha}(\mathbf{k}) - \tau_v v_{v,\alpha}(\mathbf{k})) \text{Im}(\langle v, \mathbf{k} | p_\mu | c, \mathbf{k} \rangle \langle c, \mathbf{k} | p_\nu | v, \mathbf{k} \rangle). \end{aligned} \quad (38)$$

In contrast to the linear PGE ( $\mathbf{P}^S$ -term) the circular PGE is ballistic as only diagonal elements of the state function contribute and it depends on the scattering times of the (hot) photo-generated carriers.

### C. Tensor $\mathbf{R}^S$

Linearly polarized light and  $\mathbf{B} \neq 0$  is implied in Eqs. (30,31). The relevant contributions of the state function are:

$$n = n' : \delta f_n = -q \tau_n \mathbf{B} \cdot [\nabla_{\mathbf{k}} \times \mathbf{j}_n(\mathbf{k})], \quad (39)$$

$$n \neq n' : \delta f_{nn'} = \frac{G_{nn'}^{(0)}(\mathbf{k})}{i(E_n(\mathbf{k}) - E_{n'}(\mathbf{k}))}. \quad (40)$$

The first equation describes the portion of the charge current density which is deflected by the magnetic field, analogous to the Hall-effect. The current density  $\mathbf{j}_n(\mathbf{k})$  is inserted from Eq. (20) and the contribution of Eq. (40) is used therein as the driving term. The resulting charge current density  $\mathbf{j}^{\text{Hall}}$  reads:

$$\begin{aligned} j_\alpha^{\text{Hall}} &= \frac{2q}{V} \sum_{\substack{n=v,c \\ \mathbf{k}}} v_{n,\alpha}(\mathbf{k}) \delta f_n(\mathbf{k}) = \frac{-2q^2}{V} B_\beta \epsilon_{\beta\gamma\delta} \sum_{\substack{n=v,c \\ \mathbf{k}}} v_{n,\alpha}(\mathbf{k}) \tau_n \nabla_{\mathbf{k},\gamma} j_{n,\delta}^{\text{ND}}(\mathbf{k}), \\ j_\alpha^{\text{Hall}} &= \frac{2q^2}{V} B_\beta \epsilon_{\beta\gamma\delta} \sum_{\substack{n=v,c \\ \mathbf{k}}} \nabla_{\mathbf{k},\gamma} (v_{n,\alpha}(\mathbf{k}) \tau_n) j_{n,\delta}^{\text{ND}}(\mathbf{k}). \end{aligned} \quad (41)$$

Inserting Eqs. (27,28) into Eq. (41), we get for the tensor element  $R_{\alpha\beta\mu\nu}^S$  the expression:

$$\begin{aligned} R_{\alpha\beta\mu\nu}^S &= \frac{e^4}{16\pi^2 \omega^2 m_0^3 \epsilon_0 c \eta} \epsilon_{\beta\gamma\delta} \sum_{\substack{m \neq n, n_1 \\ n, \Omega = \pm \omega}} \int_{1.BZ} d^3k (f_{n_1,0}(\mathbf{k}) - f_{n,0}(\mathbf{k})) \delta(E_{n_1}(\mathbf{k}) - E_n(\mathbf{k}) - \Omega) \times \\ &\quad (\nabla_{\mathbf{k},\gamma} [\tau_n v_{n,\alpha}(\mathbf{k})(\delta_{v,n} + \delta_{c,n}) + \tau_m v_{m,\alpha}(\mathbf{k})(\delta_{v,m} + \delta_{c,m})]) \times \\ &\quad \text{Im} \left( \frac{\langle n, \mathbf{k} | p_\delta | m, \mathbf{k} \rangle \langle m, \mathbf{k} | p_\mu | n_1, \mathbf{k} \rangle \langle n_1, \mathbf{k} | p_\nu | n, \mathbf{k} \rangle}{E_m - E_n} + \text{terms with } \mu \text{ and } \nu \text{ interchanged} \right). \end{aligned} \quad (42)$$

Performing all sums<sup>12</sup> leads to  $\mathbf{R}^S$ :

$$\begin{aligned} R_{\alpha\beta\mu\nu}^S &= \frac{e^4}{16\pi^2 \omega^2 m_0^3 \epsilon_0 c \eta} \epsilon_{\beta\gamma\delta} \int_{1.BZ} d^3k (f_{v,0}(\mathbf{k}) - f_{c,0}(\mathbf{k})) \delta(E_c(\mathbf{k}) - E_v(\mathbf{k}) - \omega) \times \\ &\quad \left\{ (\nabla_{\mathbf{k},\gamma} \tau_c v_{c,\alpha}(\mathbf{k})) \left[ -\text{Im}(\langle v, \mathbf{k} | p_\nu | c, \mathbf{k} \rangle \langle c, \mathbf{k} | \mathcal{R}_\delta^\dagger p_\mu | v, \mathbf{k} \rangle) + \frac{v_{c,\mu}}{\omega} \text{Im}(\langle v, \mathbf{k} | p_\nu | c, \mathbf{k} \rangle \langle c, \mathbf{k} | p_\delta | v, \mathbf{k} \rangle) \right] \right. \\ &\quad \left. + (\nabla_{\mathbf{k},\gamma} \tau_v v_{v,\alpha}(\mathbf{k})) \left[ -\text{Im}(\langle v, \mathbf{k} | p_\nu | c, \mathbf{k} \rangle \langle c, \mathbf{k} | p_\mu \mathcal{R}_\delta | v, \mathbf{k} \rangle) - \frac{v_{v,\mu}}{\omega} \text{Im}(\langle v, \mathbf{k} | p_\nu | c, \mathbf{k} \rangle \langle c, \mathbf{k} | p_\delta | v, \mathbf{k} \rangle) \right] \right. \\ &\quad \left. \text{plus all terms with } \mu \text{ and } \nu \text{ interchanged} \right\}. \end{aligned} \quad (43)$$

$\mathcal{R}$  is the shift operator<sup>9,11</sup>, in position representation

$$\mathcal{R}_{n,\mathbf{k}}(\mathbf{r}) = \langle \mathbf{r} | \mathcal{R} | n, \mathbf{k} \rangle = e^{i\mathbf{k}\mathbf{r}} \{ \nabla_{\mathbf{k}} + i\mathbf{X}_{nn}(\mathbf{k}) \} u_{n\mathbf{k}}(\mathbf{r}).$$

The shift operator  $\mathcal{R}$  is of importance when photogalvanic current densities are described by the nondiagonal elements of the state function  $\mathbf{f}$ . In particular, the shift vector Eq. (3) can be expressed as:

$$\mathbf{s}_{cv}(\mathbf{e}, \mathbf{k}) = \frac{\text{Im}(\langle c, \mathbf{k} | \mathcal{R}^\dagger \mathbf{e} p + \mathbf{e} p \mathcal{R} | v, \mathbf{k} \rangle \langle v, \mathbf{k} | \mathbf{e} p | c, \mathbf{k} \rangle)}{\langle v, \mathbf{k} | \mathbf{e} p | c, \mathbf{k} \rangle \langle c, \mathbf{k} | \mathbf{e} p | v, \mathbf{k} \rangle}. \quad (44)$$

The elements of  $\mathbf{R}^S$  show almost the same  $\omega$ -dependence as those of  $\mathbf{P}^S$  and - as a rule of the thumb -  $|R^S| \approx |P^S| \cdot \mu$  may be expected, where  $\mu$  is the mobility of the (hot) photocarriers.

Result (43) is completed by the diamagnetic contribution Eq. (B3)

$$R_{\alpha\beta\mu\nu}^{S,dia} = \frac{e}{\omega m_0} \epsilon_{\beta\nu\gamma} P_{\alpha\mu\gamma}^A.$$

### D. Tensor $\mathbf{R}^A$

Circularly polarized light and  $\mathbf{B} \neq 0$  is implied in Eqs. (30,31). The relevant contributions are

$$n = n' : \delta f_n = -q\tau_n \mathbf{B} \cdot [\nabla_{\mathbf{k}} \times (\tau_n \mathbf{v}_n \delta G_n^{(0)})], \quad (45)$$

$$n \neq n' : \delta f_{nn'} = \frac{\delta G_{nn'}^{(\mathbf{B})}(\mathbf{k})}{i(E_n(\mathbf{k}) - E_{n'}(\mathbf{k}))}. \quad (46)$$

Equation (45) describes the deflection of the ballistic

charge current density Eq. (36) by the magnetic field and is present only – like  $\mathbf{P}^A$  – in gyrotropic media, whereas the contribution Eq. (46) is directly related to the change of the generation matrix by the external magnetic field  $\mathbf{B}$ . Therefore,  $\mathbf{R}^A$  consists of two contributions

$$\mathbf{R}^A = \mathbf{R}^{A,bal} + \mathbf{R}^{A,shift}. \quad (47)$$

#### 1. Tensor $\mathbf{R}^{A,bal}$

Equation (45) is equivalent to Eq. (39). Following the same route as taken by Eqs. (41,43) and using Eq. (35) we arrive at<sup>12</sup>:

$$R_{\alpha\beta\mu\nu}^{A,bal} = \frac{e^4}{4\pi^2 \omega^2 m_0^2 \epsilon_0 c \eta} \epsilon_{\beta\gamma\delta} \int_{1.BZ} d^3k (f_{v,0}(\mathbf{k}) - f_{c,0}(\mathbf{k})) \delta(E_c(\mathbf{k}) - E_v(\mathbf{k}) - \omega) \times (\tau_v v_{v,\delta}(\mathbf{k}) (\nabla_{\mathbf{k},\gamma} \tau_v v_{v,\alpha}(\mathbf{k})) - \tau_c v_{c,\delta}(\mathbf{k}) (\nabla_{\mathbf{k},\gamma} \tau_c v_{c,\alpha}(\mathbf{k}))) \text{Im}(\langle v, \mathbf{k} | p_\mu | c, \mathbf{k} \rangle \langle c, \mathbf{k} | p_\nu | v, \mathbf{k} \rangle). \quad (48)$$

#### 2. Tensor $\mathbf{R}^{A,shift}$

The corresponding current density is:

$$j_\alpha^{ND,\mathbf{B}} = \frac{4q}{m_0} \sum_{\substack{n,n' \\ n \neq n'}} \frac{1}{(2\pi)^3} \int_{1.BZ} \text{Im} \left( \frac{\langle n, \mathbf{k} | p_\alpha | n', \mathbf{k} \rangle \delta \bar{G}_{n'n}^{(\mathbf{B})}(\mathbf{k})}{E_{n'} - E_n} \right) d^3k. \quad (49)$$

Inserting  $\delta \bar{G}_{n'n}^{(\mathbf{B})}(\mathbf{k})$  from Eq. (24) and regrouping terms we get

$$j_\alpha^{ND,\mathbf{B}} = I \frac{e^4}{16\pi^2 \omega^2 m_0^3 \epsilon_0 c \eta} \sum_{\substack{n_1, n_2 \\ \Omega = \pm\omega}} \int_{1.BZ} d^3k \{ [\nabla_{\mathbf{Q}_1} \times \nabla_{\mathbf{Q}_2}]_\beta [(f_{n_2,0}(\mathbf{k} + \mathbf{Q}_2) - f_{n_1,0}(\mathbf{k} + \mathbf{Q}_1)) \times \delta(E_{n_2}(\mathbf{k} + \mathbf{Q}_2) - E_{n_1}(\mathbf{k} + \mathbf{Q}_1) - \Omega) \text{sign}(\Omega) M_{\alpha\mu\nu}^{n_1 n_2}(\mathbf{k}, \mathbf{Q}_1, \mathbf{Q}_2)] \} B_\beta \text{Im}(e_\mu^* e_\nu), \quad (50)$$

with

$$M_{\alpha\mu\nu}^{n_1 n_2}(\mathbf{k}, \mathbf{Q}_1, \mathbf{Q}_2) = \sum_{\substack{n, n' \\ n \neq n'}} \text{Im} \left\{ (n, \mathbf{k} | n_2, \mathbf{k} + \mathbf{Q}_2) (n_2, \mathbf{k} + \mathbf{Q}_2 | p_\nu + k_\nu | n_1, \mathbf{k} + \mathbf{Q}_1) \frac{(n_1, \mathbf{k} + \mathbf{Q}_1 | p_\mu + k_\mu | n', \mathbf{k}) (n', \mathbf{k} | p_\alpha + k_\alpha | n, \mathbf{k})}{E_n - E_{n'}} \right. \\ \left. \text{minus all terms with } \mu \text{ and } \nu \text{ interchanged} \right\}, \\ = m_0 \sum_n \text{Im} \left\{ (n, \mathbf{k} | n_2, \mathbf{k} + \mathbf{Q}_2) (n_2, \mathbf{k} + \mathbf{Q}_2 | p_\nu + k_\nu | n_1, \mathbf{k} + \mathbf{Q}_1) (n_1, \mathbf{k} + \mathbf{Q}_1 | (p_\mu + k_\mu) \mathcal{R}_\alpha | n, \mathbf{k}) \right. \\ \left. \text{minus all terms with } \mu \text{ and } \nu \text{ interchanged} \right\}. \quad (51)$$

In the expression (51) we have used the representation of shift operator  $\mathcal{R}$  with respect to the lattice-periodic part of the Bloch-functions,  $(\mathbf{r} | \mathcal{R} | n, \mathbf{k}) = (\nabla_{\mathbf{k}} + i\mathbf{X}_{nn}(\mathbf{k})) u_{n\mathbf{k}}(\mathbf{r})$ .

As a result, we obtain<sup>12</sup>:

$$R_{\alpha\beta\mu\nu}^{A,shift} = \frac{e^4}{16\pi^2 \omega^2 m_0^3 \epsilon_0 c \eta} \int_{1.BZ} d^3k \{ [\nabla_{\mathbf{Q}_1} \times \nabla_{\mathbf{Q}_2}]_\beta [(f_{v,0}(\mathbf{k} + \mathbf{Q}_1) - f_{c,0}(\mathbf{k} + \mathbf{Q}_2)) \times \delta(E_c(\mathbf{k} + \mathbf{Q}_2) - E_v(\mathbf{k} + \mathbf{Q}_1) - \omega) (M_{\alpha\mu\nu}^{cv}(\mathbf{k}, \mathbf{Q}_2, \mathbf{Q}_1) - M_{\alpha\mu\nu}^{vc}(\mathbf{k}, \mathbf{Q}_1, \mathbf{Q}_2))] \}. \quad (52)$$



After differentiation, the vectors  $\mathbf{Q}_1$  and  $\mathbf{Q}_2$  have to be set to zero.

Due to the differentiations with respect to  $\mathbf{Q}_1$  and  $\mathbf{Q}_2$ , even an approximate evaluation of the tensor elements of  $\mathbf{R}^A$  requires details of the band structure ( $E_n(\mathbf{k})$  and as well as momentum matrix elements), at least at a symmetry point  $\mathbf{k}_0$  where the optical transition occurs. If the bands are isotropic near  $\mathbf{k}_0$ , the cross-product operation ( $\nabla_{\mathbf{Q}_1} \times \nabla_{\mathbf{Q}_2}$ ) on terms which are exclusively dependent on the  $\mathbf{Q}_i$  via the energy  $E(\mathbf{k} + \mathbf{Q}_i)$  does not contribute. We therefore expect warped energy bands as a favorite ingredient for the circular shift magneto PGE.

#### IV. SUMMARY AND DISCUSSION

We have developed a systematic semiclassical description of the PGE within the Kadanoff–Baym–Keldysh technique which ensures gauge invariance as well as particle conservation from the beginning. In addition, band renormalization terms (hermitian parts of the self-energies  $\hat{\Sigma}$ ) are identified and external (slowly varying) electric and magnetic fields are included. This approach is based on a Boltzmann type equation for the diagonal elements of the state operator and captures nondiagonal contributions by simple algebraic equations – similar to the well known Semiconductor–Bloch–Equations<sup>42</sup> (yet without Coulomb interaction).

In our approach, the PGE is a bandstructure–property of the noncentrosymmetric crystal and the photogalvanic current is caused by the absorption of light in combination with (symmetric) scattering by phonons and impurities. Sects. III A–D give explicit results for the tensors  $\mathbf{P}^S$ ,  $\mathbf{P}^A$ ,  $\mathbf{R}^S$  and  $\mathbf{R}^A$ . Here, only the case of an external magnetic field was considered because the influence of an electrical field on the PGE was studied recently in detail by Fregoso<sup>48</sup>. Not included are (i) asymmetric scattering terms, (ii) magnetic field dependence of scattering, and (iii) transitions from bound impurity states. Result (32) for  $\mathbf{P}^S$  is identical with the known result of Eq.(2) and serves as a check whereas results for  $\mathbf{P}^A$ ,  $\mathbf{R}^S$ , and  $\mathbf{R}^A$  are new.  $\mathbf{P}^A$ , Eq.(38), is equivalent to Eq.(29) of Ref.<sup>37,56</sup>. Implementation of the p–matrixelements within DFT–calculations is described in Ref.<sup>57</sup>. Appendix C provides a numerical application to GaP.

For linear polarisation there are several examples which clearly demonstrate that the magnitude and spectral structure is dominated by the shift mechanism, (i) n–GaP<sup>14</sup> (pseudopotential theory) and (ii) BaTiO<sub>3</sub><sup>18,49</sup> (DFT including the calculated phonon spectrum and electron–phonon couplings). In both cases, there is almost perfect agreement with experiment<sup>15,50</sup>, nevertheless, asymmetric phonon contributions cannot be excluded in general. For GaAs a purely ballistic theory gave a good overall description, but the predicted spectrum differed from that observed<sup>51</sup>. For a critique of the shift mechanism as a main source of the PGE see

Sturman<sup>52</sup>.

Nonlocal aspects of the PGE are usually neglected but have been already shown up in connection with the analysis of volume–phase–holograms in Ferroelectrics<sup>53</sup>. Such phenomena are captured by the semiclassical description, Eqs. (19–21), and may become relevant for optical nano–devices as recently studied by local photoexcitation<sup>54</sup> or are under discussion in connection with spatio–temporal quantum pumping by femtosecond light pulses<sup>55</sup>.

Quantum kinetic descriptions for the PGE have been *cc* means complex conjugate implicitly used in several previous publications, e.g. Belinicher et al.<sup>10</sup>, Deyo et al.<sup>58</sup> worked–out a semiclassical theory of nonlinear transport and the PGE but only the influence of electric and magnetic fields on the scattering probabilities were considered, and, recently, Kral<sup>59</sup> presented a quasiclassical description of the PGE for the problem of electron pumping in semiconductors. Barik and Sau<sup>60</sup> showed that the PGE/BPVE can be attributed to the dipole moment of the photogenerated excitons which resembles the difference [ $X_{vv,\alpha} - X_{cc,\alpha}$ ] in Eq. (32). The first attempt, probably, for a systematic theory in terms of the Kadanoff–Baym–Keldysh technique has been undertaken by one of the present authors (D.H.) in Ref.<sup>61</sup>.

There are several numerical studies of the shift vector  $\mathbf{s}_{cv}(\mathbf{e}, \mathbf{k})$  as well as an analytic estimate to find optimal parameters (concerning bandstructure and polarization directions) for the PG–response<sup>18,62</sup>. These investigations, however, are based on a simplified version of the shift vector Eq. (3) with restricted combinations of the current– and light–polarization components (see around Eq. (58) of Ref.<sup>13</sup>). To overcome such restrictions, we have worked out the general coordinate–free form the shift vector given by Eqs. (2–4).

In an external magnetic field  $\mathbf{B}$ , the currents described by  $\mathbf{P}^S$  and  $\mathbf{P}^A$  are deflected like Hall currents which result in ballistic contributions described by  $\mathbf{R}^S$  (proportional to the mobility) and a  $\mathbf{R}^{A,bal}$  (proportional to the square of the mobility), see Eqs. (40) and (45). In addition,  $\mathbf{R}^A$  includes a shift contribution  $\mathbf{R}^{A,shift}$ , which is related to the influence of magnetic field  $\mathbf{B}$  on the generation matrix  $G_{nn'}(\mathbf{k})$ . Concerning the experimental situation we refer to the work of Fridkin and his group, see Refs.<sup>1,63</sup>. For Tellurium theoretical and experimental studies are due to Ivchenko et al.<sup>64,65</sup>. However, application of their theoretical results in first principle calculations seem not straightforward.

The Hall–property of the linear PGE in a magnetic field (described by  $\mathbf{R}^S$ ) has been used to determine the mobility of photogenerated charge carriers<sup>51,63,66</sup>. Very large mobilities have been reported: GaAs  $0.5 \times 10^6 \text{cm}^2/\text{Vs}$  (4.2K), piezoelectric Bi<sub>12</sub>GeO<sub>20</sub> (point group 23) approximately  $6000 \text{cm}^2/\text{Vs}$ , and ferroelectric BaTiO<sub>3</sub> (point group 4mm) up to  $1900 \text{cm}^2/\text{Vs}$  (room temperature). The analysis of the measurements is based

on the standard Hall–formula

$$\mathbf{j}^{Hall} = \mu \mathbf{j}^{(0)} \times \mathbf{B} \quad (53)$$

which stems from a Drude–type description and holds under isotropic conditions. For  $\text{Bi}_{12}\text{GeO}_{20}$  the PG–current without magnetic field  $\mathbf{j}^{(0)}$  is strongest just below the gap (3.2eV) and is believed to originate from impurity transitions into conduction band, i.e. is of ballistic type. Hence, Eq. (53) is a suitable basis for the experimental analysis. For  $\text{BaTiO}_3$ , however, the PGE is mainly due to interband transitions<sup>18,49,50</sup> so that Eq. (53) is not appropriate, even if  $\mu_c \gg \mu_v$ , compare Eq. (32) with (43).

The idea to separate shift and ballistic contributions of the PG–current by using a magnetic field in combination with linear and circular polarized light has been pursued by Fridkin and collaborators, see e.g. Ref.<sup>63</sup> and, more recently, by Burger et al.<sup>67,68</sup> for  $\text{Bi}_{12}\text{GeO}_{20}$  and  $\text{Bi}_{12}\text{SiO}_{20}$ . Their analysis, however, is based on the assumption that the shift mechanism does not contribute to the photo Hall current (“ $j_{sh}$  describes coherence between wave packets rather than a transport process”, see above Eq. (1) of Ref.<sup>68</sup>) which is at odds with our results as given by Eqs. (41) and (49). It is also in contradiction with a previous result of Ref.<sup>65</sup> (their formula (13)). Moreover, in these studies the PG–current is due to (“ballistic”) impurity transitions and does not originate from interband transitions which are the origin of the shift mechanism<sup>69</sup>.

## ACKNOWLEDGMENTS

We thank Peter Wölfle for his advice and support with the preparation of the manuscript and Binghai Yan and Zhenbang Dai for discussions.

## Appendix A: Photon Green–function

The Keldysh–Green–function  $\mathbf{D}_{\mu\nu}$  for photons has the usual Jordan normal–form and each matrix element is a

polar tensor of rank two. We start from (Ref.<sup>43</sup>, Sec. IIA)

$$D_{\mu\nu}^<(\mathbf{r}_1, t_1; \mathbf{r}_2, t_2) = -i \langle \langle A_\nu(\mathbf{r}_2, t_2) A_\mu(\mathbf{r}_1, t_1) \rangle \rangle. \quad (A1)$$

$A_\mu(\mathbf{r}_j, t_j)$  ( $j = 1, 2$ ) denotes the (hermitian) vector potential (–field operator) of the radiation and  $\mu, \nu$  refer to the polarization of the photons.  $D_{\mu\nu}^>(\mathbf{r}_1, t_1; \mathbf{r}_2, t_2) = D_{\nu\mu}^<(\mathbf{r}_2, t_2; \mathbf{r}_1, t_1)$ , the other photon–correlation function are defined in the same way as for the electrons.

As thermal radiation at ambient temperature plays no role, radiation is described as a classical external field of a single mode. Its quantum analogue is a coherent state,  $|\alpha\rangle$ ,  $a|\alpha\rangle = \alpha|\alpha\rangle$ ,  $\langle \langle \dots \rangle \rangle \rightarrow \langle \alpha | \dots | \alpha \rangle$ .  $a, a^\dagger$  denote destruction and creation operators of the mode,  $aa^\dagger - a^\dagger a = 1$ .  $\alpha = |\alpha| \exp(i\phi)$  is a complex number where  $|\alpha|^2$  is the mean photon number of the mode which is proportional to the light intensity.

The vector potential operator reads

$$A_\mu(\mathbf{r}_j, t_j) = \sqrt{\frac{1}{2\epsilon\epsilon_0 V \omega}} \left( e_\mu a e^{i(\mathbf{q}\mathbf{r}_j - \omega t_j)} + hc \right),$$

where  $\mathbf{q}$ ,  $\omega = \omega(\mathbf{q})$ ,  $\mathbf{e}$  denote the wave vector, frequency, and polarization vector of the mode.  $\epsilon = \eta^2$  is the dielectric constant of the medium and  $V$  is the volume of the cavity (periodic boundary conditions are implied), see e.g. (Louisell<sup>70</sup>, Sec. 4.3). To lighten notation mode–indices have been suppressed.

The phase  $\phi$  of the radiation is a statistical quantity, hence terms in (A1) containing  $\alpha^2 = \langle \alpha | a^2 | \alpha \rangle$  vanish upon averaging on  $\phi$  (same for  $(\alpha^*)^2$ , equally distributed phases on  $0 \dots 2\pi$ ). Apart from a very small difference of  $|\alpha|^2$  and  $|\alpha|^2 + 1$ ,  $D_{\mu\nu}^<(\mathbf{r}, t)$  and  $D_{\mu\nu}^>(\mathbf{r}, t)$  become equal and depend only on  $\mathbf{r} = \mathbf{r}_1 - \mathbf{r}_2$ ,  $t = t_1 - t_2$ . As a result, the retarded and advanced D’s vanish and the Keldysh–component becomes

$$D_{\mu\nu}^K(\mathbf{r}, t) = -i \frac{I}{\omega^2 \epsilon_0 c \eta} \left( e_\mu e_\nu^* e^{i(\mathbf{q}\mathbf{r} - \omega t)} + cc \right). \quad (A2)$$

As the light wave length is much larger than the crystal unit cell, we may approximate  $e^{\pm i\mathbf{q}\mathbf{r}} \rightarrow 1$  (dipol approximation, neglect of photon–drag effect). This is result (14).

## Appendix B: Diamagnetic contribution to the tensor $\mathbf{R}^S$

In the velocity gauge there is a (small) “diamagnetic” contribution from the vertex operator  $\frac{q^2}{m_0} \mathbf{A}_{cl}$  to the generation matrix  $G_{nn'}$ , which is usually neglected. In linear order with respect to  $\mathbf{B}$ , this contribution reads

$$\begin{aligned} \delta G_n^{(\mathbf{B}, dia)}(\mathbf{k}) &= I \frac{\pi q^3}{\omega^3 m_0^3 \epsilon_0 c \eta} B_\beta \epsilon_{\beta\nu\gamma} \sum_{\Omega=\pm\omega}^{n'} (f_{n',0}(\mathbf{k}) - f_{n,0}(\mathbf{k})) \delta(E_{n'}(\mathbf{k}) - E_n(\mathbf{k}) - \Omega) \text{sign}(\Omega) \\ &\times \{ \text{Re}(\langle n, \mathbf{k} | p_\mu | n', \mathbf{k} \rangle \langle n', \mathbf{k} | p_\gamma | n, \mathbf{k} \rangle) \text{Im}(e_{\mu,\Omega}^* e_{\nu,\Omega}) + \text{Im}(\langle n, \mathbf{k} | p_\mu | n', \mathbf{k} \rangle \langle n', \mathbf{k} | p_\gamma | n, \mathbf{k} \rangle) \text{Re}(e_{\mu,\Omega}^* e_{\nu,\Omega}) \}. \end{aligned} \quad (B1)$$

This result is obtained in the same way as  $G_n^{(0)}$  of Eqs. (22,23), by taking into account the terms linear in  $\mathbf{B}$  in the product of the matrix elements  $\langle n, \mathbf{k} | p_\mu - \frac{q}{2}(\mathbf{B} \times \mathbf{r})_\mu | n', \mathbf{k} \rangle \langle n', \mathbf{k} | p_\nu - \frac{q}{2}(\mathbf{B} \times \mathbf{r})_\nu | n, \mathbf{k} \rangle$  of the vertex oper-

ator. Note, the phase factor contained in the approximation Eq. (17) is responsible for transforming the gauge dependent field  $\mathbf{A}_{cl}$  into the gauge independent term  $\frac{1}{2}\mathbf{B} \times \mathbf{r}$  in the vertex operator. Subsequently, the matrix element of the position operator  $\mathbf{r}$  is replaced by that of the momentum operator  $\mathbf{p}$  using the identity  $\langle n, \mathbf{k} | \mathbf{r} | m, \mathbf{k} \rangle = \frac{1}{i m_0} \langle n, \mathbf{k} | \mathbf{p} | m, \mathbf{k} \rangle / (E_n(\mathbf{k}) - E_m(\mathbf{k}))$ , which holds for  $E_n(\mathbf{k}) \neq E_m(\mathbf{k})$ . Moreover, only odd terms in  $\mathbf{k}$  contribute, i.e. terms containing  $\text{Im}(\langle n, \mathbf{k} | \dots | n, \mathbf{k} \rangle) \text{Re}(e_{\mu, \Omega}^* e_{\nu, \Omega})$ , giving a contribution to  $\mathbf{R}^S$  but not to  $\mathbf{R}^A$ . Following the same route as for  $\mathbf{P}^A$ , cf. (33-37), we obtain

$$R_{\alpha\beta\mu\nu}^{S,dia} = I \frac{q^4}{4\pi^2 \omega^3 m_0^3 \epsilon_0 c \eta} \epsilon_{\beta\nu\gamma} \sum_{\substack{n',n \\ \Omega=\pm\omega}} \int_{1.BZ} d^3k (f_{n',0}(\mathbf{k}) - f_{n,0}(\mathbf{k})) \delta(E_{n'}(\mathbf{k}) - E_n(\mathbf{k}) - \Omega) \times \\ \tau_n v_{n,\alpha}(\mathbf{k}) (\delta_{v,n} + \delta_{c,n}) \text{Im}(\langle n, \mathbf{k} | p_\mu | n', \mathbf{k} \rangle \langle n', \mathbf{k} | p_\gamma | n, \mathbf{k} \rangle) \text{sign}(\Omega). \quad (\text{B2})$$

Remarkably, result (B2) can be linked to  $\mathbf{P}^A$  by Eq. (37)

$$R_{\alpha\beta\mu\nu}^{S,dia} = \frac{e}{\omega m_0} \epsilon_{\beta\nu\gamma} P_{\alpha\mu\gamma}^A. \quad (\text{B3})$$

Hence, diamagnetic contributions to  $\mathbf{R}^S$  exist only in non-gyrotropic media, yet a different spectral dependence may be expected.

For a crude estimate we consider parabolic valence and conduction bands and disregard the angular dependence of  $\mathbf{k}$  in Eqs. (B2) and (43). Near the energy gap  $\Delta$ , we have

$$|\mathbf{R}^{S,dia}| \approx |\mathbf{R}^S| \left(1 - \frac{\Delta}{\omega}\right), \quad \omega \geq \Delta.$$

This result supports the usual approximation to neglect the diamagnetic contribution near the gap. Nevertheless, it should be taken into account in numerical calculations covering a wide frequency range.

### Appendix C: Numerical Application to GaP

The expressions for the response coefficients Eqs. (32,38,43,48,52) involve band-energies and momentum matrix elements which are directly available or can be obtained from bandstructure calculations. With respect to the shift-mechanism, n-doped GaP is a particular favorable system. Optical transitions occur from the bottom of the conduction band (near the X-point) to the next upper band which is separated by a small gap of  $\Delta = 355$  meV. The latter is solely due to the noninversion symmetry of the crystal. Previous calculations<sup>14</sup> for the absorption coefficient and linear photogalvanic tensor component  $P_{xyz}$  proved to be in almost perfect agreement with experimental results.

GaP belongs to the symmetry group  $43m$ . For  $\mathbf{P}^S$  there is only a single independent element,  $P_{xyz}$ , whereas  $\mathbf{P}^A$  vanishes identically because GaP is non-gyrotropic. In this symmetry, a fourth rank axial tensor has three independent components, which are  $R_{xxyy}^S$ ,  $R_{xyxy}^S$  and  $R_{xyxy}^A$ .

To keep the presentation simple, we use the results for GaP from a local pseudopotential calculation<sup>14</sup>. Conduc-

tion and next upper band near the X-point are nondegenerate and there are six pockets with equal occupation. Band energies are modelled analytically whereas the  $\mathbf{k}$ -dependence of the momentum matrix elements<sup>14</sup> will be neglected.  $\langle c, \mathbf{k} | p_\nu | c^*, \mathbf{k} \rangle$  ( $\nu = x, y$ ) is solely different from zero in the pockets on the  $\mathbf{k}_x$  and  $\mathbf{k}_y$  axes. At room temperature the electron system for  $n = 2.4 \times 10^{16} \text{cm}^{-3}$  is nondegenerate.

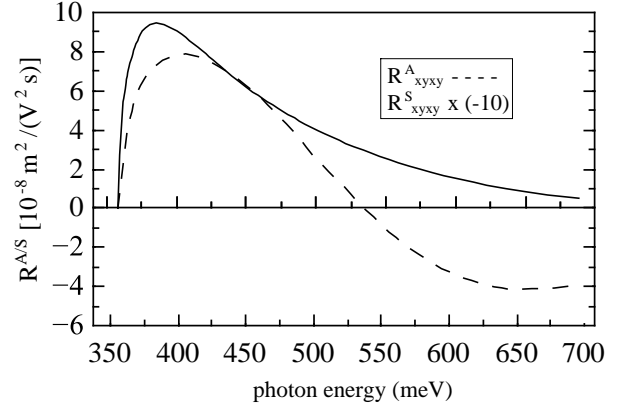


FIG. 1. Tensor components  $R_{xyxy}^A$  and  $R_{xyxy}^S$

Within this approximation (rotationally symmetric energy surfaces)  $R_{xxyy}^S$  vanish whereas  $R_{xyxy}^S$  is nonvanishing, a momentum relaxation time of  $\tau = 5.0 \cdot 10^{-14} \text{s}$  has been assumed.

To determine  $R_{xyxy}^{A,shift}$ , the  $\mathbf{Q}_i$ -derivatives ( $i = 1, 2$ ) have first to be calculated. The dominant contribution results from a sum of products whose two factors are first derivatives with respect to  $\mathbf{Q}_i$ . One factor contains the Fermi-functions and the  $\delta$ -function, while the second factor results from products of matrix elements  $M_{xx}^{vc/cv}$ . The  $\mathbf{Q}_i$ -derivatives of the latter are determined using  $\mathbf{k} \cdot \mathbf{p}$  perturbation theory. There is no contribution from  $\mathbf{R}^{A,bal}$  because GaP is non-gyrotropic,  $R_{xyxy}^A = R_{xyxy}^{A,shift}$ . Numerical results are displayed in Fig. 1. The comparatively small numerical values for  $R_{xyxy}^S$  and  $R_{xyxy}^A$  are due to the low electron concentration  $n$ .

- <sup>1</sup> B.I. Sturman and V.M. Fridkin, The Photovoltaic and Photorefractive Effects in Noncentrosymmetric Materials, (Gordon & Breach, 1992).
- <sup>2</sup> A. Kojima, K. Teshima, Y. Shirai, and T. Miyasaka, Organometal Halide Perovskites as Visible-Light Sensitizers for Photovoltaic Cells, *J. Am. Chem. Soc.* **131** (17), 6050 (2009).
- <sup>3</sup> S.Y. Xu, I. Belopolski, N. Alidoust, M. Neupane, G. Bian, C. Zhang, R. Sankar, G. Chang, Z. Yuan, C.C. Lee, S.M. Huang, H. Zheng, J. Ma, D.S. Sanchez, B.K. Wang, A. Bansil, F. Chou, P.P. Shibayev, H. Lin, S. Jia, and M.Z. Hasan, Discovery of a Weyl fermion semimetal and topological Fermi arcs, *Science* **349**(6248), 613 (2015).
- <sup>4</sup> In Ferroelectrics, circular polarized light also contributes via  $\mathbf{P}^S$ , like unpolarized light. Ballistic currents belong to the broader class of "injection" currents<sup>13</sup>, which would rise linearly with time in the absence of damping.
- <sup>5</sup> R.R. Birss, Symmetry and Magnetism, (North - Holland Publishing Company, Amsterdam, 1964).
- <sup>6</sup> R.W. Boyd, Nonlinear Optics, (Academic Press, 4. Edition 2020), ISBN-13: 978-0128110027.
- <sup>7</sup> W. Kraut and R. von Baltz, Anomalous bulk photovoltaic effect in ferroelectrics: A quadratic response theory, *Phys. Rev. B* **19**, 1548 (1979).
- <sup>8</sup> E.I. Blount, In: Solid State Physics, edited by F. Seitz and D. Turnbull, **13** (Academic Press, 1962).
- <sup>9</sup> R. von Baltz and W. Kraut, Theory of the bulk photovoltaic effect in pure crystals, *Phys. Rev. B* **23**, 5590 (1981).
- <sup>10</sup> V.I. Belinicher, E.L. Ivchenko, and B.I. Sturman, Kinetic theory of the displacement photogalvanic effect in piezoelectrics, *Sov. Phys. JETP* **56**, 359 (1982). NB: displacement  $\rightarrow$  shift (erroneous translation).
- <sup>11</sup> N. Kristoffel, R. von Baltz and D. Hornung, On the intrinsic BPVE: Performing the sum over intermediate states, *Z.Phys. B, Cond. Matter*, **47**, 293 (1982).
- <sup>12</sup> A two band situation is implied. In general, all pairs of direct optical transition have to be taken into account additively.
- <sup>13</sup> J.E. Sipe and A.I. Shkreptii, Second order nonlinear optics, *Phys Rev. B* **61**, 5337 (2000).
- <sup>14</sup> D. Hornung, R. von Baltz and U. Rössler, Band structure Investigation of the BPVE in n-GaP, *Sol. State Comm.* **48**, 225 (1983).
- <sup>15</sup> A.F. Gibson, C.B. Hatch, M.F. Kimmitt, S. Kothari and S. Serafetinides, Optical rectification and photon drag in n-type gallium phosphide, *J. Phys. C***10**(6), 905 (1977). NB: optical rectification  $\rightarrow$  photogalvanic current, misinterpretation of measurement results.
- <sup>16</sup> F. Nastos and J.E. Sipe, Optical rectification and shift currents in GaAs and GaP response: Below and above the band gap, *Phys Rev. B* **74**, 035201 (2006).
- <sup>17</sup> F. Nastos and J.E. Sipe, Optical rectification and current injection in unbiased semiconductors, *Phys. Rev. B* **82**, 235204 (2010).
- <sup>18</sup> St.M. Young and A.M. Rappe, First Principles Calculation of the Shift Current Photovoltaic Effect in Ferroelectrics, *Phys. Rev. Lett.* **109**, 116601 (2012).
- <sup>19</sup> St.M. Young, F. Zheng, and A.M. Rappe, First-Principles Calculation of the Bulk Photovoltaic Effect in Bismuth Ferrite, *Phys. Rev. Lett.* **109**, 236601 (2012).
- <sup>20</sup> Wei Ji, K. Yao and Y.C. Liang, Evidence of bulk photovoltaic effect and large tensor coefficient in ferroelectric BiFeO3 thin films, *Phys. Rev. B* **84**, 094115 (2011).
- <sup>21</sup> Ch. Paillard, X. Bai, I.C. Infante, M. Guennou, G. Geneste, M. Alexe, J. Kreisel, B. Dkhil, Photovoltaic with Ferroelectrics: Current Status and Beyond, *Advanced Materials* **28**(26), 5153 (2016).
- <sup>22</sup> P. Lopez-Varo, L. Bertoluzzi, J. Bisquert, M. Alexe, M. Coll, J. Huang, J.A. Jimenez-Tejada, T. Kirchartz, R. Nechach, F. Rosei, Y. Yuan, Physical aspects of ferroelectric semiconductors for photovoltaic solar energy conversion, *Phys. Rep.* **653**, 1-40 (2016).
- <sup>23</sup> L.Z. Tan, F. Zheng, St.M. Young, F. Wang, S. Liu and A.M. Rappe, Shift current bulk photovoltaic effect in polar materials—hybrid and oxide perovskites and beyond, *Comput. Mater.* **2**, 16026 (2016).
- <sup>24</sup> A.M. Cook, B.M. Fregoso, F. de Juan, S. Coh and J.E. Moore, Design principles for shift current photovoltaics, *Nat. Commun.* **8**, 14176 (2017).
- <sup>25</sup> N. Ogawa, M. Sotome, Y. Kaneko, M. Ogino, and Y. Tokura, Shift current in the ferroelectric semiconductor SbSI, *Phys. Rev. B* **96**, 241203(R) (2017).
- <sup>26</sup> E.J. König, H.-Y. Xie, D.A. Pesin, and A. Levchenko, Photogalvanic effect in Weyl semimetals, *Phys. Rev. B* **96**, 075123 (2017).
- <sup>27</sup> Y. Zhang, H. Ishizuka, J. van den Brink, C. Felser, B. Yan, and N. Nagaosa, Photogalvanic Effect in Weyl Semimetals from First Principles, *Phys. Rev. B* **97**, 241118(R) (2018).
- <sup>28</sup> J. Ma, Q. Gu, Y. Liu, J. Lai, P. Yu, X. Zhuo, Z. Liu, J.H. Chen, J. Feng and D. Sun, Nonlinear photoresponse of type II Weyl semimetals, *Nature Materials* **18**, 476 (2019).
- <sup>29</sup> D.E. Parker, T. Morimoto, J. Orenstein, and J.E. Moore, Diagrammatic approach to nonlinear optical response with application to Weyl semimetals, *Phys. Rev. B* **99**, 045121 (2019).
- <sup>30</sup> Results are often given in terms of a second-order conductivity  $j_\alpha = \sigma_{\alpha\mu\nu} \bar{E}_\mu \bar{E}_\nu$ , where  $\bar{E}_\mu$  are the components of the electrical field amplitude of the light in the material. Conversion:  $I = c\epsilon_0 \bar{E}^2 \eta / 2$ ,  $\bar{E}^2 \approx 750(V/A) I / \eta$ , where  $\eta$  is the refractive index. Best Si solar cells have an effective  $\sigma_{eff} \sim 1330\eta \mu A/V^2$ , ( $P_{eff} \sim 1/V$ ). From Ref.<sup>31</sup>: BaTiO<sub>3</sub> (exp.):  $\sigma_{zzz} \approx 5\mu A/V^2$ , ( $P_{zzz}^S \approx 4 \times 10^{-3}/V$ ); GeS (theor.):  $\sigma_{xxx} \approx 100\mu A/V^2$ , ( $P_{xxx}^S \approx 0.075/V$ ).
- <sup>31</sup> T. Rangel, B.M. Fregoso, B.S. Mendoza, T. Morimoto, J.E. Moore, and J.B. Neaton, Large Bulk Photovoltaic Effect and Spontaneous Polarization of Single-Layer Monochalcogenides, *Phys. Rev. Lett.* **119**, 067402 (2017).
- <sup>32</sup> A.M. Schankler, L. Gao, and A.M. Rappe, Large Bulk Piezophotovoltaic Effect of Monolayer 2H-MoS<sub>2</sub>, *J. Phys. Chem. Lett.* **12**, 1244 (2021).
- <sup>33</sup> Y. Zhang, F. de Juan, A.G. Grushin, C. Felser, and Y. Sun, Strong bulk photovoltaic effect in chiral crystal in the visible spectrum, *Phys. Rev. B* **100** 245206 (2019).
- <sup>34</sup> J. Zhao, Y. Hu, Y. Xie, L. Zhang, and Y. Wang, Largely Enhanced Photogalvanic Effects in a Phosphorene Photodetector by Strain-Increased Device Asymmetry, *Phys. Rev. Appl.* **14**, 064003 (2020).
- <sup>35</sup> G. Sundaram and Q. Niu, Wave-packet dynamics in slowly perturbed crystals: gradient corrections and Berry-phase effects, *Phys. Rev. B* **59**, 14915 (1999).

- <sup>36</sup> N.A. Sinitsyn, Q. Niu, and A.H. MacDonald, Coordinate shift in the semiclassical Boltzmann equation and the anomalous Hall effect, *Phys. Rev. B* **73**, 075318 (2006).
- <sup>37</sup> T. Holder, D. Kaplan, and B. Yan, Consequences of time-reversal-symmetry breaking in the light-matter interaction: Berry curvature, quantum metric, and diabatic motion, *Phys. Rev. Res.* **2**, 033100 (2020).
- <sup>38</sup> H. Schneider, S. Ehret, C. Schönbein, K. Schwarz, G. Bihlmann, J. Fleissner, G. Tränkle, G. Böhm, Photogalvanic effect in asymmetric quantum wells and superlattices, *Superlattices and Microstructures* **23**(6), 1289 (1998).
- <sup>39</sup> L.-k. Shi and J. C.W. Song, Shift vector as the geometrical origin of beam shifts, *Phys. Rev. B* **100**, 201405(R) (2019).
- <sup>40</sup> P. Kral, E.J. Mele, and D. Tomancek, Photogalvanic Effects in Heteropolar Nanotubes, *Phys. Rev. Lett.* **85**, 1512 (2000).
- <sup>41</sup> Y. Gao, Y. Zhang, and D. Xiao, Tunable Layer Circular Photogalvanic Effect in Twisted Bilayers, *Phys. Rev. Lett.* **124**, 077401 (2020).
- <sup>42</sup> H. Haug and S.W. Koch, *Quantum Theory of the Optical and Electronic Processes of Semiconductors*, (World Scientific Publishing Company, 2009).
- <sup>43</sup> J. Rammer and H. Smith, Quantum field-theoretical methods in transport theory of metals, *Rev. Mod. Phys.* **58**, 323 (1986).
- <sup>44</sup> G. Baym, *Lectures on Quantum Mechanics*, Benjamin/Cummings (1969).
- <sup>45</sup> Improper treatment of these terms may lead to spurious effects, as e.g. in Ref.<sup>46</sup> or mentioned by Refs.<sup>13,65</sup>.
- <sup>46</sup> N. Kristoffel, On the Possibility of Anomalous Bulk Photovoltaic Effect and of Induced Absorption in the Nominal Transparency Region of a Noncentrosymmetric Crystal in a Magnetic Field, *phys. stat. sol. (b)* **127**, 413 (1985).
- <sup>47</sup> L.P. Kadanoff and G. Baym, *Quantum Statistical Mechanics* (W.A. Benjamin, New York, 1962).
- <sup>48</sup> B.M. Fregoso, Bulk photovoltaic effects in the presence of a static electric field, *Phys. Rev. B* **100**, 064301 (2019).
- <sup>49</sup> Zh. Dai, A.M. Schankler, L. Gao, L.Z. Tan, and A.M. Rappe, Phonon-Assisted Ballistic Current from First-Principles Calculations, *Phys. Rev. Lett.* **126**, 177403 (2021).
- <sup>50</sup> W.T.H. Koch, R. Munser, W. Ruppel and P. Würfel, Bulk Photovoltaic Effect in BaTiO<sub>3</sub>, *Solid State Commun.* **17**, 3 (1975).
- <sup>51</sup> V.L. Al'perovich, V.I. Belinicher, A.O. Minaev, S.P. Moshchenko, and A.S. Terekhov, Ballistic photogalvanic effect at interband transitions in gallium arsenide, *Sov. Phys. Solid State* **30**, 1788 (1988).
- <sup>52</sup> B.I. Sturman, Ballistic and shift currents in the bulk photovoltaic effect theory, *Physics Uspekhi* **63**, 407, (2020).
- <sup>53</sup> R. von Baltz, Ch. Lingenfelder and R. Rupp, Nonlocal Photovoltaic Response Function for the Interpretation of Hologram Writing in Ferroelectric Crystals, *Appl. Phys.* **A32**, 13 (1983).
- <sup>54</sup> M. Nakamura, H. Hatada, Y. Kaneko, N. Ogawa, M. Sotome, Y. Tokura, and M. Kawasaki, Non-local photocurrent in a ferroelectric semiconductor SbSI under local photoexcitation, *Appl. Phys. Lett.* **116**, 122902 (2020).
- <sup>55</sup> U. Bajpai, B.S. Popescu, P. Plecháč, B.K. Nikolić, L.E.F. Foa Torres, H. Ishizuka and N. Nagaosa, Spatiotemporal dynamics of shift current quantum pumping by femtosecond light pulse, *J. Phys.: Mater.* **2**, 025004 (2019).
- <sup>56</sup> Private information from the authors of Ref.<sup>37</sup>.
- <sup>57</sup> J. Ibañez-Azpiroz, S.S. Tsirkin, and I. Souza, Ab initio calculation of the shift photocurrent by Wannier interpolation, *Phys. Rev. B* **97**, 245143 (2018).
- <sup>58</sup> E. Deyo, L.E. Golub, E.L. Ivchenko, B. Spivak, Semiclassical theory of the photogalvanic effect in noncentrosymmetric systems, arXiv 0904.1917v1 (2009).
- <sup>59</sup> P. Kral, Quantum kinetic theory of shift current electron pumping in semiconductors, *J. Phys.: Cond. Matter* **12**(22), 4851 (2000).
- <sup>60</sup> T. Barik and J.D. Sau, Nonequilibrium nature of optical response: Application to the bulk photovoltaic effect. *Phys. Rev. B* **101**, 045201 (2020).
- <sup>61</sup> D. Hornung, Zur kinetischen Theorie von Blochelektronen mit Anwendung auf den Photogalvanischen Effekt in Halbleitern und Isolatoren. Dissertation, Universität Karlsruhe, Germany (1986).
- <sup>62</sup> L.Z. Tan and A.M. Rappe, Upper limit on shift current generation in extended systems, *Phys. Rev. B* **100**, 085102 (2019).
- <sup>63</sup> S.B. Astafiev, V.M. Fridkin, V.G. Lazarev and A.L. Shlensky, Magnetophotovoltaic Effect in Crystals without a Center of Symmetry, *Ferroel.* **83**, 3 (1988).
- <sup>64</sup> E.L. Ivchenko and G.E. Pikus, Photogalvanic Effects in Optically Active Crystals, *Ferroel.* **43**, 131 (1982).
- <sup>65</sup> E.L. Ivchenko, Yu.B. Lyanda-Geller and G.E. Pikus, Magneto-photogalvanic effects in noncentrosymmetric crystals, *Ferroel.* **83**, 19 (1988).
- <sup>66</sup> Z. Gu, D. Imbrenda, A.L. Bennett-Jackson, M. Falmigbl, A. Podpirka, T.C. Parker, D. Shreiber, M.P. Ivill, V.M. Fridkin, and J.E. Spanier, Mesoscopic Free Path of Nonthermalized Photogenerated Carriers in a Ferroelectric Insulator, *Phys. Rev. Lett.* **118**, 096601 (2017).
- <sup>67</sup> A.M. Burger, R. Agarwal, A. Aprelev, E. Schrubba, A. Gutierrez-Perez, V.M. Fridkin and J.E. Spanier, Direct observation of shift and ballistic photovoltaic currents, *Science Advances* 2019, **5**(1), eaau 5588 (2019).
- <sup>68</sup> A.M. Burger, L. Gao, R. Agarwal, A. Aprelev, J.E. Spanier, A.M. Rappe, and V.M. Fridkin, Shift photovoltaic current and magnetically induced bulk photocurrent in piezoelectric sillenite crystals, *Phys. Rev. B* **102**, 081113(R) (2020).
- <sup>69</sup> "Shift" and "ballistic" refer to different generation processes. The corresponding currents don't have different electro-mechanical properties.
- <sup>70</sup> W.H. Louisell, *Quantum Statistical Properties of Radiation* (Wiley, 1992).