

The reducing role of hydrogen peroxide on the formation of gold nanostructures in aqueous microdroplets with dissolved tetrachloroaurate ions

Zhaoyuan Liu, Renze Yu, Xin Wang, Qiang Chen*

Institute of Electromagnetics and Acoustics, Fujian Provincial Key Laboratory of Plasma and Magnetic Resonance, Key Laboratory of Electromagnetic Wave Science and Detection Technology, Xiamen University, Xiamen 361005, China




*Email: chenqiang@xmu.edu.cn

A recent article by Lee et al.¹ in Nature Communications has reported an intriguing phenomenon that gold nanostructures (AuNSs) can be spontaneously formed in aqueous microdroplets with dissolved tetrachloroaurate ions (AuCl_4^-). The authors suggested three possible electron donors for the reduction of AuCl_4^- , including the strong electric field at the microdroplet's surface, the hydroxyl ions, and the AuCl_4^- itself ($\text{AuCl}_4^- \rightarrow \text{AuCl}_2^- + \text{Cl}_2$). However, we find that the hydrogen peroxide (H_2O_2) spontaneously produced at the microdroplets²⁻⁴ might be also responsible for the AuCl_4^- reduction.

The microdroplets in the article of Lee et al.¹ were generated by a high-pressure, dry N_2 at 120 psi. The AuNSs were observed in the collection of a fusion of aqueous AuCl_4^- microdroplets and the water microdroplets, and it was also found in the collection of aqueous AuCl_4^- microdroplets. To form AuNSs from the reduction of AuCl_4^- , electrons should be provided somehow. Three possible electron sources were suggested in Ref. ¹ as mentioned above. We noted that in a recent paper of Lee et al.⁵, spontaneous reduction of several organic molecules in aqueous microdroplets was also observed, and they pointed out that the charge separation of OH^- ($\text{OH}^- \rightarrow \text{OH} + e$) is likely the electron source for the reduction. The charge separation has been suggested to be induced by a strong intrinsic electric field spontaneously induced at the microdroplet's surface⁶. Due to the high rate constant of

$\text{OH} + \text{OH} \rightarrow \text{H}_2\text{O}_2$ ($k = 5.5 \times 10^9 \text{ M}^{-1} \text{ s}^{-1}$)⁷, this charge separation certainly leads to a spontaneous formation of H_2O_2 in the micro-sized water droplets, which has been reported by Lee et al.⁴. In the case of organic molecules, it might be the charge separation which provides the electrons, while we found that in the AuCl_4^- reduction, another electron donor is not negligible, i.e., the H_2O_2 spontaneously formed at the microdroplets²⁻⁴.

Previously, we have investigated the formation of gold nanoparticles using a discharge plasma to irradiate an aqueous solution of AuCl_4^- . The H_2O_2 generated by the plasma-liquid interactions⁸⁻¹¹ was confirmed to be an important reductant for reducing AuCl_4^- to Au (0). We have proposed Eqs. 1-3 for the AuCl_4^- reduction in an aqueous solution containing H_2O_2 and OH radicals. A simple calculation indicated that the standard Gibbs free energy change per mole of reaction are -86.85 kJ/mol, -332.25 kJ/mol, and -11.58 kJ/mol for Eqs. 1-3, respectively. The negative values of the Gibbs free energy mean that these reactions can be proceeded spontaneously¹².



Interestingly, Lee et al.¹ also observed oxygen evolution during the AuNSs formation as indicated in Eqs. 1-2. The existence of oxygen evolution implies that reaction 3 should be ruled out from the possible reduction reactions of AuCl_4^- .

To confirm the AuNSs formation of the AuCl_4^- reduction by H_2O_2 , we performed experiment by mixing aqueous solution of AuCl_4^- and H_2O_2 in a cuvette. Figure 1 shows the temporal photos of the aqueous solution of $\text{AuCl}_4^-/\text{PVP}$ with and without H_2O_2 [Polyvinylpyrrolidone (PVP) was used to stabilize the formed nanoparticles]. Obviously, the transparent aqueous solution of $\text{AuCl}_4^-/\text{PVP}$ with

H_2O_2 gradually changed to apricot (See supplementary Materials for the experimental detail and video for the change of the mixed solution). Gold nanoparticles formation is indicated by the existence of the gold surface plasmon resonance peak at 539 nm in the absorbance of the mixed solution 20 min after the mixture (Fig. 2). Measurements of scanning electron microscopy (SEM) and energy dispersive X-ray spectroscopy (EDS) further confirmed the formed particles are gold nanoparticles (Fig. 3).

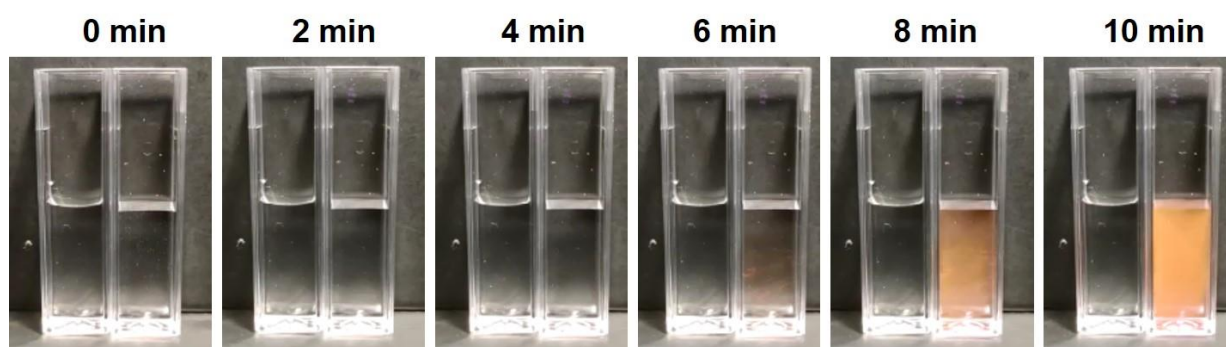


Fig. 1 Temporal photos of the mixed solution of $\text{AuCl}_4^-/\text{PVP}$ and H_2O_2 . Photos were screenshotted from a video taken after the mixing of the solution (See Supplementary Information).

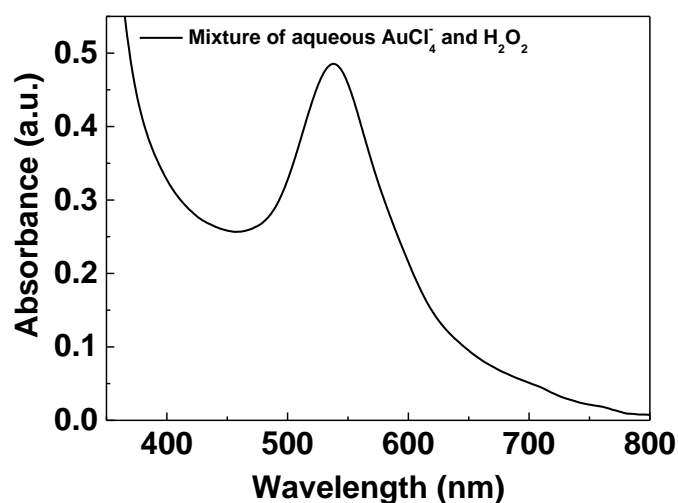


Fig. 2 Absorbance of the mixed solution of $\text{AuCl}_4^-/\text{PVP}$ and H_2O_2 after 20 min of the mixing

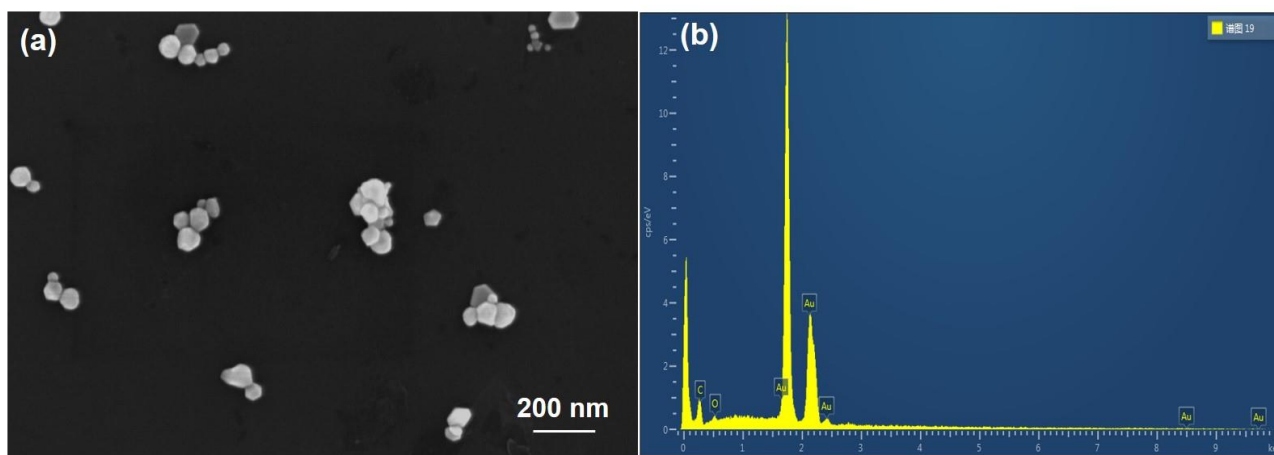


Fig. 3 SEM and EDS results of nanoparticles formed by mixing $\text{AuCl}_4^-/\text{PVP}$ and H_2O_2 . The mixture was made by directly dropping 1 ml H_2O_2 (30%, w/w) into 1 ml aqueous $\text{AuCl}_4^-/\text{PVP}$ solution, and the concentrations of AuCl_4^- and PVP were 0.25 mM, respectively.

Finally, we conclude that the H_2O_2 spontaneously produced at or near the surface of aqueous microdroplets plays an important role for reducing AuCl_4^- to form gold nanostructures in the microdroplets with AuCl_4^- .

Data availability

Supplementary Information: the experimental details and the video of the reaction for aqueous AuCl_4^- with H_2O_2 .

References

- 1 Lee, J. K., Samanta, D., Nam, H. G. & Zare, R. N. Spontaneous formation of gold nanostructures in aqueous microdroplets. *Nature Communications* **9**, 1-9 (2018).
- 2 Dulay, M. T., Lee, J. K., Mody, A. C., Narasimhan, R., Monack, D. M. & Zare, R. N. Spraying Small Water Droplets Acts as a Bacteriocide. *QRB Discovery* **1**, e3 (2020).
- 3 Gao, D., Jin, F., Lee, J. K. & Zare, R. N. Aqueous microdroplets containing only ketones or aldehydes undergo

- Dakin and Baeyer–Villiger reactions. *Chemical Science* **10**, 10974-10978 (2019).
- 4 Lee, J. K., Walker, K. L., Han, H. S., Kang, J., Prinz, F. B., Waymouth, R. M., Nam, H. G. & Zare, R. N. Spontaneous generation of hydrogen peroxide from aqueous microdroplets. *Proceedings of the National Academy of Sciences* **116**, 19294-19298 (2019).
- 5 Lee, J. K., Samanta, D., Nam, H. G. & Zare, R. N. Micrometer-sized water droplets induce spontaneous reduction. *Journal of the American Chemical Society* **141**, 10585-10589 (2019).
- 6 Xiong, H., Lee, J. K., Zare, R. N. & Min, W. Strong Electric Field Observed at the Interface of Aqueous Microdroplets. *The Journal of Physical Chemistry Letters* **11**, 7423-7428 (2020).
- 7 Buxton, G. V., Greenstock, C. L., Helman, W. P. & Ross, A. B. Critical review of rate constants for reactions of hydrated electrons, hydrogen atoms and hydroxyl radicals ($\cdot\text{OH}/\cdot\text{O}^-$ in aqueous solution. *J. Phys. Chem. Ref. Data* **17**, 513-886 (1988).
- 8 Chen, Q., Kaneko, T. & Hatakeyama, R. Reductants in gold nanoparticle synthesis using gas–liquid interfacial discharge plasmas. *Applied Physics Express* **5**, 086201 (2012).
- 9 Liu, J., He, B., Chen, Q., Li, J., Xiong, Q., Yue, G., Zhang, X., Yang, S., Liu, H. & Liu, Q. H. Direct synthesis of hydrogen peroxide from plasma-water interactions. *Scientific Reports* **6**, 38454 (2016).
- 10 He, X., Lin, J., He, B., Xu, L., Li, J., Chen, Q., Yue, G., Xiong, Q. & Liu, Q. H. The formation pathways of aqueous hydrogen peroxide in a plasma-liquid system with liquid as the cathode. *Plasma Sources Science and Technology* **27**, 085010 (2018).
- 11 Chen, Q., Lin, J., He, X., Hu, H., Li, J., Xiong, Q., Chen, B., Song, Z., Liu, H. & Liu, Q. H. Ethanol-controlled peroxidation in liquid-anode discharges. *Journal of Physics D: Applied Physics* **52**, 425205 (2019).
- 12 Chen, Q., Li, J. & Li, Y. A review of plasma–liquid interactions for nanomaterial synthesis. *Journal of Physics D: Applied Physics* **48**, 424005 (2015).

Acknowledgements

This work was supported by National Natural Science Foundation of China (Grant No.: 52077185).

Q.C thanks Dr. Kai Luo in Xiamen University for his insightful discussions.

Author information

These authors contributed equally: Zhaoyuan Liu, Renze Yu.

Affiliations

Institute of Electromagnetics and Acoustics, Fujian Provincial Key Laboratory of Plasma and Magnetic Resonance, Key Laboratory of Electromagnetic Wave Science and Detection Technology, Xiamen University, Xiamen 361005, China

Contributions

Z.L. and R.Y. performed the experiments. X.W. performed the SEM and EDS measurement. Q.C wrote the manuscript and is responsible for the conception. All authors approved the submission of the manuscript.

Ethics declarations

Competing interests

The author declares no competing interests.

Supplementary Information

The reducing role of hydrogen peroxide on the formation of gold nanostructures in aqueous microdroplets with dissolved tetrachloroaurate ions

Zhaoyuan Liu, Renze Yu, Xin Wang, Qiang Chen *

Institute of Electromagnetics and Acoustics, Fujian Provincial Key Laboratory of Plasma and Magnetic Resonance, Key Laboratory of Electromagnetic Wave Science and Detection Technology, Xiamen University, Xiamen 361005, China

*Email: chenqiang@xmu.edu.cn

Experimental details

Hydrogen peroxide (H_2O_2 , 30%, w/w) was purchased from Xilong Scientific Co., Ltd. Polyvinylpyrrolidone (PVP) $[(\text{C}_6\text{H}_9\text{NO})_n]$, average molecular weight 58000, K29-32], Hydrogen tetrachloroaurate (III) trihydrate ($\text{HAuCl}_4 \cdot 3\text{H}_2\text{O}$), ACS, 99.99%, was purchased from Alfa Aesar.

For the absorbance measurement, 1 ml aqueous solution of $\text{HAuCl}_4/\text{PVP}$ (0.25 mM/0.25 mM) was prepared in a quartz cell and then 1 ml H_2O_2 (30%, w/w) was dropped into the cell. Absorbance of the mixed aqueous solution was detected in the quartz cell using by Ocean Optics spectrometer (USB2000+) with a light source of HL-2000 (360 nm-2000 nm).

A video was taken for comparison of the aqueous solution of $\text{HAuCl}_4/\text{PVP}$ (0.25 mM/0.25 mM) and a mixture of $\text{HAuCl}_4/\text{PVP}$ (0.25 mM/0.25 mM) and H_2O_2 (30%, w/w). One can find that the solution without H_2O_2 was transparent, while the solution with H_2O_2 turned to apricot, which implies the formation of gold nanoparticles.