

Strongly anisotropic electronic and magnetic structures in oxide dichlorides RuOCl₂ and OsOCl₂

Yang Zhang,¹ Ling-Fang Lin,¹ Adriana Moreo,^{1,2} Thomas A. Maier,³ Gonzalo Alvarez,⁴ and Elbio Dagotto^{1,2}

¹*Department of Physics and Astronomy, University of Tennessee, Knoxville, TN 37996, USA*

²*Materials Science and Technology Division, Oak Ridge National Laboratory, Oak Ridge, TN 37831, USA*

³*Computational Sciences and Engineering Division,*

Oak Ridge National Laboratory, Oak Ridge, Tennessee 37831, USA

⁴*Computational Sciences & Engineering Division and Center for Nanophase Materials Sciences, Oak Ridge National Laboratory, Oak Ridge, TN 37831, USA*

(Dated: March 2, 2022)

The van der Waals oxide dichlorides MOX_2 ($M = V, Ta, Nb, Ru,$ and Os ; $X =$ halogen element), with different electronic densities, are attracting considerable attention. Ferroelectricity, spin-singlet formation, and orbital-selective Peierls phases were reported in this family with d^1 or d^2 electronic configurations, all believed to be caused by the strongly anisotropic electronic orbital degree of freedom. Here, using density functional theory and density matrix renormalization group methods, we investigate the electronic and magnetic properties of RuOCl₂ and OsOCl₂ with d^4 electronic configurations. Different from a previous study using VOI₂ with d^1 configuration, these systems with $4d^4$ or $5d^4$ do not exhibit a ferroelectric instability along the a -axis. Due to the fully-occupied d_{xy} orbital in RuOCl₂ and OsOCl₂, the Peierls instability distortion disappears along the b -axis, leading to an undistorted Immm phase (No. 71). Furthermore, we observe strongly anisotropic electronic and magnetic structures along the a -axis. The large crystal-field splitting energy (between $d_{xz/yz}$ and d_{xy} orbitals) and large hopping between nearest-neighbor Ru and Os atoms suppresses the spin-orbital effect in $MOCl_2$ ($M = Ru$ or Os) with electronic density $n = 4$, resulting in a spin-1 system instead of a $J = 0$ singlet ground state. Moreover, we find staggered antiferromagnetic order with π wavevector along the M -O chain direction (a -axis) while the magnetic coupling along the b -axis is weak. Based on Wannier functions from first-principles calculations, we calculated the relevant hopping amplitudes and crystal-field splitting energies of the t_{2g} orbitals for the Os atoms to construct a multi-orbital Hubbard model for the M -O chains. Staggered AFM with $\uparrow\downarrow\uparrow\downarrow$ spin structure dominates in our DMRG calculations, in agreement with DFT calculations. Our results for RuOCl₂ and OsOCl₂ provide guidance to experimentalists and theorists working on this interesting family of oxide dichlorides.

I. INTRODUCTION

One-dimensional (1D) material systems continue to attract considerable attention due to their rich physical properties induced by their 1D geometry and reduced dimensional phase space [1–9]. In these systems, many interesting phenomena have been found that are driven by intertwined charge, spin, orbital, and lattice degrees of freedom. For example, driven by electronic correlation effects (i.e. Hubbard repulsion U and Hund coupling J_H), high critical temperature superconductivity was reported in 1D copper or iron chains and ladders [10–17]. By considering the phonon instability caused by the coupling between empty d and fully occupied O $2p$ states, ferroelectricity was found in the chain compound WOX_4 ($X =$ halogen element) [18]. Furthermore, by mixing spin-phonon and charge-phonon instabilities, multiferroelectric states were predicted in some 1D systems [19–22]. Due to the partial or complete condensation of excitations, a charge density wave or a spin density wave were also reported in some 1D systems [2, 23–25].

A wide variety of real materials also have dominant 1D-like physical properties, even without restrictive 1D geometries in their crystal structure, due to the strongly

anisotropic electronic orbital degree of freedom. Recently, several different interesting 1D physical properties were reported in oxide dichlorides MOX_2 ($M = V, Ta, Nb, Ru$ and Os ; $X =$ halogen element) with various electronic densities n for the M atoms [26–32]. The parent phase of MOX_2 ($M = V, Ta, Nb, Os$; $X =$ halogen element) is a typical member of the layered van der Waals (vdW) family [26–28], where the MO_2X_4 octahedra are corner-sharing along the a -axis, while edge-sharing along the b -axis [see Fig. 1]. The effective 1D-like behavior of this family can be understood from the strong anisotropic behavior of different orbitals.

In MOX_2 , the MO_2Cl_4 octahedra is edge-sharing connected, opening the possibility of strong overlap of d_{xy} orbitals along the xy plane. Due to the 1D M - X chain geometric structures along the b -axis [see Figs. 1(b) and (c)], the bandstructure resulting from the xy orbital displays strong anisotropy. Furthermore, the d_{xz} and d_{yz} orbitals also display anisotropy along the a -axis due to the M - O geometric chain, while it forms the vdW layer along the c -axis. For the $n = 1$ case with d^1 electronic configuration (V or Nb), a ferroelectric (FE) distortion [29–31, 33] was theoretically predicted along the M -O direction (a -axis), where the “pseudo-Jahn-Teller” effect caused by the coupling between empty d ($d_{xz/yz}$ and $d_{3z^2-r^2}$) and

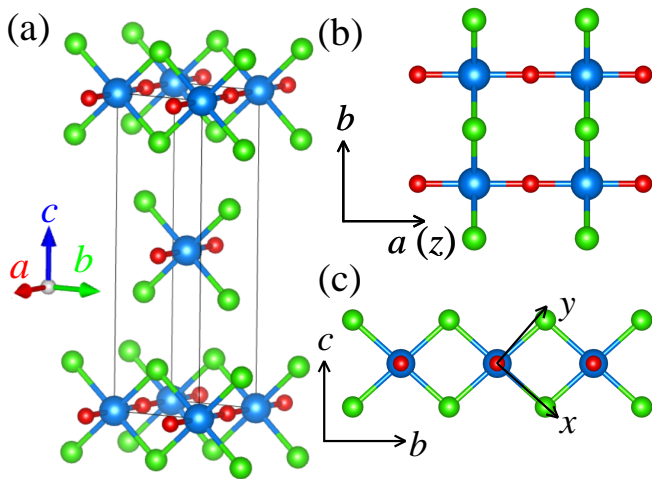


FIG. 1. (a-c) Schematic crystal structure of the undistorted parent phase of MOX_2 ($M = V, Ta, Nb, Ru$ and Os ; $X =$ halogen element): Blue = M ($M = V, Ta, Nb, Ru$ and Os); red = O ; green = X ($X =$ halogen element). (a) Conventional cell of the bulk structure. (b) Sketch of the ab plane. (c) MX_2 chain along the b -axis. Note that the local z -axis is the a -axis, while the local x - or y -axis is along the M - X bond directions, leading to d_{xy} orbitals lying on the bc plane.

O $2p$ orbitals plays an important role to stabilize the FE distortion [34]. In addition, Peierls distortions were found along the b -axis [31, 34], resulting in a spin-singlet configuration for the d_{xy} orbitals [34], due to the formation of molecular states in the d_{xy} bands. Very recently, the FE and Peierls distortions were confirmed experimentally for $NbOI_2$ with $4d^1$ electronic configuration [35]. With additional spin-orbit coupling (SOC), a spin texture was also found at the Y point along the M - X chain direction [36].

For the case of a d^2 electronic configurations, $MoOCl_2$ was experimentally reported to be a strongly correlated dimerized metal based on temperature-dependent transport measurements along the M - X chain direction [32]. The metallic conductivity arises from the strongly anisotropic Mo - $d_{xz/yz}$ bands [37, 38]. Furthermore, an interesting orbital-selective Peierls phase was also found to be stable in $MoOCl_2$ [38], because the intrahopping amplitude t is larger than the typical Hund couplings. This phase resembles the previously discussed orbital-selective Mott phase [39–43] but with the localized band induced by Peierls distortions instead of Hubbard interactions [38, 44]. Moreover, highly anisotropic plasmons were discussed in the monolayer $MoOCl_2$ [45].

Yet almost no research has been done for other electronic densities n of M atoms in this family. $RuOCl_2$ and $OsOCl_2$ with d^4 electronic configuration were synthesized [26], and it was reported that orthorhombic structures are formed with the space group $Immm$ (No. 71) [see Fig. 1]. Due to a reduced J_H , often $4d/5d$ atoms favor the total $S = 1$ configuration in compounds with more than half-filled t_{2g} states, leading to four electrons

occupying three t_{2g} orbitals in both $RuOCl_2$ and $OsOCl_2$. Considering the development of different 1D behaviors caused by different t_{2g} orbitals, a simple question naturally arises: Can $RuOCl_2$ and $OsOCl_2$ also display similar physical properties? In addition, with additional SOC, d^4 materials are expected to be nonmagnetic insulators formed by local two-hole $J = 0$ singlets [46, 47]. Is it possible to obtain $J = 0$ singlets in $RuOCl_2$ and $OsOCl_2$ as well?

To answer these questions, we employ both density functional theory (DFT) and density matrix renormalization group (DMRG) methods to numerically investigate $RuOCl_2$ and $OsOCl_2$ in detail. Based on DFT calculations, we have found that there are no FE distortions and Peierls instabilities occurring along the a - or b -axis in the undistorted phase of this system. Furthermore, we also observed a strongly anisotropic electronic structure along the a -axis. Because of the large crystal-field splitting energy (between $d_{xz/yz}$ and d_{xy} orbitals) and large nearest-neighbor (NN) hopping, the spin-orbital effect is suppressed in this system with the d^4 electronic configuration, leading to a spin-1 system, instead of a $J = 0$ singlet ground state. In addition, based on DFT calculations, we also found a strongly anisotropic electronic structure, with strong couplings along the a -axis and much weaker coupling along the b -axis for both $RuOCl_2$ and $OsOCl_2$. Using Wannier functions from first-principles calculations, we obtained the relevant hopping amplitudes and crystal-field splitting energies for the t_{2g} orbitals of the Ru/Os atoms. We found that staggered spin order is the most likely magnetic ground state, with a π wavevector order along the chain direction. Finally, we constructed a multi-orbital Hubbard model for the M - O chains and analyzed this model using DMRG. Our results show that staggered AFM order with $\uparrow\downarrow\uparrow\downarrow$ spin structure is dominant, consistent with the DFT calculations.

II. METHOD AND DFT CALCULATIONS

In the present study, first-principles DFT calculations were performed using the Vienna *ab initio* simulation package (VASP) code [48–50] with the projector augmented wave (PAW) method. Electronic correlations were considered by using the generalized gradient approximation (GGA) with the Perdew-Burke-Ernzerhof (PBE) potential [51]. The k -point mesh adopted was $16 \times 16 \times 5$ for the conventional cell of the bulk system, while the plane-wave cutoff energy was 600 eV. We have tested explicitly that this k -point mesh already leads to converged energies. Furthermore, both the lattice constants and atomic positions were fully relaxed until the Hellman-Feynman force on each atom was smaller than 0.01 eV/Å. The van der Waals (vdW) interactions Becke-Jonson damping vdW-D3 [52] were considered to deal with in-

interactions between different layers. The phonon spectra were calculated using the finite-displacement approach and analyzed by the PHONOPY software [53, 54]. In addition to the standard DFT calculation discussed thus far, the maximally localized Wannier functions (MLWFs) method was employed to fit the Ru $4d$'s or Os $5d$'s three t_{2g} bands near the Fermi level using the WANNIER90 packages [55]. All the crystal structures were visualized with the VESTA code [56].

To better understand the magnetic properties, we also relaxed the crystal structures for selected different spin configurations based on the $2 \times 2 \times 1$ supercell. Furthermore, the on-site Coulomb interactions were considered by using the local spin density approximation (LSDA) plus U with the Liechtenstein formulation for the double-counting term [57]. Based on previous experimental and theoretical studies for $4d$ and $5d$ compounds [58–60], the on-site Coulomb interaction U and on-site exchange interaction J were chosen as $U = 3$ eV and $J = 0.6$ eV for RuOCl_2 , and $U = 2$ eV and $J = 0.2$ eV for OsOCl_2 , respectively.

III. DFT RESULTS

A. Electronic properties

Based on our structural optimization calculation of the bulk nonmagnetic (NM) state, the optimized crystal lattices are $a = 3.666$, $b = 3.554$ and $c = 11.266$ Å for RuOCl_2 , close to experimental values ($a = 3.673$, $b = 3.520$ and $c = 11.258$ Å) [26]. We also obtained the lattice constants of OsOCl_2 ($a = 3.718$, $b = 3.615$ and $c = 11.079$ Å), also in agreement with experiments ($a = 3.701$, $b = 3.575$ and $c = 11.083$ Å) [26].

Before turning to the physical properties of MOCl_2 ($M = \text{Ru}$ or Os), we discuss their structural properties. We carried out phononic dispersion calculations using a $4 \times 4 \times 1$ supercell to understand the structural stability of the undistorted Immm phase (No. 71). Figure 2 indicates that there is no imaginary frequency mode obtained in the phononic dispersion spectrum for the Immm phase of RuOCl_2 and OsOCl_2 . Therefore, the undistorted Immm phase of bulk MOCl_2 ($M = \text{Ru}$ or Os) is dynamically stable, in agreement with experiments [26].

This result can be easily understood in the following way: In the octahedral crystal-field, the five d orbitals split into two higher-energy e_g ($d_{x^2-y^2}$ and $d_{3z^2-r^2}$) and three lower-energy t_{2g} (d_{xy} , d_{yz} , and d_{xz}) orbitals, as in Fig. 3 (a). Due to their reduced coupling J_H , the $4d$ and $5d$ atoms always favor the total $S = 1$ electronic configuration when the t_{2g} orbitals are more than half-filled. Then, replacing the Cl atoms of the octahedral apex by O atoms, it would induce two shortened M -O bonds ($M = \text{Ru}$ or Os) along the a -axis (z -axis) and four elongated M -Cl bonds ($M = \text{Ru}$ or Os along the bc (xy) plane in

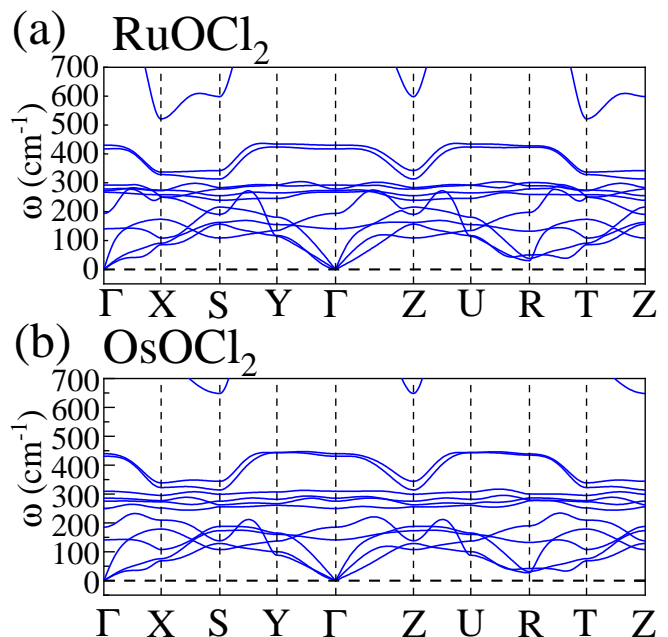


FIG. 2. Phonon spectrum of the bulk system for (a) RuOCl_2 and (b) OsOCl_2 . A $4 \times 4 \times 1$ supercell was used in our calculations and the nonmagnetic state. The coordinates of the high-symmetry points in the bulk Brillouin zone (BZ) are $\Gamma = (0, 0, 0)$, $X = (0.5, 0, 0)$, $S = (0.5, 0.5, 0)$, $Y = (0, 0.5, 0)$, $Z = (0, 0, 0.5)$, $U = (0.5, 0, 0.5)$, $R = (0.5, 0.5, 0.5)$, and $T = (0, 0.5, 0.5)$ in units of 2π .

the MO_2Cl_4 ($M = \text{Ru}$ or Os) octahedral configuration, leading to the splitting between the t_{2g} orbitals [see Fig. 3 (a)]. In this case, the four electrons form a total $S = 1$ electronic configuration with one fully-occupied lower d_{xy} orbital and two half-filled higher energy $d_{xz/yz}$ bands.

In previous studies for this vdW family of layered oxide dichlorides MOX_2 ($M = \text{V}, \text{Ta}, \text{Nb}, \text{Os}$; $X = \text{halogen element}$), the FE distortion along the a -axis and $M-M$ dimerization along the b -axis induced structural instabilities, leading to the lower symmetry structures [34]. Because two electrons occupy two $d_{xz/yz}$ orbitals in MOCl_2 ($M = \text{Ru}$ or Os), the FE distortion along the a -axis is energetically unfavorable, as discussed in VOI_2 with the d^1 configuration [34]. Furthermore, the spin-singlet formation using d_{xy} orbitals would also be suppressed along the b -axis since d_{xy} is a double-occupied state in MOCl_2 ($M = \text{Ru}$ or Os). Hence, both FE and dimerized instabilities are suppressed for RuOCl_2 and OsOCl_2 , resulting in a stable undistorted Immm phase (No. 71).

Next, we focus on the electronic structures of bulk MOCl_2 ($M = \text{Ru}$ or Os) for the nonmagnetic state without SOC. Figures 3(b) and (c) show that the e_g ($d_{x^2-y^2}$ and $d_{3z^2-r^2}$) bands of Ru's $4d$ and Os's $5d$ orbitals are located at high energy, and therefore are unoccupied. The local z -axis is the a -axis, while the local x or y axis is along the M -Cl directions [see Fig. 1(c)], leading to a d_{xy}

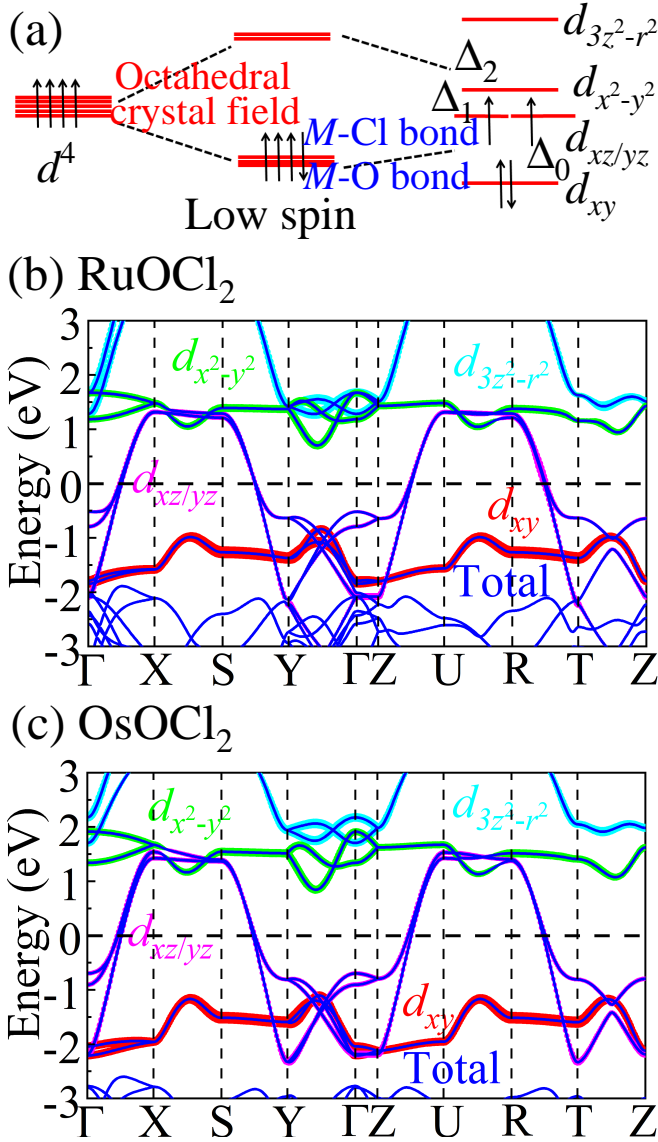


FIG. 3. (a) Energy splitting of the total $S = 1$ d^4 electronic configuration. (b-c) Projected band structures of the undistorted Immm non-magnetic phase for (b) RuOCl₂ and (c) OsOCl₂, respectively. Note that the local $\{x, y, z\}$ axes of projected orbitals are marked in Fig. 1, where the z -axis is the a -axis and x or y axes are along the M -Cl directions. The weight of each Ru or Os orbital is represented by the size of the (barely visible) circles.

orbital lying on the bc plane. In addition, we estimated that the energy splitting Δ_2 between $d_{x^2-y^2}$ and $d_{3z^2-r^2}$ orbitals is about 1.7 and 1.6 eV for RuOCl₂ and OsOCl₂, respectively, by the weight-center positions of the energy bands. Furthermore, two $4d/5d$ electrons occupy the d_{xy} bands that show only weak dispersion and are far away from the Fermi level. The other two $4d/5d$ electrons of Ru or Os occupy the d_{xz} and d_{yz} orbitals, contributing to the Fermi surface. We also estimated that the energy splitting Δ_1 (between $d_{x^2-y^2}$ and $d_{xz/yz}$) and Δ_0 (be-

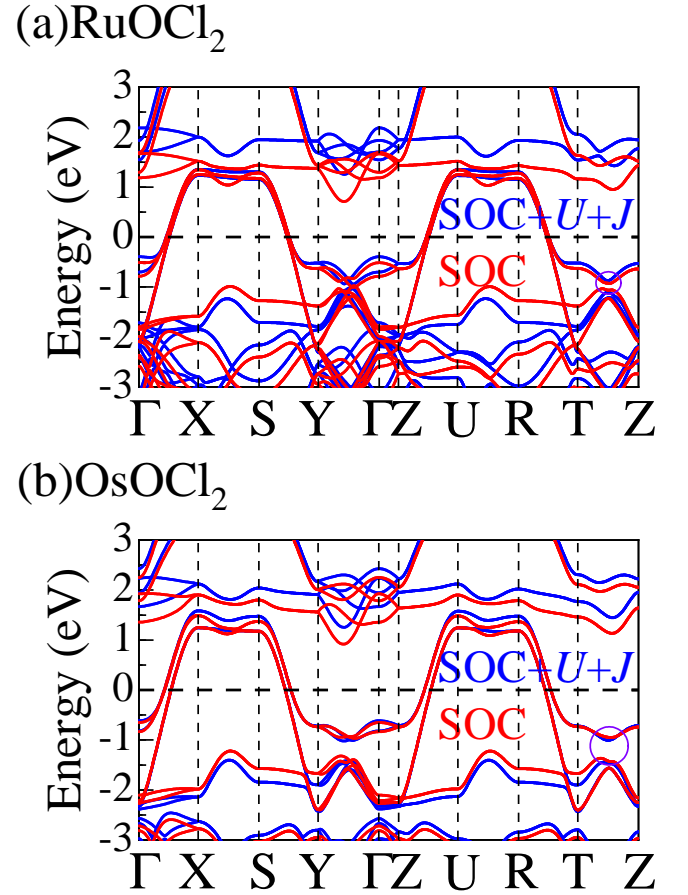


FIG. 4. (a) Band structure of RuOCl₂ in the NM state with SOC and with SOC+ U + J ($U = 3$ eV, $J = 0.6$ eV). (b) Band structure of OsOCl₂ in the NM state with SOC and with SOC+ U + J ($U = 2$ eV, $J = 0.4$ eV). The Fermi level is the horizontal dashed line. The energy gaps at about -1 eV below the Fermi level are indicated with circles.

tween d_{xy} and $d_{xz/yz}$) are $\Delta_1 = 1.2/1.3$ eV and $\Delta_0 = 1.2/1.4$ eV for RuOCl₂ and OsOCl₂, respectively. Considering the large crystal-field splitting Δ_0 , the $J = 0$ singlet ground state induced by SOC may be suppressed in $MOCl_2$ ($M = Ru$ or Os), as discussed for the OsCl₄ case with the d^4 electronic configurations [61].

Due to the fully-occupied d_{xy} state and large energy splitting Δ , the magnetic properties of $MOCl_2$ ($M = Ru$ or Os) are dictated by the d_{xz} and d_{yz} orbitals to be discussed in the following sections. Moreover, near the Fermi level, $MOCl_2$ ($M = Ru$ or Os) displays strongly quasi-1D electronic behavior with contributions from the d_{xz} and d_{yz} orbitals, and the band structures are much more dispersive along the a -axis (i.e. Γ -X path) than along other directions (i.e. X-S and Γ -Z paths).

After considering SOC in the NM state of $MOCl_2$ ($M = Ru$ or Os), the bands begin to split as displayed in Fig. 4, opening an energy gap (~ 0.12 eV for RuOCl₂ and ~ 0.41 eV for OsOCl₂) along the T-Z high-symmetry

path at ~ -1 eV below the Fermi level. However, introducing SOC, the band structures near the Fermi level do not change much. Furthermore, the large bandwidth of the $d_{xz/yz}$ states of MOCl_2 ($M = \text{Ru}$ or Os) suggests a large value for the NN hopping of Os or Ru atoms along the a -axis. Considering the typical SOC value of Ru and Os atoms [62, 63], the J_{eff} physics would be suppressed by the large crystal-field splitting and large hopping t . In this case, this system should be a spin-1 system, instead of a $J = 0$ singlet ground state. Furthermore, we also considered the electronic correlations on Ru ($U = 3$ eV and $J = 0.6$ eV) or Os ($U = 2$ eV and $J = 0.4$ eV) sites, by using the LSDA+ U method with Liechtenstein format within the double-counting term [57]. Figure 4 also indicates that the lower-energy d_{xy} states of MOCl_2 ($M = \text{Ru}$ or Os) begin to shift away from the Fermi level with fully-occupied characteristics when electronic correlations on the Ru or Os sites are considered.

For the benefit of the readers, we construct a qualitative physical picture for the breakdown of the $J = 0$ singlet ground state in this system, as shown in Fig. 5. First, let us discuss the three nearly degenerate t_{2g} orbitals in a low spin d^4 system without electronic correlations. Because λ (SOC strength) $\gg W$ (bandwidth, corresponding to the hopping t), the system is in a $J = 0$ insulator with fully-occupied $J_{\text{eff}} = 3/2$ states [See Fig. 5(a)]. In this case, the gap is opened by the splitting between $J_{\text{eff}} = 3/2$ and $J_{\text{eff}} = 1/2$ states caused by SOC, as displayed in Fig. 5(a). If, however, $\lambda \ll W$, then, the system will keep a $S = 1$ state due to the Pauli rule, as shown in Fig. 5(b). In this state, four electrons occupy three degenerate t_{2g} orbitals, leading to a metallic phase. In our case (RuOCl₂ and OsOCl₂), it is also a $S = 1$ state with one fully-occupied (d_{xy}) and two half-occupied (d_{xz} and d_{yz}) orbitals, as presented in Fig. 5(c). Then, the $J = 0$ singlet ground state is suppressed in our case by the large crystal-field splitting (Δ_0) and large bandwidth (W). Finally, as we will discuss in the following section, the system will be a Mott insulator when electron correlations are considered.

B. Wannier functions

According to the crystal-splitting analysis and electronic structures in the previous section, the e_g orbitals of Ru or Os ($d_{x^2-y^2}$ and $d_{3z^2-r^2}$) are located at high energy on the conduction band, far away from the Fermi level with a large energy splitting between e_g and t_{2g} orbitals. In this case, those systems can be regarded as four electrons on a three t_{2g} orbitals low-energy model. To better understand those low-energy orbitals, we constructed three disentangled Wannier functions based on the MLWFs method [55], involving the t_{2g} orbital basis d_{xy} , d_{yz} , and d_{xz} for each Ru or Os atom in the NM phase without SOC.

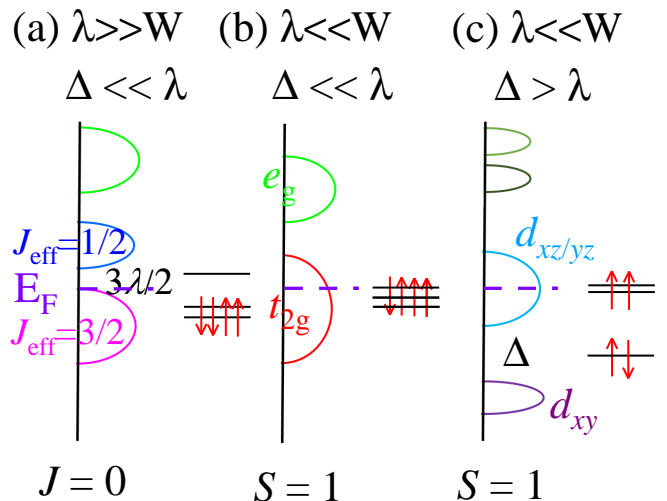


FIG. 5. The qualitative evolution of the d^4 electronic states of Ru^{4+} or Os^{4+} . Here, we consider the SOC strength λ , the bandwidth W (corresponding to t), and crystal field splitting Δ between d_{xy} and $d_{xz/yz}$ orbitals (corresponding to the Jahn-Teller distortion $Q_3 < 0$ in an octahedra). (a) $\lambda \gg W$ and $\Delta \ll \lambda$, where a $J = 0$ singlet state is realized. (b) $\lambda \ll W$ and $\Delta \ll \lambda$, where a $S = 1$ state with four electrons in three degenerate t_{2g} orbitals is obtained. (c) $\lambda \ll W$ and $\Delta > \lambda$, where a $S = 1$ state with one fully-occupied (d_{xy}) and two half-occupied $d_{xz/yz}$ orbitals is realized.

Figures 6 (a) and (c) indicate that DFT bands are fitted very well with the Wannier bands obtained from MLWFs. In fact, the blue DFT bands near the Fermi level are totally hidden by the green Wannier bands, because of the quality of the fit. As displayed in Figs. 6 (b) and (d), those orbitals obtained from MLWFs clearly display d_{xz} , d_{yz} and d_{xy} characteristics. Based on the Wannier function basis $\{d_{xz}, d_{yz}, d_{xy}\}$, here referred to as $\gamma = \{0, 1, 2\}$, we deduced the on-site energies of the three t_{2g} orbitals, as well as the hopping parameters, for RuOCl₂ and OsOCl₂, respectively.

First, we obtained the on-site matrices for the Ru or Os atoms, using the basis $\{d_{xz}, d_{yz}, d_{xy}\}$:

$$t_{\text{on-site}}^{\text{Ru}} = \begin{bmatrix} d_{xz} & d_{yz} & d_{xy} \\ 3.901 & 0.000 & 0.000 \\ 0.000 & 3.903 & 0.000 \\ 0.000 & 0.000 & 2.680 \end{bmatrix}, \quad (1)$$

$$t_{\text{on-site}}^{\text{Os}} = \begin{bmatrix} 3.721 & 0.000 & 0.000 \\ 0.000 & 3.727 & 0.000 \\ 0.000 & 0.000 & 2.255 \end{bmatrix}. \quad (2)$$

Furthermore, we also obtained the NN hopping matrices along the a -axis.

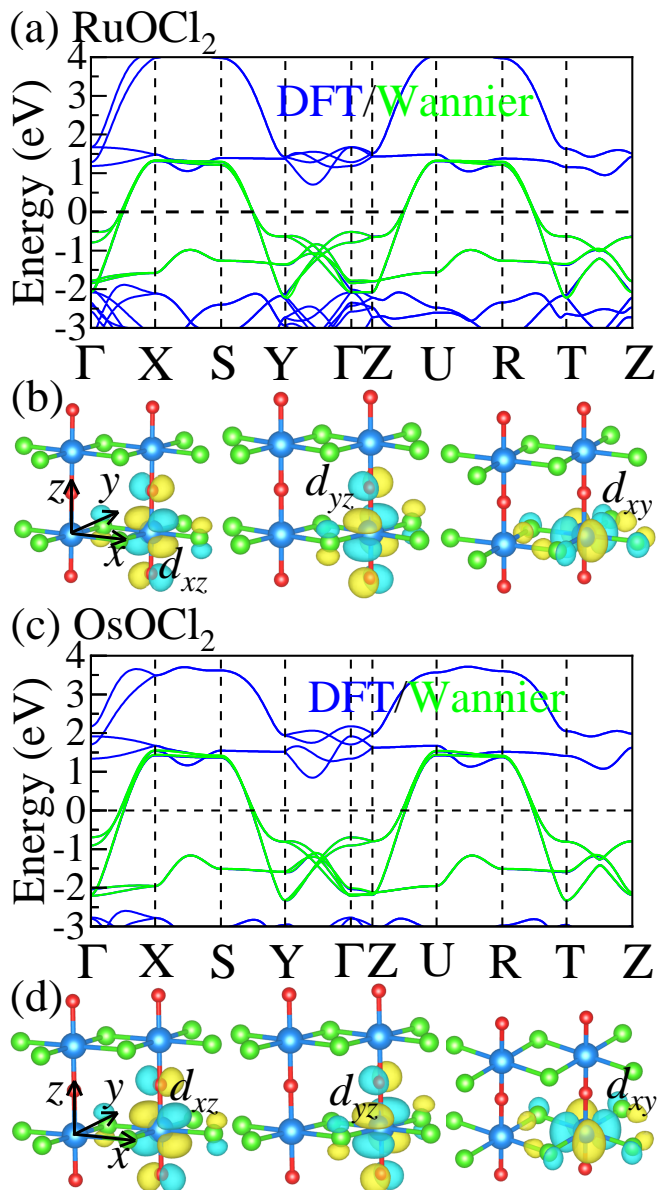


FIG. 6. (a) and (c) DFT and Wannier bands of the conventional cell of RuOCl_2 and OsOCl_2 , respectively. The Fermi level is shown with dashed horizontal lines. Note that near the Fermi level the blue DFT bands are totally hidden by the green Wannier bands, indicating the high quality of the fit. (b) and (d) are Wannier functions of the three Ru or Os t_{2g} orbitals, with lobes of opposite signs colored as blue and yellow. M ($M = \text{Ru}$ or Os), O and Cl atoms are in blue, red and green, respectively. The local basis are marked in the inset of (b) and (d), with the x - or y -axis along the M -Cl directions, while the z -axis is along the a -axis.

For RuOCl_2 :

$$t_{\gamma\gamma'}^a = \begin{bmatrix} -0.632 & 0.009 & 0.000 \\ 0.009 & -0.633 & 0.000 \\ 0.000 & 0.000 & -0.012 \end{bmatrix}. \quad (3)$$

For OsOCl_2 :

$$t_{\gamma\gamma'}^a = \begin{bmatrix} -0.713 & 0.013 & 0.000 \\ 0.013 & -0.717 & 0.000 \\ 0.000 & 0.000 & -0.011 \end{bmatrix}. \quad (4)$$

In addition, we also obtained the nearest-neighbor hopping matrices along the b -axis.

For RuOCl_2 :

$$t_{\gamma\gamma'}^b = \begin{bmatrix} 0.003 & -0.081 & 0.000 \\ -0.081 & 0.020 & 0.000 \\ 0.000 & 0.000 & -0.070 \end{bmatrix}. \quad (5)$$

For OsOCl_2 :

$$t_{\gamma\gamma'}^b = \begin{bmatrix} 0.004 & -0.103 & 0.000 \\ -0.103 & 0.033 & 0.000 \\ 0.000 & 0.000 & -0.103 \end{bmatrix}. \quad (6)$$

All the on-site and hopping matrix elements are in eV units. Note that the angle formed by M -Cl- M ($M = \text{Ru}$ or Os) is not 90° , causing a slight deviation of the local y -axis from the direction of the M -Cl bond, as shown in Fig. 1. Hence, there are tiny differences in the values of the on-site energies and hopping amplitudes between the otherwise degenerate d_{xz} and d_{yz} orbitals. Furthermore, the NN hoppings between each Ru or Os layer along the c -axis are quite small and can be neglected compared with the others. In addition, the NN hopping along the $d_{xz/yz}$ a -axis are much larger than the NN hoppings along the b -axis for both RuOCl_2 and OsOCl_2 . Then, the magnetic properties of MOCl_2 ($M = \text{Ru}$ or Os) are mainly determined by the hopping along the a -axis between NN Ru-Ru or Os-Os atoms, leading to strong anisotropic magnetism. Based on the NN hopping matrices along the a -axis of RuOCl_2 and OsOCl_2 , the hopping of the diagonal elements of $d_{xz/yz}$ orbitals are dominant, leading to a strong AFM coupling.

C. DFT magnetic properties

To better understand the in-plane magnetic properties of MOCl_2 ($M = \text{Ru}$ or Os), we also studied several magnetic configurations in a $2 \times 2 \times 1$ monolayer structure by considering different NN couplings along the a - and b -axis, as shown in Fig. 7. In addition, we also relaxed the crystal structures for different spin configurations based on the LSDA+ U method with Liechtenstein format [57]. Here, we used $U = 3$ eV and $J = 0.6$ eV for RuOCl_2 , and $U = 2$ eV and $J = 0.4$ eV for OsOCl_2 , respectively, based on previous theoretical studies [59, 64].

First, let us discuss the results without SOC, summarized in Table I. For RuOCl_2 , the Stripe- b state has the lowest energy among all tested candidates, while for OsOCl_2 the G-type AFM order is the lowest energy. Furthermore, the energy differences between Stripe- a and

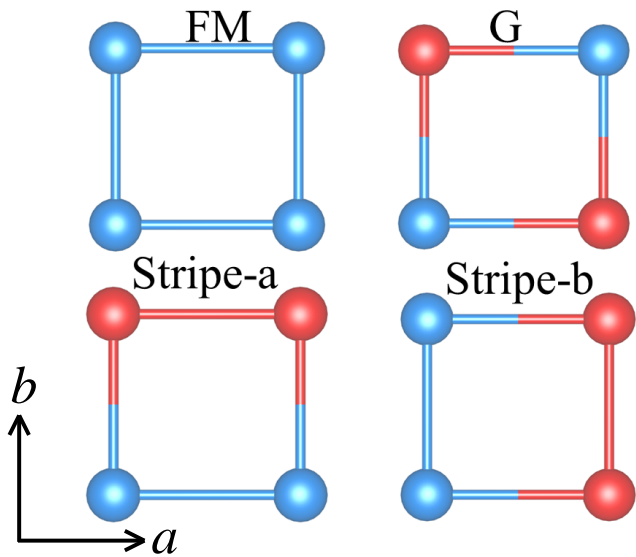


FIG. 7. Sketch of four possible magnetic patterns in the plane studied here. Spin up and down are indicated by red and blue, respectively.

TABLE I. The optimized lattice constants (\AA), local magnetic moments (in μ_B/Ru or μ_B/Os) within the default PAW sphere, and band gaps (eV) for the various magnetic configurations. Also included are the energy differences (meV/Ru or meV/Os) with respect to the Stripe-b AFM configuration, taken as the reference of energy. All the magnetic states discussed here were fully optimized.

	Magnetism	a/b	M	Gap	Energy
RuOCl ₂	FM	3.676/3.564	0.002	0.19	190.3
	G	3.709/3.558	1.051	1.46	1.82
	Stripe-a	3.676/3.562	0.177	0.28	186.5
	Stripe-b	3.710/3.560	1.047	1.39	0
OsOCl ₂	FM	3.727/3.620	0.001	0.03	80.7
	G	3.744/3.617	0.850	1.02	-0.8
	Stripe-a	3.727/3.617	0.163	0.19	75.5
	Stripe-b	3.745/3.621	0.845	0.89	0

G-AFM configurations are quite small ($\sim 1 - 2$ meV per Ru or Os), suggesting a weak magnetic exchange coupling along the $M\text{Cl}_2$ ($M = \text{Ru}$ or Os) chain direction, as in our previous intuitive analysis from the Wannier function results. In addition, the optimized crystal structures of different spin configurations are very similar to each other, indicating the spin-lattice coupling is not strong in this system. The calculated local spin magnetic moment are about $1.46 \mu_B/\text{Ru}$ and $1.02 \mu_B/\text{Os}$ for RuOCl₂ and OsOCl₂, respectively, corresponding to the $S = 1$ configuration in Ru⁴⁺ or Os⁴⁺.

Next, we compared the energies of different spin configurations with SOC. The Stripe-a and G-AFM states still have the lowest energies among all tested candidates

TABLE II. The calculated total energy (in meV) per Ru or Os with different spin orientations (along [100], [010] and [001] crystal axes) and magnetic moments (in μ_B/Ru or μ_B/Os = units) for the ground state of RuOCl₂ and OsOCl₂. The total energy with [100] spin orientation (a crystal axis) is set to zero. MAE (in meV) per Ru or Os is obtained by comparing the energy difference between [010] and [001].

	E(100)	E(010)	E(001)	m(spin)	m (orbital)	MAE
RuOCl ₂	0	-1.85	-1.85	1.052	0.002	1.85
OsOCl ₂	0	-18.26	-17.89	0.842	0.004	18.26

for RuOsCl₂ and OsOCl₂, respectively. Turning on the SOC, the spin quantization axis points to the [010] direction but with only a small difference in energy with respect to the [001] direction, indicating that the spin favors lying in the bc crystal plane, corresponding to the xy plane. Based on the energy difference between [010] and [001], we obtained that the magnetic anisotropy energies (MAE) are about 1.85 meV and 18.26 meV for RuOCl₂ and OsOCl₂, respectively, as summarized in Table II. Furthermore, the calculated orbital magnetic moment is quenched closed to zero. In this case, the magnetism of this system is almost unaffected by the SOC.

In Fig. 8, we show the band structures of the Stripe-b AFM phase of RuOCl₂ calculated with or without SOC. Figure 8(a) indicates that the half-occupied $d_{xz/yz}$ orbitals display Mott-insulating behavior with a gap ~ 1.3 eV, while the d_{xy} orbital is fully-occupied. In this case, this system is in a total $S = 1$ state, where the magnetism is contributed by the $d_{xz/yz}$ states. Turning on the SOC, the bands begin to split at some high-symmetry points. In addition, we also calculated the band structure of the G-AFM state of OsOCl₂ without or with SOC, as displayed in Fig. 9. Similar to RuOCl₂, the $d_{xz/yz}$ orbitals show strong Mott-insulating behavior with a smaller gap ~ 1 eV, while the fully-occupied d_{xy} orbital does not contribute to the magnetism. However, the band splitting under SOC is stronger in OsOCl₂ than in RuOCl₂, as shown in Fig. 9(b), considering the Os atom column in the periodic table. Furthermore, the bandstructure of the magnetic systems is strongly anisotropic along the a -axis due to the strongly anisotropic $d_{xz/yz}$ orbitals.

IV. MULTI-ORBITAL HUBBARD MODEL AND DMRG RESULTS

For low-dimensional systems, interesting phenomena caused by strongly anisotropic electronic structures have been qualitatively unveiled in theory by using simple 1D models, including 1D spin order [65], orbital ordering [66, 67], nodes in the spin density [68], as well as dimerization [34, 38].

To better understand the quasi-1D magnetic behavior

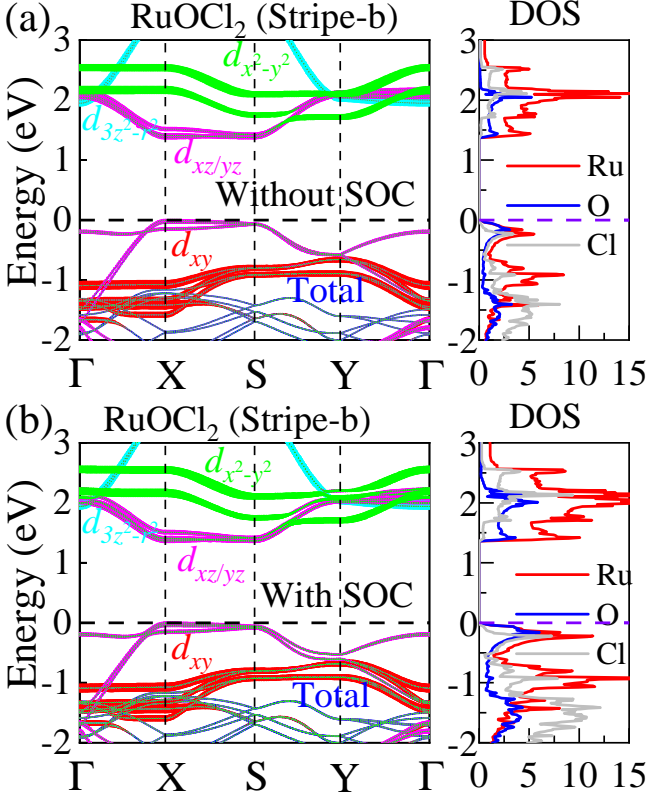


FIG. 8. Projected band structures and density of states for the Stripe-b state of RuOCl_2 (a) without SOC and (b) with SOC, respectively. The Fermi level is shown with dashed horizontal lines. The coordinates of the high-symmetry points in the BZ are $\Gamma = (0, 0, 0)$, $X = (0.5, 0, 0)$, $S = (0.5, 0.5, 0)$, and $Y = (0, 0.5, 0)$.

of MOCl_2 ($M = \text{Ru}$ or Os) along the dominant a -axis in the d^4 electronic configuration, we construct an effective multi-orbital Hubbard model and then use DMRG including quantum fluctuations [69, 70]. The model studied here includes kinetic energy and interaction energy terms $H = H_k + H_{int}$. The tight-binding kinetic portion is described as

$$H_k = \sum_{i\sigma\gamma\gamma'} t_{\gamma\gamma'} (c_{i\sigma\gamma}^\dagger c_{i+1\sigma\gamma'} + H.c.) + \sum_{i\gamma\sigma} \Delta_\gamma n_{i\gamma\sigma}, \quad (7)$$

where the first part represents the hopping of an electron from orbital γ at site i to orbital γ' at the NN site $i+1$ on a chain of length L . γ and γ' represent the three different orbitals $\{d_{xz}, d_{yz}, d_{xy}\}$ indexed as $\gamma = \{0, 1, 2\}$.

The standard interaction part of the Hamiltonian is given by

$$H_{int} = U \sum_{i\gamma} n_{i\uparrow\gamma} n_{i\downarrow\gamma} + (U' - \frac{J_H}{2}) \sum_{i \atop \gamma < \gamma'} n_{i\gamma} n_{i\gamma'} - 2J_H \sum_{i \atop \gamma < \gamma'} \mathbf{S}_{i\gamma} \cdot \mathbf{S}_{i\gamma'} + J_H \sum_{i \atop \gamma < \gamma'} (P_{i\gamma}^\dagger P_{i\gamma'} + H.c.). \quad (8)$$

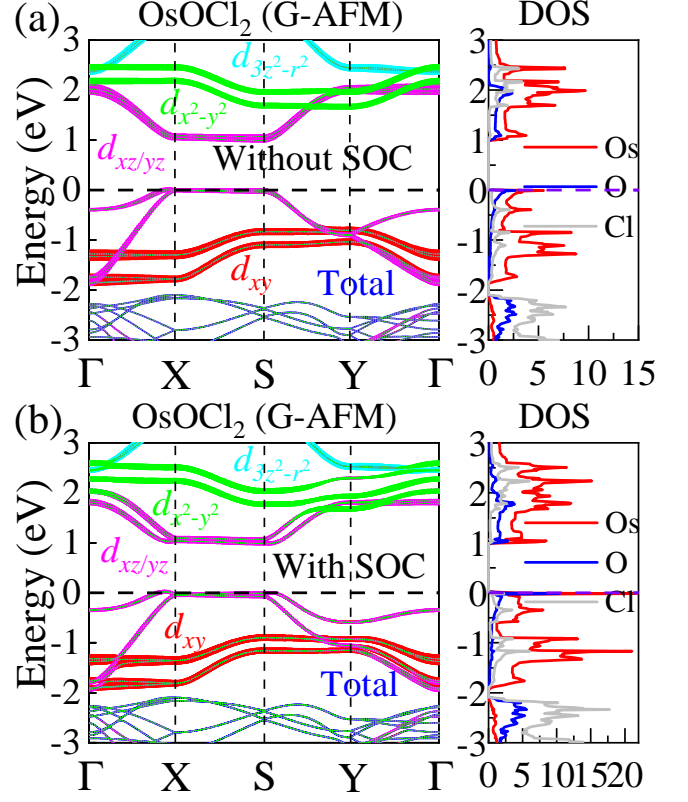


FIG. 9. Projected band structures and density of states for the G state of OsOCl_2 (a) without SOC and (b) with SOC, respectively. The Fermi level is shown with dashed horizontal lines. The coordinates of the high-symmetry points in the BZ are $\Gamma = (0, 0, 0)$, $X = (0.5, 0, 0)$, $S = (0.5, 0.5, 0)$, and $Y = (0, 0.5, 0)$.

The first term describes the intraorbital Hubbard repulsion and the second term the interorbital repulsion, where the standard relation $U' = U - 2J_H$ is assumed due to rotational invariance. The third term represents the Hund's coupling between electrons occupying the d orbitals, and the fourth term is the pair-hopping between different orbitals at the same site i , where $P_{i\gamma} = c_{i\downarrow\gamma} c_{i\uparrow\gamma}$.

As explained above, to solve this multi-orbital Hubbard model and obtain magnetic properties along the a -axis we used DMRG, as implemented in the DMRG++ software [71]. Specifically, we employed a 24-sites chain with open-boundary conditions (OBC). Furthermore, at least 1400 states were kept and up to 21 sweeps were performed during our DMRG calculations. The electronic filling $n = 4$ in the three orbitals was considered. This electronic density (four electrons in three orbitals) corresponds to the total $S = 1$ configurations of the d^4 configuration of Ru^{4+} or Os^{4+} .

In the tight-binding term, we only considered the NN hopping matrix of OsOCl_2 along the a -axis (M - O direction). The crystal-field splittings Δ_s of orbitals γ are also obtained from the Wannier results of OsOCl_2 . The total

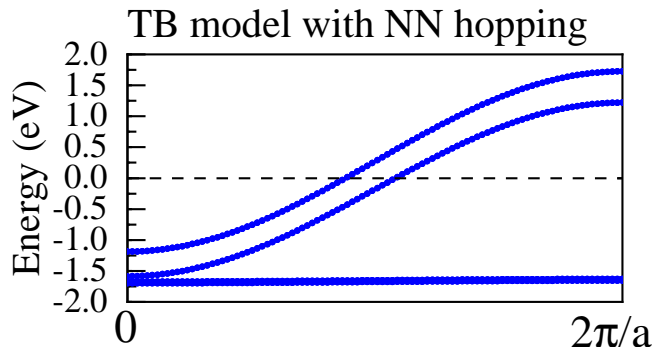


FIG. 10. Three-orbital tight-binding model with nearest-neighbor hoppings of OsOCl_2 along the a -axis. In the text in this section we explain that using three bands is a simplification from the six bands found in Fig. 6 near the Fermi level, because in the tight-binding only one Os atom is used, while in the band structure calculation we employ unit cells with two Os atoms.

kinetic energy bandwidth W is 3 eV. To reproduce the data shown in this publication, we prepared notes and input files at [72] and supplemental materials [73].

This system can be regarded as an “effective” low-energy model with four electrons in three orbitals, corresponding to an electronic density per orbital $4/3$. In addition, the SOC is not important for the magnetism, hence, we do not introduce SOC in our model. The NN hopping and on-site matrix elements of OsOCl_2 were obtained from the MLWFs calculations Sec. III.b.

This reduction in complexity allows us to perform unbiased DMRG calculations for this system. As displayed in Fig. 10, the three-orbital tight-binding bandstructure agrees qualitatively with the DFT bandstructure along the a -axis. Note that a perfect agreement Wannier and the tight-binding bands for DMRG would require more long-range hoppings. In our band structure calculation for the nonmagnetic state, see Fig. 6, we include *two layers* in a unit cell with two Os atoms. Specifically, in Fig. 6 in the range from -2.5 eV to 0 eV there are six bands because of the two Os atoms used, each contributing three t_{2g} orbitals. Meanwhile, in the tight-binding calculation Fig. 10 there are only three bands because only one Os is used. Nevertheless, qualitative features related to dominant magnetic states are expected to be captured by this simplification.

Next, we measured several observables by using the three-orbital Hubbard model and the DMRG algorithm. The real-space spin-spin correlations are defined as

$$S(r) = \langle \mathbf{S}_i \cdot \mathbf{S}_j \rangle. \quad (9)$$

Here $r = |i - j|$, and the spin at site i is

$$\mathbf{S}_i = \frac{1}{2} \sum_{\gamma} \sum_{\alpha\beta} c_{i\gamma\alpha}^{\dagger} \sigma_{\alpha\beta} c_{i\gamma\beta}, \quad (10)$$

where $\sigma_{\alpha\beta}$ are the matrix elements of the Pauli matrices. The spin structure factor is defined as

$$S(q) = \frac{1}{L} \sum_r e^{-iqr} S(r). \quad (11)$$

The site-average occupancy of orbitals is

$$n_{\gamma} = \frac{1}{L} \sum_{i,\sigma} \langle n_{i\gamma\sigma} \rangle. \quad (12)$$

The squared local spin, averaged over all the sites, is

$$\langle S^2 \rangle = \frac{1}{L} \sum_i \langle \mathbf{S}_i \cdot \mathbf{S}_i \rangle. \quad (13)$$

Figure 11 illustrates our calculation of the dominant magnetic coupling along the a -axis based on the DMRG measurements of spin-spin correlations and spin structure factors. Panel (a) shows the spin-spin correlation $S(r) = \langle \mathbf{S}_i \cdot \mathbf{S}_j \rangle$ vs. distance r , for different values of U/W , at $J_H/U = 0.15$. Here, the distance is defined as $r = |i - j|$, with site indices i and j . For weak electronic correlations, the system displays paramagnetic (PM) behavior since the spin correlation $S(r)$ decays rapidly with distance r [see the result at $U/W = 0.2$ in Fig. 11(a)]. At $U/W = 0.6$, the spin correlation $S(r)$ indicates weak staggered AFM coupling along the M -O chain direction with a small peak of the spin structure factor $S(q)$ at $q = \pi$, as shown in Fig. 11(b). Then, by increasing U/W , the spin correlation $S(r)$ shows that the system transfers into the canonical staggered AFM phase with the $\uparrow\text{-}\downarrow\text{-}\uparrow\text{-}\downarrow$ configuration in the whole region of our study ($U/W \leq 8$) [see the results at $U/W = 1.2$ and 4 in Fig. 11(a)]. As shown in Fig. 11(b), the spin structure factor $S(q)$ displays a sharp peak at $q = \pi$ at $U/W = 1.2$ and 4, corresponding to the canonical staggered AFM phase. In addition, we also calculated the spin-spin correlation $S(r)$ and spin structure factor $S(q)$ at $J_H/U = 0.2$, which are similar to the results using $J_H/U = 0.15$, as shown in Figs. 11(c) and (d). Note that in one dimension, quantum fluctuations prevent full long-range order. But the staggered order tendency is clear at both $J_H/U = 0.15$ and $J_H/U = 0.2$.

In the range of U/W studied, a dominant AFM state was found ($\uparrow\text{-}\downarrow\text{-}\uparrow\text{-}\downarrow$) in our DMRG calculations. This is physically reasonable, considering known facts about the Hubbard model. Based on the hopping matrix from MLWFs calculations, the $\gamma = 0$ and $\gamma = 1$ orbitals clearly have much larger hopping amplitudes than the $\gamma = 2$ orbital, leading to the formation of the AFM order. Furthermore, the diagonal hopping amplitudes are dominant and give rise to the superexchange mechanism in this system. In this case, the standard superexchange Hubbard spin-spin interaction dominates, causing the spins to order antiferromagnetically along the chain, in agreement with our DFT calculations.

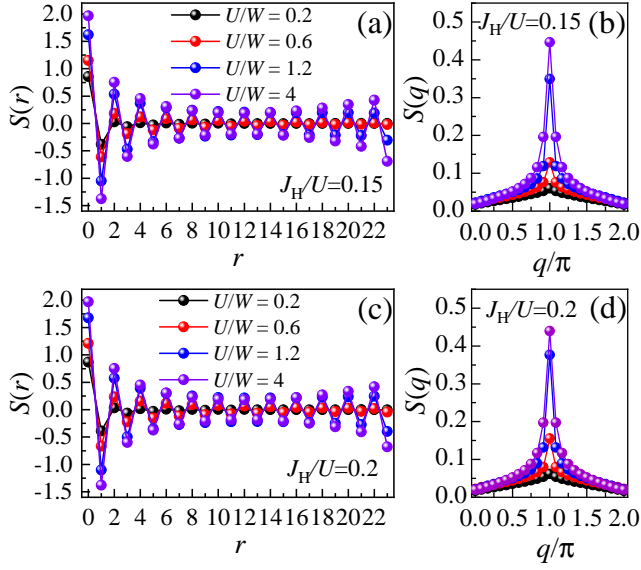


FIG. 11. Spin-spin correlations $S(r) = \langle \mathbf{S}_i \cdot \mathbf{S}_j \rangle$ (with $r = |i - j|$ in real space) for $J_H/U = 0.15$ (a) and $J_H/U = 0.2$ (c). The spin structure factor $S(q)$ for different values of U/W and $J_H/U = 0.15$ (b) and $J_H/U = 0.2$ (d). Here we have used a chain of length $L = 24$.

In addition, we also calculated the site-average occupancy of different orbitals n_γ vs U/W , for $J_H/U = 0.15$ and $J_H/U = 0.2$, respectively. As shown in Fig. 11, the population of orbital $\gamma = 2$ is 2 for the whole region of U/W , and this orbital decouples from the system. Furthermore, the other two orbitals $\gamma = 0$ and $\gamma = 1$ remain half-filled for all values of U/W . In this case, the system is in a spin $S = 1$ per site Mott-insulator staggered AFM state. Thus, increasing U/W opens a gap. Furthermore, the average value of the squared local spin averaged over all the sites $\langle S^2 \rangle$ is also displayed in Fig. 12, as a function of U/W . With increasing U/W , as the system becomes Mott insulating and antiferromagnetically ordered, $\langle S^2 \rangle$ saturates to a value of 2, as expected.

V. CONCLUSIONS

In this publication, we have systematically studied the compounds $MOCl_2$ ($M = \text{Ru}$ or Os) by using first-principles DFT and also DMRG calculations. In this system with d^4 electronic configurations, the ferroelectric distortion and Peierls instabilities disappear, leading to an undistorted Immm phase. Furthermore, with *ab initio* DFT calculations, we observed a strongly anisotropic electronic structure along the a -axis. Based on the Wannier functions from first-principles calculations, we calculated the relevant hopping amplitudes and crystal-field splitting energies of the t_{2g} orbitals for the Os atoms. In this case, this system is in a $S = 1$ state, instead of a $J = 0$ singlet groundstate, due to the large crystal-

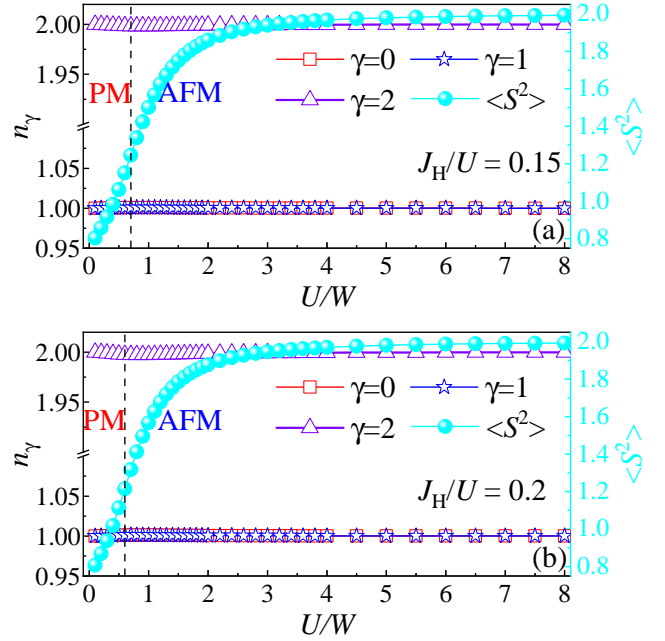


FIG. 12. Orbital-resolved occupation number n_γ , averaged total spin-squared $\langle S^2 \rangle$ vs. U/W , at (a) $J_H/U = 0.15$ and (b) $J_H/U = 0.2$, respectively. We used a 24-site chain with NN hoppings for four electrons in three orbitals.

field splitting energy (between $d_{xz/yz}$ and d_{xy} orbitals) and large nearest-neighbor hopping. In addition, based on DFT calculations, we also found strongly anisotropic magnetic structures with strong coupling along the a -axis and weak coupling along the b -axis for both RuOCl_2 and OsOCl_2 . In this case, the coupling along the M -O chain leads to staggered magnetic order with π wavevector, and the coupling along the M -Cl chain direction is weak.

In addition, we constructed a multi-orbital Hubbard model for the M -O chains. The staggered AFM with $\uparrow\text{-}\downarrow\text{-}\uparrow\text{-}\downarrow$ order was found to be dominant in our DMRG calculations, in agreement with DFT calculations. Different from the previously well-studied oxide dichlorides MOX_2 ($M = \text{V}, \text{Ta}, \text{Nb}, \text{Ru}$ and Os ; $X = \text{halogen element}$) with d^1 and d^2 configurations, note that *thus far almost no research has been reported for other electronic densities n of the M atoms in this family*. Thus, we believe our results for $MOCl_2$ ($M = \text{Ru}$ or Os) will provide guidance to experimentalists and theorists working in the oxide dichlorides family at the novel density n studied here.

ACKNOWLEDGMENTS

The work of Y.Z., L.-F.L., A.M., T.A.M., and E.D. was supported by the U.S. Department of Energy (DOE), Office of Science, Basic Energy Sciences (BES), Materials Sciences and Engineering Division. G.A. was partially

supported by the Scientific Discovery through Advanced Computing (SciDAC) program funded by U.S. DOE, Office of Science, Advanced Scientific Computing Research and BES, Division of Materials Sciences and Engineering.

-
- [1] E. Dagotto, *Rev. Mod. Phys.* **66**, 763 (1994).
- [2] M. Grioni, S. Pons and E. Frantzeskakis, *J. Phys.: Condens. Matter* **21**, 023201 (2009).
- [3] P. Monceau, *Adv. Phys.* **61**, 325 (2012).
- [4] E. Dagotto, *Rev. Mod. Phys.* **85**, 849 (2013).
- [5] B. Bertini, F. Heidrich-Meisner, C. Karrasch, T. Prosen, R. Steinigeweg, and M. Žnidarič, *Rev. Mod. Phys.* **93**, 025003 (2021).
- [6] S. Gangadharaiyah, B. Braunecker, P. Simon, and D. Loss, *Phys. Rev. Lett.* **107**, 036801 (2011).
- [7] J. Herbrych, J. Heverhagen, N. D. Patel, G. Alvarez, M. Daghofer, A. Moreo, and E. Dagotto, *Proc. Natl. Acad. Sci. USA* **117**, 16226 (2020).
- [8] J. Herbrych et. al, *Nat. Com.* **12**, 2955 (2021).
- [9] L. F. Lin, Y. Zhang, G. Alvarez, A. Moreo, and E. Dagotto, *Phys. Rev. Lett.* **127**, 077204 (2021).
- [10] E. Dagotto and T. M. Rice, *Science* **271**, 618 (1996)
- [11] E. Dagotto, *Rep. Prog. Phys.* **62**, 1525 (1999).
- [12] M. Uehara, T. Nagata, J. Akimitsu, H. Takahashi, N. Mori, and K. Kinoshita, *J. Phys. Soc. Jpn.* **65**, 2764 (1996).
- [13] H. Takahashi, A. Sugimoto, Y. Nambu, T. Yamauchi, Y. Hirata, T. Kawakami, M. Avdeev, K. Matsubayashi, F. Du, C. Kawashima, H. Soeda, S. Nakano, Y. Uwatoko, Y. Ueda, T. J. Sato and K. Ohgushi, *Nat. Mater.* **14**, 1008 (2015).
- [14] J.-J. Ying, H. C. Lei, C. Petrovic, Y.-M. Xiao and V.-V. Struzhkin, *Phys. Rev. B* **95**, 241109(R) (2017).
- [15] Y. Zhang, L. F. Lin, J. J. Zhang, E. Dagotto, and S. Dong, *Phys. Rev. B* **95**, 115154 (2017).
- [16] Y. Zhang, L. F. Lin, J. J. Zhang, E. Dagotto, and S. Dong, *Phys. Rev. B* **97**, 045119 (2018).
- [17] Y. Zhang, L. F. Lin, A. Moreo, S. Dong, and E. Dagotto, *Phys. Rev. B* **100**, 184419 (2019).
- [18] L. F. Lin, Y. Zhang, A. Moreo, E. Dagotto, and S. Dong, *Phys. Rev. Mater.* **3**, 111401(R) (2019).
- [19] J. van den Brink and D. I Khomskii, *J. Phys.: Condens. Matter* **20**, 434217 (2008).
- [20] L.-F. Lin, Q.-R. Xu, Y. Zhang, J.-J. Zhang, Y.-P. Liang, and S. Dong, *Phys. Rev. Materials* **1**, 071401(R) (2017).
- [21] S. Dong, H.-J. Xiang, and E. Dagotto, *Nat. Sci. Rev.* **6**, 629 (2019).
- [22] Y. Zhang, L. F. Lin, A. Moreo, S. Dong, and E. Dagotto, *Phys. Rev. B* **101**, 144417 (2020).
- [23] Z. Wang and S.-C. Zhang, *Phys. Rev. B* **87**, 161107(R) (2013).
- [24] J. Gooth, B. Bradlyn, S. Honnali, C. Schindler, N. Kumar, J. Noky, Y. Qi, C. Shekhar, Y. Sun, Z. Wang, B. A. Bernevig and C. Felser, *Nature* **575**, 315 (2019).
- [25] Y. Zhang, L. F. Lin, A. Moreo, S. Dong, and E. Dagotto, *Phys. Rev. B* **101**, 174106 (2020).
- [26] H. Hillebrecht, P.J. Schmidt, H.W. Rotter, G. Thiele, P. Zönnchen, H. Bengel, H.-J. Cantow, S.-N. Magonov, M.-H. Whangbo, *J. Alloys Compd.* **246**, 70 (1997).
- [27] H. G. Schnering, and H. Wöhrle, *Angew. Chem.* **75**, 684 (1963).
- [28] M. Ruck, *Acta Cryst. C* **6**, 1960 (1996).
- [29] H. Tan, M. Li, H. Liu, Z. Liu, Y. Li, and W. Duan, *Phys. Rev. B* **99**, 195434 (2019).
- [30] C. Xu, P. Chen, H. Tan, Y. Yang, H. Xiang, and L. Bellaiche, *Phys. Rev. Lett.* **125**, 037203 (2020).
- [31] Y. Jia, M. Zhao, G. Gou, X. C. Zeng, and J. Li, *Nanoscale Horiz.* **4**, 1113 (2019).
- [32] Z. Wang, M. Huang, J. Zhao, C. Chen, H. Huang, X. Wang, P. Liu, J. Wang, J. Xiang, C. Feng, Z. Zhang, X. Cui, Y. Lu, S. A. Yang, and B. Xiang, *Phys. Rev. Mater.* **4**, 041001(R) (2020).
- [33] N. Ding, J. Chen, S. Dong, and A. Stroppa, *Phys. Rev. B* **102**, 165129 (2020).
- [34] Y. Zhang, L. F. Lin, A. Moreo, G. Alvarez, and E. Dagotto, *Phys. Rev. B* **103**, L121114 (2021).
- [35] Y. Fang, F. Wang, R. Wang, T. Zhai, and F. Huang, *Adv. Mater.* **33**, 2101505 (2021).
- [36] Q. Ye, Y.-H. Shen, and C.-G. Duan, *Chin. Phys. Lett.* **38**, 087702 (2021).
- [37] J. Zhao, W. Wu, J. Zhu, Y. Lu, B. Xiang, and S. A. Yang, *Phys. Rev. B* **102**, 245419 (2020).
- [38] Y. Zhang, L. F. Lin, A. Moreo, and E. Dagotto, *Phys. Rev. B* **104**, L060102 (2021).
- [39] L. de' Medici, S. R. Hassan, M. Capone, and X. Dai, *Phys. Rev. Lett.* **102**, 126401 (2009).
- [40] N. D. Patel, A. Nocera, G. Alvarez, A. Moreo, S. Johnston and E. Dagotto, *Comm. Phys.* **2**, 64 (2019)
- [41] J. Herbrych, J. Heverhagen, N. D. Patel, G. Alvarez, M. Daghofer, A. Moreo, and E. Dagotto, *Phys. Rev. Lett.* **123**, 027203 (2019).
- [42] Y. Zhang, L.-F. Lin, G. Alvarez, A. Moreo, and E. Dagotto, *Phys. Rev. B* **104**, 125122 (2021).
- [43] L.-F. Lin, Y. Zhang, G. Alvarez, J. Herbrych, A. Moreo, and E. Dagotto, *arXiv preprint arXiv:2112.04049*.
- [44] S. A. J. Kimber, I. I. Mazin, J. Shen, H. O. Jeschke, S. V. Streltsov, D. N. Argyriou, R. Valentí, and D. I. Khomskii, *Phys. Rev. B* **89**, 081408(R) (2014).
- [45] H. Gao, C. Ding, L. Sun, X. Ma, and M. Zhao, *Phys. Rev. B* **104**, 205424 (2021).
- [46] G. Khaliullin, *Phys. Rev. Lett.* **111**, 197201 (2013).
- [47] O. N. Meetei, W. S. Cole, M. Randeria, and N. Trivedi, *Phys. Rev. B* **91**, 054412 (2015).
- [48] G. Kresse and J. Hafner, *Phys. Rev. B* **47**, 558 (1993).
- [49] G. Kresse and J. Furthmüller, *Phys. Rev. B* **54**, 11169 (1996).
- [50] P. E. Blöchl, *Phys. Rev. B* **50**, 17953 (1994).
- [51] J. P. Perdew, K. Burke, and M. Ernzerhof, *Phys. Rev. Lett.* **77**, 3865 (1996).
- [52] S. Grimme, S. Ehrlich, and L. Goerigk, *J. Comp. Chem.* **32**, 1456 (2011).
- [53] L. Chaput, A. Togo, I. Tanaka, and G. Hug, *Phys. Rev. B* **84**, 094302 (2011).
- [54] A. Togo, I. Tanaka, *Scr. Mater.* **108**, 1 (2015).
- [55] A. A. Mostofi, J. R. Yates, Y. S. Lee, I. Souza, D. Vanderbilt, and N. Marzari, *Comput. Phys. Commun.* **178**, 685 (2007).
- [56] K. Momma and F. Izumi, *J. Appl. Crystallogr.* **44**, 1272 (2011).
- [57] A. I. Liechtenstein, V. I. Anisimov, and J. Zaanen, *Phys. Rev. B* **52**, R5467 (1995).
- [58] B. Yuan, J. P. Clancy, A. M. Cook, C. M. Thompson, J. Greedan, G. Cao, B. C. Jeon, T. W. Noh, M. H. Upton,

- D. Casa, T. Gog, A. Paramakanti, and Y.-J. Kim, *Phys. Rev. B* **95**, 235114 (2017).
- [59] E. Şaşıoğlu, C. Friedrich, and S. Blügel, *Phys. Rev. B* **83**, 121101(R) (2011).
- [60] Y. Du, X. Wan, L. Sheng, J. Dong, and S. Y. Savrasov, *Phys. Rev. B* **85**, 174424 (2012).
- [61] Y. Zhang, L. F. Lin, A. Moreo, and E. Dagotto, *Appl. Phys. Lett.* **120**, 023101 (2022).
- [62] Y. Zhang, L. F. Lin, A. Moreo, and E. Dagotto, *Phys. Rev. B* **105**, 085107 (2022).
- [63] W. Witczak-Krempa, G. Chen, Y. B. Kim, and L. Balents, *Annu. Rev. Condens. Matter Phys.* **5**, 57 (2014).
- [64] L. Vaugier, H. Jiang, and S. Biermann, *Phys. Rev. B* **86**, 165105 (2012).
- [65] S. Gao, L.-F. Lin, A. F. May, B. K. Rai, Q. Zhang, E. Dagotto, A. D. Christianson, and M. B. Stone, *Phys. Rev. B* **102**, 220402(R) (2020).
- [66] B. Pandey, Y. Zhang, N. Kaushal, R. Soni, L.-F. Lin, W.-J. Hu, G. Alvarez, and E. Dagotto, *Phys. Rev. B* **103**, 045115 (2021).
- [67] L.-F. Lin, N. Kaushal, Y. Zhang, A. Moreo, and E. Dagotto, *Phys. Rev. Mater.* **5**, 025001 (2021).
- [68] L.-F. Lin, N. Kaushal, C. Şen, A. D. Christianson, A. Moreo, and E. Dagotto, *Phys. Rev. B* **103**, 184414 (2021).
- [69] S. R. White, *Phys. Rev. Lett.* **69**, 2863 (1992).
- [70] S. R. White, *Phys. Rev. B* **48**, 10345 (1993).
- [71] G. Alvarez, *Comput. Phys. Commun.* **180**, 1572 (2009).
- [72] <https://g1257.github.io/dmrgPlusPlus/>
- [73] To reproduce the data shown in this publication, see the notes in Supplemental Material at <http://link.aps.org/supplemental/10.1103/PhysRevB.xx/xxxxxx>.