

Role of disorder in the electronic and magnetic properties of $\text{Ag}_3\text{LiIr}_2\text{O}_6$

Ying Li^{1,*} and Roser Valenti^{2,†}

¹*Department of Applied Physics and MOE Key Laboratory for Nonequilibrium Synthesis and Modulation of Condensed Matter, School of Physics, Xi'an Jiaotong University, Xi'an 710049, China*

²*Institut für Theoretische Physik, Goethe-Universität Frankfurt, Max-von-Laue-Strasse 1, 60438 Frankfurt am Main, Germany*

(Dated: March 4, 2022)

The nature of magnetism in the intercalated honeycomb iridate $\text{Ag}_3\text{LiIr}_2\text{O}_6$ has been a subject of recent intensive debate, where the absence or presence of antiferromagnetic order has been reported to be related to possible structural disorder effects and, an enhanced Ir-O hybridization and itinerancy with respect to the parent $\alpha\text{-Li}_2\text{IrO}_3$ has been suggested as the origin of distinct x-ray spectroscopy features. In the present work we investigate the microscopic nature of the electronic and magnetic properties of $\text{Ag}_3\text{LiIr}_2\text{O}_6$ via a combination of density functional theory combined with exact diagonalization of ab initio-derived models for various experimental and theoretical structures. We evaluate two possible scenarios, the itinerant quasimolecular framework (QMO) on the one hand, and the localized relativistic $j_{\text{eff}} = 1/2$ and $j_{\text{eff}} = 3/2$ picture on the other hand, and find that the latter description is still viable for this system. We further calculate resonant inelastic x-ray scattering spectra and show that agreement with experimental observations can be obtained if the presence of Ag vacancies leading to changes in Ir filling and structural disorder is assumed. Finally, we show that the experimentally observed antiferromagnetic spiral magnetic order is reproduced by our ab-initio derived magnetic models.

I. INTRODUCTION

Intensive efforts have been devoted to searching material realizations of the Kitaev spin liquid state in the honeycomb lattice with bond-dependent Ising-like nearest-neighbor interactions [1–9]. Promising candidates for the Kitaev spin liquid including the layered honeycomb systems Na_2IrO_3 [10–12], $\alpha\text{-Li}_2\text{IrO}_3$ [12–14], and $\alpha\text{-RuCl}_3$ [15–21] order magnetically either in a zigzag structure (Na_2IrO_3 and $\alpha\text{-RuCl}_3$) or in an incommensurate spiral structure ($\alpha\text{-Li}_2\text{IrO}_3$ [22]) due to the presence of further non-Kitaev interactions [23–27]. For the latter, attempts have been made to modulate the magnetic interactions in terms of intercalated H atoms [28–30]. For the resulting $\text{H}_3\text{LiIr}_2\text{O}_6$, magnetic susceptibility, specific heat, and nuclear magnetic resonance (NMR) measurements showed no sign of magnetic order down to 0.05 K [30]. In fact, theoretical studies [31, 32] indicated that H positions strongly affect the magnetic interactions, and resulting magnetic models with bond disorder and vacancies were shown to reproduce the experimentally observed low-energy spectrum in the system [33, 34].

Recently, a new member of the intercalated honeycomb iridates family $\text{Ag}_3\text{LiIr}_2\text{O}_6$ has been synthesized by replacing interlayer Li in $\alpha\text{-Li}_2\text{IrO}_3$ by Ag atoms [35]. Heat capacity and magnetic susceptibility measurements on those samples suggested $\text{Ag}_3\text{LiIr}_2\text{O}_6$ to be closer to the Kitaev limit compared to $\alpha\text{-Li}_2\text{IrO}_3$. However, by improving the sample quality controlling that Ag doesn't enter the honeycomb layers, a broad peak in the magnetic

susceptibility and heat capacity at $T_N = 14$ K was observed, which, together with a sharper downturn in the magnetic susceptibility at $T_{N2} = 8$ K and the appearance of spontaneous oscillations in muon spin relaxation (μSR) measurements, evidenced the presence of long range incommensurate AFM ordering below T_{N2} [36] of the same type as in $\alpha\text{-Li}_2\text{IrO}_3$. The different behavior between the two $\text{Ag}_3\text{LiIr}_2\text{O}_6$ samples was also confirmed by NMR observations [37]. In addition, x-ray absorption and resonant inelastic x-ray scattering (RIXS) measurements on powder samples in Ref. [38] suggested an energy spectrum for $\text{Ag}_3\text{LiIr}_2\text{O}_6$ compatible with the assumption of enhanced Ir-O hybridizations. An aspect to note is that the sample characterization of Ref. [38] doesn't exclude a possible Ir charge disbalance of about 0.2%, which corresponds to the error bar of the Energy Dispersive X-Ray Analysis (EDX). Such a charge disbalance could be caused by e.g. the presence of interlayer Ag vacancies.

In view of the above observations, we investigate here the microscopic origin of the electronic and magnetic properties in $\text{Ag}_3\text{LiIr}_2\text{O}_6$ in comparison to its parent compound $\alpha\text{-Li}_2\text{IrO}_3$ and analyze the role of disorder effects related to the presence of Ag vacancies. For that, we perform density functional theory (DFT) calculations combined with exact diagonalization (ED) of ab initio-based models for various experimental and theoretically-derived structures.

Such spin models are obtained under the assumption of large spin-orbit coupling and Coulomb repulsion leading to a localized basis of $j_{\text{eff}} = 1/2$ and lower lying $j_{\text{eff}} = 3/2$ relativistic orbitals. Alternatively, due to the honeycomb backbone nature of these systems with dominant oxygen assisted $d-d$ hybridizations, one can consider a description of the electronic structure of in terms of quasimolecular orbitals (QMOs) [39, 40]. In the nonrelativistic

* yingli1227@xjtu.edu.cn

† valenti@itp.uni-frankfurt.de

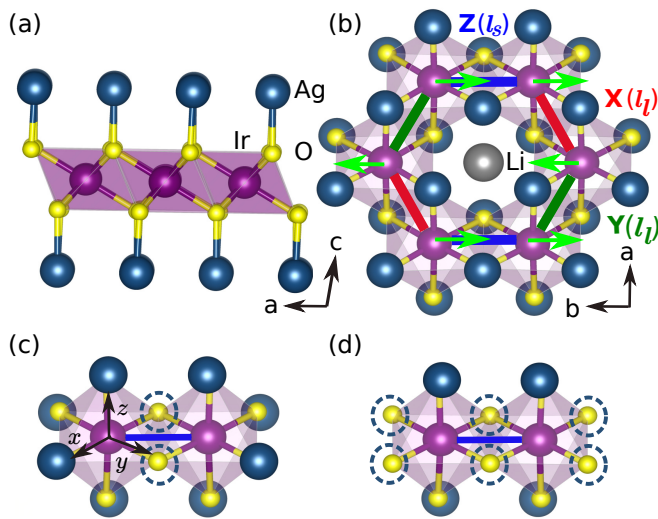


FIG. 1. Crystal structure of $\text{Ag}_3\text{LiIr}_2\text{O}_6$ in the (a) ac plane and (b) ab plane. Ir, Ag and O are displayed as magenta, dark blue and yellow balls. Red, green, and blue bonds show the three different types of bonds, X, Y, and Z, respectively. The green arrows in (b) indicate the stripy magnetic configuration used in the calculations. l_l denotes the length of the long bond (X and Y) and l_s the length of the short bond (Z) for the structure S_3 (see the main text). (c) and (d) show two types of Ag vacancies considered (marked with circles) on Z-bond Ir-Ir clusters corresponding to $\text{Ir}^{4.5+}$ and Ir^{5+} , respectively. x, y, z are the cartesian coordinates for d orbitals.

case, the electronic structure of Na_2IrO_3 for instance, is well described by the QMO basis. Inclusion of spin-orbit effects induces mixing of the QMO states, as was shown in [40]. Strong Coulomb repulsion can destroy the QMOs in favor of a description in terms of localized states, however some features of the QMOs may still be detected as it has been shown in the analysis of optical conductivity of Na_2IrO_3 and $\alpha\text{-Li}_2\text{IrO}_3$ [41]. Actually, a description in terms of fully localized (j_{eff}) or itinerant QMO scenarios strongly depends on a competition between the various energy scales involved (kinetic energy, crystal field splittings, spin-orbit coupling and Coulomb repulsion).

For stoichiometric $\text{Ag}_3\text{LiIr}_2\text{O}_6$ our results show that the Ir-O hybridization is moderate and a localized relativistic $j_{\text{eff}} = 1/2$ magnetic model is still valid for the description of the system. We also find that assuming the presence of Ag vacancies has an important impact on the experimental RIXS spectra due to the modification of Ir filling and hopping parameters. We also show that the extracted exchange parameters for the stoichiometric systems reproduce the experimentally observed spin spiral order.

The paper is organized as follows. In Sec. II we discuss the electronic properties of various structures of $\text{Ag}_3\text{LiIr}_2\text{O}_6$ from the perspective of DFT calculations. In Sec. III we calculate the RIXS spectra with the help of exact diagonalization of the multiorbital Hubbard model on small clusters. In Sec. IV the magnetic interactions

are estimated and the magnetic properties are analyzed. Finally, in Sec. V we discuss and summarize our findings.

II. DENSITY FUNCTIONAL THEORY CALCULATIONS

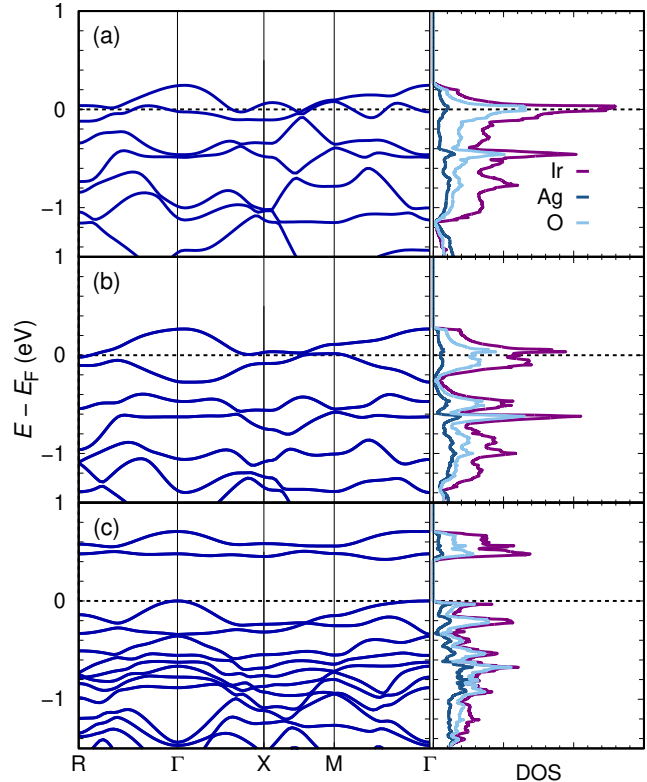


FIG. 2. Band structure and partial density of states for the relaxed structure S_2 within (a) GGA, (b) GGA+SO, and (c) GGA+SO+ U , respectively obtained with the LAPW basis [42]. In the GGA+SO+ U calculation we considered a stripy magnetization as shown in Fig. 1 with doubling of the unit cell.

The crystal structure of $\text{Ag}_3\text{LiIr}_2\text{O}_6$ is displayed in Fig. 1 (a) - (b). Edge sharing IrO_6 octahedra build the hexagonal planes in $\text{Ag}_3\text{LiIr}_2\text{O}_6$ with Li atoms in the hexagonal center while Ag atoms are placed between the layers. Since the structural details are different in various experiments, we consider here various structures of $\text{Ag}_3\text{LiIr}_2\text{O}_6$: (i) the experimental structure from Ref. [36] (S_1), (ii) the corresponding relaxed structure within DFT (S_2), (iii) the experimental structure from Ref. [38] (S_3), and (iv) in order to investigate the effects of possible charge disbalance through Ag vacancies, we remove one Ag along the Z bond from the S_3 structure resulting in structure S_4 with one Ag vacancy per six Ag atoms in the unit cell as shown in Fig. 1 (c), and we consider as well the case of one Ag vacancy per two Ag atoms per unit cell as shown in Fig. 1 (d) for the Z bond, that we denote structure S_5 . Starting from the

TABLE I. Lattice parameters ($C2/m$), nearest-neighbor Ir-Ir distances (\AA), Ir-O distances (\AA) Ir-O-Ir bond angles ($^\circ$), crystal-field splittings (meV), and nearest-neighbor hopping integrals (meV) for the five structures. The t_{2g} crystal fields Δ_1 , Δ_2 denote, respectively, the on-site hopping between d_{xz} and d_{yz} orbitals, d_{xy} and $d_{yz/xz}$ orbitals. Δ_3 is the on-site energy of d_{xy} minus $d_{yz/xz}$ [25]. The labels t_1 , t_2 , t_3 and t_4 are given in Ref. [24, 25] and shown in Fig. 3. The notations $t_{1\parallel}$, t_{1O} , $t_{1\sigma}$ and $t_{1\perp}$ are the same as in Ref. [40].

Structure	S_1			S_2			S_3			S_4			S_5		
a, b, c	5.283, 9.136, 6.486						5.345, 9.014, 6.469								
α, β, γ	90, 74.29, 90						90, 105.42, 90								
Bond	Z	X(Y)	Z	X(Y)	Z	X(Y)	Z	X(Y)	Z	X(Y)	Z	X(Y)	Z	X(Y)	Z
Ir-Ir	3.09	3.03	3.0479	3.0474	2.99	3.07	2.99	3.07	2.99	3.07	2.99	3.07	2.99	3.07	2.99
Ir-O	2.06	2.04	2.016	2.016	2.06	2.00	2.06	2.00	2.06	2.00	2.06	2.00	2.06	2.00	2.06
Ir-O-Ir	97.4	96.3	98.2	98.1	93.3	94.8	93.3	94.8	93.3	94.8	93.3	94.8	93.3	94.8	93.3
Δ_1	-72.1			-78.4			-56.9			-17.1			12.7		
Δ_2	-54.8			-62.6			-78.3			-23.0			2.0		
Δ_3	55.7			11.6			157.0			205.1			289.8		
Bond	Z	X(Y)	Z	X(Y)	Z	X(Y)	Z	X(Y)	Z	X(Y)	Z	X(Y)	Z	X(Y)	Z
t_1 ($t_{1\parallel}$)	-13.2	-17.9	-10.0	-18.4	25.0	-9.4	28.8	-17.9	-10.0	-18.4	25.0	-9.4	28.8	-17.9	-10.0
t'_1		22.4		9.4		32.6		22.4		9.4		32.6		22.4	
t_2 (t_{1O})	168.6	154.2	185.0	189.4	203.4	109.2	310.1	154.2	185.0	189.4	203.4	109.2	310.1	154.2	185.0
t_3 ($t_{1\sigma}$)	-97.0	-158.2	-75.5	-87.1	-242.8	-158.1	-137.2	-97.0	-158.2	-75.5	-87.1	-242.8	-158.1	-137.2	-124.7
t_4 ($t_{1\perp}$)	-27.7	-2.3	-39.7	-23.7	-48.1	-34.4	-6.7	-27.7	-2.3	-39.7	-23.7	-48.1	-34.4	-6.7	-9.4
t'_4		7.7		-18.4		-26.9		7.7		-18.4		-26.9		7.7	

S_3 structure, the bond lengths and angles of the resultant relaxed structure have values between those of S_2 and S_3 and its total energy is higher than that of S_2 . We therefore consider in what follows only S_2 as the theoretical relaxed structure.

We note that the vacancy cases considered correspond to a much larger concentration of vacancies than the possible concentrations present in the material. Simulation of smaller concentrations would require large supercell calculations. Since we are interested in evaluating possible effects emerging from the local presence of Ag vacancies around Ir, we consider here the very extreme cases S_4 and S_5 where not only the Ir filling of the Ag neighboring Ir is affected but the Ir-O hoppings as well. In S_4 [Fig. 1 (c)] the Ag vacancies induce on the Z bond a filling $\text{Ir}^{4.5+}$ (occupation $d^{4.5}$). In S_5 [Fig. 1 (d)] the Ir filling on the Z bond is Ir^{5+} (occupation d^4). All the structures are in the $C2/m$ symmetry as shown in Fig. 1. The corresponding lattice parameters, bond lengths and Ir-O-Ir angles for the five structures are displayed in Table. I. The anisotropy between the X (Y) and Z bonds are found to be strong in the two experimental structures S_1 and S_3 while weak in the relaxed structure S_2 . For the S_3 structure, the bond ratio $l_l/l_s \sim 1.03$, where l_l denotes the length of the long bond (X and Y) and l_s the length of the short bond (Z) is smaller than the strong dimerization case under pressure in RuCl_3 [43] with $l_l/l_s \sim 1.25$.

The S_2 structure is obtained from the experimental

structure S_1 by fixing the lattice parameters and relaxing the atomic coordinates using the Vienna *ab initio* simulation package (VASP) [44, 45]. To keep consistency with previous calculations [41] for $\alpha\text{-Li}_2\text{IrO}_3$, we considered relativistic effects as well as contributions of the Coulomb repulsion [46] ($U_{\text{eff}} = 2.4$ eV) within GGA+SO+ U . We adopted a cutoff energy of 520 eV and Monkhorst-pack k-points generated with $8 \times 6 \times 8$. The choice of $U_{\text{eff}} = 2.4$ eV was done following Ref. [41], which was determined by the gap of the electronic structures in Na_2IrO_3 . We also considered $U_{\text{eff}} = 2$ eV and 3 eV but the resultant relaxed structures are not significantly affected by the values.

The band structures were obtained from full-potential linearized augmented plane-wave (LAPW) calculations [42]. We chose the basis-size controlling parameter $\text{RK}_{\text{max}} = 8$ and a mesh of 500 \mathbf{k} points in the first Brillouin zone (FBZ) of the primitive unit cell. The density of states (DOS) were computed with 1000 \mathbf{k} points in the full Brillouin zone.

We start with the band structures and partial DOS within GGA, GGA+SO and GGA+SO+ U obtained from LAPW calculations for the relaxed structure S_2 as presented in Fig. 2 (a-c). The DOS around the Fermi level in GGA is dominated by Ir t_{2g} and O states and it includes contributions from Ag, in contrast to $\alpha\text{-Li}_2\text{IrO}_3$ and $\text{H}_3\text{LiIr}_2\text{O}_6$ where the DOS around the Fermi level has only Ir and O contributions. From this we expect that Ag will affect the oxygen assisted Ir-Ir hoppings stronger

than Li.

Inclusion of U within the GGA+SO+ U approach in the stripy magnetic configuration [see Fig. 1 (b)] which has the lowest energy within all collinear magnetic configurations, opens a gap of 409 meV [Fig. 2 (c)]. We note that the electronic properties for the two experimental structures S_1 and S_3 are similar to those obtained for the S_2 structure with Ag contribution around the Fermi level and insulating behavior within GGA+SO+ U .

Valuable information on the hybridization patterns can be obtained from the analysis of the hopping parameters extracted from GGA. Table I displays the hopping parameters between Ir $5d$ t_{2g} orbitals computed via the Wannier function projection method [25, 40] for the four structures. In terms of the t_{2g} d -orbital basis:

$$\vec{c}_i^\dagger = \left(c_{i,yz,\uparrow}^\dagger, c_{i,yz,\downarrow}^\dagger, c_{i,xz,\uparrow}^\dagger, c_{i,xz,\downarrow}^\dagger, c_{i,xy,\uparrow}^\dagger, c_{i,xy,\downarrow}^\dagger \right) \quad (1)$$

where $c_{i,a}^\dagger$ creates a hole in orbital $a \in \{d_{yz}, d_{xz}, d_{xy}\}$ at site i and the crystal field terms can be written as:

$$\mathcal{H}_{\text{CF}} = - \sum_i \vec{c}_i^\dagger \{ \mathbf{E}_i \otimes \mathbb{I}_{2 \times 2} \} \vec{c}_i \quad (2)$$

where $\mathbb{I}_{2 \times 2}$ is the 2×2 identity matrix (for the spin variables); the crystal field tensor \mathbf{E}_i is constrained by local 2-fold symmetry at each Ir site to be:

$$\mathbf{E}_i = \begin{pmatrix} 0 & \Delta_1 & \Delta_2 \\ \Delta_1 & 0 & \Delta_2 \\ \Delta_2 & \Delta_2 & \Delta_3 \end{pmatrix} \quad (3)$$

The t_{2g} crystal fields Δ_1 , Δ_2 denote the on-site hopping between d_{xz} and d_{yz} orbitals, and between d_{xy} and $d_{yz/xz}$ orbitals, respectively (Table I). Δ_3 is the on-site energy of d_{xy} minus that of $d_{yz/xz}$ [25]. There are large trigonal distortions Δ_1 and Δ_2 due to Ag atoms, which induce an anisotropic crystal field on Ir by distorting the Ir-O octahedra. Replacing Ag by Li and keeping the local geometry reduces the values to -49 meV (Δ_1) and -41 meV (Δ_2) for the S_2 structure, which is closer to the α -Li₂IrO₃ results [25]. We observe that the tetragonal distortion Δ_3 is 157 meV for the S_3 structure, which is much larger than in the case of S_1 , S_2 and α -Li₂IrO₃ (-5.5 meV) [25] and closer to that of γ -Li₂IrO₃ [47]. In this case the t_{2g} crystal field is of the same order of magnitude as the spin-orbit coupling λ and this has significant effects on the local magnetic interactions as we will show further below. In the structure S_4 with Ag vacancies, on the Z-bond the crystal field Δ_3 is enhanced while Δ_1 and Δ_2 are somewhat suppressed in comparison to the S_3 structure.

The nearest neighbor hopping parameters t_1 , t_2 , t_3 and t_4 are defined in Ref. [24, 25] and shown in Fig 3 for the Z-bond in terms of $t_1 = t_{xz,xz} = t_{yz,yz}$, $t_2 = t_{xz,yz} = t_{yz,xz}$, $t_3 = t_{xy,xy}$, and $t_4 = t_{xz,xy} = t_{yz,xy} = t_{xy,xz} = t_{xy,yz}$. In terms of the t_{2g} d -orbital basis, the hopping Hamiltonian is most generally written as

$$\mathcal{H}_{\text{hop}} = - \sum_{ij} \vec{c}_i^\dagger \{ \mathbf{T}_{ij} \otimes \mathbb{I}_{2 \times 2} \} \vec{c}_j, \quad (4)$$

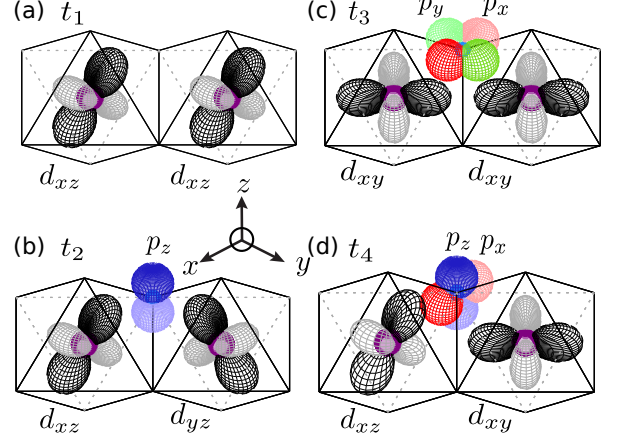


FIG. 3. Geometry of nearest-neighbor hopping integrals (a) t_1 , (b) t_2 , (c) t_3 , and (d) t_4 for the Z bond [31]. Both t_2 and t_3 include contributions of oxygen assisted hopping and direct hopping. t_2 is dominated by oxygen assisted hopping while t_3 is dominated by direct hopping. In Ag₃LiIr₂O₆ the oxygen assisted part of t_3 is strongly affected by Ag-O hybridization.

with the hopping matrices \mathbf{T}_{ij} defined for each bond connecting sites i, j . The hopping integrals for the nearest neighbor Z-bond (C_{2h} symmetry) are written as [25]

$$\mathbf{T}_Z = \begin{pmatrix} t_1 & t_2 & t_4 \\ t_2 & t_1 & t_4 \\ t_4 & t_4 & t_3 \end{pmatrix} \quad (5)$$

where X- and Y-bonds are of lower symmetry (C_i), and therefore t_1 (t_4) split into two values which are labeled as t_1 and t'_1 (t_4 and t'_4). The hopping matrices become:

$$\mathbf{T}_X = \begin{pmatrix} t_3 & t'_4 & t_4 \\ t'_4 & t'_1 & t_2 \\ t_4 & t_2 & t_1 \end{pmatrix}, \mathbf{T}_Y = \begin{pmatrix} t'_1 & t'_4 & t_2 \\ t'_4 & t_3 & t_4 \\ t_2 & t_4 & t_1 \end{pmatrix}. \quad (6)$$

For the experimental structure S_1 , there is a strong anisotropy between Z and X/Y-bonds. For the Z-bond, $t_2 > |t_3|$ while for the X bond, $|t_3|$ is slightly larger than t_2 . These anisotropies are even more pronounced for the experimental structure S_3 . The magnitude of the direct hopping $|t_3|$ is much larger than the oxygen assisted one t_2 . After structural relaxation, the bond anisotropy is suppressed in S_2 . The hopping parameters, which are very sensitive to the structural details, are slightly different between the Z bond and X/Y-bonds. The ratio of $t_2/|t_3|$ mainly depends on the angle of Ir-O-Ir [25]. Since S_2 has the largest Ir-O-Ir angle within the three structures, it hence has the largest $t_2/|t_3|$. The Ir-O-Ir angle in the S_2 structure is 98° , close to the angle of Na₂IrO₃. Ir-O bond lengths are $2.0 \sim 2.18$ Å for S_1 - S_3 in Ag₃LiIr₂O₆ and $2.06 \sim 2.08$ Å in Na₂IrO₃. However, t_2 is much smaller in Ag₃LiIr₂O₆ than in Na₂IrO₃ (264 meV) while

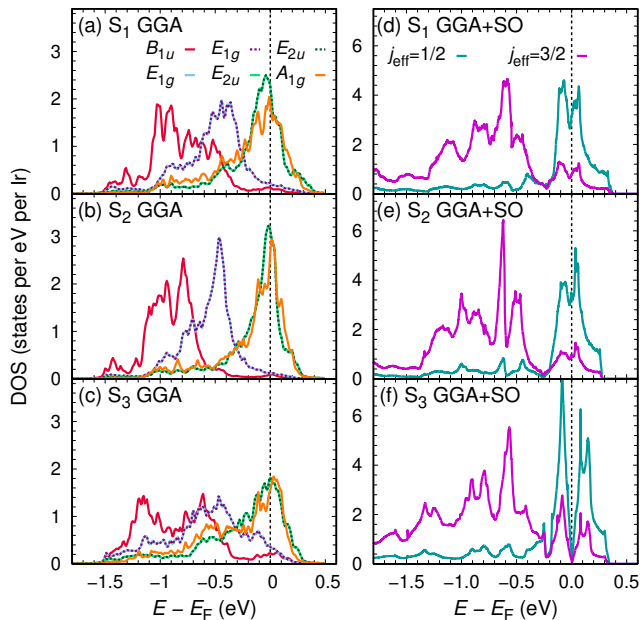


FIG. 4. (a)-(c) Nonrelativistic GGA density of states projected onto quasimolecular orbitals and (d)-(f) relativistic GGA+SO density of states projected onto the relativistic j_{eff} basis for structures $S_1 - S_3$.

the magnitude of $|t_3|$ is much larger than in Na_2IrO_3 (26.6 meV). Therefore the effect of Ag is to enhance the Ag-O hybridization and, correspondingly, the oxygen mediated d - d hopping integrals involving single (multiple) O p -orbitals are suppressed (enhanced). Taking the Z-bond as an example shown in Fig. 3, t_2 is reduced due to suppression of the hopping paths like $\text{Ir}(d_{xz}) \rightarrow \text{O}(p_z) \rightarrow \text{Ir}(d_{yz})$. Similarly, $|t_3|$ and $|t_4|$ are enhanced through hopping paths such as $\text{Ir}(d_{xz}) \rightarrow \text{O}(p_z) \rightarrow \text{Ag}(s) \rightarrow \text{O}(p_x) \rightarrow \text{Ir}(d_{xy})$.

This is opposite when vacancies are introduced. the Ag vacancy in the S_4 structure enhances t_2 in the Z bonds from 203.4 meV to 310.1 meV and reduces $|t_3|$ from 242.8 meV to 137.2 meV. This is because Ir and O have stronger hybridization without Ag. For the X (Y) bond (not shown), the symmetry of the two Ir-O-Ir hopping paths is broken by the asymmetric Ag atom positions, leading to different t_2 .

In order to discuss the choice of basis for the effective spin Hamiltonian, we first display in Fig. 4 (a) - (c) the nonrelativistic density of states within GGA projected onto the quasimolecular-orbital (QMO) [39, 40] basis for the structures $S_1 - S_3$. We observe that the separation of the density of states into isolated narrow bands of unique QMO characters is much less evident in S_1 - S_3 than in Na_2IrO_3 [39] and resembles the case of α - Li_2IrO_3 [41]. For instance, for the S_3 structure we observe a strong mixing of QMO states due to a smaller $t_2/|t_3|$ than in Na_2IrO_3 . When spin orbit effects are included, while for Na_2IrO_3 (with $t_2 \sim 0.27$ eV, $|t_3| \sim 0.025$ eV [40]) both, the relativistic basis and QMO provide a good description of the electronic properties, in $\text{Ag}_3\text{LiIr}_2\text{O}_6$ t_2

is reduced to $0.15 \sim 0.2$ eV and $|t_3|$ increases, resulting in the suppression of QMO and enhancement of the relativistic basis. We therefore present in Fig. 4 (d) - (f) the electronic structure within GGA+SO projected to the relativistic j_{eff} basis. The spin-orbit coupling largely destroys the QMOs and leads instead to the formation of relativistic $j_{\text{eff}} = 1/2$ orbitals with a small contribution from $j_{\text{eff}} = 3/2$ around the Fermi level.

III. RIXS SPECTRA

Based on the density of states from DFT, we calculated the joint density of states (see Appendix A), which corresponds to the peak positions of the RIXS spectra. However, as discussed in Ref. 47, DFT doesn't fully capture the effects originating from correlations beyond GGA+SO+ U , which are expected to be relevant when analyzing electronic excitations. Specifically, DFT does not correctly capture the spin-multiplicity associated with the localized states. In order to compare to the experimental RIXS spectra, we perform exact diagonalization of one-site and two-sites clusters of the Ir t_{2g} -only Hamiltonian

$$\mathcal{H}_{\text{tot}} = \mathcal{H}_{\text{hop}} + \mathcal{H}_{\text{CF}} + \mathcal{H}_{\text{SO}} + \mathcal{H}_U \quad (7)$$

consisting of the kinetic hopping term \mathcal{H}_{hop} , the crystal field splitting \mathcal{H}_{CF} , spin-orbit coupling \mathcal{H}_{SO} , and Coulomb interaction \mathcal{H}_U contributions. In terms of the t_{2g} basis introduced above, the spin-orbit coupling (SO) is described by:

$$\mathcal{H}_{\text{SO}} = \frac{\lambda}{2} \sum_i \vec{c}_i^\dagger \begin{pmatrix} 0 & -i\sigma_z & i\sigma_y \\ i\sigma_z & 0 & -i\sigma_x \\ -i\sigma_y & i\sigma_x & 0 \end{pmatrix} \vec{c}_i \quad (8)$$

where σ_μ , $\mu = \{x, y, z\}$ are Pauli matrices. The Coulomb terms are:

$$\begin{aligned} \mathcal{H}_U &= U \sum_{i,a} n_{i,a,\uparrow} n_{i,a,\downarrow} + (U' - J_{\text{H}}) \sum_{i,a < b,\sigma} n_{i,a,\sigma} n_{i,b,\sigma} \\ &+ U' \sum_{i,a \neq b} n_{i,a,\uparrow} n_{i,b,\downarrow} - J_{\text{H}} \sum_{i,a \neq b} c_{i,a,\uparrow}^\dagger c_{i,a,\downarrow} c_{i,b,\downarrow}^\dagger c_{i,b,\uparrow} \\ &+ J_{\text{H}} \sum_{i,a \neq b} c_{i,a,\uparrow}^\dagger c_{i,a,\downarrow}^\dagger c_{i,b,\downarrow} c_{i,b,\uparrow} \end{aligned} \quad (9)$$

where J_{H} gives the strength of Hund's coupling, U is the *intraorbital* Coulomb repulsion, and $U' = U - 2J_{\text{H}}$ is the *interorbital* repulsion. For $5d$ Ir we take $U = 1.7$ eV, $J_{\text{H}} = 0.3$ eV [25, 48]. Based on the eigenenergies, we analyzed the states. In one-site and two-site clusters, we consider states with a total of one hole or two holes in the t_{2g} orbitals, respectively. Each Ir site contains six relativistic orbitals consisting of two $j_{\text{eff}} = 1/2$ and four $j_{\text{eff}} = 3/2$ levels. As in Ref. [47, 49], the many-body basis states for the cluster can be divided into several subspaces \mathcal{B}_i ($i = 1, 2, 3, 4$) based on the occupancy of the

various orbitals and sites as shown in Fig. 5 (c). The subspace \mathcal{B}_1 contains all states with $(j_{3/2})^4(j_{1/2})^1$ occupancy at every site, which represent a significant contribution to the ground state and low-lying magnon-like spin excitations. From these configurations, promotion of a single electron via *onsite* $j_{3/2} \rightarrow j_{1/2}$ generates subspace \mathcal{B}_2 , containing all states with a single spin-orbital exciton; the characteristic excitation energy for such states is given by $\Delta E_2 \sim 3\lambda/2 \sim 0.6$ eV if the crystal-field and hopping parameters are zero. For the two-site cluster, the states with two excitons are grouped into subspace \mathcal{B}_3 with energies $\Delta E_3 \sim 2\Delta E_2$, and the basis states with site occupancy d^4-d^6 belong to \mathcal{B}_4 . We project the exact cluster eigenstates ϕ_m on different subspaces \mathcal{B}_i :

$$\Gamma_i^m = \sum_{b \in \mathcal{B}_i} |\langle \phi_m | b \rangle|^2, \quad (10)$$

and take the spectral weight (SW) of the projected excitation spectra P_i [47, 49]:

$$P_i(E_{loss}) = \sum_m \Gamma_i^m \delta(E_{loss} - E_m), \quad (11)$$

Where E_{loss} is the energy transfer from the ground state to all other states. P_i ($i = 1, 2, 3, 4$) are shown in Fig. 5 (a) for one site and (b) for two sites (Z-bond) cluster calculations. For the one-site cluster, as expected, the ground state around 0 eV has dominant \mathcal{B}_1 character (large P_1), and the peaks centered at 0.55 and 0.73 eV have dominant \mathcal{B}_2 character. For two-site cluster of Z-bond, in addition to the ground state around 0 eV, P_1 has a peak around 0.02 eV indicating low-lying magnon-like spin excitations. Regarding higher excitations, \mathcal{B}_2 is weakly mixed with the multi-particle \mathcal{B}_3 and \mathcal{B}_4 excitations via intersite hopping. P_2 has peaks of 0.58, 0.78 eV and an additional shoulder at 0.49 eV. Similar results were obtained in Ref. [49] in the analysis of the excitation spectra of Na_2IrO_3 . For the two-site cluster calculation of X-bond, the peaks are close to Z-bond but the 0.49 eV one disappears due to smaller hopping integrals.

The joint density of states (JDOS) is defined as

$$\text{JDOS}(E_{loss}) \propto \delta(E_{loss} - E_f + E_g) \quad (12)$$

where E_g and E_f are the ground states and excited states, respectively. The RIXS spectra are given by

$$\text{RIXS}(E_{loss}) \propto \sum_f \left| \sum_i e^{-i\mathbf{Q}\cdot\mathbf{R}_i} \langle f | F_i \rangle \right|^2 \delta(E_{loss} - E_f + E_g) \quad (13)$$

where the final state is generated by the RIXS process:

$$|F_i\rangle = D_i^\dagger \frac{1}{E_{in} - H_{inter} + E_g + i\Gamma_c/2} D_i^\dagger |g\rangle. \quad (14)$$

Here g (f) are the ground (excited) eigenstates of H_{tot} , and E_{in} is the energy of the incident x-ray. D_i is the

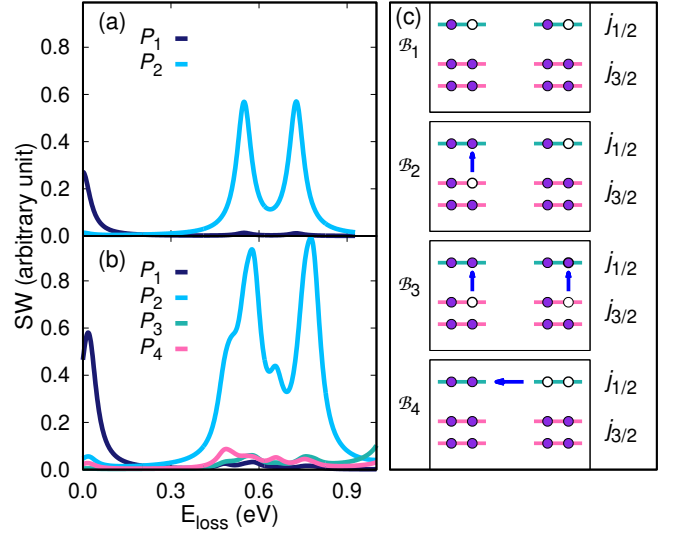


FIG. 5. Spectral weight of various states (Eq. 11) obtained from performing (a) one-site and (b) two-site cluster calculations for the experimental structure S_3 . P_1 indicates the ground state, P_2 is a local exciton, P_3 are multiple excitons while P_4 are all the projections including d^4-d^6 . (c) Schematic diagrams of the lowest-energy subspaces \mathcal{B}_1 , \mathcal{B}_2 , \mathcal{B}_3 and \mathcal{B}_4 as defined in the main text.

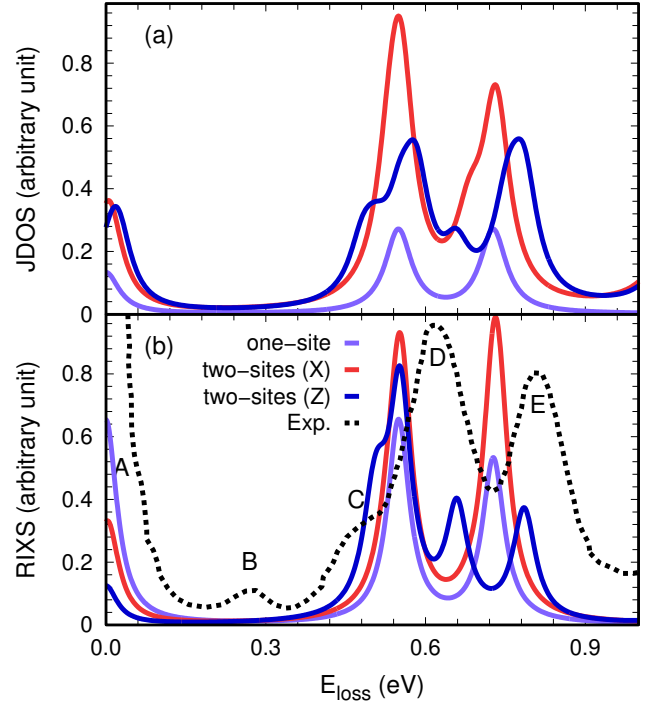


FIG. 6. (a) JDOS and (b) RIXS results obtained from one-site and two-site cluster calculations (see main text) for the experimental structure S_3 . The experimental data from Ref. [38] are shown with a black dashed line where A, B, C, D, E indicate the experimental observed peaks.

dipolar transition operator from $2p$ to $5d$ shell on the Ir site, and H_{inter} is the intermediate configuration of the RIXS process where a $2p$ core-hole is created and Γ_c is the core-hole life time broadening. \mathbf{Q} is the wave vectors of the incident and outgoing photons and \mathbf{R}_i are the positions of Ir sites. Here we use the EDRIXS software package [50] for the calculations.

In our calculation, we set $2\theta = 90^\circ$ and fix the incident beam polarization to lie in the scattering plane and average over the outgoing direction in and perpendicular to the scattering plane. JDOS and RIXS have the same peak positions while the weights are different. Including the matrix elements in RIXS, some JDOS peaks are enhanced while others are suppressed. The calculated JDOS and RIXS spectra obtained for the experimental structure S_3 are compared in Fig. 6 with the experimental measurements. There are five peaks from the experiment at A ~ 0.029 eV, B ~ 0.27 eV, C ~ 0.47 eV, D ~ 0.623 eV, and E ~ 0.811 eV. The peaks D and E which indicate the local excitations from $j_{1/2}$ to $j_{3/2}$ could be obtained both by our one-site and two-site calculations. The peaks A corresponding to magnon-like spin excitations and C arising from the mixing of local exciton state \mathcal{B}_2 with other states could be captured by our two-site calculation. We observe that the peak B does not appear in the calculated results. In Ref. [38] a large $t_2 \sim 0.525$ eV had to be assumed to reproduce the data. The JDOS and RIXS spectra have been also calculated and compared for S_1 and S_2 (see Appendix A) and find that the peaks C and D are robust for the three structures but E only appears in S_3 .

We consider now the effect of Ag vacancies [Fig. 1 (c) and (d)] in the system. We observe that consideration of Ag vacancies as introduced in the structures S_4 and S_5 enhances t_2 in the neighboring Ir as shown in Table. I and induces different occupations of Ir ($d^{4.5}$ and d^5 in the case of the Z-bond). In order to take this into account, we performed cluster calculations for the cases Ir-Ir $d^5 - d^5$, $d^{4.5} - d^{4.5}$, and $d^4 - d^4$ using the hopping parameters of Z-bond in the S_3 , S_4 and S_5 structures, respectively. The calculated JDOS and RIXS are displayed in Fig. 7. We observe that RIXS calculated with the $d^{4.5} - d^{4.5}$ cluster shows peaks around 0.06, 0.35, 0.58, 0.8, and 0.9 eV while in the $d^4 - d^4$ cluster the peaks are around 0.27, 0.39, 0.56, 0.72, and 0.94 eV. Of special importance for both cases, is that they seem to generate an important contribution in the energy region where the B peak in RIXS has been reported. Although the ratio of Ir d^4 and d^5 is expected to be small as described in Ref. [38], the local occupancies $d^{4.5} - d^{4.5}$ and $d^4 - d^4$ in our calculations may still have a measurable contribution to produce a peak comparable to the B peak in experiment. A smaller ratio of $d^{4.5}/d^5$ and $d^{4.5}/d^5$ in experiment as the one assumed in our calculations could also explain the smaller magnitude of the reported B peak in experiment than in our calculation. Furthermore, in the region of 0.4 and 0.8 eV [see Fig. 8], the comparison of the $d^5 - d^5$ case to the case of introducing Ag vacancies

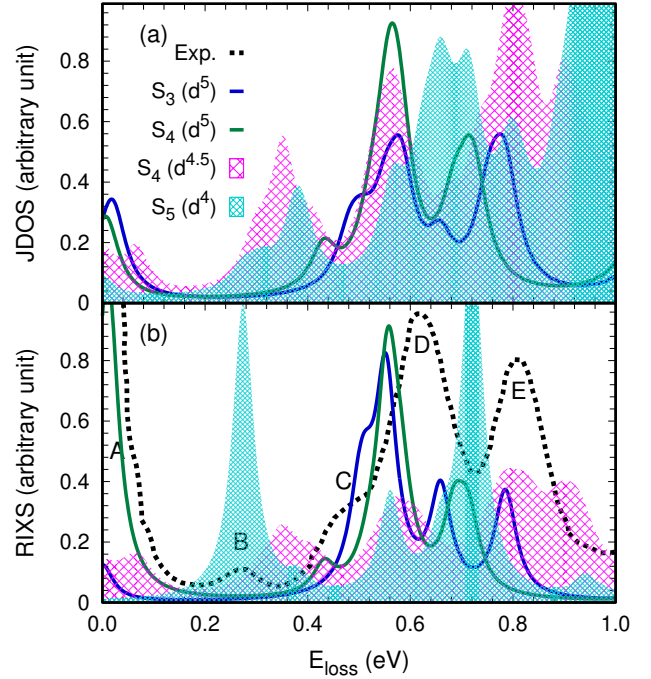


FIG. 7. (a) JDOS and (b) RIXS results obtained from two-site cluster (Z-bond) calculations for (i) the structure S_3 with Ir occupancies $d^5 - d^5$, (ii) the structure S_4 with Ir occupancies $d^5 - d^5$, (iii) the structure S_4 with Ir occupancies $d^{4.5} - d^{4.5}$, and (iv) the structure S_5 with Ir occupancies $d^4 - d^4$.

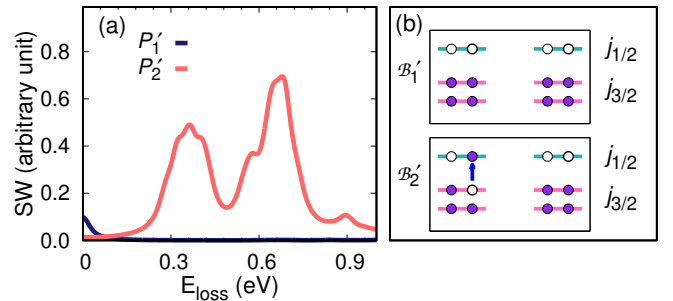


FIG. 8. (a) Spectral weight (Eq. 11) of various states obtained from two-site cluster calculations for the S_4 structure with Ir occupancies $d^4 - d^4$. P'_1 indicates the ground states, and P'_2 is local excitons for d^4 . (b) Schematic diagrams of the lowest-energy subspaces \mathcal{B}'_i ($i = 1, 2$) for $d^4 - d^4$.

($d^{4.5} - d^{4.5}$) shows some spectral shifts, which may also explain the slight discrepancies in this region between the experimental observations and the calculations from the stoichiometric case. Further supercell investigations studying more possible vacancy concentrations and the effect of vacancy-vacancy interactions, may help in the future to obtain a final picture.

In order to understand the origin of the B peak, we calculate the dominant spectral weight P'_i ($i = 1, 2$) for $d^4 - d^4$ clusters in the corresponding energy region. The

TABLE II. The magnetic interactions in meV for the four structures obtained by exact diagonalization on two-site cluster employing $U = 1.7$ eV, $J_H = 0.3$ eV, $\lambda = 0.4$ eV.

Structures	S_1		S_2		S_3		S_4	
	Z	X(Y)	Z	X(Y)	Z	X(Y)	Z	X(Y)
J_1	11.4	13.7	7.3	6.9	21.7	7.1	6.1	2.1
K_1	-6.6	-5.8	-9.8	-10.8	0.7	-2.5	-10.3	-2.5
Γ_1	1.6	3.5	0.8	1.5	9.0	2.1	10.3	-0.2
Γ'_1	-2.1	-0.7	-3.6	-2.8	-2.3	-0.9	-1.4	2.2

results in Fig. 8 show that the dominant contribution to peak B is a single exciton via *onsite* $j_{3/2} \rightarrow j_{1/2}$ in d^4 .

IV. MAGNETIC INTERACTIONS

The magnetic interactions for $\text{Ag}_3\text{LiIr}_2\text{O}_6$ displayed in Table. II were estimated by exact diagonalization in a two-site cluster of the corresponding multiorbital Hubbard model including spin-orbit coupling interactions [20, 25]. The exchange parameters are calculated with the same parameters as in the previous section, namely $U = 1.7$ eV, $J_H = 0.3$ eV, and $\lambda = 0.4$ eV [25, 48]. For the experimental structure S_1 , the Heisenberg exchange interactions are the dominant ones. Averaging the interactions of X (Y) and Z bonds, we obtain $(J_1, K_1, \Gamma_1, \Gamma'_1) \sim (12.9, -6.1, 2.9, -1.2)$ meV, leading to Neel AFM magnetic configurations following the classical calculations in Ref. [25]. For the experimental structure S_3 , J_1 is dominant and the anisotropic bond interactions are quite different. The ground state is a Neel AFM magnetic configuration. For the relaxed structure S_2 , there is less anisotropy between the Z and X/Y bonds and the average interactions are $(J_1, K_1, \Gamma_1, \Gamma'_1) \sim (7.0, -10.5, 1.3, -3.1)$ meV, leading to the experimentally observed spin-spiral order with q vector around 0.42 along the a direction, close to 0.32 of $\alpha\text{-Li}_2\text{IrO}_3$. The corresponding Weiss constant is $\Theta_0^{ab} = -\frac{3}{4k_B}[J + \frac{1}{3}K - \frac{1}{3}(\Gamma + 2\Gamma')] = -74.9$ K and $\Theta_0^c = -\frac{3}{4k_B}[J + \frac{1}{3}K + \frac{2}{3}(\Gamma + 2\Gamma')] = -34.2$ K [51]. Comparing the values for the S_2 structure with $\alpha\text{-Li}_2\text{IrO}_3$ $(J_1, K_1, \Gamma_1, \Gamma'_1) \sim (-2.7, -8.6, 8.9, -0.6)$ meV [25], J_1 and Γ'_1 are strongly enhanced while Γ_1 is reduced. We have also calculated the second and third neighbor interactions for S_2 and the averaged results are $(J_2, K_2, \Gamma_2, \Gamma'_2, D, J_3) \sim (0.5, -0.5, 0.7, 0.4, 0.6, 1.3)$,

which are much smaller than for $\alpha\text{-Li}_2\text{IrO}_3$ [25]. For the structure S_4 with Ag impurities, the exchange parameters are significantly changed due to the modified hoppings.

V. SUMMARY

In this work we have investigated the electronic and magnetic properties of the intercalated honeycomb iridate $\text{Ag}_3\text{LiIr}_2\text{O}_6$ by a combination of density functional theory and exact diagonalization of Hubbard models on finite clusters. We show that the magnetism of this system is well captured in terms of a localized relativistic $j_{\text{eff}} = 1/2$ basis. We find that the reported resonant inelastic x-ray scattering spectra can be reproduced if Ag vacancies which introduce both different Ir filling and modified hybridizations are assumed. Our results clarify the important role of impurities in intercalated Kitaev candidates. Other systems such as $\text{Ba}_3\text{CeIr}_2\text{O}_9$ [52] may also need to invoke the presence of impurities in order to fully explain RIXS data. Finally, our magnetic models for the stoichiometric structure reproduce the experimental observed spin spiral order.

ACKNOWLEDGMENTS

We thank Fazel Tafti, Faranak Bahram and Kemp Plump for fruitful discussions. Y.L. acknowledges support by the National Natural Science Foundation of China (Grant No. 12004296) and the China Postdoctoral Science Foundation (Grant No. 2019M660249). R.V. acknowledges support by the Deutsche Forschungsgemeinschaft (DFG, German Research Foundation) for funding through Project No. TRR 288 — 422213477 (project A05, B05).

- [1] A. Kitaev, Anyons in an exactly solved model and beyond, *Annals of Physics* **321**, 2 (2006).
 [2] G. Jackeli and G. Khaliullin, Mott insulators in the strong spin-orbit coupling limit: From Heisenberg to a quantum compass and Kitaev models, *Phys. Rev. Lett.*

102, 017205 (2009).

- [3] J. Chaloupka, G. Jackeli, and G. Khaliullin, Zigzag magnetic order in the iridium oxide Na_2IrO_3 , *Phys. Rev. Lett.* **110**, 097204 (2013).

- [4] W. Witczak-Krempa, G. Chen, Y. B. Kim, and L. Balents, Correlated quantum phenomena in the strong spin-orbit regime, *Annual Review of Condensed Matter Physics* **5**, 57 (2014).
- [5] J. G. Rau, E. K.-H. Lee, and H.-Y. Kee, Spin-orbit physics giving rise to novel phases in correlated systems: Iridates and related materials, *Annual Review of Condensed Matter Physics* **7**, 195 (2016).
- [6] R. Schaffer, E. K.-H. Lee, B.-J. Yang, and Y. B. Kim, Recent progress on correlated electron systems with strong spin-orbit coupling, *Rep. Prog. Phys.* **79**, 094504 (2016).
- [7] S. M. Winter, A. A. Tsirlin, M. Daghofer, J. van den Brink, Y. Singh, P. Gegenwart, and R. Valentí, Models and materials for generalized Kitaev magnetism, *Journal of Physics: Condensed Matter* **29**, 493002 (2017).
- [8] S. Trebst, Kitaev materials, *arXiv preprint arXiv:1701.07056* (2017).
- [9] G. Cao and P. Schlottmann, The challenge of spin-orbital-tuned ground states in iridates: a key issues review, *Rep. Prog. Phys.* **81**, 042502 (2018).
- [10] Y. Singh and P. Gegenwart, Antiferromagnetic mott insulating state in single crystals of the honeycomb lattice material Na_2IrO_3 , *Phys. Rev. B* **82**, 064412 (2010).
- [11] S. K. Choi, R. Coldea, A. N. Kolmogorov, T. Lancaster, I. I. Mazin, S. J. Blundell, P. G. Radaelli, Y. Singh, P. Gegenwart, K. R. Choi, S.-W. Cheong, P. J. Baker, C. Stock, and J. Taylor, Spin waves and revised crystal structure of honeycomb iridate Na_2IrO_3 , *Phys. Rev. Lett.* **108**, 127204 (2012).
- [12] Y. Singh, S. Manni, J. Reuther, T. Berlijn, R. Thomale, W. Ku, S. Trebst, and P. Gegenwart, Relevance of the Heisenberg-Kitaev model for the honeycomb lattice iridates A_2IrO_3 , *Phys. Rev. Lett.* **108**, 127203 (2012).
- [13] H. Gretarsson, J. P. Clancy, X. Liu, J. P. Hill, E. Bozin, Y. Singh, S. Manni, P. Gegenwart, J. Kim, A. H. Said, D. Casa, T. Gog, M. H. Upton, H.-S. Kim, J. Yu, V. M. Katukuri, L. Hozoi, J. van den Brink, and Y.-J. Kim, Crystal-field splitting and correlation effect on the electronic structure of A_2IrO_3 , *Phys. Rev. Lett.* **110**, 076402 (2013).
- [14] F. Freund, S. C. Williams, R. D. Johnson, R. Coldea, P. Gegenwart, and A. Jesche, Single crystal growth from separated educts and its application to lithium transition-metal oxides, *Scientific Reports* **6**, 35362 (2016).
- [15] K. W. Plumb, J. P. Clancy, L. J. Sandilands, V. V. Shankar, Y. F. Hu, K. S. Burch, H.-Y. Kee, and Y.-J. Kim, $\alpha\text{-RuCl}_3$: A spin-orbit assisted mott insulator on a honeycomb lattice, *Phys. Rev. B* **90**, 041112 (2014).
- [16] H.-S. Kim, V. V. Shankar, A. Catuneanu, and H.-Y. Kee, Kitaev magnetism in honeycomb RuCl_3 with intermediate spin-orbit coupling, *Phys. Rev. B* **91**, 241110 (2015).
- [17] R. D. Johnson, S. C. Williams, A. A. Haghighirad, J. Singleton, V. Zapf, P. Manuel, I. I. Mazin, Y. Li, H. O. Jeschke, R. Valentí, and R. Coldea, Monoclinic crystal structure of RuCl_3 and the zigzag antiferromagnetic ground state, *Phys. Rev. B* **92**, 235119 (2015).
- [18] A. Banerjee, C. A. Bridges, J.-Q. Yan, A. A. Aczel, L. Li, M. B. Stone, G. E. Granroth, M. D. Lumsden, Y. Yiu, J. Knolle, S. Bhattacharjee, D. L. Kovrizhin, R. Moessner, D. A. Tennant, D. G. Mandrus, and S. E. Nagler, Proximate Kitaev quantum spin liquid behaviour in a honeycomb magnet, *Nature Materials* **15**, 733 (2016).
- [19] A. Banerjee, J. Yan, J. Knolle, C. A. Bridges, M. B. Stone, M. D. Lumsden, D. G. Mandrus, D. A. Tennant, R. Moessner, and S. E. Nagler, Neutron scattering in the proximate quantum spin liquid $\alpha\text{-RuCl}_3$, *Science* **356**, 1055 (2017).
- [20] S. M. Winter, K. Riedl, P. A. Maksimov, A. L. Chernyshev, A. Honecker, and R. Valentí, Breakdown of magnons in a strongly spin-orbital coupled magnet, *Nature Communications* **8**, 1152 (2017).
- [21] S. M. Winter, K. Riedl, D. Kaib, R. Coldea, and R. Valentí, Probing $\alpha\text{-RuCl}_3$ beyond magnetic order: Effects of temperature and magnetic field, *Phys. Rev. Lett.* **120**, 077203 (2018).
- [22] S. C. Williams, R. D. Johnson, F. Freund, S. Choi, A. Jesche, I. Kimchi, S. Manni, A. Bombardi, P. Manuel, P. Gegenwart, and R. Coldea, Incommensurate counter-rotating magnetic order stabilized by Kitaev interactions in the layered honeycomb $\alpha\text{-Li}_2\text{IrO}_3$, *Phys. Rev. B* **93**, 195158 (2016).
- [23] V. M. Katukuri, S. Nishimoto, V. Yushankhai, A. Stoyanova, H. Kandpal, S. Choi, R. Coldea, I. Rousochatzakis, L. Hozoi, and J. van den Brink, Kitaev interactions between $\hat{j}\hat{A} = \hat{A} 1/2$ moments in honeycomb Na_2IrO_3 are large and ferromagnetic: insights from *ab initio* quantum chemistry calculations, *New Journal of Physics* **16**, 013056 (2014).
- [24] J. G. Rau, E. K.-H. Lee, and H.-Y. Kee, Generic spin model for the honeycomb iridates beyond the Kitaev limit, *Phys. Rev. Lett.* **112**, 077204 (2014).
- [25] S. M. Winter, Y. Li, H. O. Jeschke, and R. Valentí, Challenges in design of Kitaev materials: Magnetic interactions from competing energy scales, *Phys. Rev. B* **93**, 214431 (2016).
- [26] S. Ducatman, I. Rousochatzakis, and N. B. Perkins, Magnetic structure and excitation spectrum of the hyper-honeycomb Kitaev magnet $\beta\text{-Li}_2\text{IrO}_3$, *Phys. Rev. B* **97**, 125125 (2018).
- [27] I. Rousochatzakis and N. B. Perkins, Magnetic field induced evolution of intertwined orders in the kitaev magnet $\beta\text{-Li}_2\text{IrO}_3$, *Phys. Rev. B* **97**, 174423 (2018).
- [28] M. J. O'Malley, P. M. Woodward, and H. Verweij, Production and isolation of ph sensing materials by carbonate melt oxidation of iridium and platinum, *Journal of Materials Chemistry* **22**, 7782 (2012).
- [29] S. Bette, T. Takayama, K. Kitagawa, R. Takano, H. Takagi, and R. E. Dinnebier, Solution of the heavily stacking faulted crystal structure of the honeycomb iridate $\text{H}_3\text{LiIr}_2\text{O}_6$, *Dalton Trans.* **46**, 15216 (2017).
- [30] K. Kitagawa, T. Takayama, Y. Matsumoto, A. Kato, R. Takano, Y. Kishimoto, S. Bette, R. Dinnebier, G. Jackeli, and H. Takagi, A spin-orbital-entangled quantum liquid on a honeycomb lattice, *Nature* **554**, 341 (2018).
- [31] Y. Li, S. M. Winter, and R. Valentí, Role of hydrogen in the spin-orbital-entangled quantum liquid candidate $\text{H}_3\text{LiIr}_2\text{O}_6$, *Phys. Rev. Lett.* **121**, 247202 (2018).
- [32] R. Yadav, R. Ray, M. S. Eldeeb, S. Nishimoto, L. Hozoi, and J. van den Brink, Strong effect of hydrogen order on magnetic Kitaev interactions in $\text{H}_3\text{LiIr}_2\text{O}_6$, *Phys. Rev. Lett.* **121**, 197203 (2018).
- [33] J. Knolle, R. Moessner, and N. B. Perkins, Bond-disordered spin liquid and the honeycomb iridate $\text{H}_3\text{LiIr}_2\text{O}_6$: Abundant low-energy density of states from random majorana hopping, *Phys. Rev. Lett.* **122**, 047202 (2019).

- (2019).
- [34] W.-H. Kao, J. Knolle, G. B. Halász, R. Moessner, and N. B. Perkins, Vacancy-induced low-energy density of states in the Kitaev spin liquid, *Phys. Rev. X* **11**, 011034 (2021).
- [35] F. Bahrami, W. Lafargue-Dit-Hauret, O. I. Lebedev, R. Movshovich, H.-Y. Yang, D. Broido, X. Rocquefelte, and F. Tafti, Thermodynamic evidence of proximity to a kitaev spin liquid in $\text{Ag}_3\text{LiIr}_2\text{O}_6$, *Phys. Rev. Lett.* **123**, 237203 (2019).
- [36] F. Bahrami, E. M. Kenney, C. Wang, A. Berlie, O. I. Lebedev, M. J. Graf, and F. Tafti, Effect of structural disorder on the kitaev magnet $\text{Ag}_3\text{LiIr}_2\text{O}_6$, *Phys. Rev. B* **103**, 094427 (2021).
- [37] J. Wang, W. Yuan, T. Imai, P. M. Singer, F. Bahrami, and F. Tafti, NMR investigation on the honeycomb iridate $\text{Ag}_3\text{LiIr}_2\text{O}_6$, *Phys. Rev. B* **103**, 214405 (2021).
- [38] A. de la Torre, B. Zager, F. Bahrami, M. DiScala, J. R. Chamorro, M. H. Upton, G. Fabbri, D. Haskel, D. Casa, T. M. McQueen, F. Tafti, and K. W. Plumb, Enhanced hybridization in the electronic ground state of the intercalated honeycomb iridate $\text{Ag}_3\text{LiIr}_2\text{O}_6$, *Phys. Rev. B* **104**, L100416 (2021).
- [39] I. I. Mazin, H. O. Jeschke, K. Foyevtsova, R. Valentí, and D. I. Khomskii, Na_2IrO_3 as a molecular orbital crystal, *Phys. Rev. Lett.* **109**, 197201 (2012).
- [40] K. Foyevtsova, H. O. Jeschke, I. I. Mazin, D. I. Khomskii, and R. Valentí, Ab initio analysis of the tight-binding parameters and magnetic interactions in Na_2IrO_3 , *Phys. Rev. B* **88**, 035107 (2013).
- [41] Y. Li, K. Foyevtsova, H. O. Jeschke, and R. Valentí, Analysis of the optical conductivity for A_2IrO_3 (A=Na, Li) from first principles, *Phys. Rev. B* **91**, 161101 (2015).
- [42] P. Blaha, K. Schwarz, G. K. H. Madsen, D. Kvasnicka, and J. Luitz, WIEN2k, An Augmented Plane Wave Plus Local Orbitals Program for Calculating Crystal Properties (Karlheinz Schwarz, Techn. Universität Wien, Austria) (2001).
- [43] T. Biesner, S. Biswas, W. Li, Y. Saito, A. Pustogow, M. Altmeyer, A. U. B. Wolter, B. Büchner, M. Roslova, T. Doert, S. M. Winter, R. Valentí, and M. Dressel, Detuning the honeycomb of RuCl_3 : Pressure-dependent optical studies reveal broken symmetry, *Phys. Rev. B* **97**, 220401 (2018).
- [44] G. Kresse and J. Furthmüller, Efficiency of ab-initio total energy calculations for metals and semiconductors using a plane-wave basis set, *Comput. Mater. Sci.* **6**, 15 (1996).
- [45] J. Hafner, *Ab-initio* simulations of materials using vasp: Density-functional theory and beyond, *J. Comput. Chem.* **29**, 2044 (2008).
- [46] S. L. Dudarev, G. A. Botton, S. Y. Savrasov, C. J. Humphreys, and A. P. Sutton, Electron-energy-loss spectra and the structural stability of nickel oxide: An LSDA+U study, *Phys. Rev. B* **57**, 1505 (1998).
- [47] Y. Li, S. M. Winter, H. O. Jeschke, and R. Valentí, Electronic excitations in $\gamma\text{-Li}_2\text{IrO}_3$, *Phys. Rev. B* **95**, 045129 (2017).
- [48] Y. Yamaji, Y. Nomura, M. Kurita, R. Arita, and M. Imada, First-principles study of the honeycomb-lattice iridates Na_2IrO_3 in the presence of strong spin-orbit interaction and electron correlations, *Phys. Rev. Lett.* **113**, 107201 (2014).
- [49] B. H. Kim, G. Khaliullin, and B. I. Min, Electronic excitations in the edge-shared relativistic mott insulator:

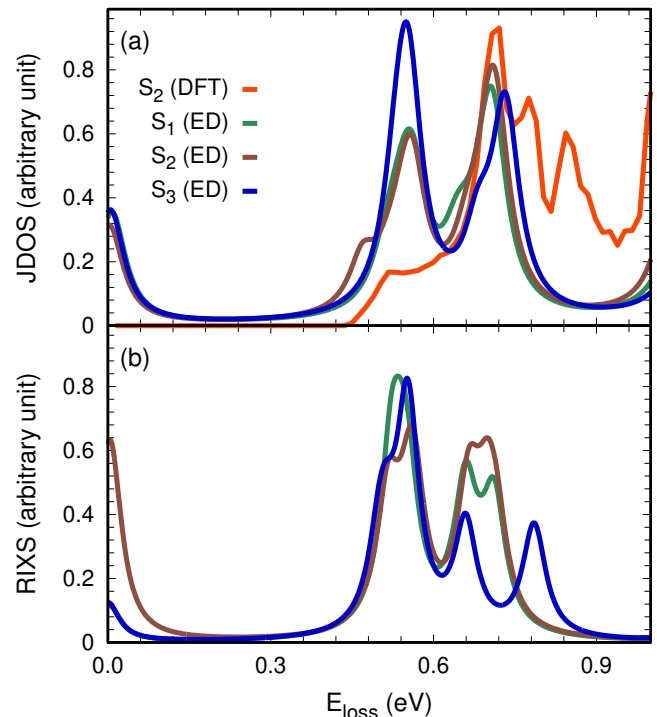


FIG. 9. (a) JDOS for S_2 obtained from DFT [S_2 (DFT)] and from two-site ED [S_2 (ED)] in comparison to the ED results for S_1 and S_3 . (b) RIXS results for S_1 - S_3 structures.

- Na_2IrO_3 , *Phys. Rev. B* **89**, 081109 (2014).
- [50] Y. Wang, G. Fabbri, M. Dean, and G. Kotliar, Edrixs: An open source toolkit for simulating spectra of resonant inelastic x-ray scattering, *Computer Physics Communications* **243**, 151 (2019).
- [51] Y. Li, S. M. Winter, D. A. S. Kaib, K. Riedl, and R. Valentí, Modified curie-weiss law for j_{eff} magnets, *Phys. Rev. B* **103**, L220408 (2021).
- [52] A. Revelli, M. M. Sala, G. Monaco, P. Becker, L. Bohatý, M. Hermanns, T. C. Koethe, T. Fröhlich, P. Warzanowski, T. Lorenz, S. V. Streltsov, P. H. M. van Loosdrecht, D. I. Khomskii, J. van den Brink, and M. Grüninger, Resonant inelastic x-ray incarnation of young's double-slit experiment, *Sci Adv.* **5**, 1 eaav4020 (2019).

Appendix A: JDOS and RIXS results for the three structures within DFT and ED

In Fig. 9 (a) we show the JDOS calculated (i) with WIEN2k within GGA+SO+U and the stripy magnetic order for the S_2 structure and (ii) via exact diagonalization for the two-site cluster (Z-bond) for the structures S_1 , S_2 , and S_3 . The corresponding RIXS spectra is shown in Fig. 9 (b). The DFT versus ED comparison for JDOS shows that DFT cannot fully capture the effects originating from correlations beyond GGA+SO+U, which are expected to be relevant when analyzing elec-

tronic excitations. The DOS and RIXS for the S_1 , S_2 , and S_3 structures indicate that the peak C and D are

robust for the three structures but E only appears in the structure S_3 .