

**The electron phonon coupling constant and fundamental BCS ratios in the LaH₁₀
doped with magnetic rare earth element**

Evgueni F. Talantsev^{1,2,*,**}

¹M.N. Mikheev Institute of Metal Physics, Ural Branch, Russian Academy of Sciences,
18, S. Kovalevskoy St., Ekaterinburg, 620108, Russia

²NANOTECH Centre, Ural Federal University, 19 Mira St., Ekaterinburg, 620002,
Russia

*corresponding author

**corresponding author's E-mail: evgney.talantsev@imp.uran.ru

Abstract

Stoichiometric near room temperature superconductors (NRTS) (for instance, H₃S and LaH₁₀) exhibit so high ground state upper critical field, $B_{c2}(0) > 100$ T, that the magnetic phase diagram in these materials cannot be measured in non-destructive experiments. However, recently, Semenok *et al* (2022 *arXiv2203.06500*) proposed the idea to explore full magnetic phase diagram in NRTS samples in which the superconducting order parameter is suppressed by the magnetic element doping. If the element is uniformly distributed in the material, then the theory of the electron-phonon mediated superconductivity predicts the suppression of the order parameter in three-dimensional *s*-wave superconductor. Semenok *et al* (*arXiv2203.06500*) experimentally proved this idea for LaH₁₀ by the substituting lanthanum in this NRTS material with magnetic rare earth neodymium. In the result, the transition temperature in La_{1-x}Nd_xH₁₀ ($x = 0.09$) was suppressed down to $T_c \sim 120$ K, and the upper critical field decreases down to $B_{c2}(T=41 \text{ K})=55$ T. Based on this, a significant part of full magnetic phase diagram can be measured. Here we analyzed reported by Semenok *et al* (*arXiv2203.06500*) magnetoresistance data for La_{1-x}Nd_xH₁₀ ($x=0.09$) compressed at $P=180$ GPa and deduced: (a) Debye temperature, $T_\theta = 1156 \pm 6$ K, (b) the electron-phonon coupling constant, $\lambda_{e-ph} = 1.65 \pm 0.01$; (c) the ground state superconducting energy gap,

$\Delta(0) = 20.2 \pm 1.3 \text{ meV}$; (d) the gap-to-transition temperature ratio, $\frac{2\Delta(0)}{k_B T_c} = 4.0 \pm 0.2$; and

(e) the relative jump in specific heat at transition temperature, $\frac{\Delta C}{C} = 1.68 \pm 0.15$. The

deduced values indicate that $\text{La}_{1-x}\text{Nd}_x\text{H}_{10}$ ($x = 0.09$; $P = 180 \text{ GPa}$) is moderately strong coupled s -wave superconductor.

The electron phonon coupling constant and fundamental BCS ratios in the LaH₁₀ doped with magnetic rare earth element

I. Introduction

The discovery a superconducting state with transition temperature above 200 K in highly compressed H₃S by Drozdov *et al* [1] with consequent discovery of the high-temperature superconductivity in superhydrides of thorium [2], and near room temperature superconductivity (NRTS) in superhydrides of lanthanum [2,3], yttrium [4-6] and lanthanum-yttrium [7] represent the most fascinating scientific explorations in the field of superconductivity since the discovery high-temperature superconductivity in cuprates [8].

While in a majority of theoretical works (comprehensive review has been published recently [9]) the electron-phonon mechanism is considered to be primary pairing mechanism in the NRTS superhydrides, alternative approaches on the nature of charge carrier interaction and pairing in NRTS are also under the development [10-12]. One of the most solid experimental facts that supports the electron-phonon pairing mechanism in superhydrides is the prominent isotope effect in respect to the transition temperature, T_c [1,3,13]. However, the effect of the hydrogen-deuterium exchange on other fundamental parameters of NRTS superhydrides, for instance, on the lower and the upper critical fields, as well as on Bardeen-Cooper-Schrieffer (BCS) ratios (i.e., $\frac{2\Delta(0)}{k_B T_c}$ where $\Delta(0)$ is ground state of the superconducting energy gap, k_B is the Boltzmann constant), remains to be explored.

Another important question which needs to be answered is the superconducting gap symmetry in NRTS hydrides. From the author's best knowledge, there is general agreement [9] that the superconducting energy gap in superhydrides exhibits *s*-wave symmetry. However, the first experimental evidence which confirms *s*-wave gap symmetry was only recently reported by Semenov *et al* [14]. This research group proposed to verify the *s*-wave gap symmetry in NRTS by employing one of the conclusions of Abrikosov-Gor'kov [15],

Anderson [16], and Openov [17,18] theories of dirty superconductors. This conclusion is that uniformly distributed (on the atomic level) impurities exhibited magnetic moment should suppress the superconducting order parameter in s -wave superconductors, but this kind of impurities should not affect the superconducting order parameter in d -wave superconductors. However, non-magnetic impurities should cause the suppression of in d -wave superconductors, but this kind of doping should not affect the s -wave superconducting state.

Thus, to reaffirm/disprove s -wave symmetry gap in LaH₁₀, Semenok *et al* [14] performed gradual doping of LaH₁₀ by magnetic rare earth element, neodymium. The hydrogen/rare earth elements stoichiometry was kept 1/10 in all samples, (La_{1-x}Nd_x)H₁₀. Thus, there was an expectation that Nd will replace La in the crystal lattice, rather than Nd will form the secondary phases. This expectation was confirmed by XRD studies for La_{1-x}Nd_xH₁₀ ($x = 0.08, 0.09, 0.20, 0.25, \text{ and } 0.50$) samples [14].

Semenok *et al* [14] reported on gradual T_c suppression on the increase in the Nd concentration. One of the interesting consequences associated with this T_c suppression is that the upper critical field, $B_{c2}(T)$, is also decreasing. This makes it possible to measure $B_{c2}(T)$ for La_{1-x}Nd_xH₁₀ within a much wide reduced temperature range, $\frac{T}{T_c}$, in comparison with the range available for undoped stoichiometric NRTS materials H₃S [19] and LaH₁₀ [20], which exhibits the ground state upper critical field well above the value which can be measurable in non-destructive experiments.

Due to the upper critical field, $B_{c2}(T)$, is one of two fundamental fields in type-II superconductors, measured $B_{c2}(T)$ datasets can be used to extract several fundamental parameters of the superconductor [21,22], for instance:

1. ground state energy gap, $\Delta(0)$;
2. relative jump in electronic specific heat at T_c , $\Delta C/C$;
3. ground state coherence length, $\xi(0)$;

4. gap-to-transition temperature ratio, $\frac{2\Delta(0)}{k_B T_c}$ (where k_B is the Boltzmann constant).
5. Fermi temperature, T_F

There are two other fundamental parameters of the electron-phonon mediated superconductors:

6. Debye temperature, T_θ ;
7. the electron-phonon coupling constant, λ_{e-ph} .

Debye temperature can be deduced from the fit of experimentally measured temperature dependent resistance, $R(T)$, to the Bloch-Grüneisen (BG) equation [23,24]:

$$R(T) = R_0 + A \left(\frac{T}{T_\theta}\right)^5 \int_0^{\frac{T_\theta}{T}} \frac{x^5}{(e^x - 1)(1 - e^{-x})} dx \quad (1)$$

where R_0 and A are free fitting parameters. From the deduced T_θ and measured T_c , the electron-phonon coupling constant, λ_{e-ph} , can be calculated as unique root of advanced McMillan equation [25,26]:

$$T_c = \left(\frac{1}{1.45}\right) \times T_\theta \times e^{-\left(\frac{1.04(1+\lambda_{e-ph})}{\lambda_{e-ph} - \mu^*(1+0.62\lambda_{e-ph})}\right)} \times f_1 \times f_2^* \quad (2)$$

where

$$f_1 = \left(1 + \left(\frac{\lambda_{e-ph}}{2.46(1+3.8\mu^*)}\right)^{3/2}\right)^{1/3} \quad (3)$$

$$f_2^* = 1 + (0.0241 - 0.0735 \times \mu^*) \times \lambda_{e-ph}^2 \quad (4)$$

where μ^* is the Coulomb pseudopotential parameter, which can be assumed to be $\mu^* = 0.13$ for all NRST materials.

In this work, we deduced $\Delta(0)$, $\Delta C/C$, $\xi(0)$, $\frac{2\Delta(0)}{k_B T_c}$, T_F , T_θ , and λ_{e-ph} for $\text{La}_{1-x}\text{Nd}_x\text{H}_{10}$ ($x = 0.09$) compressed at pressure $P = 180 \text{ GPa}$ by analysing experimental $R(T)$ and $B_{c2}(T)$ datasets reported by Semenok *et al* [14,27]. Deduced parameters showed that $\text{La}_{1-x}\text{Nd}_x\text{H}_{10}$ ($x = 0.09$; $P = 180 \text{ GPa}$) is moderately strong coupled superconductor.

The fit of $R(T)$ dataset to Eq. 1 is shown in Fig. 1. This $R(T)$ dataset reported in Figure 2,a in the Ref. 14 and raw data file is freely available online by Semenok *et al* [27]. Deduced parameters are: $R_0 = 0.729(5)$, $A = 5.42 \pm 0.06$, and $T_\theta = 1156 \pm 6$ K. By utilizing general requirement [26], that T_c should be defined at the lowest as possible $\frac{R(T)}{R_{norm}(T)}$ ratio, and considering that the same criterion should be used to define $B_{c2}(T)$ dataset from $R(T, B)$ curves (reported in Figs. 2(b,c) [14]), the ratio of $\frac{R(T)}{R_{norm}(T)} = 0.08$ was used. In the result, T_c for $R(T)$ in Fig. 1 was defined as $T_{c,0.08} = 122$ K.

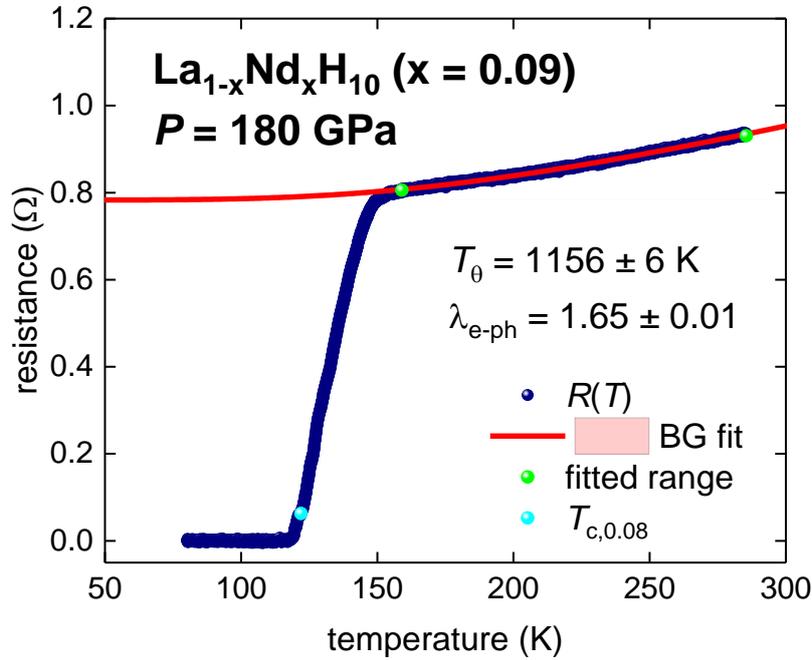


Figure 1. $R(T)$ data for highly compressed $\text{La}_{1-x}\text{Nd}_x\text{H}_{10}$ ($x = 0.09$; $P = 180$ GPa) and data fit to Eq. 1 (raw data is freely available online by Semenok *et al* [14,27]). Green balls indicate the bounds for which $R(T)$ data was used for the fit to Eq. 1. Deduced $T_\theta = 1156 \pm 6$ K, $T_{c,0.08} = 122$ K, $\lambda_{e-ph} = 1.65 \pm 0.01$, fit quality is 0.9977. 95% confidence bands are shown by pink shadow areas.

The root of Eqs. 2-4 for given T_θ , T_c , and $\mu^* = 0.13$ is $\lambda_{e-ph} = 1.65 \pm 0.01$. This deduced value is in a good agreement with λ_{e-ph} values calculated by first-principles calculations by Semenok *et al* [27] in their Table S5.

By utilizing the same criterion of $\frac{R(T)}{R_{norm}(T)} = 0.08$, the $B_{c2}(T)$ dataset was derived from $R(T, B)$ curves showed in Figs. 2(b,c) of Ref. 14. In Fig. 2 the $B_{c2}(T)$ dataset is fitted to the equation for temperature dependent upper critical field for s -wave superconductors [21,22]:

$$B_{c2}(T) = \frac{\phi_0}{2\pi \cdot \xi^2(0)} \left(\frac{1.77 - 0.43 \left(\frac{T}{T_c}\right)^2 + 0.07 \left(\frac{T}{T_c}\right)^4}{1.77} \right)^2 \times \left[1 - \frac{1}{2k_B T} \int_0^\infty \frac{d\varepsilon}{\cosh^2 \left(\frac{\sqrt{\varepsilon^2 + \Delta^2(T)}}{2k_B T} \right)} \right] \quad (5)$$

where the amplitude of temperature dependent superconducting gap, $\Delta(T)$, is given by [28,29]:

$$\Delta(T) = \Delta(0) \times \tanh \left[\frac{\pi k_B T_c}{\Delta(0)} \sqrt{\eta \frac{\Delta C}{C} \left(\frac{T_c}{T} - 1 \right)} \right] \quad (6)$$

where $\eta = 2/3$ for s -wave superconductors.

The fit converged with a high quality (with goodness of fit $R = 0.9976$) (Fig. 2).

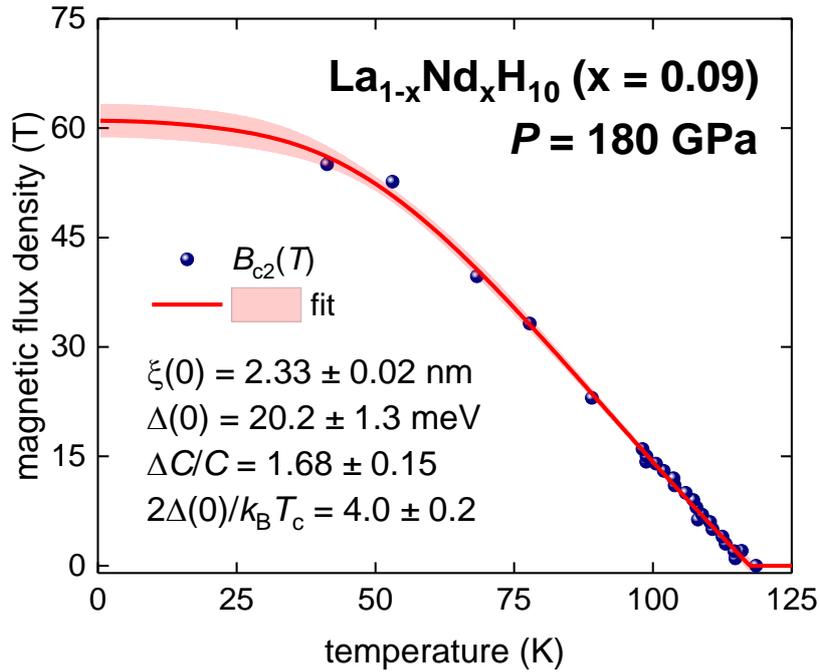


Figure 2. Superconducting upper critical field data, $B_{c2}(T)$, and data fit to Eq. 5 for highly compressed $\text{La}_{1-x}\text{Nd}_x\text{H}_{10}$ ($x = 0.09$; $P = 180$ GPa). Raw $R(T, B)$ dataset is freely available online by Semenok *et al* [14,27]. Deduced parameters are: $\xi(0) = 2.33 \pm 0.02$ nm, $T_c = 117.5 \pm 0.6$ K, $\Delta(0) = 20.2 \pm 1.3$ meV, $\Delta C/C = 1.68 \pm 0.15$, $\frac{2\Delta(0)}{k_B T_c} = 4.0 \pm 0.2$. Fit quality is 0.9976. 95% confidence bands are shown by pink shadow areas.

Deduced parameters are: $\xi(0) = 2.33 \pm 0.02 \text{ nm}$, $\Delta(0) = 20.2 \pm 1.3 \text{ meV}$, $\frac{2\Delta(0)}{k_B T_c} = 4.0 \pm 0.2$, $\frac{\Delta C}{C} = 1.68 \pm 0.15$. Considering that the weak coupling limits of the BCS theory [28-30] are: $\frac{2\Delta(0)}{k_B T_c} = 3.53$ and $\frac{\Delta C}{C} = 1.43$, and the upper limits for low- T_c electron-phonon mediated superconductors are: $\frac{2\Delta(0)}{k_B T_c} = 5.2$ (for $\text{Pb}_{0.50}\text{Bi}_{0.50}$ alloy [31]) and $\frac{\Delta C}{C} = 3.0$ (for $\text{Pb}_{0.70}\text{Bi}_{0.30}$ alloy [31]), one can conclude that $\text{La}_{1-x}\text{Nd}_x\text{H}_{10}$ ($x = 0.09$; $P = 180 \text{ GPa}$) is moderately strong coupled superconductor.

Final characterization of the superconducting properties of the $\text{La}_{1-x}\text{Nd}_x\text{H}_{10}$ ($x = 0.09$; $P = 180 \text{ GPa}$) was to position this hydride in the empirical Uemura plot [32,33], where heavy fermions, fullerenes, cuprates, pnictides, and hydrogen-rich superconductors [34] form a narrow band exhibited the ratio of the superconducting transition temperature, T_c , to the Fermi temperature, T_F , within a range:

$$0.01 \lesssim \frac{T_c}{T_F} \lesssim 0.05, \quad (7)$$

while all low- T_c conventional superconductors have much smaller $\frac{T_c}{T_F}$ ratio:

$$\frac{T_c}{T_F} \lesssim 0.001 \quad (8)$$

The Fermi temperature can be calculated by following equation [35]:

$$T_F = \frac{\pi^2}{8 \cdot k_B} \times (1 + \lambda_{e-ph}) \times \xi^2(0) \times \left(\frac{2\Delta(0)}{\hbar}\right)^2, \quad (9)$$

where all parameters we deduced above. In the result, calculated Fermi temperature is $T_F = 4430 \pm 50 \text{ K}$ and, thus, $\frac{T_c}{T_F} = 0.027$ for this superhydride. In the result, $\text{La}_{1-x}\text{Nd}_x\text{H}_{10}$ ($x = 0.09$; $P = 180 \text{ GPa}$) falls into unconventional superconductors band in the Uemura plot (Fig. 3), and it is located in close proximity to $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ and $\text{Bi}_2\text{Sr}_2\text{Ca}_2\text{Cu}_3\text{O}_{11}$ cuprates and other NRTS counterparts.

To address a possible question that the electron-phonon mediated materials are located at the unconventional superconductors band, we should point out that superhydrides are not the only known electron-phonon mediated superconductors which are located in the unconventional superconductors band in the Uemura plot (for instance, we can mention bulk s -wave R_3C_{60} ($R = K, Rb$) superconductors).

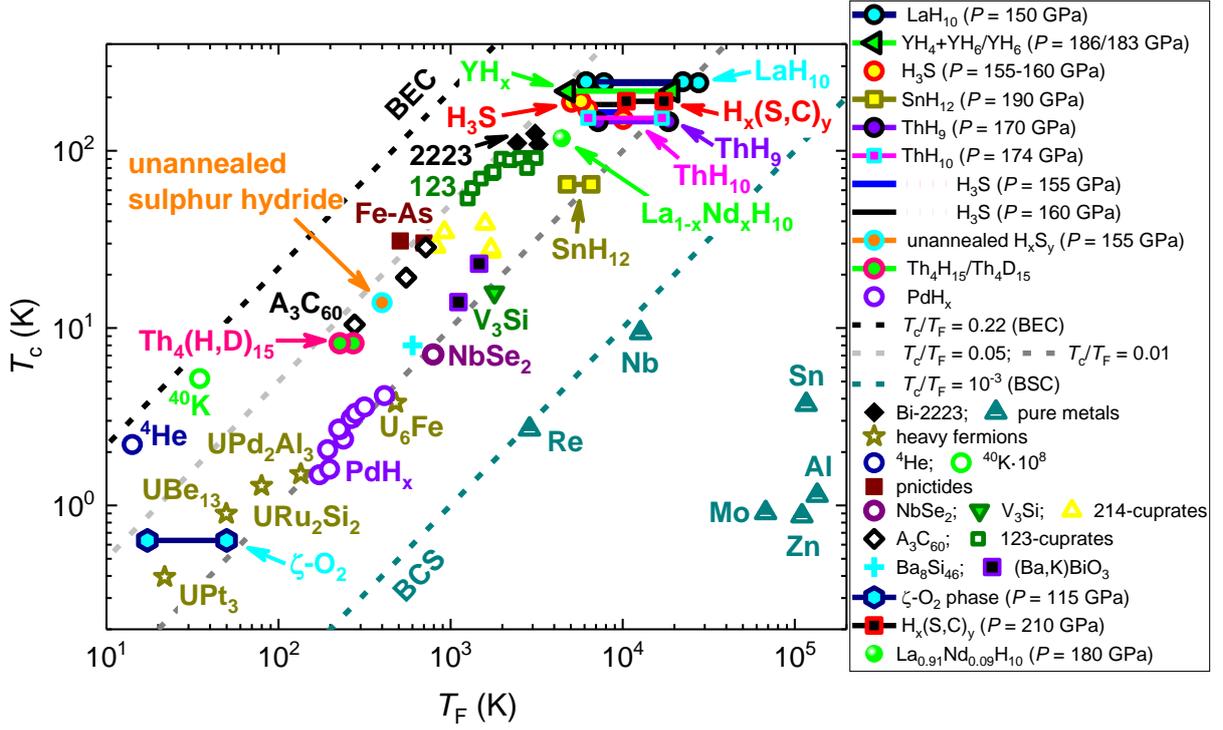


Figure 3. Uemura plot (T_c vs T_F), where the $La_{1-x}Nd_xH_{10}$ ($x = 0.09$; $P = 180$ GPa) compound is shown together with other superconducting families: metals, heavy-fermions, pnictides, cuprates, and near-room-temperature superconductors. Reference on original data can be found in Ref. 34.

From other hand, the Uemura plot is not intended to reveal the pairing mechanism, but rather indicate the geometrical ratio of the characteristic size of the Cooper pair (which is proportional to $\xi(0)$) with average spatial distance between centers of the Cooper pairs. This implies that materials with low superfluid density trend to locate closer to the Bose-Einstein condensate (BEC) line, $\frac{T_c}{T_F} = 0.22$, while materials with high volume concentration of Cooper pairs trend to be located closer to the pure metals, like aluminium for which $\frac{T_c}{T_F} \sim 10^{-5}$. This

limit also known as BCS limit. Detailed studies of the transition of one material from BEC into BCS under high pressure can be found elsewhere [36].

To summarise our findings in this work, we can mention that, while the detection of the superconductivity in elemental highly compressed hydrogen is ongoing task [37-39], the near-room temperature superconductivity has observed in several superhydrides [1-7]. Here, we analysed experimental magnetoresistance data, $R(T,B)$, for highly compressed $\text{La}_{1-x}\text{Nd}_x\text{H}_{10}$ ($x = 0.09$; $P = 180 \text{ GPa}$) superconductor in which the superconducting order parameter was suppressed by magnetic rare earth element (neodymium) impurity. Raw experimental $R(T,B)$ datasets for $\text{La}_{1-x}\text{Nd}_x\text{H}_{10}$ ($x = 0.09$; $P = 180 \text{ GPa}$) was recently reported by Semenok *et al* [14,27]. Deduced parameters, for instance, the gap-to-transition temperature ratio, $\frac{2\Delta(0)}{k_B T_c} = 4.0 \pm 0.2$, and the relative jump in specific heat at transition temperature, $\frac{\Delta C}{C} = 1.7 \pm 0.1$, indicate that $\text{La}_{1-x}\text{Nd}_x\text{H}_{10}$ ($x = 0.09$; $P = 180 \text{ GPa}$) is moderately strong coupled superconductor. This hydride exhibits the ratio of the superconducting transition temperature to the Fermi temperature of $\frac{T_c}{T_F} = 0.027$, and it falls into unconventional superconductors band in the Uemura plot.

Acknowledgement

The author thanks Dmitrii V. Semenok (Skolkovo Institute of Science and Technology) and co-workers of Refs. 14,22 for making raw experimental data is freely available prior the peer-review publication of their paper. The author thanks financial support provided by the Ministry of Science and Higher Education of Russia (theme “Pressure” No. AAAA-A18-118020190104-3).

Data availability statement

The data that support the findings of this study are available from the corresponding author upon reasonable request.

Declaration of interests

The author declares that he has no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

References

- [1] A.P. Drozdov, M. I. Eremets, I. A. Troyan, V. Ksenofontov, S. I. Shylin, *Nature* **525**, 73 (2015).
- [2] D. V. Semenov, *et al*, Superconductivity at 161 K in thorium hydride ThH₁₀: synthesis and properties *Mater. Today* **33**, 36–44 (2020)
- [3] A. P. Drozdov, *et al* Superconductivity at 250 K in lanthanum hydride under high pressures *Nature* **569**, 528-531 (2019)
- [4] M. Somayazulu, *et al* Evidence for superconductivity above 260 K in lanthanum superhydride at megabar pressures *Phys. Rev. Lett.* **122** 027001 (2019)
- [5] I. A. Troyan, *et al* Anomalous high-temperature superconductivity in YH₆ *Adv. Mater.* **33** 2006832 (2021)
- [6] P. P. Kong, *et al* Superconductivity up to 243 K in yttrium hydrides under high pressure *Nature Communications* **12**, 5075 (2021)
- [7] D. V. Semenov, *et al* Superconductivity at 253 K in lanthanum–yttrium ternary hydrides *Materials Today* **48**, 18-28 (2021)
- [8] J. G. Bednorz and K. A. Müller, Possible highT_c superconductivity in the Ba–La–Cu–O system *Zeitschrift für Physik B Condensed Matter* **64**, 189-193 (1986)
- [9] L. Boeri, *et al*. The 2021 room-temperature superconductivity roadmap *Journal of Physics: Condensed Matter* **34**, 183002 (2021)
- [10] D. R. Harshman, A.T. Fiory, The superconducting transition temperatures of C–S–H based on inter-sublattice S–H₄-tetrahedron electronic interactions *Journal of Applied Physics* **131**, 015105 (2022)
- [11] M. V. Mazziotti, *et al.*, Resonant multi-gap superconductivity at room temperature near a Lifshitz topological transition in sulfur hydrides *Journal of Applied Physics* **130**, 173904 (2021)
- [12] D. K. Sunko, High-temperature superconductors as ionic metals *Journal of Superconductivity and Novel Magnetism* **33**, 27-33 (2020)
- [13] V. S. Minkov, V. B. Prakapenka, E. Greenberg, M. I. Eremets A boosted critical temperature of 166 K in superconducting D₃S synthesized from elemental sulfur and hydrogen *Angewandte Chemie International Edition* **59**, 18970-18974 (2020)
- [14] D. V. Semenov, *et al.*, Effect of paramagnetic impurities on superconductivity in polyhydrides: *s*-wave order parameter in Nd-doped LaH₁₀ *arXiv:2203.06500* (2022)

- [15] L. P. Gor'kov, in Superconductivity: Conventional and unconventional superconductors (Eds. K. H. Bennemann & John B. Ketterson) (Springer Berlin Heidelberg, 2008) pp. 201-224
- [16] P. W. Anderson, Theory of dirty superconductors. *J. Phys. Chem. Solids* **11**, 26-30 (1959)
- [17] L. A. Openov, Critical temperature of an anisotropic superconductor containing both nonmagnetic and magnetic impurities *Phys Rev B* **58**, 9468-9478 (1998)
- [18] L. A. Openov, Effect of nonmagnetic and magnetic impurities on the specific heat jump in anisotropic superconductors *Phys Rev B* **69**, 224516 (2004)
- [19] S. Mozaffari, *et al.* Superconducting phase diagram of H₃S under high magnetic fields *Nat. Commun.* **10** 2522 (2019)
- [20] D. Sun, *et al.* High-temperature superconductivity on the verge of a structural instability in lanthanum superhydride *Nat. Commun.* **12** 6863 (2021)
- [21] E. F. Talantsev, Classifying superconductivity in compressed H₃S *Modern Physics Letters B* **33**, 1950195 (2019)
- [22] E. F. Talantsev, R. C. Mataira, W. P. Crump, Classifying superconductivity in Moiré graphene superlattices *Scientific Reports* **10**, 212 (2020)
- [23] F. Bloch, Zum elektrischen Widerstandsgesetz bei tiefen Temperaturen *Z. Phys.* **59**, 208-214 (1930)
- [24] E. Grüneisen, Die abhängigkeit des elektrischen widerstandes reiner metalle von der temperatur. *Ann. Phys.* **408**, 530–540 (1933)
- [25] W. L. McMillan, Transition temperature of strong-coupled superconductors *Phys. Rev.* **167** 331-344 (1968)
- [26] E. F. Talantsev, Advanced McMillan's equation and its application for the analysis of highly-compressed superconductors *Superconductor Science and Technology* **33** 094009 (2020)
- [27] D. V. Semenok, *et al.* SUPPORTING INFORMATION: Effect of paramagnetic impurities on superconductivity in polyhydrides: *s*-wave order parameter in Nd-doped LaH₁₀ *ResearchGate* doi: 10.13140/RG.2.2.23819.98088
- [28] F. Gross, *et al.* Anomalous temperature dependence of the magnetic field penetration depth in superconducting UBe₁₃. *Z. Phys. B* **64**, 175-188 (1986)
- [29] F. Gross-Alltag, B. S. Chandrasekhar, D. Einzel, P. J. Hirschfeld and K. Andres, London field penetration in heavy fermion superconductors *Z. Phys. B* **82**, 243-255 (1991)
- [30] J. Bardeen, L. N. Cooper, J. R. Schrieffer, Theory of superconductivity *Phys. Rev.* **108**, 1175-1204 (1957).
- [31] J. P. Carbotte, Properties of boson-exchange superconductors *Rev. Mod. Phys.* **62**, 1027-1157 (1990)
- [32] Y. J. Uemura, Bose-Einstein to BCS crossover picture for high-*T_c* cuprates *Physica C* **282-287**, 194-197 (1997)
- [33] Y. J. Uemura, Dynamic superconductivity responses in photoexcited optical conductivity and Nernst effect *Phys. Rev. Materials* **3**, 104801 (2019)
- [34] E. F. Talantsev, Comparison of highly-compressed C2/*m*-SnH₁₂ superhydride with conventional superconductors *Journal of Physics: Condensed Matter* **33**, 285601 (2021)
- [35] E. F. Talantsev, An approach to identifying unconventional superconductivity in highly-compressed superconductors *Superconductor Science and Technology* **33**, 124001 (2020)
- [36] Y. Suzuki, K. Wakamatsu, J. Ibuka, H. Oike, T. Fujii, K. Miyagawa, H. Taniguchi, and K. Kanoda, Mott-driven BEC-BCS crossover in a doped spin liquid candidate κ-(BEDT-TTF)₄Hg_{2.89}Br₈ *Phys. Rev. X* **12**, 011016 (2022)
- [37] A. Goncharov, Phase diagram of hydrogen at extreme pressures and temperatures; updated through 2019 (Review article), *Low Temperature Physics* **46**, 97 (2020)

[38] E. Gregoryanz, C. Ji, P. Dalladay-Simpson, B. Li, R. T. Howie, and H.-K. Mao, Everything you always wanted to know about metallic hydrogen but were afraid to ask. *Matter and Radiation at Extremes* **5**, 038101 (2020)

[39] M. I. Eremets, P. P. Kong, A. P. Drozdov, Metallization of hydrogen *arXiv:2109.11104* (2021)