

Three-dimensional Microstructural Image Synthesis from 2D Backscattered Electron Image of Cement Paste

Xin Zhao^a, Lin Wang^{b,c,*}, Qinfei Li^{a,d}, Heng Chen^{a,d}, Shuangrong Liu^b, Pengkun Hou^d, Xu Wu^a, Jianfeng Yuan^b, Haozhong Gao^{b,c}, Bo Yang^{c,b}

^aShandong Provincial Key Laboratory of Preparation and Measurement of Building Materials, University of Jinan, Jinan 250022, China.

^bShandong Provincial Key Laboratory of Network Based Intelligent Computing, University of Jinan, Jinan 250022, China.

^cQuan Cheng Laboratory, Jinan 250100, China

^dSchool of Materials Science and Engineering, University of Jinan, Jinan 250022, China.

Abstract

This paper proposes a deep learning-based method for generating 3D microstructures from a single two-dimensional (2D) image, capable of producing high-quality, realistic 3D images at low cost. In the method, a framework (CEM3DMG) is designed to synthesize 3D images by learning microstructural information from a 2D backscattered electron (BSE) image. Experimental results show that CEM3DMG can generate realistic 3D images of arbitrary size with a resolution of $0.47 \mu\text{m}$ per pixel. Visual observation confirms that the generated 3D images exhibit similar microstructural features to the 2D images, including pores and particles morphology. Furthermore, quantitative analysis reveals that these 3D microstructures closely match the real 2D microstructure in terms of gray level histogram, phase proportions, and pore size distribution.

Keywords: Hardened Cement Paste, 3D Microstructure Generation, Deep Learning,

1. Introduction

Cement, a fundamental component of construction materials, is ubiquitously utilized in the building industry. The cement hydration process accompanies microstructure development, directly impacting the performance of cement [1, 2]. Therefore, investigating the microstructure development during the hydration process has long been a popular topic in cement materials research [3, 4]. Over the past few decades, computational models have emerged as a convenient, efficient, and cost-effective means to simulate cement microstructure development and investigate hydration behavior [5, 6]. Within computational models of microstructure development, establishing an initial cement microstructure (typically in three-dimensional (3D) space) is a crucial step, and realistic microstructures are essential for ensuring precision in simulations.

In the study of cement microstructure development, numerous models have been proposed, which can be broadly classified into vector [5, 7, 8] and discretization [6, 9] models. To streamline computations, these models often make the assumption that cement particles are spherical (see Figure 1 (c)), leading to simulations of microstructures in states that may not accurately reflect reality. Bullard et al. recognized this issue and investigated the influence of particle shape on portland cement hydration [10]. The

study indicated that the impact of real shapes on properties of cement is significant. Despite efforts to enhance the realism of microstructures, such as introducing polyhedron and irregular shapes [11, 12], these approaches have encountered challenges in closely approximating real 3D microstructures.

To obtain real 3D microstructures, direct imaging through scanning instruments is one intuitive approach. Microtomography (Micro-CT), as a non-destructive 3D imaging device, has gained popularity in cement-based materials research [13, 14]. However, Micro-CT is limited by imaging quality and struggles to provide high-resolution images for large-size samples [15]. Scanning Electron Microscopy (SEM) can offer high-quality 2D microstructural images, but making it challenging to obtain 3D images with rich spatial information. Although Focused Ion Beam Scanning Electron Microscopy (FIB-SEM) [16] has improved SEM to enable 3D imaging [17, 18], it is limited by scanning range and sample destruction. Additionally, acquiring microstructures through scanning cement samples for each simulation is costly and impractical. Therefore, a low-cost method to generate high-quality, realistic 3D microstructures is urgently needed.

Compared to 3D microstructural images, high-quality 2D images can be obtained at a lower cost. From the perspective of image analysis, microstructural images of cement generally exhibit isotropy. It is feasible to reveal certain 3D structural characteristics by processing the 2D

*Corresponding author: Lin Wang (wangplanet@gmail.com)

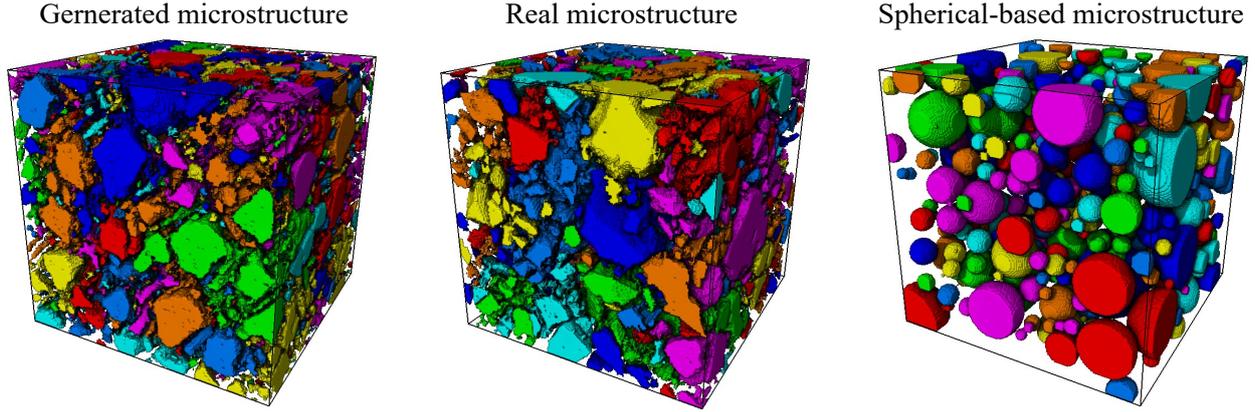


Figure 1: Various 3D microstructures.

image [19]. With the increased efficiency and accessibility of computers capturing scientists’ attention, generating 3D microstructural images from real 2D exemplars via computational methods has emerged as a feasible alternative.

At the early stage, 3D microstructural image generation efforts focused on generating specific phases, such as pores and particles, from the 2D image of cement [19, 20, 21]. As a representative example, Bentz introduced a technique [19] that utilizes stereology adjustments and the autocorrelation function to generate 3D cement microstructural images from 2D SEM images. In these methods, segmentation of the initial 2D image into distinct phases is a prerequisite to streamline the intricate microstructure. While the segmentation simplifies the computational process and reduces the difficulty of image generation, this segmentation operation transforms microstructural images into binary or multivalued formats. This transformation compresses color and detail, leading to the loss of microstructural information. Thus, such methods make it hard to convert 2D microstructures into 3D counterparts realistically.

To faithfully generate the 3D microstructural image of cement, it is essential to synthesize 3D images from the real 2D microstructural images. Guided by the principles of solid texture synthesis [22, 23], Tang et al. employed the Markov Random Field to generate 3D microstructural images from a given 2D Micro-CT image [24]. Zhang et al. introduced an innovative approach for 3D generation [25], integrating random process theory and stochastic reconstruction techniques. However, these methodologies are limited by their model complexity and learning capabilities, restricting their capability to capture complex data patterns in the intricate microstructure of cement. This limitation substantially obstructs accurately capturing detailed microstructural information in cement images.

Recently, deep learning has undergone significant advancements [26, 27], demonstrating potent learning capabilities essential for capturing complex information. Although deep learning offers a promising avenue in material science, its application in this field, particularly in generating 3D microstructural images of cement, has not

been fully explored. In 2022, the authors first proposed a deep learning-based framework for cement image synthesis [28], utilizing the VGG-based solid texture synthesis method [29, 30] to generate 3D cement microstructures. Subsequently, Saseendran et al. [31] adopted a similar solution to explore the 3D microstructure generation of space-returned cement samples. These methods rely on a pre-trained VGG-19 [30] with fixed features a priori as a tool for feature statistics. However, cement microstructures are complex and diverse, and the pre-trained VGG-19 finds it hard to represent the diverse microstructure information [32], hindering the realistic generation of cement microstructural images.

In this paper, a novel deep learning-based method is proposed to generate realistic 3D microstructure of cement, from a single 2D image, in a low-cost manner. This method includes three steps: the specimen preparation, the 2D image acquisition, and the 3D microstructural image generation. In the microstructure generation process, a **3D microstructural image Generation** framework of **CEMent** (CEM3DMG) is proposed. Given the complexity and multi-scale nature of the cement microstructures, CEM3DMG adopts the concept of Generative Adversarial Networks (GANs) [32, 33] to learn the arbitrary data distribution (microstructure information) within cement images. Moreover, a multi-scale learning strategy allows CEM3DMG to capture microstructure information at various scales. Additionally, we adopt a block-wise synthesis strategy, enabling CEM3DMG to “block-by-block” generate arbitrary-size 3D microstructural images. In the experiments, the generated 3D images and the real 2D BSE images are qualitatively analyzed through visual observation. Subsequently, the generated 3D images are quantitatively compared with the real 2D BSE images in terms of gray level histogram, various phases proportions, and pore size distribution (PSD). Finally, the proposed method’s effectiveness is further verified by quantitatively and qualitatively analyzing the similarity between real 3D Micro-CT images and generated 3D images.

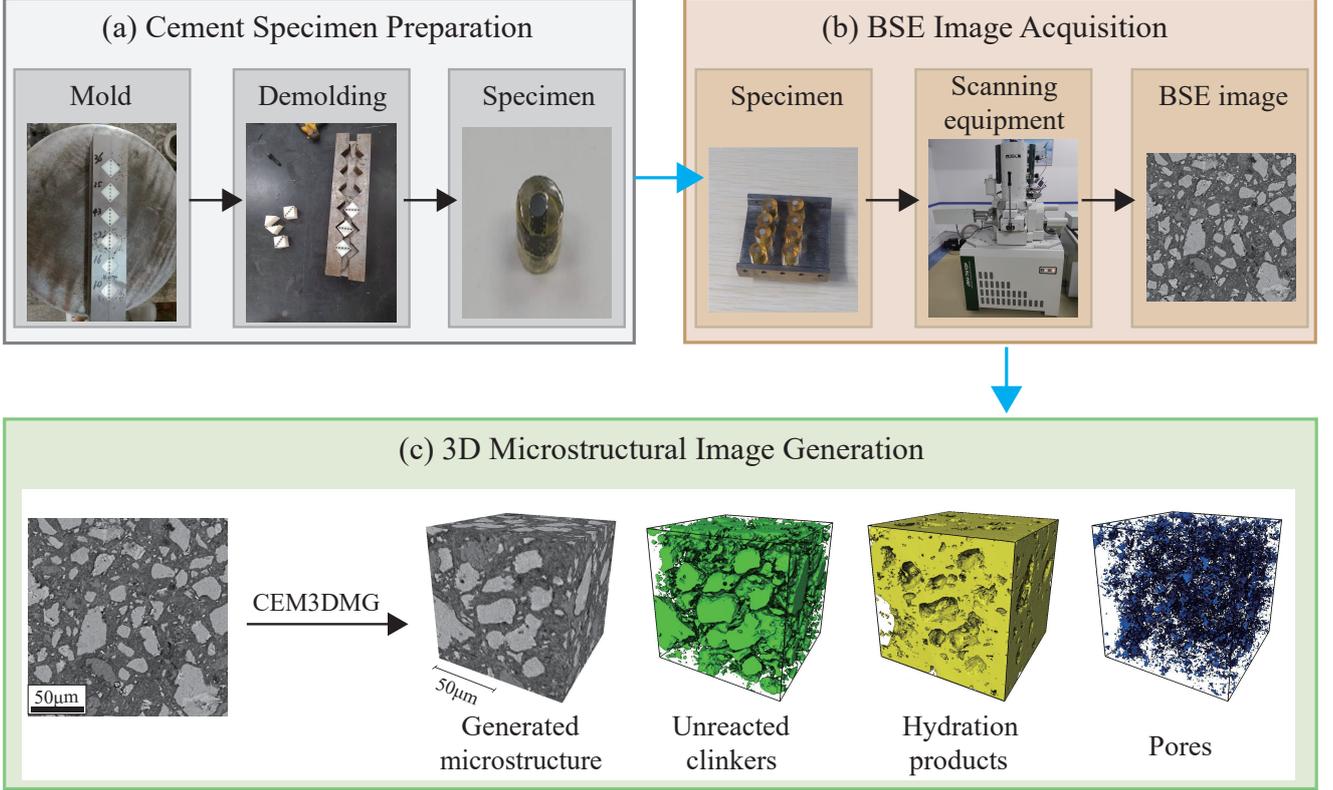


Figure 2: 3D microstructural image acquisition process. (a) the processed of hardened cement paste specimen preparation, (b) the processed of specimen is scanned to obtain BSE images, (c) the 3D microstructural images are generated from a given single 2D BSE image.

Table 1: Chemical compositions of cement sample.

Type	Sample A	Sample B
C3S (%)	66.96	64.92
C2S (%)	8.7	8.15
C3A (%)	6.21	7.23
C4AF (%)	11.3	9.61
Age (day)	18	11
W/C	0.3	0.3

2. Experimental Method

In this section, Figure 2 illustrates the experimental methodology, comprising three distinct stages. Initially, specimens of hardened cement paste are prepared (section 2.1). Subsequently, SEM is utilized to acquire high-quality 2D BSE images of the hardened cement paste (section 2.2). Finally, realistic 3D microstructural images are generated using the proposed 3D generation framework (section 2.3). Additionally, the experimental configuration (section 2.4) and the analysis metrics (section 2.5) are described.

2.1. Specimen Preparation

As shown in Table 1, Portland cement specimens of various types are prepared (Sample A, Sample B). The preparation process for these cement specimens is depicted in

Figure 2(a). Initially, the prepared cement paste is introduced into a mold, where it is subjected to stirring and vibration to eliminate bubbles. Subsequently, this cylindrical specimen undergoes curing in 95–100% RH (relative humidity) and ~ 23 °C, until the specified age is attained. Following this, the specimens are demolded from the molds and immersed in anhydrous ethanol, effectively halting the hydration process by removing moisture. Finally, the specimens are dried and subsequently impregnated with epoxy resin, solidifying the internal microstructure.

2.2. BSE Image Acquisition

The process for obtaining BSE images is shown in Figure 2(b). Initially, the specimens are ground and polished using the automatic grinding and polishing machine with metallographic sandpaper, cloth, and polishing powder. Following grinding and polishing, the specimen surface is cleaned using an ultrasonic cleaner, exhibiting a mirror-like reflective surface. This surface facilitates the acquisition of high-quality BSE images. Secondly, as the cement specimen is non-conductive, we apply a Pt coating to the specimen’s surface to prevent image distortion caused by charge accumulation.

The processed specimen is then mounted on the sample table and placed into the scanning equipment. The BSE images are acquired using the field emission scanning electron microscope (FESEM).

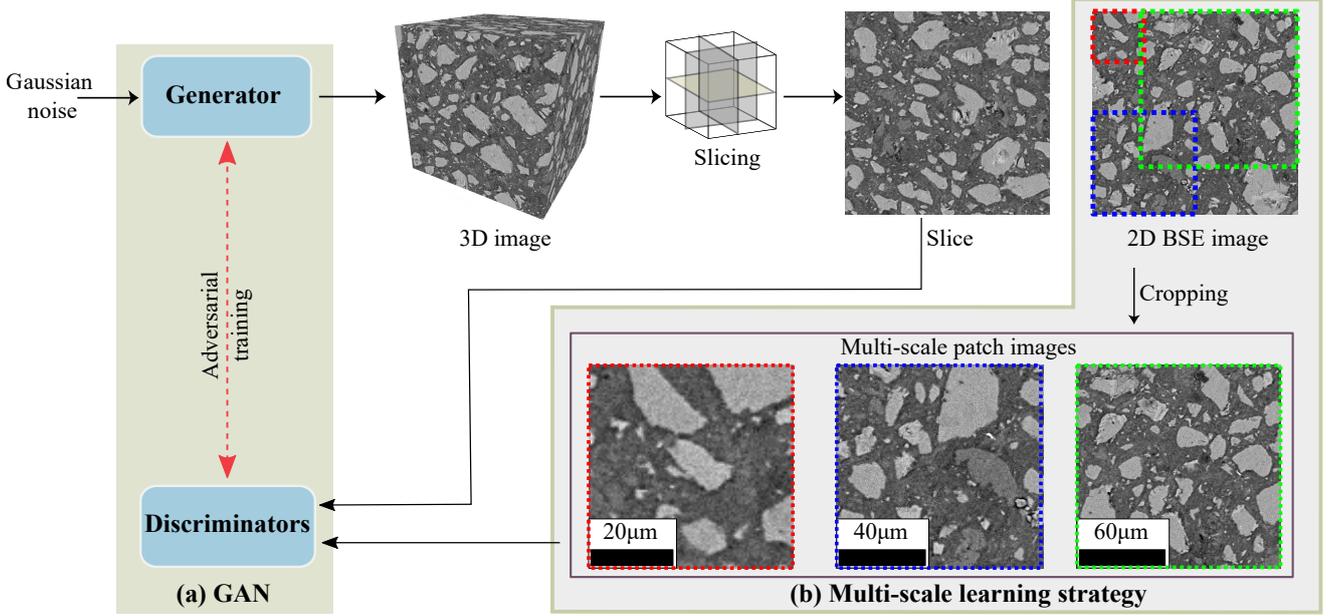


Figure 3: 3D microstructural image generation framework (CEM3DMG). (a) the generator and discriminators in GAN-based adversarial training. (b) the multi-scale learning strategy.

2.3. 3D Microstructural Image Generation

As shown in Figure 2(c), the 3D microstructural image generation phase begins with a single 2D BSE image. CEM3DMG extends the microstructural characteristics of the BSE image into 3D space, generating realistic 3D microstructural images. Finally, the 3D microstructures of the cement are displayed in various visualization forms.

2.3.1. CEM3DMG

CEM3DMG employs the concept of GANs, which have been successfully applied in solid texture synthesis [32, 34]. Moreover, CEM3DMG can generate realistic 3D microstructural images from 2D cement images, owing to the capability of GANs to learn any data distribution. Figure 3 shows the proposed CEM3DMG, which consists of the 3D microstructural image generator G and the discriminator D . The generator's role is to create 3D microstructural images, while the discriminator's role is to assess the proximity of the generated 3D images to the data distribution of 2D real images and compel the generator to generate realistic 3D images. When the discriminator cannot distinguish between real and generated images, the generator is successfully developed and can be utilized to generate realistic images.

A slicing strategy is incorporated into the CEM3DMG to facilitate the cross-dimensional correlation between 2D and 3D images. During adversarial training, when randomly selected slices of the 3D image closely resemble the provided 2D image, the resulting 3D image approximates the data distribution of the given 2D image, thereby generating realistic 3D images.

Within the CEM3DMG, Gaussian noise z is initially input into the generator G to obtain a 3D image I .

$$I = G(z), \quad (1)$$

Subsequently, 2D slices are randomly sampled from the generated 3D image in an orthogonal manner. The discriminators assess these slices against the patches cropped from the 2D BSE image. Through training (see section 2.3.4), the generator G is gradually optimized to generate realistic 3D images.

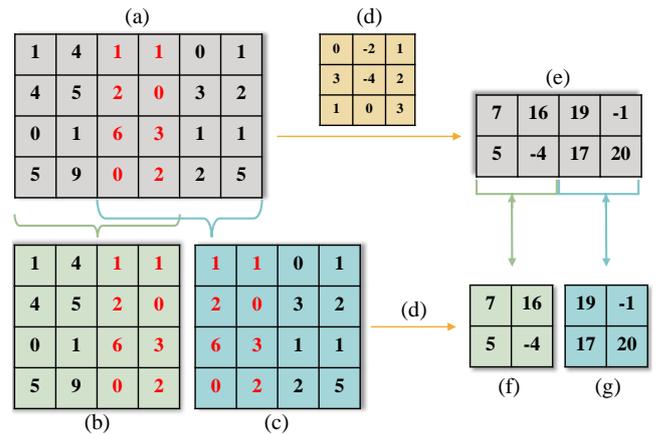


Figure 4: Conceptual diagram of the block-wise synthesis strategy. (a) Input data, (b) and (c) show (a) divided into two smaller input data blocks. The red numbers indicate the overlapping parts between (b) and (c). (d) represents the convolutional operator in the generator (no padding). After processing by the same convolutional operator (d), (a), (b), and (c) produce the output (e), (f), and (g), respectively.

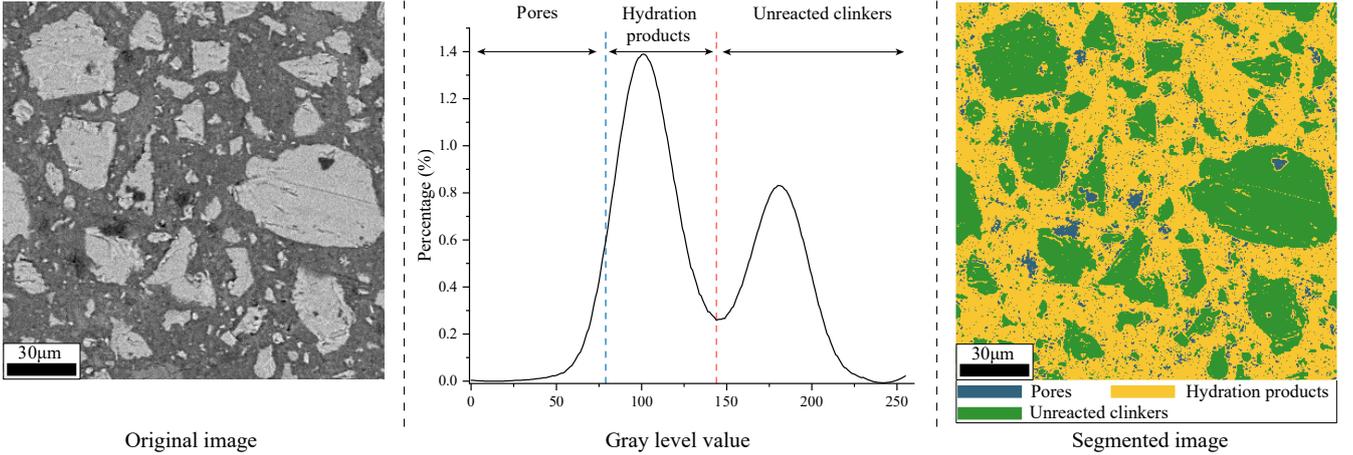


Figure 5: Phases segmentation. Pores, hydration products and unreacted clinkers are segmented based on histogram.

2.3.2. Multi-scale Learning Strategy

Given the multi-scale nature of the cement microstructures, the multi-scale learning strategy is employed in CEM3DMG to enable the generator model to learn the data distribution of BSE images at different scales. Figure 3(b) illustrates the process of obtaining multi-scale images from a single 2D BSE image. Initially, patches with various sizes are randomly cropped from the scanned BSE image, with different sizes ranging from several tens to over a hundred micrometers. Subsequently, they are standardized to the same resolution, resulting in images at different scales, where the physical dimensions represented by each pixel vary accordingly. Finally, the generator and discriminator can learn microstructural information from BSE images at different scales, generating realistic 3D microstructural images. In addition, multiple discriminators are employed to learn microstructural information at different scales to alleviate the challenge of a single discriminator learning images at various scales.

2.3.3. Block-wise Synthesis Strategy

Modeling the 3D microstructure of cement paste usually requires large-size volumetric data [35]. Due to limited computational capacity (such as memory or GPU memory size), generating large-size 3D images all at once is challenging. In CEM3DMG, the generator is designed with a fully convolutional architecture with no padding, allowing the size of the input and output of the generator to be unrestricted by the network structure. Therefore, we employ a block-wise synthesis strategy, where smaller 3D images are generated first and then pieced together. Figure 4 illustrates the concept of the block-wise synthesis strategy, where large-size outputs are obtained by piecing together small blocks of data. Specifically, during computation, each Gaussian noise input into generator G overlaps with the neighboring part noise, ensuring that large-size images are generated while maintaining structure continuity.

2.3.4. Adversarial Training

As a technique characterized by stable adversarial training, the idea of WGAN-GP [36] is adopted in CEM3DMG. Specifically, the generator is optimized based on two components: the discriminator loss and perceptual loss [29, 34, 37]. The discriminator loss promotes the generator’s learning of the real image data distribution, while the perceptual loss assists the generator in learning the texture style of the image. Together, these components facilitate the generation of realistic microstructural images. During generator training, the loss function is minimized using the equation:

$$\mathcal{L}_G = -\alpha \mathbb{E}[D(x)] + \beta Per(x, u), \quad (2)$$

where x is a 2D slice taken at random from the 3D image generated by G , Per refers to the perceptual distance loss between x and cropped image u , α and β are constants. Meanwhile, discriminator D is optimized by minimizing its loss function:

$$\mathcal{L}_D = \mathbb{E}[D(x)] - \mathbb{E}[D(u)] + \lambda \mathbb{E}[(\|\nabla_r D(r)\|_2 - 1)^2], \quad (3)$$

where λ is a constant, and r is a data point uniformly sampled between u and x .

2.4. Experimental Configuration

PyTorch, a framework for building deep learning models, is utilized to implement the proposed CEM3DMG. CEM3DMG operates on a system outfitted with an Intel Xeon Silver 4214R Processor and is further bolstered by the capabilities of an NVIDIA A100 Tensor Core GPU. This setup ensures efficient processing and robust computational support for advanced modeling tasks. In addition, the data and images are analyzed using the software Origin, ImageJ, and Avizo.

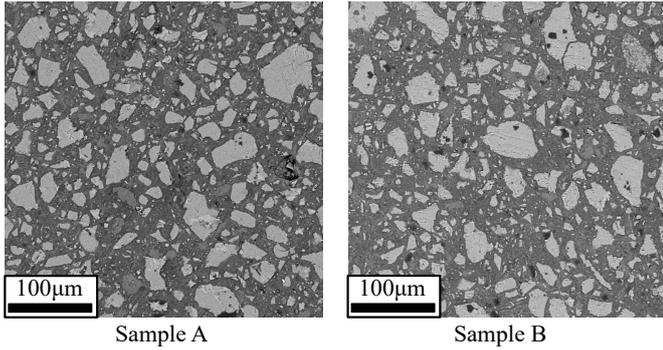


Figure 6: Acquired 2D BSE images.

2.5. Analytical Evaluation Criteria

The differences between real BSE images and the generated 3D microstructural images are compared to evaluate and analyze the proposed CEM3DMG. During our experimental assessments, various criteria, including gray level histogram, various phases proportions, and pore size distribution, are utilized to analyze the proposed method. Specifically, less variance between these metrics indicates greater similarity in images.

2.5.1. Gray Level Histogram

In the microstructure analysis of cement, the gray level histogram is recognized as a classic method [38, 39]. This histogram illustrates the frequency distribution of each gray level within the microstructure image. The overall trend of the histogram, including the positions of peaks and valleys, provides essential insights into the properties of cement. Therefore, the proximity of the gray level distribution is a crucial factor in assessing the similarity of images. In our experiments, due to differences in image sizes, we standardize the histogram by calculating the proportion of each gray level.

2.5.2. Various Phases Proportions

In experiments, the proportions of pores, hydration products and unreacted clinkers are calculated in microstructural images. These phases proportions, indicative of the material's density and hydration degree, are key characteristics in the properties of cement [40, 41]. Before calculating various phases proportions, image processing is required, specifically phases segmentation. As shown in Figure 5, various phases are segmented based on the gray level histogram. Specifically, the overflow method is adopted to find the threshold for segmenting pores [42], and the approach proposed by Scrivener et al. [43] is employed to determine the threshold between hydration products and unreacted clinkers.

2.5.3. Pore Size Distribution

Pores significantly influence several key properties of cement, including its compressive strength and transport properties [44, 45]. Pore size distribution of cement refers

to the size range and distribution of pores in cement samples, reflecting its microstructure characteristics [46, 47]. In measuring pore diameters, given that segmented pores typically exhibit irregular shapes, each pore is approximated as either a perfect circle or a perfect sphere in calculations [48, 49]. For pores in 2D microstructures, the equivalent circular diameter (ECD) of each pore is calculated by equating the area of a perfect circle to the pixel area (A_p) of a pore,

$$ECD = \sqrt[2]{4 \times \frac{A_p}{\pi}}, \quad (4)$$

In the case of 3D microstructures, the ECD of each pore is calculated by equating the volume of a perfect sphere to the pixel volume of a pore (V_p),

$$ECD = \sqrt[3]{6 \times \frac{V_p}{\pi}}, \quad (5)$$

3. Results and Discussion

3.1. Acquired 2D BSE Images

Figure 6 presents 2D BSE images acquired during the experiments, originating from hardened cement pastes. In the experiment, each sample is scanned by the SEM with a magnification of 200X, obtaining images with a resolution of 800×800 pixels² and $0.47 \mu\text{m}$ per pixel. As shown in Figure 6, the BSE images of these samples illustrate the microstructure on their surfaces.

3.2. Qualitative Analysis of 3D Microstructural Image Generation

This section primarily focuses on visually assessing the generation effectiveness of 3D microstructural images. In this experiment, CEM3DMG generates 3D microstructural images based on 2D BSE images of hardened cement pastes. In Figure 7, besides the presentation of the 3D microstructure, various phases within the microstructure are also marked with different colors, enabling a clear visualization of the internal structures of the generated 3D microstructures.

As shown in Figure 7, from a macroscopic visual perspective, it is observed that the generated 3D microstructural images visually match the given 2D BSE image. In Figure 7, the cement particles (i.e., unreacted clinkers, as indicated by the red boxes in Sample A, for example) in both the real 2D microstructure and generated microstructure particles exhibit similar morphologies, with various-sized particles reflected in the generated 3D microstructure.

In Figure 7, for example, Sample B exhibits obvious pores and is closely connected to the particles (for instance, with some pores encapsulated by cement particles, as indicated by the blue boxes). Upon closer examination,

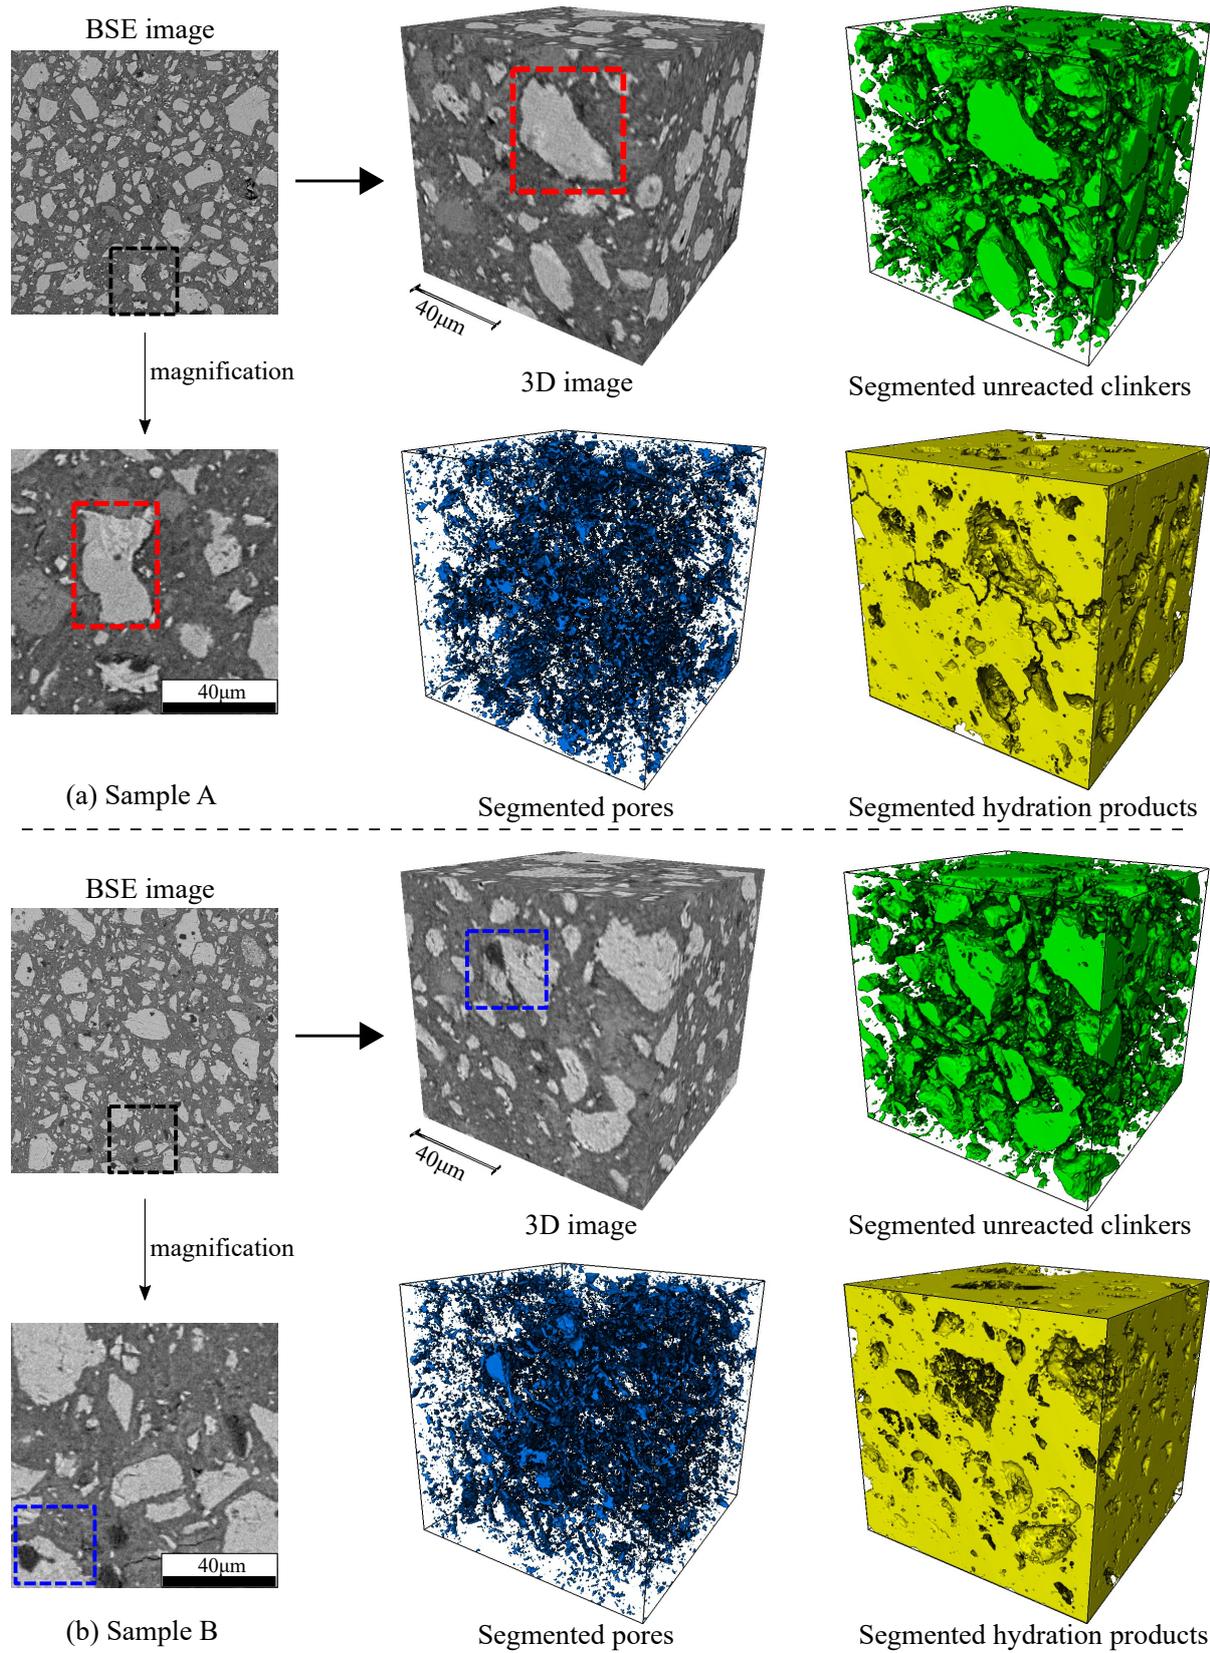


Figure 7: The generated 3D microstructural images. The left is a real BSE image, and the right are generated microstructural images. Three phases are segmented in microstructure, green denotes unreacted clinkers, blue denotes pores and yellow denotes hydration products.

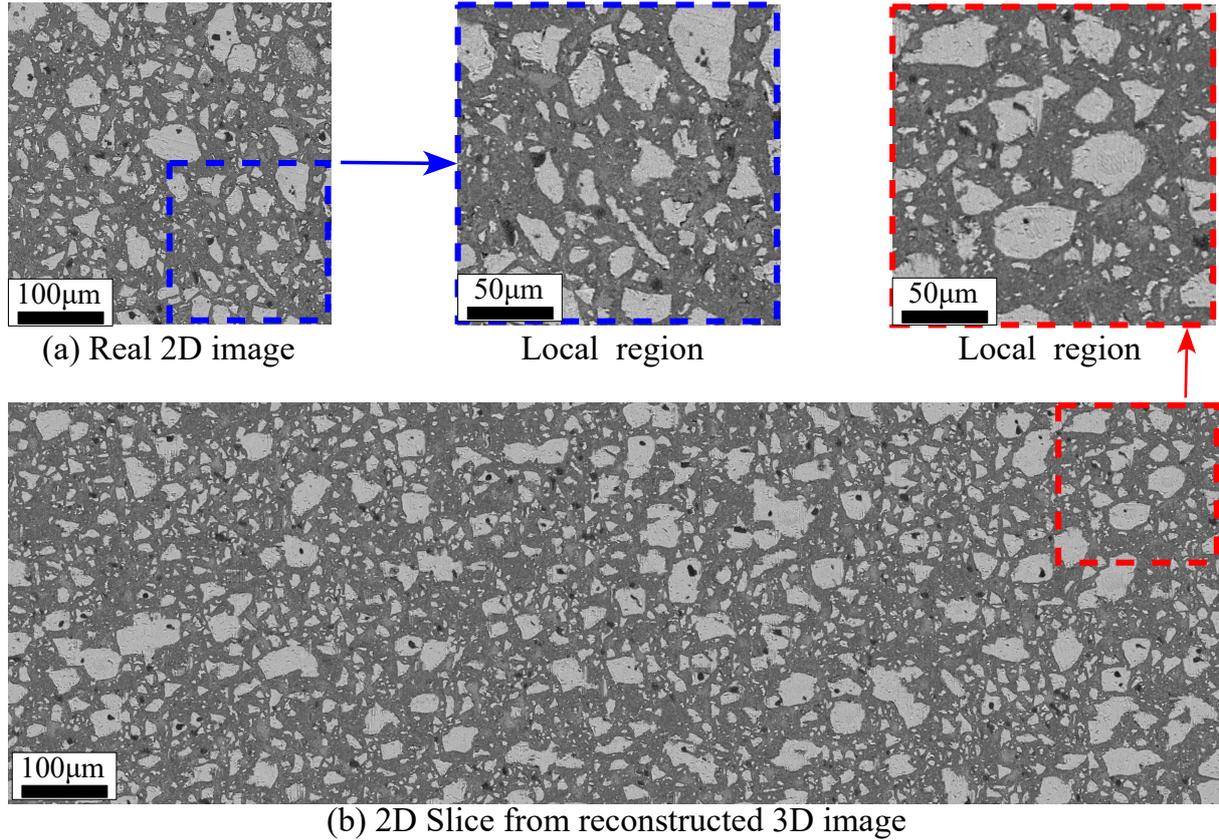


Figure 8: The generated large-size microstructural image. (a) real 2D BSE image, (b) the 2D slice from generated 3D image.

these pore characteristics are represented in generated microstructural images, as marked by the blue boxes. Observations from Figure 7 reveal that hydration products dominate the BSE images in both samples. Similarly, in the synthesized microstructure, hydration products constitute the majority and are generated around the clinker particles.

Therefore, from a visual standpoint, CEM3DMG effectively captures the microstructural information in a given 2D BSE image and generates high-quality and realistic 3D microstructures of cement.

3.3. Quantitative Analysis of 3D Microstructural Image Generation

In quantitative analysis, generated 3D microstructural images with three different sizes are evaluated: $200 \times 200 \times 200$ pixels³ (S1), $400 \times 400 \times 400$ pixels³ (S2), and $800 \times 800 \times 800$ pixels³ (S3), $0.47 \mu\text{m}$ per pixel.

3.3.1. Gray level histogram

The gray level histogram represents quantitative information about the color distribution of BSE images. Therefore, the histograms of real BSE images and generated 3D images with different sizes are first compared and analyzed in the experiment. Subsequently, the histograms between slices from 3D images and real BSE images are compared.

The first row of Figure 9 presents histograms of 2D BSE images and generated 3D images with varying sizes. Additionally, histograms between 2D slices from different orientations within the 3D image and real BSE images are depicted in the second row of Figure 9. As illustrated in Figure 9, the gray level distribution trends of the real BSE images (baseline) and the generated images are consistent. In particular, crucial information such as the positions of peak and valley in the histograms remains consistent. These details are vital for phase analysis, providing critical insights into the composition and characteristics of cement. This result indicates that CEM3DMG can learn color information from the 2D BSE image and extend it to the 3D image.

In Figure 9, while the overall trend of gray level distribution is distinct for all two samples, the trend is locally unstable (for instance, the histogram of Sample A shows a spike approximately every ten gray levels). In the experiment results, the generated 3D images smooth out these local variations, suggesting that CEM3DMG is challenging to learn thoroughly from images with the locally unstable gray level distribution. Nevertheless, these differences have minimal impact on image analysis, as the overall trend of histogram has been captured by CEM3DMG. Furthermore, eliminating these subtle discrepancies in the gray level distribution can be straightforward, for example, by using image processing techniques to smooth the

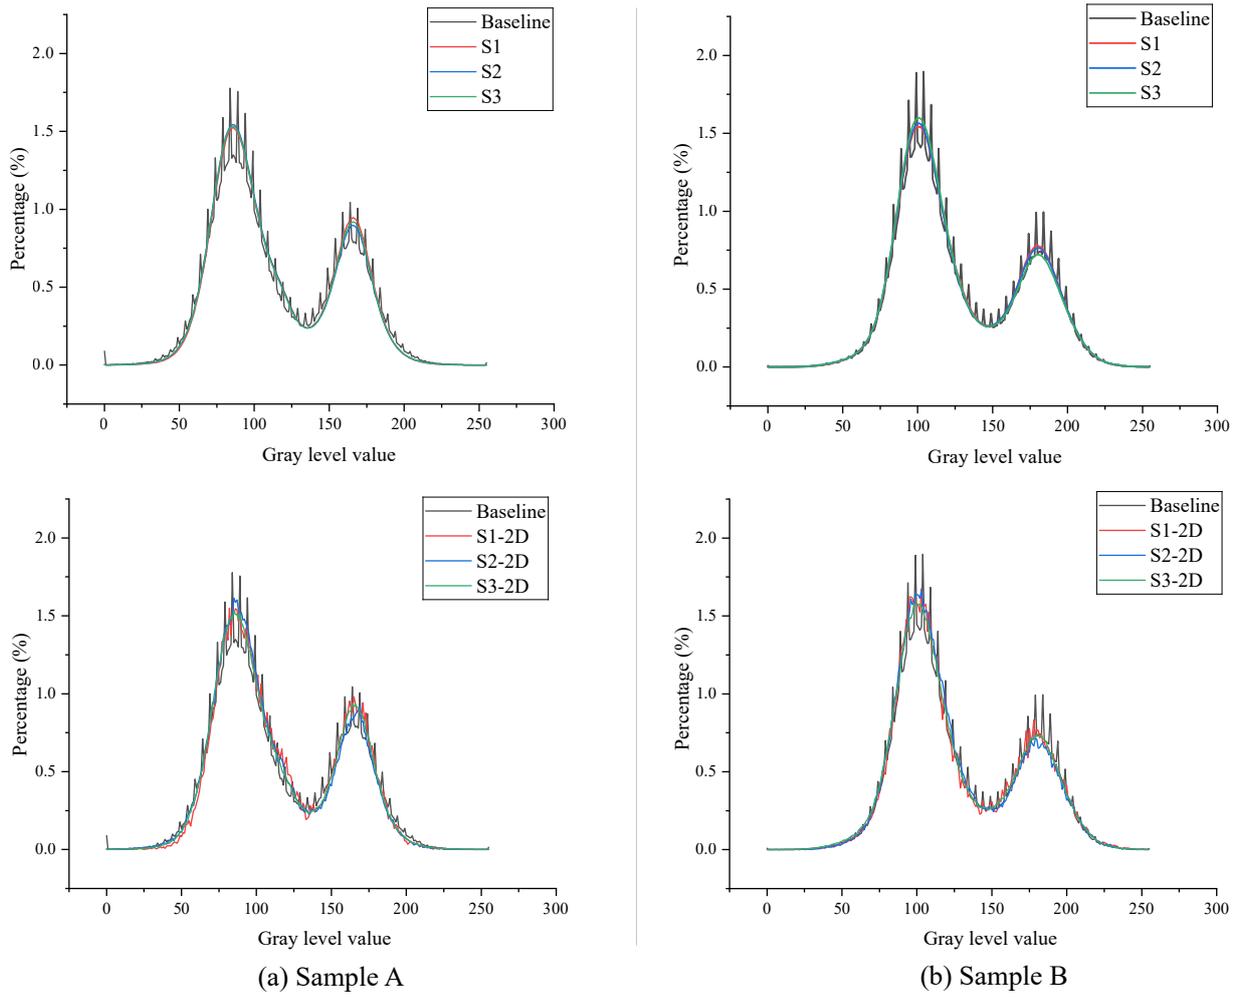


Figure 9: Gray level histograms of 2D and 3D images. The baseline represents the real 2D BSE image, while S1, S2, and S3 denote three 3D images with distinct sizes, respectively. Note that the first row displays the results of the 2D BSE image and the generated 3D image, while the second row shows the results of the 2D BSE image and the 2D slice randomly selected from the generated 3D image.

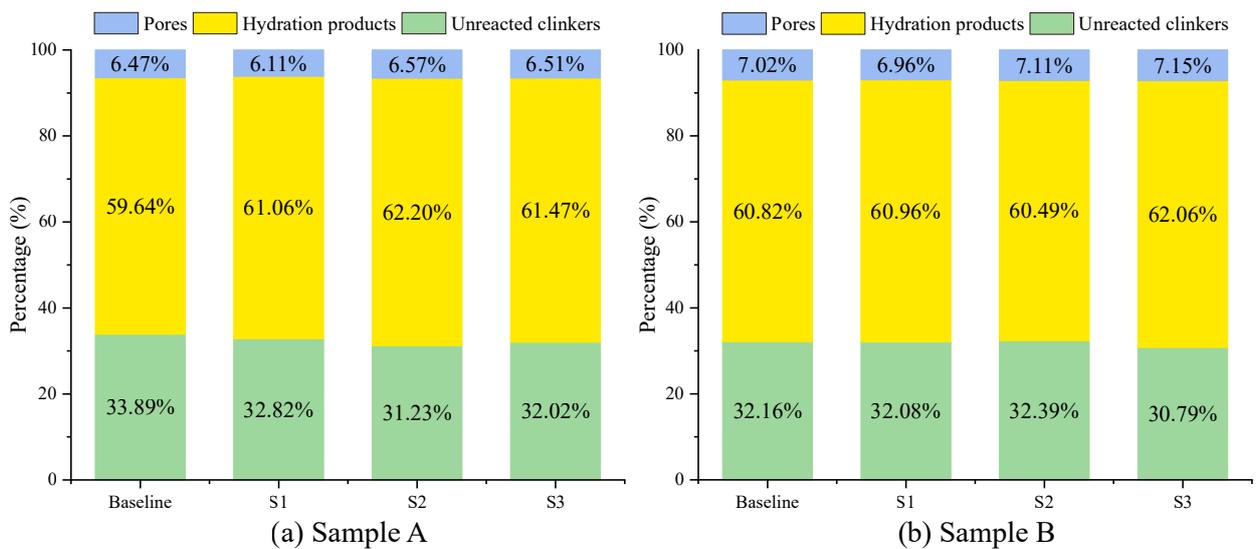


Figure 10: The various phases proportions of generated microstructures and real microstructures. The baseline represents the real 2D microstructure, while S1, S2, and S3 denote three generated 3D microstructures with distinct sizes, respectively.

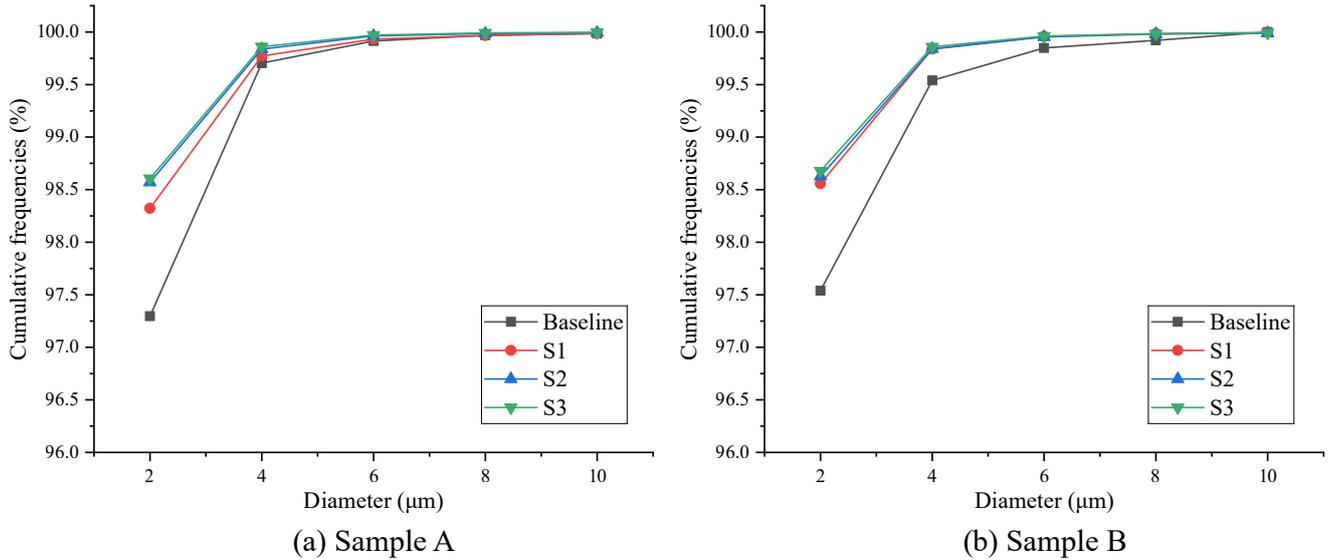


Figure 11: Pore size distribution of 2D microstructure and different-size 3D microstructures. The baseline represents the real 2D microstructure, while S1, S2, and S3 denote three generated 3D microstructures with distinct sizes, respectively.

original images or to sharpen the generated images.

In summary, CEM3DMG effectively captures the microstructure of 2D BSE images and generates corresponding 3D microstructural images. The approach’s effectiveness is demonstrated through the analysis of gray level histograms.

3.3.2. Various Phases Proportions

For cement pastes, different phases proportions are critical indicators as it directly relate to the structure and properties of the materials. In the experiment, various phases (pores, hydration products and unreacted clinkers) proportions of real 2D microstructures and generated 3D microstructures is analyzed. Figure 10 presents the phases proportions results for different microstructures. Taking the pores proportion (porosity) as an example, the porosity of the real 2D microstructure and the generated 3D microstructures for each sample is approximative, with a maximum difference (baseline and S3 of Sample B) not exceeding 0.13 %.

For hydration products, the maximum difference in Sample A is 2.56 % (S2), while in Sample B it is 1.24 % (S3). Regarding unreacted clinkers, the maximum difference in Sample A is 2.66 % (S2), and in Sample B, it is 1.37 % (S3). Hence, the proportions of hydration products and unreacted clinkers in the generated microstructures closely resemble those in the real microstructure. Furthermore, experimental results indicate that the differences between pores in the generated microstructure and those in the real microstructure are minimal, suggesting that CEM3DMG excels in learning the information related to microstructural pores.

The analysis of various phases proportions indicates that the generated 3D images align closely with the real 2D BSE images, providing further evidence that CEM3DMG can

generate realistic 3D microstructure conforming to the 2D microstructure information.

3.3.3. Pore Size Distribution

Analyzing PSD allows for an understanding of the distribution of pores of different sizes within the cement paste, further assisting researchers in comprehending the microstructural characteristics of the material. In the experiment, the PSD of 2D microstructures and 3D microstructures with various sizes is analyzed.

Figure 11 illustrates the PSD of microstructures, showing that pores with a diameter less than $2 \mu m$ dominate, indicating a high material density and aligning with the previously discussed low porosity. In the generated 3D microstructure and the real 2D microstructure, it is observed that the most significant discrepancies in pore size occur in pores with diameters less than $2 \mu m$, with the maximum difference being around 1.31 % in Sample A, 1.14 % in Sample B. As pore size increases, the distribution of pores between the 2D microstructures and 3D microstructures gradually aligns.

This observation falls within an acceptable range. The primary reason for this phenomenon is attributed to the exceedingly small size of these pores, often spanning only a few pixels. The impact of image noise on CEM3DMG’s learning of these tiny pores leads to differences between the generated 3D microstructures and real 2D microstructures in the range of tiny pores.

3.4. Large-size Microstructural Image

Large-volume microstructural images offer more abundant characterizations for cement research. CEM3DMG employs a block-wise synthesis strategy (section 2.3.3) to ensure the image generation with any size, particularly large-size 3D microstructural images. Figure 8 shows the

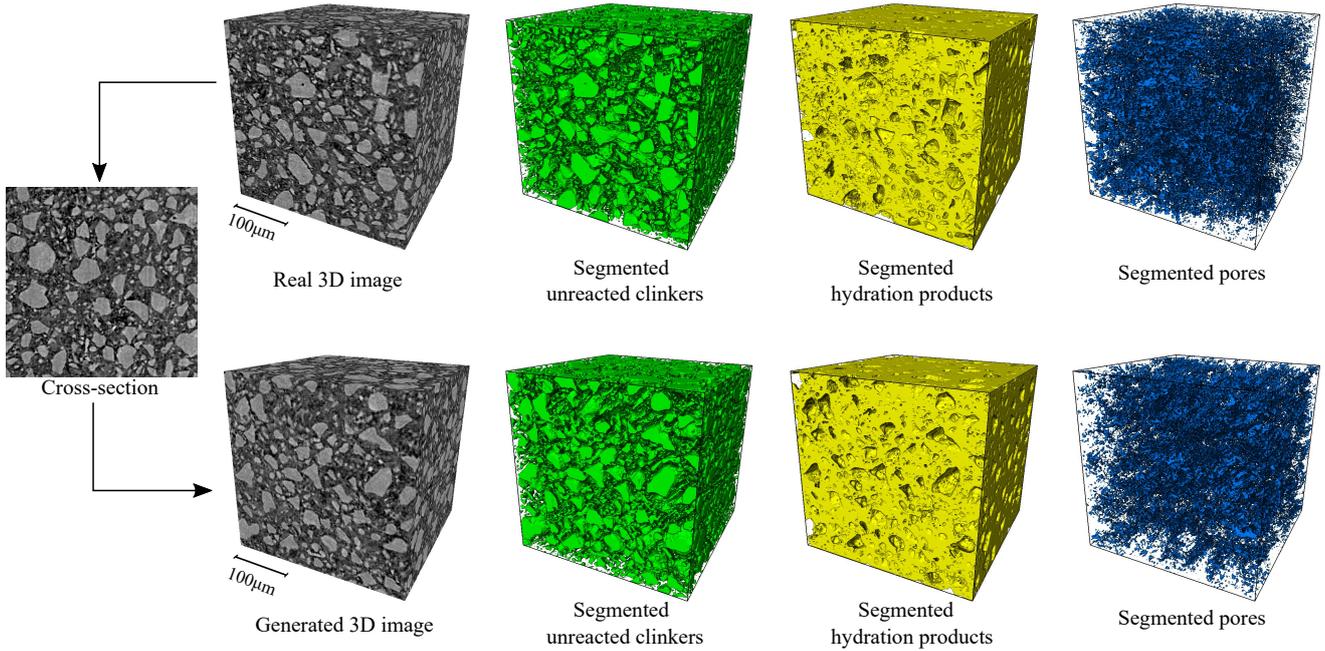


Figure 12: Comparison of real 3D images and generated 3D images. Randomly select a cross-section from a real 3D microstructural image and generate a new microstructure based on the single cross-section.

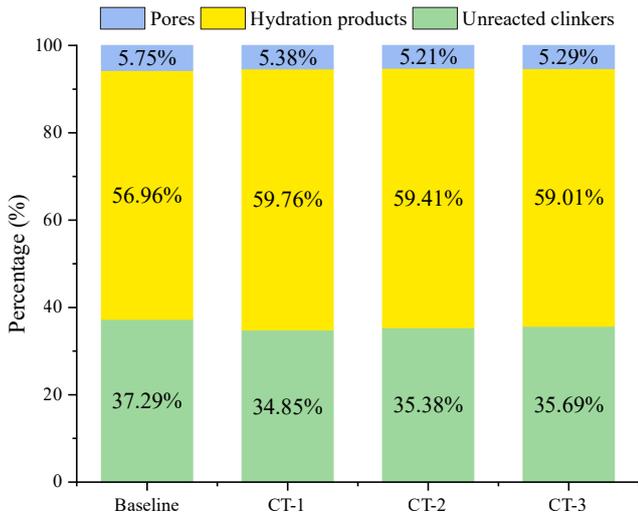


Figure 13: The various phases proportions of generated 3D microstructures and real 3D microstructure. The baseline represents the real 3D microstructure, while CT-1, CT-2, and CT-3 denote three generated 3D microstructures, respectively.

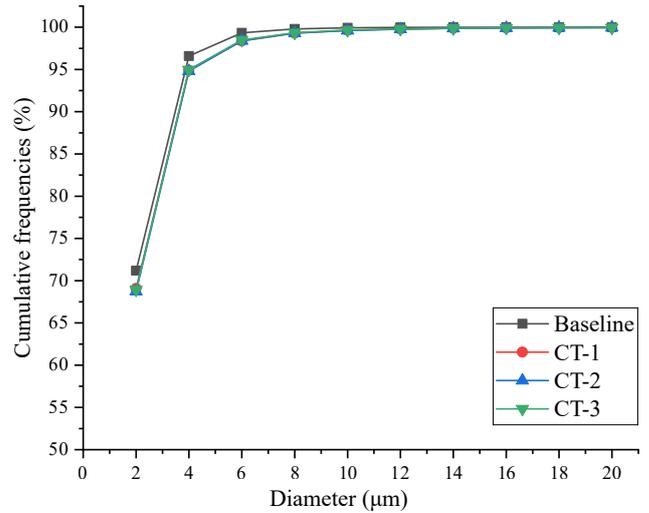


Figure 14: Pore size distribution of 3D microstructure and generated 3D microstructures. The baseline represents the real 3D microstructure, while CT-1, CT-2, and CT-3 denote three generated 3D microstructures, respectively.

generated large-size microstructural image, where the size of the real 2D image is 800×800 pixels², and the 2D slice of the generated 3D image is 1000×3000 pixels². Notably, local details of the same size are displayed for clear visualization. The results indicate that the characteristics of the real 2D images are retained even in large-size images. Therefore, CEM3DMG can generate 3D microstructural images with arbitrary sizes while maintaining similar microstructural characteristics as the given 2D images.

3.5. Verification on 3D Micro-CT Image

To further validate the generation effectiveness of CEM3DMG, real 3D Micro-CT images and generated 3D Micro-CT images are subjected to comparative analysis. The 3D micro-CT image data from the Visible Cement Dataset (available from <http://visiblecement.nist.gov>) is obtained using the European synchrotron radiation facility in Grenoble [50]. In the micro-CT dataset, specimens are scanned at a resolution of $0.95 \mu m$ per pixel. The size of the micro-CT image is $300 \times 300 \times 300$ pixels³

($285 \times 285 \times 285 \mu\text{m}^3$). In the experiment, a 2D slice is first selected from real 3D Micro-CT images, and then 3D microstructural images are generated based on the 2D slice.

Figure 12 shows that a 3D microstructural image is generated from a single 2D slice taken from the real 3D image. For the Micro-CT images, we adopted the idea of Kim et al. to determine the threshold value of the pores [51], and the segmentation value between hydration products and unreacted clinkers using the method of Scrivener et al. [43]. In visual comparison of the 3D images, the internal pores, unreacted clinkers and hydration products are displayed. From a visual perspective, the generated 3D microstructure is similar to the real 3D microstructure, albeit relying only on a single 2D image. The most notable aspect lies in the morphology of cement particles, where the real and generated microstructures closely resemble each other, making it difficult to distinguish them through visual observation.

In addition to visual analysis, as shown in Figure 13, the proportions of different phases are illustrated. It can be observed that the proportions of the three phases between the real and generated microstructures are generally consistent, with CEM3DMG showing a greater proficiency in generating pores. Although the morphology of clinkers and hydration products in the generated microstructure closely resembles that of the real microstructure, the proportions of phases within the microstructure are not entirely consistent. On one hand, this suggests that CEM3DMG still requires further refinement in learning these microstructural details. On the other hand, relying solely on histogram-based segmentation methods for different phases (hydration products and clinkers) within the microstructure makes it challenging to achieve entirely accurate segmentation.

Figure 14 presents a comparison of the PSD between the real and generated 3D microstructures, revealing a close overall distribution of pore sizes. The experiments demonstrate that the PSD in the generated microstructures closely resembles that of the real microstructure, consistent with the experimental results based on BSE images.

In summary, the proposed CEM3DMG can generate realistic 3D microstructural images and is effective in tests with real 3D images.

4. Conclusion

This paper proposes a deep learning-based method for generating 3D microstructural images of hardened cement pastes. In the method, a novel image generation framework (CEM3DMG) is designed to generate 3D microstructural images based on the given 2D BSE image.

- The proposed CEM3DMG requires only a 2D BSE image, after which any number of 3D microstructural images are generated, providing comprehensive characterization and realistic microstructures for cement

hydration. Compared to other 3D imaging techniques (such as FIB-SEM and synchrotron radiation-based Micro-CT), the economic cost is effectively controlled.

- The proposed CEM3DMG generates high-quality and realistic 3D microstructural images, with a resolution reaching $0.47 \mu\text{m}$ per pixel. In experiments, generated 3D microstructural images exhibit visual features similar to the given 2D image. Furthermore, the generated 3D images and the real 2D images show similarity in aspects such as gray level distribution, various phases proportions, and pore size distribution. Experimental results prove the effectiveness of the proposed method.
- The proposed CEM3DMG can generate arbitrary-size 3D microstructural images similar to the 2D image. In experiments, a subset of image with various sizes is verified, including 3D images of $200 \times 200 \times 200$ pixels³, $400 \times 400 \times 400$ pixels³, $800 \times 800 \times 800$ pixels³. Moreover, a slice of 1000×3000 pixels² from large-size 3D images is exhibited.

The proposed 3D microstructural image generation method is an up-and-coming technology. In the future, the proposed method will require further verification and exploration in various tasks, such as assessing 3D transport properties and conducting 3D mechanical analysis.

References

- [1] S. Lv, S. Ting, J. Liu, Q. Zhou, Use of graphene oxide nanosheets to regulate the microstructure of hardened cement paste to increase its strength and toughness, *CrystEngComm* 16 (36) (2014) 8508–8516.
- [2] K. Shuldyakov, B. Trofimov, L. Kramar, Stable microstructure of hardened cement paste—a guarantee of the durability of concrete, *Case Studies in Construction Materials* 12 (2020) e00351.
- [3] Y. Yan, A. Ouzia, C. Yu, J. Liu, K. L. Scrivener, Effect of a novel starch-based temperature rise inhibitor on cement hydration and microstructure development, *Cement and Concrete Research* 129 (2020) 105961.
- [4] F. Zumino, K. Scrivener, Microstructural developments of limestone calcined clay cement (lc3) pastes after long-term (3 years) hydration, *Cement and Concrete Research* 153 (2022) 106693.
- [5] K. Van Breugel, Numerical simulation of hydration and microstructural development in hardening cement-based materials (i) theory, *Cement and concrete research* 25 (2) (1995) 319–331.
- [6] D. P. Bentz, D. P. Bentz, CEMHYD3D: A three-dimensional cement hydration and microstructure development modelling package. Version 2.0, US Department of Commerce, National Institute of Standards and Technology, 2000.
- [7] H. M. Jennings, S. K. Johnson, Simulation of microstructure development during the hydration of a cement compound, *Journal of the American Ceramic Society* 69 (11) (1986) 790–795.
- [8] S. Bishnoi, K. L. Scrivener, *mic*: A new platform for modelling the hydration of cements, *Cement and concrete research* 39 (4) (2009) 266–274.
- [9] J. W. Bullard, A three-dimensional microstructural model of reactions and transport in aqueous mineral systems, *Modelling and Simulation in Materials Science and Engineering* 15 (7) (2007) 711.
- [10] J. W. Bullard, E. J. Garboczi, A model investigation of the influence of particle shape on portland cement hydration, *Cement and Concrete Research* 36 (6) (2006) 1007–1015.

- [11] C. Liu, R. Huang, Y. Zhang, Z. Liu, M. Zhang, Modelling of irregular-shaped cement particles and microstructural development of portland cement, *Construction and Building Materials* 168 (2018) 362–378.
- [12] Z. Zhu, W. Xu, H. Chen, Z. Tan, Evolution of microstructures of cement paste via continuous-based hydration model of non-spherical cement particles, *Composites Part B: Engineering* 185 (2020) 107795.
- [13] P. Kuusela, M. Pour-Ghaz, R. Pini, A. Voss, A. Seppänen, Imaging of reactive transport in fractured cement-based materials with x-ray ct, *Cement and Concrete Composites* 124 (2021) 104211.
- [14] G. Konstantopoulos, E. Koumoulos, A. Karatza, C. Charitidis, Pore and phase identification through nanoindentation mapping and micro-computed tomography in nanoenhanced cement, *Cement and Concrete Composites* 114 (2020) 103741.
- [15] J. Hsieh, Computed tomography: principles, design, artifacts, and recent advances.
- [16] P. Sudraud, G. Ben Assayag, M. Bon, Focused-ion-beam milling, scanning-electron microscopy, and focused-droplet deposition in a single microcircuit surgery tool, *Journal of Vacuum Science & Technology B: Microelectronics Processing and Phenomena* 6 (1) (1988) 234–238.
- [17] Y. Song, C. Davy, D. Troadec, X. Bourbon, Pore network of cement hydrates in a high performance concrete by 3d fib/sem—implications for macroscopic fluid transport, *Cement and Concrete Research* 115 (2019) 308–326.
- [18] Z.-L. Jiang, Y.-J. Pan, J.-F. Lu, Y.-C. Wang, Pore structure characterization of cement paste by different experimental methods and its influence on permeability evaluation, *Cement and Concrete Research* 159 (2022) 106892.
- [19] D. P. Bentz, Three-dimensional computer simulation of portland cement hydration and microstructure development, *Journal of the American Ceramic Society* 80 (1) (1997) 3–21.
- [20] X. Qiu, J. Chen, M. Deprez, V. Cnudde, G. Ye, G. D. Schutter, 3d microstructure simulation of reactive aggregate in concrete from 2d images as the basis for asr simulation, *Materials* 14 (11) (2021) 2908.
- [21] L. Lemmens, B. Rogiers, D. Jacques, M. Huysmans, R. Swennen, J. L. Urai, G. Desbois, E. Laloy, Nested multiresolution hierarchical simulated annealing algorithm for porous media reconstruction, *Physical Review E* 100 (5) (2019) 053316.
- [22] K. Perlin, An image synthesizer, *ACM Siggraph Computer Graphics* 19 (3) (1985) 287–296.
- [23] D. R. Peachey, Solid texturing of complex surfaces, in: *Proceedings of the 12th annual conference on Computer graphics and interactive techniques*, 1985, pp. 279–286.
- [24] K. Tang, B. Yang, L. Wang, X. Zhao, Y. Wang, H. Zhang, Three-dimensional cement microstructure texture synthesis based on cuda, in: *Intelligent Computing Theories and Application: 12th International Conference, ICIC 2016, Lanzhou, China, August 2-5, 2016, Proceedings, Part II* 12, Springer, 2016, pp. 624–634.
- [25] W. Zhang, L. Song, J. Li, Efficient 3d reconstruction of random heterogeneous media via random process theory and stochastic reconstruction procedure, *Computer Methods in Applied Mechanics and Engineering* 354 (2019) 1–15.
- [26] W. Samek, G. Montavon, S. Lapuschkin, C. J. Anders, K.-R. Müller, Explaining deep neural networks and beyond: A review of methods and applications, *Proceedings of the IEEE* 109 (3) (2021) 247–278.
- [27] K. He, X. Zhang, S. Ren, J. Sun, Deep residual learning for image recognition, in: *Proceedings of the IEEE conference on computer vision and pattern recognition*, 2016, pp. 770–778.
- [28] X. Zhao, X. Wu, L. Wang, P. Hou, Q. Li, Y. Zhang, B. Yang, Three-dimensional microstructural image synthesis from 2d backscattered electron image of cement paste, *arXiv preprint arXiv:2204.01645v1*.
- [29] J. Gutierrez, J. Rabin, B. Galerne, T. Hurtut, On demand solid texture synthesis using deep 3d networks, in: *Computer Graphics Forum*, 2020.
- [30] K. Simonyan, A. Zisserman, Very deep convolutional networks for large-scale image recognition, in: Y. Bengio, Y. LeCun (Eds.), *3rd International Conference on Learning Representations, ICLR 2015, San Diego, CA, USA, May 7-9, 2015, Conference Track Proceedings*, 2015.
- [31] V. Saseendran, N. Yamamoto, P. J. Collins, A. Radlińska, S. Mueller, E. M. Jackson, Unlocking the potential: analyzing 3d microstructure of small-scale cement samples from space using deep learning, *npj Microgravity* 10 (1) (2024) 11.
- [32] X. Zhao, J. Guo, L. Wang, F. Li, J. Li, J. Zheng, B. Yang, Sts-gan: Can we synthesize solid texture with high fidelity from arbitrary 2d exemplar?, *Proceedings of the Thirty-Second International Joint Conference on Artificial Intelligence, IJCAI-23, 2023*, pp. 1768–1776.
- [33] I. Goodfellow, J. Pouget-Abadie, M. Mirza, B. Xu, D. Warde-Farley, S. Ozair, A. Courville, Y. Bengio, Generative adversarial nets, in: Z. Ghahramani, M. Welling, C. Cortes, N. Lawrence, K. Q. Weinberger (Eds.), *Advances in Neural Information Processing Systems*, Vol. 27, Curran Associates, Inc., 2014, pp. 2672–2680.
- [34] T. Portenier, S. Arjomand Bigdeli, O. Goksel, Gramgan: Deep 3d texture synthesis from 2d exemplars, *Advances in Neural Information Processing Systems* 33 (2020) 6994–7004.
- [35] D. Bentz, E. Garboczi, H. Jennings, D. Quenard, Multi-scale digital-image-based modelling of cement-based materials, *MRS Online Proceedings Library (OPL)* 370 (1994) 33.
- [36] I. Gulrajani, F. Ahmed, M. Arjovsky, V. Dumoulin, A. C. Courville, Improved training of wasserstein gans, in: *Advances in Neural Information Processing Systems*, Vol. 30, 2017.
- [37] L. Gatys, A. S. Ecker, M. Bethge, Texture synthesis using convolutional neural networks, *Advances in neural information processing systems* 28.
- [38] M. Zhang, Y. He, G. Ye, D. A. Lange, K. Van Breugel, Computational investigation on mass diffusivity in portland cement paste based on x-ray computed microtomography (μ ct) image, *Construction and Building Materials* 27 (1) (2012) 472–481.
- [39] M. Eik, A. Antonova, J. Puttonen, Phase contrast tomography to study near-field effects of polypropylene fibres on hardened cement paste, *Cement and Concrete Composites* 114 (2020) 103800.
- [40] X. Chen, S. Wu, J. Zhou, Influence of porosity on compressive and tensile strength of cement mortar, *Construction and Building Materials* 40 (2013) 869–874.
- [41] X. Pang, L. Sun, M. Chen, M. Xian, G. Cheng, Y. Liu, J. Qin, Influence of curing temperature on the hydration and strength development of class g portland cement, *Cement and Concrete Research* 156 (2022) 106776.
- [42] H. Wong, M. Head, N. Buenfeld, Pore segmentation of cement-based materials from backscattered electron images, *Cement and Concrete Research* 36 (6) (2006) 1083–1090.
- [43] K. L. Scrivener, H. Patel, P. Pratt, L. Parrott, Analysis of phases in cement paste using backscattered electron images, methanol adsorption and thermogravimetric analysis, *MRS Online Proceedings Library (OPL)* 85 (1986) 67.
- [44] D. Hou, D. Li, P. Hua, J. Jiang, G. Zhang, Statistical modelling of compressive strength controlled by porosity and pore size distribution for cementitious materials, *Cement and Concrete Composites* 96 (2019) 11–20.
- [45] M. Yio, H. Wong, N. Buenfeld, 3d pore structure and mass transport properties of blended cementitious materials, *Cement and Concrete Research* 117 (2019) 23–37.
- [46] S. Diamond, M. E. Leeman, Pore size distributions in hardened cement paste by sem image analysis, *MRS Online Proceedings Library (OPL)* 370 (1994) 217.
- [47] W. Soja, F. Georget, H. Maraghechi, K. Scrivener, Evolution of microstructural changes in cement paste during environmental drying, *Cement and Concrete Research* 134 (2020) 106093.
- [48] K. Lyu, W. She, C. Miao, H. Chang, Y. Gu, Quantitative characterization of pore morphology in hardened cement paste via sem-bse image analysis, *Construction and Building Materials* 202 (2019) 589–602.

- [49] K. Lyu, E. Garboczi, Y. Gao, C. Miao, X. Liu, Relationship between fine aggregate size and the air void system of six mortars: I. air void content and diameter distribution, *Cement and Concrete Composites* 131 (2022) 104599.
- [50] D. P. Bentz, S. Mizell, S. Satterfield, J. Devaney, W. George, P. Ketcham, J. Graham, J. Porterfield, D. Quenard, F. Vallee, et al., The visible cement data set, *Journal of Research of the National Institute of Standards and Technology* 107 (2) (2002) 137.
- [51] J.-S. Kim, S.-Y. Chung, D. Stephan, T.-S. Han, Issues on characterization of cement paste microstructures from μ -ct and virtual experiment framework for evaluating mechanical properties, *Construction and Building Materials* 202 (2019) 82–102.