

When Superconductivity Crosses Over: From BCS to BEC

Qijin Chen,^{1,2,3} Zhiqiang Wang,⁴ Rufus Boyack,⁵ Shuolong Yang,⁶ and K. Levin⁴

¹Hefei National Research Center for Physical Sciences at the Microscale and School of Physical Sciences, University of Science and Technology of China, Hefei, Anhui 230026, China

²Shanghai Research Center for Quantum Science and CAS Center for Excellence in Quantum Information and Quantum Physics, University of Science and Technology of China, Shanghai 201315, China

³Hefei National Laboratory, University of Science and Technology of China, Hefei 230088, China

⁴Department of Physics and James Franck Institute, University of Chicago, Chicago, Illinois 60637, USA

⁵Department of Physics and Astronomy, Dartmouth College, Hanover, New Hampshire 03755, USA

⁶Pritzker School of Molecular Engineering, University of Chicago, Chicago, Illinois 60637, USA

(Dated: November 3, 2022)

New developments in superconductivity, particularly through unexpected and often astonishing forms of superconducting materials, continue to excite the community and stimulate theory. It is now becoming clear that there are two distinct platforms for superconductivity through natural and synthetic materials. Indeed, the latter category has greatly expanded in the last decade or so, with the discoveries of new forms of superfluidity in artificial heterostructures and the exploitation of proximitization. The former category continues to surprise through the Fe-based pnictides and chalcogenides, and nickelates as well as others. It is the goal of this review to present this two-pronged investigation into superconductors, with a focus on those which we have come to understand belong somewhere between the BCS and Bose-Einstein condensation (BEC) regimes. We characterize in detail the nature of this “crossover” superconductivity. In the process, we address the multiple ways of promoting a system out of the BCS and into the BCS-BEC crossover regime within the context of concrete experimental realizations. These involve natural, as well as artificial, mostly two-dimensional materials, such as magic-angle twisted bilayer and trilayer graphene, or gate-controlled devices, as well as one-layer and interfacial superconducting films. This work should be viewed as a celebration of BCS theory by showing that even though this theory was initially implemented with the special case of weak correlations in mind, it can in a very natural way be extended to treat the case of these more exotic strongly correlated superconductors.

CONTENTS

I. Introduction	2	IV. Quantitative implications for 3D crossover superconductors	11
A. Background and history	2	A. Two-gap physics present in BCS-BEC	11
B. Extending BCS-BEC theory to finite temperatures	3	B. Contrasting BCS-BEC in s and d -wave superconductors	11
C. BCS-BEC in cold-atom experimental research	3	C. The interplay of conventional fluctuations and BCS-BEC crossover physics: Normal-state transport	13
D. The pre-BCS era: Schafroth theory and the beginning of BCS-BEC	4	D. Relation between BCS-BEC and the Uemura plots	13
II. Overview of BCS-BEC Crossover	6	V. BCS-BEC Physics in the 2D Limit	14
A. Signatures of crossover	6	A. Overview of 2D theory	14
B. Analogies with an ideal Bose gas	7	B. Procedure for determining T_{BKT} in the Fermi gases	15
C. Arguments supporting BCS-BEC in the cuprates	7	C. Quantitative description of BCS-BEC crossover in 2D and comparison with 3D	15
D. Counter-arguments for BCS-BEC in cuprates	7	D. Topology and quantum geometry in BCS-BEC	16
E. Contrasting Pair-fluctuation and Phase-fluctuation scenarios	8	VI. Strongly disordered conventional films: two energy scales and a pseudogap	17
F. Key results and overview of the theory	8	VII. Application of BCS-BEC in the literature (beyond Fermi gases)	19
III. Detailed Theory of 3D BCS-BEC Superconductivity at $T \neq 0$	9	A. BCS-BEC in the iron chalcogenides	19
A. Characterizing the bosons embedded in BCS theory	9	B. BCS-BEC in interfacial superconductivity	20
B. Determining the pair mass M_{pair} and the non-condensed pair number density n_{pair} for $T \leq T_c$	10	C. BCS-BEC in magic-angle twisted bilayer and trilayer graphene	22
C. Establishing the form of T_c	11	D. BCS-BEC for 2D gated semiconductors	23
		E. Magnetoexciton condensates with BCS-BEC	24

VIII. Application to the Cuprates	26
A. Experimental evidence that BCS-BEC may be relevant to the cuprates	26
B. The spectral function: distinguishing condensed and non-condensed pairs	27
C. Transport in the Cuprates	27
D. Quantifying the Fermi arcs	29
E. Behavior of the finite- ω conductivity	29
F. Precursor diamagnetism	30
G. Other applications of BCS-BEC: Features of the non-Fermi liquid	31
IX. Conclusions	31
A. Summary	31
B. Outlook	32
X. Acknowledgments	33
Appendix A. Experimental data for 2D superconductors	33
Appendix B. General BCS-BEC Crossover Theory for D-wave Case Near Half Filling	34
Appendix C. D-wave Crossover and the Cuprate Phase Diagram	35
References	36

I. INTRODUCTION

A. Background and history

There has been a recent explosion of papers addressing the concept of BCS-BEC crossover in superconductors. Besides the well-known applications to ultracold Fermi gases and high-temperature cuprate superconductors [1–3], examples of systems exhibiting BCS-BEC-like characteristics include: iron-based superconductors, magic-angle twisted bilayer (MATBG) and trilayer graphene (MATTG), gate-controlled two-dimensional devices, interfacial superconductivity, and magnetoexcitonic condensates in graphene heterostructures. BCS-BEC crossover theory is a theory in which one contemplates that the attraction (of unspecified origin) which causes the pairing that drives superconductivity is stronger than in conventional materials. As a result, fermion pairs form before they Bose condense, much as in Bose-Einstein condensation (BEC) of a Bose superfluid. This is in contrast to the well-established theory of Bardeen, Cooper, and Schrieffer (BCS) where pairing and condensation occur at precisely the same temperature.

This Review article is written to summarize what has been observed in these candidate two-dimensional (2D) and three-dimensional superconductors which are somewhere between BCS and BEC. We will discuss how these reported phenomena relate to BCS-BEC crossover, paying special attention to 2D materials where there seems to be a surprisingly large number of examples. In the process we

present a theoretical understanding at general temperatures. Lest there be any confusion at the start, throughout this paper what we mean by “BCS-BEC crossover” is **not** the onset or proximity to the BEC as defined by some, but an intermediate regime between BCS and BEC, where a significant departure from strict BCS theory is apparent.

We begin the discussion of BCS-BEC crossover by focusing on a particular choice of ground state, namely that having the form originally introduced in BCS theory. The appreciation of this broader applicability of BCS theory and its straightforward extension to a form of Bose condensation underlines how remarkable the original contribution of Bardeen, Cooper, and Schrieffer was. It should be noted that their discovery has provided support and a crucial framework for multiple Nobel prizes besides their own. One could argue that these number of the order of 10 or so, extending into nuclear and particle physics as well. In this way, the recognition of its even greater generality is particularly significant.

This recognition can be credited to two physicists: A. J. Leggett [4] and D. M. Eagles [5]. Leggett’s contribution was motivated by the discovery of a BCS-like triplet-pairing state in the neutral superfluid helium-3. He emphasized that this form of fermionic superfluidity has features which are clearly distinct from conventional superconductors; here the Cooper pairs have complex degrees of freedom. Moreover, the underlying attraction which leads to superconductivity in this neutral system must derive from a quite distinct pairing mechanism [6].

In making his claims, Leggett pointed to the sweeping generality of the BCS ground state:

$$\Psi^{\text{BCS}} = \Pi'_{\mathbf{k}} \left(u_{\mathbf{k}} + v_{\mathbf{k}} a_{\mathbf{k},\uparrow}^{\dagger} a_{-\mathbf{k},\downarrow}^{\dagger} \right) |0\rangle, \quad (1)$$

where the prime on the product indicates that each distinct pair $(\mathbf{k}, -\mathbf{k})$ is counted only once. This greater applicability is exhibited by self consistently adjusting the variational parameters $u_{\mathbf{k}}$ and $v_{\mathbf{k}}$ along with the fermionic chemical potential, which accommodates a continuous evolution from weak to strong pairing. This leads to a smooth crossover or transition between a BCS phase with large pair size and having a chemical potential $\mu = E_F > 0$ (where E_F is the Fermi energy) and a BEC-like phase (with small pair size) in which μ becomes negative. It is important to emphasize, however, that this BEC phase is specific to the ground-state fermionic wave function and need not represent that of a true weakly interacting Bose gas.

In a related way, Eagles [5] also made ground breaking observations. He should be credited with emphasizing the concept of “pairing without superconductivity”. This preformed-pair normal-state scenario is at the heart of BCS-BEC theory, once one leaves the BCS regime. He should be additionally credited with drawing attention to the possibility that superconductivity in lightly doped semiconductors may be considered to be described by a form of BCS-BEC crossover. Indeed, we will see in this Review that there is currently renewed interest in these low carrier density semiconducting superconductors.

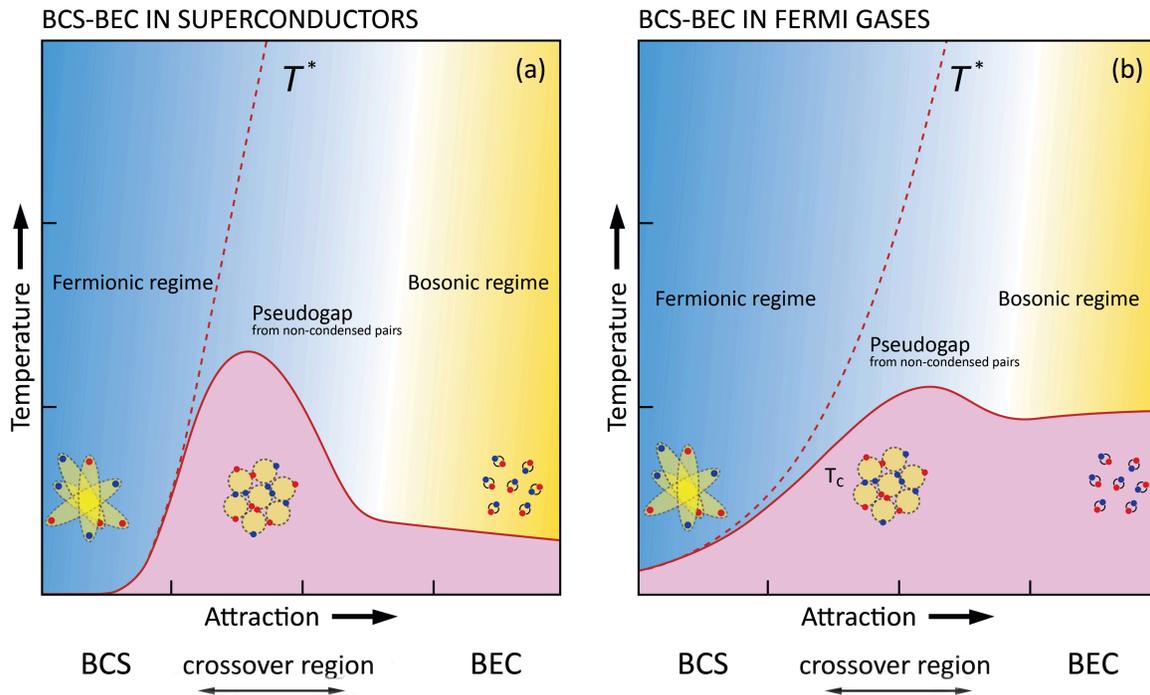


Figure 1. Comparison of the 3D, s -wave BCS-BEC phase diagram for (a) superconductors and (b) Fermi gases, showing the contrasting behavior in the BEC regime in which T_c approaches either zero (a) or a finite number (b). Note the ubiquitous dome shape in the solid-state system. The minimum or shoulder in the T_c curves marks a transition to a different physical regime, as it corresponds to the onset of a bosonic superfluid, with $\mu = 0$. Important to stress here is that **the crossover regime begins at the point where the two temperature scales (T^* corresponding to the opening of a pairing gap) and T_c become distinct**. Microscopic units for the superconducting case are provided in Fig. 10(a) in a later section of the paper.

B. Extending BCS-BEC theory to finite temperatures

In 1985, Nozières and Schmitt-Rink (NSR) wrote a famous paper [7] that brought attention back to this earlier work by Eagles and Leggett. They presented an in-depth discussion of the ground state of Eq. (1). Moreover, they suggested an approach for computing the transition temperature T_c . A subtle but often-missed point is that their T_c calculation is not to be associated with the ground state they addressed. It corresponds to a different and rather complex phase [8]. The NSR paper was the first to emphasize that BCS-BEC crossover theory in a solid-state lattice system assumes a character in the strong-coupling BEC regime quite different from that of a Fermi gas. This behavior is illustrated schematically in Fig. 1 which contrasts the 3D phase diagrams associated with a solid-state superconductor in panel (a) and a Fermi gas in panel (b). The difference arises from the kinetic energy degrees of freedom associated with the motion of fermions in periodic solids as distinct from gases. The most striking consequence is that in a solid which is in the BEC regime, T_c can become arbitrarily small.

Indeed, we emphasize this distinction in the present paper, as it bears on the relevance (or lack thereof) of the ultracold atomic Fermi gas superfluids to the solid-state superconductors we discuss here. Related work in the form of a review was written by Micnas in 1990 [9] addressing superconductors in this BEC-like or strong-attraction limit.

Subsequently, the finite-temperature theory of the NSR paper was followed by work from Sá de Melo, Randeria, and Engelbrecht [10], which provided a precise functional-integral reformulation.

Around the same time, and in collaboration with Trivedi and others [11], these researchers presented a series of papers using Monte-Carlo techniques to address normal-state features of the attractive 2D Hubbard model. This was thought to be relevant to high-temperature superconductivity and its anomalous “pseudogap” phase. This phase corresponds to an above- T_c , or “normal” state in which there is an excitation gap for fermionic excitations. Understanding the origin of this pseudogap has been a central focus in the cuprate field. In their work it was presumed that the latter is associated with pairing in the absence of condensation¹.

C. BCS-BEC in cold-atom experimental research

Adding to this chronology were the groundbreaking observations made beginning around 2003 of Fermi condensates in trapped atomic gases. Condensation was

¹They noted their particular numerics supported the interpretation of the pseudogap (or equivalently a normal-state excitation gap) as a “spin gap” in which the charge degrees of freedom did not equally participate.

initially observed [12, 13] at strong coupling in the BEC regime (where $\mu < 0$) and shortly thereafter [14, 15] at intermediate coupling (in a “unitary” gas, where the chemical potential was positive). These experiments should be recognized by the solid-state physics community as a true “tour de force”. Researchers managed to surmount multiple challenges stemming from the fact that the atomic gases are neutral, they are confined to inaccessible traps, and moreover there is no direct way of measuring their temperature.

As a result, in the first few generations of experiments, “proof” of superfluidity was established indirectly through magnetic field sweeps. These sweeps make use of a Feshbach resonance to take a gas in the more fermionic regime and quickly change the magnetic field thereby projecting the system onto the strong-pairing regime. In this limit a bimodality in the density profiles reveals the presence of a condensate. Over the next year or two, subsequent experiments established superfluidity through measurements of the specific heat [16] and later, quite spectacularly, through direct observation of quantized vortices [17].

With increasing understanding of these Fermi gas superfluids, the community then focused on additional probes such as transport [18, 19] and additional complexities associated with spin-imbalanced or polarized gases [20, 21] (very much like superconductors in magnetic fields) as well as in optical lattices [22]. Along these lines, there were interesting accompanying theoretical contributions [23, 24] as well as those which contemplated even more exotic (spin-orbit coupled and topological) phases [25–28]. Also notable were the interesting contrasts with solid-state superconductors centered around low viscosity or “perfect fluids” [29, 30] in the Fermi gases and “bad metals” [31, 32] associated with highly resistive transport as in the cuprate superconductors.

The collective contribution of the dedicated experimental groups who met the challenge of finding and characterizing these Fermi condensates deserves enormous respect. Among the groups were those of Jin [12, 14, 33], Ketterle [15, 34], Grimm [13, 35], Thomas [36, 37], Hulet [38, 39], Salomon [40] and Bloch [41]. Accompanying the experiments were, of course, theoretical developments. Review articles are available which summarize several different variations [42] of BCS-BEC crossover theory at finite temperature. Among these are those from our own group [1], from the Camerino group [43], and the Munich group [44].

Among the first theorists [45] to apply BCS-BEC theory to the cold gases were Y. Ohashi and A. Griffin. This was followed by work from our group [46] which, shortly before the 2003 discovery, called attention to the expected importance of a pseudogap in these cold gases. This, in turn, helped motivate experimental efforts beginning with early observations of possible pseudogap signatures [13] using radio frequency (RF) spectroscopy [47].

Later research by Jin and her colleagues [33] introduced a rather ingenious analogue of angle resolved photoemission spectroscopy (ARPES) to investigate the pseudogap in more detail. In addition to this pseudogap focus, substantial effort was devoted to the unitary gas, intermediate between BCS and BEC, where the scattering length becomes infinite. Here

precise numbers for thermodynamic features, variables in the equation of state, and special inter-relationships [48–50] provided a series of challenges to test the numerical accuracy of different BCS-BEC crossover theories.

D. The pre-BCS era: Schafroth theory and the beginning of BCS-BEC

In the context of this chronological summary it is useful to revisit an approach due to Schafroth [51] which antedated BCS theory. It provides a platform, nevertheless, for a more expanded interpretation of superconductivity. Schafroth had an interesting and rather intuitive approach. He argued that superconductivity could be thought of as associated with Bose condensation of an ideal charged Bose gas. Here the condensation onsets at the transition temperature T_c and the expression for this temperature, following that of an ideal Bose gas, is given by:

$$T_c = \left(\frac{2\pi}{C} \right) \left[\frac{n_B^{2/3}(T_c)}{M_B(T_c)} \right], \quad (2)$$

where $C = [\zeta(3/2)]^{2/3}$ with $\zeta(3/2) \approx 2.61$, where ζ is the Riemann zeta function. Here also we set $\hbar = k_B = 1$. The parameters n_B and M_B represent the (3D) density and mass of the bosons which condense. We should view these as yet unspecified bosons as representing fermionic pair degrees of freedom so that

$$n_B \equiv n_{\text{pair}} \quad \text{and} \quad M_B \equiv M_{\text{pair}}. \quad (3)$$

Note that, at the time of the BCS discovery, there was some resistance to Schafroth’s notion that his approach had anything in common with BCS theory. The key point which Schafroth emphasized is that there must be a form of Bose condensation embedded in superconductivity theory and this boson inevitably involves a pair of electrons.

This leads to a central question and one that we will answer here. What kind of out-of-condensate boson or preformed pair is in fact compatible with BCS theory? The answer to this query allows us to compute the transition temperature, after establishing a precise meaning for n_{pair} and M_{pair} . Presumably because his work predated BCS theory, Schafroth did not ascribe any complexity to these quantities which we now know must depend on both temperature and attractive interaction strength. Importantly, because of the latter, we inevitably have to deal with BCS-BEC crossover physics. We will see that the ground state of Eq. (1) suggests one should think of superconductors as associated with quasi-ideal-Bose-gas condensation. In this way the simple expression in Eq. (2) represents the transition temperature of a quasi-ideal system throughout the crossover.

Thus, what is needed first is to quantitatively characterize what we call these out-of-condensate pairs, for both weak and strong attraction. The challenge is to do so in a manner which is consistent with BCS theory at general temperatures. It is useful to remark at this stage that all of this suggests that we

will view the phenomena of BCS-BEC crossover not as an extension of BCS theory but more as a natural corollary.

This differentiates the work we summarize here from other approaches to BCS-BEC crossover, such as that of Nozières and Schmitt-Rink and others [7, 10, 45, 52]. Their finite-temperature analysis was presumably designed to accommodate some of the physics of bosonic Bogoliubov theory for the fermion pairs. In their picture, which involves more strongly interacting composite bosons than would be associated with a BCS-like ground state, the bosonic degrees of freedom are described [7] as: “A bound pair [which] is a collective mode of the superfluid ... T_c thus results from thermal excitation of collective modes”.

Their scenario can be compared with other work [53] which addresses the extreme BEC regime and directly establishes the nature of that fermionic ground-state wave function associated with a composite-boson Bogoliubov picture (including Lee-Yang corrections). While it is different from the expression in Eq. (1), the complex ground state of the NSR approach has, however, been given some attention in the literature [8]. This and related alternative schemes [52, 54] have problems inherited from theories of interacting Bose gases. They exhibit first-order transitions at T_c . In the context of the present paper, this complicates the understanding of a number of issues including how the non-Fermi-liquid (or pseudogap) normal state [1, 55] evolves into the ordered phase.

In this Review we hope to communicate what exactly BCS-BEC crossover is and what it is not. A crucial consequence of crossover theory is the separation of energy and temperature scales associated with the onset of pairing (T^*) and condensation (T_c). Another crucial feature is the association with relatively “strong” pairing attraction, when compared with characteristic electronic energies. This is manifested as a large zero-temperature gap to E_F ratio: $\Delta(T=0)/E_F$, and a small pair size. It necessarily follows that these superconductors in many ways have a more gentle onset of superconducting features. This relates to the fact that there are preformed pairs (as noted by Eagles [5]) or equivalently there is a normal-state gap in the fermionic spectrum.

Moreover, there may be more direct evidence that bosonic degrees of freedom are present above the transition. This is seen most readily as a depression [56, 57] in the resistivity at T^* . The pairing gap and the bosonic degrees of freedom are indeed two sides of the same coin, although the latter are more difficult to identify. Finally, we wish to emphasize that it is highly unlikely that any but a very small number of solid-state superconductors associated with BCS-BEC crossover are in the BEC regime. This corresponds to an extreme situation in which all fermionic signatures have been lost.

This review article will focus primarily on two-dimensional superconducting materials, mostly in the clean limit. Notably, as stated by Kosterlitz [58] “The onset of superconductivity in 2D ... requires a pre-existing condensate or pairing of electrons.” One can understand this by noting that the underlying physical picture characterizing the onset of two dimensional superconductivity (or the

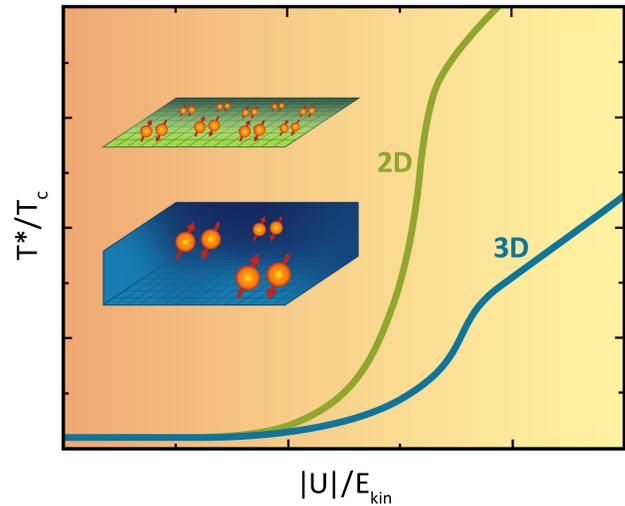


Figure 2. Central figure showing three different ways of promoting a superconductor into the crossover regime – defined by the requirement that T^*/T_c substantially exceeds unity. These three ways involve reducing the dimensionality to two, increasing the attraction $|U|$, or decreasing the electronic energy scales E_{kin} (through smaller density or smaller hopping t).

Berezinskii-Kosterlitz-Thouless (BKT) superconducting state [59, 60]) assumes the separation of energy scales: phase coherence cannot occur until a pairing amplitude is established.

Also important is a stronger tendency to pair that is a consequence of the two dimensionality. In 2D, in the particular case of a quadratic dispersion near the conduction band bottom, there is no critical value of the pairing interaction which is required to form two-body bound states. This is in contrast to the situation in 3D. Hence the “pairing glue” in a 2D superconductor need not be anomalously strong to promote the system into the BCS-BEC regime. In this way, in 2D one necessarily finds that (quasi)condensation and pairing occur at different temperatures. These observations may explain why there are many 2D examples in the recent BCS-BEC literature.

Figure 2 represents an important figure of this Review, as it shows the three distinct ways of promoting a superconductor into the crossover regime. Plotted on the vertical axis is the important parameter T^*/T_c (or for the two-dimensional system T^*/T_{BKT}). Here T^* is the temperature at which a pairing gap first opens and T_c (or T_{BKT}) represent the temperatures at which phase-coherent order appears. Within the BCS-BEC crossover scenario, when this ratio deviates substantially from unity the superconductor is no longer in the BCS regime. The horizontal axis indicates the strength of the attractive interaction in units of a characteristic electronic energy scale E_{kin} .

This figure shows that a relatively weaker attraction is needed to promote 2D superconductors into the crossover regime, where T^*/T_c deviates from unity. The figure is characteristic of the low-density limit. There are two other ways of obtaining values for T^*/T_c in excess of unity.

There is the possibility of a very strong pairing “glue”, i.e., associated with anomalously large $|U|$. We might speculate this stronger pairing scenario applies, if at all, to the cuprate superconductors. Finally, an important alternative for arriving at the strong-pairing regime is when the characteristic electronic energy scales (called E_{kin}) become anomalously small. This can occur through flat bands (or small hopping or bandwidth) or through low electronic densities which reduce E_F . We will see in this Review that both two dimensionality and/or small electronic energy scales are likely responsible for the many recent observations of BCS-BEC crossover superconductivity.

How do we think about the transition in 2D to a quasi-condensed state? In this paper we address the approach to the BKT state from the high-temperature side. We emphasize that we will use the methodology advocated by the cold-atom community [61–63], where in atomic Bose gases one finds some of the most convincing evidence for a Kosterlitz-Thouless state.

Originally, much of this literature was focused on BKT for bosonic superfluids. By extension to fermionic superconductors and superfluids, we argue that this transition temperature is given by

$$T_{\text{BKT}} \propto \left[\frac{n_{\text{B}}(T_{\text{BKT}})}{M_{\text{B}}(T_{\text{BKT}})} \right], \quad (4)$$

where, again, these as yet unspecified bosons with (2D) number density n_{B} and mass M_{B} represent pair degrees of freedom as defined in Eq. (3). It is important to note that a fraction involving the same temperature-dependent terms $n_{\text{pair}}(T)$ and $M_{\text{pair}}(T)$ enters in both the 2D and 3D expressions for the transition temperature.

This discussion serves to help interpret the illustrations to the left of the curves in Fig. 2. These are schematic representations of the number of pairs (or pair density, n_{pair}) in the 2D sheets or 3D volumes at the onset of the transition. For the same fixed attractive interaction, these schematic figures emphasize that in 2D there is a significantly higher density of pairs at T_{BKT} than for the analogue in the 3D system.

We end this section by noting these Schafroth-like expressions for the transition temperatures in 2D and 3D (Eqs. 2 and 4) provide a simple expression for the important superconducting coherence length, ξ_0^{coh} , given by: $\hbar^2/[2M_{\text{pair}}(\xi_0^{\text{coh}})^2] = k_{\text{B}}T_c$. Moreover they establish that ξ_0^{coh} depends only on the pair density n_{pair} (presumed at the onset of the transition), thus serving to reveal the location of a given system within the BCS-BEC crossover. We will show how to exploit these results later in this Review as well as demonstrate that the superconducting coherence length is rather widely discussed in the experimental literature. Importantly, it is readily accessible through the magnetic-field response of charged superconductors. This is in contrast to the pair size, which strictly speaking is distinct. One should be wary in the theoretical literature, however, that often a shorthand notation is used which blurs the distinction between these two lengths.

II. OVERVIEW OF BCS-BEC CROSSOVER

A. Signatures of crossover

Since the concept of BCS-BEC crossover is sometimes interpreted in different ways in the literature it is important to emphasize what we associate with the term “crossover” in this Review. We consider here solid state superconductors (as distinct from Fermi gases) which are promoted out of the strict BCS regime through moderately strong pairing interactions. These interactions, in turn, lead to emerging bosonic degrees of freedom which coexist with a well defined Fermi surface. With ever increasing interaction strength the bosonic component will eventually become dominant leading to a disappearance of the fermiology; here the system enters the BEC regime. It is still an open question whether a BEC phase (with its attendant very low transition temperatures) has ever been observed in a solid state system. While some [64] have identified crossover with the onset of the BEC limit, in this paper, we adhere to the conventional definition of “BCS-BEC” crossover emphasizing the associated new and interesting properties, which are distinct from those observed in either the BEC or BCS regime.

There are a number of signatures of BCS-BEC crossover which we more precisely enumerate here. Many of these features can have multiple interpretations. A conclusion in support of the appropriateness of a BCS-BEC crossover for a particular superconductor comes from the preponderance of evidence, rather than from any “smoking gun”, single signature in this list.

One observes [1]:

1. Large values of $\Delta(T=0)/E_F$, from $\approx 0.05 - 1.0$.
2. The presence of a normal-state gap (or pseudogap) with onset at $T^* > T_c$ which is a necessary, but not sufficient signature of crossover physics.
3. BCS mean-field-like relations which characterize the ratio of the ground-state excitation gap, $\Delta(T=0)$, and the pairing onset temperature, T^* .
4. A precursor downturn [56] in the temperature dependence of the resistivity around the gap onset temperature T^* .
5. A moderately short coherence length, somewhat lower than but of the order of $k_{\text{F}}\xi_0^{\text{coh}} \lesssim 6$. This will be quantified in more detail later in Fig. 10(c).
6. A smooth evolution of the measured (e.g., via angle resolved photoemission spectroscopy (ARPES)) excitation gap from above to below T_c . For a nodal superconductor this applies to the gap determined away from nodal regions in the Brillouin zone.
7. Superconducting fluctuation-like behavior, particularly in the diamagnetic response, well above T_c .

8. A small mid-infrared feature (slight maximum) in the optical conductivity as a function of frequency, which is associated with the pseudogap energy scale.
9. Two characteristic energy gaps. The gap associated with coherent superconducting phenomena is distinct from that associated with bosonic or pair excitations. This ensures that the Meissner effect, Andreev reflection, and Josephson tunneling all vanish above T_c , reinforcing the fact that they are not associated with the presence of a pairing gap.
10. Additional normal-state experimental observations which support a crossover picture, such as shot noise indications of $2e$ charge carriers and “back bending” electronic band dispersion in the vicinity but above T_c .

B. Analogies with an ideal Bose gas

What is essential is that the treatment of the BCS-BEC crossover which we present here be compatible with BCS physics, both in the ground state as well as at all temperatures $T \leq T_c$. A central theoretical question one needs to address is what kind of boson is embedded in BCS theory. These bosons or preformed pairs will be present at the onset of condensation in substantial numbers in the BEC and only virtually in the BCS limit.

To understand these preformed pairs we present a simple figure based on a rather close analogy to an ideal Bose gas. The reason the quasi-ideal gas system is a useful prototype stems from the form of the ground-state wave function of Eq. (1), which can be rewritten as $\Psi^{\text{BCS}} \propto e^{b_0^\dagger} |0\rangle$ with the composite bosonic operator $b_0^\dagger = \sum_{\mathbf{k}} (v_{\mathbf{k}}/u_{\mathbf{k}}) a_{\mathbf{k},\uparrow}^\dagger a_{-\mathbf{k},\downarrow}^\dagger$. We see that this condensate corresponds to a ground state of noninteracting bosons.

The upper row of Fig. 3 is a schematic representation of the temperature evolution of a BCS-BEC superfluid. This shows that as temperature decreases below an onset temperature, called T^* say, a new form of quasiparticle or excitation appears. These are non-condensed pairs and are represented by dashed circles in red. At this same temperature a pairing gap or pseudogap is present which reflects the fact that there must be an input of energy to create fermionic excitations by breaking pairs. As temperature further decreases to just above T_c , the number of these preformed pairs increases. Note that, the figure shows that there are also a number of unpaired fermions at the transition. The ratio of the boson to fermion number continuously increases from BCS to BEC. In the BCS limit the number of pairs at T_c is essentially zero, while in the BEC limit that number approaches $n/2$.

Below T_c , condensed pairs (solid circles in blue) appear. As temperature is lowered further, non-condensed pairs gradually (and at $T = 0$ completely) convert to the condensate. There are no non-condensed pairs in the BCS-like ground state. Importantly, strict BCS theory is the special case where $T^* = T_c$ and concomitantly where the number of non-condensed

bosons becomes arbitrarily small at any temperature T . This signals that there is essentially no pairing gap at T_c .

C. Arguments supporting BCS-BEC in the cuprates

The question of whether a BCS-BEC scenario is relevant to the cuprates is, like all aspects of the cuprate literature, a highly controversial one. Despite this controversy it is useful to let the reader independently judge; thus, at the end of this Review article we show what the implications are of such a theory for the cuprates. We address aspects that are both consistent and inconsistent with the data.

There are claims in the literature that the cuprates are somewhere between BCS and BEC. We cite some of these here.

- From A. J. Leggett [65]: “*The small size of the cuprate pairs puts us in the intermediate regime of the so-called BCS-BEC crossover.*”
- From G. Sawatzky and colleagues [66]: “*High- T_c superconductors cannot be considered as classical BCS superconductors, but rather are smoothly evolving from BEC into the BCS regime.*”
- From I. Bozovic and J. Levy [67]: “*We show the likely existence of preformed pairs in the cuprates ... The existence of preformed pairs is a necessary but not sufficient condition for BEC or for BCS-BEC crossover to occur.*”
“*Indeed, since Fermi surfaces have been mapped out ... this favors a picture in which pairing is relatively strong, pre-formed pairs first appear at $T > T_c$... but copper oxides are still on the BCS side of the crossover.*”
- From Y. Uemura [68]: “*Combining universal correlations ... and pseudogap behavior in the underdoped region, we obtain a picture to describe superconductivity in cuprate systems in evolution from Bose-Einstein to BCS condensation.*”

D. Counter-arguments for BCS-BEC in cuprates

It should be noted that even if BCS-BEC theory plays a role in the cuprate superconductors this will not address or elucidate a number of important issues which characterize their behavior and need to be understood in an ultimate theory. Among these are [55] the pairing mechanism, which remains unknown; also challenging is arriving at an understanding of the “strange metal” behavior including the linear temperature dependence of the resistivity which is, indeed, very widespread among other strongly correlated superconductors [69]. Another puzzle is the distinct change observed in carrier concentration which seems to correlate with the presence of a pseudogap [70]. This appears consistent with recent ARPES claims [71] that the pseudogap suddenly collapses at a fixed hole concentration. As

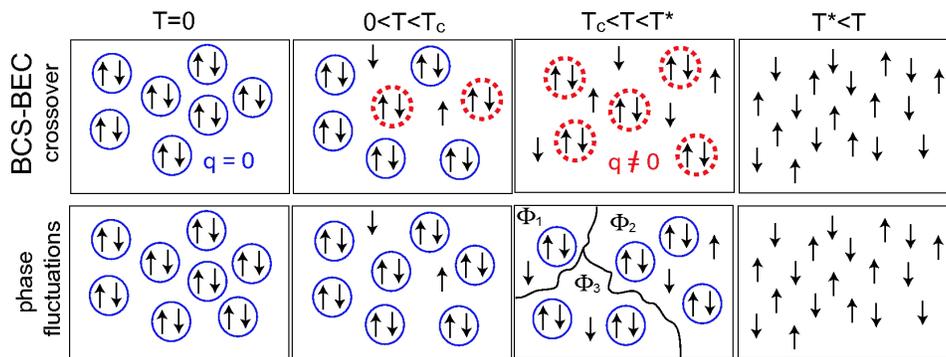


Figure 3. Illustration comparing the BCS-BEC crossover and phase-fluctuation scenarios. Throughout, blue closed circles, lone arrows, and dashed red circles represent condensed fermion pairs, unpaired fermions, and finite-lifetime pairs, respectively. The crossover theory is distinguished by the presence of noncondensed $\mathbf{q} \neq 0$ pairs for nonzero temperatures less than T^* . The defining feature of the phase-fluctuation picture is the presence of different phase domains above T_c , indicated by the regions labeled with different Φ 's.

emphasized throughout, this Review will focus on strongly correlated superfluids other than the Fermi gases and cuprates.

Nevertheless, in the interest of completeness it is useful to list some of the issues that have been raised to challenge the relevance of BCS-BEC theory for the cuprates. Examples are the following:

1. Current cuprate experiments show no signs of the chemical potential μ becoming negative, as might be expected in the BEC regime.
2. T_c and T^* are observed to vary inversely in the underdoped regime.
3. One finds that a number of (but not all) superconducting fluctuation phenomena appear only in the immediate vicinity of T_c , well away from the pseudogap onset temperature T^* .
4. There are multiple signatures of “two-gap” physics [72], which phenomena some would say are inconsistent with a theoretical description involving preformed pairs.
5. There are indications [73] of additional ordering within the pseudogap phase, even possibly with an onset associated with its boundary [74, 75].
6. There are claims [76] suggesting that quantum critical behavior is present so that T^* actually vanishes beneath the superconducting dome; this is inconsistent with a BCS-BEC picture in which T^* is necessarily larger than T_c .
7. There are ARPES experiments [77] which indicate that at higher temperatures in the normal state, but well below T^* , the fermionic dispersion shows disagreement with the characteristic energy dispersion associated with BCS-like quasi-particles.

We note that the first four of these seem to be compatible with a BCS-BEC scenario for the cuprates. We defer all

discussion of the cuprates until the last section of the paper as well as in Appendix C, where we discuss some of these other issues, noting that this is a relatively less consequential part of the present paper.

E. Contrasting Pair-fluctuation and Phase-fluctuation scenarios

We emphasize that the pairing fluctuations we consider are distinct from phase fluctuations [78]. This is made more explicit by comparing the two panels in Fig. 3. The pair-fluctuation or BCS-BEC crossover picture in the upper panel is to be associated with a new type of paired quasi-particle whereas the phase fluctuations relate to more collective behavior. This collective behavior reflects an alternative physical picture [78], often applied to the cuprate superconductors, in which low carrier density is associated with poor screening and, therefore, small phase stiffness. By contrast, the pair fluctuations of BCS-BEC theory are associated with strong pairing “glue”. One can observe in Fig. 3 that in the phase-fluctuation scenario there is no direct counterpart to the new form of quasi-particle found in the crossover scenario.

We note that this contrast has been emphasized previously by Emery and Kivelson [78] who describe the phase-fluctuation scenario as follows: “*Our discussion attributes the properties of high-temperature superconductors to the low superfluid density ... and not to a short in-plane coherence length and a crossover to real-space pairing*”.

F. Key results and overview of the theory

It should not be surprising that accompanying these two forms of quasi-particles in Fig. 3 are two different forms of fermionic excitation gaps: Δ_{pg} and Δ_{sc} . One can think of these as representing the energies which must be applied in order to break the two types of (non-condensed and condensed) pairs and, thereby, create fermions.

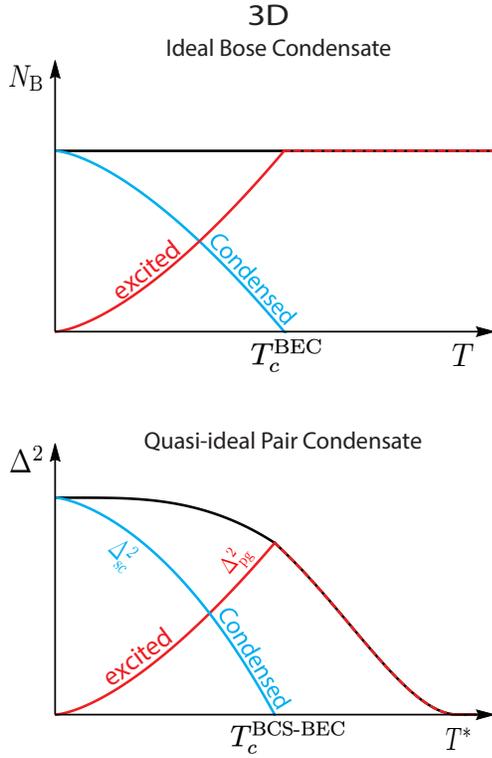


Figure 4. Comparison of ideal gas decomposition of the boson number into condensed and excited contributions (upper panel) with the analogue decomposition for a fermionic superfluid (lower panel) which involves the square of the pairing gap Δ^2 . This figure shows that the two gap contributions to Δ^2 , called Δ_{pg}^2 and Δ_{sc}^2 , are closely analogous to their counterparts in the ideal Bose gas. Indicated schematically is how to arrive at the respective transition temperatures associated with the intersection of the curves marking the onset of the condensate contributions.

A more detailed theory [1], discussed in the next section, reveals that the gaps combine in quadrature in such a way as to yield the total, physically measurable fermionic excitation gap called $\Delta(T)$. Thus

$$\Delta^2(T) = \Delta_{\text{sc}}^2(T) + \Delta_{\text{pg}}^2(T). \quad (5)$$

A central consequence of this picture to be established below is that

$$\Delta^2(T) = \Delta_{\text{BCS}}^2(T) \quad \text{for } T \leq T_c. \quad (6)$$

In this way, in the ordered phase the total excitation gap coincides with the results of mean-field BCS theory.

As shown in Fig. 4, the two gap contributions to Δ^2 called, Δ_{pg}^2 and Δ_{sc}^2 , play a similar role to their respective counterparts in the ideal-Bose-gas scenario. This latter theory considers a decomposition of the total number of bosonic particles, N , in terms of those deriving from the excited bosons N^{excited} and the condensed bosons $N^{\text{condensed}}$. As a function of decreasing temperature the former convert to the latter so that there are no excitations in the ground state. The

temperature-dependent quantity $N^{\text{condensed}}$ is established by evaluating the difference $N - N^{\text{excited}}$.

Similarly, as in an ideal Bose gas, the condensate contribution Δ_{sc}^2 is obtained by subtracting the non-condensate piece Δ_{pg}^2 from the total Δ^2 , approximated as $\Delta_{\text{BCS}}^2(T)$ near but above T_c . This determines T_c from the condition that the non-condensed contribution is no longer sufficiently large to accommodate the full value of the mean-field gap squared. Thus, there must be an additional contribution from the condensate, Δ_{sc}^2 .

In this way, not only can one directly derive the Schafroth [51] expression shown in Eq. (2), but one can write this same equation in a way which is more familiar from the perspective of BCS theory. We note that in strict BCS theory, T_c is obtained from

$$1 = (-U) \sum_{\mathbf{k}} \frac{1 - 2f(|\xi_{\mathbf{k}}|)}{2|\xi_{\mathbf{k}}|} \Big|_{T=T_c}, \quad (7)$$

where $U < 0$ and $f(x) = 1/(e^{x/T} + 1)$ is the Fermi-Dirac distribution function. It will be shown that, in BCS-BEC crossover theory, precisely at T_c :

$$1 = (-U) \sum_{\mathbf{k}} \frac{1 - 2f(\tilde{E}_{\mathbf{k}})}{2\tilde{E}_{\mathbf{k}}} \Big|_{T=T_c}, \quad (8)$$

where $\tilde{E}_{\mathbf{k}} = \sqrt{\xi_{\mathbf{k}}^2 + \Delta^2(T_c)}$. Here $\xi_{\mathbf{k}} = \epsilon_{\mathbf{k}} - \mu$ is the bare fermion dispersion with μ the fermionic chemical potential.

Thus, the central change from strict BCS theory (aside from a self-consistent readjustment of the fermionic chemical potential [4]) is that T_c **is determined in the presence of a finite excitation gap, $\Delta(T_c)$** . Solving for T_c involves finding the point of intersection between Δ_{pg}^2 and the mean-field gap Δ^2 .

It should be clear that both of these expressions for the transition temperature in BCS-BEC crossover theory are intuitively quite reasonable. What is satisfying is to find that these two equations (Eq. (8) and the Schafroth expression in Eq. (2)) are equivalent, provided one properly computes the number of pairs and their mass. Thus, this meets the goal of connecting a Schafroth-like approach to a more microscopic approach based on BCS theory.

III. DETAILED THEORY OF 3D BCS-BEC SUPERCONDUCTIVITY AT $T \neq 0$

The discussion in the previous section provides a reasonably complete summary of results from the formalism. In this section we provide additional details for the interested reader.

A. Characterizing the bosons embedded in BCS theory

Here we determine how to understand the non-condensed bosons of the BCS approach from a more microscopic

and quantitative theory [1], building on a key and central point. We present the theory for the s -wave case, while the application to d -wave superconductivity can be found elsewhere [79]. At any temperature in which there is a condensate, the non-condensed bosons which are in equilibrium with the condensate must have a vanishing chemical potential:

$$\mu_{\text{pair}} = 0 \quad \text{for } T \leq T_c. \quad (9)$$

This statement is equivalent to the famous Hugenholtz-Pines theorem. How do we guarantee that the chemical potential is zero? BCS provides us with an important temperature-dependent self-consistency condition known as the gap equation, valid for all $T \leq T_c$. This gap equation is

$$0 = \frac{1}{U} + \sum_{\mathbf{k}} \frac{1 - 2f(E_{\mathbf{k}})}{2E_{\mathbf{k}}}, \quad (10)$$

where $E_{\mathbf{k}} = \sqrt{\xi_{\mathbf{k}}^2 + \Delta^2}$ and Δ is the temperature-dependent pairing gap.

We argue that Eq. (10) should be incorporated in some way or another to arrive at an understanding of pair excitations. This leads us to constrain the form of the pair propagator $t(p)$ for the non-condensed pairs to satisfy

$$t^{-1}(p=0) \equiv \mu_{\text{pair}} = 0, \quad T \leq T_c. \quad (11)$$

Indeed, Thouless has argued that a divergence of a ‘‘ladder’’ sum of diagrams (embedded in a pair propagator) is to be associated with the BCS transition temperature. Here we assert that this Thouless condition can be extended to characterize the *full* temperature-dependent gap equation, not just the transition region. This leads to a pair propagator of the form

$$t^{-1}(p) = \sum_{\mathbf{k}} G(\mathbf{k})G_0(p - \mathbf{k}) + U^{-1}. \quad (12)$$

In this equation $G_0(k) = (i\omega_n - \xi_{\mathbf{k}})^{-1}$ and $G(k) \equiv [G_0^{-1}(k) - \Sigma(k)]^{-1}$, corresponding to the bare and dressed fermionic Green’s functions with $\Sigma(k) = -\Delta^2 G_0(-k)$. We define $k = (i\omega_n, \mathbf{k})$ and $p = (i\Omega_m, \mathbf{p})$ as two four-vectors with $\omega_n = (2n + 1)\pi T$ and $\Omega_m = 2m\pi T$, and $\sum_{\mathbf{k}}$ is a short-hand notation for $T \sum_n \sum_{\mathbf{k}}$. It is important here to properly define the fermionic chemical potential μ . (To be consistent this requires setting $\text{Re}\Sigma(\mathbf{k}_\mu) = 0$, so that the diagonal part of the Hartree self energy is absorbed into the chemical potential. Here \mathbf{k}_μ is the wavevector on the Fermi surface.)

In this way one avoids unphysical effects. These stem from the fact that the t-matrix of BCS theory takes an asymmetric form, involving different spin states pertaining to dressed and bare Green’s functions. If care is not taken [80], such calculations may lead incorrectly to the presumption that there is a Fermi surface mismatch for the two spin states and, consequently, regions of unstable superconductivity.

In a more complete and systematic study of coupled equations of motion, Kadanoff and Martin [81, 82] arrived

at a similar conclusion concerning the presence of both dressed and bare Green’s functions. As stated by Kadanoff and Martin: ‘‘This asymmetry ... has led several people to surmise that the symmetrical equation ... solved in the same approximation would be more accurate. This surmise is not correct...’’.

B. Determining the pair mass M_{pair} and the non-condensed pair number density n_{pair} for $T \leq T_c$

The fundamental quantities which determine the transition temperatures [1] in Eqs. (2) and (4) require we determine n_{pair} and M_{pair} . We argue that both of these must depend on the BCS gap Δ . In general t-matrix theories the self energy is given by a product of a Green’s function and the t-matrix. Here this self energy due to non-condensed pairs takes the form

$$\Sigma_{\text{pg}}(k) = \sum_{p \neq 0} t(p)G_0(p - k). \quad (13)$$

Note that the $p = 0$ component of $t(p)$ (which corresponds to the condensate) is necessarily excluded in the summation above. Here one adopts the so-called ‘‘pseudogap (pg) approximation’’, which is the central and only approximation of the theory. This was motivated originally by detailed numerical work [83, 84]. It should be emphasized that it is appropriate at all T below T_c . It also applies for a restricted set of temperatures in the vicinity but slightly above the transition [83, 84] where $|\mu_{\text{pair}}|$ is very small. Since $|\mu_{\text{pair}}| \approx 0$, $t(p)$ is strongly peaked about $p = 0$, so that the self energy can be approximated by

$$\Sigma_{\text{pg}}(k) \approx -\Delta_{\text{pg}}^2 G_0(-k), \quad (14a)$$

$$\text{with } \Delta_{\text{pg}}^2(T) = -\sum_{p \neq 0} t(p), \quad T \lesssim T_c. \quad (14b)$$

We are now in a position to compute the pair mass and number density. After analytical continuation, $i\Omega_m \rightarrow \Omega + i0^+$, we expand the t-matrix for small argument p to find

$$t(\Omega, \mathbf{p}) = \frac{Z^{-1}}{\Omega - \Omega_{\mathbf{p}} + \mu_{\text{pair}} + i\Gamma_{\Omega}}, \quad (15)$$

where Z is a frequency- and momentum-independent proportionality constant; the pair mass is contained in the pair dispersion $\Omega_{\mathbf{p}} = \mathbf{p}^2/(2M_{\text{pair}})$; the last term in the denominator $i\Gamma_{\Omega}$ is frequency dependent and describes the finite lifetime of the non-condensed pairs due to decay into the two-fermion continuum. Defining the propagator for the non-condensed pairs as $Zt(\Omega, \mathbf{p})$ and neglecting the generally small dissipative term $i\Gamma_{\Omega}$, one can obtain the non-condensed pair density as

$$n_{\text{pair}}(T) = \sum_{\mathbf{p}} b(\Omega_{\mathbf{p}}) = Z(T)\Delta_{\text{pg}}^2(T), \quad (16)$$

which is naturally temperature dependent. Here, $b(x) = 1/(e^{x/T} - 1)$ is the Bose-Einstein distribution function.

We have asserted above that the self energy is $\Sigma(k) = -\Delta^2 G_0(-k)$. To complete the arguments we now show that this derives from two contributions – from the condensate (sc) and the non-condensate (pg):

$$\Sigma(k) = \sum_p t(p)G_0(-k+p) = \Sigma_{\text{sc}}(k) + \Sigma_{\text{pg}}(k). \quad (17)$$

Here, Σ_{sc} comes from the Dirac delta function piece of $t(p)$ at $p = 0$, i.e., $t_{\text{sc}} \equiv t(p = 0) = -(\Delta_{\text{sc}}^2/T)\delta(p)$. Using Eq. (14a), we then obtain

$$\Sigma(k) \approx -(\Delta_{\text{sc}}^2 + \Delta_{\text{pg}}^2)G_0(-k) \equiv -\Delta^2 G_0(-k). \quad (18)$$

In this way, Eq. (5) results and we have $\Delta^2 = \Delta_{\text{sc}}^2 + \Delta_{\text{pg}}^2$.

C. Establishing the form of T_c

We approach T_c from high temperatures, where $\Delta_{\text{pg}}^2 = \Delta^2$ and $\mu_{\text{pair}} < 0$. As T decreases, μ_{pair} increases, and Eq. (16) will be satisfied under the condition $\Delta_{\text{pg}}^2 = \Delta^2$, with $T \geq T_c$. The transition temperature T_c is reached when this is no longer possible; at this temperature Δ_{pg}^2 can not accommodate the value of Δ^2 , so that an additional contribution Δ_{sc}^2 is needed. This occurs when μ_{pair} , as a function of decreasing T , first reaches zero in Eq. (16). As a consequence, one recovers a Schafroth-like expression for T_c :

$$T_c = \left(\frac{2\pi}{\mathcal{C}}\right) \left[\frac{n_{\text{pair}}^{2/3}(T_c)}{M_{\text{pair}}(T_c)}\right], \quad (19)$$

as was anticipated in Eq. (2). It was not recognized in the original Schafroth calculations, but on the right-hand side of Eq. (19), both n_{pair} and M_{pair} depend on Δ^2 , and are therefore functions of T . Below T_c , Eq. (16) is valid with $\mu_{\text{pair}} = 0$ and $\Delta_{\text{pg}}^2 < \Delta^2$.

IV. QUANTITATIVE IMPLICATIONS FOR 3D CROSSOVER SUPERCONDUCTORS

A. Two-gap physics present in BCS-BEC

The above arguments underline the importance of having two distinct energy gaps in BCS-BEC crossover physics. These were illustrated in Fig. 4. The recognition of these two distinct gaps is an issue which bears on some of the interesting candidate materials which are claimed to exhibit BCS-BEC, as we discuss in this Review.

Indeed, one of the central ways in which these two gap contributions are manifested has to do with the distinction between two classes of experiments: these are associated with phenomena which reflect superfluid coherence and those which reflect an excitation or pairing gap. The superfluid density [85] provides a useful example, as it necessarily vanishes when coherence is destroyed. But, notably, it also depends on the fermionic excitation gap Δ :

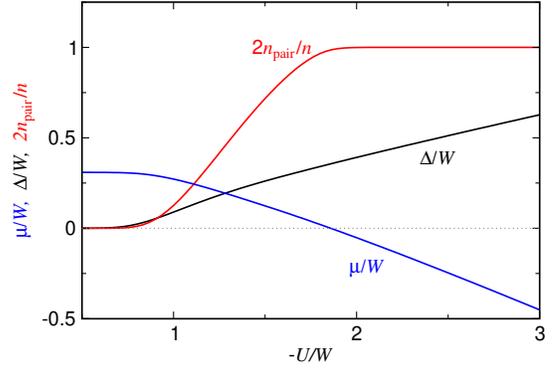


Figure 5. Quantitative values of the parameters μ , Δ , and the number of pairs n_{pair} at T_c for the s -wave BCS-BEC superconductor on a 3D cubic lattice in Fig. 1(a) as a function of the attractive interaction U (normalized by the half bandwidth $W = 6t$) with the electron density $n = 0.1$ per unit cell. Here the normal-state electronic energy dispersion is $\epsilon_{\mathbf{k}} = 2t(3 - \cos k_x - \cos k_y - \cos k_z)$, where the lattice constant a has been set to unity.

$$\frac{n_s}{m} = \frac{2}{3} \sum_{\mathbf{k}} \left(\frac{\partial \xi_{\mathbf{k}}}{\partial \mathbf{k}}\right)^2 \frac{\Delta_{\text{sc}}^2}{E_{\mathbf{k}}^2} \left[\frac{1 - 2f(E_{\mathbf{k}})}{2E_{\mathbf{k}}} + \frac{\partial f(E_{\mathbf{k}})}{\partial E_{\mathbf{k}}}\right]. \quad (20)$$

It is useful at this point to emphasize the fact that even though the bosonic degrees of freedom may be viewed as “quasi ideal” within this generalized BCS framework, in contrast to an ideal Bose gas this does not compromise the existence of stable superfluidity. As is implied in Eq. (20), superconductivity is stable in this framework as it is to be associated with the underlying fermionic degrees of freedom.

This analysis of the superfluid density provides a template for other experiments such as Andreev and Josephson tunneling which reflect true long-range order in a superconductor. In these tunneling experiments, two gap physics also reveals itself and this can be rather dramatic, particularly in the case of anisotropic pairing, such as in systems having d -wave gap symmetry. We end by noting that this two-gap behavior appears to have no counterpart in other preformed-pair scenarios (e.g., the phase-fluctuation approach) for the pseudogap.

B. Contrasting BCS-BEC in s and d -wave superconductors

A crucial feature of BCS-BEC in superconductors (in either 2D or 3D) to be emphasized throughout this Review is that the canonical plots of the phase diagram (based on the Fermi gases) do not capture the physics of superconductivity in the solid state. For the latter, as shown in Fig. 1(a), one finds T_c follows a superconducting dome as a function of variable interaction strength, within the fermionic regime. Thus, one should not infer, as is often the case, that for solid-state superconductors in the BEC there is a large and maximal transition temperature so that in this limit T_c becomes independent of the attractive coupling.

Importantly, for fermions on a lattice, T_c approaches zero in the extreme BEC. This asymptotic behavior sets in once μ becomes negative and it is associated with the onset of the shoulders in Fig. 1. This is reasonably straightforward to understand [7]. The hopping of pairs requires the individual hopping of fermions, and, when two fermions are tightly glued together, this hopping is highly suppressed, leading to the asymptotic behavior seen in Fig. 1(a). More quantitatively, this suppressed hopping of pairs varies as $t^2/|U|$, where t is the fermionic hopping matrix element and $|U|$ is the magnitude of the attractive interaction.

Figure 5 provides more quantitative details on the key energy scale parameters which enter BCS-BEC crossover for the s -wave lattice case of Fig. 1(a). Here and throughout this paper with the exception of the Appendices we use a simple nearest neighbor tight binding band structure. The figure indicates the behavior of Δ and μ at T_c in units of a characteristic electronic scale (in this case corresponding to the bandwidth). These energies are plotted as a function of varying attractive interaction, normalized to the half bandwidth $W = 6t$, where t is the hopping matrix element. Also plotted here is the important parameter n_{pair} which corresponds to the number of pairs at the onset of the transition (normalized by $n/2$, as determined from Eq. (16)).

In particular, one can glean from the plot of n_{pair} that the BEC or $\mu = 0$ transition is associated with the absence of fermions so that only pairs are present ($n_{\text{pair}} = n/2$). More generally, one can view the function n_{pair} as a kind of ‘‘dial’’ informing about where a given system is within the crossover. Tuning the dial provides access to the counterpart values of μ and Δ at T_c . When n_{pair} is essentially zero this corresponds to the BCS case and when $n_{\text{pair}} \approx n/2$ one enters the BEC regime.

The crossover behavior for a d -wave superconductor is generally different [86] and some aspects are additionally discussed in Appendix B. For definiteness, we consider here the symmetry to be of the form $d_{x^2-y^2}$, which is relevant to the cuprate superconductors. The central contrasting feature is the termination of d -wave superconductivity well before the BEC regime is entered. This is found at all but very low electron densities and derives principally from the fact that d -wave pairs have a more extended size. As a result a pair-pair repulsive interaction which is always present [9] is sufficiently strong so that it inhibits pair hopping and pairs become localized. And, importantly, this happens in the fermionic regime, well away from the $\mu < 0$ regime. Consequently, in the d -wave case, the BEC limit cannot generally be accessed [86]. This important effect is illustrated in the phase diagram shown in Fig. 6.

What this implies more concretely is that the d -wave system undergoes a transition at moderately strong attraction, where $T_c \rightarrow 0$. Here superconductivity continuously disappears, albeit in the presence of a finite pairing gap Δ or finite T^* . This has features which are suggestive of the widely discussed ‘‘Cooper-pair insulator’’ [87–89] although this can also include a pair density wave alternative [90]. This form of pair localization pertains to a clean system and represents a different mechanism, deriving from strong

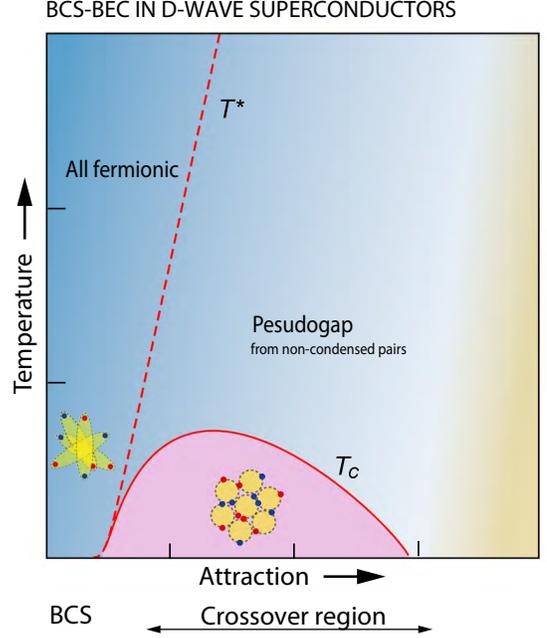


Figure 6. BCS-BEC phase diagram for a d -wave superconductor [86], showing that this system (near half filling) has vanishing T_c before the onset of the BEC regime. This can be compared with the s -wave case in Fig. 1(a) in which the BEC regime is accessible.

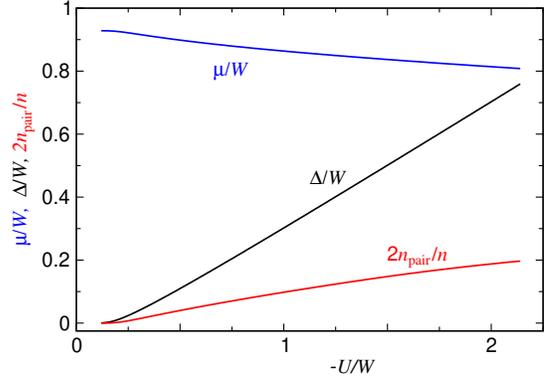


Figure 7. Quantitative values of the parameters μ , Δ , and the number of pairs n_{pair} at T_c for the quasi-2D d -wave BCS-BEC superconductor in Fig. 6 as a function of the attractive interaction (normalized again by the half bandwidth). Here normal state kinetic energy dispersion is $\epsilon_{\mathbf{k}} = (4t + 2t_z) - 2t(\cos k_x + \cos k_y) - 2t_z \cos k_z$ with $t_z/t = 0.01$. The electron density is $n = 0.85$.

intra-pair attraction and strong inter-pair repulsion, which inhibits pair hopping. This same localization has been observed in cases where the band filling is high in s -wave superconductors, as well as in 2D systems. In these instances it provides an interesting comparison, but is not to be associated with strong disorder effects which are known to drive a superconductor-insulator transition in superconducting films [87, 88, 91, 92].

Figure 7 provides more quantitative details on the characteristic energy scale parameters which enter BCS-BEC crossover for this d -wave lattice case [86]. Plotted here is the behavior of Δ and μ at T_c as a function of varying attractive interaction. Also indicated is the number of pairs (derived from Eq. (16)), n_{pair} , at the onset of the transition.

C. The interplay of conventional fluctuations and BCS-BEC crossover physics: Normal-state transport

The question of how conventional superconducting fluctuations relate to BCS-BEC crossover physics continues to be raised in the literature. In this regard it is interesting to note that the treatment of preformed pairs presented here is closely related to self-consistent theories of fluctuation superconductivity. In particular, it represents a natural extension to arbitrarily strong attraction of time-dependent Ginzburg-Landau-based transport theory [93] when the quartic terms in this free-energy expansion are treated in a self-consistent Hartree-level approximation [82, 93–95]. This observation suggests that there is a continuous variation, associated with an *enhancement* of many transport fluctuation signatures, as the coupling varies from weak to strong.

To address these issues more quantitatively, we note that dominating transport in these more strongly correlated superconductors [57, 96, 97] is the fact that there are now two distinct temperature scales which control “fluctuation” effects: T_c and T^* . Transport is complicated additionally by the fact that there are two types of quasiparticles: fermions which experience the gap onset at T^* at which point they generally become less conducting, and bosons which are expected to become more conducting at temperatures somewhat below T^* . These two types of quasiparticles are represented schematically in the upper row of Fig. 3.

The fermionic contribution has been discussed [98, 99] in some detail both above and below T_c . The more familiar fluctuation contributions to bosonic transport derive from the Aslamazov-Larkin [100] diagrams and are associated with a small pair chemical potential, $\mu_{\text{pair}}(T)$, which is found in the immediate vicinity of T_c . In conventional superconductors, μ_{pair} depends only on T_c , but in the presence of more stable preformed pairs one expects that T^* will play an important role. It is at this higher temperature that the pair density vanishes; consequently, fluctuation effects are expected to have some presence even at temperatures as high as T^* .

The above discussion leads one to conclude that, for more strongly coupled superconductors, the nature of “fluctuation” effects associated with T^* in transport requires that one establish the relative size of the contributions from the fermionic and bosonic channels; as we have seen these generally introduce opposite temperature dependencies in their conduction properties. Their relative size depends on their relative scattering times.

Central to this comparison is the fact that the resistivity downturn, a canonical signature of the pseudogap onset at T^* , is frequently associated with the concomitant and rather ubiquitous large normal-state resistivity. This

“bad-metal” behavior [31, 57] (where resistivity saturation is absent) reflects a suppressed fermionic conduction channel. Importantly, bad metallicity allows the bosonic conducting channel to become more prominent and, for example, leads to a boson-related downturn near T^* in the resistivity which would otherwise be obscured by gap effects in the fermionic spectrum.

We will see later in this Review examples of transport signatures which are viewed as indicative of the presence of BCS-BEC crossover physics. In addition to a resistivity downturn, these include enhanced diamagnetism and Nernst signatures, albeit not all uniquely pointing to a BCS-BEC crossover scenario.

D. Relation between BCS-BEC and the Uemura plots

In an interesting series of papers, Y. Uemura [68, 101] has used muon spin resonance (μ SR) experiments to establish a classification scheme for superconducting materials. This classification, in effect, distinguishes so-called “exotic” superconductors from conventional superconductors. The μ SR relaxation rates in these experiments effectively measure the London penetration depth which in turn reflects the ratio of the number of superfluid electrons n_s to their effective mass m^* . Notably, at sufficiently low temperatures where $n_s \approx n$, these same two quantities help to determine the Fermi temperature.

Uemura used this analysis to suggest that “unconventional” superconductors are characterized by the proportionality $T_c \propto T_F$, where T_F is the Fermi temperature. This observation, which follows from plots of the transition temperature versus muon-spin relaxation rate, has led many to believe that a dependence on a single parameter T_F is suggestive of a Bose-condensation description of exotic superconductors. Underlying this inference is the behavior of the Fermi-gas phase diagram as shown, for example, in Fig 1(b), where the asymptotic BEC value of T_c is given by $T_c \equiv T_{\text{BEC}} = T_F/8$ in 2D (and $0.218T_F$ in 3D).

In Uemura’s analysis it would seem that there are a very large number of superconductors belonging to the unconventional category, although one should not presume that all of these are associated with Bose condensation or BCS-BEC crossover. While focusing on a smaller subset of just the high-temperature superconductors, Tallon and co-workers [102] have argued for an interesting and modified version of the Uemura scheme which plots the ratio $T_c/\Delta(T=0)$ versus T_F , thereby introducing a second energy scale which reflects T^* . Figure 8 shows this rather universal scaling of the cuprate data. The solid black line represents the d -wave BCS-BEC theory at moderate band filling which was discussed above.

Such an analysis emphasizes that, for an arbitrary superconductor, more relevant for establishing that a crossover picture is applicable is showing the presence of distinct energy scales T^* and T_c . This is a necessary but not sufficient requirement. In the crossover scenario there must be simultaneously present a moderately large value for

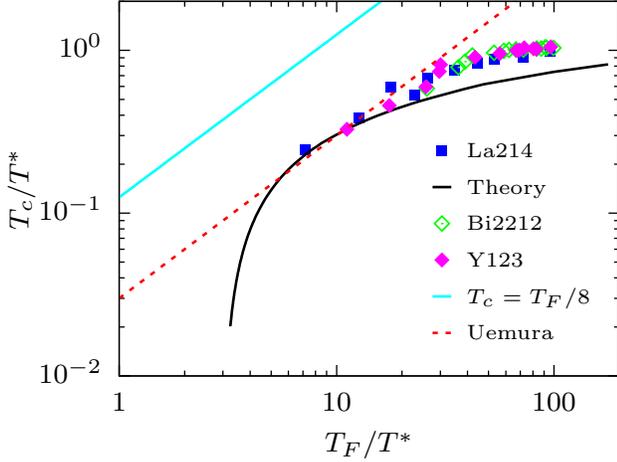


Figure 8. A replot of results from Tallon and co-workers [102] which suggests a modification of the Uemura plot in which T_c depends not only on T_F but also on T^* . This replotting yields a simple, complete scaling of cuprate transition temperatures for different hole concentrations. A BCS-BEC theory curve for the quasi-2D d -wave case [86] is included here.

Δ/E_F . In this way the Uemura plots have elucidated a useful classification scheme, but we emphasize that one should be cautious about inferring too strong a connection to BCS-BEC crossover.

It will be useful, thus, in this Review to show how to arrive at a more discriminating procedure, inspired to some extent by Fig. 8. We will do so here, focusing on 2D superconductors in the form of plots of Δ/E_F versus T^*/T_{BKT} . First, however, one has to have a better understanding of 2D superconductivity.

V. BCS-BEC PHYSICS IN THE 2D LIMIT

A. Overview of 2D theory

In two dimensions there is no true condensation. More quantitatively, in the language of the BCS-BEC crossover, the chemical potential for pairs μ_{pair} never reaches zero. Fermionic 2D superconductivity/superfluidity is necessarily associated with a pseudogap (or non-condensed pairs), but not with a gap deriving from a superconducting order parameter.

In this Review we build on the cold-atom literature to address the BKT phase transition. This focuses on the approach from the high-temperature side and on bosonic degrees of freedom or bosonic “quasi-condensation” (associated with algebraic rather than long range order). The onset of this transition can be equivalently described as that of the onset of vortex-pair binding and unbinding; in this context the role of superfluid phase stiffness is more apparent.

From the bosonic perspective, the BKT transition occurs when the de Broglie wavelength is large and comparable to the inter-pair separation. More precisely, this transition arises

when the temperature-dependent *bosonic* phase-space density reaches a critical value as was independently established in famous papers by Hohenberg and Fisher [103] and also by Popov [104]. This leads to

$$T_{\text{BKT}} = \left(\frac{2\pi}{\mathcal{D}_{\text{pair}}^{\text{crit}}} \right) \left[\frac{n_{\text{pair}}(T_{\text{BKT}})}{M_{\text{pair}}(T_{\text{BKT}})} \right]. \quad (21)$$

Importantly, here we have replaced the number density and mass of true bosons appearing in the **standard expression** (Eq. (4)) by their counterpart values for a composite-boson (or fermion-pair) system. In this way we see that the pair density and pair mass play a similar role as in the 3D superfluid transition in Eq. (19).

Note that, since $n_{\text{pair}}(T)$ is temperature dependent and disappears at T^* , there is a significant difference between BKT behavior in Bose and Fermi superfluids. That is, the latter will be implicitly dependent on two distinct temperature scales. Since $T_{\text{BKT}} \leq T^*$, the physical implications of these two scales become apparent only when studying the BKT transition, as we do here, by approaching the transition from the normal state.

The most detailed numerical analysis of 2D atomic-gas condensates focuses on the Bose gas in the weakly interacting limit and provides [63] results for the critical value $\mathcal{D}_{\text{pair}}^{\text{crit}}$ which is given by

$$\mathcal{D}_{\text{pair}}^{\text{crit}} = \ln(C/\tilde{g}), \quad (22)$$

where \tilde{g} is a dimensionless coupling constant reflecting the **repulsive** interaction between pairs. Importantly, the constant

$$C \approx 380 \quad (23)$$

has been established [63] from Monte-Carlo studies. We note that describing the normal-state approach to the BKT transition in this way has been supported by numerous experimental studies on atomic Bose gases [61, 105, 106].

It is useful to compare this with the more familiar expression [107] for the same T_{BKT} in a superconductor, when approached from the low-temperature superfluid side. This provides a complementary interpretation.

$$T_{\text{BKT}} = \frac{\pi}{2} \rho_s(T_{\text{BKT}}) \equiv \frac{\pi}{8} \left[\frac{n_s}{m} \right] (T_{\text{BKT}}), \quad (24)$$

where one introduces the temperature-dependent superfluid phase stiffness $\rho_s(T)$, evaluated at T_{BKT} , instead of the total pair density as in the formula of Eq. (21). In this equation, n_s and m are the superfluid density and effective mass of fermions. To connect Eq. (21) to Eq. (24), one replaces $\mathcal{D}_{\text{pair}}^{\text{crit}}$ with 4 and converts from pairs to fermions, following Halperin and Nelson [108].

It should be noted that there is a practical difficulty in using either of these formulations. We need phenomenological input to arrive at \tilde{g} in Eq. (22); although, fortunately the dependence is logarithmic and therefore weak. Whereas to apply Eq. (24), one must approximate $\rho_s(T)$ by a suitably chosen (generally mean-field) expression ².

²This excludes using the present theory, more precisely Eq. (20), where

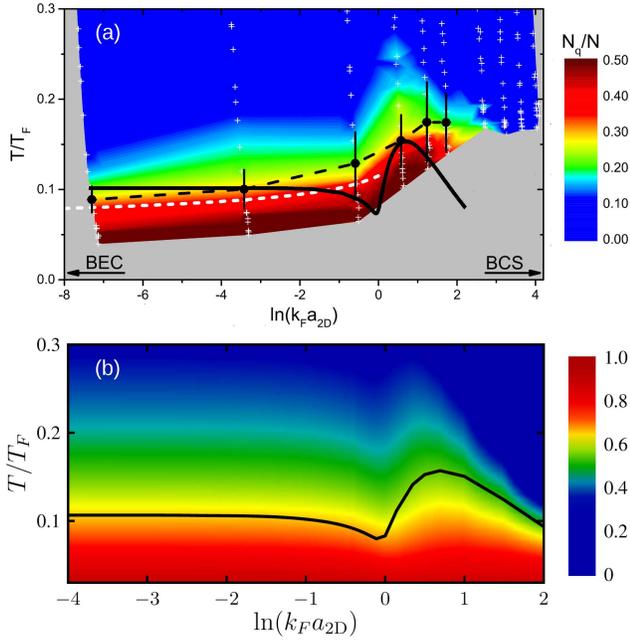


Figure 9. (a) Overlay of theory [112] and experiment for T_{BKT} versus scattering length a_{2D} in a 2D Fermi gas. The color variations indicate the measured quasi-condensate fractions. [110]. (b) Theory results (with a trap included) [112]. Here the color variations represent the calculated condensation fractions.

B. Procedure for determining T_{BKT} in the Fermi gases

The Heidelberg cold-atom group [109] has claimed that the fits for their 2D Fermi gas data find [109, 110] a range of values for $\mathcal{D}_{\text{pair}}^{\text{crit}} = 4.9 - 6.45$. These values are close to but somewhat different from values for atomic Bose gases, where the range is about 6 – 10. In general, $\mathcal{D}_{\text{pair}}^{\text{crit}}$ depends on the non-universal boson-boson interaction strength \tilde{g} , about which one has no precise knowledge. However, a relatively small value of \tilde{g} is presumed in the theoretical framework [63, 111], representing an effectively weakly interacting gas. This would be expected in a BCS ground state of composite bosons, as the bosonic degrees of freedom enter this wave function in a quasi-ideal manner. For the analysis in this Review, we adopt the value $\mathcal{D}_{\text{pair}}^{\text{crit}} = 4.9$, which turns out to best fit the data on Fermi gases³.

Therefore, based on experiments [110] in Fermi gases, the 2D BKT superconducting transition is thus interpreted as a “quasi-condensation” of preformed Cooper pairs. For application to 2D superconductors, more generally, the BKT transition temperature is presumed to be:

$$\frac{n_{\text{pair}}(T_{\text{BKT}})}{M_{\text{pair}}(T_{\text{BKT}})} = \left(\frac{4.9}{2\pi}\right) T_{\text{BKT}} \quad \text{in 2D.} \quad (25)$$

the superfluid density n_s is necessarily zero in 2D, reflecting the fact that simple bosonic condensation cannot occur.

³It should be noted that this best fit case does presume a larger value of \tilde{g} than would be expected for the weakly interacting case [109].

Experiments from the Heidelberg group [109, 110] on a strongly interacting 2D Fermi gas use the momentum distribution to establish the presence of a quasi condensate. This is based on magnetic field sweeps which, through a Feshbach resonance, convert pairs to deeply bound molecules. As shown in the upper panel in Fig. 9, in this way one obtains a plot of the transition temperature as a function of scattering length or equivalently variable interaction strength. Importantly, these measurements show BKT signatures. An overlay of theory and experiment is shown in the top panel of Fig. 9, while the bottom panel represents only the theory [112]. It should be noted that there are claims [113] that the maximum observed experimentally, which goes beyond $T_F/8$, could be an artifact of coupling to a third dimension in the trap, although this issue which pertains exclusively to the 2D Fermi gas, has not been settled.

Subsequent experiments on the 2D gas [114, 115] extended these measurements on trapped gases to accommodate a box potential. Here an alternative methodology was used to obtain the momentum distribution. Importantly these studies presented more direct measurements of superfluidity, as distinct from pair condensation. Determination of one particular critical temperature in the BEC regime yielded consistency with the experiments of the Heidelberg group as a check.

C. Quantitative description of BCS-BEC crossover in 2D and comparison with 3D

Equation (25) is adopted along with the results of Sec. III B to characterize T_{BKT} and other features of 2D superconductors. Figure 10 presents a comparison of transition temperatures, pairing onset temperatures, pair size [116], gap size and coherence length in both two and three dimensions for the s -wave case. In panel (a) one sees the presence of a dome-like structure reflecting BCS-BEC crossover in the solid state, which should be evident for T_c or T_{BKT} . This dome persists as long as the superconductor is within the fermionic regime where $\mu > 0$. The transition to the BEC with negative μ is also evident here as a shoulder in each of the transition temperature curves. There has been some emphasis on bounds on the magnitude of the highest transition temperature in these 2D systems [113], although one should be cautioned that in a lattice system, these are less indicative of the BEC limit, as the maximum is found in the fermionic regime.

The inset of Fig. 10(a) quantifies the important effect of two dimensionality which was presented earlier in the schematic plot shown in Fig. 2. The figure, representing low filling $n = 0.1$ per unit cell, shows that the deviation from BCS behavior (associated with T^*/T_c substantially above 1.0) occurs at significantly smaller attraction for 2D as compared with 3D superconductors.

We turn now to Figs. 10(b) and 10(c) which are the basis for more experimentally relevant studies. The main plots in these two figures represent a natural extension of the Tallon-Uemura scaling in Fig. 8, but for the case of s -wave pairing and both

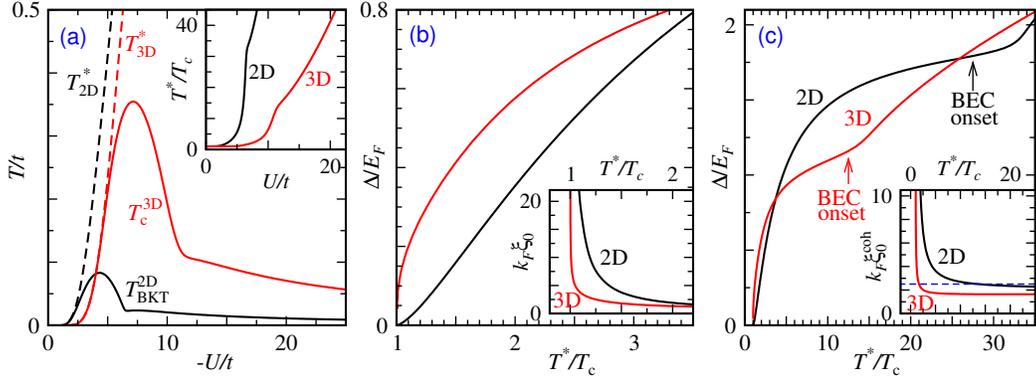


Figure 10. Comparison of 2D and 3D transition temperatures as well as other properties in the BCS-BEC scenario for a tight-binding s -wave superconductor at low densities $n = 0.1$. (a) Transition (T_c or T_{BKT}) and pairing onset (T^*) temperatures, as a function of $-U/t$, the strength of the attractive interaction in units of the hopping matrix element t . The vertical axis in the inset quantifies the degree of departure from strict BCS (through the difference between T^*/T_c and unity). (b) Characteristic magnitude of Δ/E_F in 2D and 3D on a normalized scale, along with the pair size in the inset. Panel (c) represents a more extended view of the results in (b). Indicated here are the (rather high) critical values of T^*/T_c at which the system crosses over to a BEC. The inset shows the behavior of the superconducting coherence length which should be contrasted with the pair size. The former reaches a finite saturation value in the BEC regime, while the latter continuously decreases towards zero.

two and three dimensions. They show that the ratio of the two distinct temperature scales T^*/T_c or T^*/T_{BKT} (which are, in principle, measurable), is correlated with the magnitude of the $T \approx 0$ value for Δ/E_F (which is also measurable).

The inset in Fig. 10(b) shows how the zero-temperature pair size, ξ_0 , varies as the system crosses out of the BCS regime. Representing this crossover in the figure is T^*/T_c , chosen as the horizontal axis. The pair size is a reasonably good indicator of when the system is promoted out of the BCS regime. However, it can be inferred from Fig. 10(c), (where the BEC onsets are marked) that it does not display features at the onset of the BEC; rather the pair size decreases continuously toward zero as this limit is approached. Interestingly, in 2D the pair sizes for equivalent T^*/T_c are significantly larger than in the 3D case.

Finally, it should be emphasized that the pair size and the coherence length represent important but distinct length scales. The “bare” coherence length which can be most readily extracted from the magnetic field response is given by [96, 97]

$$\xi_0^{\text{coh}} = \frac{\hbar}{\sqrt{2}(k_B T_c) M_{\text{pair}}}, \quad (26)$$

and this quantity times the Fermi wave-vector is plotted in the inset in Fig. 10(c).

The coherence length can be rather readily interpreted by making use of the expressions for the transition temperatures in Eqs. (2) and (21). It follows that $k_F \xi_0^{\text{coh}}$ evaluated near the transition temperature depends only on the normalized pair density, n_{pair}/n . This leads to

$$k_F \xi_0^{\text{coh}} = 1.6(n/n_{\text{pair}})^{1/2} \quad (27)$$

and

$$k_F \xi_0^{\text{coh}} = 1.2(n/n_{\text{pair}})^{1/3} \quad (28)$$

for 2D and 3D respectively. From plots of n_{pair}/n such as those in Fig. 5, one sees that $k_F \xi_0^{\text{coh}}$ allows a very useful and direct monitoring of the location of a system between the BCS and BEC limits. Notably, $k_F \xi_0^{\text{coh}}$ reaches a finite saturation number at the onset of the BEC, given by $k_F \xi_0^{\text{coh}} \approx 2.2$ for 2D and 1.5 for 3D (for the case of s -wave superconductors).

We end this section with Fig. 10(c) which presents a “zoomed out” view of the main figure in Fig. 10(b). This provides information about where one should expect the onset of the BEC. Importantly, the BEC regime appears to be associated with very large values of T^*/T_c . In this way, one might expect the BEC limit to be rather inaccessible.

D. Topology and quantum geometry in BCS-BEC

In this Review, we will see that current experimental candidates for BCS-BEC crossover tend to have values of T^*/T_c of the order of 2 or 3, and corresponding values of Δ/E_F on the order of 0.5. From Fig. 10(c), one might infer that these are not likely to be in the BEC regime. There is, however an exception having to do with flat-band, topological systems. These may be relevant to the recent discovery of 2D superconductivity in MATBG and MATTG where there are claims [117–119] that these flat-band systems are somewhere between BCS and BEC (MATBG) and possibly even beyond and within the BEC regime (MATTG).

Experimentally, when twist angles in these graphene systems are associated with very flat bands, this seems to correlate with the highest transition temperatures. There is, however, a subtle and important feature here. In flat-band superconductors, pair hopping, like single-particle hopping, is also suppressed [120–122]. As a consequence, the pair mass M_{pair} becomes large and the superfluid stiffness is small. This would lead to a vanishing T_{BKT} in the extremely flat-band limit, were it not for multi-band/multi-orbital effects.

Moreover, it has been emphasized [121] that these latter interband contributions (which work to decrease M_{pair}) can be amplified in the presence of nontrivial band topology. This occurs through so-called quantum geometric effects.

Such multiband effects have been incorporated into a 2D s -wave BCS-BEC framework [122] where a phase diagram with the usual superconducting dome is found, as shown in Fig. 11(a). The model topological Hamiltonian yields two bands, whose bandwidth is much smaller than the inter-band energy separation. The calculated phase diagram resembles that obtained from Monte Carlo results [123] using the same model Hamiltonian.

Importantly, this phase diagram can be used to extract the ratio T^*/T_{BKT} along with the number of bosons n_{pair}/n , as shown in Fig. 11(b); both these variables are plotted as a function of renormalized interaction strength. The quantity n_{pair} provides a ready indication of where the BEC sets in, as here n_{pair} first reaches $n/2$.

At the transition point to the BEC regime (indicated by the arrows), the interaction strength U is on the order of the entire conduction band width. Correspondingly, $\Delta/E_F \sim 3$ as shown in Fig. 11(c), which is not so different from the single band result in Fig. 10(c). On the other hand, because of quantum geometry, T_{BKT} is substantially enhanced by inter-band effects while T^* is almost unaffected, leading to a smaller and physically more accessible value of $T^*/T_{\text{BKT}} \sim 5$. This behavior is summarized in Fig. 11(c), where the BEC onset point is indicated by the arrow. This provides a counterpart plot of Fig. 10(c) but here for a multi-band, topological case. We note that the value of Δ/E_F at the BEC onset is non-universal. For a topological band structure with an extremely flat conduction band [122], Δ/E_F can be as large as 30.

The above contrast leads us to the interesting conclusion that in the presence of flat bands and non-trivial band topology a BEC phase can potentially become more accessible, as it leads to a moderate size for T^*/T_{BKT} . We emphasize that these effects derive from the participation of more than one band in the superconductivity and note that there are other, rather different approaches in the literature which also treat BCS-BEC phenomena in multi-band systems both analytically [124, 125] and numerically [126].

VI. STRONGLY DISORDERED CONVENTIONAL FILMS: TWO ENERGY SCALES AND A PSEUDOGAP

We return to Fig. 10(b) noting that this figure presents a unique signature of 2D pseudogap effects associated with a strong-pairing mechanism. It may seem surprising, but strong disorder can lead to similar pseudogap effects in 2D superconducting films [127]. However, the parameters governing these dirty thin films are very different from those indicated in Fig. 10(b). In understanding the origin of this other pseudogap, it is important to recall that 2D superconductors have a propensity for manifesting a separation of the two energy scales T^* and T_{BKT} which can be thought of as corresponding to the onset temperatures

for amplitude and phase coherence, respectively. As an important signature, those conventional superconducting films in which the two temperature scales are well separated due to disorder [127, 128] will have rather small values of Δ/E_F .

While the distinctions between the two scenarios for a pseudogap (strong pairing and strong disorder) should be obvious, a number of phenomenological similarities are rather striking. Most notable among these are the reported observations of charge $2e$ pairs [67, 129], the contrasting behavior of Andreev and conventional tunneling [130, 131], and the observations of boson or pair localization [86, 89].

The behavior found rather generically for a highly disordered 2D superconductor is illustrated in Fig. 12 which represents an experimentally determined phase diagram [132] with temperature on the vertical axis and disorder measured through $k_F l$ on the horizontal axis. Here k_F is the Fermi wavevector and l is the mean-free path. In Fig. 12, the superconducting state is shown in orange, the pseudogap state in red, and the normal-state metal in white. Also indicated are the temperatures T^* and $T_c = T_{\text{BKT}}$.

There are three demarcated regions. At very small disorder (region I) a pseudogap is absent and $T^* \approx T_c$, while as disorder increases (region II), T^* separates from T_c and is relatively independent of the disorder strength, while the transition temperature (which is more sensitive to the undermining of coherence) rapidly decreases. Finally in region III, T_c vanishes although there are indications that pairing persists. The two temperatures become distinct at a critical value of $k_F l$.

These experiments on NbN are reasonably generic and similar observations have been made for TiN and InO_x as well, where [127] the authors claim that a pseudogap appears to be present which reflects the existence of paired electrons above T_{BKT} . Importantly, this pseudogap is found to be continuously and directly transformed into a superconducting gap below the transition.

An interesting set of parallel experiments [128] shown in Fig. 13 was performed on Pb films by a group at Tsinghua University, who determined the experimental phase diagram obtained by studying crystalline and atomically flat Pb films, now as a function of variable thickness. In Fig. 13, temperature appears on the vertical axis and increasing thickness on the horizontal axis. Here the superconducting state is shown in green, the ‘‘fluctuating’’ or pseudogap state in blue (where non-superconducting Cooper pairs are said to exist) and the normal-state metal in yellow. The solid symbols represent superconducting or phase-coherent order, as determined by transport with an onset at $T_\phi \equiv T_{\text{BKT}}$; the open symbols represent the pairing transition ($T_\Delta \equiv T^*$), which is established by tunneling spectroscopy.

From Fig. 13 one can infer that the pairing temperature remains nearly constant with variable thickness, while the coherence temperature is strongly depressed. This appears to suggest that disorder may be playing a role⁴, as supported by the sheet resistance data measured by the same group.

⁴Since T^* represents a mean-field transition temperature of an s -wave

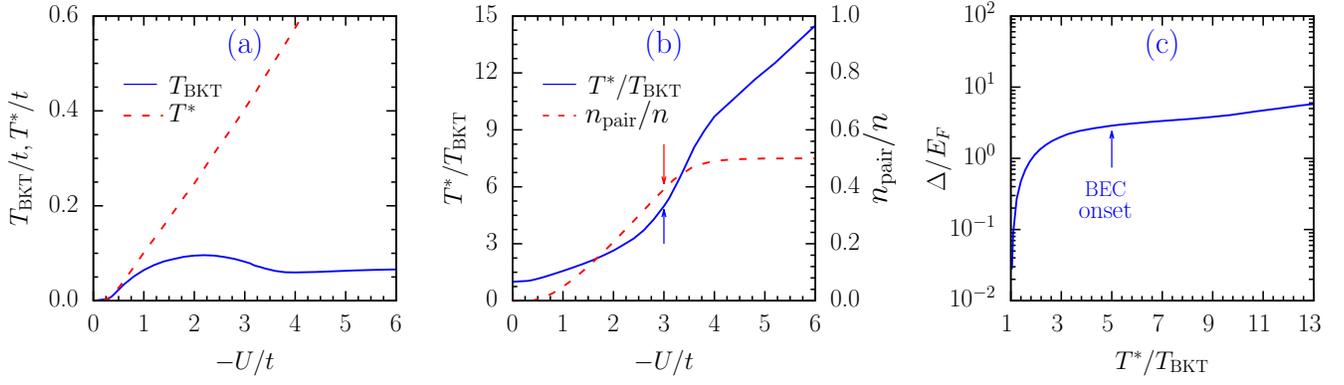


Figure 11. Flat band and quantum geometric effects in the BCS-BEC crossover theory [122] showing (a) T_{BKT} and T^* for a 2D topological band structure. Panel (b) presents a plot of T^*/T_{BKT} as well as the number of pairs as a function of attractive interaction strength. The BEC onset, determined from $\mu(T=0) = 0$, is indicated by arrows. Panel (c) presents plots analogous to Fig. 10(c), but here the BEC appears with a similar Δ/E_F and considerably smaller T^*/T_{BKT} . Here T^*/T_{BKT} is reduced by quantum geometric effects which substantially increase T_{BKT} without affecting T^* . A tight-binding bandstructure for a square lattice (with t the nearest-neighbor hopping) leads to two energy bands whose width is ≈ 0.2 times the inter-band separation. Here $n = 0.3$ is the electron density per square lattice site.

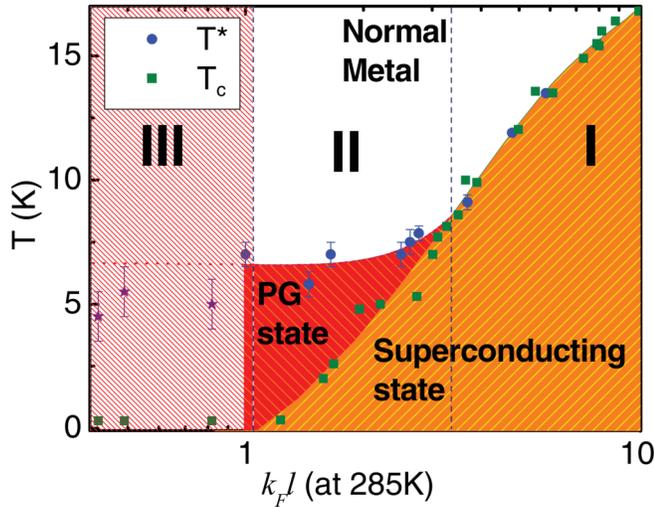


Figure 12. Experimental temperature scales as a function of mean-free path $k_F l$ in disordered NbN films [132]. The value of $k_F l$ is determined from resistance and Hall-coefficient measurements at $T = 285\text{K}$. With increasing disorder, or sufficiently small $k_F l$, a pseudogap phase appears associated with $T^* \neq T_c$ in region II, while in region III, T_c is zero although pairing likely persists in this insulating phase.

By contrast, it is reasonably well established that, quite generally, T_{BKT} decreases with decreasing thickness in 2D films [134], although there is no consensus on the extent to which disorder is the only relevant mechanism. The central point, then, is that pairs form at higher temperatures than

superconductor, this should satisfy Anderson's theorem [133] of disordered superconductivity; T^* is thus expected to remain relatively robust in the presence of disorder that does not break time-reversal symmetry, provided that the effective pairing interaction is not strongly affected by localization effects.

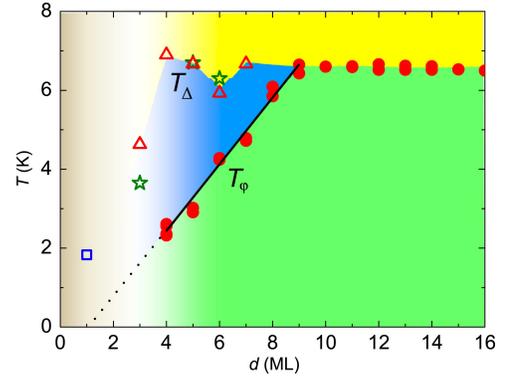


Figure 13. Experimental behavior of characteristic temperatures $T^* \equiv T_{\Delta}$ and $T_{\phi} \equiv T_{\text{BKT}}$ as a function of increasing thickness of Pb films [128]. A more extensive analysis of the resistivity (see text) suggests that these evident pseudogap effects are likely associated with high disorder, rather than strong pairing correlations.

those at which they exhibit superfluidity. Equivalently, at T_{ϕ} , while phase coherence is destroyed, the superconducting gap remains non-zero. Note that for Pb, the two characteristic temperatures merge in the 3D regime, as is the hallmark of a “conventional” bulk superconductor.

A key finding of the Tsinghua group [128] pertains to the voltage-current (V - I) characteristics which provide an alternative method for deducing the pairing onset temperature T^* . We emphasize that this “short-cut” procedure should be applicable to all 2D superconductors. More precisely, the authors have shown that V - I plots of this type can be used to *simultaneously* measure the two important energy scales T^* and T_{BKT} . This is illustrated in Fig. 14 where voltage-current plots are presented for a range of different temperatures in one particular Pb thin film.

More specifically, it is well known [108] that estimates based on V - I curves allow one to determine the BKT transition which occurs when the condition $V = I^{\alpha}$ is

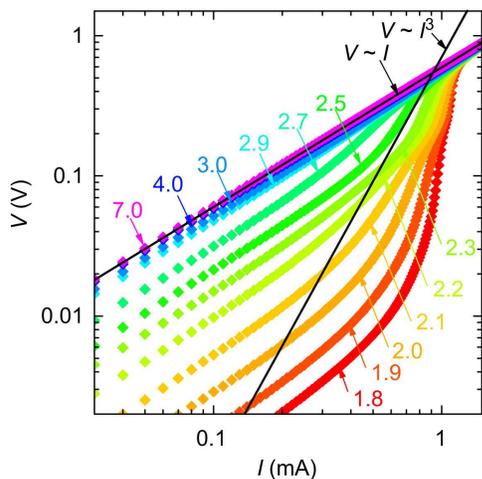


Figure 14. V - I isotherms on a log-log plot associated with the Pb films in the previous figure [128]. Each curve is labeled by its temperature and a straightforward analysis identifies T_{BKT} with the $V \sim I^3$ black line. One sees the resistance displays a continuous evolution towards Ohmic behavior with increasing current as the temperature is raised to the pairing onset temperature T^* , here identified to be 7 K (the $V \sim I$ black line) for a Pb film of a particular fixed thickness.

satisfied with a particular value of $\alpha = 3$. Importantly, the authors in the Pb experiments [128] have pointed out that one can also obtain the pairing onset temperature, T^* , from V - I plots. This is associated with the recovery of fully Ohmic behavior shown in Fig. 14 by the $V \sim I$ black line.

While this observation could seem intuitively obvious, the authors have made the last point more convincing by accompanying their analysis with more direct measurements of the pairing gap through STM experiments which yield $\Delta(T)$ from which they infer T^* . We caution by noting that one should take care in establishing the “Ohmic recovery” temperature as it involves the behavior of the entire V - I curve.

VII. APPLICATION OF BCS-BEC IN THE LITERATURE (BEYOND FERMI GASES)

A. BCS-BEC in the iron chalcogenides

Considerable attention has been paid to superconducting properties of the iron chalcogenides [135–141] where there appears to be growing evidence that FeSe and isovalent substituted $\text{FeSe}_{1-x}\text{S}_x$ and $\text{FeSe}_{1-x}\text{Te}_x$ may be in the BCS-BEC crossover regime. These systems, in which the characteristic electronic energy scales are anomalously low, appear to exhibit strong pairing effects, but not because of two dimensionality or because the pairing “glue” is itself anomalously large on an absolute scale. Rather, the attractive interaction is large when compared to the characteristic very low Fermi energies. Also present, and possibly relevant are nematic effects [140, 142] associated with broken rotational symmetry (but preserved translational symmetry). FeSe is

a layered anisotropic material; it is also a compensated semi-metal, with roughly equal densities of electron and hole carriers. This leads to both electron and hole pockets and a more complicated scenario for BCS-BEC crossover.

Adding to the support for a BCS-BEC crossover picture is the fact that in the iron chalcogenides [140] the characteristic Fermi energies and zero-temperature gap sizes are comparable. STM and STS experiments indicate gap sizes of the order of $\Delta_1 \approx 3.5\text{meV}$ and $\Delta_2 \approx 2.5\text{meV}$, for the two bands. From this it follows that the ratios of the pairing gaps to transition temperatures ($T_c \approx 9\text{K}$) in FeSe are large, of the order of $2\Delta_1/k_B T_c \approx 9$ and $2\Delta_2/k_B T_c \approx 6.5$, well beyond the BCS value of 3.5. The Fermi energies associated with the two nearly cylindrical Fermi surface sheets are anomalously small, of the order of $E_F \approx 10 \sim 20\text{meV}$ for the hole-like Fermi surface [140]. Importantly this leads to estimates of $T_c/T_F \approx 0.04 \sim 0.08$, which is larger than seen, for example, in the cuprate superconductors. This analysis has led many to conclude that these superconductors are well outside the strict BCS regime.

ARPES experiments [142] on bulk FeSe show that rather than the characteristic back-bending associated with conventional BCS superconductors, there is instead a flat dispersion near $\mathbf{k} = 0$, which appears to be more typical of the crossover regime. This flat-band feature is even more enhanced with the addition of sulfur.

Of considerable importance is the characteristic correlation length extracted from magnetic field data [136] which is argued to be small, of the order of $k_F \xi_0^{\text{coh}} \approx 1 - 4$. One can deduce from these numbers that FeSe superconductors are most likely not in the BCS regime. One should also compare with earlier theoretical estimates [Fig. 10(c)] of $k_F \xi_0^{\text{coh}}$ which found a BEC saturation value of approximately 2 to 3. Despite these rather comparable numbers, we caution, however, that important diagnostic information also comes from vortex imaging using scanning tunneling microscopy. This derives from the subgap fermionic states which are inside the vortex core. The observation of Friedel-like oscillations [139, 143] suggests that fermionic degrees of freedom are still present in bulk FeSe and thus these superconductors are not yet in the BEC regime.

Also notable is that there are enhanced superconducting fluctuation effects [135] in FeSe. This enables identification of a characteristic temperature T^* where, in particular, diamagnetism sets in. Figure 15 presents a plot of this “unprecedented, giant” diamagnetic response. The inset serves to emphasize the key point that the diamagnetic fluctuation regime in FeSe is considerably wider than predicted from the conventional fluctuation theory of Aslamazov and Larkin [144]. It is argued that this provides evidence for preformed pairs associated with BCS-BEC crossover, as fluctuation effects are expected to be amplified. Similarly, studies of the DC conductivity show that the expected downturn behavior is observed. Additionally, NMR experiments [140] show the expected suppression of $1/(T_1 T)$ around T^* , although there seem to be [145] none of these large fluctuation effects in the heat capacity.

There has also been a focus on crossover from BCS to BEC

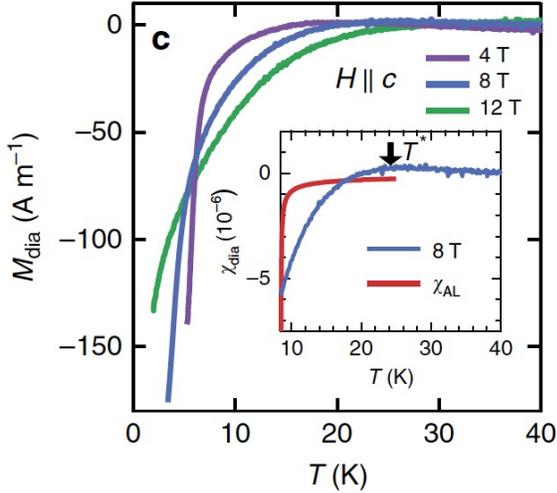


Figure 15. Diamagnetic magnetization response [135] in bulk FeSe as a function of temperature at different magnetic fields. The inset presents a comparison of the diamagnetic susceptibility with the predictions of Aslamazov-Larkin (AL) theory [144], showing a very extended range of fluctuations.

in a slightly different iron chalcogenide [146] $\text{Fe}_{1+y}\text{Se}_x\text{Te}_{1-x}$ where chemically doping the carrier concentration, through decreasing y , introduces an increased ratio of Δ/E_F , where E_F can be as small as a few milli-electron volts. Here, for example, there are claims⁵ based on figures such as Fig. 16 that as Δ/E_F increases, the dispersion of the peak in ARPES evolves from the characteristic back-bending behavior seen in the BCS regime to a BEC-like signature with a gap minimum at $\mathbf{k} = 0$.

All of this would make a nice illustration of superconductivity in the intermediate and even strong coupling regime were it not for the fact that STM/STS experiments do not support the existence of a spectroscopic pseudogap [140] in this class of compounds. Understanding this behavior is still a work in progress; it can be speculated that the multiband character of the iron chalcogenides may be relevant here. Issues such as inter-band pairing may also be playing an important role.

B. BCS-BEC in interfacial superconductivity

A great deal of excitement has been generated recently in studies of interfacial superconductivity [141, 147–160], particularly involving the iron chalcogenide FeSe. Here one sees an unexpected and dramatic enhancement of the pairing onset temperature [160] in interfacial monolayer FeSe. While the early literature [153, 159, 161] did not often distinguish this pairing gap onset from that of coherent superconductivity,

⁵There are complications in this analysis due to the vicinity of a heavy d_{xy} band which may affect the interpretation

it is now becoming clear that this system is associated with a large pseudogap, as well as a sizeable BKT transition temperature.

Indeed, it was discovered in 2012 that one-unit-cell-thick (1UC) FeSe grown on SrTiO_3 exhibits a gap [162] which survives up to 60 – 70K. This remarkable gap onset temperature is one order of magnitude higher than the T_c of bulk FeSe, and it has inspired an enormous effort to reveal the mechanism driving the interfacial enhancement. Due to the extreme air sensitivity, it has been challenging to perform traditional resistivity measurements. FeTe-capping or *in situ* transport measurements have made it possible to characterize the T_c from the resistivity transition. Among these measurements, except for a singular study which reported a T_c of 109 K, all other transport studies reported a resistivity onset associated with coherent superconductivity at $T < 45\text{K}$.

Recent work by one of the coauthors [163] combined *in situ* ARPES and *in situ* transport measurements to simultaneously characterize the spectroscopic and resistive transitions (Fig. 17). The former is sensitive to the presence of a pseudogap which can be associated with pairing while the latter probes superconductivity. The bandstructure of the 1UC FeSe is somewhat simpler than in the bulk system. Only electron-like Fermi surfaces are identified by ARPES near the Brillouin zone corners, with a Fermi energy $E_F \approx 60\text{meV}$ [164]. An excitation gap $\Delta \approx 15\text{meV}$ is observed at 12K and persists up to 73K. This leads to a ratio of Δ/E_F of the order of 0.25. The coherence length from vortex mapping is about 2nm [165], which suggests $k_F \xi_0^{\text{coh}} \approx 4$. This places 1UC FeSe/ SrTiO_3 firmly in the BCS-BEC crossover regime, but not yet in the BEC.

A second example of interfacial superconductors which has been interpreted in terms of a possible BCS-BEC crossover [67] scenario corresponds to a superconductor formed within the conducting 2D interface between two band insulators, LaAlO_3 and SrTiO_3 . This belongs to the class of superconductors with anomalously low carrier density. Indeed, it is argued that this 2D superconductor is similar in many ways to the behavior in 3D doped SrTiO_3 , and also has features of the high T_c copper oxides. The phase diagram [147] shown in Fig. 18 is analogous to the cuprates in many ways; additionally there are claims of preformed pairs in both. In the two cases the gap onset temperature does not follow T_c in the underdoped region but increases with charge carrier depletion.

This heterostructural system is particularly useful as it can be tuned continuously through gating. There is a superconducting dome along with a pairing gap Δ , which survives up to $T^* \approx 500\text{mK}$ [147] for the 2D carrier density $n \sim 0.02$ per unit cell. At $T = 0$, $\Delta \approx 65\mu\text{eV}$. Moreover, with decreasing temperature, the pseudogap Δ evolves smoothly into the pairing gap within the superconducting phase. Also supporting the pairing-onset interpretation of T^* is that the ratio of $\Delta(T = 0)$ to T^* remains close to the BCS prediction; at more general temperatures the pairing gap follows the BCS-like mean-field temperature dependence.

Using an atomic force microscope (AFM) tip, the Levy

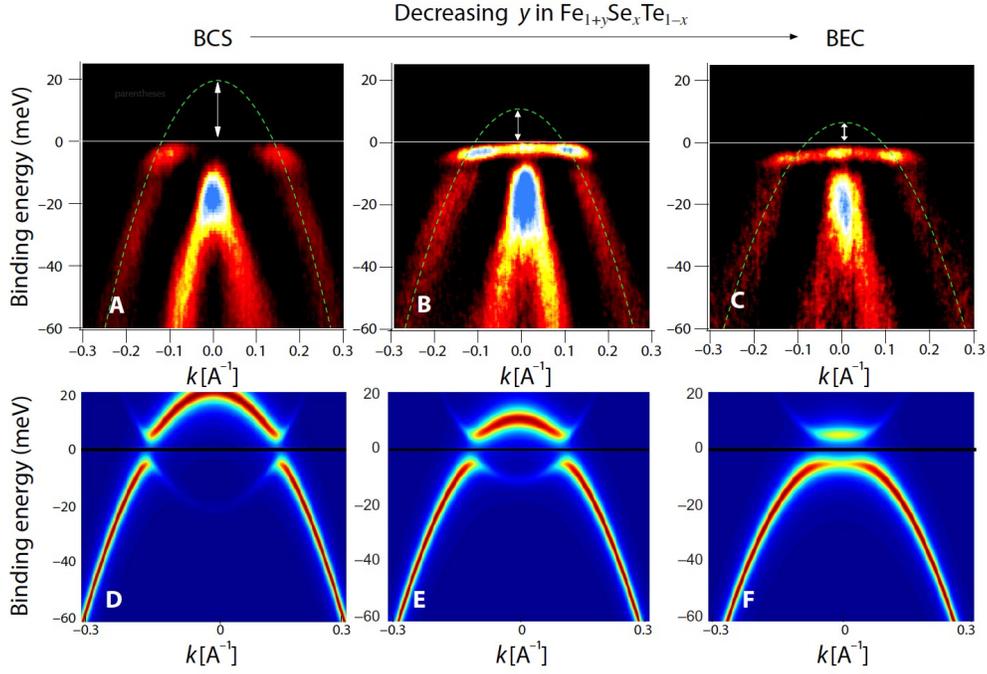


Figure 16. ARPES signatures in $\text{Fe}_{1+y}\text{Se}_x\text{Te}_{1-x}$ where chemically doping the carrier concentration is through decreasing y . Shown in (A-C) are ARPES spectra [146] for three samples in order of decreasing y from left to right. The green dashed line is the best fit to the data. The three lower panels (D-F) are theory plots using parabolic band dispersion and other model parameters.

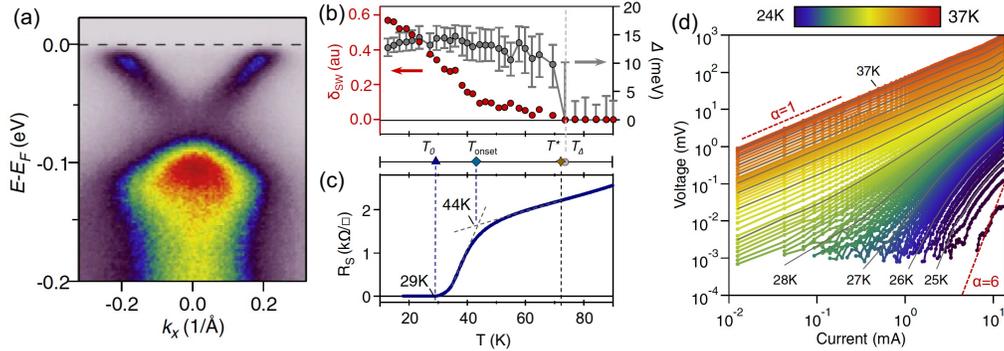


Figure 17. Combined ARPES and transport studies [163] on 1UC FeSe/SrTiO₃ showing (a) ARPES data near the M point of the Brillouin zone taken at 12K. (b) Extracted values of gap Δ and spectral weights δ_{SW} at the Fermi level. (c) Resistivity measurements. (d) Voltage-current relationship.

group [149] was able to draw single-electron transistors on the $\text{LaAlO}_3/\text{SrTiO}_3$ interface. Importantly, this enabled observation of preformed pairs which persist up to 900mK, well above the transition temperature which ranges between 200 – 300mK.

These temperature scales, however, pose some concerns about interpreting the nature of interfacial superconductivity in $\text{LaAlO}_3/\text{SrTiO}_3$. The Fermi energies of various t_{2g} bands have been characterized by soft X-ray ARPES [166] and found to be around 50meV for the d_{xy} orbital band [167,

168]⁶, which leads to a rather small ratio of $\Delta/E_F \sim 10^{-3}$. This observation, indicative of a more BCS-like system, seems to be incompatible with a strong pairing crossover scenario. Even more persuasive of this incompatibility is the additional fact that the measured coherence length is large, of the order of 30 – 70nm [170], leading to $k_F\xi_0^{\text{coh}} \sim 30 - 70$.

⁶We note that in the literature it is still being debated whether the d_{xy} orbital actively participates in the superconductivity or not (see, for example [169]). Using the d_{xz}/d_{yz} orbital band for E_F would lead to a relatively larger $\Delta/E_F \sim 0.05$. Our choice of the d_{xy} band for E_F is based on the consistency between the estimated Δ/E_F and $k_F\xi_0^{\text{coh}}$.

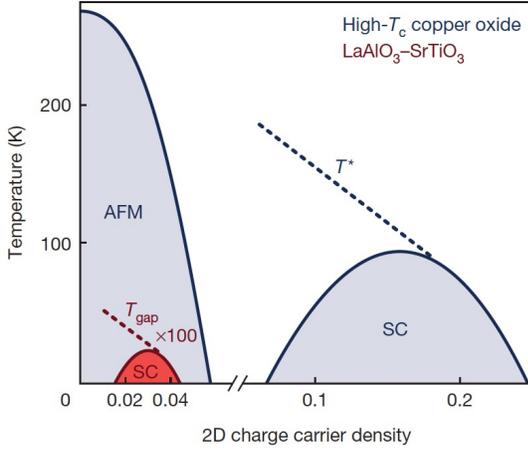


Figure 18. Interface superconductivity in $\text{LaAlO}_3\text{-SrTiO}_3$ (shown in red) which is tuned with an electric gate field. The figure [147] represents a comparison between high- T_c cuprate superconductors and the n-doped interface superconductors. In this figure the horizontal axis is the carrier density per unit cell. SC: superconducting; AFM: antiferromagnetic. The end point of the $\text{LaAlO}_3\text{-SrTiO}_3$ SC dome on the underdoped side is a quantum critical point that separates the superconducting from an insulating phase [150].

This is based on previous estimates in the literature for $k_F \approx 0.1 \text{ \AA}^{-1}$ [168].

At the same time this interfacial system does not obviously fit into the class of highly disordered superconductors discussed in Sec. VI as for example the behavior of T^* is different from that observed for other materials in this class. Thus we are left to conclude that, at this stage, it is difficult to firmly categorize the nature of interfacial superconductivity in $\text{LaAlO}_3/\text{SrTiO}_3$, but a strong pairing mechanism does not seem to be operative. Possibly relevant to these observations are theoretical calculations [171], albeit for 3D s-wave systems, which reveal that disorder induced superconductor-insulator quantum phase transitions can occur in the BCS regime; here the superconducting order is destroyed leading to an insulating phase which is caused by a residual pseudogap.

C. BCS-BEC in magic-angle twisted bilayer and trilayer graphene

There is growing support that MATBG [117] as well as MATTG [118, 119] superconductors exhibit BCS-BEC crossover features. Notably, these are very clean systems, associated with a BKT transition. One piece of cited evidence is based on the relatively large values of T_{BKT}/T_F . These were reported in the initial groundbreaking paper [117] as well as in subsequent work [119, 130, 172]. Such estimates are, in turn, based on V - I plots which allow one to determine the BKT transition that occurs when $V = I^\alpha$ with a specific value of $\alpha = 3$. As a caution we note that the ratio T_{BKT}/T_F should not be viewed as a proxy for the fraction of electrons involved in superconductivity; in the BEC regime,

this parameter becomes very small.

More recent [130] tunneling experiments (which are summarized in Fig.19(a)) on MATBG help to make the association with BCS-BEC stronger; they have presented clearer indications of an extensive pseudogap regime in the phase diagram, as can be seen from the figure. These STM experiments suggest [130] an anomalously large value for the ratio $2\Delta/(k_B T_{\text{BKT}}) \approx 25$, which can be viewed as representative of strong pseudogap effects, equivalently associated with large T^*/T_{BKT} . Adding support to a BCS-BEC scenario is the presence of another much smaller energy-gap scale associated with point-contact Andreev tunneling which is only present in the ordered phase where there is phase-coherent order.

The results from this STM tunneling [130] provide a value for $\Delta \approx 1.4\text{meV}$ in MATBG. In an earlier section we pointed out that V - I measurements in 2D films can be used [128] for estimates of T^* . One can infer from these data [117] that $T^* = 3 \sim 5\text{K}$, which is obtained from the Ohmic recovery temperatures⁷. This should be compared with the transition temperature $T_{\text{BKT}} \approx 1\text{K}$ and the Fermi energy of the bilayer system which is estimated to be $T_F \approx 20\text{K}$ [117]. The resulting relatively large ratios of T^*/T_{BKT} and Δ/E_F suggest that this is a superconductor in the intermediate BCS-BEC crossover regime.

Indeed, based on the claims [130] that the measured $2\Delta/T_c \approx 25$ and that MATBG has some similarities with the high T_c superconductors, it is striking to observe similar characteristic numbers in Table III (Appendix C) for the most underdoped cuprate. Based on the predictions for d -wave BCS-BEC theory, we report there that in this case $2\Delta/T_c \approx 25$ and that $T^*/T_c \approx 5$.

The situation for MATTG appears to be somewhat clearer and provides more quantitative information. Some pertinent results [118, 119] are summarized in Fig. 19, where panels (c) and (d) address very useful coherence-length experiments [118] based on the magnetic-field dependence of the superconducting transition temperature. Fig. 19(c) shows this published data for ξ_0^{coh} as well as the inter-particle distance d as a function of the band filling factor ν , along with the transition temperature T_{BKT} .

The experimentally observed ratio ξ_0^{coh}/d (Fig. 19(d)) can be compared with theory in Fig. 19(e), where ξ_0^{coh}/d is plotted as a function of T^*/T_c . (This is similar to the inset in Fig. 10(c)). We highlight that the plot in Fig. 19(d) and the theory plot in Fig. 19(e) are for different horizontal axis variables; however, a direct association of the two would allow one to relate the important ratio T^*/T_c with the filling factor ν , hence completing the T^*/T_c versus ν phase diagram. From the data in the figures it follows that the relevant parameters for $\nu \gtrsim -2.5$ suggest that MATTG also belongs in the intermediate BCS-BEC crossover regime.

⁷Ideally one could arrive at more accurate numbers by making systematic V - I plots over finely separated temperature intervals in order to more precisely establish the temperature for the Ohmic recovery, corresponding to T^* .

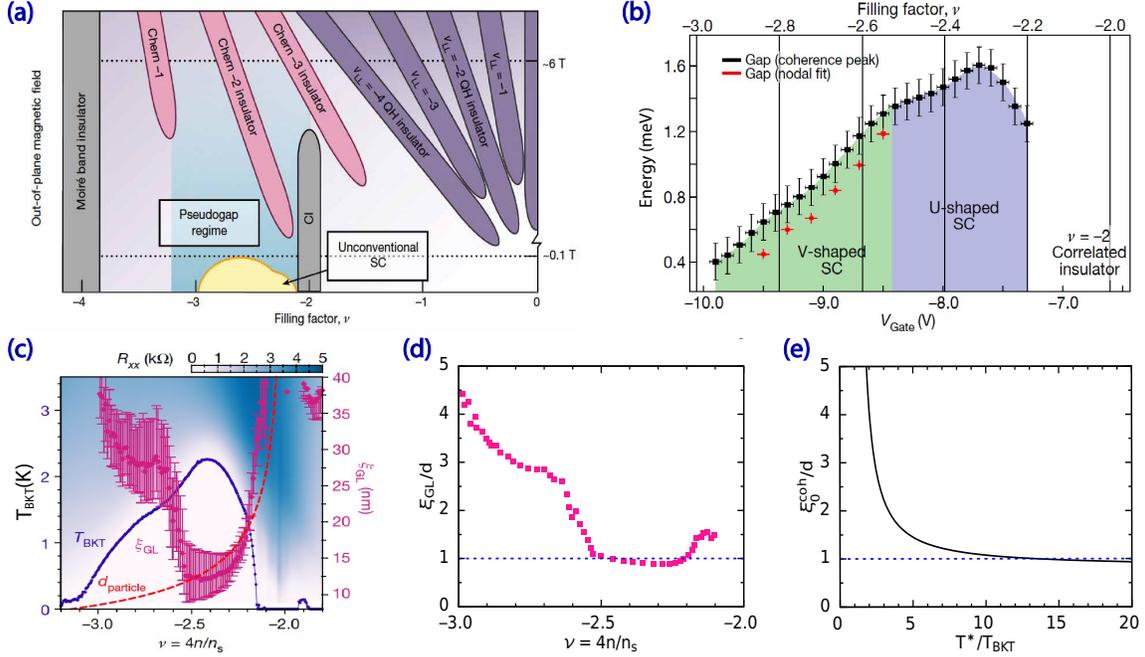


Figure 19. Superconducting properties of MATBG and MATTG. (a) Phase diagram of hole doped MATBG. SC stands for superconductor. The electron filling factor $\nu = 4n/n_s$, where n is the carrier density defined by the applied gate voltage and n_s is the corresponding n when the lower four-fold degenerate moire flat band is fully filled. In this diagram, a very large pseudogap regime, indicated in light blue, is determined by combining conventional STM and point-contact Andreev tunneling spectroscopy [130]. (b) Gap size Δ versus the gate voltage V_{Gate} (and the filling factor ν) for MATTG. The Δ is measured from conventional STM tunneling at low temperatures. The data points are extracted from the separation between coherence peaks at the half-way point (black squares) and from a nodal gap fit (red dots) [119]. In the green and violet regions the dI/dV curve exhibits a V shape and a U shape, respectively. (c) The $T - \nu$ phase diagram of MATTG at displacement field $D/\epsilon_0 = -0.5 \text{ V nm}^{-1}$, along with the curves of the interparticle distance $d \equiv d_{\text{particle}}$ and the coherence length ξ_{GL} [118]. Here $d = 1/\sqrt{n^*}$ where n^* is the effective carrier density that can be deduced from quantum oscillation and Hall density measurements. Note that n^* is different from the density n . (d) The ratio ξ_{GL}/d as extracted from (c). (e) The ratio ξ_{GL}/d calculated theoretically as a function of T^*/T_{BKT} for a 2D s-wave superconductor.

Recent tunneling experiments [119] provide additional important quantitative information about MATTG with a focus on the gap energy scale as plotted in Fig. 19(b) as a function of ν . These studies indicate $T^* = 7\text{K}$ at the ν value where the gap is maximum. Additional parameters are: $T_{\text{BKT}} \approx 2.25\text{K}$ [118] with the estimated Fermi temperature given by $T_F \approx 30\text{K}$.

Overall, there appears to be compatibility between the ξ_0^{coh} data from the MIT group and pairing gap experiments [119] shown in Fig. 19(b). Making use of the estimates of E_F based on quantum oscillation experiments [118] it follows that the ratio Δ/E_F exhibits a similar trend as ξ_0^{coh} , changing from more BCS-like behavior at $\nu \approx -3$ to characteristic crossover behavior at $\nu \approx -2.2$. We note that interpretations of these tunneling experiments [119] have suggested that the BEC regime is reached around the upper half of the T_{BKT} dome at $\nu \gtrsim -2.5$, although this is not straightforward to reconcile with the presence of coherence peaks in the tunneling data.

Finally, it should additionally be noted that the theory plot of the coherence length in Fig. 19(e) is for the s-wave case, while the experimental data seem to suggest a nodal form of superconductivity. Some aspects of crossover theory for the nodal case have been addressed in this Review

(in Sect. IV B)⁸, but one might additionally expect that other ingredients such as flat energy bands and quantum geometry (in Sect. V D) may play an important role as well in reaching an ultimate understanding of BCS-BEC crossover for MATBG and MATTG.

D. BCS-BEC for 2D gated semiconductors

There has been recent interest [173–175] in a group of layered nitrides, Li_xZrNCl , which are intrinsically semiconductors and exhibit superconductivity through Li-intercalated doping. These experiments impose control of the carrier density by use of ionic gating which provides access to very low carrier density systems that are otherwise inaccessible. Concomitantly the varying carrier number enables a tuning of the weakly- to strongly-coupled

⁸In the single band d-wave case, the counterpart of the curve in Fig. 19(e) looks qualitatively similar at very low density but will not reach BEC until a much larger T^*/T_{BKT} . No BEC is allowed at high densities.

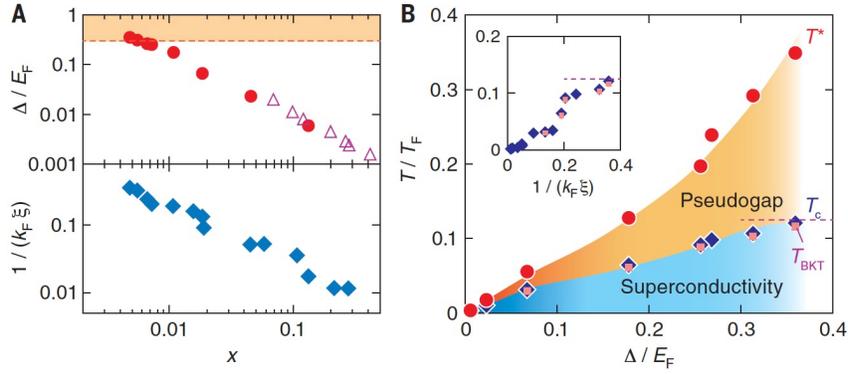


Figure 20. Experimental data [173] in electron-doped zirconium nitride chloride. The results shown here are from tunneling spectroscopy and DC resistivity measurements. The transition temperature T_c is defined as the midpoint in the resistivity curves, which is identified as T_{BKT} . The (in-plane) coherence length $\xi = \xi_0^{\text{coh}}$ is determined from the upper critical magnetic field.

superconducting regimes by controlling both the carrier density and simultaneously a dimensional crossover from anisotropic-3D to 2D. Both tunneling and resistivity measurements [173] yield systematic information about the detailed phase diagram of this system.

The phase diagram [173], shown in Fig. 20, indicates a pronounced pseudogap regime established from dI/dV measurements. This is particularly notable in the low-doping regime, where the system is more two dimensional. In particular, at extreme underdoping T_{BKT} shows a maximum of 19K. In the most underdoped sample probed, $\Delta/E_F \approx 0.3$, $T_{BKT}/T_F \approx 0.12$, and T^* is roughly $3T_{BKT}$.

A summary of experimental observations is presented in Fig. 20 as a plot in terms of T/T_F vs Δ/E_F with data points indicating T_{BKT} and T^* . The pseudogap and associated T^* were found to be largest when the carrier number was lowest. Here, for these large gap systems (which are in the strong-coupling limit) one finds the smallest coherence length, $k_F \xi_0^{\text{coh}} \approx 3$, as obtained from the upper critical fields. This behavior is compatible with the behavior of the theoretically determined coherence length shown in Fig. 10(c). In the opposite regime, at the highest electron doping regime one recovers more characteristic BCS behavior with $T_{BKT} \approx T^*$. We conclude that all of this adds up to a body of evidence which lends reasonably strong support to a BCS-BEC crossover description of these ionic gated superconductors.

E. Magnetoexciton condensates with BCS-BEC

The concept of condensation based on particle-hole pairs [176–178] should be thought of as a very natural extension of particle-particle pairing in superconductors. Indeed one usually invokes the same ground-state wave function as in Eq. (1) modified by the replacement of one of the electron operators with a hole operator and presuming that the two are associated with different bands. This subject has generated considerable excitement as one could conceive of such condensation as taking place at very high temperatures.

There are a number of subtle features, however, as the electrons and holes need to be sufficiently well separated so as to avoid recombination. Their number and effective masses also need to be equivalent, otherwise pairing can be impeded as this system behaves like a superfluid with population or mass imbalance.

An important configuration for arriving at exciton condensation involves quantum Hall fluids [179, 180], as was first implemented by Eisenstein et al. in a GaAs/AlGaAs heterostructure. Here two thin GaAs layers are separated by the AlGaAs spacer layer, which serves to mitigate electron-hole recombination processes. Because each layer forms a 2D electron gas, in the presence of a strong perpendicular magnetic field B , their energies are quantized into Landau levels (LL). These bilayer quantum Hall systems have the potential to realize novel quantum states that have no analog in a single layer. A relevant parameter for characterizing such states is d/ℓ_B , where d is the inter-layer spacing and $\ell_B = \sqrt{\hbar/eB}$ ($eB > 0$) is the magnetic length.

There has been a focus [179] on the interlayer coherent state observed in the zero or small interlayer tunneling limit and at total electron filling fraction $\nu_{\text{tot}} = \nu_1 + \nu_2 = 1/2 + 1/2 = 1$. Here, the electron filling fraction, $\nu_i = n_i(2\pi\ell_B^2)$, is defined for each individual layer with n_i the electron density of the i -th layer. Important questions such as whether there is a quantum phase transition separating the large and small d/ℓ_B limits have been raised [181–184], although recently [185–187] there has been the suggestion that the evolution of the state from the large to small d/ℓ_B might be understood as a crossover of BCS to BEC condensation of magneto-excitons.

This picture can be understood in terms of Jain’s composite fermions (CF) [188], where a CF can be roughly viewed as the original electron attached to two magnetic flux quanta (h/e). In the extreme $d \rightarrow \infty$ limit, the two layers decouple and each of them has a LL filling fraction $\nu = 1/2$ which can be described by a metallic state [189] of either electron-like or, equivalently, hole-like CFs with well defined Fermi surfaces.

At finite d one can then consider electron- and hole-like CFs from the two different layers forming inter-layer Cooper pairs, i. e., magnetoexcitons. Importantly, it is reasonable to

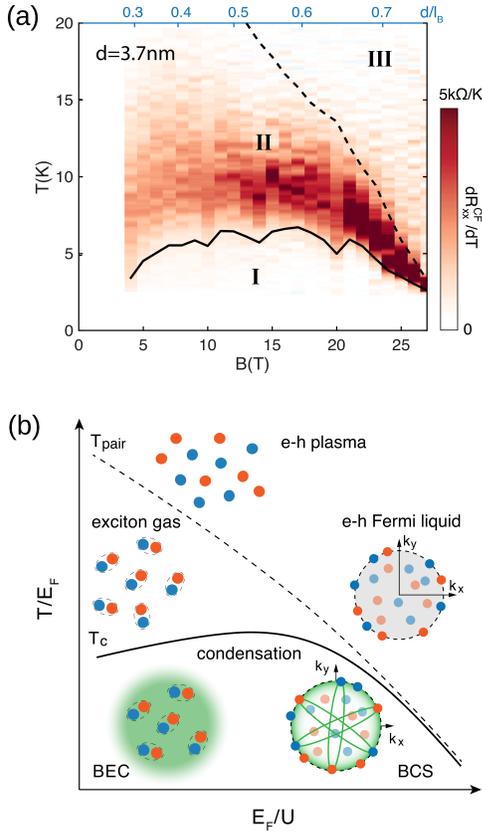


Figure 21. BCS-BEC for magnetoexcitons [185]. The color coding in panel (a) is associated with the temperature derivatives of the measured longitudinal resistance in the counterflow design. Hall drag and counterflow resistances are used to arrive at the dashed line, representing the pairing onset temperature T^* as a function of effective attraction/kinetic energy ratio (through the magnetic field B), and to infer T_c shown by the solid black line. (b) Schematic phase diagram expected for a magnetoexciton condensate. T_{pair} is the same as T^* .

assume that their effective masses are equal near $\nu = 1/2$, due to an approximate particle-hole symmetry. The pair formation is driven by an inter-layer attraction, U which is derived from the original interlayer Coulomb interaction between electrons, whose magnitude is $|U| \sim V_{\text{inter}} \sim e^2/(\epsilon d)$ ⁹, where ϵ is the background dielectric constant. At the same time the parameter E_{kin} , which represents the kinetic energy of a partially filled Landau state is set by the intralayer Coulomb repulsion [189], $E_{\text{kin}} \sim V_{\text{intra}} \sim e^2/(\epsilon \ell_B)$.

In this way the important ratio $|U|/E_{\text{kin}} \propto \ell_B/d$, which sets the scale of a BCS-BEC crossover can be tuned experimentally by varying either d or B . Large d or high

magnetic fields corresponds to the BCS-like limit, while the more BEC regime is present at small d or low magnetic fields (see Fig. 21). This BCS-BEC crossover picture is supported by recent measurements on graphene double-layer heterostructures [185, 191] Compared to the GaAs/GaAlAs double-layer experiments, this graphene bilayer system has an additional advantage as it allows the two graphene layers to be separated by a thin hexagonal boron nitride layer, which prohibits direct interlayer tunneling without introducing disorder.

Because the magnetoexcitons are neutral and cannot be probed in traditional electronic transport, two unconventional designs for resistance measurements have been employed to experimentally probe the magnetoexciton superfluidity via “counterflow” and “drag” experiments [179]. Figure 21 presents a summary of the results from these measurements for the double-layer graphene system [185].

In the counterflow configuration electric currents in the two layers are of the same magnitude but flow in opposite directions. The absence of dissipation due to “superfluidity” is associated with a vanishing R_{xx}^{counter} , which measures the longitudinal resistance. These experiments serve to determine the transition temperature T_c (solid black line) in Fig. 21(a).

A striking signature of magneto-excitonic superfluidity is a quantized Hall drag resistance at low temperature in the “drag” configuration. Here the electric current is fed only to one layer, while the Hall voltage drops are measured in both layers, from which one can define the usual Hall resistance, R_{xy} , for the current-driving layer. One can also define a Hall drag resistance, R_{xy}^{drag} , for the passive layer.

Both R_{xy} and R_{xy}^{drag} are expected to be quantized to the same value $h/(e^2\nu_{\text{tot}})$ at low temperature T . As T increases above T_c , R_{xy}^{drag} decreases monotonically. In Ref. [185] the important temperature scale, T^* is defined as the point where R_{xy}^{drag} drops to below 5% of $h/(e^2\nu_{\text{tot}})$. This T^* is plotted in Fig. 21(a) as the dashed black line. It is reasonable to associate the residual R_{xy}^{drag} at high temperatures with incoherent pair correlations between electron- and hole-like CFs. In this way one interprets T^* as the onset of electron-hole CF pair formation. While there are some uncertainties in the definition of T^* , a clear separation of the two temperature scales, T_c and T^* , is apparent from Fig. 21(a), which is to be compared to the schematic phase diagram sketched in Fig. 21(b).

What is not as clear is whether at the lowest applied magnetic field $B \approx 5\text{T}$ the system has reached the BEC regime, as suggested by the schematic figure¹⁰. In comparing with a prototypical example of BCS-BEC, as in the 2D electron gas it is useful to establish the magnitude of the effective Δ/E_F , which would be expected to become arbitrarily large in a more traditional BEC superconductor.

⁹When $d \ll \ell_B$, the inter-layer interaction is actually governed by $e^2/(\epsilon \ell_B)$, not $e^2/(\epsilon d)$. It should also be noted that the actual inter-layer interaction between CFs is not the same as V_{inter} . Instead, it is mediated by an emergent Chern-Simons gauge field that makes the renormalized interaction highly frequency dependent [182, 189, 190]. Here, we ignore these complications.

¹⁰Rescaling the measured T_c of the top panel by T_F , which can be estimated as $e^2/(\epsilon \ell_B)$, and plotting the obtained T_c/T_F as a function of B shows that this ratio has not passed the point where it starts to decrease with decreasing B even at $B \approx 5\text{T}$. It suggests that the system may still be in the crossover regime, not yet into the BEC, if we compare this trend of T_c/T_F to that for a 2D electron gas in Fig. 9

On the other hand, exact diagonalization studies [186] show that for the bilayer magnetoexciton system $\Delta \lesssim E_F$. This contrast highlights some of the key differences between traditional superconductors and the magnetoexciton bilayer that one needs to bear in mind in the interpretation of the phenomenology. It is clear that quantification of the exact behavior of T_c/T_F , and other quantities characteristic of BCS-BEC crossover, for the entire range of d/ℓ_B from ∞ to 0 requires further work, both theoretical and experimental.

One might speculate that, since one defining feature of the BEC regime is the disappearance of Fermi surfaces, a potentially useful future experiment is to directly probe the Fermi surface of CFs at $T_c < T < T^*$ for small d/ℓ_B , using geometric resonance techniques as employed in the determination of the Fermi wave vector of CFs for the single layer $\nu = 1/2$ state [192]. Achieving a number of these goals seems promising given the high tunability of the bilayer graphene heterostructure, as demonstrated by the new generation of experiments [185, 191].

VIII. APPLICATION TO THE CUPRATES

Attributing the cuprate pseudogap to preformed pairs as distinguished from a competing order parameter is admittedly highly controversial and this should not be viewed as a central component of this review. Here we focus principally on non-cuprate superconductors. Nevertheless, for completeness, it is useful to present the predictions concerning the cuprates which derive from one particular pre-formed-pair scenario – a BCS-BEC crossover perspective – and leave the reader to make their own assessments. The discussion presented here and in Appendices B and C should be viewed as a catalogue summary of some relevant theory literature. The interested reader can consult the cited papers to obtain more details.

A. Experimental evidence that BCS-BEC may be relevant to the cuprates

There is evidence, albeit far from conclusive, that the cuprates are intermediate between BCS and BEC. All indications are that, if this concept is applicable, these superconductors are on the BCS side and well away from BEC. This is consistent with the claims in a recent preprint [64], although these authors adopted a different definition of “crossover” associating it with proximity to a BEC. Indeed, there are several experiments which stand out as providing among the strongest support for a BCS-BEC-like description of the copper oxides.

ARPES measurements [193] reveal a Bogoliubov-like dispersion in part of the Brillouin zone which is away from the nodal Fermi-arc region. Importantly this is observed somewhat above T_c , as shown in Fig. 22. It is highly unlikely, and indeed inconsistent with the theory we are discussing, that this Bogoliubov dispersion continues up to much higher temperatures, near the onset of the pseudogap. Indeed, there

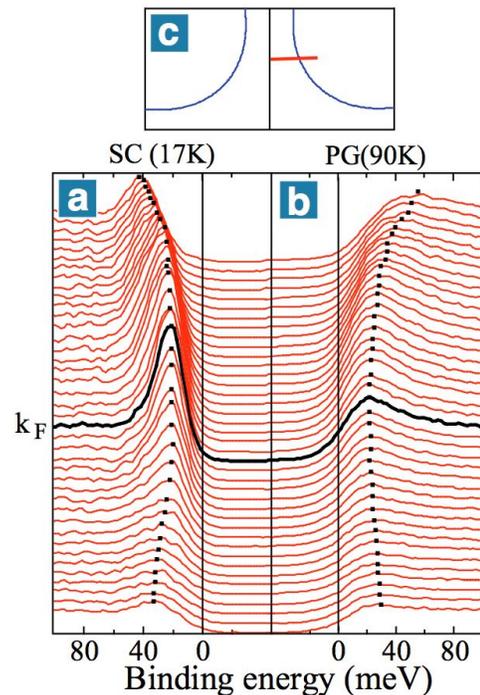


Figure 22. Experimental pseudogap ARPES data [193] showing backbending of the dispersion in the normal state (b), suggestively similar to that in the superconducting state (a).

are studies [77] that suggest this characteristic back-bending dispersion is absent well below T^* . But in the normal state, not too far from T_c , these experiments [193] provide indications that the presence of a pseudogap is associated with the same fermionic quasi-particles as are found in the ordered phase.

An additional, conceptually simple experiment involves STM studies which compare the ratio of the zero-temperature pairing gap to T^* . This ratio appears to be very close to the expected mean-field result [194, 195]. This associates the ratio of $\Delta(T = 0)$ and T^* in an analogous fashion as for the BCS prediction of $\Delta(T = 0)$ and T_c , and for a d -wave case.

There are additional classes of experiments which constitute less direct support, but which are worthy of note and will be discussed in this section. These involve (i) recent shot-noise measurements [197] which provide a more direct and quantitative signature of pairing above T_c . Through pair contributions to tunneling these shot-noise experiments indicate [197] that “pairs of charge $2e$ are present in large portions of the parameter space dominated by the pseudogap.” We caution here, however, that evidence [129] of $2e$ pairing may be found in the pseudogap phase of highly disordered, presumably weakly coupled 2D superconductors. In this way, $2e$ pairing is a necessary but not sufficient effect to establish BCS-BEC crossover.

(ii) Also relevant is the two-gap dichotomy [66, 72] in which there are distinctive temperature dependencies of the ARPES- or STM-associated gaps in the nodal and anti-nodal regions. In the BCS-BEC scenario this two-gap behavior

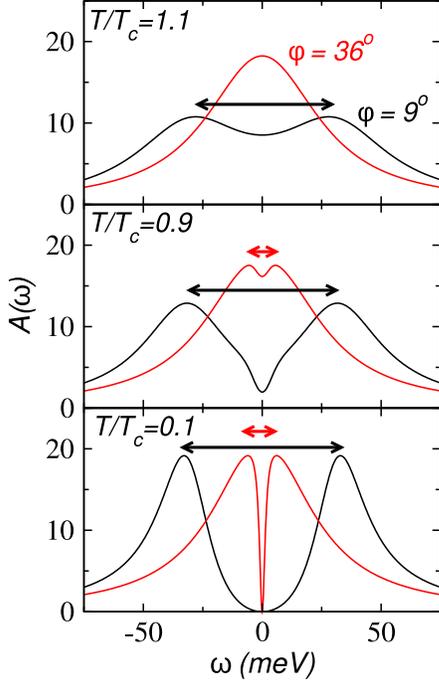


Figure 23. Calculated [196] spectral function $A(\varphi, \omega)$ at $T/T_c = 1.1, 0.9, 0.1$ (from top to bottom) for $\varphi = 9^\circ$ (black) and $\varphi = 36^\circ$ (red). Black and red arrows indicate size of the spectral gap, which is measured in ARPES. φ is defined in Fig. 25.

derives from the simultaneous presence of condensed and non-condensed pairs.

(iii) Additionally, an observed downturn [56] in the DC resistivity near or below T^* seems most naturally to be associated with the contribution from bosonic transport or from preformed pairs. Indeed this small downturn feature is often used as the canonical signature of T^* .

(iv) Finally, there is a notable similarity between many properties of a single layer cuprate material and that found for its counterpart in bulk systems [198]; this would seem to be compatible with the similarity contained in Eqs. (2) and (4).

We will discuss some of these experiments in the following subsections.

B. The spectral function: distinguishing condensed and non-condensed pairs

We first address the so-called “two-gap dichotomy” [66, 72] which pertains to the behavior of the spectral function where it should be clear that d -wave pairing plays an important role. In the BCS-BEC crossover scenario [1] the fermionic self energy which is measured in the spectral function has two contributions from non-condensed (pg) and condensed (sc)

pairs:

$$\Sigma(\omega, \mathbf{k}) = \frac{\Delta_{\text{pg}, \mathbf{k}}}{\omega + \xi_{\mathbf{k}} + i\gamma} + \frac{\Delta_{\text{sc}, \mathbf{k}}}{\omega + \xi_{\mathbf{k}}}. \quad (29)$$

It might be noted that because of these two components, this BCS-BEC scheme has Green’s functions which are similar to those in a highly regarded cuprate theory often called “YRZ” theory [199] after the authors Yang, Rice, and Zhang. In the BCS-BEC scenario one finds Fermi arcs whereas YRZ incorporates Fermi pockets [200].

In the normal state, a form [201] similar to Eq. 29 was shown to provide a reasonably good fit to ARPES data and insights into the Fermi arcs [202], when one also includes an additional single particle decay rate. How do the Fermi arcs originate? One should note that the non-condensed pairs have finite lifetime, in contrast to the condensate. This is particularly important for the case of d -wave pairing. If we consider cooling from above to below T_c , we see that the onset of the condensate gap Δ_{sc} in the fermionic spectral function is more dramatic in the nodal region where there is no normal state background gap already present. By contrast, in the antinodal region the onset of Δ_{sc} on top of a large Δ_{pg} has very little impact. Thus, as illustrated below, it is the temperature dependence of the nodal gap which reflects the onset of the ordered state.

More quantitatively [196, 201], one defines the spectral (or ARPES) gap as one-half the peak to peak separation in the spectral function. Figure 23 illustrates the temperature evolution of the spectral function for $\varphi = 9^\circ$ (close to the antinodes in Fig. 25) and $\varphi = 36^\circ$ (close to the nodes) at varying T/T_c from top to bottom. Above T_c (top panel) the well understood behavior [193, 203, 204] sets the stage for the normal phase which underlies the superconducting state in the next two panels. Here one sees Fermi arcs, which derive from the presence of a temperature independent broadening term γ in Σ_{pg} . When T is slightly below T_c (middle panel), a dip in the spectral function at $\varphi = 36^\circ$ suddenly appears at $\omega = 0$. At this ϕ the underlying normal state is gapless so that the onset of the additional component of the self energy via Σ_{sc} with long-lived pairs leads to the opening of a spectral gap.

By contrast, the presence of this order parameter is not responsible for the gap near the anti-nodes ($\varphi = 9^\circ$), which, instead, primarily derives from Δ_{pg} . Here the positions of the two maxima are relatively unchanged from their counterparts in the normal phase. Nevertheless, Δ_{sc} does introduce a sharpening of the spectral function, associated with the deepening of the dip at $\omega = 0$. When $T \ll T_c$ (lower panel), pairing fluctuations are small so that $\Delta(T) \approx \Delta_{\text{sc}}(T)$ and one returns to a conventional BCS-like spectral function with well established gaps at all angles except at the precise nodes.

C. Transport in the Cuprates

That the cuprates are highly resistive or bad metals [31] is important for understanding their transport properties. This is what allows the boson-related downturn for transport at T^* in the resistivity, a canonical signature of the pseudogap

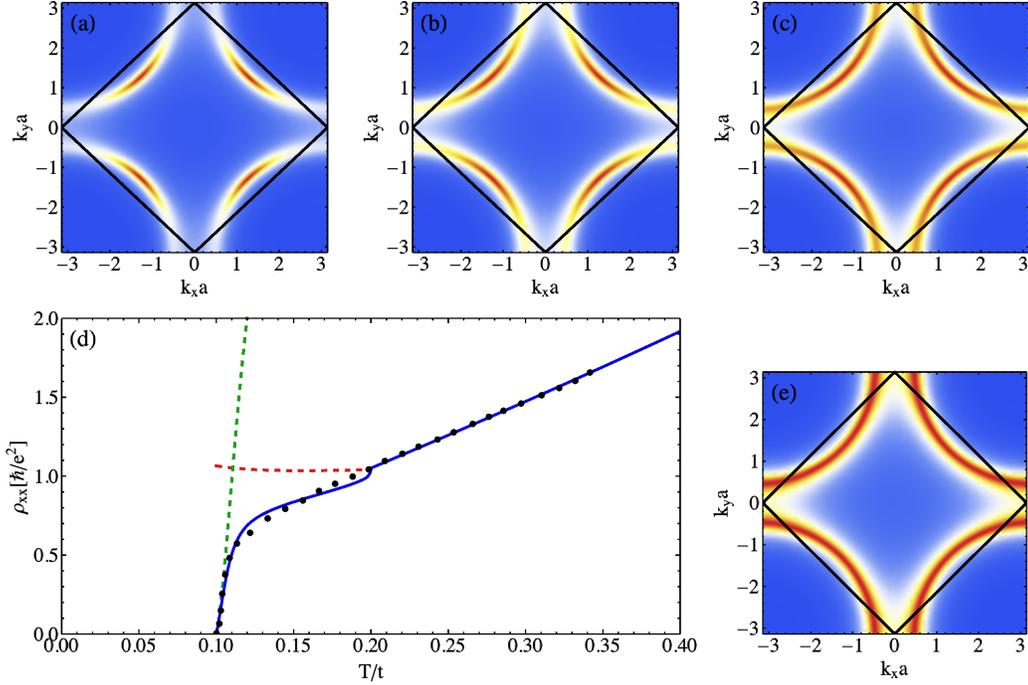


Figure 24. Calculated [57] behavior of the cuprate resistivity and temperature evolution of the Fermi arcs. “Bad-metal” behavior is important here as the small conductivity in the fermionic channel enables the bosonic downturn in the resistivity to be more evident.

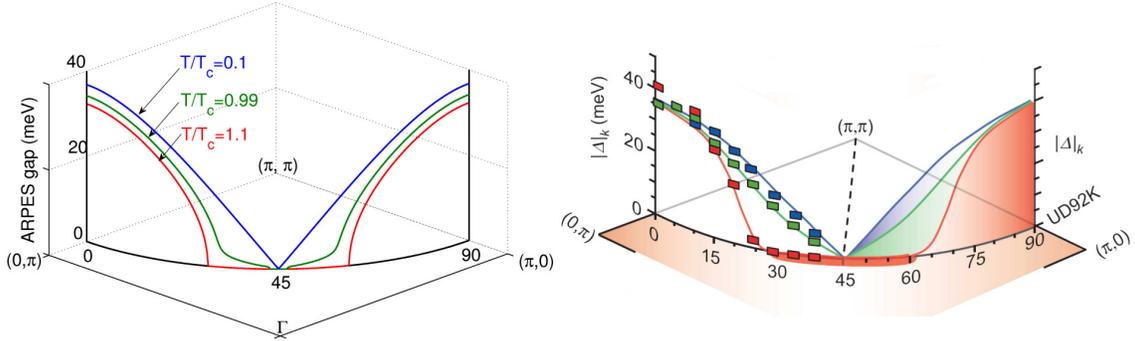


Figure 25. Inferred ARPES gaps relating to Fermi arc physics (associated with d -wave order). Comparison of theory [196] on the left with experiment [205] on the right.

onset [56], to become evident (see Fig. 24). This would otherwise be obscured by gap effects in the fermionic spectrum. The fits to the longitudinal DC resistivity shown in Fig. 24 are based on a phenomenological model [57] for the pair chemical potential (μ_{pair}) which incorporates the standard fluctuation behavior within the critical regime,

$$\mu_{\text{pair}} \approx (8/\pi)(T - T_c), \quad (30)$$

along with the natural interpolation of higher temperature effects which associate T^* with that temperature at which the number of pairs must necessarily vanish. This leads to

a consolidated form:

$$\mu_{\text{pair}} = \frac{8}{\pi}(T^* - T_c) \ln \frac{T^* - T}{T^* - T_c}. \quad (31)$$

The fits to the resistivity, $\rho(T)$, and its downturn in Fig. 24 are not unreasonable; also emphasized here is the presence of “Fermi arcs” which additionally help to reveal bosonic transport by suppressing the gap in the fermionic spectrum. With the same parameters one can arrive at some understanding of the Nernst effect [57]. However there are problematic issues concerning the Hall coefficient [57, 207] and the thermopower, which affect essentially all theoretical attempts to understand these cuprate data and make a direct comparison between theory and experiment difficult.

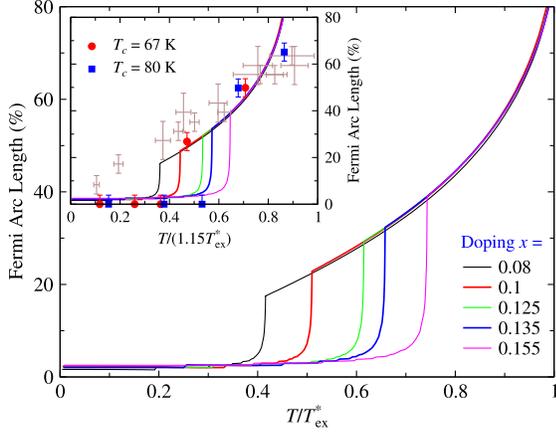


Figure 26. ARPES comparisons in cuprates showing collapse of the Fermi arcs at the superconducting transition. The figure compares experimental [206] data points with theoretical curves [201]. Here T_{ex}^* is the experimental T^* determined by ARPES data.

Indeed, there is a sizeable literature dealing with the Hall coefficient in the underdoped regime [208–216]. Among the most serious problems is that the measured σ_{xy} appears to be not as singular near T_c as is predicted by Gaussian fluctuation theories, where the expected singularity is stronger than in σ_{xx} . This is presumably associated with the experimental observation that $R_H \propto \rho_{yx}$ starts to drop with decreasing T at T slightly above T_c [210, 212] and can even change its sign as T decreases towards T_c .

Similarly, the normal state thermopower in underdoped cuprates [217–221] (at $T \sim T^*$) is positive in the experiments for the samples with the largest pseudogap. This is opposite to the usual band structure predictions, and also opposite to the sign of the Hall coefficient. Given these problems for the thermopower and Hall coefficients, comparisons between experiments are best addressed in the case of the Nernst coefficient.

D. Quantifying the Fermi arcs

Understanding and quantifying the Fermi arcs has become an important issue in the cuprates. In addition to ARPES experiments the existence of Fermi arcs appears to have been independently established in STM data as well [222, 223]. The right hand panel of Fig. 25 presents gaps extracted from ARPES data [205] for a moderately underdoped sample. The three different curves correspond to three different temperatures with the legend the same as that in the left panel (representing the results of theory). Importantly one sees a pronounced temperature dependence in the behavior of the ARPES spectral gap for the nodal region (near 45°) as compared with the antinodal region (near 0 and 90°), where there is virtually no T dependence. The left panel presents the counterpart theoretically predicted behavior, which exhibits some similarities.

Figure 26 addresses the temperature dependence of the

Fermi arcs and their sharp collapse [201] from above to below T_c . Note that here it is assumed (for simplicity) that the broadening parameter γ is temperature independent as the non-condensed pairs which persist below T_c continue to be distinguished from the condensate there. Plotted is the percentage of arc length as a function of T/T^* and for different doping concentrations from the optimal to the underdoped regime. There is a clear universality seen in the normal state, in both theory and experiment [206] (shown in the inset).

E. Behavior of the finite- ω conductivity

There is a substantial interest [225] in the ac-conductivity $\sigma(\omega)$ in the cuprates, notably both in the optical regime and at THz frequencies. These experiments are particularly useful as they can reveal important information about low-energy excitations and charge dynamics. Both gapped fermions and non-condensed Cooper pairs can contribute to $\sigma(\omega)$. In work summarized here only the fermionic contributions were considered.

A key feature of the in-plane $\sigma(\omega)$ is its two component nature consisting of a “coherent” Drude-like low- ω feature followed by an approximately T -independent mid-infrared (MIR) peak [225–227]. This is illustrated in Fig. 27. As stated in Ref. 226: “*The two component conductivity extends to the pseudogap boundary in the phase diagram... Moreover a softening of the mid-infrared band with doping resembles the decrease of the pseudogap temperature T^* .*” Also of importance is the fact [228] that “*high T_c materials are in the clean limit*” and also that “*...the MIR feature is seen above and below T_c .*” Thus, it appears that this MIR feature is not associated with disordered superconductivity and related momentum non-conserving processes, but rather it is due to the unconventional nature of the finite-frequency response [225].

Within the crossover scenario, the presence of non-condensed pairs both above and below T_c yields [98] a mid-infrared peak. This peak occurs around the energy needed to break pairs and thereby create conducting fermions. Its position is doping dependent, and only weakly temperature dependent, following the weak T dependence of the excitation gap $\Delta(T)$. As T decreases below T_c , the relatively high frequency spectral weight from these pseudogap effects, present in the normal phase, is transferred to the condensate. This leads to a narrowing of the low- ω Drude feature, as can be seen in both plots in Fig. 27.

Figure 28 right and left panels, respectively, show the theoretical prediction [99] and experimental behavior [229] found for the imaginary part of the THz conductivity, $\sigma_2(\omega)$. With decreasing temperature, at roughly T_c , σ_2 shows a sharp upturn at low ω , of the form $\sigma_2 \propto n_s/\omega$, where n_s is the superfluid density. The low- ω contribution above T_c is of interest to the extent that it may reflect the presence of dynamical superfluid correlations. This is shown in the insets which present an expanded view of the temperature dependencies near T_c . Both theory and experiment show that

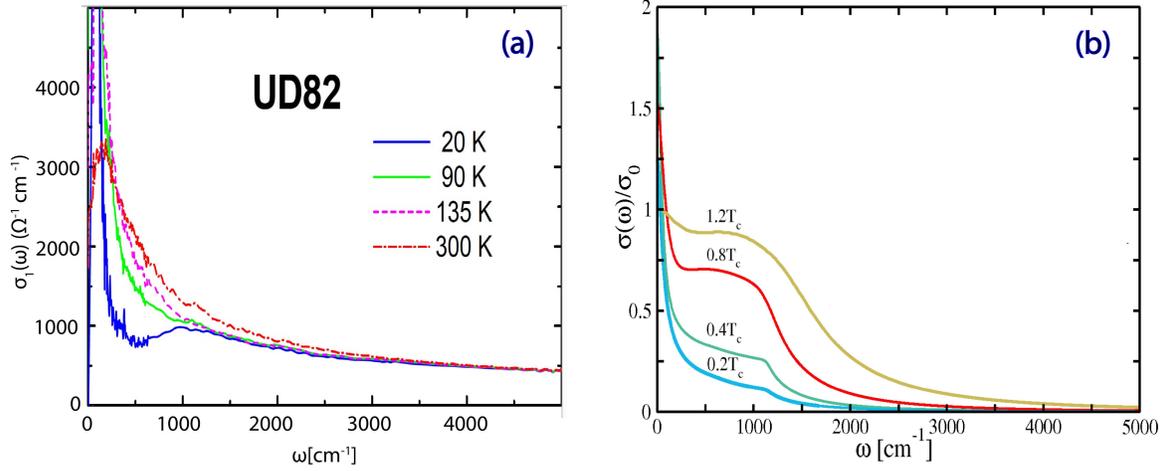


Figure 27. Mid-infrared conductivity plots in cuprates showing that in the theory [98], plotted on the right, and experiment [224], plotted on the left for Bi2212, the mid-infrared peak is associated with the presence of a pseudogap.

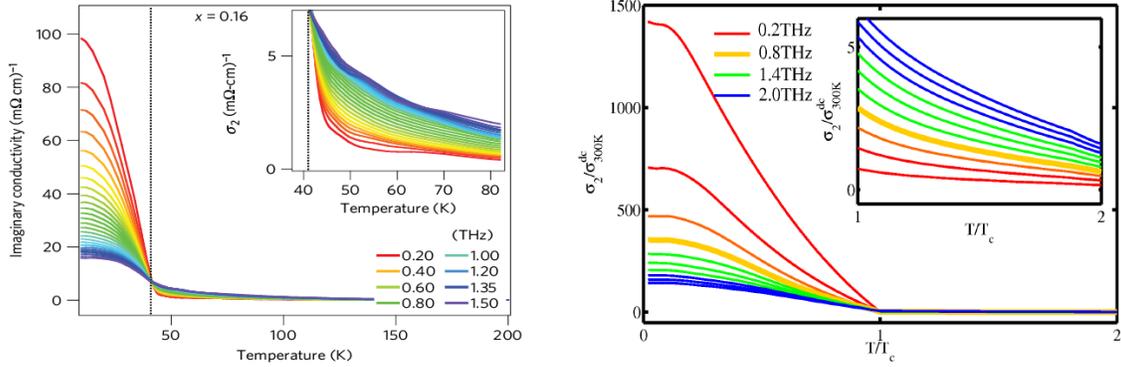


Figure 28. Comparison of the behavior of the imaginary part of the THz conductivity in cuprates. Experiment [229] is plotted on the left and theory [99] on the right.

the nesting of the σ_2 versus T curves switches order above T_c . It should be stressed that for this particular class of experiments the contribution from preformed pairs does not extend to very high temperatures. Indeed, here the effects are confined to temperatures in the vicinity of T_c , well below T^* . This is in contrast to other fluctuation experiments. It is notable, however, that the experimental data shows a more pronounced normal-state contribution than found in theory.

F. Precursor diamagnetism

The normal-state diamagnetic susceptibility in cuprates has also been widely discussed [231]. Here, by contrast with the discussion surrounding $\sigma(\omega)$ above, the interest is focused on the bosonic contributions. In conventional fluctuation theory [144] the diamagnetic susceptibility, χ_{dia} , in the vicinity of $T \approx T_c$ can be relatively large as it scales (in three dimensions) with the inverse of $T - T_c$. What happens in BCS-BEC theory as a consequence of the presence of a

pseudogap? In a BCS-BEC scenario χ_{dia} now scales [97] as $1/|\mu_{\text{pair}}|$ and, as can be seen from Eq. (31), the principal effect is that the inverse pair chemical potential remains appreciable now for an extended range of temperatures well beyond the critical region around T_c , and strictly vanishing only at T^* .

This, in turn, suggests that there are fluctuation contributions to the diamagnetism at relatively higher temperatures than generally observed in conventional superconductors. It should be noted, however, that the visibility of fluctuation diamagnetism depends on other background, generally paramagnetic, contributions, which are often difficult to quantify. A more detailed analysis leads to the results in Fig. 29 which shows a comparison between experiment [230] and theory [97].

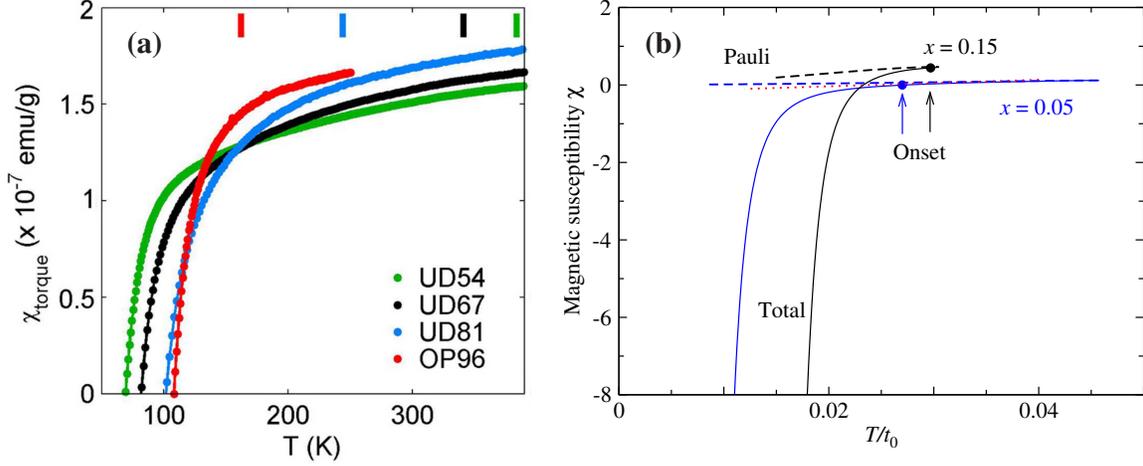


Figure 29. Comparison of the behavior of diamagnetic response above T_c with (a) experiment [230] on the left and (b) theory [97] on the right.

G. Other applications of BCS-BEC: Features of the non-Fermi liquid

By way of completeness we end by including several other literature contributions which address BCS-BEC theory in cuprates but for which there are no direct back-to-back experimental comparisons. These involve studies of how the non-Fermi liquid pseudogap state is reflected in quasi-particle-interference (QPI) experiments based on STM probes, and how it is reflected in quantum oscillations.

In particular, it is found [232] that the observation of a QPI pattern consistent with the so-called [233] “octet model” is a direct signature of coherent superconducting order. As a consequence, the QPI pattern in the pseudo-gap state is distinctly different from that in the superconducting phase. Also important is the observation [234] that, despite the presence of a pairing gap, oscillatory behavior is found in the thermodynamics for this non-Fermi liquid pseudogap phase.

IX. CONCLUSIONS

A. Summary

This Review article has been written in response to the large and relatively recent experimental literature on strongly correlated superconductors which are thought to exhibit BCS-BEC crossover phenomena. Many of these derive from artificial materials such as magic-angle twisted bilayer and trilayer graphene, quantum Hall bi-layers, or ionic-gate tuned semiconductors, as well as single unit cell and interfacial superconducting films. Also exciting are naturally grown superconductors, such as the Fe chalcogenides.

Because of the widespread interest, it is important to establish more precisely what BCS-BEC theory is and what it is not. We have done so in this Review and in the process clarified distinctions between the Fermi gas and solid-state superconductors, between two and

three-dimensional materials, between s - and d -wave order parameter symmetries and we have established distinguishing features of the BEC phase.

More generally, in this paper and in the context of different experiments, we addressed the three distinct ways of promoting a system out of the BCS and into the crossover regime via either (i) small electronic energy scales, (ii) two dimensionality, or (iii) strong pairing “glue”. We have emphasized that “domes” and “pseudogaps” are ubiquitous for crossover systems in periodic lattices.

The narrative arc of this Review is encapsulated through the evolution from Fig. 1 to the last figure we now discuss, Fig. 30. Fig. 1 introduces the concept of BCS-BEC crossover by raising the question of how to treat superconductivity in the presence of progressively stronger attractive interaction strengths. Notably, in contrast to the cold Fermi gases, solid state experiments have little access to this interaction strength parameter.

Fig. 30, which represents a summary of many of the various superconducting materials discussed in this Review, allows us to compare crossover theory and experiment. This is made possible by effectively representing the dimensionless interaction strength parameter in BCS-BEC crossover theory through dimensionless ratios of physically accessible parameters, such as T^*/T_{BKT} and Δ/E_F . One could similarly consider $k_F \xi_0^{\text{coh}}$ in counterpart plots. All of these are strongly inter-connected and, importantly, the figure indicates that their inter-dependencies are generally robust to variations in the pairing symmetry (here from s -wave to d -wave).

Plotted on the vertical axis in a logarithmic scale is Δ/E_F , where Δ is the zero-temperature excitation gap, while on the horizontal axis in a linear scale is T^*/T_{BKT} for two-dimensional superconductors. The upper (black) and lower (blue) theory curves are for s - and d -wave pairing symmetries, respectively. The data points come from the lithium-intercalated nitride films [173], from one unit cell FeSe on strontium titanate [163] and from magic-angle twisted bilayer as well as trilayer graphene [117–119, 130].

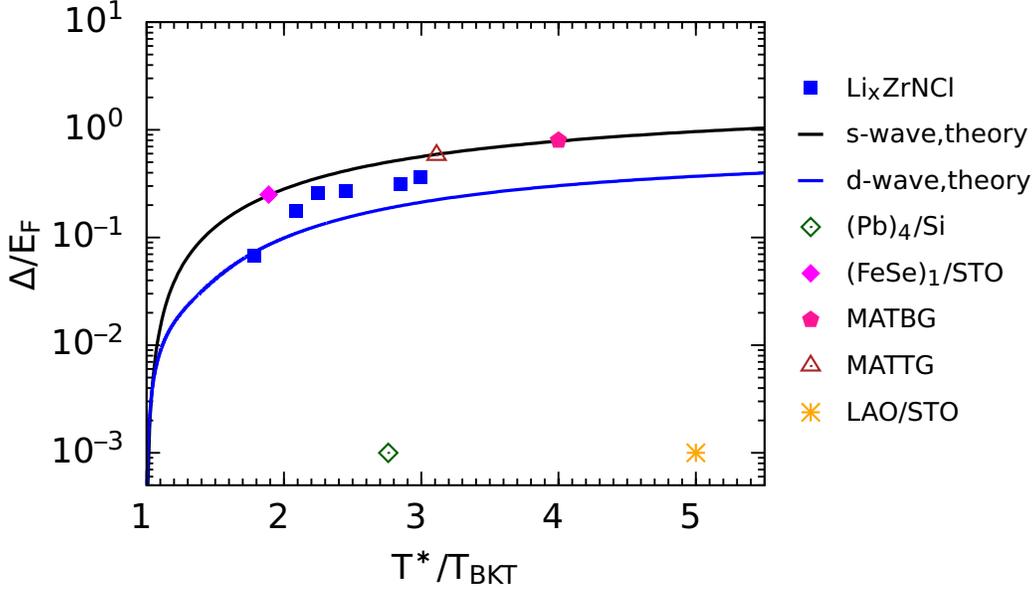


Figure 30. Summary figure comparing 2D BCS-BEC crossover theoretical predictions and experimental systems discussed in this paper. The two theory curves correspond to *s*- and *d*-wave pairing and the value of Δ is assumed to be at $T = 0$. The data points (see Appendix A) come from experiments on the lithium-intercalated nitride films [173], one unit cell FeSe on strontium titanate [163] and magic-angle twisted bilayer and trilayer graphene [117–119, 130]. Two additional data sets are associated with strongly disordered Pb films [128] and from the interface superconductor $\text{LaAlO}_3/\text{SrTiO}_3$ [67] which is difficult to classify.

Two additional data sets are associated with strongly disordered Pb films [128] and from the interface superconductor $\text{LaAlO}_3/\text{SrTiO}_3$ [67]; this latter system does not fall into any simple category. In this plot, because of their small Δ/E_F ratios, both are clearly distinct from BCS-BEC candidate materials. A comparison of theory and experiment in this replotting, thus, serves to highlight the distinction between strong pairing and strong disorder. In this way, the figure serves as a template for helping identify BCS-BEC crossover systems. The existence of a pseudogap (through the deviation of T^*/T_c from unity), as well as observations of $2e$ pairing appear insufficient.

Additionally, we have addressed the question of under what circumstances should one expect to reach the Bose-Einstein-condensation limit for a solid-state superconductor. In general, in this regime, rather than a very large transition temperature, one finds very small magnitudes of T_c or T_{BKT} . This point is often missed in the literature because the standard for the BCS-BEC phase diagrams is based on Fermi-gas physics where the BEC asymptote is large. This distinction is emphasized in Fig. 1 of this Review.

In the BEC regime, all signs of a Fermi surface have disappeared. Thus far, we are not able to report any unambiguous evidence that candidate systems have reached the BEC limit. Some signatures of the BEC we invoked earlier are that in this limit the character of the states within vortex cores [143] is distinctly different. Similarly, in this limit, coherence peaks in the quasiparticle tunneling characteristics will be absent. Theoretical indications are that a Bose condensed Fermi superconductor can occur when either T^*/T_{BKT} is much larger, say of the order of 10, accompanied

by more conventional values of Δ/E_F or alternatively with Δ/E_F of the order of 10 or more, accompanied by more conventional values of T^*/T_{BKT} . The latter relates to the interesting scenario in which superconductivity occurs in the presence of very flat energy bands with nontrivial band-topology and quantum geometry.

It is important to stress for future research that, in many ways, the most directly useful dimensionless parameter to measure is $k_F \xi_0^{\text{coh}}$ because it can be readily quantified in terms of a fundamental variable of crossover physics: the normalized pair density n_{pair}/n at the transition temperature. This necessarily varies continuously from 0 in the strict BCS limit to exactly 1/2 (discounting small thermal effects) in the BEC regime, where here $k_F \xi_0^{\text{coh}}$ saturates. As discussed in this Review, such a compact expression for the coherence length follows from the Schafroth-like equation for T_c in Eq. (2). We note that k_F here reflects the fixed density of electrons in the superconductor and, thus, does not contain many body effects or other band structure complexities. Finally, it is most gratifying that experiments studying superconductivity in the solid state (as distinct from the cold gases) can rather readily measure this parameter, as outlined in Sec. VII.

B. Outlook

More generally in looking toward the future, we are poised at the beginning of an extremely exciting era where the development of synthetic superconductors by design seems limitless. It is clear that tunable 2D superconductors (such as MATBG [117, 130], MATTG [118, 119], Li_xZrNCl [173]

etc.) will be crucial to realize superconductivity in the strong coupling regime. The coupling strength and Fermi energy can be dramatically and precisely tuned by twisting, gating, and doping, which provides the best platform to observe BCS-BEC crossover physics and to compare with theory.

Importantly, the present review can serve as a blueprint for future experimental endeavors, as it establishes concrete, experimentally falsifiable criteria to determine whether a given superconductor is in the BCS-BEC crossover regime. A singular observation of only the pseudogap phase, or pairing above T_c no longer suffices. Future experimental studies will need to combine measurements of Δ , E_F , T^* , and T_c or T_{BKT} to place candidate materials on Fig. 30. Critical tests will be to perform these measurements with a continuous tuning parameter (gating, doping, twisting, or isovalent substitution), to enable the comparison between theory and experiment in an extended region of Fig. 30. An example of such studies has been done on Li_xZrNCl [173].

It should be noted that other tunable 2D superconductors such as twisted transition metal dichalcogenides can also host flat bands [235, 236], and should be viewed as future candidates for superconductivity in the BCS-BEC crossover regime. It has also been predicted that nonequilibrium optical driving on twisted bilayer graphene can induce flat-band behavior associated with an effective Floquet Hamiltonian [237]; this provides a nonequilibrium route towards the strong-coupling limit. The implications of the BCS-BEC crossover scenario in the general nonequilibrium context will be important to address. Ultrafast spectroscopic experiments should more generally be explored to characterize this nonequilibrium band structure engineering and its potentially new forms of superconductivity.

Additionally, the study of high- T_c Fe-based superconductors will lead to new opportunities and challenges to explore the connection between the BCS-BEC physics, high- T_c superconductivity, and topological superconductivity. It is worth noting that the disparity between the transport T_c ($\sim 40\text{K}$) and the spectroscopic T^* ($\sim 70\text{K}$) has been a fundamental issue undermining further progress on monolayer $\text{FeSe}/\text{SrTiO}_3$ systems [163]. This review can serve as the starting point to systematically explore crossover physics for understanding this remarkable 2D high- T_c superconductor. A systematic tuning experiment using gating, doping, or Se:Te substitution will need to be performed. Importantly, with a specific Se:Te ratio = $x : 1-x$ between $x = 0.45$ and $x = 0.55$ the $\text{FeTe}_{1-x}\text{Se}_x$ bulk system exhibits a nontrivial topology with a superconducting topological surface state [238].

Among new theoretical challenges, BCS-BEC theories of superconductivity will need to accommodate the effect of magnetic fields, which will complete understanding of the canonical superconducting phase diagrams. What is the nature of the non-condensed pairs in the presence of a field [239]? How does condensation proceed when the dimensions of the system are effectively reduced by the presence of Landau levels [51, 240] and how does one understand the dynamics of vortices [241] from BCS to BEC? Conceptually related is the central and difficult issue:

how to generalize the Bogoliubov de Gennes equations to the crossover situation at finite temperature. This would enable other important calculations, for example, describing Andreev tunneling, effects of proximitization and addressing the vast number of situations which involve spatially dependent superconductivity. It is notably a difficult problem as one needs to incorporate two distinct types of (now spatially dependent) gaps, associated with condensed and non-condensed pairs.

In a discipline, where theory and experiment work hand-in-hand, it should be clear that the multiple experimental platforms described in this section, collectively present enormous opportunities for future theoretical developments. In the process they enhance our understanding of this generalized BCS theory in a deeper and much broader sense.

X. ACKNOWLEDGMENTS

We would like to thank our various collaborators who contributed to this work and to our understanding over the years: B. Jankó, I. Kosztin, J. Maly, J. Stajic, A. Iyengar, S. Tan, C.-C. Chien, Y. He, H. Guo, D. Wulin, P. Scherpelz, B. Anderson, C.-T. Wu, X. Wang, K. M. Shen, and D. G. Schlom. This work was partially (KL, ZW) supported by Department of Energy (DE-SC0019216). Q. C. was supported by the Innovation Program for Quantum Science and Technology (Grant No. 2021ZD0301904). R. B. was supported by the Department of Physics and Astronomy, Dartmouth College. S.-L. Y. acknowledges the support by the U.S. National Science Foundation through Grant 2145373.

Appendix A: Experimental data for 2D superconductors

In this Appendix, we present in Table I the data collected for Fig. 30 from various sources. In this table, if T_{BKT} is not available, we use the corresponding T_c . The abbreviations are: $(\text{FeSe})_1/\text{STO}$ = monolayer FeSe grown on the SrTiO_3 substrate, $(\text{Pb})_4/\text{Si}$ = 4-monolayer Pb film grown on the Si substrate, (001) LAO/STO = (001)-oriented $\text{LaAlO}_3/\text{SrTiO}_3$ interface, MATBG = magic-angle twisted bilayer graphene, and MATTG = magic-angle twisted trilayer graphene.

The sources of the data are as follows: for $(\text{FeSe})_1/\text{STO}$, $\{T_{\text{BKT}}, T^*\}$ are taken from Ref. [163], and $\{\Delta, E_F\}$ from Ref. [164]. For $(\text{Pb})_4/\text{Si}$ the data for $\{T_{\text{BKT}}, T^*\}$ are from Ref. [128]. To estimate Δ/E_F we use Ref. [242], where the sample used is actually a monolayer Pb film on Si substrate, $(\text{Pb})_1/\text{Si}$. We do not expect Δ/E_F to differ much between $(\text{Pb})_4/\text{Si}$ and $(\text{Pb})_1/\text{Si}$.

The data for Li_xZrNCl are taken from Ref. [173]. For (001)LAO/STO we use Ref. [168] for T_{BKT} , Ref. [147] for $\{T^*, \Delta\}$, and Ref. [167, 168] for E_F . In this system we have used the d_{xy} orbital band to arrive at E_F , and the data collected all roughly correspond to the same gating voltage $V_g \approx -100\text{ V}$.

Table I. Experimental data collected for Fig. 30. For Li_xZrNCl different rows are for different carrier densities.

Materials	T_{BKT}	T^*	Δ	E_F	T^*/T_c	Δ/E_F
(FeSe) ₁ /STO	38 K	72 K	15 meV	60 meV	1.89	0.25
(Pb) ₄ /Si	2.4 K	6.9 K	0.35 meV	380 meV	2.9	0.001
(001) LAO/STO	100 mK	500 mK	65 μeV	47 meV	5	0.001
Li_xZrNCl	0.031 T_F	0.055 T_F	–	–	1.78	0.067
	0.061 T_F	0.13 T_F	–	–	2.1	0.18
	0.088 T_F	0.20 T_F	–	–	2.25	0.26
	0.097 T_F	0.24 T_F	–	–	2.45	0.27
	0.10 T_F	0.30 T_F	–	–	2.84	0.31
	0.12 T_F	0.35 T_F	–	–	3.0	0.36
MATBG	1.0 K	4 K	1.4 meV	20 K	4	0.8
MATTG	2.25 K	7 K	1.6 meV	32 K	3.1	0.58

The values of $\{T_{\text{BKT}}, T^*, E_F\}$ for MATBG are taken from Ref. [117] for a twist angle $\theta \approx 1.05^\circ$. Here, T^* is estimated from the Ohmic recovery point from the V-I characteristic measurement. Δ is obtained from Ref. [130] which is appropriate to a very close but slightly different twist

angle $\theta \approx 1.01^\circ$ system.

For MATTG we use Ref. [118] for T_{BKT} and Ref. [119] for $\{T^*, \Delta\}$. The value of E_F is estimated by Stevan Nadj-Perge and provided through a private communication.

Appendix B: General BCS-BEC Crossover Theory for D-wave Case Near Half Filling

In this appendix we present additional details about BCS-BEC crossover theory in the d-wave case, focusing on the region around half filling in the electron band. The results here are presumed to be generally appropriate to nodal superconductors in this half-filled regime where (as discussed in the text) a BEC is not accessible. In the next Appendix C we make contact with some aspects of cuprate experiments, but it is important not to confuse the phenomenological appendix with the more precise predictions we present here.

For definiteness we look at a typical band structure which happens to be used for cuprates (but otherwise is of no particular consequence). We take $\epsilon_{\mathbf{k}} = (4t + 4t' + 2t_z) - 2t(\cos k_x + \cos k_y) - 4t' \cos k_x \cos k_y - 2t_z \cos k_z$ with $t'/t = -0.3$. This band structure is more complicated than that used in the main text of the paper (for both s and d wave systems), as it has a Van Hove singularity which is prominent for the band fillings we address. This is found to affect some properties of the crossover.

The goal of this appendix is to present the general behavior of the T^* and T_c phase diagrams, and the associated properties of the chemical potential. The latter is useful to establish because it can, in principle be measured. Moreover, the size of the fermionic chemical potential is often viewed as a measure of where a given system is in the crossover spectrum. By contrast, we emphasize here, unlike in the Fermi gases, how improbable it is to find a solid state superconductor anywhere in proximity to a BEC. As discussed in the main text there are better indicators of crossover physics than found in μ , through

the behavior, for example, of T^*/T_c and the coherence length.

Fig. 31(a) plots a phase diagram at a hole concentration $p = 1 - n = 0.15$ as a function of attractive coupling constant. Indicated are representative values of T^* and T_c . In the next figure, the solid line in Fig. 31(b) serves to characterize the behavior of the self-consistently determined fermionic chemical potential $\mu(T)$ for this particular interaction strength, as a function of temperature T . The dashed line indicates the counterpart value in the extrapolated normal state, $\mu_N(T)$, obtained by turning off the attraction. A crucial point follows by comparing Figs. 31(a) and 31(b) where we see that, although, there is an appreciable separation between T^* and T_c the chemical potential differs only slightly from its normal state value.

Figure 32 presents results for a range of hole concentrations, near half filling. For reasons which will become clear later, we choose T^*/T_c to be 4.7 to illustrate the behavior for a slightly lower hole doping $p = 0.1$, while $T^*/T_c = 1.05$ for a system with higher doping corresponding to $p = 0.25$. These two cases respectively show the effects of increasing and decreasing the size of the pseudogap.

Table II summarizes some central findings. Here we tabulate results for all three hole doping levels, $p = \{0.1, 0.15, 0.25\}$, including the behavior of the chemical potentials. This table presents the ratios of the zero temperature chemical potential μ to their normal state counterparts. The difference from unity is small and in the most extreme case, still less than 10%. From this comparison, one might view these systems as conventional BCS superconductors, but it should be stressed that they all belong to the BCS-BEC crossover regime as T_c and T^* are

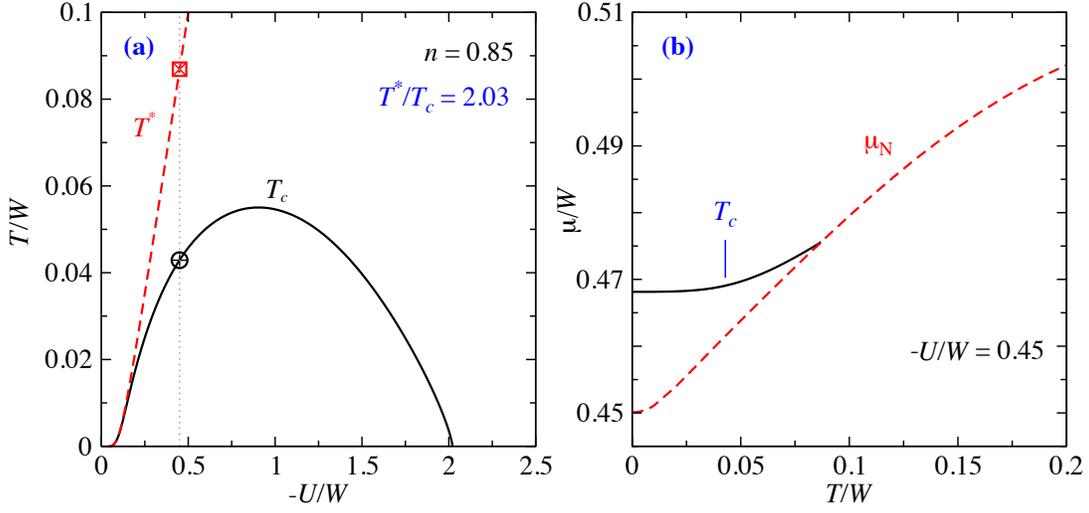


Figure 31. (a) $T_c - U$ phase diagram for a d-wave superconductor with electron density $n = 0.85$ on a quasi-2D square lattice. The energy dispersion is $\epsilon_{\mathbf{k}} = (4t + 4t' + 2t_z) - 2t(\cos k_x + \cos k_y) - 4t' \cos k_x \cos k_y - 2t_z \cos k_z$ with $t' = -0.3t$ and $t_z/t = 0.01$. All energies are normalized by $W = 4t$. The pairing gap is $\Delta_{\mathbf{k}} = \Delta \varphi_{\mathbf{k}}$ with $\varphi_{\mathbf{k}} = \cos k_x - \cos k_y$. (b) Temperature dependencies of the chemical potential μ and the extrapolated normal state μ_N , for interaction strength $U/W = -0.45$, corresponding to the vertical dotted line in (a). Here μ changes by -0.5% from $T = 0$ to the pairing onset T^* , and $(\mu - \mu_N)/\mu_N$ is found to be 3.8% at $T = 0$.

quite distinct.

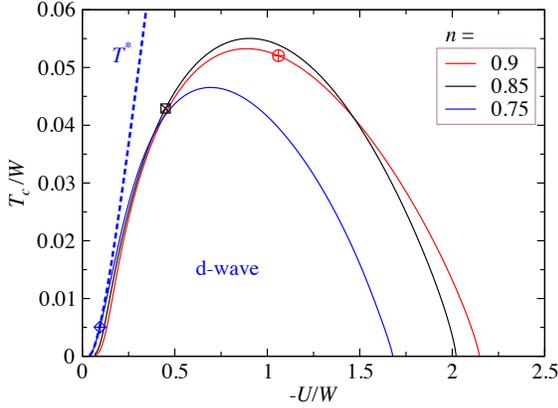


Figure 32. $T_c - U$ phase diagrams for quasi-2D d-wave superconductors with $t' = -0.3t$ and $t_z/t = 0.01$, computed for different electron densities $n = 1 - p$, where p is the hole doping. The symbols indicate where a given system (represented by the n value and T^*/T_c) is located in the corresponding phase diagram. For clarity, here we show the T^* line for $n = 0.75$ only.

Appendix C: D-wave Crossover and the Cuprate Phase Diagram

Whether any of the above discussion is relevant to the cuprates cannot be unequivocally proved. But it is useful to explore what the consequences are if we assume the values of n and T^*/T_c chosen above and then establish the implications of this d -wave BCS-BEC crossover. Indeed, the correspondence between both of these parameters can be seen to be reasonably compatible with the cuprate phase

Table II. Table showing changes in chemical potential associated with different values of T^*/T_c . Here $W = 4t$.

hole doping (p)	T^*/T_c	$ U /W$	$\mu(T=0)/\mu_N(T=0)$
$p = 0.10$	4.73	1.06	1.09
$p = 0.15$	2.03	0.45	1.04
$p = 0.25$	1.05	0.095	1.003

diagram, which is shown in Fig. 33 [72]. This compatibility of the parameter set, of course, depends on assuming that the measured T^* is related to pairing.

We stress that there are complexities concerning this phase diagram which are still not fully settled. Among these is the observation of a second characteristic temperature [243]. This temperature is typically about 20% above T_c , although significantly below T^* for heavily underdoped cuprates; one might speculate that this is associated with the onset of a more extended fluctuation regime where bosonic transport, derived from quasi-stable pre-formed pairs near condensation, is significant. Here we focus only on the presumed gap opening temperature T^* plotted above. We stress that there is no unanimity about whether one should associate the experimental T^* with pairing or an alternative energy scale, for example, deriving from possible ordering (e.g., d -density wave [244]) or fluctuations in the particle-hole channel.

We view the ratio T^*/T_c and corresponding density as input parameters. However, one test of the applicability of this theory comes from establishing the corresponding size of the electronic energy scales needed to match the size of the measured T_c and T^* , say in Kelvin. At issue is the hopping matrix elements t which determine the bandwidth and Fermi energy for each cuprate with a different hole concentration.

Table III. Key parameters for hole doped cuprates. In some sense these are near weak coupling which reflects the fact the cuprate T^*/T_c are not very large except at extreme underdoping. Here $\Delta(0) = 2\Delta$, which is the zero temperature spectral gap $|\Delta_{\mathbf{k}}| = |\Delta(\cos k_x - \cos k_y)|$ at $(k_x, k_y) = (\pi, 0)$ as measured in ARPES.

hole doping (p)	T^* (K)	T_c (K)	T^*/T_c	hopping, t (meV)	$2\Delta(0)/k_B T_c$	T_F (K)	T_c/T_F
$p = 0.10$	260	55	4.73	22.7	25.9	502	0.11
$p = 0.15$	190	93	2.03	46.6	9.85	975	0.095
$p = 0.25$	32	30.6	1.05	130	4.28	2466	0.012

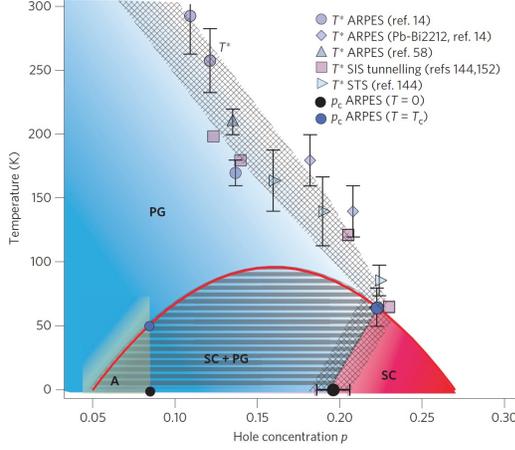


Figure 33. Experimental cuprate phase diagram, taken from Ref. [72].

To begin with we can obtain an order of magnitude estimate of the Fermi temperature T_F directly from Figure 32 if we take the vertical axis as $\approx T_c/2T_F$ for the near half-filled case. Then, knowing T_c is around 50–100K implies that the Fermi temperature is of the order of 1000K or so.

Figure 32 similarly suggests that T_c/T_F is around 0.1, as is confirmed in Table III where we present a more precise analysis. It should be stressed here that in the literature

the observation that $T_c/T_F \approx 0.1$ is often misinterpreted as representing the BEC limit of a Fermi gas. By contrast, the analysis here shows that this characteristic number is associated with a solid state superconductor which is very far from the BEC regime.

More specific cuprate parameters are presented in Table III which indicates the (only) adjustable parameter, t , in the fifth column of the table. It should be noted that this fitting suggests that the effective bandwidths will have to decrease as the system becomes more underdoped. Moreover, the values for T_F shown appear to be slightly smaller, but not by orders of magnitude, than those presented by Uemura [68]. As yet this remains an unsettled issue.

Finally we note recent work applying BCS-BEC crossover theory to the cuprates [245]. Here it was suggested that the cuprates with a “magic” ratio of $2\Delta(0)/T_c = 6.5$ can be identified with the unitary point in a three dimensional cold Fermi gas. This unitary point relates to the location of an isolated two-body bound state. However, as emphasized in this review, the superconducting phase diagrams of solid-state superconductors and Fermi gases are quite different, making such an identification difficult to support. In particular, from Table III it follows that even at optimal doping $p = 0.15$, we have $2\Delta(0)/T_c = 9.85$, which is, indeed, also consistent with numbers obtained from photoemission experiments [246]. This value is larger than 6.5 and it follows that, on the basis of the analysis of the chemical potential (Table II), such systems are far from the BEC as well.

- [1] Q. J. Chen, J. Stajic, S. Tan, and K. Levin, *Phys. Rep.* **412**, 1 (2005).
- [2] S. Giorgini, L. P. Pitaevskii, and S. Stringari, *Rev. Mod. Phys.* **80**, 1215 (2008).
- [3] M. Randeria and E. Taylor, *Annu. Rev. Condens. Matter Phys.* **5**, 209 (2014).
- [4] A. J. Leggett, in *Modern trends in the theory of condensed matter*, Lecture Notes in Physics, Vol. 115, edited by A. Pekalski and J. A. Przystawa (Springer-Verlag, Berlin, West Germany, 1980) pp. 13–27, proceedings of the XVI Karpacz Winter School of Theoretical Physics, February 19 - March 3, 1979, Karpacz, Poland.
- [5] D. M. Eagles, *Phys. Rev.* **186**, 456 (1969).
- [6] K. Levin and O. T. Valls, *Phys. Rep.* **98**, 1 (1983).
- [7] P. Nozières and S. Schmitt-Rink, *J. Low Temp. Phys.* **59**, 195 (1985).
- [8] R. B. Diener, R. Sensarma, and M. Randeria, *Phys. Rev. A* **77**, 023626 (2008).
- [9] R. Micnas, J. Ranninger, and S. Robaszkiewicz, *Rev. Mod. Phys.* **62**, 113 (1990).
- [10] C. A. R. Sá de Melo, M. Randeria, and J. R. Engelbrecht, *Phys. Rev. Lett.* **71**, 3202 (1993).
- [11] N. Trivedi and M. Randeria, *Phys. Rev. Lett.* **75**, 312 (1995).
- [12] M. Greiner, C. A. Regal, and D. S. Jin, *Nature* **426**, 537 (2003).
- [13] S. Jochim *et al.*, *Science* **302**, 2101 (2003).
- [14] C. A. Regal, M. Greiner, and D. S. Jin, *Phys. Rev. Lett.* **92**, 040403 (2004).
- [15] M. W. Zwierlein, C. A. Stan, C. H. Schunck, S. M. F. Raupach, A. J. Kerman, and W. Ketterle, *Phys. Rev. Lett.* **92**, 120403 (2004).
- [16] J. Kinast, A. Turlapov, J. E. Thomas, Q. J. Chen, J. Stajic, and K. Levin, *Science* **307**, 1296 (2005).

- [17] M. W. Zwierlein, J. R. Abo-Shaer, A. Schirotzek, C. H. Schunck, and W. Ketterle, *Nature* **435**, 1047 (2005).
- [18] A. Sommer, M. Ku, G. Roati, and M. W. Zwierlein, *Nature* **472**, 201 (2011).
- [19] J. A. Joseph, E. Elliott, and J. E. Thomas, *Phys. Rev. Lett.* **115**, 020401 (2015).
- [20] G. B. Partridge, W. Li, R. I. Kamar, Y. an Liao, and R. G. Hulet, *Science* **311**, 503 (2006).
- [21] M. W. Zwierlein, A. Schirotzek, C. H. Schunck, and W. Ketterle, *Science* **311**, 492 (2006).
- [22] J. K. Chin, D. E. Miller, Y. Liu, C. Stan, W. Setiawan, C. Sanner, K. Xu, and W. Ketterle, *Nature* **443**, 961 (2006).
- [23] L. Radzihovsky and D. E. Sheehy, *Rep. Prog. Phys.* **73**, 076501 (2010).
- [24] C.-C. Chien, Q. J. Chen, Y. He, and K. Levin, *Phys. Rev. Lett.* **97**, 090402 (2006).
- [25] C.-T. Wu, B. M. Anderson, R. Boyack, and K. Levin, *Phys. Rev. B* **91**, 220504 (2015).
- [26] B. M. Anderson, C.-T. Wu, R. Boyack, and K. Levin, *Phys. Rev. B* **92**, 134523 (2015).
- [27] L. He, X.-G. Huang, H. Hu, and X.-J. Liu, *Phys. Rev. A* **87**, 053616 (2013).
- [28] J. Zhang, H. Hu, X.-J. Liu, and H. Pu, in *Annual Review of Cold Atoms and Molecules*, Vol. 2, edited by K. W. Madison, K. Bongs, L. D. Carr, A. M. Rey, and H. Zhai (World Scientific, Singapore, 2014) Chap. 2, pp. 81–143.
- [29] P. K. Kovtun, D. T. Son, and A. O. Starinets, *Phys. Rev. Lett.* **94**, 111601 (2005).
- [30] H. Guo, D. Wulin, C.-C. Chien, and K. Levin, *New J. Phys.* **13**, 075011 (2011).
- [31] O. Gunnarsson, M. Calandra, and J. E. Han, *Rev. Mod. Phys.* **75**, 1085 (2003).
- [32] H. Guo, D. Wulin, C.-C. Chien, and K. Levin, *Phys. Rev. Lett.* **107**, 020403 (2011).
- [33] J. T. Stewart, J. P. Gaebler, and D. S. Jin, *Nature* **454**, 744 (2008).
- [34] M. W. Zwierlein, C. A. Stan, C. H. Schunck, S. M. F. Raupach, S. Gupta, Z. Hadzibabic, and W. Ketterle, *Phys. Rev. Lett.* **91**, 250401 (2003).
- [35] M. Bartenstein, A. Altmeyer, S. Riedl, S. Jochim, C. Chin, J. H. Denschlag, and R. Grimm, *Phys. Rev. Lett.* **92**, 120401 (2004).
- [36] K. M. O'Hara *et al.*, *Science* **289**, 2179 (2002).
- [37] J. Kinast, S. L. Hemmer, M. E. Gehm, A. Turlapov, and J. E. Thomas, *Phys. Rev. Lett.* **92**, 150402 (2004).
- [38] W. Zhang, C. A. Sackett, and R. G. Hulet, *Phys. Rev. A* **60**, 504 (1999).
- [39] K. E. Strecker, G. B. Partridge, and R. G. Hulet, *Phys. Rev. Lett.* **91**, 080406 (2003).
- [40] T. Bourdel, L. Khaykovich, J. Cubizolles, J. Zhang, F. Chevy, M. Teichmann, L. Tarruell, S. J. J. M. F. Kokkelmans, and C. Salomon, *Phys. Rev. Lett.* **93**, 050401 (2004).
- [41] I. Bloch, J. Dalibard, and W. Zwerger, *Reviews of modern physics* **80**, 885 (2008).
- [42] K. Levin, Q. J. Chen, C.-C. Chien, and Y. He, *Ann. Phys. (New York)* **325**, 233 (2010).
- [43] G. C. Strinati, P. Pieri, G. Röpke, P. Schuck, and M. Urban, *Phys. Rep.* **738**, 1 (2018).
- [44] W. Zwerger, ed., *The BCS-BEC crossover and the unitary Fermi gas*, Lecture Notes in Physics, Vol. 836 (Springer-Verlag, Berlin, Germany, 2012).
- [45] Y. Ohashi and A. Griffin, *Phys. Rev. Lett.* **89**, 130402 (2002).
- [46] J. Stajic, J. N. Milstein, Q. J. Chen, M. L. Chiofalo, M. J. Holland, and K. Levin, *Phys. Rev. A* **69**, 063610 (2004).
- [47] C. Chin, M. Bartenstein, A. Altmeyer, S. Riedl, S. Jochim, J. H. Denschlag, and R. Grimm, *Science* **305**, 1128 (2004).
- [48] S. Nascimbène, N. Navon, K. Jiang, F. Chevy, and C. Salomon, *Nature* **463**, 1057 (2010).
- [49] S. Tan, *Ann. Phys. (New York)* **323**, 2952 (2008).
- [50] M. J. Ku, A. T. Sommer, L. W. Cheuk, and M. W. Zwierlein, *Science* **335**, 563 (2012).
- [51] M. R. Schafroth, *Phys. Rev.* **100**, 463 (1955).
- [52] P. Pieri, L. Pisani, and G. C. Strinati, *Phys. Rev. B* **70**, 094508 (2004).
- [53] S. Tan and K. Levin, *Phys. Rev. A* **74**, 043606 (2006).
- [54] R. Haussmann and W. Zwerger, *Phys. Rev. A* **78**, 063602 (2008).
- [55] P. A. Lee, N. Nagaosa, and X.-G. Wen, *Rev. Mod. Phys.* **78**, 17 (2006).
- [56] T. Timusk and B. Statt, *Rep. Prog. Phys.* **62**, 61 (1999).
- [57] R. Boyack, Z. Wang, Q. J. Chen, and K. Levin, *Phys. Rev. B* **104**, 064508 (2021).
- [58] J. M. Kosterlitz, *Rep. Prog. Phys.* **79**, 026001 (2016).
- [59] J. M. Kosterlitz and D. J. Thouless, *J. Phys. C. Solid State* **6**, 1181 (1973).
- [60] V. Berezinskii, *Sov. Phys. JETP* **34**, 610 (1972).
- [61] J. V. Jose, ed., *40 years of Berezinskii-Kosterlitz-Thouless theory* (World Scientific, Singapore, 2013).
- [62] A. Hadzibabic, P. Kruger, M. Cheneau, B. Battelier, and J. Dalibard, *Nature* **441**, 1118 (2006).
- [63] N. Prokof'ev and B. Svistunov, *Phys. Rev. A* **66**, 043608 (2002).
- [64] J. Sous, Y. He, and S. A. Kivelson, *arxiv:2210.13478* (2022).
- [65] A. J. Leggett, *Nat. Phys.* **2**, 134 (2006).
- [66] S. Hufner, M. A. Hossain, A. Damascelli, and G. Sawatzky, *Rep. Prog. Phys.* **71**, 062501 (2008).
- [67] I. Božović and J. Levy, *Nat. Phys.* **16**, 712 (2020).
- [68] Y. J. Uemura, *Physica C* **282-287**, 194 (1997).
- [69] C. M. Varma, *Rev. Mod. Phys.* **92**, 031001 (2020).
- [70] C. Proust and L. Taillefer, *Annu. Rev. Condens. Matter Phys.* **10**, 409 (2019).
- [71] S.-D. Chen, M. Hashimoto, Y. He, D. Song, K.-J. Xu, J.-F. He, T. P. Devereaux, H. Eisaki, D.-H. Lu, J. Zaanen, *et al.*, *Science* **366**, 1099 (2019).
- [72] M. Hashimoto, I. M. Vishik, R.-H. He, T. P. Devereaux, and Z.-X. Shen, *Nat. Phys.* **10**, 483 (2014).
- [73] G. Ghiringhelli, M. Le Tacon, M. Minola, S. Blanco-Canosa, C. Mazzoli, N. Brookes, G. De Luca, A. Frano, D. Hawthorn, F. He, *et al.*, *Science* **337**, 821 (2012).
- [74] J. Xia, E. Schemm, G. Deutscher, S. A. Kivelson, D. A. Bonn, W. N. Hardy, R. Liang, W. Siemons, G. Koster, M. M. Fejer, and A. Kapitulnik, *Phys. Rev. Lett.* **100**, 127002 (2008).
- [75] L. Zhao, C. Belvin, R. Liang, D. Bonn, W. Hardy, N. Armitage, and D. Hsieh, *Nat. Phys.* **13**, 250 (2017).
- [76] J. L. Tallon, J. Loram, G. Williams, J. Cooper, I. Fisher, J. Johnson, M. Staines, and C. Bernhard, *physica status solidi (b)* **215**, 531 (1999).
- [77] M. Hashimoto, R.-H. He, K. Tanaka, J.-P. Testaud, W. Meevasana, R. G. Moore, D. Lu, H. Yao, Y. Yoshida, H. Eisaki, *et al.*, *Nat. Phys.* **6**, 414 (2010).
- [78] V. J. Emery and S. A. Kivelson, *Nature* **374**, 434 (1995).
- [79] Q. J. Chen, *Generalization of BCS theory to short coherence length superconductors: A BCS-Bose-Einstein crossover scenario*, Ph.D. thesis, University of Chicago (2000), see also arXiv:1801.06266.
- [80] M. Pini, P. Pieri, and G. C. Strinati, *Phys. Rev. B* **99**, 094502 (2019).
- [81] L. P. Kadanoff and P. C. Martin, *Phys. Rev.* **124**, 670 (1961).

- [82] B. R. Patton, *Phys. Rev. Lett.* **27**, 1273 (1971).
- [83] J. Maly, B. Jankó, and K. Levin, *Physica C* **321**, 113 (1999).
- [84] J. Maly, B. Jankó, and K. Levin, *Phys. Rev. B* **59**, 1354 (1999).
- [85] Q. J. Chen, I. Kosztin, B. Jankó, and K. Levin, *Phys. Rev. Lett.* **81**, 4708 (1998).
- [86] Q. J. Chen, I. Kosztin, B. Jankó, and K. Levin, *Phys. Rev. B* **59**, 7083 (1999).
- [87] A. F. Hebard and M. A. Paalanen, *Phys. Rev. Lett.* **65**, 927 (1990).
- [88] M. A. Paalanen, A. F. Hebard, and R. R. Ruel, *Phys. Rev. Lett.* **69**, 1604 (1992).
- [89] S. M. Hollen, H. Q. Nguyen, E. Rudisaile, M. D. Stewart, J. Shainline, J. M. Xu, and J. M. Valles, *Phys. Rev. B* **84**, 064528 (2011).
- [90] Y. M. Che, J. B. Wang, and Q. J. Chen, *Physical Review A* **93**, 063611 (2016); Q. J. Chen, J. B. Wang, L. Sun, and Y. Yu, *Chin. Phys. Lett.* **37**, 053702 (2020); L. Sun, J. B. Wang, X. Chu, and Q. J. Chen, *Annalen der Physik* **534**, 2100511 (2022); L. Sun and Q. Chen, *Phys. Rev. A* **106**, 013317 (2022).
- [91] M. P. A. Fisher, *Phys. Rev. Lett.* **65**, 923 (1990).
- [92] A. Yazdani and A. Kapitulnik, *Phys. Rev. Lett.* **74**, 3037 (1995).
- [93] S. Ullah and A. T. Dorsey, *Phys. Rev. B* **44**, 262 (1991).
- [94] J. Stajic, A. Iyengar, Q. J. Chen, and K. Levin, *Phys. Rev. B* **68**, 174517 (2003).
- [95] S. Tan and K. Levin, *Phys. Rev. B* **69**, 064510 (2004).
- [96] R. Boyack, X. Wang, Q. J. Chen, and K. Levin, *Phys. Rev. B* **99**, 134504 (2019).
- [97] R. Boyack, Q. J. Chen, A. A. Varlamov, and K. Levin, *Phys. Rev. B* **97**, 064503 (2018).
- [98] D. Wulin, H. Guo, C.-C. Chien, and K. Levin, *Phys. Rev. B* **86**, 134518 (2012).
- [99] D. Wulin and K. Levin, *Phys. Rev. B* **86**, 134519 (2012).
- [100] L. G. Aslamazov and A. I. Larkin, *Sov. Phys. Solid State* **10**, 875 (1968).
- [101] Y. J. Uemura, G. M. Luke, B. J. Sternlieb, J. H. Brewer, J. F. Carolan, W. N. Hardy, R. Kadono, J. R. Kempton, R. F. Kiefl, S. R. Kretzman, P. Mulhern, T. M. Riseman, D. L. Williams, B. X. Yang, S. Uchida, H. Takagi, J. Gopalakrishnan, A. W. Sleight, M. A. Subramanian, C. L. Chien, M. Z. Cieplak, G. Xiao, V. Y. Lee, B. W. Statt, C. E. Stronach, W. J. Kossler, and X. H. Yu, *Phys. Rev. Lett.* **62**, 2317 (1989).
- [102] J. L. Tallon, J. W. Loram, J. R. Cooper, C. Panagopoulos, and C. Bernhard, *Phys. Rev. B* **68**, 180501 (2003).
- [103] D. S. Fisher and P. C. Hohenberg, *Phys. Rev. B* **37**, 4936 (1988).
- [104] V. N. Popov, *Functional integrals in quantum field theory and statistical physics* (Springer Science & Business Media, Dordrecht, Holland, 2001).
- [105] S. Tung, G. Lamporesi, D. Lobser, L. Xia, and E. A. Cornell, *Phys. Rev. Lett.* **105**, 230408 (2010).
- [106] P. Cladé, C. Ryu, A. Ramanathan, K. Helmerson, and W. D. Phillips, *Phys. Rev. Lett.* **102**, 170401 (2009).
- [107] D. R. Nelson and J. M. Kosterlitz, *Phys. Rev. Lett.* **39**, 1201 (1977).
- [108] B. Halperin and D. R. Nelson, *J. Low Temp. Phys.* **36**, 599 (1979).
- [109] P. A. Murthy, I. Boettcher, L. Bayha, M. Holzmann, D. Kedar, M. Neidig, M. G. Ries, A. N. Wenz, G. Zürn, and S. Jochim, *Phys. Rev. Lett.* **115**, 010401 (2015).
- [110] M. G. Ries, A. N. Wenz, G. Zürn, L. Bayha, I. Boettcher, D. Kedar, P. A. Murthy, M. Neidig, T. Lompe, and S. Jochim, *Phys. Rev. Lett.* **114**, 230401 (2015).
- [111] N. Prokof'ev, O. Ruebenacker, and B. Svistunov, *Phys. Rev. Lett.* **87**, 270402 (2001).
- [112] C.-T. Wu, B. M. Anderson, R. Boyack, and K. Levin, *Phys. Rev. Lett.* **115**, 240401 (2015).
- [113] T. Hazra, N. Verma, and M. Randeria, *Physical Review X* **9**, 031049 (2019).
- [114] K. Hueck, N. Luick, L. Sobirey, J. Siegl, T. Lompe, and H. Moritz, *Phys. Rev. Lett.* **120**, 060402 (2018).
- [115] L. Sobirey, N. Luick, M. Bohlen, H. Biss, H. Moritz, and T. Lompe, *Science* **372**, 844 (2021).
- [116] J. Ruvalds, *Quantum Liquids* (Elsevier, 2012) article by A. J. Leggett, "Theory of superfluidity in helium-3".
- [117] Y. Cao, V. Fatemi, S. Fang, K. Watanabe, T. Taniguchi, E. Kaxiras, and P. Jarillo-Herrero, *Nature* **556**, 43 (2018).
- [118] J. M. Park, Y. Cao, K. Watanabe, T. Taniguchi, and P. Jarillo-Herrero, *Nature* **590**, 249 (2021).
- [119] H. Kim, Y. Choi, C. Lewandowski, A. Thomson, Y. Zhang, R. Polski, K. Watanabe, T. Taniguchi, J. Alicea, and S. Nadj-Perge, *Nature* **606**, 494 (2022).
- [120] P. Törmä, S. Peotta, and B. A. Bernevig, *Nat. Rev. Phys.* **4**, 5287542 (2022).
- [121] S. Peotta and P. Törmä, *Nat. Commun.* **6**, 8944 (2015), article.
- [122] Z. Wang, G. Chaudhary, Q. J. Chen, and K. Levin, *Phys. Rev. B* **102**, 184504 (2020).
- [123] J. S. Hofmann, E. Berg, and D. Chowdhury, *Phys. Rev. B* **102**, 201112 (2020).
- [124] A. V. Chubukov, I. Eremin, and D. V. Efremov, *Physical Review B* **93**, 174516 (2016).
- [125] H. Tajima, P. Pieri, and A. Perali, *Condensed Matter* **6**, 8 (2021).
- [126] Y. L. Loh, M. Randeria, N. Trivedi, C.-C. Chang, and R. Scalettar, *Physical Review X* **6**, 021029 (2016).
- [127] B. Sacépé, C. Chapelier, T. I. Baturina, V. M. Vinokur, M. R. Baklanov, and M. Sanquer, *Nat. Commun.* **1**, 140 (2010).
- [128] W. Zhao, Q. Wang, M. Liu, W. Zhang, Y. Wang, M. Chen, Y. Guo, K. He, X. Chen, Y. Wang, *et al.*, *Solid State Commun.* **165**, 59 (2013).
- [129] K. M. Bastiaans, D. Chatzopoulos, J.-F. Ge, D. Cho, W. O. Tromp, J. M. van Ruitenbeek, M. H. Fischer, P. J. de Visser, D. J. Thoen, E. F. Driessen, *et al.*, *Science* **374**, 608 (2021).
- [130] M. Oh, K. P. Nuckolls, D. Wong, R. L. Lee, X. Liu, K. Watanabe, T. Taniguchi, and A. Yazdani, *Nature* **600**, 240 (2021).
- [131] T. Dubouchet, B. Sacépé, J. Seidemann, D. Shahar, M. Sanquer, and C. Chapelier, *Nat. Phys.* **15**, 233 (2019).
- [132] M. Chand, G. Saraswat, A. Kamlapure, M. Mondal, S. Kumar, J. Jesudasan, V. Bagwe, L. Benfatto, V. Tripathi, and P. Raychaudhuri, *Phys. Rev. B* **85**, 014508 (2012).
- [133] P. W. Anderson, *J. Phys. Chem. Solids* **11**, 26 (1959).
- [134] E. Khestanova, J. Birkbeck, M. Zhu, Y. Cao, G. Yu, D. Ghazaryan, J. Yin, H. Berger, L. Forro, T. Taniguchi, *et al.*, *Nano Lett.* **18**, 2623 (2018).
- [135] S. Kasahara, T. Yamashita, A. Shi, R. Kobayashi, Y. Shimoyama, T. Watashige, K. Ishida, T. Terashima, T. Wolf, F. Hardy, *et al.*, *Nat. Commun.* **7**, 12843 (2016).
- [136] S. Kasahara, T. Watashige, T. Hanaguri, Y. Kohsaka, T. Yamashita, Y. Shimoyama, Y. Mizukami, R. Endo, H. Ikeda, K. Aoyama, *et al.*, *Proc. Nat'l Acad. Sci. U.S.A.* **111**, 16309 (2014).
- [137] K. Okazaki, Y. Ito, Y. Ota, Y. Kotani, T. Shimojima, T. Kiss, S. Watanabe, C.-T. Chen, S. Niitaka, T. Hanaguri, *et al.*, *Sci. Rep.* **4**, 1 (2014).
- [138] Y. Mizukami, M. Haze, O. Tanaka, K. Matsuura, D. Sano, J. Böker, I. Eremin, S. Kasahara, Y. Matsuda, and

- T. Shibauchi, [arXiv:2105.00739](https://arxiv.org/abs/2105.00739) (2021).
- [139] T. Hanaguri, S. Kasahara, J. Böker, I. Eremin, T. Shibauchi, and Y. Matsuda, *Phys. Rev. Lett.* **122**, 077001 (2019).
- [140] T. Shibauchi, T. Hanaguri, and Y. Matsuda, *J. Phys. Soc. Jpn.* **89**, 102002 (2020).
- [141] B. L. Kang, M. Z. Shi, S. J. Li, H. H. Wang, Q. Zhang, D. Zhao, J. Li, D. W. Song, L. X. Zheng, L. P. Nie, T. Wu, and X. H. Chen, *Phys. Rev. Lett.* **125**, 097003 (2020).
- [142] T. Hashimoto, Y. Ota, A. Tsuzuki, T. Nagashima, A. Fukushima, S. Kasahara, Y. Matsuda, K. Matsuura, Y. Mizukami, T. Shibauchi, *et al.*, *Sci. Adv.* **6**, eabb9052 (2020).
- [143] C.-C. Chien, Y. He, Q. J. Chen, and K. Levin, *Phys. Rev. A* **73**, 041603 (2006).
- [144] A. Larkin and A. Varlamov, *Theory of Fluctuations in Superconductors*, rev. ed. (Oxford University Press, Oxford, UK, 2009).
- [145] F. Hardy, M. He, L. Wang, T. Wolf, P. Schweiss, M. Merz, M. Barth, P. Adelman, R. Eder, A.-A. Haghighirad, and C. Meingast, *Phys. Rev. B* **99**, 035157 (2019).
- [146] S. Rinott, K. Chashka, A. Ribak, E. D. Rienks, A. Taleb-Ibrahimi, P. Le Fevre, F. Bertran, M. Randeria, and A. Kanigel, *Sci. Adv.* **3**, e1602372 (2017).
- [147] C. Richter, H. Boschker, W. Dietsche, E. Fillis-Tsirakis, R. Jany, F. Loder, L. F. Kourkoutis, D. A. Muller, J. R. Kirtley, C. W. Schneider, *et al.*, *Nature* **502**, 528 (2013).
- [148] S. Zhang, G. Miao, J. Guan, X. Xu, B. Liu, F. Yang, W. Wang, X. Zhu, and J. Guo, *Chin. Phys. Lett.* **36**, 107404 (2019).
- [149] G. Cheng, M. Tomczyk, S. Lu, J. P. Veazey, M. Huang, P. Irvin, S. Ryu, H. Lee, C.-B. Eom, C. S. Hellberg, *et al.*, *Nature* **521**, 196 (2015).
- [150] A. Caviglia, S. Gariglio, N. Reyren, D. Jaccard, T. Schneider, M. Gabay, S. Thiel, G. Hammerl, J. Mannhart, and J.-M. Triscone, *Nature* **456**, 624 (2008).
- [151] N. Reyren, S. Thiel, A. Caviglia, L. F. Kourkoutis, G. Hammerl, C. Richter, C. W. Schneider, T. Kopp, A.-S. Ruetschi, D. Jaccard, *et al.*, *Science* **317**, 1196 (2007).
- [152] S. Gariglio, M. Gabay, J. Mannhart, and J.-M. Triscone, *Physica C: Supercond.* **514**, 189 (2015).
- [153] W.-H. Zhang, Y. Sun, J.-S. Zhang, F.-S. Li, M.-H. Guo, Y.-F. Zhao, H.-M. Zhang, J.-P. Peng, Y. Xing, H.-C. Wang, *et al.*, *Chin. Phys. Lett.* **31**, 017401 (2014).
- [154] Y. Song, Z. Chen, Q. Zhang, H. Xu, X. Lou, X. Chen, X. Xu, X. Zhu, R. Tao, T. Yu, *et al.*, *Nat. Commun.* **12**, 5926 (2021).
- [155] S. Han, C.-L. Song, X.-C. Ma, and Q.-K. Xue, *Comptes Rendus. Physique* **22**, 163 (2021).
- [156] Y. E. Suyolcu, Y. Wang, F. Baiutti, A. Al-Temimy, G. Gregori, G. Cristiani, W. Sigle, J. Maier, P. A. van Aken, and G. Logvenov, *Sci. rep.* **7**, 1 (2017).
- [157] V. Gasparov, A. Audouard, L. Drigo, X. He, and I. Bozovic, *Int'l J. Mod. Phys. B* **31**, 1745016 (2017).
- [158] Z. Wang, C. Liu, Y. Liu, and J. Wang, *J. Phys. Condens. Matter* **29**, 153001 (2017).
- [159] S. N. Rebec, T. Jia, C. Zhang, M. Hashimoto, D.-H. Lu, R. G. Moore, and Z.-X. Shen, *Phys. Rev. Lett.* **118**, 067002 (2017).
- [160] J.-F. Ge, Z.-L. Liu, C. Liu, C.-L. Gao, D. Qian, Q.-K. Xue, Y. Liu, and J.-F. Jia, *Nat. Mater.* **14**, 285 (2015).
- [161] A. K. Pedersen, S. Ichinokura, T. Tanaka, R. Shimizu, T. Hitosugi, and T. Hirahara, *Phys. Rev. Lett.* **124**, 227002 (2020).
- [162] Q.-Y. Wang, Z. Li, W.-H. Zhang, Z.-C. Zhang, J.-S. Zhang, W. Li, H. Ding, Y.-B. Ou, P. Deng, K. Chang, *et al.*, *Chin. Phys. Lett.* **29**, 037402 (2012).
- [163] B. D. Faeth, S.-L. Yang, J. K. Kawasaki, J. N. Nelson, P. Mishra, C. T. Parzyck, C. Li, D. G. Schlom, and K. M. Shen, *Phys. Rev. X* **11**, 021054 (2021).
- [164] D. Liu, W. Zhang, D. Mou, J. He, Y.-B. Ou, Q.-Y. Wang, Z. Li, L. Wang, L. Zhao, S. He, *et al.*, *Nat. Commun.* **3**, 931 (2012).
- [165] C. Chen, Q. Liu, W.-C. Bao, Y. Yan, Q.-H. Wang, T. Zhang, and D. Feng, *Phys. Rev. Lett.* **124**, 097001 (2020).
- [166] C. Cancellieri, M. L. Reinle-Schmitt, M. Kobayashi, V. N. Strocov, P. R. Willmott, D. Fontaine, P. Ghosez, A. Filippetti, P. Delugas, and V. Fiorentini, *Phys. Rev. B* **89**, 121412 (2014).
- [167] J. A. Sulpizio, S. Ilani, P. Irvin, and J. Levy, *Annu. Rev. Mater. Res.* **44**, 117 (2014).
- [168] Y.-Y. Pai, A. Tylan-Tyler, P. Irvin, and J. Levy, *Rep. Prog. Phys.* **81**, 036503 (2018).
- [169] M. S. Scheurer and J. Schmalian, *Nat. Commun.* **6**, 6005 (2015).
- [170] E. Fillis-Tsirakis, C. Richter, J. Mannhart, and H. Boschker, *New J. Phys.* **18**, 013046 (2016).
- [171] Y. M. Che, L. F. Zhang, J. B. Wang, and Q. J. Chen, *Phys. Rev. B* **95**, 014504 (2017).
- [172] X. Lu, P. Stepanov, W. Yang, M. Xie, M. A. Aamir, I. Das, C. Urgell, K. Watanabe, T. Taniguchi, G. Zhang, *et al.*, *Nature* **574**, 653 (2019).
- [173] Y. Nakagawa, Y. Kasahara, T. Nomoto, R. Arita, T. Nojima, and Y. Iwasa, *Science* **372**, 190 (2021).
- [174] Y. Saito, T. Nojima, and Y. Iwasa, *Nat. Rev. Mater.* **2**, 1 (2016).
- [175] Y. Nakagawa, Y. Saito, T. Nojima, K. Inumaru, S. Yamanaka, Y. Kasahara, and Y. Iwasa, *Phys. Rev. B* **98**, 064512 (2018).
- [176] C. Comte and P. Nozieres, *J. de Physique* **43**, 1069 (1982).
- [177] M. Combescot, R. Combescot, and F. Dubin, *Rep. Prog. Phys.* **80**, 066501 (2017).
- [178] W. Kohn and D. Sherrington, *Rev. Mod. Phys.* **42**, 1 (1970).
- [179] J. Eisenstein, *Annu. Rev. Condens. Matter Phys.* **5**, 159 (2014).
- [180] J. P. Eisenstein, L. N. Pfeiffer, and K. W. West, *Phys. Rev. Lett.* **123**, 066802 (2019).
- [181] S. Q. Murphy, J. P. Eisenstein, G. S. Boebinger, L. N. Pfeiffer, and K. W. West, *Phys. Rev. Lett.* **72**, 728 (1994).
- [182] N. E. Bonesteel, I. A. McDonald, and C. Nayak, *Phys. Rev. Lett.* **77**, 3009 (1996).
- [183] B. I. Halperin, *Helvetica Physica Acta* **56**, 75 (1983).
- [184] K. Moon, H. Mori, K. Yang, S. M. Girvin, A. H. MacDonald, L. Zheng, D. Yoshioka, and S.-C. Zhang, *Phys. Rev. B* **51**, 5138 (1995).
- [185] X. Liu, J. Li, K. Watanabe, T. Taniguchi, J. Hone, B. I. Halperin, P. Kim, and C. R. Dean, *Science* **375**, 205 (2022).
- [186] G. Wagner, D. X. Nguyen, S. H. Simon, and B. I. Halperin, *Phys. Rev. Lett.* **127**, 246803 (2021).
- [187] I. Sodemann, I. Kimchi, C. Wang, and T. Senthil, *Phys. Rev. B* **95**, 085135 (2017).
- [188] J. K. Jain, *Composite fermions* (Cambridge University Press, 2007).
- [189] B. I. Halperin, P. A. Lee, and N. Read, *Phys. Rev. B* **47**, 7312 (1993).
- [190] Z. Wang, I. Mandal, S. B. Chung, and S. Chakravarty, *Annals of Physics* **351**, 727 (2014).
- [191] X. Liu, K. Watanabe, T. Taniguchi, B. I. Halperin, and P. Kim, *Nature Physics* **13**, 746 (2017).
- [192] D. Kamburov, Y. Liu, M. A. Mueed, M. Shayegan, L. N. Pfeiffer, K. W. West, and K. W. Baldwin, *Phys. Rev. Lett.* **113**, 196801 (2014).
- [193] A. Kanigel, U. Chatterjee, M. Randeria, M. R. Norman, G. Koren, K. Kadowaki, and J. C. Campuzano, *Phys. Rev. Lett.* **101**, 137002 (2008).

- [194] M. Kugler, O. Fischer, C. Renner, S. Ono, and Y. Ando, *Phys. Rev. Lett.* **86**, 4911 (2001).
- [195] M. Oda, K. Hoya, R. Kubota, C. Manabe, N. Momono, T. Nakano, and M. Ido, *Physica C* **281**, 135 (1997).
- [196] C.-C. Chien, Y. He, Q. J. Chen, and K. Levin, *Phys. Rev. B* **79**, 214527 (2009).
- [197] P. Zhou, L. Chen, Y. Liu, I. Sochnikov, A. T. Bollinger, M.-G. Han, Y. Zhu, X. He, I. Bozovic, and D. Natelson, *Nature* **572**, 493 (2019).
- [198] Y. Yu, L. Ma, P. Cai, R. Zhong, C. Ye, J. Shen, G. D. Gu, X. H. Chen, and Y. Zhang, *Nature* **575**, 156 (2019).
- [199] T. M. Rice, K.-Y. Yang, and F.-C. Zhang, *Rep. Prog. Phys.* **75**, 016502 (2011).
- [200] P. Scherpelz, A. Rañon, Y. He, and K. Levin, *Phys. Rev. B* **90**, 060506 (2014).
- [201] Q. J. Chen and K. Levin, *Phys. Rev. B* **78**, 020513 (2008).
- [202] T. Kondo, W. Malaeb, Y. Ishida, T. Sasagawa, H. Sakamoto, T. Takeuchi, T. Tohyama, and S. Shin, *Nature communications* **6**, 1 (2015).
- [203] A. V. Chubukov, M. R. Norman, A. J. Millis, and E. Abrahams, *Phys. Rev. B* **76**, 180501 (2007).
- [204] M. R. Norman, A. Kanigel, M. Randeria, U. Chatterjee, and J. C. Campuzano, *Phys. Rev. B* **76**, 174501 (2007).
- [205] W.-S. Lee, I. Vishik, K. Tanaka, D. Lu, T. Sasagawa, N. Nagaosa, T. Devereaux, Z. Hussain, and Z.-X. Shen, *Nature* **450**, 81 (2007).
- [206] A. Kanigel, U. Chatterjee, M. Randeria, M. R. Norman, S. Souma, M. Shi, Z. Z. Li, H. Raffy, and J. C. Campuzano, *Phys. Rev. Lett.* **99**, 157001 (2007).
- [207] V. B. Geshkenbein, L. B. Ioffe, and A. I. Larkin, *Phys. Rev. B* **55**, 3173 (1997).
- [208] J. P. Rice, J. Giapintzakis, D. M. Ginsberg, and J. M. Mochel, *Phys. Rev. B* **44**, 10158 (1991).
- [209] H. Y. Hwang, B. Batlogg, H. Takagi, H. L. Kao, J. Kwo, R. J. Cava, J. J. Krajewski, and W. F. Peck, *Phys. Rev. Lett.* **72**, 2636 (1994).
- [210] W. Lang, G. Heine, P. Schwab, X. Z. Wang, and D. Bäuerle, *Phys. Rev. B* **49**, 4209 (1994).
- [211] A. V. Samoilov, *Phys. Rev. B* **49**, 1246 (1994).
- [212] R. Jin and H. R. Ott, *Phys. Rev. B* **57**, 13872 (1998).
- [213] Z. Konstantinovic, Z. Z. Li, and H. Raffy, *Phys. Rev. B* **62**, R11989 (2000).
- [214] D. Matthey, S. Gariglio, B. Giovannini, and J.-M. Triscone, *Phys. Rev. B* **64**, 024513 (2001).
- [215] Y. Ando and K. Segawa, *J. Phys. Chem. Solids* **63**, 2253 (2002), proceedings of the Conference on Spectroscopies in Novel Superconductors.
- [216] K. Segawa and Y. Ando, *Phys. Rev. B* **69**, 104521 (2004).
- [217] F. Munakata, K. Matsuura, K. Kubo, T. Kawano, and H. Yamauchi, *Phys. Rev. B* **45**, 10604 (1992).
- [218] D. Huang, R. Wang, W. Cai, G. Gu, Q. Shi, Y. Zhou, J. Fu, C. Huang, Y. Ruan, and Y. Zhang, *Physica C: Supercond.* **199**, 337 (1992).
- [219] T. Fujii, I. Terasaki, T. Watanabe, and A. Matsuda, *Physica C: Supercond.* **378-381**, 182 (2002).
- [220] S. Badoux, S. A. A. Afshar, B. Michon, A. Ouellet, S. Fortier, D. LeBoeuf, T. P. Croft, C. Lester, S. M. Hayden, H. Takagi, K. Yamada, D. Graf, N. Doiron-Leyraud, and L. Taillefer, *Phys. Rev. X* **6**, 021004 (2016).
- [221] O. Cyr-Choinière, S. Badoux, G. Grissonnanche, B. Michon, S. A. A. Afshar, S. Fortier, D. LeBoeuf, D. Graf, J. Day, D. A. Bonn, W. N. Hardy, R. Liang, N. Doiron-Leyraud, and L. Taillefer, *Phys. Rev. X* **7**, 031042 (2017).
- [222] A. Pushp, C. V. Parker, A. N. Pasupathy, K. K. Gomes, S. Ono, J. Wen, Z. Xu, G. Gu, and A. Yazdani, *Science* **324**, 1689 (2009).
- [223] J. Lee, K. Fujita, A. Schmidt, C. K. Kim, H. Eisaki, S. Uchida, and J. Davis, *Science* **325**, 1099 (2009).
- [224] J. Hwang, T. Timusk, and G. Gu, *J. Phys. Condens. Matter* **19**, 125208 (2007).
- [225] D. N. Basov and T. Timusk, *Rev. Mod. Phys.* **77**, 721 (2005).
- [226] Y. S. Lee, K. Segawa, Z. Q. Li, W. J. Padilla, M. Dumm, S. V. Dordevic, C. C. Homes, Y. Ando, and D. N. Basov, *Phys. Rev. B* **72**, 054529 (2005).
- [227] A. F. Santander-Syro, R. P. S. M. Lobo, N. Bontemps, W. Lopera, D. Giratá, Z. Konstantinovic, Z. Z. Li, and H. Raffy, *Phys. Rev. B* **70**, 134504 (2004).
- [228] K. Kamarás, S. L. Herr, C. D. Porter, N. Tache, D. B. Tanner, S. Etemad, T. Venkatesan, E. Chase, A. Inam, X. D. Wu, M. S. Hegde, and B. Dutta, *Phys. Rev. Lett.* **64**, 84 (1990).
- [229] L. Bilbro, R. V. Aguilar, G. Logvenov, O. Pelleg, I. Bozovic, and N. Armitage, *Nat. Phys.* **7**, 298 (2011).
- [230] G. Yu, D.-D. Xia, D. Pelc, R.-H. He, N.-H. Kaneko, T. Sasagawa, Y. Li, X. Zhao, N. Barišić, A. Shekhter, and M. Greven, *Phys. Rev. B* **99**, 214502 (2019).
- [231] L. Li, Y. Wang, S. Komiya, S. Ono, Y. Ando, G. D. Gu, and N. P. Ong, *Phys. Rev. B* **81**, 054510 (2010).
- [232] D. Wulin, Y. He, C.-C. Chien, D. K. Morr, and K. Levin, *Phys. Rev. B* **80**, 134504 (2009).
- [233] Y. Kohsaka, C. Taylor, P. Wahl, A. Schmidt, J. Lee, K. Fujita, J. Alldredge, K. McElroy, J. Lee, H. Eisaki, S. Uchida, D.-H. Lee, and J. C. Davis, *Nature* **454**, 1072 (2008).
- [234] Y. He, P. Scherpelz, and K. Levin, *Phys. Rev. B* **88**, 064516 (2013).
- [235] T. Devakul, V. Crépel, Y. Zhang, and L. Fu, *Nat. Commun.* **12**, 6730 (2021).
- [236] H. Li, S. Li, M. H. Naik, J. Xie, X. Li, J. Wang, E. Regan, D. Wang, W. Zhao, S. Zhao, *et al.*, *Nat. Mater.* **20**, 945 (2021).
- [237] I. A. Assi, J. P. F. LeBlanc, M. Rodriguez-Vega, H. Bahlouli, and M. Vogl, *Phys. Rev. B* **104**, 195429 (2021).
- [238] P. Zhang, K. Yaji, T. Hashimoto, Y. Ota, T. Kondo, K. Okazaki, Z. Wang, J. Wen, G. Gu, H. Ding, *et al.*, *Science* **360**, 182 (2018).
- [239] P. Scherpelz, D. Wulin, K. Levin, and A. K. Rajagopal, *Phys. Rev. A* **87**, 063602 (2013).
- [240] P. A. Lee and S. R. Shenoy, *Phys. Rev. Lett.* **28**, 1025 (1972).
- [241] D. Mozyrsky and A. V. Chubukov, *Phys. Rev. B* **99**, 174510 (2019).
- [242] T. Zhang, P. Cheng, W.-J. Li, Y.-J. Sun, G. Wang, X.-G. Zhu, K. He, L. Wang, X. Ma, X. Chen, *et al.*, *Nat. Phys.* **6**, 104 (2010).
- [243] I. Vishik, *Reports on Progress in Physics* **81**, 062501 (2018).
- [244] S. Chakravarty, R. B. Laughlin, D. K. Morr, and C. Nayak, *Phys. Rev. B* **63**, 094503 (2001).
- [245] N. Harrison and M. K. Chan, *Physical Review Letters* **129**, 017001 (2022).
- [246] Y. He, M. Hashimoto, D. Song, S.-D. Chen, J. He, I. Vishik, B. Moritz, D.-H. Lee, N. Nagaosa, J. Zaanen, *et al.*, *Science* **362**, 62 (2018).