

# Nodal higher-order topological superconductivity from a $C_4$ -symmetric Dirac semimetal

Zhenfei Wu and Yuxuan Wang

*Department of Physics, University of Florida, Gainesville, Florida, 32601, USA*

(Dated: September 2, 2022)

We analyze the topological properties of the possible superconducting states emerging from a  $Cd_3As_2$ -like,  $C_4$ -symmetric Dirac semimetal, with two four-fold degenerate Dirac points separated in the  $k_z$  direction. Unlike the simplest Weyl semimetal for which all pairing orders are topologically obstructed and nodal, we show that the topological obstruction for pairing in Dirac semimetals crucially only exists for certain pairing symmetries. In particular, we focus on odd-parity  $B_{1u}$  and  $B_{2u}$  pairing states, both of which can be induced by Ising ferromagnetic fluctuations. The  $B_{1u}$  and  $B_{2u}$  pairing states inherit the topological obstruction from the normal state, which dictates that these states necessarily hosts four BdG Dirac point nodes protected by a  $\mathbb{Z}_2$  monopole charge. By a Wannier state analysis, we show that the topological obstruction in the superconducting states is of higher-order nature. As a result, in a rod geometry with gapped surfaces, arcs of higher-order Majorana zero modes exist in certain  $k_z$  regions of the hinges between the BdG Dirac points. Unlike Fermi arcs in Weyl semimetals, the higher-order Majorana arcs are stable against self-annihilation due to an additional  $\mathbb{Z}$ -valued monopole charge of the BdG Dirac points protected by  $C_4$  symmetry. We find that the same  $\mathbb{Z}$ -valued charge is also carried by  $B_{1g}$  and  $B_{2g}$  channels, where the BdG spectrum hosts bulk “nodal cages”, i.e., cages formed by nodal lines, that are stable against symmetry preserving perturbations.

## CONTENTS

I. Introduction	1
II. Dirac semimetals protected by $C_4$ rotation symmetry	3
A. Wannier representation	4
B. HOFAs	4
III. $B_{1u}$ and $B_{2u}$ pairing in Dirac Semimetals	5
A. $B_{1u}$ vs $B_{2u}$ instabilities	6
B. Higher-order topology and HOMAs	7
C. Irremovability of HOMAs due to additional $\mathbb{Z}$ -valued monopole charges	9
D. Mirror-protected gapless surface states and HOMAs	10
E. Symmetry breaking effects	10
IV. Topological properties of other pairing states	11
V. Summary	12
Acknowledgments	12
A. Derivations of form factors $F_{1,2}(\mathbf{k})$	12
B. Topological invariant of the 1D Hamiltonian $H_{1D}(k_x)$	13
References	13

## I. INTRODUCTION

Topological semimetals are gapless states that exhibit topologically stable band crossings in the Brillouin Zone

(BZ), including Weyl [1–11] and Dirac semimetals [12–19], nodal line semimetals [20–28] and multifold fermions [29–31]. Owing to the nontrivial topology, topological semimetals display interesting spectral and transport properties. For example, in Weyl semimetals there exist gapless surface states that are restricted in certain ranges in momentum space, known as Fermi arcs, which leads to interesting features seen in ARPES and quantum oscillation measurements [1–4].

Moreover, topological semimetals are fertile playgrounds for the interplay between correlation effects and band topology. In particular, interacting topological semimetals can host novel superconducting instabilities upon doping, whose topological properties descend from the normal state [32, 33]. For example, in a Weyl semimetal with two Weyl points, it has been shown that *all* possible pairing orders are necessarily topologically obstructed, i.e., hosting point nodes in the BdG spectrum [32]. The topological obstruction comes from a Chern number for surfaces enclosing the Weyl points, which is inherited by the superconducting state. As a consequence, the surface Fermi arcs in the normal states get reconnected in the superconducting states and terminate at the BdG point nodes instead [33].

Recently, the notion of band topology has been extended to higher-order ones, with examples ranging from higher-order topological insulators [34–38], higher-order topological superconductors [28, 39–65], and higher-order topological semimetals [66–70]. In general,  $n$ -th order higher-order topological phases are protected by spatial symmetries and host gapless or degenerate states on its  $(d - n)$ -dimensional boundary ( $1 < n \leq d$ ) while its bulk and surface spectra are gapped. As examples, interesting higher-order topological superconductivity has been shown to emerge from nodal line semimetals [28],

time-reversal invariant Weyl semimetals [39], and Dirac semimetals [40, 41].

Different from Weyl semimetals [1–6], the topological stability of Dirac semimetals requires additional symmetry. In Dirac semimetals such as  $\text{Cd}_3\text{As}_2$  and  $\text{Au}_2\text{Pb}$ , the Dirac points are protected by a  $\mathbb{Z}_2$  topological invariant in the presence of time-reversal, inversion, and four-fold rotational  $\mathcal{C}_4$  symmetries [71–73]. In terms of bulk-boundary correspondence, Dirac semimetals do not host stable Fermi arcs on the surfaces [71, 74–76]. Instead, recent studies have shown that certain Dirac semimetals display higher-order Fermi arcs (HOFAs) [77–79], which are one dimensional (1D) degenerate dispersive states localized on the lower dimensional hinges when two open boundaries intersect [38, 66–68]. The HOFAs terminate at the projections of bulk Dirac points onto 1D hinges, and are protected by the same symmetries protecting the bulk Dirac points.

Superconductivity has been reported in Dirac materials such as  $\text{Cd}_3\text{As}_2$  [80–82] and  $\text{Au}_2\text{Pb}$  [83], followed by several theoretical investigations of topological superconductivity in doped Dirac semimetals [71, 84–86]. In this work we investigate possible topologically obstructed nodal superconducting states from a  $\mathcal{C}_4$  symmetric Dirac semimetal. A similar question was addressed in Ref. [86], but the authors considered a mirror reflection symmetry that squares to +1, which does not apply to these Dirac materials. Furthermore, if such obstructed nodal superconducting states do exist, a natural issue is their indication to the bulk-boundary correspondence, which has not been addressed in the model studied in Ref. [86]. Given that the normal state exhibits nontrivial higher-order topology, such pairing states may display nodal higher-order topological superconductivity.

Motivated by these questions, we begin with a simple tight-binding model for a doped Dirac semimetal with two Dirac points protected by time-reversal symmetry and the  $D_{4h}$  point group [71]. In the normal state, there are two closed Fermi surfaces around each Dirac point. Such a model can be thought of two copies of Weyl semimetals that are time-reversal partners, with two types of spin-orbit coupling terms  $\lambda_1$  and  $\lambda_2$  at lowest order in  $\mathbf{k}$  that couple the two copies. These spin-orbit coupling terms eliminate the surface Fermi arcs and reveals the HOFAs at the hinges.

We show that just like the normal state, the topological obstruction of the superconducting state strongly depends on spatial symmetries and, in particular, the irreducible representation thereof [86]. Out of all possible pairing channels that are irreducible representations of  $D_{4h}$ , we show that  $B_{1u}$  and  $B_{2u}$  pairing channels, both of which are odd in parity, inherit the topological obstruction from the normal state. This is in sharp contrast with superconductivity in doped Weyl semimetals with two Weyl points, in which all possible pairing states are necessarily topologically obstructed and nodal [32]. We compare the relative strength of these two pairing instabilities. Assuming a scenario with Ising ferromagnetic fluc-









Sample Cut		
DSM	 HOFAs	 HOFAs
$B_{1u}$ -DSC	 HOMAs	 gapless
$B_{2u}$ -DSC	 gapless	 HOMAs

TABLE I. Surface states or corner states for a 2D subsystem in different cases. “DSM” refers to Dirac semimetal and “DSC” refers to Dirac superconductor. We use green dots to denote corner states in normal state and red dots to denote corner Majorana zero modes in superconducting state.

tuations, the effective interaction is attractive for both pairing channels, and whether  $B_{1u}$  or  $B_{2u}$  is energetically favorable is determined by the relative strength of  $\lambda_1$  and  $\lambda_2$ . Even for a realistic system beyond the simple tight-binding model we consider, we expect the result to hold for small Fermi surfaces.

We further consider the topological nature and the resulting bulk-boundary correspondence of  $B_{1u}$  and  $B_{2u}$  superconducting states. Crucially, we find that the topological properties are completely determined by the transformation properties of the order parameter under the point group  $D_{4h}$ . We find that the superconducting order parameters create BdG Dirac points residing on the North and South poles of each of the two disjointed FSs in the BdG Hamiltonian. Higher-order Majorana arcs (HOMAs) localized along the hinges of a 3D rod geometry (finite in  $xy$  but infinite along  $z$ ) exist, originating and terminating at the projections of bulk BdG Dirac points onto the hinges. In the normal state, generally HOFAs are dispersive in the spectrum for a finite chemical potential. By contrast, HOMAs are always pinned at zero energy due to the particle-hole symmetry. We show that the existence of HOMAs can be detected by a  $\mathbb{Z}_2$  topological invariant corresponding to the filling anomaly of the 2D subsystems at a given  $k_z$  within the relevant range, captured by the positions of the Wannier center of the 2D subsystem.

Interestingly, unlike the normal state, in the pairing state HOMAs only appear for certain vertical hinges, depending on how the finite sample is cut. Preserving all the point group symmetries, the finite sample can either be in a “square cut” or in a “diamond cut”, with edges at 45 degrees relative to each other.  $B_{1u}$  pairings and  $B_{2u}$  pairings leave certain surfaces gapless. These gapless surfaces are protected by mirror symmetries. Naturally, a finite sample hosts HOMAs only when the surfaces are gapped, which we summarize in Table I.

We further show that the BdG Dirac points host an additional  $\mathbb{Z}$  monopole charge protected by the  $\mathcal{C}_4$  symmetry, which are the same at the same side of the Brillouin zone. As a result, the BdG Dirac points at the North and South poles cannot annihilate each other, and the corresponding HOMAs at the hinges cannot be removed,

at least in the weak-pairing limit.

We note that a method based on inversion-symmetry indicator has been proposed in Ref. [87–89]. However, directly applying their results to our case would yield a trivial result. This is because the indicator there is only a diagnostic for HOMAs at  $k_z = 0$ , while in our cases HOMAs occur at finite  $k_z$ 's. Therefore, our results enrich the classification of HOMAs in Ref. [87].

Based on the same method, we also analyze the topological properties other pairing channels, out of which we identify  $B_{1g}$  and  $B_{2g}$  states as hosting the same monopole charges as the  $B_{1u}$  and  $B_{2u}$  states. However, these states host cages of nodal lines in the spectra; thus the higher-order topology is not well defined. However, each nodal cage still host a well-defined  $\mathbb{Z}$  monopole charge of two, ensuring the stability of the structure.

The rest of this paper is organized as follows. In Sec. II we present the 3D model for a  $\mathcal{C}_4$  symmetric Dirac semimetal and the topological protections of bulk Dirac nodes. We perform a real space Wannier orbital analysis on the 2D slice Hamiltonian between the two bulk Dirac points in Sec. II A and find an inevitable filling anomaly. We claim in Sec. II B that surface states are gapped out by SOC and HOFAs connecting the projections of bulk Dirac points are present in the 3D rod Hamiltonian. In Sec. III, we focus on the odd-parity pairing states in  $B_{1u}/B_{2u}$  channels. We show that they are the leading instabilities induced by Ising ferromagnetic fluctuations, shown in Sec. III A. In Sec. III B, a higher-order  $\mathbb{Z}_2$  invariant from the  $\mathcal{C}_4$  symmetry is defined by applying Wannier orbital analysis to the 2D subsystem of the BdG Hamiltonian, which characterizes the higher-order corner Majorana zero modes. An additional  $\mathbb{Z}$  valued topological invariant protecting HOMAs is identified in Sec. III C. In Sec. III D, we elucidate the relation between HOMAs with gapless surface states protected by mirror symmetries. We discuss the effects of  $\mathcal{C}_4$ , time-reversal and inversion breaking perturbations in Sec. III E. We briefly discuss other pairing channels in Sec. IV. The results are summarized in Sec V.

## II. DIRAC SEMIMETALS PROTECTED BY $\mathcal{C}_4$ ROTATION SYMMETRY

An effective Hamiltonian of a well-known Dirac semimetal such as  $\text{Cd}_3\text{As}_2$  is given by [71]

$$\begin{aligned} H_0(\mathbf{k}) = & [M_0 - t_{xy}(\cos k_x + \cos k_y) - t_z \cos k_z] \sigma_z s_0 \\ & + \eta \sin k_x \sigma_x s_z - \eta \sin k_y \sigma_y s_0 \\ & + \lambda_1 \sin k_z (\cos k_y - \cos k_x) \sigma_x s_x \\ & + \lambda_2 \sin k_z \sin k_x \sin k_y \sigma_x s_y, \end{aligned} \quad (1)$$

where  $M_0, t_{xy}, t_z, \eta, \lambda_1$  and  $\lambda_2$  are model parameters and  $\sigma_i/s_i$  denotes Pauli matrices in orbital/spin spaces. A pair of Dirac points appear at  $(0, 0, \pm k_0)$  in the 3D Brillouin Zone (BZ) for  $t_z > (M_0 - 2t_{xy}) > 0$  and  $k_0$  is defined by  $M_0 = t_z \cos k_0 + 2t_{xy}$  with  $k_0 > 0$ . Eq. (1) includes

all the possible terms up to  $k^3$  order allowed by the symmetries. In particular  $\lambda_1$  and  $\lambda_2$  are two lowest-order spin-orbit coupling terms allowed by symmetry.

The Hamiltonian preserves inversion  $\mathcal{I}$ , time-reversal  $\mathcal{T}$ , three Mirror  $\mathcal{M}_{x,y,z}$ , and a  $\mathcal{C}_4$  rotation symmetry about the  $z$  axis, satisfying

$$\begin{aligned} \mathcal{I}H_0(k_x, k_y, k_z)\mathcal{I}^{-1} &= H_0(-k_x, -k_y, -k_z), \\ \mathcal{T}H_0(k_x, k_y, k_z)\mathcal{T}^{-1} &= H_0(-k_x, -k_y, -k_z), \\ \mathcal{C}_4H_0(k_x, k_y, k_z)\mathcal{C}_4^{-1} &= H_0(k_y, -k_x, k_z), \\ \mathcal{M}_xH_0(k_x, k_y, k_z)\mathcal{M}_x^{-1} &= H_0(-k_x, k_y, k_z), \\ \mathcal{M}_yH_0(k_x, k_y, k_z)\mathcal{M}_y^{-1} &= H_0(k_x, -k_y, k_z), \\ \mathcal{M}_zH_0(k_x, k_y, k_z)\mathcal{M}_z^{-1} &= H_0(k_x, k_y, -k_z), \end{aligned} \quad (2)$$

where

$$\begin{aligned} \mathcal{I} &= \sigma_z, \quad \mathcal{T} = is_y \mathcal{K}, \quad \mathcal{C}_4 = is_z e^{i(\pi/4)\sigma_z s_z}, \\ \mathcal{M}_x &= is_x, \quad \mathcal{M}_y = i\sigma_z s_y, \quad \mathcal{M}_z = is_z. \end{aligned} \quad (3)$$

The forms of the symmetry operators are chosen according to the transformation properties of four spin-orbit coupled degrees of freedom with angular momenta  $J = \pm 1/2$  and  $J = \pm 3/2$ . The corresponding point group of  $H_0(\mathbf{k})$  is  $D_{4h}$ .

To see how  $\mathcal{C}_4$ ,  $\mathcal{T}$ , and  $\mathcal{I}$  together protects the Dirac point, we note that  $(\mathcal{I}\mathcal{T})^2 = -1$ , which protects a two-fold Kramers degeneracy at any point in the BZ. Along  $k_x = k_y = 0$ , every Bloch state can be labeled by its angular momentum under the fourfold rotation symmetry, forming two Kramers pairs. The Dirac points occur at  $k_x = k_y = 0$  when the  $|J| = 1/2$  bands and  $|J| = 3/2$  bands cross, which are robust against any symmetry-preserving perturbations. Here it is important that the two pairs of bands carry different absolute values of angular momenta.

One can define a  $\mathbb{Z}_2$  monopole charge for the Dirac point at  $(0, 0, k_0)$  [71–73], given by

$$\Delta\nu(k_0) = [\nu_J(k_0^+) - \nu_J(k_0^-)] \pmod{2}, \quad (4)$$

where

$$\nu_J(k_0^\pm) = [N_J(0, 0, k_0^\pm) - N_J(\pi, \pi, k_0^\pm)] \pmod{2} \quad (5)$$

and  $N_J(0, 0, k_0^\pm)$  is the number of occupied bands with  $\mathcal{C}_4$  eigenvalue  $J$  at the  $\mathcal{C}_4$ -invariant momenta  $(0, 0, k_0^\pm)$  above (below)  $k_0$  along the  $\mathcal{C}_4$  invariant axis. Time-reversal symmetry and filling constraints ensures that  $\nu_J$  is independent of the particular  $J$  one chooses, and in our model, it is straightforward to verify that  $\Delta\nu(\pm k_0) = 1$ .

We will show in the following subsections that the charge defined in Eq. (4) is a higher-order topological invariant connected with the Wannier representation for each  $k_z$  layer.

### A. Wannier representation

Consider the 2D subsystem of  $H_0(\mathbf{k})$  at a fixed  $k_z$  between two Dirac points

$$\begin{aligned} H_{2D}(k_x, k_y) = & [M'_0 - (\cos k_x + \cos k_y)]\sigma_z s_0 \\ & + \sin k_x \sigma_x s_z - \sin k_y \sigma_y s_0 \\ & + \lambda'_1 (\cos k_y - \cos k_x) \sigma_x s_x \\ & + \lambda'_2 \sin k_x \sin k_y \sigma_x s_y, \end{aligned} \quad (6)$$

where  $M'_0 = M_0 - \cos k_z$ ,  $\lambda'_{1,2} = \lambda_{1,2} \sin k_z$ , and we set  $t_{xy} = t_z = \eta = 1$  without loss of generality. When  $k_z \neq k_0$ ,  $H_{2D}(k_x, k_y)$  describes a 2D subsystem of a crystalline insulator. Note that the slice Hamiltonian  $H_{2D}(k_x, k_y)$  preserves a 2D time reversal symmetry defined by the 3D time reversal operator  $\mathcal{T}$  times the mirror reflection  $\mathcal{M}_z$ , such that

$$\bar{\mathcal{T}} H_{2D}(k_x, k_y) \bar{\mathcal{T}}^{-1} = H_{2D}(-k_x, -k_y), \quad (7)$$

where  $\bar{\mathcal{T}} = \mathcal{T} \mathcal{M}_z = i s_x \mathcal{K}$  and  $\bar{\mathcal{T}}^2 = +1$ . Such a time-reversal symmetry does not enable a Kramers degeneracy and the edges (corresponding to side surfaces at a given  $k_z$ ) are in general gapped. Lacking protected edge states,  $H_{2D}(k_x, k_y)$  for  $k_z \neq \pm k_0$  can be represented by Wannier states.

Constrained by spatial symmetries and  $\mathcal{T}\mathcal{I}$  symmetry, there are two possible representations of two filled Wannier states, with overlapping Wyckoff positions at  $\mathbf{r} = (1/2, 1/2)$  and  $\mathbf{r} = (0, 0)$ . The configuration corresponding to  $H_{2D}(k_x, k_y)$  can be obtained by investigating the  $\mathcal{C}_4$  eigenvalues of the occupied bands at  $\mathcal{C}_4$  invariant momentum  $\Gamma = (0, 0)$  and  $M = (\pi, \pi)$  in the 2D Brillouin zone, which we denote as  $C_\Gamma e^{\pm i \frac{\pi}{4}}$  and  $C_M e^{\pm i \frac{\pi}{4}}$ . Due to  $\mathcal{T}\mathcal{I}$  symmetry ensuring Kramers doublets,  $C_M$  and  $C_\Gamma$  are both real numbers — for  $|J| = 1/2$ , the corresponding  $C_{M,\Gamma} = 1$  and for  $|J| = 3/2$ ,  $C_{M,\Gamma} = -1$ .

One can define a topological invariant

$$(-1)^\nu = C_M C_\Gamma. \quad (8)$$

In real space, it is straightforward to check that  $\nu = 1$  represents the configuration of two Wannier orbitals centered at the Wyckoff position  $\mathbf{r} = (1/2, 1/2)$  and  $\nu = 0$  corresponds to the trivial case when the Wannier centers are at  $\mathbf{r} = (0, 0)$  [41]. Under open boundary conditions, the case with Wannier centers at  $\mathbf{r} = (1/2, 1/2)$  exhibits a filling anomaly, i.e., it is impossible for the system to maintain both charge neutrality and  $\mathcal{C}_4$  rotation symmetry (see Fig. 1). This phenomenon leads to the quantization of fractionalized corner charges in a finite geometry, hence the 2D subsystem is in a second-order topological insulating phase [34–38, 79]. Even though we have only depicted a “square cut” geometry, it can be readily verified that the filling anomaly exists for *any* finite geometry that preserves the  $\mathcal{C}_4$  symmetry, including a “diamond cut” along the diagonal direction.

From Eq. (6), for  $-2 < M_0 - \cos k_z < 2$ , which is precisely the range of  $k_z$  between the two Dirac points,

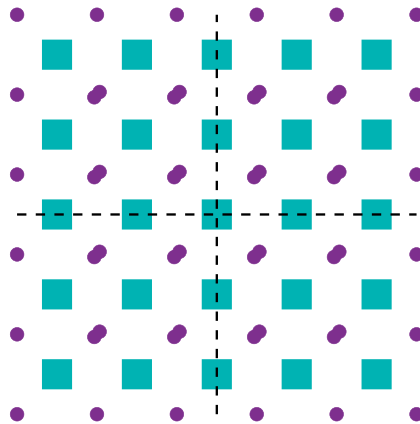


FIG. 1. Wannier representations for the nontrivial phase in 2D subsystem of the Hamiltonian in Eq. (6). Cyan squares represent atom sites and purple dots denote Wannier orbital centers at  $\mathbf{r} = (\frac{1}{2}, \frac{1}{2})$ . Two dashed lines denote mirror planes and their crossing point is the rotation axis. The corner atom site in the finite sample acquires a charge  $\pm \frac{1}{2}e$  due to the filling anomaly.

the filled bands carries  $|J| = 3/2$  at  $\Gamma$  and  $|J| = 1/2$  at  $M$ . Therefore for this range of  $k_z$ , we have  $\nu = 1$ , exhibiting a filling anomaly.

Note that the second-order topological invariant  $\nu$  defined here is equivalent with  $\nu_J$  defined in Eq. (4), and the topological charge  $\Delta\nu$  of the Dirac point can be interpreted as a relative  $\mathbb{Z}_2$  invariant of two  $k$ -space layers sandwiching the Dirac point.

### B. HOFAs

Corresponding to a nontrivial  $\nu = 1$ , one can show that the system in a rod geometry hosts gapless HOFAs on the vertical hinges, provided that the side surfaces are gapped. We note that this necessarily excludes the  $k_z = 0$  slice of the side surfaces due to a mirror Chern number [71]. However, surface states with momenta  $k_z \neq 0, \pm k_0$  can all be gapped out without breaking the symmetries. Our findings are consistent with those obtained in Ref. [77–79], and we present our full analysis here for completeness.

Indeed, this can be seen from splitting Eq. (6) in two parts

$$\begin{aligned} H_{2D} \equiv & H_0 + \lambda'_1 (\cos k_y - \cos k_x) \sigma_x s_x \\ & + \lambda'_2 \sin k_x \sin k_y \sigma_x s_y, \end{aligned} \quad (9)$$

where

$$\begin{aligned} H_0 = & [M'_0 - (\cos k_x + \cos k_y)]\sigma_z s_0 \\ & + \sin k_x \sigma_x s_z - \sin k_y \sigma_y s_0. \end{aligned} \quad (10)$$

It can be readily verified that  $H_0$  hosts helical surface states. On the  $yz$  surfaces they satisfy

$$\sigma_y s_z |\Psi\rangle = \pm |\Psi\rangle, \quad (11)$$

where  $\alpha, \beta$  are constants. For small  $k_y$ , the Hilbert space of the surface Hamiltonian is spanned by  $|\sigma_y = 1\rangle \otimes |s_z = 1\rangle$  and  $|\sigma_y = -1\rangle \otimes |s_z = -1\rangle$ , giving rise to

$$H_0^{yz} \simeq k_y s_z. \quad (12)$$

The surface dispersion  $H_0^{xz}$  on the  $xz$  surface can be similarly obtained. It then follows that  $\lambda'_1$  term in (9) gets projected onto the surface and becomes  $\lambda'_1 \langle k_x^2 \rangle s_y$ , which gaps out the surface Hamiltonian [75, 76, 90]. To see how hinge modes emerge, it is helpful to set  $\lambda'_2 = 0$ , and consider a smooth hinge where  $xz$  and  $yz$  surfaces are smoothly connected. On this smooth manifold, due to the  $\cos k_y - \cos k_x$  dependence,  $\lambda'_1$  term necessarily vanishes in the diagonal direction, indicating a mass domain wall of the helical fermion in Eq. (12), therefore leading to a localized zero mode at the hinge. The  $\lambda'_2$  term has a nonzero projection at the corner, i.e., the diagonal direction, and shifts the energy of the hinge mode. Nonetheless, due to the  $C_4$  symmetry, such an energy shift is the same for all four corners, and thus the hinge modes are degenerate.

The same argument can be applied to obtain hinge states in a ‘‘diamond cut’’, in which the relevant surfaces are  $(x + y), z$  and  $(x - y), z$ . Without  $\lambda'_{1,2}$  terms, the gapless edge states are given by. e.g.,

$$H_0^{(x-y)z} \simeq (k_x - k_y) (\sigma_x s_z + \sigma_y s_0) \quad (13)$$

and

$$\frac{\sigma_x + \sigma_y s_z}{\sqrt{2}} |\Psi\rangle = \pm |\Psi\rangle. \quad (14)$$


The  $\lambda'_2$  term gaps out the surface states such that when viewed as a smooth edge, the gap changes sign from the  $(x - y), z$  surface to the  $(x + y), z$  surface, leading to a zero mode. Further, the  $\lambda'_1$  term displaces the bound state energies while maintaining their degeneracy for all corners.

In Fig. 2 we show numerical results confirming the existence of higher-order corner states in a 2D square cut subsystem and we schematically plot the HOFAs’s in the rod Hamiltonian  $H_0(x, y, k_z)$  in Fig. 3.


### III. $B_{1u}$ AND $B_{2u}$ PAIRING IN DIRAC SEMIMETALS

With a nonzero chemical potential, there exists two closed Fermi surfaces near the two Dirac points. In this section we focus on the odd-parity pairing states belonging to  $B_{1u}$  and  $B_{2u}$  irreducible representations. They are described by the following equal-spin pairing terms:

$$\begin{aligned} B_{1u} : & \Delta_1 \psi^\dagger(\mathbf{k}) (\sigma_y s_0) \psi^\dagger(-\mathbf{k}), \\ B_{2u} : & \Delta_2 \psi^\dagger(\mathbf{k}) (\sigma_y s_z) \psi^\dagger(-\mathbf{k}), \end{aligned} \quad (15)$$

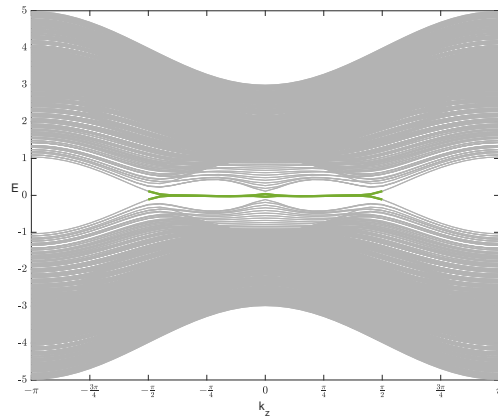

(a)

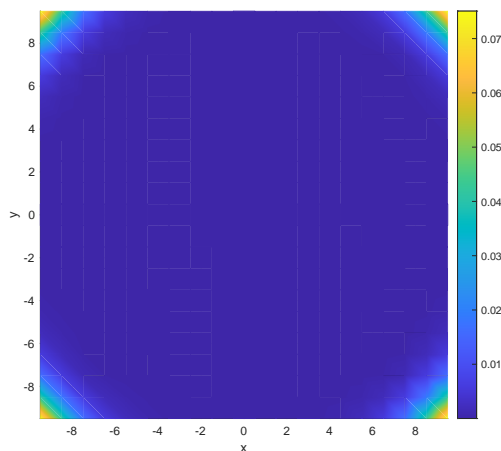

(b)

FIG. 2. (a) Energy spectrum of the rod Hamiltonian  $H_0(x, y, k_z)$  as a function of  $k_z$  for  $N = 20$ . Hinge states are marked Green. (b) Wavefunction distributions of the mid-gap states on a 2D slice in (a) at  $k_z = \pi/4$ . Parameters are  $M_0 = 2$  and  $t_{xy} = t_z = \eta = \lambda_1 = 1$ . The corner states are visible.

and we list their transformation properties under point-group symmetries of  $D_{4h}$  in Table II. Note that, due to the particle-particle nature, the pairing order transforms under symmetry operations as, e.g.,

$$\Delta_1 \sigma_y s_0 \rightarrow \Delta_1 \mathcal{M}_x \sigma_y s_0 \mathcal{M}_x^T = -\Delta_1 \sigma_y s_0. \quad (16)$$

These pairing channels are favored by certain electronic interactions, for example, ferromagnetic spin fluctuations. In fact, we show below that in the presence of short-ranged Ising ferromagnetic fluctuations, the leading pairing instabilities are in these two channels. We will then analyze the topological properties of these two pairing states.

Representative pairing order	Irrep	$C_4 = is_z e^{i\frac{\pi}{4}\sigma_z s_z}$	$\mathcal{I} = \sigma_z$	$\mathcal{M}_x = is_x$	$\mathcal{M}_y = i\sigma_z s_y$	$\mathcal{M}_z = is_z$
$\Delta_1 \sigma_y$	$B_{1u}$	–	–	–	–	–
$\Delta_2 \sigma_y s_z$	$B_{2u}$	–	–	+	+	–

TABLE II. Transformation properties of  $\Delta_1$  and  $\Delta_2$ , which forms  $B_{1u}$  and  $B_{2u}$  irrep of  $D_{4h}$ .

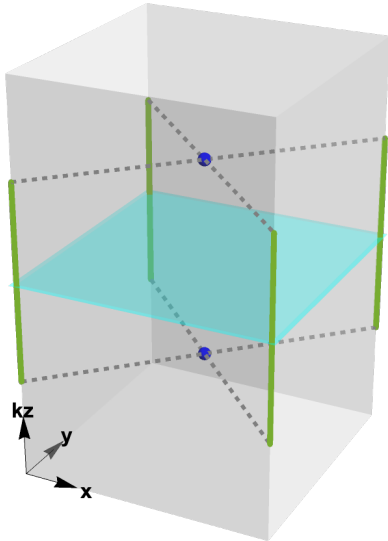


FIG. 3. The  $C_4$  symmetric Dirac semimetal phase in a rod geometry. Two blue dots denote the bulk Dirac points and the cyan plane corresponds to a nontrivial mirror Chern number at  $k_z = 0$ . HOFAs (Green) cross  $k_z = 0$  and terminate at the projections of bulk Dirac nodes onto four vertical hinges.

### A. $B_{1u}$ vs $B_{2u}$ instabilities

Let us consider an electronic interaction that is attractive in both  $B_{1u}$  and  $B_{2u}$  channels. For concreteness, we focus on interactions mediated by short-ranged Ising ferromagnetic fluctuations, given by in second-quantized form

$$\mathcal{H}_{\text{fm}} = V \int d\mathbf{r} [\psi^\dagger(\mathbf{r})(\sigma_0 s_z)\psi(\mathbf{r})]^2, \quad (17)$$

where  $V < 0$  is the strength of the ferromagnetic fluctuation. It is well-known that ferromagnetic spin fluctuations suppress spin-singlet  $s$ -wave ( $A_{1g}$ ) pairing and promote odd-parity pairing. It turns out the leading instabilities with this interaction are in the  $B_{1u}$  and  $B_{2u}$  channels that are equal-spin, orbital-triplet, and constant in  $\mathbf{k}$ . The linearized gap equations are given by

$$\Delta_1 \sigma_y = -T \sum_{\omega_m, \mathbf{k}} V s_z G(i\omega_m, \mathbf{k}) (\Delta_1 \sigma_y) G^T(-i\omega_m, -\mathbf{k}) s_z, \quad (18)$$

$$\Delta_2 \sigma_y s_z = -T \sum_{\omega_m, \mathbf{k}} V s_z G(i\omega_m, \mathbf{k}) (\Delta_2 \sigma_y s_z) G^T(-i\omega_m, -\mathbf{k}) s_z, \quad (19)$$

where  $G(i\omega_m, \mathbf{k}) = [i\omega_m - H_0(\mathbf{k}) + \mu]^{-1}$  is the (matrix) fermionic Green's function, and  $\omega_m$  is the fermionic Matsubara frequency. It can be straightforwardly verified that  $\Delta_1 \sigma_y$  and  $\Delta_2 \sigma_y s_z$  are indeed eigenvectors of the kernel.

After multiplying both sides respectively by  $\sigma_y$  and  $\sigma_y s_z$  and taking the trace, we have

$$\begin{aligned} -1/V &= T_{c1} \sum_{\omega_m, \mathbf{k}} \text{Tr} [\sigma_y G(i\omega_m, \mathbf{k}) \sigma_y G^T(-i\omega_m, -\mathbf{k})] \\ &\equiv \sum_{FS_{\pm}} F_1(\mathbf{k}) \frac{\tanh \frac{\epsilon(\mathbf{k}) - \mu}{2T_{c1}}}{\epsilon(\mathbf{k}) - \mu}, \end{aligned} \quad (20)$$

$$\begin{aligned} -1/V &= T_{c2} \sum_{\omega_m, \mathbf{k}} \text{Tr} [\sigma_y s_z G(i\omega_m, \mathbf{k}) \sigma_y s_z G^T(-i\omega_m, -\mathbf{k})] \\ &\equiv \sum_{FS_{\pm}} F_2(\mathbf{k}) \frac{\tanh \frac{\epsilon(\mathbf{k}) - \mu}{2T_{c2}}}{\epsilon(\mathbf{k}) - \mu}, \end{aligned} \quad (21)$$

where  $\epsilon(\mathbf{k})$  is the dispersion of  $H_0(\mathbf{k})$  and we have assumed  $\mu > 0$ . Note that the momentum summation  $FS_{\pm}$  indicates that only electrons near two Fermi surfaces surrounding  $(0, 0, \pm k_0)$  form Cooper pairs. Beyond the specific interaction we consider, we note that Eq. (20) and (21) hold for *any* short-ranged interaction attractive in these channels. For example, these pairing channels can also be induced by an inter-orbital attractive interactions which dominate over intra-orbital ones [71, 84].

The derivations of form factors  $F_{1,2}(\mathbf{k})$  are given in Appendix A, where we find that

$$F_1(\mathbf{k}) \simeq \frac{k_x^2 + k_y^2 + \lambda_1^2 \left( \frac{k_x^2 - k_y^2}{2} \right)^2 \sin^2 k_0}{\mu^2}, \quad (22)$$

$$F_2(\mathbf{k}) \simeq \frac{k_x^2 + k_y^2 + \lambda_2^2 k_x^2 k_y^2 \sin^2 k_0}{\mu^2}. \quad (23)$$

Here in  $F_{1,2}(\mathbf{k})$  we have set  $\epsilon(\mathbf{k}) = \mu$  and hence the  $\simeq$  sign. For approximately spherical Fermi surfaces, we find that  $\sum_{\mathbf{k}} F_1(\mathbf{k}) > \sum_{\mathbf{k}} F_2(\mathbf{k})$ , i.e.,  $T_{c1} > T_{c2}$  when  $|\lambda_1| > |\lambda_2|$ , thus favoring  $\Delta_1$  as the pairing state, and vice versa. This conclusion holds for small Fermi surfaces that can be sufficiently approximated by a  $k \cdot p$  Hamiltonian. For larger Fermi surfaces a more detailed analysis of the realistic band structure is needed.

We note that  $F_{1,2}(\mathbf{k})$  vanishes at  $k_x = k_y = 0$ , which are the polar points on the two disjoint Fermi surfaces. These  $\mathbf{k}$  points thus do not participate in pairing. In fact, as we shall see, there exist gapless nodal points at the poles of the Fermi surfaces.

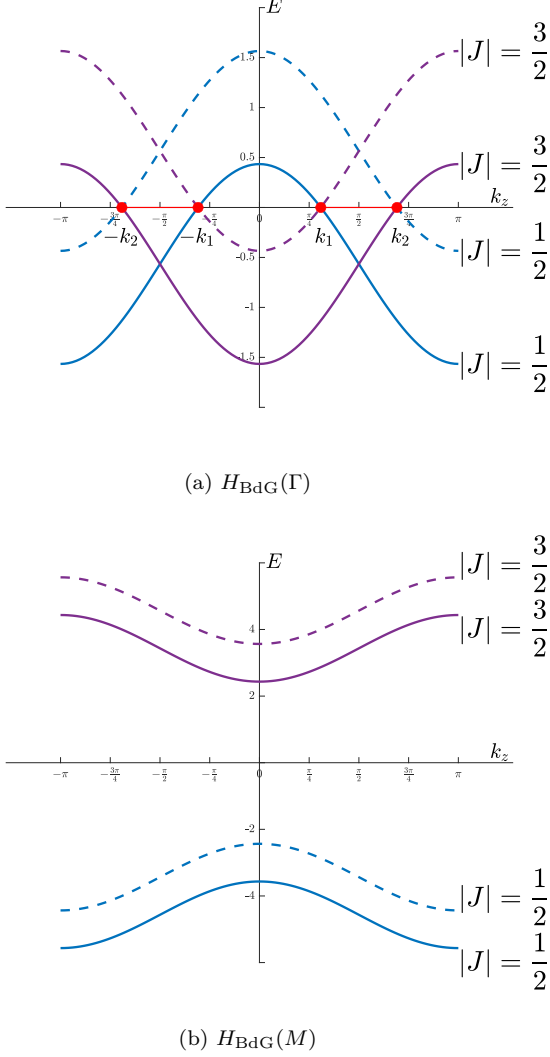


FIG. 4. Energy spectrum of (a)  $H_0(0, 0, k_z)$  and (b)  $H_0(\pi, \pi, k_z)$  with  $M_0 = 2$  and  $\mu = \Delta_1 = 0.4$ . All bands are two-fold degenerate due to the product of time reversal and inversion symmetry  $(\tilde{T}\tilde{I})^2 = -1$ . Purple bands correspond to  $|J| = 3/2$  while blue bands correspond to  $|J| = 1/2$ . Dashed lines denote BdG shadow bands. In (a), there are four BdG Dirac points (marked by red dots) at  $k_z = \pm k_1$  and  $k_z = \pm k_2$ , between which the 2D slice Hamiltonian represents a nontrivial higher-order topological superconducting phase.

## B. Higher-order topology and HOMAs

The corresponding Bogoliubov de Gennes (BdG) Hamiltonian for the  $B_{1u}(B_{2u})$  pairing state is

$$\begin{aligned}
 H_{\text{BdG}}(\mathbf{k}) = & (M_0 - \cos k_x - \cos k_y - \cos k_z)\sigma_z\tau_z \\
 & + \sin k_x\sigma_xs_z - \sin k_y\sigma_y\tau_z - \mu\tau_z \\
 & + \lambda_1 \sin k_z (\cos k_y - \cos k_x)\sigma_xs_x \\
 & + \lambda_2 \sin k_z \sin k_x \sin k_y\sigma_xs_y\tau_z \\
 & + \Delta_1\sigma_y\tau_y (+\Delta_2\sigma_ys_z\tau_x), \quad (24)
 \end{aligned}$$

where  $\tau_{x/y/z}$  are Pauli matrices in the Nambu space. The symmetry operators are elevated to the BdG level as

$$\tilde{I} = \sigma_z\tau_z, \quad \tilde{T} = is_y\mathcal{K}, \quad \tilde{C}_4 = is_z e^{i(\pi/4)\sigma_zs_z\tau_z}. \quad (25)$$

Mirror symmetry operators are different for  $B_{1u}$  and  $B_{2u}$  order, such that

$$\begin{aligned}
 \text{for } B_{1u}, \quad & \tilde{M}_x = is_x, \quad \tilde{M}_y = i\sigma_zs_y\tau_z, \\
 \text{for } B_{2u}, \quad & \tilde{M}_x = is_x\tau_z, \quad \tilde{M}_y = i\sigma_zs_y. \quad (26)
 \end{aligned}$$

Since  $\Delta_1$  and  $\Delta_2$  in general do not coexist from our energetic analysis, all point group symmetries are preserved. In addition, a particle-hole symmetry  $\tilde{\mathcal{P}} = \tau_x\mathcal{K}$  is present, such that  $\tilde{\mathcal{P}}H_{\text{BdG}}(\mathbf{k})\tilde{\mathcal{P}}^{-1} = -H_{\text{BdG}}(-\mathbf{k})$ .

Before we analyze the higher-order topology, it can be directly checked that Eq. (24) has a mirror Chern number  $C_M = 2$  at  $k_z = 0$ . Compared with the normal states, the doubling in  $C_M$  comes from the Nambu space. This corresponds to protected gapless surface states at  $k_z = 0$ . For all other  $k_z$  values the 2D subsystem does not have nontrivial first-order topology, but may still possess nontrivial second-order topology.

By directly diagonalizing the Hamiltonian, we see that  $\Delta_1$  and  $\Delta_2$  pairing terms both create nodal points on the North pole and South pole of the spherical Fermi surface in the bulk BdG spectra. For the  $B_{1u}$  order parameter  $\Delta_1$ , we write down  $H_{\text{BdG}}(\mathbf{k})$  in Eq. (24) along  $(0, 0, k_z)$

$$H_{\text{BdG},\Gamma}(k_z) = -\mu\tau_z - \cos k_z\sigma_z\tau_z + \Delta_1\sigma_y\tau_y, \quad (27)$$

where we set  $M_0 = 2$  without loss of generality. The corresponding energy dispersion is

$$E = \pm \cos k_z \pm \sqrt{\mu^2 + \Delta_1^2}, \quad (28)$$

which we plot in Fig. 4(a). We see that there exist four four-fold degenerate crossing points at zero energy — these are the Dirac points in the BdG spectrum (hereafter referred to as “BdG Dirac points”) pinned to zero energy by particle-hole symmetry. Their locations are at  $(0, 0, k_z)$  with

$$\begin{aligned}
 k_z = \pm k_1 &= \pm \arccos\left(\sqrt{\mu^2 + \Delta_1^2}\right), \text{ and} \\
 k_z = \pm k_2 &\equiv \pm(\pi - k_1). \quad (29)
 \end{aligned}$$

In the weak-pairing limit,  $\Delta \ll \mu$ , and the BdG Dirac points are located at the north and south poles of the two Fermi surfaces.

Using  $B_{1u}$  order parameter as an example, (the analysis for the  $B_{2u}$  order parameter  $\Delta_2$  is exactly the same until Sec. III D), the 2D subsystem of  $H_{\text{BdG}}(\mathbf{k})$  for a  $k_z$  slice is given by

$$\begin{aligned}
 H_{\text{BdG},2d}(k_x, k_y) = & (M'_0 - \cos k_x - \cos k_y)\sigma_z\tau_z \\
 & + \sin k_x\sigma_xs_z - \sin k_y\sigma_y\tau_z \\
 & + \lambda'_1 (\cos k_y - \cos k_x)\sigma_xs_x \\
 & + \lambda'_2 \sin k_x \sin k_y\sigma_xs_y\tau_z \\
 & + \Delta_1\sigma_y\tau_y - \mu\tau_z. \quad (30)
 \end{aligned}$$

$H_{\text{BdG}}(k_x, k_y)$  satisfies the 2D version of time reversal, particle-hole, chiral symmetries and a BdG version of  $\tilde{\mathcal{C}}_4 = \text{diag}\{\mathcal{C}_4, -\mathcal{C}_4\}$ . The system above can be regarded as an insulator before taking the particle-hole symmetry into account, and we can deduce a similar topological invariant following the HOFAs case. The difference is that the corner states in this Hamiltonian are pinned at zero energy due to the particle-hole symmetry, hence they are Majorana zero modes. Eq. (30) then describes a second-order topological superconducting phase in 2D.

In Fig. 4, we label the angular momenta of each BdG band. We see that for  $|k_z| > k_2$  and for  $|k_z| < k_1$ , the four negative-energy bands of the 2D subsystem in Eq. (30) carry the same  $\mathcal{C}_4$  eigenvalues both at  $\Gamma$  and  $M$ . For  $k_1 < k_z < k_2$  and  $-k_2 < k_z < -k_1$ , there are two negative-energy bands with  $|J| = 1/2$  (i.e.,  $\mathcal{C}_4 = \exp(\pm i\pi/4)$ ) and the other two negative-energy bands with  $|J| = 3/2$  (i.e.,  $\mathcal{C}_4 = \exp(\pm 3i\pi/4)$ ) in  $H_{\text{BdG}}(\Gamma)$  — this is simply derived from the normal state band structure. On the other hand, both pairs of negative-energy bands at  $M$  point have  $|J| = 1/2$  (see Fig. 4(b)).

Formally, the same  $\mathbb{Z}_2$  topological invariant for the 2D subsystem can be constructed as a characterization of the second-order topological superconducting phase. With four negative-energy BdG bands, the topological invariant  $\nu$  is given by

$$(-1)^\nu = \prod_i C_{\Gamma,i} C_{M,i} \quad (31)$$

where  $C_{\Gamma,i}$  is defined the same way as in (8) and  $i$  runs over two sets of two-fold degenerate BdG bands. It is now straightforward to see that  $\nu = 1$  for  $-k_2 < k_z < -k_1$  and  $k_1 < k_z < k_2$ , while  $\nu = 0$  otherwise. Mapping to real space, the nontrivial 2D system corresponds to the configuration sketched in Fig. 5, where two Wannier orbitals are centered at  $\mathbf{r} = (1/2, 1/2)$  and two Wannier centers are at  $\mathbf{r} = (0, 0)$ , displaying a filling anomaly. The two  $k_z$  slices sandwiching each of the four BdG Dirac points at  $(0, 0, \pm k_1)$  and  $(0, 0, \pm k_2)$  differ by  $\Delta\nu = 1$ , which can be viewed as the  $\mathbb{Z}_2$  monopole charge of the BdG Dirac points.

To highlight the role of the pairing order in determining the topology, it is helpful to go to the weak-pairing limit  $\Delta \ll \mu$ , i.e., when the pairing order does not change the band structure away from the Fermi surfaces. Note that at  $M$ , one of the negative-energy band with  $J = \pm 1/2$  is the same as the normal state, while the other is the BdG shadow of the unfilled band with  $J = \pm 3/2$ . Importantly, the  $B_{1u}/B_{2u}$  pairing order parameter carry an angular momentum  $\Delta J = 2$ , which causes the shadow band to take a different angular momentum from the original band, which is

$$J = \left( \mp \frac{3}{2} + 2 \right) \pmod{4} = \pm \frac{1}{2}. \quad (32)$$

As at  $\Gamma$  point all the negative-energy states have  $J = \pm 1/2, \pm 3/2$ , there is a mismatch between  $\Gamma$  and  $M$

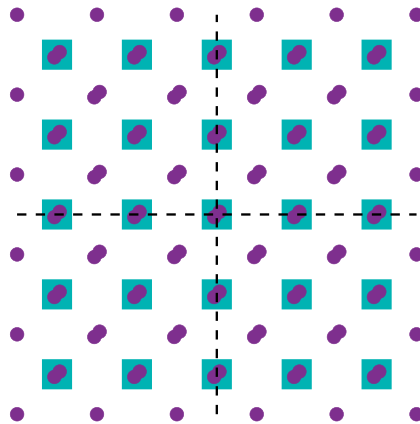


FIG. 5. Wannier representations for the nontrivial phase in 2D subsystem of the BdG Hamiltonian in Eq. (30). Two Wannier orbitals are centered at  $\mathbf{r} = (0, 0)$  and the other two at  $\mathbf{r} = (\frac{1}{2}, \frac{1}{2})$ . Each corner acquires a charge  $\pm \frac{1}{2}e$  due to the filling anomaly, indicating Majorana zero modes.

points, which leads to one pair of Wannier states centered at  $\mathbf{r} = (1/2, 1/2)$  in Fig. 5. Here we see that the nontrivial pairing symmetry  $B_{1u}/B_{2u}$  plays an important role, just as much as the normal state band structure. Had the pairing order transformed trivially under  $\mathcal{C}_4$ , the BdG shadow band would carry instead  $J = \pm 3/2$ , leading to an on-site Wannier center at  $\mathbf{r} = (0, 0)$  and no filling anomaly.

By the same token as in the normal state in a rod geometry, due to the filling anomaly, as long as the side surfaces are gapped (see further discussion on this in Sec. III D), there should be HOMAs in the rod Hamiltonian  $H_{\text{BdG}}(x, y, k_z)$  in these  $k_z$  regions. However, here due to an effective 2D particle-hole symmetry  $\tilde{\mathcal{P}}' \equiv \tilde{\mathcal{P}}\mathcal{M}_z$  of the BdG Hamiltonian, the HOMAs are pinned exactly at zero energy.

We numerically solve the BdG Hamiltonian Eq. (24) and the results that visualize the corner Majorana modes are shown in Fig. 6. At  $k_z = 0$ , the gapless surface modes are due to the mirror Chern number, as we mentioned (see Fig. 6(a)). The 3D rod Hamiltonian  $H_{\text{BdG}}(x, y, k_z)$  displays hinge HOMAs that terminate at the projections of bulk BdG Dirac points, together with surface Majorana helical states at the nontrivial mirror plane  $k_z = 0$ . Generally the HOMAs in this  $\mathcal{C}_4$  symmetric Dirac superconductor are disconnected (see Fig. 7).

As a comparison, a higher-order topological Dirac superconductor phase protected by  $\mathcal{C}_6$  rotation and inversion symmetry is introduced in Ref. [87], which hosts 3D bulk Dirac nodes, 2D gapped surface states and 1D HOMAs simultaneously in the BdG spectrum. The authors also propose an inversion symmetry indicator  $\kappa_{2d}$  at  $k_z = 0$  to characterize the 1D HOMAs. However, this symmetry indicator as a justification of HOMAs does not apply to our case because HOMAs do not cross the



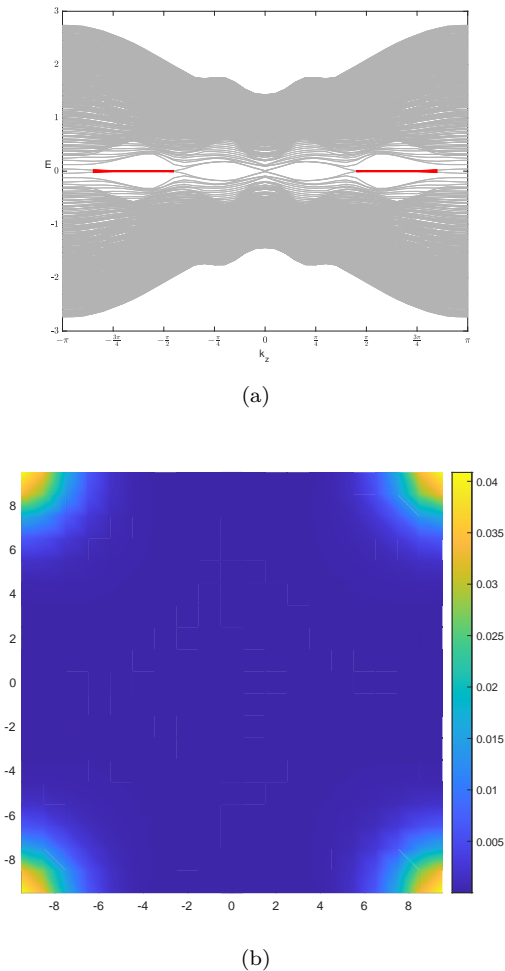


FIG. 6. (a) Energy spectrum of the BdG rod Hamiltonian  $H_{\text{BdG}}(x, y, k_z)$  as a function of  $k_z$  for  $N = 20$ . Red lines represent the mid-gap Majorana zero modes on hinges. (b) Wavefunction distributions of the Majorana corner states on a 2D slice in (a) at  $k_z = 2\pi/3$ . Parameters are  $M_0 = 1.5$ ,  $t_{xy} = t_z = \eta = \lambda_1 = 1$ ,  $\lambda_2 = 0$  and  $\mu = \Delta_1 = 0.4$ .

$k_z = 0$  plane in general. The  $\mathbb{Z}_2$  higher-order topological invariant on a  $k_z$  slice Hamiltonian defined in Eq. (31) is sufficient to diagnose the HOMAs, as long as the surface is gapped. Our  $\mathcal{C}_4$  symmetric Dirac superconductor instead displays a hybrid higher-order topology [91].

### C. Irremovability of HOMAs due to additional $\mathbb{Z}$ -valued monopole charges

In Sec. III B we have identified a nontrivial  $\mathbb{Z}_2$  monopole charge hosted by each of the four BdG Dirac points. If that were the only the monopole charge hosted by a BdG Dirac point, then *any* of the two Dirac points could annihilate each other. In particular, if the BdG Dirac points at  $(0, 0, k_1)$  and  $(0, 0, k_2)$  annihilated, the HOMA terminating at  $k_z = k_1$  and  $k_z = k_2$  would disap-

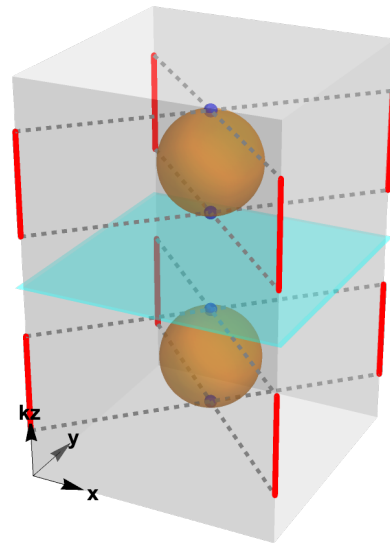


FIG. 7. A schematic plot of the  $\mathcal{C}_4$  symmetric Dirac superconductor phase with hybrid higher-order topology. Two brown spheres represent a pair of disjoint FSs and four blue dots denote the bulk BdG Dirac points on the North poles and South poles of two FSs. Red lines denote HOMAs which sink into the bulk at hinge projections of the four Dirac points. The cyan plane at  $k_z = 0$  carries a nontrivial mirror Chern number, ensuring surface Majorana zero modes.

pear. Since for small Fermi surfaces (small  $\mu$ )  $k_1$  and  $k_2$  are close, this naturally raises the question whether the BdG Dirac points and HOMAs are stable beyond small perturbations.

Fortunately, the BdG Dirac points are stabilized by an additional monopole charge  $\in \mathbb{Z}$  protected by the  $\mathcal{C}_4$  symmetry. To this end, we note that for each  $k_z$  layer

$$\lambda(k_z) = N_{J=1/2}(0, 0, k_z) \in \mathbb{Z}, \quad (33)$$

i.e., the occupation number of the band with  $J = 1/2$  at  $\Gamma$  point, is a topological invariant which cannot change without a gap closing. From Fig. 4(a) it is straightforward to read off that for  $\lambda = 0$  for  $|k_z| < k_1$ ,  $\lambda = 1$  for  $k_1 < |k_z| < k_2$ , and  $\lambda = 2$  for  $|k_z| > k_2$ .

We can thus similarly assign a monopole charge  $\Delta\lambda = 1$  for the BdG Dirac points at  $k_z = k_{1,2}$ , and  $\Delta\lambda = -1$  for  $k_z = -k_{1,2}$  to the BdG Dirac points. Importantly, we see that the BdG Dirac points originating from the same normal state Dirac point, e.g., with  $k_z = k_1$  and  $k_2$ , cannot annihilate, since they carry a total  $\mathbb{Z}$  monopole charge  $\Delta\lambda = 2$  [92]. Just like the  $\mathbb{Z}_2 = 1$  monopole charge  $\Delta\nu$  we showed in Sec. III B, the origin of  $\Delta\lambda = 2$  can be traced back to the nonzero angular momentum carried by the  $B_{1u}$  and  $B_{2u}$  pairing order.

Thus we conclude that the BdG Dirac points are stable due to the additional  $\mathbb{Z}$  monopole charge protected by  $\mathcal{C}_4$  symmetry. As a result, the HOMA connecting the BdG Dirac points is a stable spectral feature that cannot be removed by perturbations. Indeed, in the BdG Hamiltonian Eq. (24), as  $\mu \rightarrow 0$  the two BdG Dirac points with

the same sign of  $k_z$  coincide, but as  $\mu$  changes sign the two BdG Dirac points simply cross each other without annihilating each other.

In spirit, our argument here is similar to the doubly-charged topological nodes studied in Ref. [22] with inversion symmetry only, where an additional topological monopole charge protects the nodal structure from annihilating itself. Our argument goes beyond the classification there, since the  $\mathcal{C}_4$  rotation symmetry plays an important role in defining the additional monopole charge and protecting the HOMAs.

#### D. Mirror-protected gapless surface states and HOMAs

While the higher-order topology and BdG Dirac points are protected by  $\mathcal{C}_4$  and  $\mathcal{TI}$  symmetries alone, the system has many additional spatial symmetries, such as mirror symmetries. As the existence of HOMAs requires the surface states to be gapped, the surfaces need to avoid the orientations in which there are mirror-protected gapless surface states. In this subsection, we show that  $B_{1u}$  state exhibits robust gapless states on the side surfaces in the  $(x \pm y), z$  (diagonal) direction, and similarly for the  $B_{2u}$  state on surfaces in the  $xz$  and  $yz$  direction. Therefore,  $B_{1u}$  and  $B_{2u}$  states exhibit HOMAs in different geometrical configurations. Moreover, we show that the HOMAs obtained previously have a close relationship to these surface states from the perspective of mirror symmetries.

Let us first focus on the  $B_{2u}$  state. For definiteness, we consider a 2D subsystem with  $k_z = k_0$ , a plane that contains the normal-state Dirac point and is topologically nontrivial. Without loss of generality, we set  $\mu = 0$ , and from Eq. (24), the BdG Hamiltonian can be written as

$$\begin{aligned} H_{\text{BdG},2\text{D}}(k_x, k_y) = & (2 - \cos k_x - \cos k_y)\sigma_z\tau_z + \Delta_2\sigma_y s_z\tau_x \\ & + \sin k_x\sigma_x s_z - \sin k_y\sigma_y\tau_z \\ & + \lambda'_1(\cos k_y - \cos k_x)\sigma_x s_x \\ & + \lambda'_2 \sin k_x \sin k_y\sigma_x s_y, \end{aligned} \quad (34)$$

where  $M'_0 = 2$  at  $k_z = k_0$ . We consider the edge of the system along  $x$  and  $y$  direction. For the  $x$ -edge,  $k_y$  is a good quantum number and we set  $k_y = 0$ . The 1D Hamiltonian is

$$\begin{aligned} H_{1\text{D}}(k_x) = & (1 - \cos k_x)\sigma_z\tau_z + \Delta_2\sigma_y s_z\tau_x \\ & + \sin k_x\sigma_x s_z + \lambda'_1(1 - \cos k_x)\sigma_x s_x, \end{aligned} \quad (35)$$

which is symmetric under several composite symmetries, including an effective time-reversal symmetry

$$\tilde{\mathcal{T}}' = \tilde{\mathcal{T}}\tilde{\mathcal{M}}_x\tilde{\mathcal{M}}_y\tilde{\mathcal{I}} = s_x\mathcal{K} \quad (36)$$

and an effective particle-hole symmetry

$$\tilde{\mathcal{P}}' = \tilde{\mathcal{P}}\tilde{\mathcal{M}}_x\tilde{\mathcal{I}} = \sigma_z s_x\tau_x\mathcal{K} \quad (37)$$

satisfying  $\tilde{\mathcal{T}}'^2 = +1$  and  $\tilde{\mathcal{P}}'^2 = +1$ . The two symmetries together place the 1D subsystem  $H_{1\text{D}}(k_x)$  in class BDI [65, 93–97], which admits a  $\mathbb{Z}$  classification given by a winding number. Via a direct computation (see Appendix B), we find that the winding number is  $w = 2$ , corresponding to two Majorana zero modes. Extended to finite  $k_y$ , this indicates that the  $x$ -edge hosts helical Majorana states. Therefore, the  $yz$  and  $xz$  (related to  $yz$  by a  $\mathcal{C}_4$  rotation) surfaces for the  $B_{2u}$  state are gapless.

Similar considerations show that the  $B_{1u}$  state also hosts gapless surfaces. While  $B_{1u}$  and  $B_{2u}$  order parameters transform differently under mirror reflection, it can be directly verified that the  $(x \pm y), z$  surfaces are gapless, protected by the diagonal reflection symmetries  $\tilde{\mathcal{M}}_{x\pm y} \equiv \tilde{\mathcal{M}}_{x,y}\mathcal{C}_4$ .

As the existence of HOMAs requires gapped surfaces, we conclude that the  $B_{1u}$  state hosts HOMAs in a “square cut” (with  $xz$  and  $yz$  surfaces), and the  $B_{2u}$  state hosts HOMAs in a “diamond cut” (with  $(x \pm y), z$  surfaces). This is the central result of this work, illustrated in Table I.

We note that the existence of HOMAs can be analytically understood from the gapless surfaces as well, using an argument similar to that in Sec. II B. Namely, one can view the hinge as a curved surface in the extreme limit. For the  $B_{2u}$  state, as the surface curls away from the  $yz$  direction, the surface helical states acquire a mass, and by continuity the induced mass should change sign as the curved surfaces turn from  $(x + y), z$  direction to  $(x - y), z$  direction. Therefore at the mass domain wall there exists a Majorana zero mode, which is localized at the hinge.

#### E. Symmetry breaking effects

Like those in the normal state, the BdG Dirac points and the HOMAs are stabilized by  $\mathcal{TI}$  and  $\mathcal{C}_4$  symmetries. The mirror symmetries we discussed in Sec. III D can be broken by adding a small  $\sin k_x \sin k_y \sin k_z$  component to the  $\lambda_1$  term, or by mixing  $B_{1u}$  and  $B_{2u}$  states, and gapless surface modes will be removed. Nevertheless, the BdG Dirac points and the HOMAs remain robust due to the remaining  $\mathcal{C}_4$  symmetry.

In a system with an additional inversion breaking term such as  $\sin k_z s_z$ , or an additional time-reversal breaking Zeeman term [85] such as  $m s_z \tau_z$ , the BdG Dirac points split into two Weyl points with opposite chiralities along the  $z$  axis. Surface Majorana arcs appear in  $k_z$  regions between Weyl points with opposite chiralities because the corresponding 2D subsystem carries a non-trivial Chern number and it is not Wannier representable. Since HOMAs are locally protected by a 2D version of particle-hole symmetry  $\mathcal{PM}_z$ , the hinge modes are stable under time reversal breaking perturbations. Therefore, the  $\mathcal{T}$  breaking phase is a higher-order Weyl superconductor defined in Ref. [87], in which HOMAs and surface Majorana arcs coexist. On the other hand, an inversion breaking term breaks  $\mathcal{M}_z$ , and correspondingly destroys

Representative pairing order	Irrep	$\mathcal{C}_4 = is_z e^{i\frac{\pi}{4}\sigma_z s_z}$	$\mathcal{I} = \sigma_z$	$\mathcal{M}_x = is_x$	$\mathcal{M}_y = i\sigma_z s_y$	$\mathcal{M}_z = is_z$
$\Delta_1 \sigma_y$	$B_{1u}$	–	–	–	–	–
$\Delta_2 \sigma_y s_z$	$B_{2u}$	–	–	+	+	–
$\Delta_3 k_z s_x, \Delta_4 k_z \sigma_z s_x$	$A_{1u}$	+	–	–	–	–
$\Delta_5 k_x k_y \sigma_y, \Delta_6 (k_x^2 - k_y^2) \sigma_y s_z$	$A_{2u}$	+	–	+	+	–
$\Delta_7 (\sigma_y s_x, \sigma_x s_y), \Delta_8 k_z (\sigma_z, s_z)$	$E_u$	0	–	0	0	+
$\Delta_9 k_z \sigma_x s_z$	$B_{1g}$	–	+	+	+	+
$\Delta_{10} k_z \sigma_x$	$B_{2g}$	–	+	–	–	+
$\Delta_{11} s_y, \Delta_{12} \sigma_z s_y$	$A_{1g}$	+	+	+	+	+
$\Delta_{13} k_z (k_x^2 - k_y^2) \sigma_x, \Delta_{14} k_z k_x k_y \sigma_x s_z$	$A_{2g}$	+	+	–	–	+
$\Delta_{15} k_z (\sigma_x s_x, \sigma_y s_y)$	$E_g$	0	+	0	0	–

TABLE III. List of representative pairing order, irreducible representations, and their corresponding characters of all possible pairings channels in  $D_{4h}$ . Entries with 0 correspond to 2d representations with opposite eigenvalues.

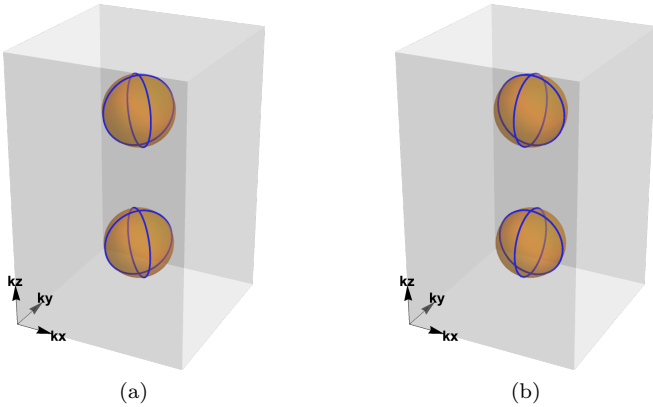


FIG. 8. Schematic plots of bulk nodal cages (marked blue) in the 3D BZ for (a)  $B_{1g}$  and (b)  $B_{2g}$  channels, both  $\mathcal{C}_4$  symmetric. Brown spheres denote Fermi surfaces.

HOMAs.

Moreover,  $\mathcal{C}_4$  symmetry can be broken down to  $\mathcal{C}_2$  e.g., by mixing a  $A_{1u}$  pairing term  $\sin k_z s_x \tau_x$  with  $B_{1u}$ , which gaps out the bulk BdG Dirac points. The 2D slice Hamiltonian thus becomes a boundary obstructed topological superconductor [41], in which corner Majorana modes still exist and are protected by the surface gap instead of the bulk gap. In this case the bulk is fully gapped and the HOMA terminates at a surface gap closing point instead.

#### IV. TOPOLOGICAL PROPERTIES OF OTHER PAIRING STATES

So far we have focused on the  $B_{1u}$  and  $B_{2u}$  pairing channels in a Dirac semimetal. Remarkably, we have shown the topological properties are largely determined by their symmetry properties, in particular the transformation of the pairing order under the  $\mathcal{C}_4$  rotations. In this section we briefly discuss the topological properties

of the system in other pairing channels.

In Table III we list all irreducible representations of the point group  $D_{4h}$  and their representative order parameters to the lowest orders in  $k$ .

We note that  $B_{1g}$  and  $B_{2g}$  orders transform under  $\mathcal{C}_4$  the same way as  $B_{1u}$  and  $B_{2u}$ , but are of even parity. Direct diagonalization of the corresponding BdG Hamiltonians shows that the system exhibits  $\mathcal{C}_4$  symmetric cages of nodal lines [25] in both pairing states between  $k_1 < |k_z| < k_2$ , shown in Fig. 8. These nodal lines are four-fold degenerate, and are protected by a  $2\mathbb{Z}$  topological invariant in the  $AZ+\mathcal{I}$  classification table [22]. The gaplessness of the 2D subsystem for  $k_1 < |k_z| < k_2$  renders the higher-order topological invariant  $\nu$ , and consequently the HOMAs, ill-defined. However, the monopole charge  $\Delta\lambda = \lambda(k > k_2) - \lambda(k < k_1)$ , is still valid. As  $\lambda$  in Eq. (33) is solely determined by  $\mathcal{C}_4$  operations, which is identical for  $B_{1g}/B_{2g}$  and for  $B_{1u}/B_{2u}$ , we conclude, by a similar analysis to that in Secs. IIIB and IIIC, that the nodal cage also carries a monopole charge of  $\Delta\lambda = 2$ . For this reason, the nodal cages are stable and cannot self-annihilate. Indeed, as  $\mu$  goes through zero, the nodal cages shrink to a point but then reemerges. In this case they are protected by a doubly charged monopole beyond the classification in Ref. [22].

The entries ( $E_u$  and  $E_g$ ) with characters 0 indicates these irreps are two-dimensional; indeed they have angular momenta  $\pm 1$ , each of which breaks time-reversal symmetry. In these cases the system either breaks time-reversal or  $\mathcal{C}_4$  symmetry, but cannot preserve both. Yet, they may still exhibit interesting topological properties. However, we will restrict ourselves to time-reversal and  $\mathcal{C}_4$  invariant system in this work and leave a detailed analysis of the  $E_u$  and  $E_g$  states to a future study.

All other pairing channels transform trivially under  $\mathcal{C}_4$  rotation, and it is straightforward to show that they do not carry any nontrivial  $\mathbb{Z}_2$  or  $\mathbb{Z}$  monopole charges in relation to HOMAs studied here. A recent study [98] investigated a  $A_{1g}$  pairing channel with a special form factor in doped Dirac semimetals. The authors found a second-order topological superconducting phase with helical Ma-

gorana modes on the top and bottom hinges. However, this nontrivial phase requires a fine tuning of model parameters. The conclusion that a Dirac semimetal is topologically obstructed only for certain pairing channels was also obtained in Ref. [86]. However, the symmetries in consideration are different from those in our case.

Finally, while we demonstrated from a microscopic calculation that  $B_{1u}$  and  $B_{2u}$  pairing orders are naturally induced by Ising-ferromagnetic fluctuations, an interesting open problem is what microscopic interactions promote other nontrivial pairing channels, such as  $B_{1g}$  and  $B_{2g}$ .

## V. SUMMARY

In this work, we analyzed the higher-order topology in superconducting Dirac semimetals protected by fourfold rotation, spatial inversion and time reversal symmetries. In the normal state, the Dirac semimetal is known [77–79] to exhibit HOFAs. We showed that in certain pairing channels the normal state topology gets inherited in the superconducting state.

First, we showed that in the presence of an Ising-ferromagnetic fluctuations, the leading pairing instability of the system is toward  $B_{1u}$  or  $B_{2u}$  pairing orders. These pairing states display Dirac nodal points in the BdG spectrum. In a rod geometry, they display HOMA states at the hinges that terminate at the projections of bulk BdG Dirac points onto the hinges. While HOFAs are generally dispersive in the energy spectrum, HOMAs are pinned at zero energy due to the particle-hole symmetry. Importantly, the BdG Dirac points and the HOMAs are protected by an additional  $\mathbb{Z}$  valued monopole charge defined via the  $\mathcal{C}_4$  symmetry.

Moreover, the recipe for diagnosis of higher-order topology and monopole charge here can be directly applied to all other pairing orders, which are irreps of the

$D_{4h}$  group. In particular, we found that  $B_{1g}$  or  $B_{2g}$  displays nodal cages with a monopole charge, each of which is stable under  $\mathcal{C}_4$  symmetric perturbations.

In this work we showed that Dirac semimetals are promising “parent states” for higher-order topological superconducting states. Since HOFAs have been experimentally confirmed in the Dirac semimetal  $\text{Cd}_3\text{As}_2$  [99, 100], it would be interesting to search for nontrivial pairing states in these systems.

## ACKNOWLEDGMENTS

We thank Yi Li, Shengshan Qin, and Junyi Zhang for illuminating discussions. The work is supported by startup funds at the University of Florida and by NSF under award number DMR-2045781.

### Appendix A: Derivations of form factors $F_{1,2}(\mathbf{k})$

We simplify the form of the normal state Hamiltonian  $H_0(\mathbf{k})$  in Eq. (1) as

$$H_0(\mathbf{k}) = f_1(\mathbf{k})\sigma_z + f_2(\mathbf{k})\sigma_x s_z + f_3(\mathbf{k})\sigma_y + f_4(\mathbf{k})\sigma_x s_x + f_5(\mathbf{k})\sigma_x s_y. \quad (\text{A1})$$

The Green’s function for finite  $\mu$  is given by

$$G_0(i\omega_m, \mathbf{k}) = [i\omega_m - H_0(\mathbf{k}) + \mu]^{-1} = \frac{(i\omega_m + \mu)\sigma_0 s_0 + H_0(\mathbf{k})}{(i\omega_m + \mu)^2 - \epsilon^2}, \quad (\text{A2})$$

where  $\omega_m = (2m + 1)\pi T$  is the fermionic Matsubara frequency and  $\epsilon = \sum_{i=1}^5 \sqrt{f_i^2(\mathbf{k})}$  is the dispersion. The trace in Eq. (20) can be explicitly evaluated as (e.g., for  $\Delta_1$ )

$$\begin{aligned} & \text{Tr} [\sigma_y G_0(i\omega_m, \mathbf{k}) \sigma_y G_0^T(-i\omega_m, -\mathbf{k})] \\ &= \frac{\text{Tr} \{ [(i\omega_m + \mu)\sigma_0 s_0 + \sigma_y H_0(\mathbf{k}) \sigma_y] [(-i\omega_m + \mu)\sigma_0 s_0 + H_0^T(-\mathbf{k})] \}}{[(i\omega_m + \mu)^2 - \epsilon^2][(-i\omega_m + \mu)^2 - \epsilon^2]} \\ &= \frac{\text{Tr} \{ (\omega_m^2 + \mu^2)\sigma_0 s_0 + \sigma_y H_0(\mathbf{k}) \sigma_y H_0^T(-\mathbf{k}) \}}{[\omega_m^2 + (\epsilon + \mu)^2][\omega_m^2 + (\epsilon - \mu)^2]} \\ &= \frac{4[\omega_m^2 + \mu^2 - \epsilon^2 + 2(f_2^2(\mathbf{k}) + f_3^2(\mathbf{k}) + f_4^2(\mathbf{k}))]}{[\omega_m^2 + (\epsilon + \mu)^2][\omega_m^2 + (\epsilon - \mu)^2]} \\ &\simeq \frac{2[f_2^2(\mathbf{k}) + f_3^2(\mathbf{k}) + f_4^2(\mathbf{k})]}{\mu^2[\omega_m^2 + (\epsilon - \mu)^2]}, \end{aligned} \quad (\text{A3})$$

where we take  $\epsilon \simeq \mu$  in the last step. The sum over Matsubara frequencies yields

$$\begin{aligned} & T_{c1} \sum_{\omega_m} \frac{2[f_2^2(\mathbf{k}) + f_3^2(\mathbf{k}) + f_4^2(\mathbf{k})]}{\mu^2[\omega_m^2 + (\epsilon - \mu)^2]} \\ &= \frac{f_2^2(\mathbf{k}) + f_3^2(\mathbf{k}) + f_4^2(\mathbf{k})}{\mu^2} \frac{\tanh \frac{\epsilon - \mu}{2T_{c1}}}{\epsilon - \mu}. \end{aligned} \quad (\text{A4})$$

There are two nearly spherical Fermi pockets surrounding the Dirac points at  $(0, 0, \pm k_0)$ . By expanding  $f_2(\mathbf{k})$ ,  $f_3(\mathbf{k})$  and  $f_4(\mathbf{k})$  in lowest order of momentum, we obtain

the corresponding  $F_1(\mathbf{k})$  in the main text.  $F_2(\mathbf{k})$  can be derived similarly.

### Appendix B: Topological invariant of the 1D Hamiltonian $H_{1D}(k_x)$

We follow Ref. [93] to derive the topological invariant of the Hamiltonian in Eq. (35). Note that  $H_{1D}(k_x)$  has a chiral symmetry defined as  $\tilde{S} = \tilde{T}'\tilde{P}' = \sigma_z\tau_x$ , such that  $\tilde{S}H_{1D}(k_x)\tilde{S}^{-1} = -H_{1D}(k_x)$ . It can be made purely off-diagonal by a unitary transformation in the particle-hole space

$$\tilde{H}(k_x) = UH_{1D}(k_x)U^\dagger = \begin{bmatrix} & A(k_x) \\ A^\dagger(k_x) & \end{bmatrix}, \quad (\text{B1})$$

where  $U = e^{-i\frac{\pi}{4}\tau_y}$  and we obtain

$$A(k_x) = (1 - \cos k_x)s_0\nu_z + (\sin k_x + i\Delta_2)s_z\nu_x + \lambda'_1(1 - \cos k_x)s_x\nu_x, \quad (\text{B2})$$

where  $\nu_{x,y,z}$  are Pauli matrices spanning the subspace ( $\sigma_z\tau_z = 1|\sigma_i\tau_j|\sigma_z\tau_z = -1$ ). The topological invariant in BDI class is defined as the winding number of the phase factor carried by  $\det A(k_x)$ , which is

$$w = \frac{-i}{\pi} \int_{k_x=0}^{k_x=\pi} \frac{dz(k_x)}{z(k_x)}, \quad (\text{B3})$$

where  $z(k_x) = e^{i\theta(k_x)} = \det A(k_x)/|\det A(k_x)|$ . Note that

$$\det A(k_x) = [(1 + \lambda_1'^2)(1 - \cos k_x)^2 + \sin^2 k_x - \Delta_2^2 + 2i\Delta_2 \sin k_x]^2 \quad (\text{B4})$$

and  $\Delta_2 \ll 1$  in the weak pairing limit. Hence  $\theta(k_x)$  shifts from  $k_x = 0$  to  $k_x = \pi$  by  $2\pi$ , which gives rise to a winding number  $w = 2$ .

- 
- [1] B. Q. Lv, H. M. Weng, B. B. Fu, X. P. Wang, H. Miao, J. Ma, P. Richard, X. C. Huang, L. X. Zhao, G. F. Chen, Z. Fang, X. Dai, T. Qian, and H. Ding, Experimental Discovery of Weyl Semimetal TaAs, *Phys. Rev. X* **5**, 031013 (2015).
- [2] S.-Y. Xu, I. Belopolski, N. Alidoust, M. Neupane, G. Bian, C. Zhang, R. Sankar, G. Chang, Z. Yuan, C.-C. Lee, S.-M. Huang, H. Zheng, J. Ma, D. S. Sanchez, B. Wang, A. Bansil, F. Chou, P. P. Shibayev, H. Lin, S. Jia, and M. Z. Hasan, Discovery of a Weyl fermion semimetal and topological Fermi arcs, *Science* **349**, 613 (2015).
- [3] S.-Y. Xu, N. Alidoust, I. Belopolski, Z. Yuan, G. Bian, T.-R. Chang, H. Zheng, V. N. Strocov, D. S. Sanchez, G. Chang, C. Zhang, D. Mou, Y. Wu, L. Huang, C.-C. Lee, S.-M. Huang, B. Wang, A. Bansil, H.-T. Jeng, T. Neupert, A. Kaminski, H. Lin, S. Jia, and M. Zahid Hasan, Discovery of a Weyl fermion state with Fermi arcs in niobium arsenide, *Nature Physics* **11**, 748 (2015).
- [4] B. Q. Lv, N. Xu, H. M. Weng, J. Z. Ma, P. Richard, X. C. Huang, L. X. Zhao, G. F. Chen, C. E. Matt, F. Bisti, V. N. Strocov, J. Mesot, Z. Fang, X. Dai, T. Qian, M. Shi, and H. Ding, Observation of Weyl nodes in TaAs, *Nature Physics* **11**, 724 (2015).
- [5] X. Wan, A. M. Turner, A. Vishwanath, and S. Y. Savrasov, Topological semimetal and Fermi-arc surface states in the electronic structure of pyrochlore iridates, *Phys. Rev. B* **83**, 205101 (2011).
- [6] S.-M. Huang, S.-Y. Xu, I. Belopolski, C.-C. Lee, G. Chang, B. Wang, N. Alidoust, G. Bian, M. Neupane, C. Zhang, S. Jia, A. Bansil, H. Lin, and M. Z. Hasan, A Weyl Fermion semimetal with surface Fermi arcs in the transition metal monpnictide TaAs class, *Nature Communications* **6**, 7373 (2015).
- [7] H. Weng, C. Fang, Z. Fang, B. A. Bernevig, and X. Dai, Weyl Semimetal Phase in Noncentrosymmetric Transition-Metal Monophosphides, *Phys. Rev. X* **5**, 011029 (2015).
- [8] S. Murakami, M. Hirayama, R. Okugawa, and T. Miyake, Emergence of topological semimetals in gap closing in semiconductors without inversion symmetry, *Science Advances* **3**, e1602680 (2017).
- [9] A. A. Burkov, M. D. Hook, and L. Balents, Topological nodal semimetals, *Phys. Rev. B* **84**, 235126 (2011).
- [10] A. A. Burkov and L. Balents, Weyl Semimetal in a Topological Insulator Multilayer, *Phys. Rev. Lett.* **107**, 127205 (2011).
- [11] K.-Y. Yang, Y.-M. Lu, and Y. Ran, Quantum Hall effects in a Weyl semimetal: Possible application in pyrochlore iridates, *Phys. Rev. B* **84**, 075129 (2011).
- [12] J. A. Steinberg, S. M. Young, S. Zaheer, C. L. Kane, E. J. Mele, and A. M. Rappe, Bulk Dirac Points in Distorted Spinels, *Phys. Rev. Lett.* **112**, 036403 (2014).
- [13] Z. K. Liu, J. Jiang, B. Zhou, Z. J. Wang, Y. Zhang, H. M. Weng, D. Prabhakaran, S.-K. Mo, H. Peng, P. Dudin, T. Kim, M. Hoesch, Z. Fang, X. Dai, Z. X. Shen, D. L. Feng, Z. Hussain, and Y. L. Chen, A stable three-dimensional topological Dirac semimetal Cd<sub>3</sub>As<sub>2</sub>, *Nature Materials* **13**, 677 (2014).
- [14] Z. K. Liu, B. Zhou, Y. Zhang, Z. J. Wang, H. M. Weng, D. Prabhakaran, S.-K. Mo, Z. X. Shen, Z. Fang, X. Dai, Z. Hussain, and Y. L. Chen, Discovery of a Three-Dimensional Topological Dirac Semimetal, Na<sub>3</sub>Bi, *Science* **343**, 864 (2014).
- [15] Z. Wang, Y. Sun, X.-Q. Chen, C. Franchini, G. Xu, H. Weng, X. Dai, and Z. Fang, Dirac semimetal and topological phase transitions in A<sub>3</sub>Bi (A = Na, K, Rb), *Phys. Rev. B* **85**, 195320 (2012).
- [16] S. M. Young, S. Zaheer, J. C. Y. Teo, C. L. Kane, E. J. Mele, and A. M. Rappe, Dirac Semimetal in Three Dimensions, *Phys. Rev. Lett.* **108**, 140405 (2012).

- [17] Z. Wang, H. Weng, Q. Wu, X. Dai, and Z. Fang, Three-dimensional Dirac semimetal and quantum transport in  $\text{Cd}_3\text{As}_2$ , *Phys. Rev. B* **88**, 125427 (2013).
- [18] I. Crassee, R. Sankar, W.-L. Lee, A. Akrap, and M. Orlita, 3D Dirac semimetal  $\text{Cd}_3\text{As}_2$ : A review of material properties, *Phys. Rev. Materials* **2**, 120302 (2018).
- [19] L. M. Schoop, L. S. Xie, R. Chen, Q. D. Gibson, S. H. Lapidus, I. Kimchi, M. Hirschberger, N. Haldolaarachchige, M. N. Ali, C. A. Belvin, T. Liang, J. B. Neaton, N. P. Ong, A. Vishwanath, and R. J. Cava, Dirac metal to topological metal transition at a structural phase change in  $\text{Au}_2\text{Pb}$  and prediction of  $\mathbb{Z}_2$  topology for the superconductor, *Phys. Rev. B* **91**, 214517 (2015).
- [20] Y. X. Zhao, A. P. Schnyder, and Z. D. Wang, Unified Theory of  $PT$  and  $CP$  Invariant Topological Metals and Nodal Superconductors, *Phys. Rev. Lett.* **116**, 156402 (2016).
- [21] Z. Song, T. Zhang, and C. Fang, Diagnosis for Nonmagnetic Topological Semimetals in the Absence of Spin-Orbital Coupling, *Phys. Rev. X* **8**, 031069 (2018).
- [22] T. Bzdušek and M. Sigrist, Robust doubly charged nodal lines and nodal surfaces in centrosymmetric systems, *Phys. Rev. B* **96**, 155105 (2017).
- [23] C. Fang, Y. Chen, H.-Y. Kee, and L. Fu, Topological nodal line semimetals with and without spin-orbital coupling, *Phys. Rev. B* **92**, 081201 (2015).
- [24] J. Ahn, D. Kim, Y. Kim, and B.-J. Yang, Band Topology and Linking Structure of Nodal Line Semimetals with  $\mathbb{Z}_2$  Monopole Charges, *Phys. Rev. Lett.* **121**, 106403 (2018).
- [25] H. Li, C. Fang, and K. Sun, Diagnosis of topological nodal lines with nontrivial monopole charge in the presence of rotation symmetries, *Phys. Rev. B* **100**, 195308 (2019).
- [26] C.-K. Chiu and A. P. Schnyder, Classification of reflection-symmetry-protected topological semimetals and nodal superconductors, *Phys. Rev. B* **90**, 205136 (2014).
- [27] Y. Kim, B. J. Wieder, C. L. Kane, and A. M. Rappe, Dirac Line Nodes in Inversion-Symmetric Crystals, *Phys. Rev. Lett.* **115**, 036806 (2015).
- [28] J. Ahn and B.-J. Yang, Higher-order topological superconductivity of spin-polarized fermions, *Phys. Rev. Research* **2**, 012060 (2020).
- [29] B. Bradlyn, J. Cano, Z. Wang, M. G. Vergniory, C. Felser, R. J. Cava, and B. A. Bernevig, Beyond Dirac and Weyl fermions: Unconventional quasiparticles in conventional crystals, *Science* **353**, aaf5037 (2016).
- [30] B. J. Wieder, Y. Kim, A. M. Rappe, and C. L. Kane, Double Dirac Semimetals in Three Dimensions, *Phys. Rev. Lett.* **116**, 186402 (2016).
- [31] J. Cano, B. Bradlyn, and M. G. Vergniory, Multifold nodal points in magnetic materials, *APL Materials* **7**, 101125 (2019).
- [32] Y. Li and F. D. M. Haldane, Topological Nodal Cooper Pairing in Doped Weyl Metals, *Phys. Rev. Lett.* **120**, 067003 (2018).
- [33] B. Lu, K. Yada, M. Sato, and Y. Tanaka, Crossed Surface Flat Bands of Weyl Semimetal Superconductors, *Phys. Rev. Lett.* **114**, 096804 (2015).
- [34] W. A. Benalcazar, T. Li, and T. L. Hughes, Quantization of fractional corner charge in  $C_n$ -symmetric higher-order topological crystalline insulators, *Phys. Rev. B* **99**, 245151 (2019).
- [35] W. A. Benalcazar, B. A. Bernevig, and T. L. Hughes, Quantized electric multipole insulators, *Science* **357**, 61 (2017).
- [36] W. A. Benalcazar, B. A. Bernevig, and T. L. Hughes, Electric multipole moments, topological multipole moment pumping, and chiral hinge states in crystalline insulators, *Phys. Rev. B* **96**, 245115 (2017).
- [37] F. Schindler, M. Brzezińska, W. A. Benalcazar, M. Iraola, A. Bouhon, S. S. Tsirkin, M. G. Vergniory, and T. Neupert, Fractional corner charges in spin-orbit coupled crystals, *Phys. Rev. Research* **1**, 033074 (2019).
- [38] Z. Song, Z. Fang, and C. Fang, (d-2)-Dimensional Edge States of Rotation Symmetry Protected Topological States, *Phys. Rev. Lett.* **119**, 246402 (2017).
- [39] A. Jahin, A. Tiwari, and Y. Wang, Higher-order topological superconductors from Weyl semimetals, *SciPost Phys.* **12**, 53 (2022).
- [40] Y. Wang, M. Lin, and T. L. Hughes, Weak-pairing higher order topological superconductors, *Phys. Rev. B* **98**, 165144 (2018).
- [41] A. Tiwari, A. Jahin, and Y. Wang, Chiral Dirac superconductors: Second-order and boundary-obstructed topology, *Phys. Rev. Research* **2**, 043300 (2020).
- [42] X. Zhu, Second-Order Topological Superconductors with Mixed Pairing, *Phys. Rev. Lett.* **122**, 236401 (2019).
- [43] J. Langbehn, Y. Peng, L. Trifunovic, F. von Oppen, and P. W. Brouwer, Reflection-Symmetric Second-Order Topological Insulators and Superconductors, *Phys. Rev. Lett.* **119**, 246401 (2017).
- [44] E. Khalaf, Higher-order topological insulators and superconductors protected by inversion symmetry, *Phys. Rev. B* **97**, 205136 (2018).
- [45] M. Kheirkhah, Z. Yan, Y. Nagai, and F. Marsiglio, First- and Second-Order Topological Superconductivity and Temperature-Driven Topological Phase Transitions in the Extended Hubbard Model with Spin-Orbit Coupling, *Phys. Rev. Lett.* **125**, 017001 (2020).
- [46] Q. Wang, C.-C. Liu, Y.-M. Lu, and F. Zhang, High-Temperature Majorana Corner States, *Phys. Rev. Lett.* **121**, 186801 (2018).
- [47] Z. Wu, Z. Yan, and W. Huang, Higher-order topological superconductivity: Possible realization in Fermi gases and  $\text{Sr}_2\text{RuO}_4$ , *Phys. Rev. B* **99**, 020508 (2019).
- [48] C.-H. Hsu, P. Stano, J. Klinovaja, and D. Loss, Majorana Kramers Pairs in Higher-Order Topological Insulators, *Phys. Rev. Lett.* **121**, 196801 (2018).
- [49] T. Liu, J. J. He, and F. Nori, Majorana corner states in a two-dimensional magnetic topological insulator on a high-temperature superconductor, *Phys. Rev. B* **98**, 245413 (2018).
- [50] Y. Volpez, D. Loss, and J. Klinovaja, Second-Order Topological Superconductivity in  $\pi$ -Junction Rashba Layers, *Phys. Rev. Lett.* **122**, 126402 (2019).
- [51] R.-X. Zhang, W. S. Cole, and S. Das Sarma, Helical Hinge Majorana Modes in Iron-Based Superconductors, *Phys. Rev. Lett.* **122**, 187001 (2019).
- [52] Z. Yan, Higher-Order Topological Odd-Parity Superconductors, *Phys. Rev. Lett.* **123**, 177001 (2019).
- [53] X.-H. Pan, K.-J. Yang, L. Chen, G. Xu, C.-X. Liu, and X. Liu, Lattice-Symmetry-Assisted Second-Order Topological Superconductors and Majorana Patterns, *Phys. Rev. Lett.* **123**, 156801 (2019).

- [54] R.-X. Zhang, W. S. Cole, X. Wu, and S. Das Sarma, Higher-Order Topology and Nodal Topological Superconductivity in Fe(Se,Te) Heterostructures, *Phys. Rev. Lett.* **123**, 167001 (2019).
- [55] M. Kheirkhah, Y. Nagai, C. Chen, and F. Marsiglio, Majorana corner flat bands in two-dimensional second-order topological superconductors, *Phys. Rev. B* **101**, 104502 (2020).
- [56] Y.-T. Hsu, W. S. Cole, R.-X. Zhang, and J. D. Sau, Inversion-Protected Higher-Order Topological Superconductivity in Monolayer WTe<sub>2</sub>, *Phys. Rev. Lett.* **125**, 097001 (2020).
- [57] B. Roy, Higher-order topological superconductors in  $\mathcal{P}$ -,  $\mathcal{T}$ -odd quadrupolar Dirac materials, *Phys. Rev. B* **101**, 220506 (2020).
- [58] B. Roy and V. Juričić, Mixed-parity octupolar pairing and corner Majorana modes in three dimensions, *Phys. Rev. B* **104**, L180503 (2021).
- [59] D. Vu, R.-X. Zhang, and S. Das Sarma, Time-reversal-invariant  $C_2$ -symmetric higher-order topological superconductors, *Phys. Rev. Research* **2**, 043223 (2020).
- [60] M. Kheirkhah, Z. Yan, and F. Marsiglio, Vortex-line topology in iron-based superconductors with and without second-order topology, *Phys. Rev. B* **103**, L140502 (2021).
- [61] A. K. Ghosh, T. Nag, and A. Saha, Hierarchy of higher-order topological superconductors in three dimensions, *Phys. Rev. B* **104**, 134508 (2021).
- [62] X.-J. Luo, X.-H. Pan, and X. Liu, Higher-order topological superconductors based on weak topological insulators, *Phys. Rev. B* **104**, 104510 (2021).
- [63] K. Plekhanov, N. Müller, Y. Volpez, D. M. Kennes, H. Schoeller, D. Loss, and J. Klinovaja, Quadrupole spin polarization as signature of second-order topological superconductors, *Phys. Rev. B* **103**, L041401 (2021).
- [64] S. Qin, C. Fang, F.-C. Zhang, and J. Hu, Topological Superconductivity in an Extended  $s$ -Wave Superconductor and Its Implication to Iron-Based Superconductors, *Phys. Rev. X* **12**, 011030 (2022).
- [65] S. Qin, Z. Zhang, Y. Wang, C. Fang, F.-c. Zhang, and J. Hu, Symmetry-Protected Topological Superconductivity in Magnetic Metals (2022), [arXiv:2208.10225](https://arxiv.org/abs/2208.10225) [cond-mat.supr-con].
- [66] M. Lin and T. L. Hughes, Topological quadrupolar semimetals, *Phys. Rev. B* **98**, 241103 (2018).
- [67] S. A. A. Ghorashi, T. Li, and T. L. Hughes, Higher-Order Weyl Semimetals, *Phys. Rev. Lett.* **125**, 266804 (2020).
- [68] Y. Zhou and P. Ye, Entanglement Signature of Hinge Arcs, Fermi Arcs, and Crystalline Symmetry Protection in Higher-Order Weyl Semimetals (2022), [arXiv:2205.01654](https://arxiv.org/abs/2205.01654) [cond-mat.supr-con].
- [69] S. A. A. Ghorashi, T. Li, and M. Sato, Non-Hermitian higher-order Weyl semimetals, *Phys. Rev. B* **104**, L161117 (2021).
- [70] S. A. A. Ghorashi, T. Li, M. Sato, and T. L. Hughes, Non-Hermitian higher-order Dirac semimetals, *Phys. Rev. B* **104**, L161116 (2021).
- [71] S. Kobayashi and M. Sato, Topological Superconductivity in Dirac Semimetals, *Phys. Rev. Lett.* **115**, 187001 (2015).
- [72] B.-J. Yang, T. Morimoto, and A. Furusaki, Topological charges of three-dimensional Dirac semimetals with rotation symmetry, *Phys. Rev. B* **92**, 165120 (2015).
- [73] B.-J. Yang and N. Nagaosa, Classification of stable three-dimensional Dirac semimetals with nontrivial topology, *Nature Communications* **5**, 4898 (2014).
- [74] M. Kargarian, M. Randeria, and Y.-M. Lu, Are the surface Fermi arcs in Dirac semimetals topologically protected?, *Proceedings of the National Academy of Sciences* **113**, 8648 (2016).
- [75] M. Kargarian, Y.-M. Lu, and M. Randeria, Deformation and stability of surface states in Dirac semimetals, *Phys. Rev. B* **97**, 165129 (2018).
- [76] C. Le, X. Wu, S. Qin, Y. Li, R. Thomale, F.-C. Zhang, and J. Hu, Dirac semimetal in  $\beta$ -CuI without surface Fermi arcs, *Proceedings of the National Academy of Sciences* **115**, 8311 (2018).
- [77] B. J. Wieder, Z. Wang, J. Cano, X. Dai, L. M. Schoop, B. Bradlyn, and B. A. Bernevig, Strong and fragile topological Dirac semimetals with higher-order Fermi arcs, *Nature Communications* **11**, 627 (2020).
- [78] Y. Fang and J. Cano, Classification of Dirac points with higher-order Fermi arcs, *Phys. Rev. B* **104**, 245101 (2021).
- [79] Y. Fang and J. Cano, Filling anomaly for general two- and three-dimensional  $C_4$  symmetric lattices, *Phys. Rev. B* **103**, 165109 (2021).
- [80] L. Aggarwal, A. Gaurav, G. S. Thakur, Z. Haque, A. K. Ganguli, and G. Sheet, Unconventional superconductivity at mesoscopic point contacts on the 3D Dirac semimetal Cd<sub>3</sub>As<sub>2</sub>, *Nature Materials* **15**, 32 (2016).
- [81] H. Wang, H. Wang, H. Liu, H. Lu, W. Yang, S. Jia, X.-J. Liu, X. C. Xie, J. Wei, and J. Wang, Observation of superconductivity induced by a point contact on 3D Dirac semimetal Cd<sub>3</sub>As<sub>2</sub> crystals, *Nature Materials* **15**, 38 (2016).
- [82] L. He, Y. Jia, S. Zhang, X. Hong, C. Jin, and S. Li, Pressure-induced superconductivity in the three-dimensional topological Dirac semimetal Cd<sub>3</sub>As<sub>2</sub>, *npj Quantum Materials* **1**, 16014 (2016).
- [83] L. M. Schoop, L. S. Xie, R. Chen, Q. D. Gibson, S. H. Lapidus, I. Kimchi, M. Hirschberger, N. Hal-dolaarachhige, M. N. Ali, C. A. Belvin, T. Liang, J. B. Neaton, N. P. Ong, A. Vishwanath, and R. J. Cava, Dirac metal to topological metal transition at a structural phase change in Au<sub>2</sub>Pb and prediction of  $\mathbb{Z}_2$  topology for the superconductor, *Phys. Rev. B* **91**, 214517 (2015).
- [84] T. Hashimoto, S. Kobayashi, Y. Tanaka, and M. Sato, Superconductivity in doped Dirac semimetals, *Phys. Rev. B* **94**, 014510 (2016).
- [85] E. Bobrow and Y. Li, Monopole Superconductivity in Magnetically Doped Cd<sub>3</sub>As<sub>2</sub> (2022), [arXiv:2204.04249](https://arxiv.org/abs/2204.04249) [cond-mat.supr-con].
- [86] C. Sun and Y. Li,  $\mathbb{Z}_2$  Topologically Obstructed Superconducting Order (2020), [arXiv:2009.07263](https://arxiv.org/abs/2009.07263) [cond-mat.supr-con].
- [87] R.-X. Zhang, Y.-T. Hsu, and S. Das Sarma, Higher-order topological Dirac superconductors, *Phys. Rev. B* **102**, 094503 (2020).
- [88] A. Skurativska, T. Neupert, and M. H. Fischer, Atomic limit and inversion-symmetry indicators for topological superconductors, *Phys. Rev. Research* **2**, 013064 (2020).
- [89] S. Ono, Y. Yanase, and H. Watanabe, Symmetry indicators for topological superconductors, *Phys. Rev. Research* **1**, 013012 (2019).

- [90] J. Zhang, J. Kim, D. Vanderbilt, and Y. Li, Quantum Hall Effects in Dirac Semimetal Films (unpublished).
- [91] N. Bultinck, B. A. Bernevig, and M. P. Zaletel, Three-dimensional superconductors with hybrid higher-order topology, *Phys. Rev. B* **99**, 125149 (2019).
- [92] The BdG Dirac points can only annihilate with those from another Dirac point. However, that does not happen in the  $\Delta \ll \mu$  limit for the Dirac semimetal normal state.
- [93] S. Tewari and J. D. Sau, Topological Invariants for Spin-Orbit Coupled Superconductor Nanowires, *Phys. Rev. Lett.* **109**, 150408 (2012).
- [94] J. J. He, J. Wu, T.-P. Choy, X.-J. Liu, Y. Tanaka, and K. T. Law, Correlated spin currents generated by resonant-crossed Andreev reflections in topological superconductors, *Nature Communications* **5**, 3232 (2014).
- [95] A. P. Schnyder, S. Ryu, A. Furusaki, and A. W. W. Ludwig, Classification of topological insulators and superconductors, *AIP Conference Proceedings* **1134**, 10 (2009).
- [96] S. Ryu, A. P. Schnyder, A. Furusaki, and A. W. W. Ludwig, Classification of topological insulators and superconductors in three spatial dimensions, *New J. Phys.* **12**, 065010 (2010).
- [97] A. P. Schnyder, S. Ryu, A. Furusaki, and A. W. W. Ludwig, Classification of topological insulators and superconductors in three spatial dimensions, *Phys. Rev. B* **78**, 195125 (2008).
- [98] M. Kheirkhah, Z.-Y. Zhuang, J. Maciejko, and Z. Yan, Surface Bogoliubov-Dirac cones and helical Majorana hinge modes in superconducting Dirac semimetals, *Phys. Rev. B* **105**, 014509 (2022).
- [99] C.-Z. Li, A.-Q. Wang, C. Li, W.-Z. Zheng, A. Brinkman, D.-P. Yu, and Z.-M. Liao, Reducing Electronic Transport Dimension to Topological Hinge States by Increasing Geometry Size of Dirac Semimetal Josephson Junctions, *Phys. Rev. Lett.* **124**, 156601 (2020).
- [100] A.-Q. Wang, P.-Z. Xiang, T.-Y. Zhao, and Z.-M. Liao, Topological nature of higher-order hinge states revealed by spin transport, *Science Bulletin* **67**, 788 (2022).