

Spin-order-dependent magneto-elastic coupling in two dimensional antiferromagnetic MnPSe₃ observed through Raman spectroscopy

Daniel J. Gillard^{*1}, Daniel Wolverson², Oscar M. Hutchings¹, and Alexander I. Tartakovskii¹

¹Department of Physics and Astronomy, University of Sheffield, Sheffield S3 7RH, UK

²Department of Physics, University of Bath, Bath, BA2 7AY, UK

*Corresponding author: d.j.gillard@sheffield.ac.uk

January 9, 2024

Abstract

Layered antiferromagnetic materials have emerged as a novel subset of the two-dimensional family providing a highly accessible regime with prospects for layer-number-dependent magnetism. Furthermore, transition metal phosphorous trichalcogenides, MPX₃ (M = transition metal; X = chalcogen) provide a platform for investigating fundamental interactions between magnetic and lattice degrees of freedom providing new insights for developing fields of spintronics and magnonics. Here, we use a combination of temperature dependent Raman spectroscopy and density functional theory to explore magnetic-ordering-dependent interactions between the manganese spin degree of freedom and lattice vibrations of the non-magnetic sub-lattice via a Kramers-Anderson super-exchange pathway in both bulk, and few-layer, manganese phosphorous triselenide (MnPSe₃). We observe a nonlinear temperature dependent shift of phonon modes predominantly associated with the non-magnetic sub-lattice, revealing their non-trivial spin-phonon coupling below the Néel temperature at 74 K, allowing us to extract mode-specific spin-phonon coupling constants.

Introduction

Devices and structures constructed using two-dimensional (2D) layered materials¹ have garnered an increasing amount of research interest ever since the discovery of isolated monolayers of graphene,² transition metal dichalcogenides (TMDs),^{3,4} and beyond.^{5,6} The number of different 2D materials encompassing and driving this area of research is rapidly growing.⁶ Most recently, the focus has turned to the discovery of intrinsic long range magnetic ordering in low dimensional van der Waals (vdW) crystals, offering of a highly accessible regime in which to study 2D magnetism.^{7–15} Spin fluctuations are expected to be strongly enhanced in the low dimensional limit,^{16–20} while control and tuning of magnetic states and properties should be easily achieved through engineering perturbations within the system such as strain, alloying, light coupling, gating, proximity effects, and moiré patterns, in a similar manner to conventional 2D materials.^{4,9,10}

A key challenge however, is the detection of such long range magnetic ordering, along with the underlying domains and associated magnetic fluctuations and excitations. Standard techniques currently employed to detect such occurrences in bulk crystals, thin film and even nanoparticles suspended in solutions, such as superconducting quantum interference device (SQUID) magnetometry and neutron scattering, have limited applicability in 2D magnetic materials due to the reduced volumes.²¹

Optical techniques can offer greater insights due to the increased spacial resolution available. Spectroscopic magnetic circular dichroism,^{8,11,22,23} which takes advantage of the Faraday and Kerr effects, can provide an insight into the magnetic behaviour of a few layer sample, such as the strength and sign of the exchange, along with the identification of bands relevant to the magnetic ordering.^{22,23} The first evidence of long range magnetic ordering in a single layer of vdW magnetic material was discovered in FePS₃ using Raman spectroscopy.^{13,24} Raman spectroscopy^{25,26} has successfully been used to reveal the magnetic exchange interaction strength via measurements of the two-magnon joint density of states,²⁷ as well as uncovering novel topology via measurement of fractional spin excitations.²⁸ In this investigation, we employ high-resolution temperature-dependent Raman spectroscopy in order to probe the magnetic spin-ordering-dependent magneto-elastic interactions of bulk, and few layer, MnPSe₃.

MnPSe₃ is a layered vdW magnetic material belonging to the transition metal phosphorus trichalcogenide, MPX_3 (M = transition metal; X = chalcogen), family with each layer possessing a D_{3d} symmetry.^{29–33} The unit cell of MnPSe₃ can be considered as two distinct atomic groups of Mn₂ and P₂Se₆, formed as a dumbbell-like structure of two PSe₃ tetrahedrons either end of a vertically (out-of-plane) orientated P-P bond, centred within the ionic bonded Mn hexagonal lattice (see Fig.1a). Below the Néel temperature of 74 K, the Mn²⁺ ions form inversion-breaking Néel type ordering with $S=5/2$ spins

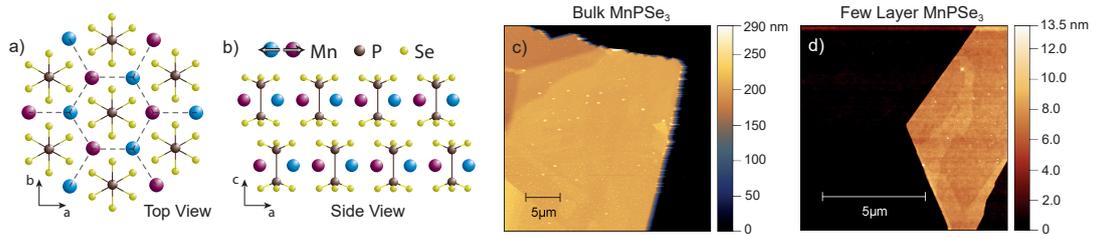


Figure 1: **Structure of MnPSe₃.** **a, b)** The MnPSe₃ crystal structure as viewed from the top (a) and the side (b). Manganese atoms are shown in purple and blue (depending on the spin state), while phosphorus is shown in brown, and selenium in yellow. Mn²⁺ ions are arranged in a hexagonal lattice and form the antiferromagnetic magnetic structure, with the in-plane spin state highlighted by colour. The [P₂Se₆]⁴⁻ ions possess no inherent magnetism and are arranged in a dumbbell-like formation centred within the Mn²⁺ atoms. **c, d)** Atomic force microscopy images of c) a bulk (209 nm), and d) a 9L (7.3 nm) MnPSe₃ sample. Lateral scale bars are 5 nm.

aligned in-plane (spin dimensionality of 1¹⁰) within an antiferromagnetic Néel type lattice, as shown in Fig.1b.^{29–33} The P₂Se₆ cluster acts as an intermediary anion for a Kramers-Anderson super-exchange pathway between neighbouring magnetic Mn²⁺ ions, formed through the spin state of the Mn²⁺ donor electrons coupling to that of the receiving [P₂Se₆]⁴⁻ anion.^{34,35} This effectively couples the magnetic static spin-state correlation function of the manganese sub-lattice to the phonon modes of the phosphorus triselenide.^{19,36–39}

While 2D magnetic materials are being studied more actively, MnPSe₃ remains relatively unexplored. Recent investigations include evidence of phonon-magnon hybridisation, observed between a 2-magnon continuum and the low frequency Raman modes of heavy Mn ions,⁴⁰ and is also explored in this work. Using polarisation resolved second harmonic generation, it is possible to observe the different antiferromagnetic domains within a MnPSe₃ flake.³³ The Néel vector in AFM domains is seen to reliably switch back and forth as a function of thermal cycle, along with a controllable rotation of the Néel vector via the application of uniaxial strain.³³ The direct Mn-Mn nearest neighbour magnetic exchange interactions, both in-plane and out-of-plane, has been explored using a combination of DFT and neutron scattering techniques.⁴¹ Theoretical investigations into the electronic and magnetic properties of MnPSe₃ predict a switching to ferromagnetic ordering when a large ($\sim 10^{14}$ cm⁻²) p- or n-doping is introduced to MnPSe₃.³⁰ Further DFT calculations of MnPSe₃/MoS₂⁴², MnPSe₃/WS₂⁴³ and MnPSe₃/CrSiTe₃⁴⁴ heterostructures, with an emphasis on strain tunability and spin-valley physics highlight the potential for MnPSe₃-based heterostructures with both TMDs and other 2D magnetic materials.

In this study, a combination of temperature dependent low-frequency Raman spectroscopy and density functional theory (DFT) is used to probe the atomic vibrations of the non-magnetic ions. These phonons are used as a proxy by which to investigate the changing long range antiferromagnetic spin-ordering in

MnPSe₃, via the aforementioned spin-phonon coupling, as the temperature is increased from 5 K through the Néel temperature (T_N) at 74 K, up to room temperature.^{19,36-39} We also consider the impact of sample thickness on spin-phonon coupling.

Results and Discussion

Flakes of MnPSe₃ are prepared via micromechanical exfoliation and thicknesses are determined via atomic force microscopy (AFM). The thinnest flakes measured have a thickness of 7.3 nm (9 layers³³) (Fig.1d) and 7.9 nm (10 layers³³), while the thickest flake measured more than 200 nm (Fig.1c), considered here as ‘bulk’ material. Measurements are also taken on 14.1 nm (\sim 18 layers) and 17.4 nm (\sim 22 layers) thick MnPSe₃ flakes. It has been suggested that MnPSe₃ possesses a non-negligible interlayer magnetic coupling^{30,41} such that long range magnetic ordering, as observed in bulk samples at temperatures below the Néel transition, will be modified as we approach the 2D limit. The exact thickness at which the magnetic ordering might begin to weaken is currently unknown, however the results presented here suggest it is not above 9 layers.

Initial observations of the low frequency Raman spectra of MnPSe₃ are carried out on three independent bulk samples, all showing a similar temperature dependence of the peak positions. The bulk MnPSe₃ Raman response at a temperature of 15 K and 250 K is shown in Figure 2a, and is consistent with previous investigations.^{32,40,41} The MnPSe₃ bulk Raman spectrum typically consists of seven main peaks, labelled here P1 at 84 cm⁻¹, through to P7 at 221 cm⁻¹. Two additional, but much dimmer, peaks can often be observed above the noise level at approximately 50 cm⁻¹ (not shown here), and 160 cm⁻¹ (labelled * in Fig.2a).⁴⁰

Density functional theory is also used to corroborate the identity of these vibrational modes, providing further insight into the characteristics of each mode, which will be discussed in depth later. Each mode consists of contributions from one, or both, of the magnetic, Mn²⁺, and non-magnetic, [P₂Se₆]⁴⁻, sublattices. The two lowest frequency, immediately visible, Raman lines of P1 (84 cm⁻¹) and P2 (109 cm⁻¹), are largely comprised of in-plane lattice vibrations of the heavy manganese Mn²⁺ ions, with smaller contributions from the non-magnetic phosphorus triselenide ions. Oppositely, the relatively unexplored P4 (148 cm⁻¹), P5 (156 cm⁻¹), P6 (173 cm⁻¹), and P7 (221 cm⁻¹) are formed mostly (or in the case of P4, entirely) due to vibrations of the non-magnetic ions, as detailed later in this study.

The broad dim peak seen at 126 cm⁻¹, labelled in Figure 2a as P3, is identified as 2-magnon (2M) scattering, hybridising with P1 and P2. Consistent with previous reports,^{40,45} the 2-magnon excitation (P3) is seen to red-shift as the temperature is increased and the magnetic ordering is destabilised with

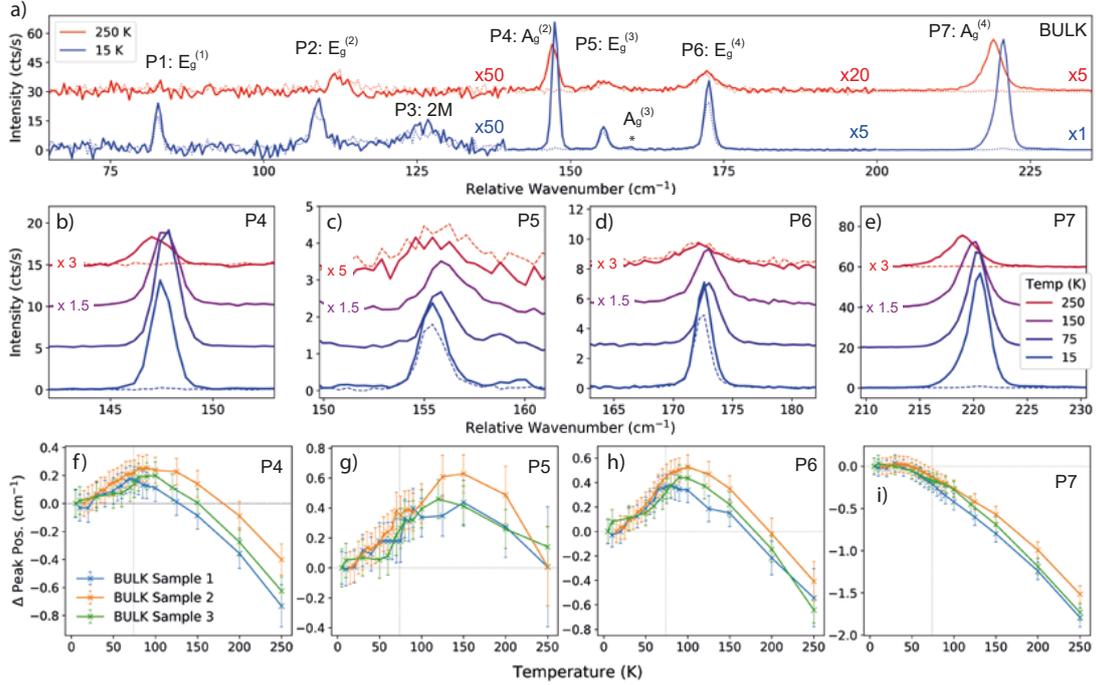


Figure 2: **Raman spectroscopy of bulk MnPSe₃.** **a)** Raman spectra of bulk MnPSe₃ at low (15 K), and high (250 K), displaying clearly identifiable peaks. **b-e)** Temperature dependence of the non-magnetic vibrational modes P4 through to P7. A clear shift and change in intensity is observed as temperature is increased. **f-i)** Change in peak position as a function of temperature determined from three separate bulk MnPSe₃ samples. The zero-line (Initial peak position at T=0 K) is highlighted with a horizontal dotted line. A vertical dotted line highlights the Néel temperature of 74 K. For visual purposes, some peak intensities have been magnified by the given factors.

increasing thermal fluctuations. As P3 shifts through the two phonon modes, a broadening of the peak width, along with an associated drop in phonon lifetime, highlights the point of maximum hybridisation (See SI Note 4). The 2-magnon peak is a purely magnetic phenomenon, and therefore disappears when the magnetic ordering is lost at 74 K. As a consequence of such hybridisation, P1 and P2 present atypical temperature dependent behaviour and are seen to be blue-shifted at 250 K, when compared to 15 K, as can be seen in Figure 2a.

In this investigation we concentrate on the previously unstudied phonon modes labelled here P4, P5, P6, and P7. Figure 2b-e details the Raman spectra of these four phonon modes at select temperatures of 15 K, 75 K, 150 K, and 250 K, highlighting the shift of each mode as a function of temperature. Solid lines show the Raman response detected in a co-polarised basis (HH), while the dashed line show the cross-polarised (HV) response, highlighting the polarisation dependence of each mode. We observe a near-unity polarisation degree $(I_{HH} - I_{HV})/(I_{HH} + I_{HV})$ of P4 (148 cm⁻¹) and P7 (221 cm⁻¹) that

is maintained throughout the temperature range measured in each sample, while P5 (156 cm^{-1}) and P6 (173 cm^{-1}) are polarisation independent (observed in both HH and HV).^{32,40,46}

Figure 2f-i shows the change of peak position of the four phonon modes due to the increasing temperature across three different bulk MnPSe₃ samples. The phonon modes are fitted using a Voigt curve, and peak position extracted at each temperature point, before subtracting the peak position at the lowest temperature. Each phonon line displays a distinct nonlinear temperature dependent behaviour that is repeated throughout multiple bulk samples. The most intense peak, P7 ($A_g^{(4)}$; 221 cm^{-1}), is seen to initially be constant with temperature increase until the Néel temperature is reached, at which point the peak is observed to start shifting towards lower frequencies. The other three peaks, P4 ($A_g^{(2)}$; 148 cm^{-1}), P5 ($E_g^{(3)}$; 156 cm^{-1}), and P6 ($E_g^{(4)}$; 173 cm^{-1}), initially tend towards higher frequencies until the Néel temperature is reached, when similarly to P7, the trend is inverted and the peak position is observed to shift to lower frequencies. P4 is seen to reach a maximum peak shift, $\sim 0.2 \text{ cm}^{-1}$, close to the Néel transition, while P5 and P6 both continue slightly beyond T_N reaching $\sim 0.4 \text{ cm}^{-1}$. A specific change in trend observed around the Néel temperature is indicative of a magnetic ordering origin of this phenomena, as we discuss below.

Moving towards thinner samples, we investigate a range of sample thicknesses down to 9 layers³³ (7.3 nm), as determined by atomic force microscopy. As the thicknesses of the sample is decreased, we note a corresponding reduction in overall intensity of the Raman signal which can be clearly seen in the signal to noise ratio observed in Figure 3a-e. To compensate this drop in collected intensity, the acquisition exposure time is increased accordingly. The Raman signal obtained from a 14 nm (18 layer ³³) MnPSe₃ sample at low (5 K) and high (250 K) temperature is shown in Figure 3a-e. Similarly to the bulk samples, a Voigt fit is applied at each temperature increment and change in peak position is extracted and displayed in Figure 3f-i. The temperature dependent Raman response is very similar to that of the bulk samples. For reference, the data for bulk sample 2 shown in Figure 2 is also shown here in Figure 3f-i. It should be noted that the accuracy of fitting is reduced as the signal to noise ratio in the thinner samples is diminished, producing noisier dependencies in Figure 3f-i for the thinnest two samples (9 and 10 layers, respectively)³³. Even so, they generally match well with the bulk data, suggesting any out of plane inter-layer magnetic coupling component that could disrupt the antiferromagnetic ordering⁴¹ is not significant for the range of thicknesses studied here.

In order to fully analyse the temperature dependence of the Raman modes we identify a key figure of merit, the spin-phonon coupling strength, λ ,^{19,37-39} which represents how strongly the magnetic spin-ordering within the Mn sub-lattice influences the atomic vibrations of the non-magnetic sub-lattice via the super-exchange pathway. In this case, λ manifests as the difference between the observed Raman

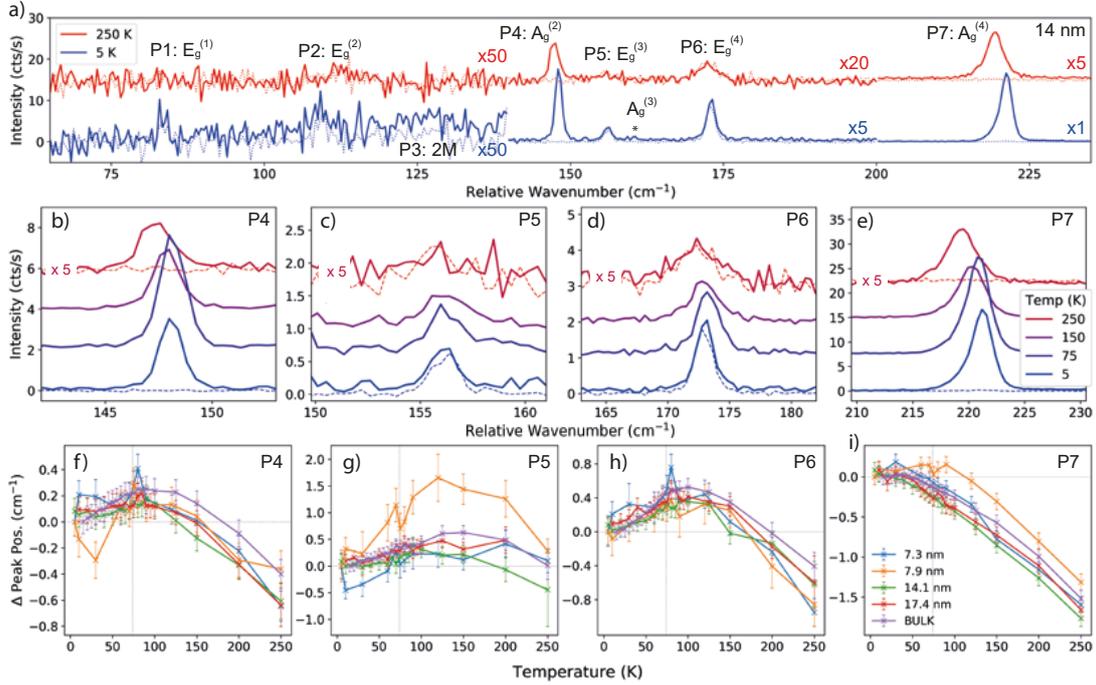


Figure 3: **Raman Spectroscopy of few layer MnPSe₃.** **a)** Raman spectra of 14 nm thin MnPSe₃ at low (5 K), and high (250 K), displaying 7 clearly identifiable peaks. **b-e)** Temperature dependence of the phonon modes P4 through to P7. Intensity is increased for visual purposes with the given magnification factors. **f-i)** Change in peak position as a function of temperature measured in a range of MnPSe₃ sample thicknesses from 7.3 nm (9 L) to >200 nm (bulk). The initial peak position is set to 0 and is highlighted with a horizontal dotted line. Peak position is seen to be mostly consistent throughout the full range of thicknesses tested. Variations seen in P5 are explored further in the main text and SI.

shift at $T \approx 0$ K, and that expected by the temperature dependence without magnetic coupling (See SI Note 2 for a detailed interpretation). As such, the temperature dependent peak positions of each phonon mode, and flake thickness, are fitted using a combination of Brillouin function,^{19,31,37,47} and anharmonic phonon model. The Brillouin function is used to define the overall magnetisation state of our 2D system as a function of temperature and is defined by the material properties. Figure 4 displays the results of this combined anharmonic phonon plus Brillouin function fitting applied to bulk and few-layer (14 nm, 18 layers³³) MnPSe₃ samples, with emphasis on the transition from ordered antiferromagnetism below 74 K (pale blue regions) to the disordered paramagnetism above 74 K (red regions). The experimental data can be seen as black crosses obtained via Voigt peak fitting of each Raman mode. The error bars shown are derived from a combination of errors associated with fitting the phonon modes and spectrometer resolution. The anharmonic temperature dependence, which defines the non-magnetic temperature dependent behaviour of the phonon modes, is applied to the experimental data

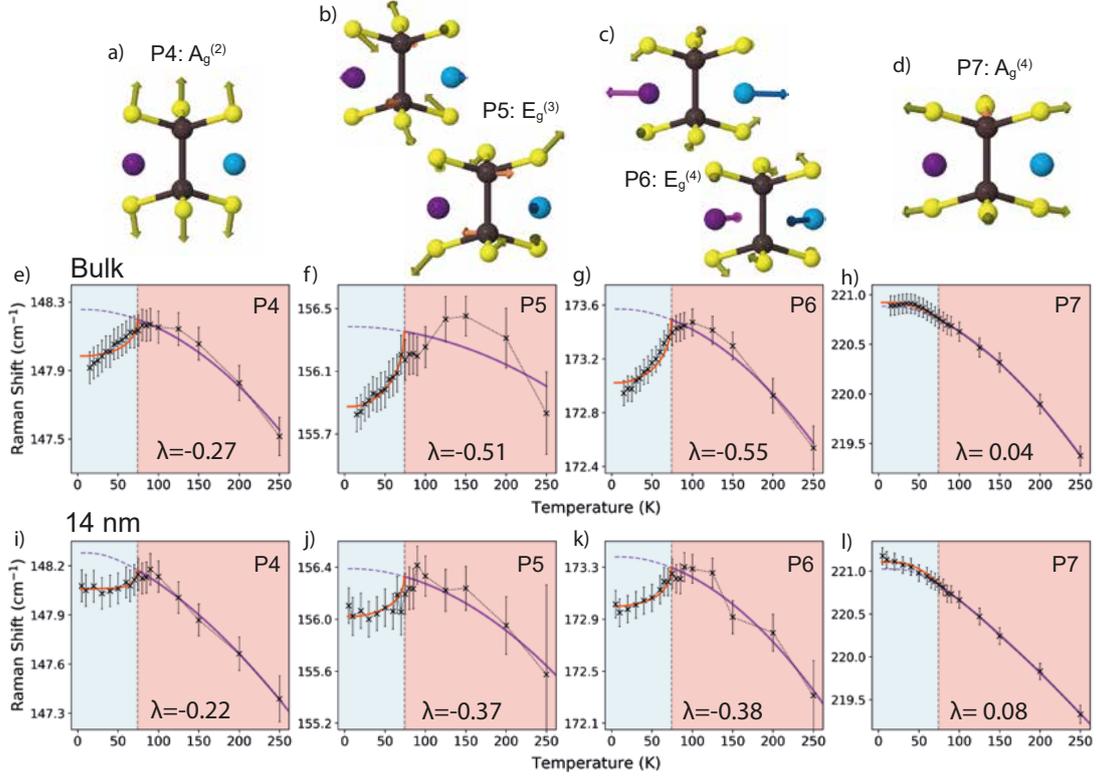


Figure 4: **Spin-phonon coupling.** **a-d)** Vibrational modes of MnPSe_3 as calculated by DFT for a) P4, b) P5, c) P6, and d) P7. Manganese atoms are shown as light and dark blue solid spheres, highlighting the alternating spin states, phosphorous atoms are brown spheres, and selenium are yellow spheres. Arrows represent the atomic shifts (from equilibrium) **e-l)** Temperature dependent Raman shift of e-h) Bulk and i-l) few layer MnPSe_3 , with emphasis on the transition from an ordered antiferromagnetic state (blue shaded region) to a disordered paramagnetic state (Red shaded region) about the Néel Temperature (dotted grey line) at 74 K. Black crosses show the experimental data with errors associated with peak fitting, while the calculated spin-phonon coupling and anharmonic phonon dependencies are shown in orange and purple solid lines, respectively. The extracted strength of the spin-phonon coupling, λ , is given for each Raman mode.

above the Néel temperature (solid purple line).^{19,48,49} The magnetic dependence of the phonon modes, is defined as the difference between the anharmonic fitting extended below T_N (dashed purple line), and the experimentally obtained data points (black crosses). This magnetisation dependence is recreated in each phonon mode (solid orange line) using the MnPSe_3 reduced magnetism, defined by the Brillouin function normalised to 0 at T_N and 1 at $T = 0$ K, multiplied by the spin-phonon coupling, λ .^{19,31,37–39,47–49}

Fitting parameters of all sample thicknesses, along with a full description of the fitting process is available in SI Note 2. Table 1 lists the spin-phonon coupling strength, λ , of all thicknesses measured. The variation in λ , for a given phonon mode, between samples does not show any obvious trend with

Table 1: Spin-phonon coupling strength, λ , as determined by the Brillouin function and anharmonic phonon fitting procedures.

Sample Thickness	Spin-phonon coupling, λ			
Raman Mode	P4 (148 cm^{-1})	P5 (156 cm^{-1})	P6 (173 cm^{-1})	P7 (221 cm^{-1})
7.3 nm (9 L)	-0.19	-0.45	-0.57	-0.07
7.9 nm (10 L)	-0.23	-0.99	-0.43	-0.18
14.1 nm (18 L)	-0.17	-0.37	-0.38	0.08
17.4 nm (22 L)	-0.17	-0.37	-0.42	0.11
Bulk 1	-0.21	-0.38	-0.39	0.06
Bulk 2	-0.27	-0.51	-0.55	0.04
Bulk 3	-0.31	-0.53	-0.57	0.00

respect to sample thicknesses. Therefore, we attribute these discrepancies to a combination of random variations in sample strain and reduced signal-to-noise ratio in the thinner samples. It can be seen, however, that each sample measured, regardless of sample thickness, shows the same overall trends with P5 and P6 displaying the largest spin-phonon coupling strength, with P7 the lowest providing an overall consistency between all samples measured.

Density functional theory provides extra insight into the atomic vibrational composition of the phonon modes (See Figs.4a-d) and is used here to qualitatively analyse the relationship between magnetic spin-ordering and atomic movements via the super-exchange. A specific consideration is made to the Mn-Se-Mn ionic bond lengths and bond angle, which provides the greatest influence over the strength of the super-exchange pathway between neighbouring manganese atoms.^{41,45} Full details are given in SI Note 1 but, briefly, we used both frozen phonon⁵⁰ and perturbation theory⁵¹ approaches within density functional theory at the generalised gradient approximation level^{52,53} including the local spin-density approximation and taking into account a possible on-site Hubbard U ^{54,55} term whose value was determined as part of this work. A frozen phonon approach calculates the inter-atomic forces with zero vibrations to construct a force constant matrix by which the normal modes at a given wave-vector can be calculated, essentially forming the phonon dispersion. Density functional perturbation theory goes a step further by introducing perturbations to the system in order to measure the response in spin and charge densities, as well as polarizability. In order to account for non-homogeneity of spin and charge densities, a generalized gradient approximation is added, while the Hubbard parameter accounts for electron localisation and hopping.⁵¹

Figure 4a shows that the atomic vibrational composition of P4 (148 cm^{-1}) is entirely due to the Se atoms shifting out-of-plane, with zero contribution from the manganese sub-lattice. This leads to the conclusion that the spin-phonon coupling, λ , observed in P4 is entirely due to the Mn-Se-Mn super-exchange pathway, with a significant variation in both pathway length and ionic bond angle leading to a large spin-phonon coupling, λ , as shown in Table 1.

The atomic vibrational calculations suggest P5 (156 cm^{-1}) should possess a relatively low spin-phonon coupling due to the low vibrational contribution from the Mn sub-lattice. Experimental evidence however, indicates a large spin-phonon coupling, as shown in Table 1. Further investigations (See SI Note 3) show a merging with a close by mode (labelled * in Figs. 1a and 2a) which has the effect of broadening the observed peak near the Néel temperature where the two separate modes are closest, and shifting the fitted peak centre to higher relative wavenumbers. When applying the temperature dependent Brillouin fitting to P5 we therefore obtain a higher experimental spin-phonon coupling from the experimental results than expected via DFT. Taking this into account with a multiple peak analysis reduces the extracted spin-phonon coupling to a value more compatible with DFT results, as explored in SI Note 3. Since this multiple peak fitting can only be applied to samples with large signal (i.e. Bulk samples with large excitation powers), the results presented in Table 1 are without taking this mode merging into account.

P6 (173 cm^{-1}) is expected to show the largest spin-phonon coupling due to the large contribution from the Mn sub-lattice, along with a large change in both Mn-Se-Mn bond length and angle. This expectation is fulfilled by the experimental data displayed in Figs.4 and 1. The thinner samples generally have a reduced spin-phonon coupling strength, λ , compared to the bulk samples.

Finally, P7 (221 cm^{-1}) is observed to have a near-zero spin-phonon coupling, as shown by Figure 4. Considering the atomic shifts of this vibrational mode, it can be seen that the Mn-Se-Mn bond angle is not perturbed, while the change in bond lengths are symmetrical and small when compared to the other modes. Combined with zero magnetic sub-lattice contribution, this provides little framework for neither spin-phonon coupling through a super-exchange path, nor direct coupling.

Conclusions

This work represents an investigation into an overlooked area of the opto-mechanical properties of MnPSe_3 . The higher frequency phonon modes, predominantly attributed to the non-magnetic sub-lattice of MnPSe_3 , have now been thoroughly explored through a combination of density functional theory and Raman spectroscopy. A previous investigation detailing the temperature dependent mode shifts of MnPSe_3 ⁴⁶ suggested a linear dependence of peak position towards lower frequencies in both bulk and

few layer MnPSe₃ samples. Our observations deviate significantly from that conclusion. We believe that the higher resolution grating used here, as well as pursuing a lower temperature region allows us to obtain a more accurate picture of the temperature dependent magnetic ordering than has previously been reported. Furthermore, we also note that significantly more samples are measured here, all repeating the same nonlinear temperature dependence. Our analytical approach is, likewise, more complete. We use a combination of anharmonic temperature dependent shift and magnetic specific Brillouin-like function to extract a spin-phonon coupling strength, λ , from each phonon resonance.

Methods

Temperature dependent Raman spectroscopy. Ultra-low frequency Raman spectroscopy is performed using a custom-built free-space micro-Raman setup. Flakes of MnPSe₃ are placed within a flow cryostat (MicrostatHiRes, Oxford Instruments) and cooled to ~ 5 K. A flow controller and heater is used to control the sample temperature as required. The phonon modes of MnPSe₃ are excited using a 532 nm diode pumped solid state laser (model 04-01, Cobalt) with linewidth < 1 MHz. The excitation beam is focused onto the samples via a high (0.55) NA 50x microscope objective (M Plan Apo 50X, Mitutoyo). Back-scattered light is collected using the same objective lens. The laser line is rejected using three 10 cm^{-1} Bragg notch filters (BragGrate[™], Optigrate). The Raman signal is analysed using a 0.75 cm monochromator (SP750, Princeton Instruments) with a 1800 g/mm holographic grating and a nitrogen cooled charge-coupled device camera with a pixel size of $20 \mu\text{m} \times 20 \mu\text{m}$ (PyLon:100BR, Princeton Instruments) providing spectral resolution of $\approx 0.4 \text{ cm}^{-1}$ per pixel. The linewidths of the phonons studied here are larger than one pixel, allowing for sub-pixel precision when finding peak position, see SI Note 2. Polarisation optics are configured as, quarter wave plate - motorised linear polariser - Sample - motorised linear polariser - motorised half wave plate, to allow for linear polarisation excitation of arbitrary polarisation angle without loss of power, selection of co- and cross- polarisation detection without loss of signal to the holographic grating. Laser power at the sample is typically 0.5 mW (Power density of $6.37 \times 10^4 \text{ W/cm}^2$) unless stated otherwise. We observe no effect from laser heating in our data (No shift in Néel temperature towards lower temperatures), thanks in part to the large cooling power of the flow cryostat. The spectral resolution of this system is $\approx 0.4 \text{ cm}^{-1}$, with spatial resolution of $\approx 1 \mu\text{m}$. A schematic of the experimental setup is available in SI Note 7.

Density Functional Theory. We used both frozen phonon and perturbation theory approaches within density functional theory at the generalised gradient approximation level of approximation including the local spin-density approximation and taking into account a possible on-site Hubbard U term whose value

was determined as part of this work. A full description of the DFT analysis is provided in SI Note 1.

Acknowledgments

We acknowledge IT services at the Universities of Sheffield and Bath for the provision of services for High Performance Computing (HPC). Computational work in Bath was supported by the EU Horizon 2020 OCRE project “Cloud funding for research”. D. J. G., O. H., and A. I. T. acknowledge support from the European Graphene Flagship Project under grant agreement number 881603 and EPSRC grants EP/S030751/1, EP/V006975/1, and EP/V026496/1.

Author Contributions

D.J.G. and O.H. carried out micro-mechanical exfoliation of the MnPSe₃ flakes and performed experimental observations using Raman spectroscopy. D.W. performed density functional theory of MnPSe₃. D.W. provided insight into the analytical model used to fit the temperature dependent Raman response while D.J.G. performed the fitting procedures. D.J.G., D.W., O.M., and A.I.T. had ongoing analytical discussions regarding the experimental and DFT data throughout the project. D.J.G., D.W., and A.I.T. managed various aspects of the project. A.I.T. conceived of, and supervised the project. D.J.G. wrote the manuscript with major contributions from DW and further contributions from all co-authors.

Data Availability

The data that support the plots within this paper and other findings of this study are available from the corresponding author upon reasonable request.

Code availability

The codes that support the findings of this study are available from <https://www.quantum-espresso.org/>. Inputs to these codes are available free of charge at <https://doi.org/10.15125/BATH-01218>

Competing interests

The authors declare no competing interests.

References

1. Geim, A. K. & Grigorieva, I. V. Van der Waals heterostructures. *Nature* **499**, 419–425 (2013).
2. Novoselov, K. S. *et al.* Electric field in atomically thin carbon films. *Science* **306**, 666–669 (2004).
3. Mak, K. F., Lee, C., Hone, J., Shan, J. & Heinz, T. F. Atomically Thin MoS₂: A new Direct-Gap Semiconductor. *Phys. Rev. Lett.* **105**, 136805 (2010).
4. Manzeli, S., Ovchinnikov, D., Pasquier, D., Yazyev, O. V. & Kis, A. 2D transition metal dichalcogenides. *Nat. Rev. Mater.* **2**, 17033 (2017).
5. Choi, W. *et al.* Recent development of two-dimensional transition metal dichalcogenides and their applications. *Mater. Today* **20**, 116–130 (2017).
6. Scarano, D. & Cesano, F. Graphene and Other 2D Layered Nanomaterials and Hybrid Structures: Synthesis, Properties and Applications. *Materials* **14**, 7108 (2021).
7. Park, J.-G. Opportunities and challenges of 2D magnetic van der Waals materials: magnetic graphene? *J. Phys.: Condens. Matter* **28**, 301001 (2016).
8. Gong, C. *et al.* Discovery of intrinsic ferromagnetism in two-dimensional van der Waals crystals. *Nature* **546**, 265–269 (2017).
9. Burch, K. S., Mandrus, D. & Park, J. G. Magnetism in two-dimensional van der Waals materials. *Nature* **563**, 47–52 (2018).
10. Gibertini, M., Koperski, M., Morpurgo, A. F. & Novoselov, K. S. Magnetic 2D materials and heterostructures. *Nat. Nanotechnol.* **14**, 408–419 (2019).
11. Huang, B. *et al.* Layer-dependent ferromagnetism in a van der Waals crystal down to the monolayer limit. *Nature* **546**, 270–273 (2017).
12. Fei, Z. *et al.* Two-dimensional itinerant ferromagnetism in atomically thin Fe₃GeTe₂. *Nat. Mater.* **17**, 778–782 (2018).
13. Lee, J. U. *et al.* Ising-Type Magnetic Ordering in Atomically Thin FePS₃. *Nano Lett.* **16**, 7433–7438 (2016).
14. Kim, M. *et al.* Micromagnetometry of two-dimensional ferromagnets. *Nat. Electron.* **2**, 457–463 (2019).
15. Lyons, T. P. *et al.* Interplay between spin proximity effect and charge-dependent exciton dynamics in MoSe₂/CrBr₃ van der Waals heterostructures. *Nat. Commun.* **11**, 6021 (2020).

16. Huang, B. *et al.* Electrical control of 2D magnetism in bilayer CrI₃. *Nat. Nanotechnol.* **13**, 544–548 (2018).
17. Samarth, N. Magnetism in flatland. *Nature* **546**, 216–217 (2017).
18. Lado, J. L. & Fernández-Rossier, J. On the origin of magnetic anisotropy in two dimensional CrI₃. *2D Mater.* **4**, 035002 (2017).
19. Prosnikov, M. A. *et al.* Magnetic dynamics and spin-phonon coupling in the antiferromagnet Ni₂NbBO₆. *Phys. Rev. B* **98**, 104404 (2018).
20. Kim, K. *et al.* Antiferromagnetic ordering in van der Waals 2D magnetic material MnPS₃ probed by Raman spectroscopy. *2D Mater.* **6**, 041001 (2019).
21. Hellman, F. *et al.* Interface-induced phenomena in magnetism. *Rev. Mod. Phys.* **89**, 025006 (2017).
22. Ando, K., Takahashi, K., Okuda, T. & Umehara, M. Magnetic circular dichroism of zinc-blende-phase MnTe. *Phys. Rev. B* **46**, 12289–12297 (1992).
23. Burch, K. S., Awschalom, D. D. & Basov, D. N. Optical properties of III-Mn-V ferromagnetic semiconductors. *J. Magn. Magn. Mater.* **320**, 3207–3228 (2008).
24. Wang, X. *et al.* Raman spectroscopy of atomically thin two-dimensional magnetic iron phosphorus trisulfide (FePS₃) crystals. *2D Mater.* **3**, 031009 (2016).
25. Raman, C. V. & Krishnan, K. S. The Negative Absorption of Radiation. *Nature* **122**, 12–13 (1928).
26. Wolverson, D. in *Characterization of Semiconductor Heterostructures and Nanostructures (Second Edition)* (eds Lamberti, C. & Agostini, G.) Second Edition, 753–802 (Elsevier, Oxford, 2013).
27. Sandilands, L. J. *et al.* Stability of exfoliated Bi₂Sr₂Dy_xCa_{1-x}Cu₂O_{8+δ} studied by Raman microscopy. *Phys. Rev. B* **82**, 064503 (2010).
28. Nasu, J., Knolle, J., Kovrizhin, D. L., Motome, Y. & Moessner, R. Fermionic response from fractionalization in an insulating two-dimensional magnet. *Nat. Phys.* **12**, 912–915 (2016).
29. Grasso, V. & Silipigni, L. Optical absorption and reflectivity study of the layered MnPSe₃ seleniophosphate. *J. Opt. Soc. Am. B* **16**, 132–136 (1999).
30. Chittari, B. L. *et al.* Electronic and magnetic properties of single-layer MPX₃ metal phosphorous trichalcogenides. *Phys. Rev. B* **94**, 184428 (2016).
31. Wiedenmann, A., Rossat-Mignod, J., Louisy, A., Brec, R. & Rouxel, J. Neutron diffraction study of the layered compounds MnPSe₃ and FePSe₃. *Solid State Commun.* **40**, 1067–1072 (1981).

32. Makimura, C., Sekine, T., Tanokura, Y. & Kurosawa, K. Raman scattering in the two-dimensional antiferromagnet MnPSe₃. *J. Phys.: Condens. Matter* **5**, 623–632 (1993).
33. Ni, Z. *et al.* Imaging the Néel vector switching in the monolayer antiferromagnet MnPSe₃ with strain-controlled Ising order. *Nat. Nanotechnol.* **16**, 782–787 (2021).
34. Kramers, H. L’interaction Entre les Atomes Magnétogènes dans un Cristal Paramagnétique. *Physica* **1**, 182–192 (1934).
35. Anderson, P. W. Antiferromagnetism. Theory of Superexchange Interaction. *Phys. Rev.* **79**, 350–356 (1950).
36. Lockwood, D. J. & Cottam, M. G. The spin-phonon interaction in FeF₂ and MnF₂ studied by Raman spectroscopy. *J. Appl. Phys.* **64**, 5876–5878 (1988).
37. Ghosh, A. *et al.* Spin-phonon coupling and magnon scattering in few-layer antiferromagnetic FePS₃. *Phys. Rev. B* **103**, 064431 (2021).
38. Casto, L. D. *et al.* Strong spin-lattice coupling in CrSiTe₃. *APL Mater.* **3**, 041515 (2015).
39. Fainstein, A., Etchegoin, P., Trodahl, H. J. & Tallon, J. L. Spin-order-dependent Raman scattering in RuSr₂GdCu₂O₈. *Phys. Rev. B* **61**, 15468–15473 (2000).
40. Mai, T. T. *et al.* Magnon-phonon hybridization in 2D antiferromagnet MnPSe₃. *Sci. Adv.* **7**, eabj3106 (2021).
41. Calder, S., Haglund, A. V., Kolesnikov, A. I. & Mandrus, D. Magnetic exchange interactions in the van der Waals layered antiferromagnet MnPSe₃. *Phys. Rev. B* **103**, 024414 (2021).
42. Pei, Q., Song, Y., Wang, X., Zou, J. & Mi, W. Superior Electronic Structure in Two-Dimensional MnPSe₃/MoS₂ van der Waals Heterostructures. *Sci. Rep.* **7**, 9504 (2017).
43. Sharma, D. K., Kumar, S. & Auluck, S. Strain induced optoelectronic properties of two dimensional MnPSe₃/WS₂ heterostructure. *J. Phys.: Condens. Matter* **32**, 315501 (2020).
44. Pei, Q., Wang, X., Zou, J. & Mi, W. Efficient band structure modulations in two-dimensional MnPSe₃/CrSiTe₃ van der Waals heterostructures. *Nanotechnology* **29**, 214001 (2018).
45. Vaclavkova, D. *et al.* Magnetoelastic interaction in the two-dimensional magnetic material MnPS₃ studied by first principles calculations and Raman experiments. *2D Mater.* **7**, 035030 (2020).
46. Liu, P. *et al.* Exploring the magnetic ordering in atomically thin antiferromagnetic MnPSe₃ by Raman spectroscopy. *J. Alloy. Compd.* **828**, 154432 (2020).

47. Darby, M. I. Tables of the Brillouin function and of the related function for the spontaneous magnetization. *Br. J. Appl. Phys.* **18**, 1415–1417 (1967).
48. Balkanski, M., Wallis, R. F. & Haro, E. Anharmonic effects in light scattering due to optical phonons in silicon. *Phys. Rev. B* **28**, 1928–1934 (1983).
49. Lan, T., Tang, X. & Fultz, B. Phonon anharmonicity of rutile TiO₂ studied by Raman spectrometry and molecular dynamics simulations. *Phys. Rev. B* **85**, 094305 (2012).
50. Yin, M. T. & Cohen, M. L. Theory of static structural properties, crystal stability, and phase transformations: Application to Si and Ge. *Phys. Rev. B* **26**, 5668–5687 (1982).
51. Baroni, S., de Gironcoli, S., Dal Corso, A. & Giannozzi, P. Phonons and related crystal properties from density-functional perturbation theory. *Rev. Mod. Phys.* **73**, 515–562 (2001).
52. Perdew, J. P., Burke, K. & Ernzerhof, M. Generalized Gradient Approximation Made Simple. *Phys. Rev. Lett.* **77**, 3865–3868 (1996).
53. Constantin, L. A., Perdew, J. P. & Pitarke, J. M. Exchange-correlation hole of a generalized gradient approximation for solids and surfaces. *Phys. Rev. B* **79**, 075126 (2009).
54. Timrov, I., Marzari, N. & Cococcioni, M. Self-consistent Hubbard parameters from density-functional perturbation theory in the ultrasoft and projector-augmented wave formulations. *Phys. Rev. B* **103**, 045141 (2021).
55. Timrov, I., Marzari, N. & Cococcioni, M. Hubbard parameters from density-functional perturbation theory. *Phys. Rev. B* **98**, 085127 (2018).