

Transformation of hexagonal Lu to cubic LuH_{2+x} single-crystalline films

Peiyi Li,^{1,*} Jiachang Bi,^{1,*} Shunda Zhang,¹ Rui Cai,¹ Guanhua Su,¹ Fugang Qi,¹ Ruyi Zhang,¹ Zhiyang Wei,¹ and Yanwei Cao^{1,2,†}

¹*Ningbo Institute of Materials Technology and Engineering, Chinese Academy of Sciences, Ningbo 315201, China*

²*Center of Materials Science and Optoelectronics Engineering,
University of Chinese Academy of Sciences, Beijing 100049, China*

(Dated: April 18, 2023)

With the recent report of near ambient superconductivity at room temperature in the N-doped lutetium hydride (Lu-H-N) system, the understanding of cubic Lu-H compounds has attracted worldwide attention. Generally, compared to polycrystal structures with non-negligible impurities, the single-crystalline form of materials with high purity can provide an opportunity to show their hidden properties. However, the experimental synthesis of single-crystalline cubic Lu-H compounds has not been reported thus far. Here, we developed an easy way to synthesize highly pure LuH_{2+x} single-crystalline films by the post-annealing of Lu single-crystalline films (purity of 99.99%) in the H₂ atmosphere. The crystal and electronic structures of films were characterized by X-ray diffraction, Raman spectroscopy, and electrical transport. Interestingly, Lu films are silver-white and metallic, whereas their transformed LuH_{2+x} films become purple-red and insulating, indicating the formation of an unreported electronic state of Lu-H compounds possibly. Our work provides a novel route to synthesize and explore more single-crystalline Lu-H compounds.

arXiv:2304.07966v1 [cond-mat.mtrl-sci] 17 Apr 2023

* These authors contributed equally to this work

† ywcao@nimte.ac.cn

I. INTRODUCTION

A very recent report of near ambient superconductivity at room temperature in the Lu-H-N system immediately ignited the worldwide interest of studying Lu-H compounds [1–22]. Regarding this subject, one fundamental identification is about the composition and structure of the red matter showing near ambient superconductivity at room temperature. In the initial report, the authors assigned the emergent superconductivity to cubic $Fm\bar{3}m$ -LuH_{3- δ} N _{ϵ} (92.25% purity) with both N-substitution and H-vacancy defects [1]. However, identifying the composition and structure of $Fm\bar{3}m$ -LuH_{3- δ} N _{ϵ} is still a big challenge.

Generally, the stable phase of LuH₃ has a rhombohedra structure with space group $P\bar{3}c1$, not the cubic structure with space group $Fm\bar{3}m$ [9, 17]. Therefore, based on a combination of pressure-dependent color, the X-ray diffraction data, and the Raman data, the composition of experimental $Fm\bar{3}m$ -LuH_{3- δ} N _{ϵ} was considered to be LuH_{2+ x} N _{y} by several experimental works [4, 11, 12]. Moreover, high-throughput first-principles calculations pointed out that there are no thermodynamic stable Lu-H-N ternary structures and the experimental $Fm\bar{3}m$ -LuH_{3- δ} N _{ϵ} may be a mixture of LuH₂ and LuN [7]. However, a very recent experimental work shows that N-doped $Fm\bar{3}m$ -LuH₃ can be synthesized by applying a 2 GPa pressure [16]. Furthermore, it is found that both N-doping and pressure can stabilize $Fm\bar{3}m$ -LuH₃, and Lu₈H₂₁N is a stable Lu-H-N ternary at 1 GPa [9]. It is noteworthy that both $Fm\bar{3}m$ -LuH₂ and $Fm\bar{3}m$ -LuH₃ are cubic with a lattice parameter ~ 5 Å [9, 17]. Therefore, it is not easy work to distinguish them experimentally. Synthesizing single-crystalline Lu-H compounds is very helpful to understand their intrinsic properties, but it has not been reported thus far.

To address the above, we developed an easy method of synthesizing single-crystalline cubic LuH_{2+ x} films by the post-

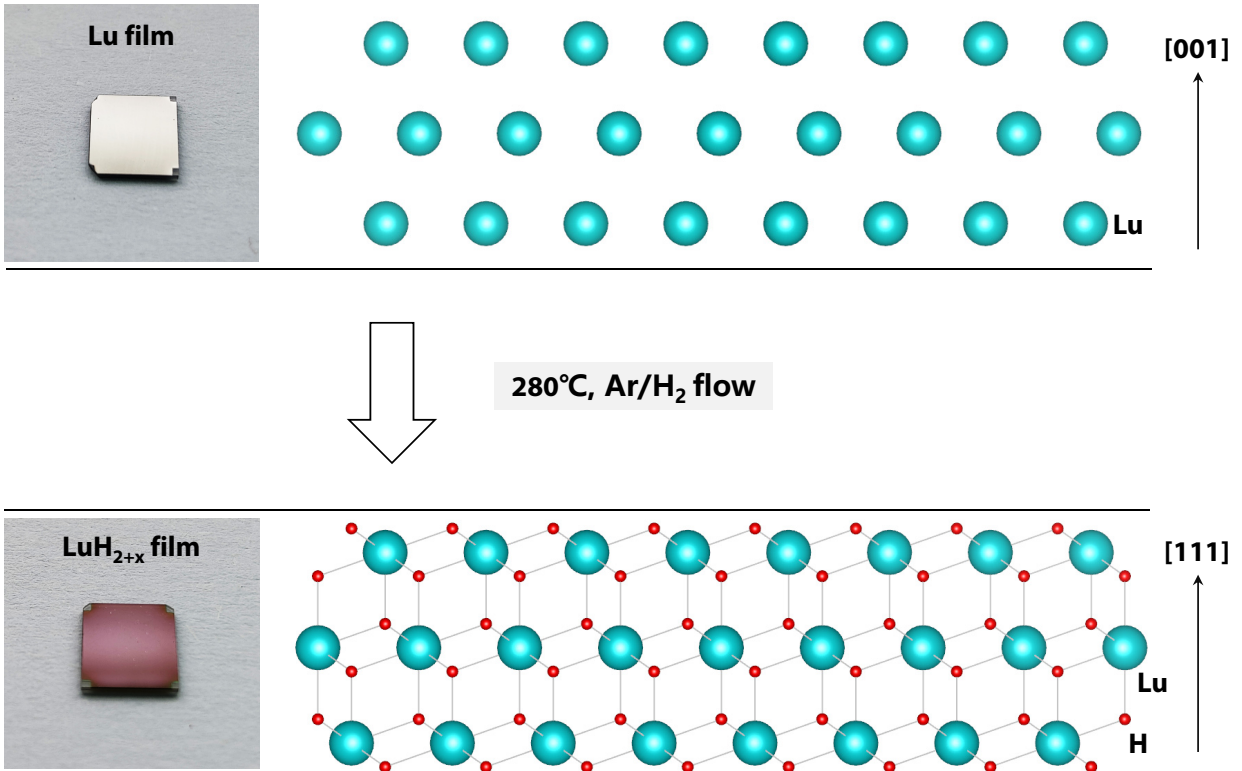


FIG. 1. The photographs and crystal structures of hexagonal Lu (top panel) and cubic LuH_{2+ x} (bottom panel) films.

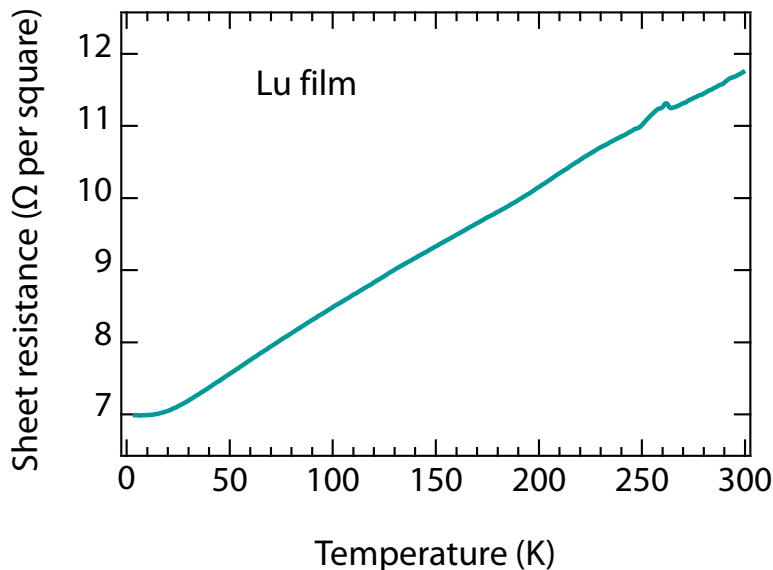


FIG. 2. Temperature-dependent sheet resistance of the Lu film from 300 to 2 K.

annealing of single-crystalline Lu films in the H_2 atmosphere. Unexpectedly, in sharp contrast to metallic LuH_2 powders, the LuH_{2+x} films become purple-red and insulating, indicating the formation of an unreported electronic state of Lu-H compounds. Our work provides a novel route to synthesize more single-crystalline Lu-H compounds.

II. EXPERIMENTS

Single-crystalline Lu thin films (thicknesses ~ 80 nm) were grown on (111)-MgO single crystal substrates ($5 \times 5 \times 0.5$ mm³) by a home-made high-pressure radio frequency (RF) magnetron sputtering, the setup of which is analogous to our previous reports [23–26]. For this sputtering system, the base vacuum pressure is $\sim 1 \times 10^{-7}$ Torr, and the purities of the 2-inch Lu target and the Ar reactive gas are 99.99% and 99.999%, respectively. During growth, the Ar pressure was kept at 0.02 torr with a gas flow of 5.6 sccm, and the substrate temperature was held at 300 °C. The power of the RF generator was 80 W. Furthermore, to ensure the uniformity of the films, the heating stage was rotated during growth. After deposition, the samples were cooled down to room temperature in the same Ar atmosphere. Then, the Lu films on MgO substrates were annealed at 280 °C for 4 hours in a flow of H_2/Ar mixture gas (the volume fraction of H_2 is 8%, purity of 99.99%). During the post-annealing, the pressure of Ar/H_2 was kept at 0.14 MPa.

The crystal structures of Lu and LuH_{2+x} films were characterized by a high-resolution X-ray diffraction (XRD, Bruker D8 Discovery) with the Cu K_α source ($\lambda = 1.5406$ Å) and confocal Raman spectroscopy (Renishaw inVia Reflex) using a 532 nm laser. The electrical properties were measured from 300 to 2 K by Physical Property Measurement System (PPMS) in a van der Pauw geometry (DynaCool, Quantum Design).

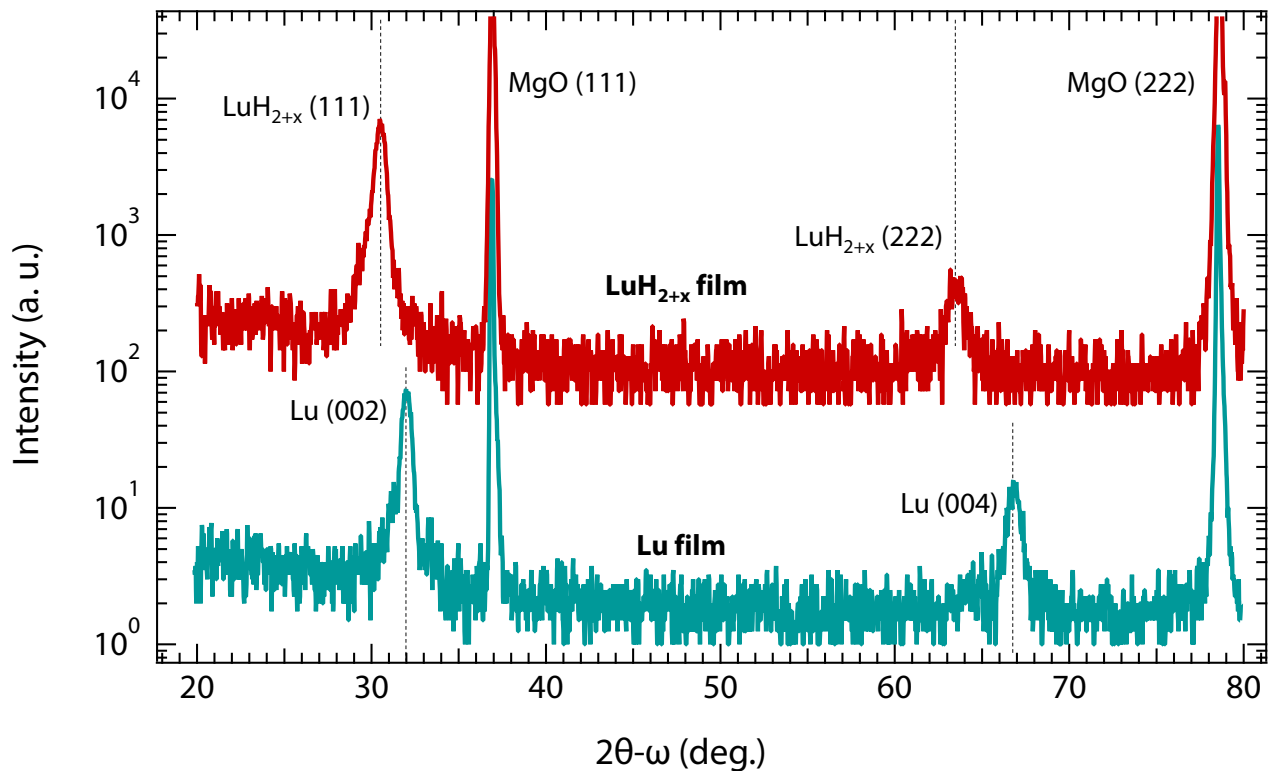


FIG. 3. Wide-range 2θ - ω scans of LuH_{2+x} (red) and Lu (green) films on (111)-MgO substrates.

III. RESULTS AND DISCUSSION

Figure 1 shows the schematic transformation of hexagonal Lu (top panel) to cubic LuH_{2+x} (bottom panel). Generally, single-crystalline Lu has a hexagonal close-packed (hcp) crystal structure with space group $P6_3/mmc$. Its lattice parameters are $a = b = 3.516 \text{ \AA}$ and $c = 5.573 \text{ \AA}$ [27]. Experimentally, the color of Lu films is silver-white before post-annealing (see the top panel in Fig. 1). Unexpectedly, after post-annealing the color of the films change to purple-red (see the bottom panel in Fig. 1), indicating the formation of Lu-H compounds. However, it has been known that bulk $Fm\bar{3}m$ -LuH and $Fm\bar{3}m$ - LuH_3 are unstable at ambient conditions [17]. Therefore, the composition and structure of our purple-red samples are likely to be $Fm\bar{3}m$ - LuH_{2+x} . Also, it is noted that both $Fm\bar{3}m$ - LuH_2 and $Fm\bar{3}m$ - LuH_3 are cubic with a lattice parameter $\sim 5 \text{ \AA}$ [9, 17]. Moreover, N-doped $Fm\bar{3}m$ - LuH_3 has been synthesized at 2 GPa pressure [16]. Considering the existence of strain effect and defects in our purple-red films, the value of x may be positive.

First, to understand the conductivity of Lu and LuH_{2+x} films, we measured electrical transport from 300 to 2 K. As seen in Fig. 2, the Lu films are highly conducting, the sheet resistance of which is $\sim 11 \Omega$ at room temperature. With decreasing the temperature from 300 to 2 K, the resistance of Lu films has a linear dependence of the temperature down to 20 K, then becomes a constant below 20 K. This behavior is consistent with our previous observation of polycrystal Lu bulk [6]. Unexpectedly, in sharp contrast to metallic LuH_2 powders and polycrystals [4–6, 11–15], our LuH_{2+x} films is highly insulating, indicating the formation of an unreported electronic state of Lu-H compounds.

Next, to investigate the crystal structures of Lu and LuH_{2+x} films, we carried out XRD characterization. As seen in Fig. 3, the wide-range 2θ - ω scan on Lu films (see the green curve) only shows the (002) and (004) diffraction peaks without detectable

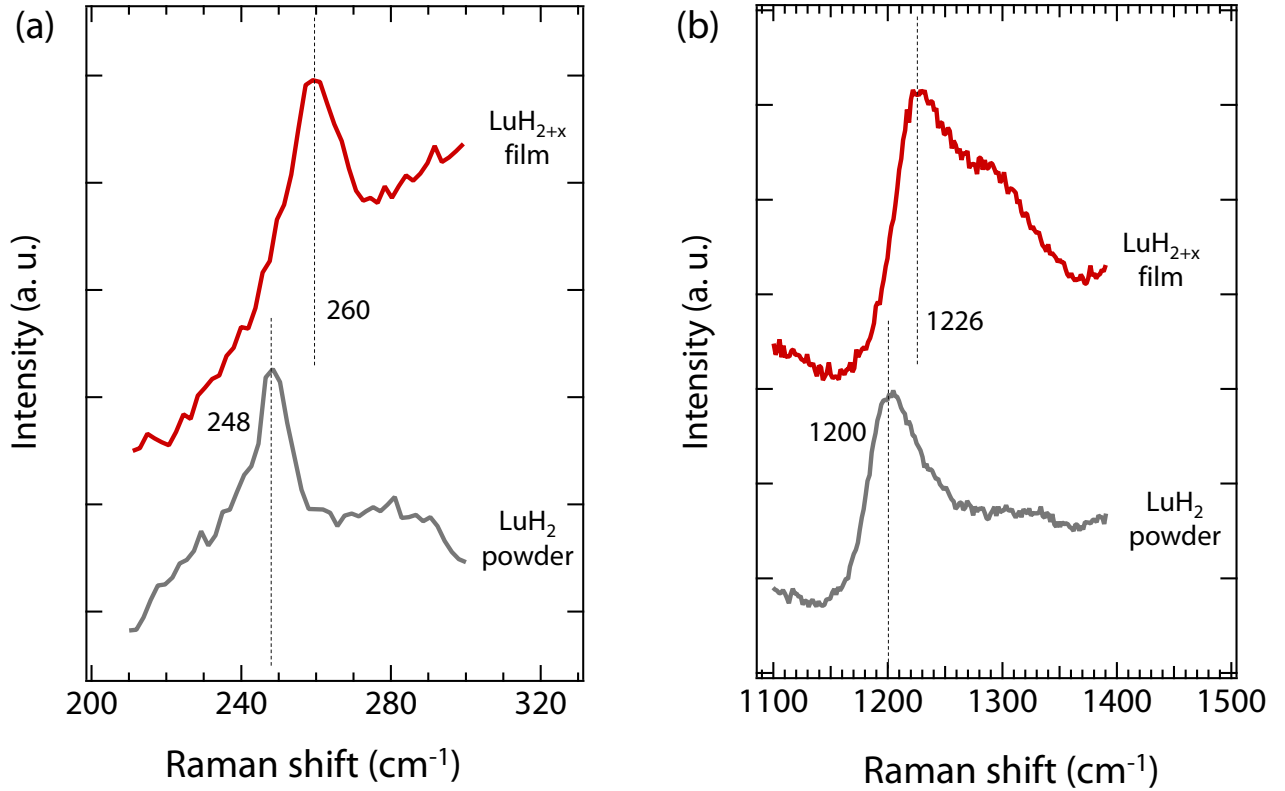


FIG. 4. Raman spectra of LuH_{2+x} films (red curves) and LuH_2 powders (grey curves).

secondary phases, indicating the epitaxial growth of single-crystalline Lu films. The peak position of (002) peak is around 31.998° , corresponding to the lattice parameter $d_{002} = 2.495 \text{ \AA}$, which is close to the value of bulk Lu ($d_{002} = 2.491 \text{ \AA}$), indicating the epitaxy of Lu films on MgO substrates. Interestingly, after the post-annealing, the two diffraction peaks have significant shifts to low diffraction angles (see the red curve in Fig. 3). The peak positions of LuH_{2+x} are around 30.478° and 63.398° , respectively, which agree well with the (111) and (222) diffractions peak positions of cubic LuH_2 or cubic LuH_3 . The extracted out-of-plane lattice parameter of our LuH_{2+x} films is around 5.07 \AA , which is consistent to the value of bulk LuH_2 or LuH_3 ($\sim 5 \text{ \AA}$) [9, 17].

To further understand the crystal structure of LuH_{2+x} films, we measured Raman spectroscopy on both LuH_{2+x} films and LuH_2 powders. It is noted that the contribution of MgO single-crystalline is as small as being ignored. Therefore, the Raman signals of LuH_{2+x} films are strong. As seen in Fig. 4, the two characteristic peaks (~ 250 and 1200 cm^{-1}) can be observed in both LuH_{2+x} films and LuH_2 powders. In contrast to the reported peak positions (248 and 1200 cm^{-1}) of LuH_2 powders and polycrystals [1, 4, 12, 16], these two Raman characteristic peaks have a blue shift to ~ 260 and 1226 cm^{-1} , respectively. It has been pointed out that the strong mode 1200 cm^{-1} can be associated with the T_{2g} Raman-active mode of the cubic structure [16], further demonstrating the formation of cubic LuH_{2+x} . Based on the purple-red color, the insulating state, and the cubic structure of our LuH_{2+x} films, it indicates a formation of an unreported electronic state in LuH_{2+x} films.

IV. CONCLUSION

In this work, we developed an easy way to synthesize single-crystalline cubic LuH_{2+x} films by the post-annealing of single-crystalline Lu films in the H_2 atmosphere. The crystal and electronic structures of films were characterized by XRD, Raman, and electrical transport. Interestingly, Lu films are silver-white and metallic, whereas their transformed LuH_{2+x} films become purple-red and insulating. Based on the purple-red color, the insulating state, and the cubic structure of LuH_{2+x} films, it indicates the formation of an unreported electronic state in our LuH_{2+x} films. Our work provides a novel route to synthesize and explore more single-crystalline Lu-H compounds.

V. ACKNOWLEDGMENTS

We acknowledge insightful discussions with Rui Peng. This work was supported by the National Key R&D Program of China (Grant No. 2022YFA1403000), the National Natural Science Foundation of China (Grant Nos. U2032126 and 11874058), the Pioneer Hundred Talents Program of the Chinese Academy of Sciences, the Zhejiang Provincial Natural Science Foundation of China under Grant No. LXR22E020001, the Beijing National Laboratory for Condensed Matter Physics, the Ningbo Natural Science Foundation (Grant No. 20221JCGY010338), and the Ningbo Science and Technology Bureau (Grant No. 2022Z086).

-
- [1] N. Dasenbrock-Gammon, E. Snider, R. McBride, H. Pasan, D. Durkee, N. Khalvashi-Sutter, S. Munasinghe, S. E. Dissanayake, K. V. Lawler, A. Salamat, and R. P. Dias, Evidence of near-ambient superconductivity in a N-doped lutetium hydride, *Nature* **615**, 244 (2023).
 - [2] Z. Li, X. He, C. Zhang, K. Lu, B. Min, J. Zhang, S. Zhang, J. Zhao, L. Shi, Y. Peng, S. Feng, Z. Deng, J. Song, Q. Liu, X. Wang, R. Yu, L. Wang, Y. Li, J. Bass, V. Prakapenka, S. Chariton, H. Liu, and C. Jin, Superconductivity above 70 K experimentally discovered in lutetium polyhydride, *Sci. China Phys. Mech. Astron.* **66**, 267411 (2023).
 - [3] M. Liu, X. Liu, J. Li, J. Liu, Y. Sun, X.-Q. Chen, and P. Liu, On parent structures of near-ambient nitrogen-doped lutetium hydride superconductor, arXiv:2303.06554 (2023).
 - [4] P. Shan, N. Wang, X. Zheng, Q. Qiu, Y. Peng, and J. Cheng, Pressure-induced color change in the lutetium dihydride LuH_2 , *Chinese Phys. Lett.* **40**, 046101 (2023).
 - [5] X. Ming, Y.-J. Zhang, X. Zhu, Q. Li, C. He, Y. Liu, B. Zheng, H. Yang, and H.-H. Wen, Absence of near-ambient superconductivity in $\text{LuH}_{2\pm x}\text{N}_y$, arXiv:2303.08759 (2023).
 - [6] S. Zhang, J. Bi, R. Zhang, P. Li, F. Qi, Z. Wei, and Y. Cao, Electronic and magnetic properties of Lu and LuH_2 , arXiv:2303.11063 (2023).
 - [7] F. Xie, T. Lu, Z. Yu, Y. Wang, Z. Wang, S. Meng, and M. Liu, Lu-H-N phase diagram from first-principles calculations, *Chinese Phys. Lett.* **40**, 057401 (2023).
 - [8] Z. Huo, D. Duan, T. Ma, Q. Jiang, Z. Zhang, D. An, F. Tian, T. Cui, First-Principles Study on the Superconductivity of N doped Fcc- LuH_3 , arXiv:2303.12575 (2023).
 - [9] Y. Sun, F. Zhang, S. Wu, V. Antropov, and K.-M. Ho, Effect of nitrogen doping and pressure on the stability of cubic LuH_3 , arXiv:2303.14034 (2023).
 - [10] K. P. Hilleke, X. Wang, D. Luo, N. Geng, B. Wang, and E. Zurek, Structure, Stability and Superconductivity of N-doped Lutetium Hydrides at kbar Pressures, arXiv:2303.15622 (2023).
 - [11] Y.-J. Zhang, X. Ming, Q. Li, X. Zhu, B. Zheng, Y. Liu, C. He, H. Yang, H.-H. Wen, Pressure Induced Color Change and Evolution of Metallic Behavior in Nitrogen-Doped Lutetium Hydride, arXiv:2303.17453 (2023).

- [12] X. Xing, C. Wang, L. Yu, J. Xu, C. Zhang, M. Zhang, S. Huang, X. Zhang, B. Yang, X. Chen, Y. Zhang, J. Guo, Z. Shi, Y. Ma, C. Chen, X. Liu, Observation of Non-Superconducting Phase Changes in $\text{LuH}_{2\pm x}\text{N}_y$, arXiv:2303.17587 (2023).
- [13] S. Cai, J. Guo, H. Shu, L. Yang, P. Wang, Y. Zhou, J. Zhao, J. Han, Q. Wu, W. Yang, T. Xiang, H. Mao, L. Sun, No Evidence of Superconductivity in the Compressed Sample Prepared from the Lutetium Foil and H_2/N_2 Gas Mixture, arXiv:2304.03100 (2023).
- [14] N. Wang, J. Hou, Z. Liu, P. Shan, C. Chai, S. Jin, X. Wang, Y. Long, Y. Liu, H. Zhang, X. Dong, J. Cheng, Percolation-Induced Resistivity Drop in Cold-Pressed LuH_2 , arXiv:2304.00558 (2023).
- [15] X. Zhao, P. Shan, N. Wang, Y. Li, Y. Xu, J. Cheng, Pressure Tuning of Optical Reflectivity in LuH_2 , Sci. Bull. (2023).
- [16] O. Moulding, S. Gallego-Parra, P. Toulemonde, G. Garbarino, P. Derango, P. Giroux, and M. Méasson, Trigonal to cubic structural transition in possibly N-doped LuH_3 measured by Raman and X-ray diffraction, arXiv:2304.04310 (2023).
- [17] P. P. Ferreira, L. J. Conway, A. Cucciari, S. Di Cataldo, F. Giannessi, E. Kogler, L. T. F. Eleno, C. J. Pickard, C. Heil, L. Boeri, Search for Ambient Superconductivity in the Lu-N-H System, arXiv:2304.04447 (2023).
- [18] R. Lucrezi, P. P. Ferreira, M. Aichhorn, and C. Heil, Temperature and quantum anharmonic lattice effects in lutetium trihydride: stability and superconductivity, arXiv:2304.06685 (2023).
- [19] H. Song, Z. Zhang, T. Cui, C. J. Pickard, V. Z. Kresin, and D. Duan, High T_c superconductivity in Heavy Rare Earth hydrides: correlation between the presence of the f states on the Fermi surface, nesting and the value of T_c , arXiv:2010.12225 (2020).
- [20] M. Du, H. Song, Z. Zhang, D. Duan, and T. Cui, Room-Temperature Superconductivity in Yb/Lu Substituted Clathrate Hexahydrides under Moderate Pressure, Research **2022**, 9784309 (2022).
- [21] M. Shao, S. Chen, W. Chen, K. Zhang, X. Huang, and T. Cui, Superconducting ScH_3 and LuH_3 at Megabar Pressures, Inorg. Chem. **60**, 15330 (2021).
- [22] D. Wang, Y. Ding, and H.-K. Mao, Future Study of Dense Superconducting Hydrides at High Pressure, Materials **14**, 7563 (2021).
- [23] J. Bi, R. Zhang, S. Peng, J. Sun, X. Wang, W. Chen, L. Wu, J. Gao, H. Cao, and Y. Cao, Robust plasmonic properties of epitaxial TiN films on highly lattice-mismatched complex oxides, Phys. Rev. Mater. **5**, 075201 (2021).
- [24] R. Zhang, X. Li, J. Bi, S. Zhang, S. Peng, Y. Song, Q. Zhang, L. Gu, J. Duan, and Y. Cao, One-step epitaxy of high-mobility La-doped BaSnO_3 films by high-pressure magnetron sputtering, APL Mater. **9**, 061103 (2021).
- [25] R. Zhang, Q. Ma, H. Liu, T. Sun, J. Bi, Y. Song, S. Peng, L. Liang, J. Gao, H. Cao, L. Huang, and Y. Cao, Crystal orientation-dependent oxidation of epitaxial TiN films with tunable plasmonics, ACS Photonics **8**, 847 (2021).
- [26] R. Zhang, X. Li, F. Meng, J. Bi, S. Zhang, S. Peng, J. Sun, X. Wang, L. Wu, J. Duan, H. Cao, Q. Zhang, L. Gu, L. Huang, and Y. Cao, Wafer-scale epitaxy of flexible nitride films with superior plasmonic and superconducting performance, ACS Appl. Mater. Interfaces **13**, 60182 (2021).
- [27] G. N. Chesnut and Y. K. Vohra, Phase transformation in lutetium metal at 88 GPa, Phys. Rev. B **57**, 10221 (1998).