

Understanding the local structure, magnetism and optical properties in layered compounds with d^9 ions: Insight into silver fluorides and K_2CuF_4

Inés Sánchez-Movellán, Guillermo Santamaría-Fernández, Pablo García-Fernández,
José Antonio Aramburu* and Miguel Moreno

Departamento de Ciencias de la Tierra y Física de la Materia Condensada, Universidad
de Cantabria, Cantabria Campus Internacional, 39005 Santander, Spain

* antonio.aramburu@unican.es

Abstract

Using first-principles DFT calculations, we analyze the origin of the different crystal structures, optical and magnetic properties of two basic families of layered fluoride materials with formula A_2MF_4 ($M = Ag, Cu, Ni, Mn$; $A = K, Cs, Rb$). On one hand, Cs_2AgF_4 and K_2CuF_4 compounds (both with d^9 metal cations) crystallize in an orthorhombic structure with $Cmca$ space group and $M_A - F - M_B$ bridge angle of 180° , and they exhibit a weak ferromagnetism (FM) in the layer plane. On the other hand, K_2NiF_4 or K_2MnF_4 compounds (with d^8 and d^5 metal cations, respectively) have a tetragonal $I4/mmm$ space group with 180° bridge angle and exhibit antiferromagnetism (AFM) in the layer plane. Firstly, we show that, contrary to what is claimed in the literature, the $Cmca$ structure of Cs_2AgF_4 and K_2CuF_4 is not related to a cooperative Jahn-Teller effect among elongated MF_6^{4-} units. Instead, first-principles calculations carried out in the $I4/mmm$ parent phase of these two compounds show that MF_6^{4-} units are axially compressed because the electrostatic potential from the rest of lattice ions force the hole to lie in the $3z^2 - r^2$ molecular orbital (z being perpendicular to the layer plane). This fact increases the metal-ligand distance in the layer plane and makes that covalency in the bridging ligand has a residual character (clearly smaller than in K_2NiF_4 or $KNiF_3$) stabilizing for only a few meV (7.9 meV for Cs_2AgF_4) an AFM order. However, this $I4/mmm$ parent phase of Cs_2AgF_4 is unstable thus evolving towards the experimental $Cmca$ structure with an energy gain of 140 meV, FM ordering and orthorhombic MF_6^{4-} units. As a salient feature, it is shown that the FM order in Cs_2AgF_4 and K_2CuF_4 is due to the asymmetry of the in-plane $M_A - F - M_B$ bridge, giving rise to a negligible covalency for the long bond. Moreover, in K_2NiF_4 or K_2MnF_4 , the lack of excited states within the d^n manifold ($n = 8, 5$) of M which can be coupled to the ground state for a local b_{1g} distortion mode hamper the orthorhombic instability thus favoring the AFM ordering. The present ideas also account for the experimental optical and EPR data of Cs_2AgF_4 and K_2CuF_4 . An additional discussion on the silver compound Rb_2AgF_4 is also reported.

1. Introduction

In the realm of insulating layered perovskites^{1,2}, much research is currently focused on those containing the 3d⁹ ion Cu²⁺ due to their attractive optical and magnetic properties³⁻⁶. Inorganic compounds⁷⁻¹² like K₂CuF₄ or Rb₂CuCl₄ as well as organic-inorganic hybrid perovskites of the (C_nH_{2n+1}NH₃)₂CuCl₄ or [NH₃(CH₂)_nNH₃]CuX₄ (X = Cl, Br) families¹³⁻¹⁶ belong to this kind of materials. In all these insulating transition-metal compounds properties are greatly dependent on the equilibrium geometry and the related electronic structure of the CuX₆⁴⁻ complex (X = F, Cl, Br) formed in the crystal.

In the last two decades significant efforts have been focused to exploring insulating compounds that contain the 4d⁹ ion, Ag²⁺, partially driven by the search of new superconducting materials¹⁷. As the optical electronegativity¹⁸ of Ag²⁺ ($\chi = 2.8$) is higher than that of Cu²⁺ ($\chi = 2.4$) and identical to that of Br⁻ ion¹⁹, only crystals of silver(II) fluorides have been synthesized up to now. In chloride and bromide lattices Ag²⁺ has been found only as impurity. For instance, Ag²⁺ has been formed in alkali chlorides²⁰⁻²² and SrCl₂²⁰⁻²² while the AgBr₆⁴⁻ complex has been observed in CdBr₂:Ag²⁺²³ and AgBr_{0.15}Cl_{0.85}:Ag²⁺²⁴ where the hole is mainly placed on ligands and not on the central cation^{18,22}.

Silver compounds of the series A₂AgF₄ (A = Cs, Rb) display a layered structure being Cs₂AgF₄ the most studied compound up to now²⁵⁻³⁶. From the first X-ray measurements, Odenthal et al. initially proposed²⁵ a tetragonal layered structure like that of K₂NiF₄ (space group I4/mmm) for Cs₂AgF₄. However, accurate neutron diffraction data by McLain et al. proved²⁸ that Cs₂AgF₄ is actually orthorhombic (space group Cmca) thus displaying the same crystal structure as K₂CuF₄.

In many previous works, the local geometry and electronic ground state of AgF₆⁴⁻ units in Cs₂AgF₄ have been assumed to be the result of a Jahn-Teller (JT) effect and/or orbital ordering²⁶⁻³⁶. Nonetheless, the existence of a JT effect in Cs₂AgF₄ is hard to accept as the lattice is orthorhombic while doubts were already raised¹¹ on the orbital ordering as responsible for the structure of both K₂CuF₄ and La₂CuO₄. Moreover, we believe that the existence of a small ferromagnetic (FM) coupling in the layer plane of Cs₂AgF₄ and K₂CuF₄ has not been explained in a clear and convincing way. For example, no compelling reasons have been proposed to explain why the transition temperature, T_c, observed for both Cs₂AgF₄ (15 K)²⁸ and K₂CuF₄ (6.25 K)⁷ is certainly smaller than that for the tetragonal perovskite K₂NiF₄ (97.3 K) or the cubic perovskite KNiF₃ (246 K) which are both antiferromagnetic^{37,38} (AFM).

This work is firstly devoted to clearing up the origin of the equilibrium geometry and electronic ground state of AgF₆⁴⁻ units in A₂AgF₄ (A = Cs, Rb) compounds paying special attention to Cs₂AgF₄. To achieve this goal, first-principles calculations together with an analysis of available experimental data are carried out. Once this key issue is clarified,

we further discuss the origin of the FM ordering in the layer plane of Cs_2AgF_4 observed below $T_c = 15$ K.

Interestingly, we try to verify in this work whether some new ideas used for understanding copper layered compounds^{11,12,39} are also valid for the present case. Accordingly, we firstly focus on the $I4/mmm$ parent phase of Cs_2AgF_4 paying attention to the internal electric field, $\mathbf{E}_R(\mathbf{r})$, due to the rest of lattice ions on the behavior of the AgF_6^{4-} unit where active electrons are confined. This internal field plays a key role for understanding the color of Cr^{3+} gemstones^{22,40} or the ground state^{41,42} of CuF_6^{4-} units in $\text{K}_2\text{ZnF}_4:\text{Cu}^{2+}$. For this reason, we explore here the influence of $\mathbf{E}_R(\mathbf{r})$ on the nature of the electronic ground state of AgF_6^{4-} complexes in Cs_2AgF_4 and the associated metal-ligand distances. If the parent phase's structure is different from the equilibrium geometry of Cs_2AgF_4 , it implies the existence of an instability¹² discussed in a second step.

Available electron paramagnetic resonance (EPR) and optical data of Rb_2AgF_4 are quite close^{26,43,44} to those found for Cs_2AgF_4 thus suggesting that Rb_2AgF_4 also exhibits a Cmca structure, a matter also analyzed in the present work.

This work is organized as follows: section 2 provides a detailed explanation of the computational tools employed. In section 3.1, an overlook on previous interpretations of structural, optical and magnetic data of layered silver fluorides is presented, while the remaining part of section 3 displays the main results obtained for Cs_2AgF_4 and K_2CuF_4 . As Cs_2AgF_4 and K_2CuF_4 are model systems in the realm of layered compounds, section 3 is devoted to improving the knowledge on the structural (3.2), EPR (3.3) and optical data (3.4) of both compounds, as well as discussing the origin of their FM behavior not observed in K_2NiF_4 or K_2MnF_4 (3.5). Additionally, section 3.6 briefly discusses the main results obtained in Rb_2AgF_4 . Finally, some conclusions are provided in section 4.

2. Computational Tools

First principles calculations based on Kohn-Sham DFT⁴⁵ were performed on pure K_2CuF_4 , Cs_2AgF_4 , Cs_2CdF_4 , Rb_2AgF_4 and K_2NiF_4 . In order to carry out periodic calculations, Crystal17 package was used^{46,47}. This software makes a full use of the crystal symmetry, allowing us to perform geometry optimizations within specific space groups. In this sense, we can compute unstable phases, such as the high-symmetry parent phases of these compounds, that cannot experimentally be measured^{11,12,48-50}. The instabilities occurring in these phases were explored through frequency calculations considering both FM and AFM orders, as discussed in section 3.5. In Crystal 17 code, Bloch wavefunctions are represented by linear combinations of Gaussian type basis functions^{51,52} centred at atomic sites. The basis sets for the ions were taken from Crystal's webpage⁵². High-quality triple-zeta polarized basis developed by Peitinger et al. were employed⁵¹. For heavy ions (Ag^{2+} , Cd^{2+} and Cs^+), pseudopotentials were used to describe the inner electrons. The exchange-correlation functional employed in these calculations was the hybrid PW1PW, which incorporates 20% of Hartree-Fock (HF) exact exchange.

This functional has been proven to yield accurate results for the geometry and properties of several pure and doped systems⁵³. The obtained results were also cross-verified with another hybrid functional (B1WC) including 16% of HF exchange and different basis sets, leading to similar outcomes.

To ensure convergence, tight criteria were imposed for energy variations (10^{-9} a.u.), as well as for root mean square (RMS) gradients and atomic displacement (0.0001 a.u.). A Monkhorst-Pack grid of 8x8x8 was used to sample the Brillouin zone for numerical integrations.

In addition to periodic calculations, cluster simulations were performed using the ADF software⁵⁴. Hybrid B3LYP functional, which incorporates 25% of HF exchange, together with triple-zeta polarized basis sets were used in the calculations. The core electrons were kept frozen as they do not significantly influence the properties under study. These calculations make possible to explore optical spectra of both isolated and embedded complexes just considering^{11,12,39,55,56} the potential created by the rest of lattice ions V_R . The electrostatic potential, particularly relevant in layered systems, was previously computed by Ewald-Evjen summations^{57,58}. As shown in section 3.4, we can reproduce the experimental optical d-d transitions for CuF_6^{4-} and AgF_6^{4-} with reasonable accuracy when including the electrostatic potential V_R . Despite apparent differences in d-d transitions of these two systems, we demonstrate their consistent behaviour. Furthermore, our calculations on complexes provided valuable information about hybridization and covalency parameters of molecular orbitals, which are closely associated with the exchange constant J , as discussed in section 3.5.

3. Results and discussion on Cs_2AgF_4 and K_2CuF_4

3.1 Survey of previous works on layered silver fluorides

According to the results by McLain et al., Cs_2AgF_4 is a layered compound belonging to the orthorhombic Cmca space group²⁸, being \mathbf{a} the crystal axis perpendicular to the layer plane (Fig. 1). The experimental values of lattice parameters and Ag-F distances are also shown on Fig. 1. $R_z = 2.111 \text{ \AA}$ corresponds to the Ag-F direction perpendicular to the layer plane while $R_x = 2.112 \text{ \AA}$ and $R_y = 2.441 \text{ \AA}$ are associated, respectively, with the short and long Ag-F distances within the layer plane.

Cs_2AgF_4 exhibits an antiferrodistortive arrangement and thus, if we move along the line joining two nearest Ag^{2+} the local longest y axes of two involved AgF_6^{4-} units, are perpendicular (Fig. 2). Interestingly, there is a weak FM exchange coupling, H_{ex} , between two nearest cations (with spins \mathbf{S}_1 and \mathbf{S}_2) in the layer plane of Cs_2AgF_4 described through the effective exchange interaction

$$H_{\text{ex}} = J \mathbf{S}_1 \cdot \mathbf{S}_2 \quad (1)$$

with $J = -3.79 \text{ meV}^{28}$. This situation, also found in $\text{K}_2\text{CuF}_4^{7,28}$, is somewhat surprising as in layered compounds like K_2NiF_4 or K_2MnF_4 the coupling between magnetic cations in the layer plane is AFM³⁸.

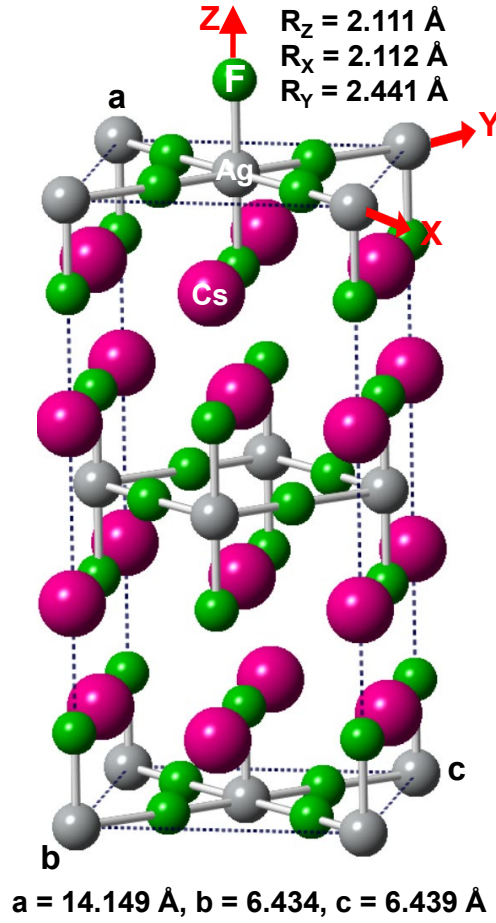


Figure 1. Experimental Cmca structure of Cs_2AgF_4 displaying the local $\{X, Y, Z\}$ axes of a orthorhombic AgF_6^{4-} unit. Values of the lattice parameters and the three $\text{Ag}^{2+}\text{-F}^-$ bond distances are shown.

Concerning EPR spectra of Cs_2AgF_4 in powder, two peaks are well observed^{26,43}. One signal, $g(\mathbf{a})$, corresponds to the magnetic field \mathbf{B} parallel to the \mathbf{a} axis while $g(\perp\mathbf{a})$ is the gyromagnetic factor when \mathbf{B} lies in the layer plane. This isotropic response when \mathbf{B} is in the layer plane obeys to the exchange interaction⁵⁹ between two nearest complexes, A and B. Indeed, using the local $\{x, y, z\}$ bases of A and B complexes in Fig. 2, the $g(i)$ ($i = A, B$) tensors in the crystal $\{X, Y, Z\}$ basis are given by

$$g(A) = \begin{pmatrix} g_y & 0 & 0 \\ 0 & g_x & 0 \\ 0 & 0 & g_z \end{pmatrix} \quad g(B) = \begin{pmatrix} g_x & 0 & 0 \\ 0 & g_y & 0 \\ 0 & 0 & g_z \end{pmatrix} \quad (2)$$

Nevertheless, when the interaction of \mathbf{B} with \mathbf{S}_1 or \mathbf{S}_2 is much smaller than H_{ex} the phenomenon of exchange narrowing takes place⁵⁹ and then $g(\perp\mathbf{a})$ is just given by

$$g(\perp\mathbf{a}) = (g_x + g_y)/2 \quad (3)$$

If $J = -3.79$ meV, the condition $|J| \gg \mu_B B$ (μ_B is the Bohr magneton) is well fulfilled working in the Q band ($B = 1.2$ T) or even using $B = 10$ T²⁶.

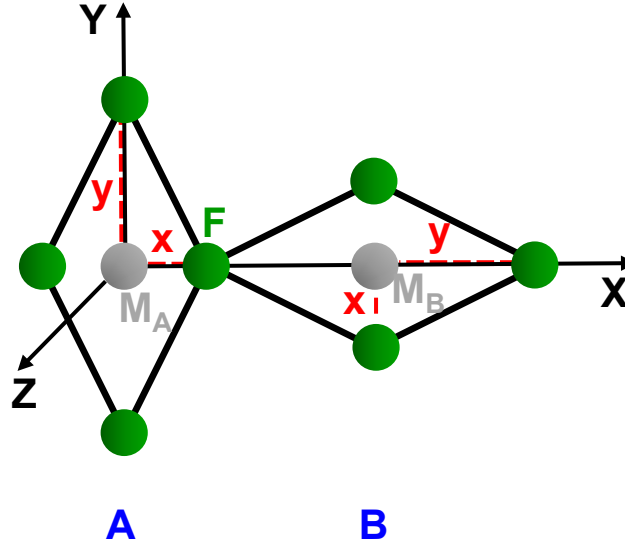


Figure 2. Schematic view of the in-plane antiferrodistortive arrangement of two adjacent A and B AgF_6^{4-} units in Cs_2AgF_4 , where the two local longest y axes are perpendicular.

The local geometry around Ag^{2+} in Cs_2AgF_4 has widely been assumed to arise from a JT effect leading to elongated tetragonal AgF_6^{4-} units^{26,28,30,33,35,43} with y as the local principal axis of the complex and the hole placed in a molecular orbital transforming like $z^2 - x^2$. To underpin this view, McLain et al. argue²⁸ that for JT complexes of d^9 ions the hole is always placed in an orbital of the type $x^2 - y^2$. Accepting the JT assumption, the experimental $g(\mathbf{a}) = g_z$ value should then correspond to the g_{\perp} quantity characteristic of a tetragonal complex while $g_y = g_{\parallel}$ and $g_x = g_{\perp}$. Therefore, in that case $g(\perp\mathbf{a})$ should be equal to

$$g(\perp\mathbf{a}) = (g_{\perp} + g_{\parallel})/2 \quad (4)$$

Nonetheless, doubts are raised by the JT assumption due to the following reasons:

(i) The existence of a JT effect requires a degenerate electronic state in the *initial* geometry⁶⁰⁻⁶². Even if that parent geometry corresponds to a $I4/mmm$ tetragonal phase the electronic ground state of an AgF_6^{4-} unit should not be degenerate due to symmetry reasons.

(ii) Cs_2AgF_4 is a layered compound where layers are perpendicular to the \mathbf{a} crystal axis. Therefore, it is surprising that under the JT assumption the principal axis of the AgF_6^{4-} unit is in the layer plane and not perpendicular to it.

(iii) The local equilibrium geometry for AgF_6^{4-} in Cs_2AgF_4 is not tetragonal but orthorhombic although R_z and R_x are very close as shown in Fig. 1.

(iv) From Eq. (4) and the experimental values $g(\mathbf{a}) = 2.07$ and $g(\perp\mathbf{a}) = 2.25$ we get $g_{\parallel} - g_0 = 0.42$ and $g_{\perp} - g_0 = 0.07$ which are rather different from $g_{\parallel} - g_0 = 0.57$ and $g_{\perp} - g_0 = 0.11$ measured for the cubic lattice CsCdF_3 doped with Ag^{2+} , where EPR data prove the existence of a static JT effect with elongated AgF_6^{4-} units⁶³.

(v) Optical spectra on Cs_2AgF_4 and Rb_2AgF_4 by Friebel and Reinen in the range 0.5 - 3.5 eV suggest the existence of four and not three $d-d$ transitions⁴³, a fact consistent with a local orthorhombic symmetry around Ag^{2+} . However, in the case of K_2CuF_4 , that also displays a Cmca structure, only three $d-d$ transitions have been observed¹⁰ even working at $T = 5$ K, a matter that is certainly puzzling⁶⁴.

(vi) Although most of d^9 systems which exhibit a static JT effect are elongated with a hole in a $x^2 - y^2$ type orbital^{21,60,62} this is not a general rule. For instance, in the cubic CaO lattice doped with Ni^{2+} the hole is in a $3z^2 - r^2$ orbital and the octahedron compressed^{65,66}. In non-JT systems like $\text{K}_2\text{ZnF}_4:\text{Cu}^{2+}$, where the host lattice is tetragonal^{41,42}, the hole is also in $3z^2 - r^2$.

The following sections are addressed to clarify all these questions with the help of first principles simulations.

3.2 Origin of the structure and electronic ground state

In order to explain in a consistent way the experimental results on Cs_2AgF_4 exposed in section 3.1, it is crucial to know the actual ground state of involved AgF_6^{4-} units and the origin of its equilibrium geometry. For achieving this goal, we have followed 3 steps:

(1) Firstly, we have determined the *parent phase* of the Cmca structure of Cs_2AgF_4 by substituting all Ag^{2+} ions of Cs_2AgF_4 by the closed shell cation Cd^{2+} , with an ionic radius similar to that of Ag^{2+} , and performed a geometry optimization keeping fixed the Cmca space group. As shown in Table 1, under the $\text{Ag}^{2+} \rightarrow \text{Cd}^{2+}$ substitution, the structure evolves from the initial orthorhombic to a final one where $a = b$ and $R_x = R_y$, associated to a tetragonal $I4/mmm$ symmetry. In this parent structure, $R_z < R_x$ although $R_x - R_z$ is equal only to 0.044 Å. This $I4/mmm$ parent phase, characteristic of compounds like K_2NiF_4 or K_2ZnF_4 , is the same previously found^{11,12} in K_2CuF_4 .

(2) Then, it is useful to explore the behavior of Cs_2AgF_4 fixing the $I4/mmm$ structure of the parent phase. Interestingly, the results of this step (2) (Table 1) show that in the $I4/mmm$ structure the AgF_6^{4-} units are tetragonally compressed ($R_z < R_x = R_y$) with a hole in the antibonding molecular orbital transforming like $3z^2 - r^2$. Therefore, in this step the

principal axis of the AgF_6^{4-} unit is perpendicular to the layer plane. As it also happens^{11,12,41,42} for $\text{K}_2\text{ZnF}_4:\text{Cu}^{2+}$ or K_2CuF_4 , this ground state is helped by the action of the internal electric field $\mathbf{E}_R(\mathbf{r})$ on active electrons confined in the AgF_6^{4-} unit. Fig. 3 depicts the energy of an electron ($-e$ charge) of an AgF_6^{4-} unit under the electrostatic potential, $V_R(\mathbf{r})$, generating the internal electric field, $\mathbf{E}_R(\mathbf{r})$, through $\mathbf{E}_R(\mathbf{r}) = -\nabla V_R(\mathbf{r})$. It can be seen that $-eV_R(\mathbf{r})$ raises the energy of an electron placed in $3z^2 - r^2$ while it lowers that of a $x^2 - y^2$ electron and thus this fact alone favors locating the hole in a $3z^2 - r^2$ orbital. This behavior of the $-eV_R(\mathbf{r})$ energy is thus similar to that found in compounds like K_2BF_4 ($B = \text{Mg}, \text{Zn}, \text{Cu}$) which also exhibit a layered structure^{11,12,41,42}.

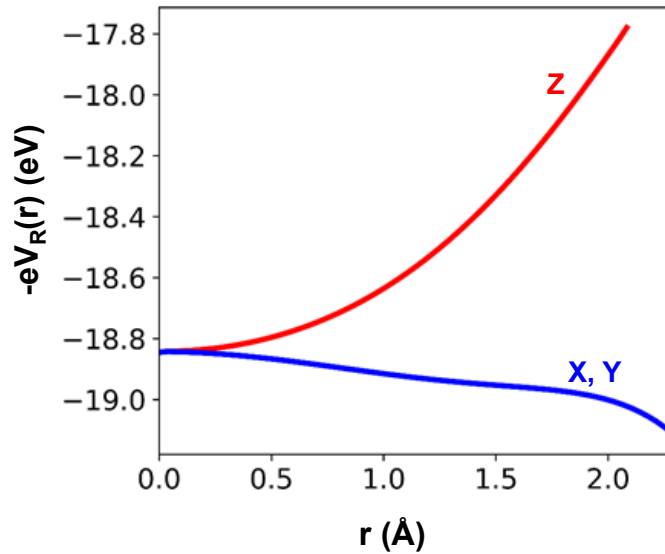


Figure 3. Potential energy $-eV_R(\mathbf{r})$ corresponding to the internal electric field created by the rest of lattice ions on a AgF_6^{4-} unit of Cs_2AgF_4 in the tetragonal $I4/mmm$ parent phase, depicted along the local X, Y, and Z directions of the complex.

It is worth noting that on passing from Cs_2CdF_4 to Cs_2AgF_4 keeping the $I4/mmm$ structure, $R_x - R_z$ increases by a factor close to five. This significant difference just reflects that Ag^{2+} has not a closed shell⁵⁸ structure as Cd^{2+} . Indeed, if in the tetragonal phase of Cs_2AgF_4 there is a hole in the $3z^2 - r^2$ orbital, this induces⁶⁷ an attractive force on two axial ligands and an increase of $R_x - R_z$. Due to this process, at the end of the step (2) there are two Ag-F bonds with $R_z = 2.081 \text{ \AA}$ while four *softer* at a distance $R_x = R_y = 2.292 \text{ \AA}$.

(3) In a further step, when the $I4/mmm$ restriction is lifted the calculated structure of Cs_2AgF_4 evolves until reaching a Cmca space group. As shown in Table 1, the optimized lattice parameters and Ag-F distances in step (3) coincide with those measured experimentally within 1.6%.

It should be remarked that, on passing from step (2) to step (3), R_z undergoes a slight increase of 0.049 Å while $R_y - R_x$ moves from zero to 0.35 Å implying a significant distortion in the layer plane. This fact supports that the local equilibrium geometry of the AgF_6^{4-} unit in the step (3) is essentially orthorhombic despite the experimental R_x and R_z values differ at the end by 0.001 Å (Table 1). Considering this fact alone, previous works on Cs_2AgF_4 have assumed^{26,28,30,33,35,43} the existence of a JT effect with the local y as principal axis. The same assumption has been applied^{9,10,68} to explain K_2CuF_4 where experimental Cu^{2+} -F⁻ distances⁸ are $R_z = 1.939$ Å, $R_x = 1.941$ Å and $R_y = 2.234$ Å.

Step	compound	Space group	a	b	c	R_z	R_x	R_y
(1)	Cs_2CdF_4	Cmca	14.773	6.392	6.392	2.216	2.260	2.260
(2)	Cs_2AgF_4	I4/mmm	4.585	4.585	14.238	2.081	2.292	2.292
(3)	Cs_2AgF_4	Cmca	14.382	6.454	6.455	2.130	2.106	2.458
Experim.	Cs_2AgF_4	Cmca	14.149	6.434	6.439	2.112	2.111	2.441

Table 1. Step (1): calculated values of lattice parameters and Cd-F distances for Cs_2CdF_4 assuming an initial Cmca structure, which is the equilibrium structure of Cs_2AgF_4 . It evolves until reaching an equilibrium tetragonal I4/mmm structure where $b = c$ and $R_x = R_y$. Step (2): calculated lattice parameters and Ag-F distances corresponding to Cs_2AgF_4 but *fixing* a I4/mmm space group. Step (3): Idem that step (2) but derived for the Cmca equilibrium structure. The last values are compared to experimental ones²⁸. Note that the c axis in the standard I4/mmm becomes the a axis in the standard Cmca. All distances are given in Å units.

The nature of the electronic ground state of AgF_6^{4-} units derived from present calculations sheds light to clarify this key issue. Indeed, they reveal that the hole keeps a dominant $3z^2 - r^2$ character at the equilibrium geometry of Cs_2AgF_4 (step (3)). More precisely, an orthorhombic distortion allows the admixture of the molecular orbitals $|3z^2 - r^2\rangle$ and $|x^2 - y^2\rangle$ of the AgF_6^{4-} unit for describing the wavefunction of the hole, $|\varphi_H\rangle$, and thus

$$|\varphi_H\rangle = \alpha |3z^2 - r^2\rangle - \beta |x^2 - y^2\rangle \quad (5)$$

The present calculations give $\beta^2 = 19\%$ underlining that the orthorhombic distortion has only a moderate effect on $|\varphi_H\rangle$, a situation consistent with the degree of orthorhombicity given by the quantity $\eta = 2(R_y - R_x)/(R_y + R_x)$. Indeed, using the R_y and R_x values given in Table 3 we obtain $\eta = 14.5\%$.

The results in Table 1 support that the parent phase I4/mmm (where $R_y = R_x$) is not the stable one for Cs_2AgF_4 . This instability is helped by the vibronic coupling between the electronic ground state of a AgF_6^{4-} unit, ${}^2A_{1g}$, and ${}^2B_{1g}$ excited states driven by a b_{1g} distortion mode described in Figure 4. That coupling is symmetry allowed and can lead

to a total force constant that becomes negative ($K < 0$) thus favoring a $Cmca$ phase at equilibrium. According to that distortion mode (Fig. 4) the four planar F^- ligands of a given Ag^{2+} forming initially a square give rise at the end to a rhombus where $R_y \neq R_x$.

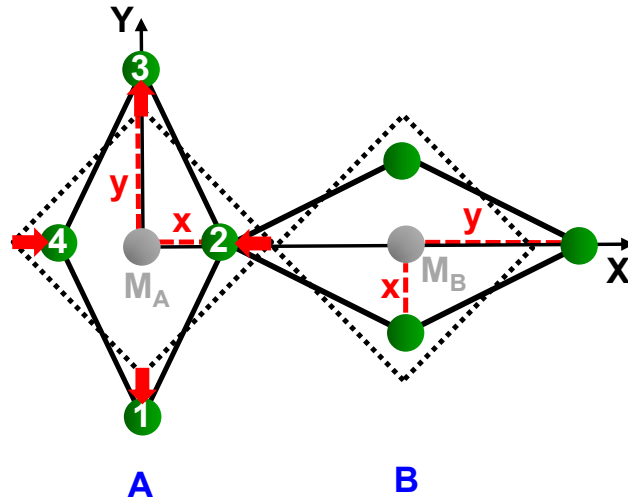


Figure 4. b_{1g} distortion mode of the four planar F^- ligands (red arrows) of a given AgF_6^{4-} unit of Cs_2AgF_4 , going from a square to a rhombus where $R_y \neq R_x$. The b_{1g} distortion mode can be described in terms of the normal coordinate Q , given by $Q = \frac{1}{2}(-u_1 - u_2 + u_3 + u_4)$, where u_i ($u_1 = -u_3 = u_2 = -u_4$) are the displacements of atoms 1-4.

To clarify this relevant matter a negative force constant can take place as there are two contributions⁶⁹ to the force constant K . Let us designate by $H_0(\mathbf{r})$ the electronic Hamiltonian when the lattice is frozen at equilibrium positions. The corresponding ground state wavefunction is termed $\Psi_0(\mathbf{r})$ while excited states are $\Psi_i(\mathbf{r})$ with $i > 0$. If we move around the equilibrium position activating a Q coordinate a new vibronic term, $h(Q, \mathbf{r})$, has to be added to the Hamiltonian

$$H = H_0(\mathbf{r}) + h(Q, \mathbf{r}) \quad (6)$$

with $h(0, \mathbf{r}) = 0$. A first elastic contribution to the force constant, called K_0 , comes from considering only $h(Q, \mathbf{r})$ and $\Psi_0(\mathbf{r})$, thus neglecting the changes on the ground state wavefunction caused by the Q distortion. However, the presence of $h(Q, \mathbf{r})$ also makes that the ground state wavefunction is no longer $\Psi_0(\mathbf{r})$ but involves an admixture of excited states $\Psi_i(\mathbf{r})$ giving rise to a negative vibronic contribution, K_v , to the force constant. If Q is a non-symmetric non-degenerate vibration mode transforming as irrep Γ , $h(Q, \mathbf{r})$ is usually expanded as

$$h(Q, \mathbf{r}) = V(\mathbf{r})Q + \dots \quad (7)$$

where, in the linear electron-vibration coupling, $V(\mathbf{r})$ transforms like Q . In second-order perturbation theory, this coupling give rise to the following expression for K_v

$$K_v = - \sum_{i>0} \frac{|\langle \Psi_0 | V(r) | \Psi_i \rangle|^2}{E_i - E_0} \quad (8)$$

Accordingly, $K_v < 0$ for the electronic ground state, and K is just given by⁶⁹

$$K = K_0 - |K_v| \quad (9)$$

The excited states in Eq. (8) must have the same spin as the ground state. Moreover, if $\Psi_0(\mathbf{r})$ and $\Psi_i(\mathbf{r})$ belong to the irreps Γ_0 and Γ_i , respectively, non-zero matrix elements in Eq. (8) are obtained only when $\Gamma_0 \otimes \Gamma_i \supset \Gamma$. Therefore, in a tetragonal MF_6^{4-} complex ($M = \text{Cu, Ag}$), a ${}^2A_{1g}$ ground state can be mixed with an excited ${}^2B_{1g}$ state, involving a hole in $x^2 - y^2$, through the vibronic coupling involving a local b_{1g} distortion mode⁷⁰.

According to Eq. (9), the instability develops when K becomes negative and is favored for low values of K_0 and thus soft bonds. If initially there is a compressed tetragonal complex, then $R_z < R_y = R_x$ and thus the equatorial bonds are softer than axial ones. This fact favors in principle the development of an orthorhombic distortion in the equatorial plane^{11,12,39,67} provided $K < 0$. On the contrary, when the complex is elongated and $R_z > R_y = R_x$, it hardens the equatorial bonds a fact that works against the distortion. For this reason, in systems like NaCl:M^{2+} ^{20,21,71} or $\text{CsCdF}_3:\text{M}^{2+}$ ($M = \text{Cu, Ag}$)⁴⁹ where MX_6^{4-} units ($X = \text{Cl, F}$) are tetragonally elongated, no orthorhombic distortion in the equatorial plane has been observed. The same situation is encountered for La_2CuO_4 ¹¹.

In the case of layered compounds, the condition $K < 0$ can be better fulfilled for chlorides than for fluorides where bonds are stronger. For this reason, the orthorhombic distortion in the layer plane has already been observed⁷² for Cu^{2+} -doped $(\text{CH}_3\text{NH}_3)_2\text{CdCl}_4$ but not for $\text{K}_2\text{ZnF}_4:\text{Cu}^{2+}$ where CuF_6^{4-} units display a compressed tetragonal symmetry⁷³. Nevertheless, if we move to the pure compound K_2CuF_4 two adjacent CuF_6^{4-} complexes share a common ligand and this fact has been shown¹² to help K to become negative. This situation is also found in Cs_2AgF_4 .

3.3 Interpretation of EPR data of Cs_2AgF_4 and K_2CuF_4

The orthorhombic instability taking place in Cs_2AgF_4 obeys to the same grounds previously discussed^{11,12} for K_2CuF_4 . For this reason, we have now to reinterpret the EPR data obtained^{26,43} for Cs_2AgF_4 based on AgF_6^{4-} units initially compressed along the z axis that undergo a moderate orthorhombic distortion ($\eta = 14.5\%$) in the layer plane. For a compressed tetragonal AgF_6^{4-} unit, g_z differs from g_0 only in third-order perturbations⁷⁴ and thus the tetragonal expression is

$$g_z(T) = g_0 - \Delta g^{(3)} \quad (10)$$

For AgF_6^{4-} , the estimated third-order correction is $\Delta g^{(3)} \approx 0.02$. In a further step, a moderate orthorhombicity induces an admixture of $|x^2 - y^2\rangle$ in $|3z^2 - r^2\rangle$ (Eq. (5)), thus giving rise to a contribution to g_z in second-order perturbations. Accordingly, the octahedral expression of g_z in the equilibrium situation can be estimated by^{39,70,74}

$$g_z(O) = g_0 - \Delta g^{(3)} + \beta^2 \delta g_z(x^2 - y^2) \quad (11)$$

Here, $\delta g_z(x^2 - y^2) \equiv g_z(x^2 - y^2) - g_0$ corresponds to a hole fully located in a pure $|x^2 - y^2\rangle$ orbital. Taking $\delta g_z(x^2 - y^2) \approx 0.55$ from EPR data⁴⁹ of $\text{CsCdF}_3:\text{Ag}^{2+}$ and $\beta^2 = 19\%$ from present calculations for Cs_2AgF_4 , we finally obtain $g_z(O) = 2.086$, a figure reasonably close to the experimental value²⁶ $g_z = 2.077$.

Although for a compressed tetragonal AgF_6^{4-} unit with z as main axis $g_y = g_x = g_{\perp}(T)$ the orthorhombic distortion in the layer plane leads finally to $g_y(O) \neq g_x(O)$. As the orthorhombicity is moderate ($\eta = 14.5\%$), the difference between $g_y(O)$ and $g_x(O)$ comes mainly from the hybridization of $|3z^2 - r^2\rangle$ and $|x^2 - y^2\rangle$ (Eq. (5)). In this case, the expressions of $g_y(O)$ and $g_x(O)$ are^{39,70,74}

$$\begin{aligned} g_y(O) - g_0 &= [g_{\perp}(T) - g_0] \left[1 + \frac{\beta}{\sqrt{3}}\right]^2 \\ g_x(O) - g_0 &= [g_{\perp}(T) - g_0] \left[1 - \frac{\beta}{\sqrt{3}}\right]^2 \end{aligned} \quad (12)$$

Therefore, $g_y(O) - g_x(O)$ is given by

$$g_y(O) - g_x(O) = \frac{4\beta}{\sqrt{3}} [g_{\perp}(T) - g_0] \quad (13)$$

Due to the phenomenon of exchange narrowing⁴⁵, when the magnetic field is in the layer plane of Cs_2AgF_4 only an isotropic signal $g(\perp \mathbf{a}) = (1/2)[g_x(O) + g_y(O)]$ is observed. From Eq. (12) that quantity can be expressed as follows

$$\frac{g_x(O) + g_y(O)}{2} - g_0 = [g_{\perp}(T) - g_0] \left[1 + \frac{\beta^2}{9}\right] \quad (14)$$

Therefore, from the experimental value^{26,43} $g(\perp \mathbf{a}) = 2.25$ and the calculated $\beta^2 = 19\%$ we derive from Eqs. (13) and (14) the values $g_y(O) = 2.38$ and $g_x(O) = 2.12$.

It is worth noting now that a similar situation is encountered in the layered compound K_2CuF_4 where experimental EPR data⁷ yield $g(\mathbf{a}) = 2.08$ and $g(\perp \mathbf{a}) = 2.30$ while a value $\beta^2 = 17\%$ is obtained from calculations¹¹. Interestingly, in the layered hybrid perovskite $(\text{CH}_3\text{NH}_3)_2\text{CdCl}_4$ doped with Cu^{2+} there is also an orthorhombic distortion giving rise to the experimental values^{72,12}, measured at $T = 10$ K, $g_z = 2.05$, $g_y = 2.33$ and $g_x = 2.12$. This pattern is thus comparable to that estimated for Cs_2AgF_4 . The fingerprint of the orthorhombic instability in the chlorine plane is also found in NH_4Cl containing the $\text{CuCl}_4(\text{H}_2\text{O})_2^{2-}$ radical where EPR data⁷⁵ at $T = 4.2$ K yield $g_z = 2.02$, $g_y = 2.41$ and $g_x = 2.18$. Obviously, in these cases involving impurities, there is no exchange narrowing but the average signal at $(1/2)(g_x + g_y)$ is also well seen upon raising the temperature due to a motional narrowing process^{74,20,21,48}.

3.4 Interpretation of optical data of Cs_2AgF_4 and K_2CuF_4

Concerning optical spectra, it is first necessary to understand why only three d-d transitions¹⁰ have been reported experimentally for K_2CuF_4 while four⁴³ for Cs_2AgF_4 , despite both compounds exhibit the same $Cmca$ structure.

	$x^2 - y^2 \rightarrow 3z^2 - r^2$	$xz \rightarrow 3z^2 - r^2$	$yz \rightarrow 3z^2 - r^2$	$xy \rightarrow 3z^2 - r^2$
Isolated CuF_6^{4-}	0.77	1.13	1.32	1.31
CuF_6^{4-} under $V_R(\mathbf{r})$	1.04	1.17	1.42	1.51
Experimental	1.03	1.17	1.50	1.50

Table 2. Calculated energy values (in eV) of four d-d transitions for a CuF_6^{4-} unit in K_2CuF_4 at the equilibrium $Cmca$ structure where experimental $Cu^{2+}-F^-$ distances are $R_z = 1.939$ Å, $R_x = 1.941$ Å and $R_y = 2.234$ Å. For the sake of clarity, the transitions are firstly derived ignoring the internal potential $V_R(\mathbf{r})$, whereas its influence upon the CuF_6^{4-} unit is considered in a second step. Experimental values¹⁰ for K_2CuF_4 are also reported for comparison. Due to the local orthorhombic symmetry of CuF_6^{4-} units in K_2CuF_4 a transition termed as $x^2 - y^2 \rightarrow 3z^2 - r^2$ only reflects the dominant character of involved orbitals.

The calculated d-d transitions for K_2CuF_4 at equilibrium are gathered in Table 2. These results firstly show the importance of considering the effect of the internal electric field $E_R(\mathbf{r})$ on the electrons confined in the CuF_6^{4-} unit, where the shape¹² of the associated electrostatic potential, $V_R(\mathbf{r})$, is similar to that depicted in Fig. 3 for an AgF_6^{4-} unit in Cs_2AgF_4 . Once $V_R(\mathbf{r})$ is incorporated into the calculation the two lowest d-d transitions essentially coincide with those observed experimentally¹⁰ (Table 2). Interestingly the present calculations for K_2CuF_4 reveal that there are four different transitions although the two highest ones derived at 1.42 eV and 1.51 eV are only separated by 0.09 eV. The comparison of this figure with the bandwidth (~ 0.30 eV) measured at $T = 5$ K of the band peaked at 1.50 eV reasonably explains why the two highest d-d transitions are not resolved in the optical spectrum of K_2CuF_4 in agreement with a previous work⁵⁰

		$x^2 - y^2 \rightarrow 3z^2 - r^2$	$xz \rightarrow 3z^2 - r^2$	$yz \rightarrow 3z^2 - r^2$	$xy \rightarrow 3z^2 - r^2$	CT
Experim.	Friebel et al [43]	1.59	1.92	2.27	2.45	–
	Tong et al [44]	–	1.91	–	2.48	4.59
Calculated	Isolated AgF_6^{4-}	1.03	1.70	1.94	1.94	5.0
	AgF_6^{4-} with $V_R(\mathbf{r})$	1.43	1.74	1.97	2.18	4.94

Table 3. Experimental d-d transitions for Cs_2AgF_4 compared to those derived from present calculations. The transitions are firstly calculated ignoring the $V_R(\mathbf{r})$ potential while its influence upon the AgF_6^{4-} unit is considered in a second step. Due to the local orthorhombic symmetry of AgF_6^{4-} units in Cs_2AgF_4 a transition termed as $x^2 - y^2 \rightarrow 3z^2 - r^2$ only reflects the dominant character of involved orbitals. The energy of the charge

transfer (CT) transition observed⁴⁴ by Tong et al. is also given and compared to the calculated value. Transition energies are given in eV.

Experimental optical data for Cs₂AgF₄ are collected in Table 3 together with the results of present calculations. As shown in Table 3, calculated d-d transitions follow the experimental pattern but, in this case, they underestimate the experimental energies by ~ 0.2 eV. Again, the results gathered in Table 3 stress the significant role played by the internal field $\mathbf{E}_R(\mathbf{r})$, specially for understanding the value of the lowest $x^2 - y^2 \rightarrow 3z^2 - r^2$ transition and the 0.2 eV gap between the $yz \rightarrow 3z^2 - r^2$ and $xy \rightarrow 3z^2 - r^2$ transitions. At variance with what happens for K₂CuF₄, the existence of such a gap can well be inferred looking at the optical spectrum⁴³ of Cs₂AgF₄.

In view of the method followed for clarifying the structure of Cs₂AgF₄ in section 3.2, it is worth analyzing the evolution of d-d transitions on passing from the I4/mmm parent phase to the equilibrium Cmca and the influence that the internal field, $\mathbf{E}_R(\mathbf{r})$, has upon them^{50,57}. Results of present calculations are displayed in Fig. 5. In the initial I4/mmm phase, ignoring $\mathbf{E}_R(\mathbf{r})$, the calculated d-d transitions are consistent with a local compressed tetragonal symmetry of the AgF₆⁴⁻ unit with z as main axis. Accordingly, the $xz \rightarrow 3z^2 - r^2$ and $yz \rightarrow 3z^2 - r^2$ transitions are degenerate and the highest d-d transition is $xy \rightarrow 3z^2 - r^2$. The local orthorhombic distortion associated with the I4/mmm \rightarrow Cmca step increases significantly the gap between the mainly $3z^2 - r^2$ and $x^2 - y^2$ levels from 0.64 eV to 1.03 eV as a result of the repulsion of these orbitals, both belonging to the a_g irrep under D_{2h} symmetry. At the same time, as the distortion makes that R_y becomes the longest metal-ligand distance, the energy of two levels yz and xy decreases and the $yz \rightarrow 3z^2 - r^2$ and $xy \rightarrow 3z^2 - r^2$ transitions are found to be accidentally degenerate. Finally, the inclusion of the V_R(r) potential tends to increase the energy along z direction (Fig. 3). For this reason, it also enhances the energy of the transition between the mainly $x^2 - y^2$ and $3z^2 - r^2$ orbitals that moves from 1.03 eV to 1.43 eV. In the same vein, the $xy \rightarrow 3z^2 - r^2$ transition increases from 1.94 eV to 2.18 eV. Due to this fact that transition is no longer degenerate with $yz \rightarrow 3z^2 - r^2$ nearly insensitive to the effects of V_R(r).

The measurements⁴⁴ by Tong et al. on Cs₂AgF₄ also show a band peaked at 4.6 eV ascribed to a charge transfer transition of the AgF₆⁴⁻ unit. In the case of fluoride complexes a charge transfer excitation in the optical range (up to 6.2 eV) cannot usually be observed due to the high electronegativity of fluorine ($\chi = 3.9$). This hindrance however disappears for AgF₆⁴⁻ complexes⁷⁶ due to the high optical electronegativity of Ag²⁺ ($\chi = 2.8$). Interestingly, in the case of the layered (C₂H₅NH₃)₂CdCl₄ compound doped with Cu²⁺ the first allowed charge transfer transition is observed at 3.1 eV⁵. Thus, according to the optical electronegativities¹⁹ of chlorine ($\chi = 3.0$) and Cu²⁺ ($\chi = 2.4$), we can estimate that such a transition would occur around 4.9 eV for Cs₂AgF₄. Our calculations (Table 3) lead to a transition energy equal to 4.95 eV.

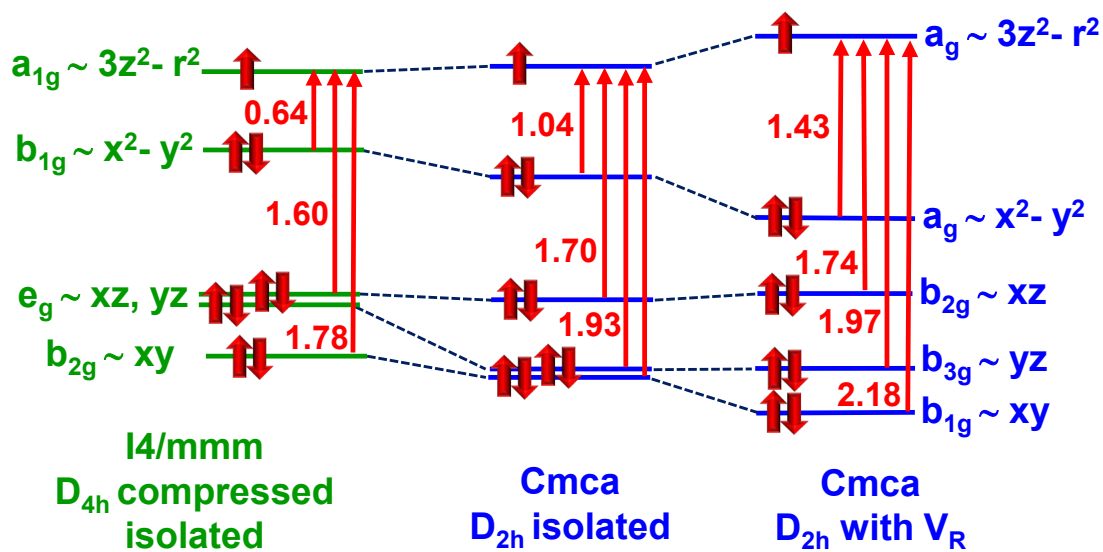


Figure 5. Evolution of mainly d orbitals of a AgF_6^{4-} unit of Cs_2AgF_4 and the corresponding d-d transitions (given in eV units) along 3 steps. Left: isolated complex with the tetragonally compressed geometry (D_{4h} symmetry with $R_y = R_x > R_z$) optimized for the metastable $I4/mmm$ parent phase. Center: isolated complex with the orthorhombic geometry (D_{2h} symmetry with $R_y \neq R_x$) optimized in the Cmca equilibrium structure. Right: same geometry than in previous step but adding the effect of the internal electrostatic potential $V_R(r)$.

3.5 Insight into the ferromagnetism of Cs_2AgF_4 and K_2CuF_4 and comparison with K_2NiF_4

This section addresses the origin of the two significant differences between the magnetic behavior of layered compounds Cs_2AgF_4 and K_2CuF_4 and that of the model system K_2NiF_4 .

The main magnetic mechanism in play in these insulating lattices is superexchange that usually favors AFM ordering when the metal-ligand-metal bond occurs along a straight line. The main model describing superexchange, Anderson's model⁷⁷⁻⁷⁹, is usually applied in a straightforward manner to K_2NiF_4 . However, systems containing d^9 ions, like Cs_2AgF_4 and K_2CuF_4 , are usually said to contain an orbital degree of freedom, i.e., the energy of the system and magnetic ordering are heavily influenced by how the occupied orbitals orient with respect to each other. Kugel and Khomskii proposed⁸⁰ the orbital ordering model based on two basic assumptions: (i) the $3z^2-r^2$ and x^2-y^2 orbitals are degenerate, and (ii) the energy of the system depends, essentially, on superexchange interactions between these orbitals. In 1973 they applied the orbital model to K_2CuF_4 predicting an antiferrodistortive orbital order at the $I4/mmm$ phase, characterized by electrons in alternating $3x^2-r^2/3y^2-r^2$ orbitals, that would be the seed that leads to the orthorhombic distortion⁸¹. Moreover, they argued that this orbital antiferrodistortive

order was necessary to obtain a FM ordering. However, the results in the previous section clearly show that the assumptions of the orbital ordering model are not correct. There exists a large gap between the a_{1g} and b_{1g} states in the $I4/mmm$ parent phase so the orbitals are not degenerate favoring the hole to move to the $3z^2-r^2$ orbital in fluoride lattices. This FM ordering of the orbitals would be contrary to that predicted by the Kugel-Khomskii model and would lead to AFM ordering in the $I4/mmm$ parent phase. This will be confirmed by first-principles simulations below. Moreover, if the orbital ordering is applicable to K_2CuF_4 it would also be applicable to La_2CuO_4 , a system well known for its strong AFM ordering¹¹. Thus, we believe that the use of the orbital ordering model in these lattices is compromised⁶, and the origin of the magnetic structure should be re-analyzed in detail.

When in the $M_A - F - M_B$ exchange path (Fig. 2) the involved angle, $\phi(M_A - F - M_B)$ is equal to 180° it usually gives rise to an AFM ordering, a situation found in the tetragonal K_2NiF_4 and K_2NiF_4 compounds belonging to the $I4/mmm$ space group as well as in the cubic perovskite $KNiF_3$ ³⁸. For this reason, the experimental FM arrangement displayed in the layer planes of both Cs_2AgF_4 and K_2CuF_4 compounds with a $Cmca$ crystal structure and $\phi(M_A - F - M_B) = 180^\circ$ is puzzling. Furthermore, there are also huge differences in the transition temperature, T_c . Indeed, K_2NiF_4 is AFM up to a temperature $T_c = 97.23$ K³⁸, while for K_2CuF_4 and Cs_2AgF_4 the FM order disappears at much lower temperatures, namely at $T_c = 6.5$ K⁷ and $T_c = 15$ K²⁸, respectively. This situation is, in principle, surprising as, in superexchange interactions, an increase of the covalency tends to enhance T_c as it happens on passing from $RbMnF_3$ ($T_c = 83$ K) to $KNiF_3$ (246 K)³⁸. However, the optical electronegativity¹⁹ of Ni^{2+} ($\chi = 2.2$) is smaller than that for Cu^{2+} ($\chi = 2.4$) or Ag^{2+} ($\chi = 2.8$)^{18,76} and then, in a simple view, one would expect a smaller covalency and T_c value for K_2NiF_4 than for compounds involving d^9 cations.

Compound	Phase	Data	R_z (Å)	$R_x = R_y$ (Å)	ΔE (meV)	J (meV)
K_2NiF_4	$I4/mmm$	Experimental	2.001	2.006	53.1	8.9
K_2CuF_4	$I4/mmm$	Calculated	1.906	2.061	4.4	2.2
Cs_2AgF_4	$I4/mmm$	Calculated	2.081	2.292	7.92	3.9

Table 4. Comparison of experimental data for the layered compound K_2NiF_4 ³⁸, where the Ni^{2+} spin is $S = 1$, with those calculated in this work for K_2CuF_4 and Cs_2AgF_4 in the parent $I4/mmm$ phase. The spin of d^9 ions is $S = \frac{1}{2}$. $\Delta E = E(FM) - E(AFM)$ per magnetic ion and depends on the exchange constant, J , and the spin of magnetic cation.

Seeking to clear these puzzling issues up we follow the procedure employed in section 3.2 thus exploring in a first step the behavior of K_2CuF_4 and Cs_2AgF_4 in the $I4/mmm$ parent phase. To achieve this goal, we have calculated the total energy per magnetic ion, $E(FM)$ and $E(AFM)$, corresponding, respectively, to the FM and AFM phases

associated to the same crystal structure and from them we derive the key quantity $\Delta E = E(\text{FM}) - E(\text{AFM})$. It should firstly be stressed that the equilibrium geometry obtained for both magnetic configurations is essentially the same as they involve differences in metal-ligand distances smaller than $5 \times 10^{-3} \text{ \AA}$. The obtained ΔE values for both K_2CuF_4 and Cs_2AgF_4 are displayed in Table 4 and lie in the range 1 – 10 meV and thus they are much smaller than $|E(\text{AFM})|$. For instance, for K_2CuF_4 $\Delta E/|E(\text{AFM})| \approx 5 \times 10^{-8}$, a fact that once more underlines the subtle origin of magnetic ordering.

The value $\Delta E = 53.1 \text{ meV}$ for K_2NiF_4 in Table 4 is derived from the experimental exchange constant, $J = 8.85 \text{ meV}$, associated with two coupled cations (Eq. (1)) using the expression

$$\Delta E = zJS_{\text{max}}(S_{\text{max}} + 1)/4 \quad (15)$$

Here, z means the number of neighbor cations, equal to 4 for a layered compound, while S_{max} is the maximum value of the total spin corresponding to two coupled cations with spin S , and thus equal to 2 for K_2NiF_4 .

The main source of ΔE in compounds like KNiF_3 or K_2NiF_4 has been explained by Anderson and Hay et al. just considering a simple M - F - M symmetric dimer^{77,79}. According to these models, ΔE is essentially related to *valence* electrons and involves the difference of two contributions

$$\Delta E = E_V(\text{FM}) - E_V(\text{AFM}) \quad (16)$$

where the $E_V(\text{FM})$ and $E_V(\text{AFM})$ contributions associated only with valence electrons are both negative and favor the FM and AFM configuration, respectively. These contributions typically lie in the range 1 - 100 meV. In the same vein the exchange constant, J , of two coupled cations (Eqs. (1) and (15)) can be expressed as the difference between two positive contributions

$$J = J(\text{AFM}) - J(\text{FM}) \quad (17)$$

According to the work by Anderson and Hay et al. on a symmetric dimer, the $J(\text{AFM})$ contribution greatly depends on the charge transferred from the cation to the ligand in orbitals containing *unpaired* electrons⁷⁷⁻⁷⁹. For clarifying this issue, we start considering a NiF_6^{4-} unit in the cubic KNiF_3 compound that involves two unpaired electrons in the $|\theta\rangle$ and $|\varepsilon\rangle$ antibonding molecular orbitals (Fig. 6), described by⁸²

$$\begin{aligned} |\theta\rangle &= N \{ |d(3z^2 - r^2)\rangle - (\mu/\sqrt{12})[2(|p_\sigma(5)\rangle + |p_\sigma(6)\rangle) - (|p_\sigma(1)\rangle + |p_\sigma(2)\rangle + |p_\sigma(3)\rangle + |p_\sigma(4)\rangle)] \} \\ |\varepsilon\rangle &= N \{ |d(x^2 - y^2)\rangle - (\mu/2)[|p_\sigma(1)\rangle - |p_\sigma(2)\rangle + |p_\sigma(3)\rangle - |p_\sigma(4)\rangle] \} \end{aligned} \quad (18)$$

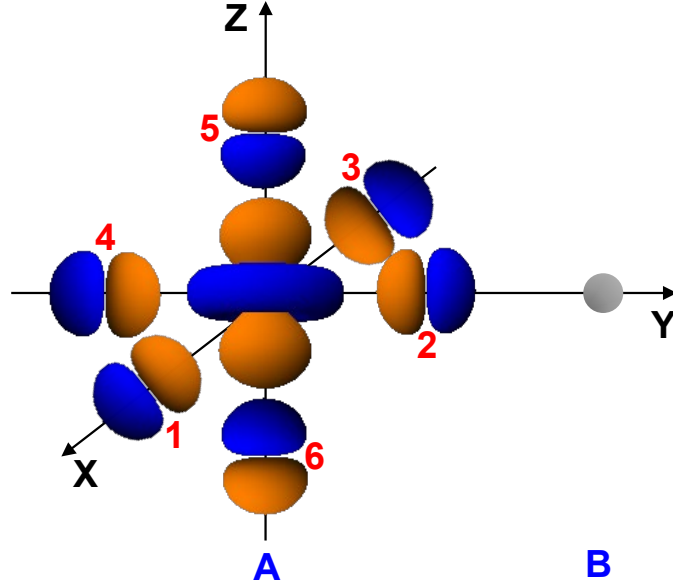


Figure 6. Picture of the antibonding $|\theta\rangle \sim 3z^2 - r^2$ molecular orbital for an octahedral NiF_6^{4-} unit in cubic KNiF_3 perovskite.

Due to the existence of covalency, the two non-filled orbitals of a simple NiF_6^{4-} unit have not pure $|d(3z^2 - r^2)\rangle$ or $|d(x^2 - y^2)\rangle$ characters thus involving a partial transfer of charge from metal to six ligands. If we consider the bridging ligand number 2 (Fig. 6), the charge transferred to it in σ -orbitals $|\theta\rangle$ and $|\varepsilon\rangle$ is equal to $(N\mu)^2/12$ and $(N\mu)^2/4$, respectively, thus implying a total charge, termed f_σ , equal to

$$f_\sigma(\text{NiF}_6^{4-}) = (N\mu)^2/3 \quad (19)$$

Due to cubic symmetry in KNiF_3 the same charge is transferred to any ligand of the NiF_6^{4-} unit. Obviously, if we consider a $M_A - F(2) - M_B$ dimer (Fig. 6), the charge transferred from M_A to the bridging ligand, $f_\sigma(A)$, is the same to that from M_B , $f_\sigma(B)$, provided the dimer is symmetric and then we can write $f_\sigma(A) = f_\sigma(B) = f_\sigma$. This symmetric situation happens in both KNiF_3 and K_2NiF_4 although in the last case only the four ligands³⁸ of a NiF_6^{4-} unit in the layer plane are involved in the superexchange.

A central issue in the work by Anderson and Hay et al. on a symmetric dimer is the dependence of the $J(\text{AFM})$ contribution on f_σ that, for the present purposes, can simply be written as⁷⁷⁻⁷⁹

$$J(\text{AFM}) \propto f_\sigma^2 \quad (20)$$

This fact agrees with the measured decrease³⁸ of J on passing from KNiF_3 (8.4 meV) to RbMnF_3 (0.57 meV) following the smaller covalency^{78, 82-85} in MnF_6^{4-} ($f_\sigma \sim 1\%$) than in NiF_6^{4-} ($f_\sigma \sim 4\%$), a result also consistent with the lower optical electronegativity of Mn^{2+} ($\chi \approx 1.4$)^{19,22,86,87} when compared¹⁹ to $\chi = 2.2$ for Ni^{2+} .

The NiF_6^{4-} complex in the tetragonal K_2NiF_4 compound is nearly octahedral (Table 4), with metal-ligand distances $R_x = R_y = 2.006 \text{ \AA}$ and $R_z = 2.001 \text{ \AA}$ which are very close to $R = 2.007 \text{ \AA}$ measured³⁸ in the cubic perovskite KNiF_3 . As the Ni^{2+} spin in the electronic ground state of K_2NiF_4 is also $S = 1$ the exchange constant J in K_2NiF_4 (8.9 meV) and KNiF_3 (8.7 meV) derived from experimental data are very near. Despite this fact, the transition temperature T_c is higher for KNiF_3 (246 K) than for the layered compound K_2NiF_4 (97.2 K) as a result of the different number of neighbor cations, z , in both compounds⁸⁸.

It is worth noting now that, if we move from K_2NiF_4 to K_2CuF_4 keeping the $I4/mmm$ structure, the number of unpaired electrons is reduced from 2 to 1. Furthermore, the unpaired electron in K_2CuF_4 is located in a $|3z^2 - r^2\rangle$ molecular orbital of a D_{4h} CuF_6^{4-} complex helped by the electrostatic potential, $V_R(\mathbf{r})$, due to the rest of lattice ions (Fig. 2). It should be noticed that in this orbital, coming from $|\theta\rangle$ in O_h symmetry, the dominant bonding is with the two axial ligands, while the charge transferred to the in-plane bridging ligands is smaller. More precisely, if, as a rough first step, we approximate $|3z^2 - r^2\rangle$ by $|\theta\rangle$ we obtain for the bridge ligand $f_\sigma(\text{CuF}_6^{4-}) = (N\mu)^2/12$, which is thus four times smaller than the value $f_\sigma = (N\mu)^2/3$ derived for (NiF_6^{4-}) (Eq. (19)), provided $N\mu$ is the same for both systems.

Seeking to clarify this central issue we have calculated the f_σ value for both the bridging and axial ligands of K_2CuF_4 and Cs_2AgF_4 in the $I4/mmm$ parent phase. Results are collected in Table 5 and compared to those for K_2NiF_4 . They confirm that f_σ is much higher for axial than for the in-plane bridging ligands of K_2CuF_4 and Cs_2AgF_4 thus stressing that covalency in the latter ligands is residual. At the same time, they show that AgF_6^{4-} is more covalent than CuF_6^{4-} in accord with the electronegativity scale. Despite these facts the f_σ values derived for bridging ligands in K_2CuF_4 (1.70%) and Cs_2AgF_4 (2.43%) are clearly smaller than $f_\sigma = 4.1\%$ calculated for K_2NiF_4 and KNiF_3 . Values of f_σ in the range 3.5% - 6% have been reported for NiF_6^{4-} by other authors^{78,82-85}. This relevant fact is thus consistent with the smaller J value derived for K_2CuF_4 and Cs_2AgF_4 when compared to that for K_2NiF_4 (Table 4). Now, if we take into account the different value of $S_{\max}(S_{\max} + 1)$ in both compounds, this explains why ΔE is one order of magnitude higher in the case of K_2NiF_4 .

Compound	Phase	$f_\sigma(\text{axial})$ (%)	$f_\sigma(\text{bridging})$ (%)	ΔE (meV)
K_2CuF_4	$I4/mmm$	7.98	1.70	4.4
Cs_2AgF_4	$I4/mmm$	11.28	2.43	7.92
K_2NiF_4	$I4/mmm$	4.1	4.1	53.1

Table 5. Calculated charge transferred to axial and equatorial ligands for the hole of MF_6^{4-} units ($M = \text{Cu}, \text{Ag}$) in K_2CuF_4 and Cs_2AgF_4 compounds in the $I4/mmm$ parent phase. Results are compared to those for K_2NiF_4 with two unpaired electrons. The ΔE values calculated for the three systems are also included for comparison.

A key question in the present analysis is to understand the influence of the $I4/mmm \rightarrow Cmca$ structural transition upon the magnetic ordering⁶ of K_2CuF_4 and Cs_2AgF_4 . In that process the MF_6^{4-} complexes ($M = Cu, Ag$) change from tetragonal to orthorhombic symmetry a distortion described by the Q coordinate.

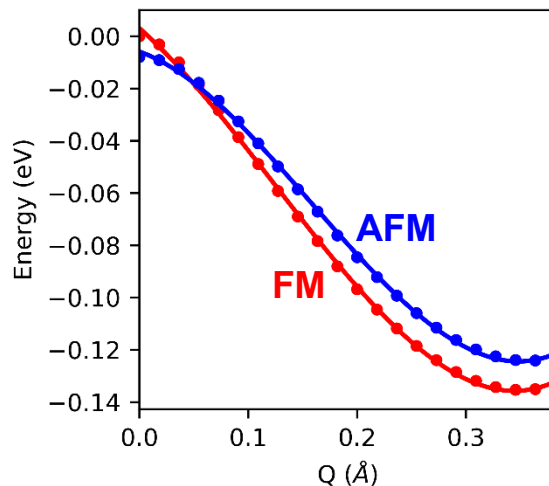


Figure 7. Energy (given per formula unit) of Cs_2AgF_4 obtained by single point calculations throughout the antiferrodistortive distortion from the parent tetragonal $I4/mmm$ phase to the minimum at the orthorhombic $Cmca$ one. These data are similar to those reported in Reference [6] although in that article the abscissa reflects the position of the bridge ligand and not the distortion coordinate, Q .

The variation of $\Delta E = E(FM) - E(AFM)$ calculated for Cs_2AgF_4 as a function of the Q distortion coordinate is displayed in Fig. 7. For simplicity, in that figure, $E(FM)$ is chosen to be equal to zero for $Q = 0$. As a salient feature, Fig. 7 shows that a small orthorhombic distortion induces a change of sign of ΔE and thus Cs_2AgF_4 becomes FM at the final equilibrium geometry ($Q = 0.34 \text{ \AA}$). A similar situation is found⁶ for K_2CuF_4 . Experimental and calculated ΔE and J values at the equilibrium structures of Cs_2AgF_4 and K_2CuF_4 are collected in Table 6.

Compound	Phase	$\Delta E(\text{exper})$	$J(\text{exper})$	$\Delta E(\text{calc})$	$J(\text{calc})$
Cs_2AgF_4	$Cmca$	-7.58	-3.79	-11.2	-5.6
K_2CuF_4	$Cmca$	-3.44	-1.72	-5.3	-2.7

Table 6. Experimental and calculated ΔE and J values (in meV) at the equilibrium structures of Cs_2AgF_4 and K_2CuF_4 described in Tables 1 and 2. Experimental data come from [28] for Cs_2AgF_4 and [7] for K_2CuF_4 .

It is worthwhile to remark that, on passing from $Q = 0$ to the equilibrium geometry in Fig. 7, there is an energy gain of around 140 meV per formula unit driven by the vibronic interaction of Eq. (8). When this quantity is compared to $\Delta E = 7.92$ meV at $Q = 0$ (Table 4) we then realize that the magnetism in Cs_2AgF_4 is just a consequence of vibronic coupling in the electronic ground state.

The switch to a FM arrangement induced by the orthorhombic distortion in Cs_2AgF_4 can be understood through the ideas by Anderson^{77,78} on a $M_A - F - M_B$ dimer which in that situation is no longer symmetric. If we consider the complex associated with the cation at A (Fig. 2), then the charge transferred to ligands placed at *local* x axis is expected to be higher than that corresponding to ligands placed along the local y axis that involve a higher metal-ligand distance as a result of the orthorhombic distortion. Accordingly, we can write

$$\begin{aligned} f_\sigma(A,x) &> f_\sigma(A,y) \\ f_\sigma(B,x) = f_\sigma(A,x) &> f_\sigma(B,y) = f_\sigma(A,y) \end{aligned} \quad (21)$$

A central issue in the analysis of a non-symmetric dimer is the dependence of the $J(\text{AFM})$ contribution upon the quantities $f_\sigma(A,x)$ and $f_\sigma(B,y)$ involved in the bridging ligand of Fig. 2. Following a similar procedure to that by Anderson in the symmetric dimer⁷⁷ it can easily be obtained⁶

$$J(\text{AFM}) \propto f_\sigma(A,x) f_\sigma(B,y) = f_\sigma(A,x) f_\sigma(A,y) \quad (22)$$

This result just means that, if bonding is significantly reduced in the longer $F - M_B$ bond, the exchange constant, J , could then be dominated by the FM contribution, $J(\text{FM})$, which is less sensitive to chemical bonding than $J(\text{AFM})$. Indeed the dependence of $J(\text{FM})$ on $f_\sigma(A,x)$ and $f_\sigma(A,y)$ has the form⁶ $p_x f_\sigma(A,x) + p_y f_\sigma(A,y)$ thus implying that $J(\text{FM})$ is not zero even if $f_\sigma(A,y) = 0$.

According to Eq. (22), it is therefore crucial to determine the charge transferred to the ligand in the short, $f_\sigma(A,x)$, and long, $f_\sigma(A,y)$, bonds in the equilibrium geometry of both Cs_2AgF_4 and K_2CuF_4 compounds. Henceforth, these charges are simply denoted as $f_\sigma(x)$ and $f_\sigma(y)$.

Results of present calculations on this central issue are portrayed in Table 7. As a salient feature the obtained value of $f_\sigma(y)$ is equal to zero at the $Cmca$ equilibrium geometry of both Cs_2AgF_4 and K_2CuF_4 compounds, a fact that strongly suggests that the AFM contribution, $J(\text{AFM})$, disappears. In other words, this key fact means that the orthorhombic distortion unveils the $J(\text{FM})$ contribution to J that is somewhat hidden in the $I4/mmm$ parent phase. According to this view and the calculated values in Tables 4 and 5, we can estimate $J(\text{AFM}) \approx 9.6$ meV and $J(\text{FM}) \approx 5.6$ meV for the $I4/mmm$ parent phase of Cs_2AgF_4 , while $J(\text{AFM}) \approx 4.9$ meV and $J(\text{FM}) \approx 2.7$ meV would correspond to K_2CuF_4 .

It is worthwhile to remark that the present results are underpinned by EPR data carried out on $\text{CuCl}_4\text{X}_2^{2-}$ centers ($\text{X} = \text{NH}_3, \text{H}_2\text{O}$) formed in $\text{NH}_4\text{Cl}:\text{Cu}^{2+}$ crystals grown in solutions with different pH^{89,90,75}. While the equilibrium geometry of $\text{CuCl}_4(\text{NH}_3)_2^{2-}$ is tetragonal with four equivalent Cl^- ions, lying in a plane perpendicular to the main axis, in $\text{CuCl}_4(\text{H}_2\text{O})_2^{2-}$ there is an orthorhombic distortion in the plane formed by chlorine ions^{70,75}. Interestingly, no superhyperfine interaction of the unpaired electron with the two far chlorine nuclei of the $\text{CuCl}_4(\text{H}_2\text{O})_2^{2-}$ center have been observed by EPR⁷⁵, thus proving that $f_\sigma(y) = 0$. Moreover, from EPR data the calculated charge transferred to one of close Cl nuclei in $\text{CuCl}_4(\text{H}_2\text{O})_2^{2-}$ ($f_\sigma(x) = 8.7\%$) is about twice that found for the tetragonal $\text{CuCl}_4(\text{NH}_3)_2^{2-}$ species as it is also shown on Table 7.

System	Complex	Symmetry	R_x	R_y	$f_\sigma(x)$ (%)	$f_\sigma(y)$ (%)
K_2CuF_4	CuF_6^{4-}	Tetragonal	2.061	2.061	1.70	1.70
		Orthorhombic	1.941	2.234	4.86	0
Cs_2AgF_4	AgF_6^{4-}	Tetragonal	2.292	2.292	2.43	2.43
		Orthorhombic	2.106	2.458	6.82	0
$\text{NH}_4\text{Cl}:\text{Cu}^{2+}$ (pH=7)	$\text{CuCl}_4(\text{NH}_3)_2^{2-}$	Tetragonal	2.78	2.78	4.70	4.70
$\text{NH}_4\text{Cl}:\text{Cu}^{2+}$ (pH=3)	$\text{CuCl}_4(\text{H}_2\text{O})_2^{2-}$	Orthorhombic	2.52	2.97	8.7	0

Table 7. Charge transferred to ligands in the layer plane for the Cmca equilibrium geometry of K_2CuF_4 and Cs_2AgF_4 . In this table $f_\sigma(x) \equiv f_\sigma(\text{A},x)$ and $f_\sigma(y) \equiv f_\sigma(\text{A},y)$ correspond to close and far ligands of a given complex lying along x and y directions, respectively. For the sake of completeness, the value $f_\sigma(x) = f_\sigma(y)$ associated with the tetragonal parent phase is also collected. The results are compared to those derived from EPR experiments on $\text{CuCl}_4(\text{NH}_3)_2^{2-}$ and $\text{CuCl}_4(\text{H}_2\text{O})_2^{2-}$ centers formed in $\text{NH}_4\text{Cl}:\text{Cu}^{2+}$ crystals grown in solution with different pH. While the equilibrium geometry of $\text{CuCl}_4(\text{NH}_3)_2^{2-}$ is tetragonal with the four Cl^- ions, lying in a plane perpendicular to the main axis, at the same distance from Cu^{2+} in $\text{CuCl}_4(\text{H}_2\text{O})_2^{2-}$ there is an orthorhombic distortion in the plane formed by chlorine ions. The values of R_x and R_y distances (in Å) for these centers are taken from [70].

The present results thus prove that the FM displayed in the layer planes of Cs_2AgF_4 and K_2CuF_4 is strongly dependent on the orthorhombic distortion⁶. As discussed in section 3.2 that distortion is fostered by the allowed vibronic coupling of the ${}^2\text{A}_{1g}$ ground state of a tetragonal MF_6^{4-} complex ($\text{M} = \text{Cu}, \text{Ag}$) with the excited ${}^2\text{B}_{1g}$ state through the local b_{1g} distortion mode.

It is worth noting now that a similar situation cannot take place for K_2NiF_4 where the ground state of the tetragonal NiF_6^{4-} complex is ${}^3\text{B}_{1g}$ simply described⁸² by the Slater determinant $|x^2 - y^2 \uparrow 3z^2 - r^2 \uparrow|$. Indeed, the ${}^1\text{A}_{1g}$ excited state $|3z^2 - r^2 \uparrow 3z^2 - r^2 \downarrow|$ cannot vibronically be coupled to the ${}^3\text{B}_{1g}$ ground state as the spin in both states is different, a

matter already discussed in section 3.2. Furthermore, a ${}^3B_{1g}$ ground state can only vibronically be coupled to ${}^3A_{1g}$ excited states if a b_{1g} distortion mode is involved. However, within the 45 states emerging from the d^8 configuration there are no ${}^3A_{1g}$ states in a local D_{4h} symmetry⁸². This simple reasoning thus sheds some light on the lack of orthorhombic distortion in K_2NiF_4 and thus its AFM behavior. Along this line the ground state of the MnF_6^{4-} complex in the $I4/mmm$ K_2MnF_4 crystal has a spin $S = 5/2$. Accordingly, it cannot be coupled vibronically to any of the rest of 246 states coming from the d^5 configuration⁸² which have at most $S = 3/2$. This relevant fact also helps to avoid the orthorhombic instability in K_2MnF_4 . According to this reason, the local $O_h \rightarrow T_d$ symmetry change observed⁹¹ for $BaF_2:Mn^{2+}$ involves the coupling of the electronic ground state ($S = 5/2$) with a charge transfer state of the same spin⁹².

3.6. Insight into Rb_2AgF_4

The Rb_2AgF_4 compound was also firstly synthesized by Odenthal et al²⁵ in 1974 and subsequently explored by Friebel and Reinen⁴³ through EPR and optical spectroscopy. Despite the structure of Rb_2AgF_4 was not determined, the closeness of their experimental EPR and optical data to those reported for Cs_2AgF_4 already suggested that both compounds could display the same crystal structure. In 2016, Kurzydłowski et al. carried out DFT+U calculations on the Rb_2AgF_4 compound⁹³. Although these authors find that the stable phase of Rb_2AgF_4 is described by the $Cmca$ space group, they do not report the values of lattice parameters nor $Ag^{2+}-F^-$ distances.

		a	b	c	β	R_z	R_x	R_y	E_r
Cmca	FM	13.509	6.373	6.372	90	2.109	2.076	2.430	0
	AFM	13.502	6.379	6.379	90	2.109	2.074	2.437	+12
I4/mmm	FM	4.521	4.521	13.360	90	2.066	2.261	2.261	+150
	AFM	4.522	4.522	13.350	90	2.063	2.261	2.261	+133
P2 ₁ /c	FM	3.885	10.627	6.713	91.0	2.076	2.092	2.909	+130
	AFM	3.885	10.628	6.714	91.0	2.076	2.092	2.910	+130

Table 8. Calculated lattice parameters (axes a, b, c, in Å, and monoclinic angle β , in degrees) and metal-ligand distances (axial R_z , and equatorials R_x , R_y , all in Å) for Rb_2AgF_4 in three different structures (orthorhombic $Cmca$, tetragonal $I4/mmm$ and monoclinic $P2_1/c$) and two magnetic orders (FM, AFM). E_r is the difference in energy (in meV/formula) with respect to the phase with minimum energy (FM $Cmca$). Note the different notation of the long axis in each structure.

For this reason, we have carried out DFT calculations, with the PW1PW hybrid functional, seeking to optimize the geometry of Rb_2AgF_4 in three possible layered phases namely $Cmca$, $I4/mmm$ and $P2_1/c$. The $P2_1/c$ structure is included as it seems to be

involved⁹² in K_2AgF_4 and Na_2AgF_4 . Of course, for each kind of structure we have also explored both the FM and AFM arrangements of magnetic moments arising from silver ions. Results are gathered in Table 8 where the relative energy, E_r , of six considered phases is reported and $E_r=0$ corresponds to the $Cmca$ structure with FM ordering.

The calculated E_r values in Table 8 mean that the stable phase in Rb_2AgF_4 corresponds to a $Cmca$ structure with FM ordering such as it is experimentally found for Cs_2AgF_4 . Moreover, if we consider for Rb_2AgF_4 an AFM ordering keeping the $Cmca$ structure the changes of $Ag^{2+}-F^-$ distances are smaller than 0.01 Å and $E_r = 12$ meV. In this case E_r is equal to the quantity $-\Delta E$ used in section 3.5. Thus, the value $E_r = -\Delta E = 12$ meV found for Rb_2AgF_4 is similar to that for Cs_2AgF_4 reflected in the results of Table 6 and Figure 7 of section 3.5. Along this line the values of $Ag^{2+}-F^-$ distances calculated for Rb_2AgF_4 in the stable phase (Table 8) are certainly close to $R_z = 2.112$ Å, $R_x = 2.111$ Å and $R_y = 2.441$ Å obtained for Cs_2AgF_4 (Table 1). This result is thus consistent with the practically identical d-d transitions⁴³ and EPR spectra^{26,43} measured experimentally for both Rb_2AgF_4 and Cs_2AgF_4 . For instance, the accurate EPR measurements carried out by Kurzydowski et al. give²⁶ $g(\mathbf{a}) = 2.076$ and $g(\perp\mathbf{a}) = 2.26$ for Rb_2AgF_4 and $g(\mathbf{a}) = 2.077$ and $g(\perp\mathbf{a}) = 2.257$ for Cs_2AgF_4 .

Concerning the $I4/mmm$ parent phase with AFM ordering the present results on Rb_2AgF_4 yield $E_r = 133$ meV a quantity nearly identical to that derived for Cs_2AgF_4 such as it is shown in Figure 7 (section 3.5). According to the results of Table 8 such parent phase should be instable. We have verified that in that situation, there are two modes, b_{1g} and a_{2g} , with the same imaginary frequency $401i$ cm^{-1} , which correspond to similar orthorhombic distortions of the F ligands within a plane but for the $z = 0$ and $z = 1/2$ layers, respectively.

As regards a possible monoclinic $P2_1/c$ structure, the results of Table 8 imply an energy per magnetic ion which is again 130 meV above that for the stable phase of Rb_2AgF_4 .

4. Final Remarks

The present results stress the importance of exploring the $I4/mmm$ parent phase of K_2CuF_4 and Cs_2AgF_4 for understanding the origin of their magnetic properties very distinct from those exhibited by other layered fluorides like K_2NiF_4 or K_2MnF_4 . At the same time, they prove that the ferromagnetism observed for both K_2CuF_4 and Cs_2AgF_4 compounds greatly depends on the orthorhombic distortion⁹⁴. As explained in sections 3.2 and 3.5 that instability is driven by the *allowed* vibronic admixture of the $^2A_{1g}$ ground state of a tetragonal MF_6^{4-} complex ($M = Cu, Ag$) with the excited $^2B_{1g}$ state. On the contrary, the lack of excited states which, within the d^5 configuration, can be vibronically coupled with the ground state hamper the orthorhombic distortion in K_2MnF_4 . This situation is thus similar to that taking place in $SrCl_2$ where the d^9 impurities Ni^+ , Cu^{2+} and Ag^{2+} all move off-centre^{21,22,95} while a Mn^{2+} impurity remains⁹⁶ at the Sr^{2+} site. Nevertheless, for d^9 impurities this situation changes when we replace $SrCl_2$ by CaF_2

where only Ni^{2+} moves off-center while Ag^{2+} and Cu^{2+} remain at the Ca^{2+} site²². The substitution of chlorine by fluorine, the increase of the nominal charge of the cation and the reduction of interatomic distances all tend to increase the value of the K_0 contribution in Eq. (9) and thus they help to suppress the off-center instability.

These ideas also shed light on the occurrence of ferroelectricity in BaTiO_3 but not in CaTiO_3 involving smaller interatomic distances. Indeed, an *isolated* Ti^{4+} cannot move spontaneously off-center in these perovskites but at equilibrium K_0 is higher for CaTiO_3 than for BaTiO_3 following the smaller interatomic distances. As ferroelectricity requires the *simultaneous* off-center motion of all Ti^{4+} ions this explains⁹⁷, albeit qualitatively, why BaTiO_3 is better suited than CaTiO_3 .

In the case of Cu^{2+} complexes the existence of close excited states that can vibronically be mixed with the ground state favors changes of the electronic density and the associated distortion provided $K < 0$. This characteristic of Cu^{2+} complexes not shared by high spin Mn^{2+} or Ni^{2+} ones is sometimes referred to as plasticity⁹⁸.

From the present analysis an understanding of optical and magnetic properties of layered compounds with d^9 ions requires to explore the influence of the electrostatic potential, $V_R(\mathbf{r})$, in the parent phase and the possible instabilities driven by a force constant that becomes negative. By contrast, the attempts to explain such properties assuming a JT effect in tetragonal, orthorhombic or monoclinic lattices are meaningless. An exception to this behavior is the widely studied AgF_2 ⁹⁹ whose parent phase is cubic. In this case the AgF_6^{4-} units are trigonally distorted and thus under this symmetry the ground state is strictly degenerate making possible the existence of a JT effect as it has recently been discussed⁵⁰.

Further work on silver fluorides like K_2AgF_4 ¹⁰⁰ or Na_2AgF_4 is now underway.

5. Acknowledgments

We acknowledge financial support from Grant No. PGC2018-096955-B-C41 funded by MCIN/AEI/10.13039/501100011033. I. S.-M. (grant BDNS:589170) and G. S.-F. acknowledge financial support from Universidad de Cantabria and Gobierno de Cantabria.

6. References

- (1) Correa-Baena, J. P.; Saliba, M.; Buonassisi, T.; Grätzel, M.; Abate, A.; Tress, W.; Hagfeldt, A. Promises and challenges of perovskite solar cells. *Science* **2017**, *358* (6364), 739–744.
- (2) Akkerman, Q. A.; Manna, L. What defines a halide perovskite? *ACS Energy Lett.* **2020**, *5* (2), 604–610.

- (3) Jaffe, A.; Lin, Y.; Mao, W. L.; Karunadasa, H. I. Pressure-induced conductivity and yellow-to-black piezochromism in a layered Cu–Cl hybrid perovskite. *J. Am. Chem. Soc.* **2015**, *137* (4), 1673–1678.
- (4) Gupta, S.; Pandey, T.; Singh, A. K. Suppression of Jahn–Teller distortions and origin of piezochromism and thermochromism in Cu–Cl hybrid perovskite. *Inorg. Chem.* **2016**, *55* (13), 6817–6824
- (5) Carrasco-Busturia, D.; Sánchez-Movellán, I.; Tygesen, A. S.; Bhowmik, A.; García-Lastra, J. M.; Aramburu, J. A.; Moreno, M. Red shift in optical excitations on layered copper perovskites under pressure: role of the orthorhombic instability. *Chem. Eur. J.* **2022**, *29* (5) e202202933 (1 of 11)
- (6) Sánchez-Movellán, I.; Moreno, M.; Aramburu, J. A.; García-Fernández, P. Strain-induced ferromagnetic to antiferromagnetic crossover in d⁹-ion (Cu²⁺ and Ag²⁺)-layered perovskites. *J. Phys. Chem. C* **2023**, *127* (17), 8332–8341.
- (7) Yamada, I. Magnetic Properties of K₂CuF₄: A transparent two-dimensional ferromagnet. *J. Phys. Soc. Jpn.* **1972**, *33* (4), 979–988.
- (8) Hidaka, M.; Inoue, K.; Yamada, I.; Walker, P. J. X-ray diffraction study of the crystal structures of K₂CuF₄ and K₂Cu_xZn_{1-x}F₄. *Physica B+C* **1983**, *121* (3), 343–350.
- (9) Ishizuka, M.; Terai, M.; Hidaka, M.; Endo, S.; Yamada, I.; Shimomura, O. Pressure-induced structural phase transition in the two-dimensional Heisenberg ferromagnet K₂CuF₄. *Phys. Rev. B: Condens. Matter Mater. Phys.* **1998**, *57* (1), 64–67.
- (10) Riley, M. J.; Dubicki, L.; Moran, G.; Krausz, E. R.; Yamada, I. Optical spectrum of K₂CuF₄. *Inorg. Chem.* **1990**, *29* (9), 1614–1626.
- (11) García-Fernández, P.; Moreno, M.; Aramburu, J. A. Electrostatic control of orbital ordering in noncubic crystals. *J. Phys. Chem. C* **2014**, *118* (14), 7554–7561.
- (12) Aramburu, J. A.; García-Fernández, P.; Mathiesen, N. R.; García-Lastra, J. M.; Moreno, M. Changing the usual interpretation of the structure and ground state of Cu²⁺-layered perovskites. *J. Phys. Chem. C* **2018**, *122* (9), 5071–5082.
- (13) Steadman, J. P.; Willett, R. D. The crystal structure of (C₂H₅NH₃)₂CuCl₄. *Inorg. Chim. Acta* **1970**, *4*, 367–371.
- (14) Ohwada, K.; Ishii, K.; Inami, T.; Murakami, Y.; Shobu, T.; Ohsumi, H.; Ikeda, N.; Ohishi, Y. Structural properties and phase transition of holt-orbital-ordered (C₂H₅NH₃)₂CuCl₄ studied by resonant and non-resonant x-ray scatterings under high pressure. *Phys. Rev. B* **2005**, *72* (1), 014123.
- (15) Lim, A. R.; Kwac, L. K. Advances in physicochemical characterization of lead-free hybrid perovskite [NH₃(CH₂)₃NH₃]CuBr₄ crystals. *Sci. Rep.* **2022**, *12* (1), 8769.

- (16) Choi, M. Y.; Lee, S. J.; Ju, H.; Lim, A. R. Phase transition, thermal stability, and molecular dynamics of organic–inorganic hybrid perovskite $[\text{NH}_3(\text{CH}_2)_6\text{NH}_3]\text{CuCl}_4$ crystals. *RSC Adv.* **2022**, *12* (32), 20679–20685.
- (17) Grochala, W. Silverland: the realm of compounds of divalent silver – and why they are interesting. *J. Supercond. Novel Magn.* **2018**, *31* (3), 737–752.
- (18) Aramburu, J. A.; Moreno, M. The anomalous quasi isotropic (g) tensor found for $\text{CdBr}_2:\text{Ag}^{2+}$ and $\text{AgBr}_{0.15}\text{Cl}_{0.85}:\text{Ag}^{2+}$: An explanation through strong covalency. *Solid State Commun.* **1987**, *62* (7), 513–516.
- (19) Jørgensen, C. K. Electron transfer spectra. In *Prog. Inorg. Chem.*; S. J. Lippard, Eds.; John Wiley & Sons, Inc.: New York, 1970; pp 101–158.
- (20) Sierro, J. Paramagnetic resonance of the Ag^{2+} ion in irradiated alkali chlorides. *J. Phys. Chem. Solids* **1967**, *28* (3), 417–422.
- (21) Bill, H. Observation of the Jahn-Teller Effect with Electron Paramagnetic Resonance in *The Dynamical Jahn-Teller Effect in Localized Systems*; Perlin, Y. E., Wagner, M., Eds.; Elsevier: Amsterdam, 1984; pp 754.
- (22) Moreno, M.; Barriuso, M. T.; Aramburu, J. A.; García-Fernández, P.; García-Lastra, J. M. Microscopic insight into properties and electronic instabilities of impurities in cubic and lower symmetry insulators: the influence of pressure. *J. Phys.: Condens. Matter* **2006**, *18*, R315–R360.
- (23) Miyanaga, T. EPR studies of strong Jahn-Teller coupling systems $\text{CdCl}_2:\text{Ag}^{2+}$ and $\text{CdBr}_2:\text{Ag}^{2+}$. *J. Phys. Soc. Jpn.* **1979**, *46* (1), 167–175.
- (24) Yamaga, M.; Hayahsi, Y.; Yoshioka, H. Jahn-Teller Effect in the ESR spectrum of $(\text{AgBr}_6)^{4-}$ in Mixed Crystals $\text{AgBr}_{1-x}\text{Cl}_x$. *J. Phys. Soc. Jpn.* **1979**, *47*, 677–678.
- (25) Odenthal, R.-H.; Paus, D.; Hoppe, R. Zur magnetochemie des zweiwertigen silbers neue fluoroargentate(II): Cs_2AgF_4 , Rb_2AgF_4 , und K_2AgF_4 . *Z. anorg. allg. Chem.* **1974**, *407* (2), 144–150.
- (26) Kurzydłowski, D.; Jaroń, T.; Ozarowski, A.; Hill, S.; Jagličić, Z.; Filinchuk, Y.; Mazej, Z.; Grochala, W. Local and cooperative Jahn–Teller Effect and resultant magnetic properties of M_2AgF_4 (M = Na–Cs). *Inorg. Chem.* **2016**, *55* (21), 11479–11489.
- (27) Gawraczynski, J.; Wolanski, Ł.; Grzelak, A.; Mazej, Z.; Struzhkin, V.; Grochala, W. Phase transitions and amorphization of M_2AgF_4 (M = Na, K, Rb) compounds at high pressure. *Crystals* **2022**, *12* (4), 458 (11 pages).
- (28) McLain, S. E.; Dolgos, M. R.; Tennant, D. A.; Turner, J. F. C.; Barnes, T.; Proffen, T.; Sales, B. C.; Bewley, R. I. Magnetic behavior of layered Ag(II) fluorides. *Nat. Mater.* **2006**, *5* (7), 561–565.

- (29) Dai, D.; Whangbo, M. H.; Kohler, J.; Hoch, C.; Villesuzanne, A. Electronic structure analysis of the difference between Cs₂AgF₄ and Rb₂MnF₄ in their magnetic properties and single-crystal structure determination of Rb₂MnF₄. *Chem. Mater.* **2006**, *18* (14), 3281–3286.
- (30) Lancaster, T.; Blundell, S. J.; Baker, P. J.; Hayes, W.; Giblin, S. R.; McLain, S. E.; Pratt, F. L.; Salman, Z.; Jacobs, E. A.; Turner, J. F. C. et al. Intrinsic magnetic order in Cs₂AgF₄ detected by muon-spin relaxation. *Phys. Rev. B* **2007**, *75* (2), 220408.
- (31) Tong, J.; Kremer, R. K.; Köhler, J.; Simon, A.; Lee, Ch.; Kan, E.; Whangbo, M.-H. The layered ferromagnet Cs₂AgF₄: antiferromagnetic inter-layer coupling driven by magnetic dipole-dipole interactions. *Z. Kristallogr.* **2010**, *225* (11), 498–503.
- (32) Lee, C.; Shim, J. H.; Whangbo, M. H. Cause for the orbital ordering of Cs₂AgF₄ and its effect on thermoelectric properties. *Inorg. Chem.* **2018**, *57* (19), 11895–11900.
- (33) Hao, X.; Xu, Y.; Wu, Z.; Zhou, D.; Liu, X.; Meng, J. Orbital ordering in Cs₂AgF₄ from first principles. *Phys. Rev. B* **2007**, *76*, 054426 (1-6).
- (34) Kan, E.; Yuan, L.-F.; Yang, J.; Hou, J. G. First-principles calculations of the electronic and magnetic properties of Cs₂AgF₄. *Phys. Rev. B* **2007**, *76*, 024417 (1-5).
- (35) Wu, H.; Khomskii, D. I. Orbital ordering in the ferromagnetic insulator Cs₂AgF₄ from first principles. *Phys. Rev. B* **2007**, *76*, 155115 (1-4).
- (36) Kasinathan, D.; Koepernik, K.; Nitzsche, U.; Rosner, H. Ferromagnetism induced by orbital order in the charge-transfer insulator Cs₂AgF₄: an electronic structure study. *Phys. Rev. Lett.* **2007**, *99*, 247210 (1-4).
- (37) de Jongh, L. J.; Miedema, A. R. Experiments on simple magnetic model systems. *Advances in Physics* **1974**, *23* (1), 1-260.
- (38) de Jongh, L. J.; Block, R. On the exchange interactions in some 3d-Metal ionic compounds. *Physica B+C* **1975**, *79* (6), 568–593.
- (39) Aramburu, J. A.; Bhowmik, A.; García-Lastra, J. M.; García-Fernández, P.; Moreno, M. Insight into compounds with Cu(H₂O)₆²⁺ units: new ideas for understanding Cu²⁺ in Tutton salts. *J. Phys. Chem. C* **2019**, *123* (5), 3088–3101.
- (40) Aramburu, J. A.; García-Fernández, P.; García-Lastra, J. M.; Barriuso, M. T.; Moreno, M. Colour due to Cr³⁺ ions in oxides: a study of the model system MgO:Cr³⁺. *J. Phys.: Condens. Matter* **2013**, *25* (17), 175501.
- (41) García-Lastra, J. M.; Aramburu, J. A.; Barriuso, M. T.; Moreno, M. Impurities in non-cubic crystals: stabilization mechanisms for Jahn-Teller ions in layered perovskites. *Phys. Rev. Lett.* **2004**, *93* (22), 226402.

- (42) Aramburu, J. A.; García-Lastra, J. M.; García-Fernández, P.; Barriuso, M. T.; Moreno, M. Cu²⁺ in layered compounds: origin of the compressed geometry in the model system K₂ZnF₄:Cu²⁺. *Inorg. Chem.* **2013**, *52* (12), 6923–6933.
- (43) Friebel, C.; Reinen, D. Ligandenfeld- und ESR-spektroskopische untersuchungen zum Jahn-Teller-effekt des Ag²⁺-Ions in fluoridischer koordination. *Z. anorg. allg. Chem.* **1976**, *413* (1), 51-60.
- (44) Tong, J.; Köhler, J.; Simon, A.; Lee, Ch.; Whangbo, M-H. Optical properties of the orchid colored silver(II) fluoride Cs₂AgF₄. *Z. Anorg. Allg. Chem.* **2012**, *638* (11), 1792–1795.
- (45) Kohn, W.; Sham, L. J. Self-consistent equations including exchange and correlation effects. *Phys. Rev.* **1965**, *140* (4A), A1133-A1138.
- (46) Dovesi, R.; Saunders, V. R.; Roetti, C.; Orlando, R.; Zicovich-Wilson, C. M. CRYSTAL17 user's manual; University of Torino, Torino, **2017**.
- (47) Crystal web site. <https://www.crystal.unito.it> (accessed 2023-02-15).
- (48) Aramburu, J. A.; Moreno, M. Understanding the structure and ground state of the prototype CuF₂ compound not due to the Jahn–Teller effect. *Inorg. Chem.* **2019**, *58* (7), 4609–4618.
- (49) Aramburu, J. A.; Moreno, M. Explaining the optical spectrum of CrF₂ and CuF₂ model materials: role of the tetragonal to monoclinic instability. *Phys. Chem. Chem. Phys.* **2019**, *21* (22), 11714–11723.
- (50) Sánchez-Movellán, I.; Moreno-Ceballos, J.; García-Fernández, P.; Aramburu, J. A.; Moreno, M. New ideas for understanding the structure and magnetism in AgF₂: Prediction of ferroelasticity. *Chem.–Eur. J.* **2021**, *27* (54), 13582–13590.
- (51) Peintinger, M. F.; Oliveira, D. F.; Bredow, T. J. Consistent Gaussian basis sets of triple-zeta valence with polarization quality for solid-state calculations. *Jour. Comput. Chem.* **2013**, *34* (6), 451-459.
- (52) Crystal basis sets. <https://www.crystal.unito.it/basis-sets.php> (accessed 2023-03-04).
- (53) Bredow, T; Gerson, A. R. Effect of exchange and correlation on bulk properties of MgO, NiO, and CoO. *Phys. Rev. B* **2000**, *61* (5194), 5194–5201.
- (54) te Velde, G; Bickelhaupt, F. M.; Baerends, E. J.; Guerra, C. F.; van Gisbergen, S. J. A. Chemistry with ADF. *J. Comput. Chem.* **2001**, *22* (9), 931–967.
- (55) Moreno, M; Aramburu, J. A.; Barriuso, M. T. Electronic properties and bonding in transition metal complexes: influence of pressure. In *Optical spectra and chemical*

bonding in inorganic compounds. Structure and bonding; Mingos, D. M. P.; Schönherr, T., Eds.; Springer: Berlin, Heidelberg, 2004; pp 127-152.

(56) Colaneri, M. J.; Vitali, J. Effect of the lattice field on the electronic structure and dynamics of copper–hexahydrate in Tutton salts. *J. Phys. Chem. A* **2021**, *125* (16), 3268–3278.

(57) Van Gool, W.; Piken, A. G. Lattice self-potentials and Madelung constants for some compounds. *J. Mater. Sci.* **1969**, *4* (2), 95–104.

(58) Tosi, M. P. Cohesion of ionic solids in the Born model. *Solid State Phys.* **1964**, *16*, 1–120.

(59) Owen, J.; Harris E.A. Pair spectra and exchange interactions. In *Electron Paramagnetic Resonance*; Geschwind, S., Ed.; Plenum: New York, 1972.

(60) Ham, F. S. Jahn-Teller effects in EPR spectra. In *Electron Paramagnetic Resonance*; Geschwind, S., Ed.; Plenum: New York, 1972 pp 1-119.

(61) García-Fernández, P.; Trueba, A.; Barriuso, M. T.; Aramburu, J. A.; Moreno, M. Tunneling splitting of Jahn-Teller ions in oxides. *Phys. Rev. Lett.* **2010**, *104* (3), 035901.

(62) García-Fernández, P.; Trueba, A.; Barriuso, M. T.; Aramburu, J. A.; Moreno, M. Dynamic and static Jahn-Teller effect in impurities: determination of the tunneling splitting. *Prog. Theor. Chem. Phys.* **2011**, *23*, 105–142.

(63) Minner, E.; Lovy, D.; Bill, H. Electron-Paramagnetic-Resonance and relaxation study of copper(II) and silver(II) In CsCdF₃ single-crystals. *J. Chem. Phys.* **1993**, *99* (9), 6378–6383.

(64) García-Fernández, P.; Barriuso, M. T.; Garcia-Lastra, J. M.; Moreno, M.; Aramburu, J. A. Compounds containing tetragonal Cu²⁺ complexes: is the d_{x²-y²}-d_{3z²-r²} gap a direct reflection of the distortion? *J. Phys. Chem. Lett.* **2013**, *4* (14), 2385–2390.

(65) Low, W.; Suss, J. T. Jahn-Teller effect of Ni⁺ and Cu²⁺ in single crystals of calcium oxide. *Phys. Lett.* **1963**, *7* (5), 310–312.

(66) Aramburu, J. A.; García-Fernández, P.; García-Lastra, J. M.; Moreno, M. A genuine Jahn-Teller system with compressed geometry and quantum effects originating from zero-point motion. *Chem. Phys. Chem.* **2016**, *17* (14), 2146–2156.

(67) Sánchez-Movellán, I.; Aramburu, J. A.; Moreno, M. Local structure and excitations in systems with CuF₆⁴⁻ units: lack of Jahn–Teller effect in the low symmetry compound Na₂CuF₄. *Phys. Chem. Chem. Phys.* **2020**, *22* (15), 7875–7887.

(68) Reinen, D. The modulation of Jahn–Teller coupling by elastic and binding strain perturbations: a novel view on an old phenomenon and examples from solid-state chemistry. *Inorg. Chem.* **2012**, *51* (8), 4458–4472.

- (69) Bersuker, I. B.; Gorinchoi, N. N.; Polinger, V. Z. On the origin of dynamic instability of molecular systems. *Theor. Chim. Acta* **1984**, *66* (3), 161–172.
- (70) García-Fernández, P.; García-Lastra, J. M.; Trueba, A.; Barriuso, M. T.; Aramburu, J. A.; Moreno, M. Insulators containing $\text{CuCl}_4\text{X}_2^{2-}$ ($\text{X} = \text{H}_2\text{O}, \text{NH}_3$) units: origin of the orthorhombic distortion observed only for $\text{CuCl}_4(\text{H}_2\text{O})_2^{2-}$. *Phys. Rev. B: Condens. Matter Mater. Phys.* **2012**, *85*, 094110.
- (71) Borcherts, R. H.; Kanzaki, H.; Abe, H. EPR spectrum of a Jahn-Teller system, $\text{NaCl}:\text{Cu}^{2+}$. *Phys. Rev. B* **1970**, *2* (1), 23–27.
- (72) Valiente, R.; Lezama, L. M.; Rodríguez, F.; Moreno, M. Study of bidimensional $(\text{CH}_3\text{NH}_3)_2\text{CdCl}_4:\text{Cu}^{2+}$ and $(\text{CH}_3\text{NH}_3)_2\text{CuCl}_4$. *Mater. Sci. Forum* **1997**, *239* (241), 729–732.
- (73) Riley, M.J.; Hitchman, M.A.; Reinen, D. Effects of vibronic coupling on the EPR spectra of copper(II) doped K_2ZnF_4 . *Chemical Physics* **1986**, *102* (1), 11–28.
- (74) Abragam, A.; Bleaney, B. *Electron paramagnetic resonance of transition ions*; Clarendon Press: Oxford, 1970; pp. 461.
- (75) Boettcher, F.; Spaeth, J. M. ENDOR investigation of Cu^{2+} centres in NH_4Cl . *Phys. Status Solidi B* **1974**, *61*, 465–473.
- (76) Valiente, R.; Aramburu J. A.; Barriuso, M. T.; Moreno, M. Electronic structure of Ag^{2+} impurities in halide lattices. *J. Phys.: Condens. Matter* **1994**, *6*, 4515–4525.
- (77) Anderson, P. W. Theory of magnetic exchange interactions: exchange in insulators and semiconductors *Solid state Phys.*, **1963**, *14*, 99–214.
- (78) Owen, J.; Thornley, J.H. Covalent bonding and magnetic properties of transition metal ions. *Rep. Prog. Phys.* **1966**, *29* (2), 675.
- (79) Hay, P. J.; Thibeault, J. C.; Hoffmann, R. Orbital interactions in metal dimer complexes. *J. Am. Chem. Soc.* **1975**, *97* (17), 4884–4899.
- (80) Kugel, K.; Khomskii, D.I. The Jahn-Teller effect and magnetism: transition metal compounds. *Sov. Phys. Usp.* **1982**, *25* (4), 621–664.
- (81) Kugel, K.; Khomskii, D.I. Orbital and magnetic structure of two-dimensional ferromagnets with Jahn-Teller ions. *Solid State Commun.* **1973**, *13* (7), 763–766.
- (82) Sugano, S.; Tanabe, Y.; Kamimura, H. *Multiplets of transition-metal ions in crystals*; Academic Press: New York, 1970; pp 263–270, 126–153.
- (83) Larsson, S.; Connolly, J.W.D. Spin and bonding properties and optical spectra of octahedral transition metal complexes using the multiple scattering $\text{X}\alpha$ method. *J. Chem. Phys.* **1974**, *60* (4), 1514–1521.

- (84) Adachi, H.; Shiokawa, S.; Tsukada, M.; Satoko, C.; Sugano, S. Discrete variational X α cluster calculations. III. Application to transition metal complexes. *J. Phys. Soc. Japan* **1979**, *47*, 1528-1537.
- (85) Jeck, R.K.; Krebs, J.J. First and second-shell hyperfine interactions in iron-group-doped perovskite fluorides. *Phys. Rev. B* **1972**, *5* (5), 1677-1687.
- (86) Simonetti, J.; McClure, D. S. Electron transfer bands of the divalent 3d series ions in LiCl. *J. Chem. Phys.* **1979**, *71* (2), 793-801.
- (87) Moreno, M.; Aramburu, J. A.; Barriuso, M. T. Ni⁺ in fluoride lattices: a 3d \rightarrow 4p transition in the near-ultraviolet region. *J. Phys. C: Solid State Phys.* **1986**, *19*, L315 - L319.
- (88) Stanley, H.E.; Kaplan, T.A. Possibility of a phase transition for the two-dimensional Heisenberg model. *Phys. Rev. Lett.* **1966**, *17* (17), 913-915.
- (89) Hagen, S. H.; Trappeniers, N. J. ESR of copper complexes in NH₄Cl, ND₄Cl and CsCl. *Physica* **1970**, *47* (2), 165-181.
- (90) Breñosa, A.G.; Moreno, M.; Rodríguez, F.; Couzi, M. Evidence for anomalous relaxation of the CuCl₄(NH₃)₂²⁻ center in NH₄Cl below T_c. *Phys. Rev. B* **1991**, *44* (18), 9859-9863.
- (91) Soethe, H.; Vetrov, V. A.; Spaeth, J. M. Local instability of The MnF₈ complex in BaF₂:Mn²⁺ studied by ENDOR. *J. Phys.: Condens. Matter* **1992**, *4* (39), 7927-7936.
- (92) García Fernández, P.; Aramburu, J. A.; Barriuso, M. T.; Moreno, M. Local symmetry change in BaF₂:Mn²⁺ at ~50 K: microscopic insight. *J. Chem. Phys.* **2008**, *128* (12), 124513 (1-7).
- (93) Kurzydłowski, D.; Derzsi, M.; Mazejc, Z.; Grochala, W. Crystal, electronic, and magnetic structures of M₂AgF₄ (M = Na-Cs) phases as viewed from the DFT+U method. *Dalton Trans.* **2016**, *45* (41), 16255-16261.
- (94) Grochala, W. Small changes, big consequences. *Nat. Mater.* **2006**, *5* (7), 513-514.
- (95) García Fernández, P.; Aramburu, J. A.; Barriuso, M. T.; Moreno, M. Cu²⁺ impurities in fluorite-type crystals: mechanisms favoring an off-center motion. *Phys. Rev. B* **2004**, *69*, 174110 (1-8).
- (96) Roelfsema, K. E.; Den Hartog, H. W. Electric field effect of EPR spectra of cubic impurities in SrCl₂. *J. Magnetic Resonance* **1978**, *29* (2), 255-273.
- (97) García-Lastra, J. M.; García-Fernández, P.; Calle-Vallejo, F.; Trueba, A.; Aramburu, J. A.; Moreno, M. Quantifying local and cooperative components in the ferroelectric distortion of BaTiO₃: learning from the off-center motion in the MnCl₆⁵⁻ complex formed in KCl:Mn⁺. *Inorg. Chem.* **2014**, *53* (13), 6534-6543.


(98) Gážo, J.; Bersuker, I. B.; Garaj, J.; Kabesova, M.; Kohout, J.; Langfelderova, H.; Melnik, M.; Serator, M.; Valach, F. Plasticity of coordination sphere of copper(II) complexes, its manifestation and causes. *Coord. Chem. Rev.* **1976**, *19* (3), 253–297.

(99) Gawraczyński, J.; Kurzydłowski, D.; Ewings, R. A.; Bandaru, S.; Gadomski, W.; Mazej, Z.; Ruani, G.; Bergenti, I.; Jaroń, T.; Ozarowski, A. et al. Silver route to cuprate analogs. *Proc. Natl. Acad. Sci. U.S.A.* **2019**, *116* (5), 1495-1500.

(100) Mazej, Z.; Goreshnik, E.; Jagličić, Z.; Gaweł, B.; Łasocha, W.; Grzybowska, D.; Jarón, T.; Kurzydłowski, D.; Malinowski, P.; Koźminski, W. et al. $KAgF_3$, K_2AgF_4 and $K_3Ag_2F_7$: important steps towards a layered antiferromagnetic fluoroargentate(II). *Cryst. Eng. Comm.* **2009**, *11* (8), 1702-1710.

9. TOC Graphic

Influence of orthorhombic distortion on magnetism



Tetragonal \rightarrow orthorhombic

