

Feshbach hypothesis of high-T_c superconductivity in cuprates

Lukas Homeier,^{1, 2,*} Hannah Lange,^{1, 2, 3} Eugene Demler,⁴ Annabelle Bohrdt,^{5, 2} and Fabian Grusdt^{1, 2, †}

¹*Department of Physics and Arnold Sommerfeld Center for Theoretical Physics (ASC), Ludwig-Maximilians-Universität München, Theresienstr. 37, München D-80333, Germany*

²*Munich Center for Quantum Science and Technology (MCQST), Schellingstr. 4, München D-80799, Germany*

³*Max-Planck-Institute for Quantum Optics, Hans-Kopfermann-Str. 1, Garching D-85748, Germany*

⁴*Institute for Theoretical Physics, ETH Zurich, 8093 Zürich, Switzerland*

⁵*University of Regensburg, Universitätsstr. 31, Regensburg D-93053, Germany*

(Dated: December 6, 2023)

Resonant interactions associated with the emergence of a bound state constitute one of the cornerstones of modern many-body physics, ranging from Kondo physics, BEC-BCS crossover, to tunable interactions at Feshbach resonances in ultracold atoms [1] or 2D semiconductors [2, 3]. Here we present a Feshbach perspective on the origin of strong pairing in Fermi-Hubbard type models. We perform a theoretical analysis of interactions between charge carriers in doped Mott insulators, modeled by a near-resonant two-channel scattering problem, and find strong evidence for Feshbach-type interactions in the $d_{x^2-y^2}$ channel that can support strong pairing, consistent with the established phenomenology of cuprates. Existing experimental and numerical results on hole-doped cuprates lead us to conjecture the existence of a light, long-lived, low-energy excited state of two holes with bipolaron character in these systems, which enables near-resonant interactions and can thus provide a microscopic foundation for theories of high-temperature superconductivity involving strong attraction, as assumed e.g. in BEC-BCS crossover scenarios. To put our theory to a direct test we suggest to use coincidence angle-resolved photoemission spectroscopy (cARPES), pair-tunneling measurements or less direct pump-probe experiments. The emergent Feshbach resonance we propose could also underlie superconductivity in other doped antiferromagnetic Mott insulators, as recently proposed for bilayer nickelates, highlighting its potential as a unifying strong-coupling pairing mechanism rooted in quantum magnetism.

High-temperature superconductivity in the cuprate compounds has a long and storied history and has remained an active field of research since its discovery in 1986 [4]. The phase diagram of hole-doped cuprates features several types of orders or regimes, such as antiferromagnetism, the pseudogap phase, and the charge and spin density wave states [5–8]. How the superconducting phase arises from these potential parent states – as a competing or intertwined order or as a separate phenomenon – remains debated until today, and a generally accepted unifying theme capturing all phases continues to appear out of sight.

Naturally, the question about the origin of high-temperature superconductivity is closely tied to the question about the underlying pairing mechanism. In this regard, many aspects are well understood today. While in principle present, electron-phonon coupling responsible for conventional Bardeen-Cooper-Schrieffer (BCS) superconductivity [9] is widely believed to be insufficient and too weak for explaining the high transition temperatures and rich phenomenology of cuprate compounds [10]. There is wide agreement that magnetic correlations play a central role in pairing, a view that is also supported by experimental evidence [11]. In the weak-coupling limit it is well understood how magnetic fluctuations can mediate d -wave attractive interactions [12, 13], explaining the

BCS-like appearance of the order parameter [14] in overdoped cuprates and its experimentally established nodal $d_{x^2-y^2}$ symmetry [15]. This picture of magnetic pairing has been further corroborated by numerous theoretical studies [12, 13, 16, 17], leading to various proposed scenarios such as (para-) magnon exchange [18–21], spin-bag mechanism [22, 23] and antiferromagnetic (AFM) Fermi liquids [24–26].

The strong coupling regime of the Fermi-Hubbard type models has been analyzed with numerical methods [27–34], variational RVB approach [5, 35], by the functional renormalization group [13, 17], and using field theoretical methods [36–39]. While these studies indicated the emergent strong pairing from magnetic fluctuations, they did not provide a simple physical picture that explains its origin. To provide a simple physical explanation of this phenomenon is the central goal of our paper.

On the experimental side, a key motivation for our analysis comes from observations that the superconducting transition in underdoped cuprates is qualitatively different from the conventional, mean-field, BCS-like characteristics observed at high doping [14]. Uemura [40], Emery and Kivelson [41] suggested that the superconducting T_c corresponds to the phase ordering transition with a non-BCS character [42–45]; thereby, holes may bind into (preformed) Cooper pairs already at temperatures higher than T_c . This points towards much stronger attractive interactions in the underdoped regime.

One of the surprising findings of recent state-of-the-art numerical studies in the context of Fermi-Hubbard type models has been a strong sensitivity of d -wave pair-

* lukas.homeier@physik.uni-muenchen.de

† fabian.grusdt@physik.uni-muenchen.de

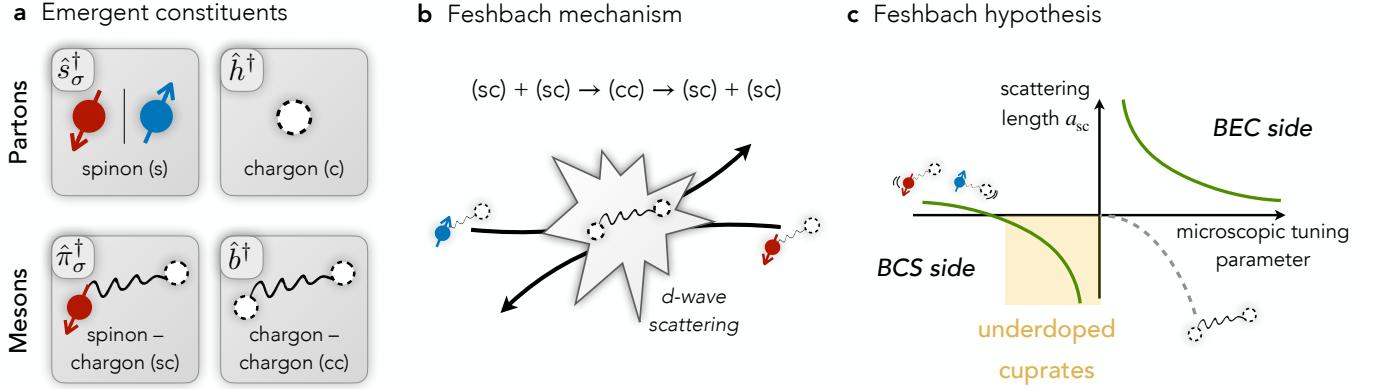


FIG. 1. Emergent Feshbach resonance. **a** In the presence of strong AFM correlations, the emergent charge carriers can be described by partons, the spinon (s) and chargon (c), which form the meson bound states: fermionic (sc)'s and bosonic (cc)'s. **b** In the low-energy scattering process between two (sc)'s with opposite spin, the mesons virtually recombine into an excited, light and tightly-bound (cc) bound state. Due to the mesons' internal structure, this process is dominated by $d_{x^2-y^2}$ -wave scattering. **c** If the formation of a (cc) state is a resonant process, the scattering length diverges and yields strong effective interactions between the underlying (sc) mesons. In the Feshbach hypothesis we conjecture that the normal state of underdoped cuprates is constituted by fermionic (sc)'s, located on the BCS side and in the vicinity of the scattering resonance.

ing to details of the model. The ground state of the plain-vanilla Hubbard model at typical parameters has been shown to be non-superconducting [30] owing to a competition with stripes; however slight modifications of e.g. the band structure lead to d -wave superconductivity [34], in line with predictions by functional renormalization group calculations [13, 17].

Another line of theoretical studies into properties of high- T_c cuprates has been to introduce strong attraction between charge carriers phenomenologically and investigate generic properties of such systems. This approach has been pursued by Nozières and Schmitt-Rink [46], Leggett [47], Randeria [48], and several others. Their methodology has been to introduce an effective attractive interaction between electrons that could be varied to tune the system between the BCS and BEC regimes, where spatially extended Cooper pairs continuously evolve into tightly bound bosonic pairs. These studies shed light on some of the surprising properties of high- T_c cuprates [49] but do not address the origin of the strong attraction between electrons.

Here we propose an alternative perspective on the pairing mechanism at strong coupling, also based on magnetic correlations: emergent Feshbach resonance. The central message of this paper is that the microscopic mechanism behind strong pairing in doped Mott insulators is a Feshbach resonance that enhances interactions between doped holes. Recent numerical studies of the t - J model [50] pointed out the existence of light but tightly bound, bosonic d -wave pairs of two holes with bi-polaron character in Mott insulators. These pairs complement individual fermionic holes to provide the basis of a two-channel Feshbach resonance model of pairing, see Figure 1. We point out that our scenario does not require the d -wave bi-polarons to be the ground state in systems with only two doped holes. Instead, we con-

sider the case when the bi-polaron corresponds to a resonance at finite positive energy, however this energy is small. Then coupling of fermionic holes to the bosonic channel can give rise to strong attractive d -wave interactions between holes. In the scenario we describe, the short-distance microscopic structure of the fermionic and bosonic charge carriers in the AFM background leads to the long-lived state at finite energies associated with the bosonic bi-polaron. This distinguishes our perspective from geometric resonances usually discussed in the context of BEC-BCS crossover [46–48], where the bosonic state ceases to exist on the BCS side.

Our starting point is a weakly hole-doped parent state with strong local antiferromagnetism and a sufficiently large AFM correlation length $\xi_{\text{AFM}} \gg a$, where $a = 1$ is the lattice spacing. In cuprates, this regime is believed to be realized below the pseudogap temperature, $T < T^*$ [17, 29]. Charge carriers in this regime correspond to mobile holes and give rise to hole pockets, smoothly developing into Fermi-arcs [51], observed around the nodal points, $\mathbf{k} = (\pm\pi/2, \pm\pi/2)$, in angle-resolved photoemission spectroscopy (ARPES) [52] and by quantum oscillations [52, 53]. At low doping in the square lattice Hubbard model with large on-site interaction $U \gg t$, the individual holes are well described by magnetic polarons, as revealed by analytical [54–59] and numerical studies [60–67], as well as experiments in solids [68] and recently in ultracold atoms [69].

In contrast, the two-hole excitation spectrum of the doped AFM is much harder to access experimentally and less understood theoretically. On the one hand, weak attraction between magnetic polarons, such as phonon- or magnon-exchange would suggest, could give rise to loosely bound Cooper-like pairs and would naturally lead to a BCS-type instability. On the other hand, numerical studies based on Hubbard and t - J models have indi-

cated the existence of much more tightly bound pairs of holes [56, 70–74] with only small energy differences between different pairing channels [50, 72, 75]. Moreover, recent density matrix renormalization group (DMRG) studies of the t - J model reported the existence of long-lived two-hole resonances with distinct dispersion relations associated with different pairing symmetries [50]. The observed spectral features in that study can be explained by models of tightly bound holes connected with a string of displaced spins [71, 76] (light bi-polarons).

This leads us to the main idea of our work. If low-energy excitations in the ground state retain their fermionic character – as observed experimentally [51, 52, 77, 78] – the tightly bound, bosonic two-hole pairs must correspond to meta-stable excited states. This situation is familiar from the case of (Fano-) Feshbach resonances and in the context of two particles: on the BCS side, the tightly bound bosonic state is replaced by a low energy two-particle resonance. However, it is the existence of this resonance that gives rise to a large negative scattering length – i.e. strong attraction – between the underlying fermions and is responsible for the high transition temperature predicted in a corresponding BEC-BCS crossover [49].

Feshbach resonances have been observed in various settings, from nuclear reactions in high-energy physics [79], cold atoms [1, 80, 81], to solid state materials [2, 3]; they have recently been proposed as a route to unconventional pairing in strongly correlated electron systems [82–88], and give rise to universal strong-coupling behavior e.g. in the above-mentioned BEC-BCS crossover [49]. The microscopic description we provide here suggests that this scenario is also relevant to underdoped cuprates, and the Feshbach-paradigm naturally leads to near-resonant $d_{x^2-y^2}$ attraction, in line with the established phenomenology in these systems.

To put our idea on a solid footing, we need to describe in a common theoretical framework the individual fermionic charge carriers, which we model as magnetic polarons, and the tightly bound bosonic pairs. To this end, the parton picture provides a powerful construction, in which the fundamental constituents are decomposed into spinons (s) and chargons (c) [89–92], see Figure 1a. Within this picture, magnetic polarons constitute a mesonic spinon-chargon bound state (sc) [93, 94] with a rich set of internal ro-vibrational excitations. Similarly, the tightly-bound two-hole states are viewed as mesonic chargon-chargon bound states (cc). Their internal rotational quantum numbers correspond to different pairing symmetries [50, 71, 76]. Among the evidence for the parton picture are numerical studies at low doping which have confirmed the predicted internal excitations [94–98] and effective masses of the mesons [50, 93].

Next, we discuss how the (sc) pairs (magnetic polarons) constituting the normal state in our model interact upon including a coupling to (cc) states. To this end, we consider an individual scattering event between two (sc) mesons with opposite spin. When they start

to overlap spatially, they can recombine into a virtual (cc) state, realizing the sequence

$$(sc)_\uparrow + (sc)_\downarrow \rightarrow (cc) \rightarrow (sc)_\uparrow + (sc)_\downarrow. \quad (1)$$

This naturally leads us to a two-channel description of the emergent (mesonic) Feshbach resonance, with $(sc)^2$ defining the open- and (cc) defining the closed channel, respectively, see Figure 1b. As we will argue below, the scattering process is dominated by a resonant d -wave (cc) state in the doped Hubbard model.

This leads us to formulate the following hypothesis:

- (i) Cuprates, as well as commonly used models of the latter, i.e. Fermi-Hubbard or t - J models at strong coupling, have a low-doping ground state close to a d -wave $(sc)^2$ - (cc) scattering resonance.
- (ii) More specifically, underdoped cuprates are on the BCS side of the conjectured d -wave resonance, but sufficiently close for the induced attraction to overcome the intrinsic repulsion of two charge carriers in the (sc) channel.

This situation is illustrated in Figure 1c, where we took the liberty to include an effective microscopic parameter tuning the relative energy of (sc) and (cc) channels independently. In reality, changing microscopic model parameters always affects the structure of both (sc) and (cc) mesons. On the level of theoretical models, a nearest-neighbor (NN) Hubbard interaction V is a promising candidate to tune across the resonance [85, 99–104].

Such tuning of the interactions may find a realization in solids when the screening of Coulomb interactions becomes increasingly poor in the low-doping regime [105]: Hence, at extremely low dopings, strong Coulomb repulsion is expected to lead to highly excited (cc) states and a normal state well in the BCS regime. Here, the attraction induced by couplings to (cc) states is expected to be unable to overcome the intrinsic repulsion between the individual dopants, caused e.g. by kinetic (Pauli repulsion) or Coulomb effects. As the Coulomb repulsion becomes screened, the emergent Feshbach resonance is approached. Once the induced attraction among (sc)'s is sufficiently large, a weak-coupling d -wave BCS state of magnetic polarons is expected to form. This is consistent with recent observations of BCS quasiparticle peaks in ARPES studies of strongly underdoped layered $\text{Ba}_2\text{Ca}_5\text{Cu}_6\text{O}_{12}(\text{F},\text{O})_2$ compounds [52] at 4.3 % hole doping. At higher doping, screening effects become even more effective. Here, the weak coupling BCS description can break down if near-resonant induced interactions are realized, which can lead to high critical temperatures T_c as in BCS-BEC cross-over scenarios [49] and may explain the observed non-BCS nature of the superconducting transition [14].

How close a given cuprate compound, or state in a given Hubbard model, is to the conjectured resonance can depend sensitively on details. On the one hand, this

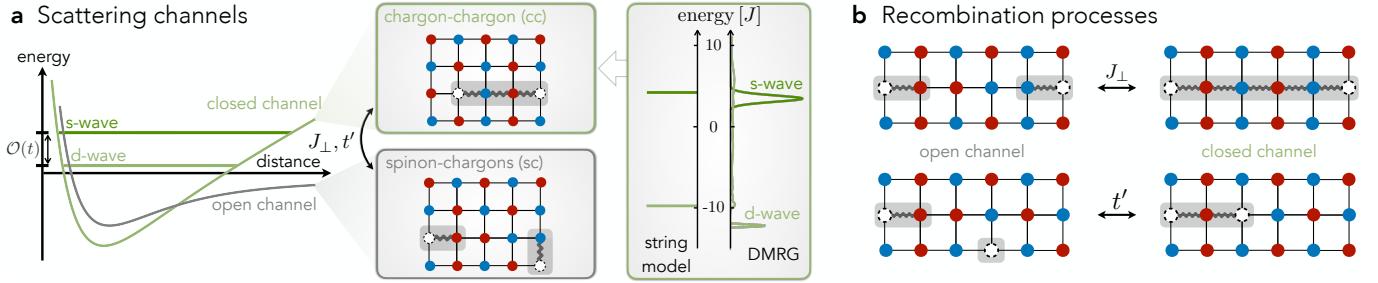


FIG. 2. Geometric string theory of the two-channel model. **a** Magnetic polarons, i.e. (sc) mesons, are fermionic quasiparticles of single holes doped into an AFM Mott insulator. In contrast, tightly bound (cc) mesons exist as long-lived *s*- and *d*-wave resonances in the spectrum. The two types of mesons constitute open and closed scattering channels, and can be described in a truncated string basis defined in a classical Néel background (see insets); they are composed of chargons (white circles) connected to a spinon (bottom) or another chargon (top) at the opposite end of the string. We plot the (cc) excitation spectrum at $\mathbf{Q} = \mathbf{0}$ obtained from the string model [76] (left) and from DMRG studies in the *t-J* model [50] (right), which shows the large energy separation between the *s*-wave and *d*-wave (cc) resonances. **b** Two spinons, each bound to a single chargon, can recombine into a longer string connecting the two chargons. Thereby spin exchange J_{\perp} and NNN tunneling t' processes couple the open and closed channel states and mediate an effective scattering interaction between the former.

may require some fine-tuning in order to reach the largest values of T_c by reaching parameters closest to resonant interactions. On the other hand, as explained below, we expect relatively strong coupling between the open and closed channels, set by the super-exchange energy J or the next-nearest neighbor (NNN) tunneling t' . This can lead to a broad Feshbach resonance, realizing strong attraction between (sc)'s even well before the resonance is reached [106]. Overall this scenario is broadly consistent with the considerable range of maximally achievable critical temperatures T_c in different compounds.

To support our hypothesis, we directly calculate the two-hole scattering interactions using a truncated basis approach in which we treat both the (sc) and (cc) channels on equal footing. To be concrete, we consider the *t-t'-J* model [107],

$$\begin{aligned} \hat{\mathcal{H}}_{t-t'-J} = & -t \sum_{\langle \mathbf{i}, \mathbf{j} \rangle} \sum_{\sigma} \hat{\mathcal{P}} \left(\hat{c}_{\mathbf{i}, \sigma}^{\dagger} \hat{c}_{\mathbf{j}, \sigma} + \text{h.c.} \right) \hat{\mathcal{P}} \\ & - t' \sum_{\langle\langle \mathbf{i}, \mathbf{j} \rangle\rangle} \sum_{\sigma} \hat{\mathcal{P}} \left(\hat{c}_{\mathbf{i}, \sigma}^{\dagger} \hat{c}_{\mathbf{j}, \sigma} + \text{h.c.} \right) \hat{\mathcal{P}} \\ & + J_z \sum_{\langle \mathbf{i}, \mathbf{j} \rangle} \left(\hat{S}_{\mathbf{i}}^z \hat{S}_{\mathbf{j}}^z - \frac{1}{4} \hat{n}_{\mathbf{i}} \hat{n}_{\mathbf{j}} \right) \\ & + \frac{J_{\perp}}{2} \sum_{\langle \mathbf{i}, \mathbf{j} \rangle} \left(\hat{S}_{\mathbf{i}}^{+} \hat{S}_{\mathbf{j}}^{-} + \text{h.c.} \right), \end{aligned} \quad (2)$$

with spin-1/2 fermions $\hat{c}_{\mathbf{j}, \sigma}^{\dagger}$ residing on sites \mathbf{j} with spin $\sigma = \downarrow, \uparrow$, and number (spin) operator $\hat{n}_{\mathbf{j}} = \hat{n}_{\mathbf{j}, \downarrow} + \hat{n}_{\mathbf{j}, \uparrow}$ ($\hat{S}_{\mathbf{j}}$). We denote the links between NN and NNN sites as $\langle \mathbf{i}, \mathbf{j} \rangle$ and $\langle\langle \mathbf{i}, \mathbf{j} \rangle\rangle$, respectively. The Gutzwiller projector $\hat{\mathcal{P}}$ removes energetically costly double occupancies such that $\hat{n}_{\mathbf{j}} \leq 1$ for all \mathbf{j} is enforced. The ground state $|0\rangle$ at half-filling is AFM Néel ordered.

Next, we describe the (sc) and (cc) bound states, which arise in the sectors of the Hilbert space with one and two

holes, respectively, upon doping the vacuum $|0\rangle$. We employ the semi-analytic geometric string theory, in which (sc) [(cc)] meson eigenstates are expanded in a truncated basis of orthonormal string states $|\mathbf{j}_{\sigma}, \Sigma\rangle \langle |\mathbf{x}_c, \Sigma_{cc}\rangle$. Here \mathbf{j}_{σ} [\mathbf{x}_c] denotes the spinon [first chargon] position and Σ [Σ_{cc}] is a sequence of non-retracing string segments connecting to the other parton, providing a confining force. These states can be constructed explicitly for one and two holes in a classical Néel state by displacing spins along the string Σ , see Figure 2a and Methods, and have been shown to provide an accurate, yet analytically tractable, approximation of the mesons' ground and excited states [54, 55, 71, 75, 76, 97, 108].

The open channel (sc) states constitute the starting point of the analysis. The gap to their internal excitations is sufficiently large $\mathcal{O}(J)$ such that at low energies only *s*-wave (sc) mesons $\hat{\pi}_{\mathbf{k}, \sigma}$ exist [98]. Therefore, in the low-doping limit, we describe the open channel by the following free-fermion Hamiltonian,

$$\hat{\mathcal{H}}_{\text{open}} = \sum_{\mathbf{k}, \sigma} [\varepsilon_{\text{sc}}(\mathbf{k}) - \mu] \hat{\pi}_{\mathbf{k}, \sigma}^{\dagger} \hat{\pi}_{\mathbf{k}, \sigma}. \quad (3)$$

The dispersion relation $\varepsilon_{\text{sc}}(\mathbf{k})$ has its minimum at the nodal points $\mathbf{k} = (\pm\pi/2, \pm\pi/2)$ [57, 58], around which two Fermi pockets form upon increasing the chemical potential μ [52]. Since we assume the AFM correlation length ξ to be sufficiently larger than the size of a (sc) meson, we can analyze the case of an AFM ordered state. Thus, all excitations are defined with momenta \mathbf{k} in the magnetic Brillouin zone (MBZ), which is rotated by $\pi/4$ and reduced with respect to the original crystal Brillouin zone (CBZ). We describe the internal structure of the (sc) mesons independently from each other and use the truncated string basis.

The closed channel states are constituted by (cc) mesons $\hat{b}_{\mathbf{Q}, \alpha, m_{\alpha}}^{\dagger}$, with momentum \mathbf{Q} and band index α [50, 76]. As in the case of (sc) mesons we ignore vi-

brational excitations; it is however important to include their rotational structure described by the C_4 angular momentum $m_4 = 0, \dots, 3$. The resulting free (cc) Hamiltonian is

$$\hat{\mathcal{H}}_{\text{closed}} = \sum_{\mathbf{Q}, \alpha, m_4} \varepsilon_{\text{cc}}^{m_4}(\mathbf{Q}) \hat{b}_{\mathbf{Q}, \alpha, m_4}^\dagger \hat{b}_{\mathbf{Q}, \alpha, m_4}, \quad (4)$$

with the dispersion $\varepsilon_{\text{cc}}^{m_4}(\mathbf{Q})$ of the tightly bound pair. In the truncated string basis, the (cc) states do not distinguish between the two magnetic sublattices and can be defined in the CBZ. In order to describe their coupling to the open channel in the next step, we fold the CBZ into the MBZ by restricting ourselves to $\mathbf{Q} \in \text{MBZ}$ and introducing the band index $\alpha = 0, 1$. Because the (cc) wavefunction of the two fermionic holes can be (anti)symmetric in the band index, any value of m_4 can be realized at the C_4 -invariant momenta; in particular at $\mathbf{Q} = \mathbf{0}$ shown below to be relevant for low-energy scattering.

Now we turn to a description of the coupling between the open and closed channels. In the effective string basis, we recognize microscopic processes $\propto J_\perp, t'$ leading to recombination processes from a (sc)² into a (cc) configuration, see Figure 2b. In order to describe the corresponding low-energy two-particle scattering problem, we consider two (sc)'s in a spin-singlet state and with momenta $\pm \mathbf{k}$ from opposite sides of the Fermi surface. Note that we focus here on intra-pocket recombinations: two (sc)'s from the same hole pocket recombine into a (cc) pair with total momentum $\mathbf{Q} = \boldsymbol{\pi}$, which leads to zero-momentum Cooper pairs in the MBZ. Hence the allowed pairing symmetries are of *d*- or *s*-wave nature.

To understand into which (cc) states the (sc)² can recombine, we formulate the relevant selection rules associated with the translational and C_4 -rotational symmetries of the system. The former ensures that total momentum is conserved, i.e. only couplings to (cc) mesons with C_4 -invariant momenta $\mathbf{Q} = \mathbf{0}$ or $\boldsymbol{\pi}$ are allowed. At these momenta, the latter symmetry further ensures conservation of total C_4 angular momentum m_4 . Since the individual (sc)'s have *s*-wave (internal) character, only the orbital angular momentum associated with their relative motion contributes to m_4 , as defined by the corresponding zero-momentum Cooper pair operator,

$$\hat{\Delta}_{m_4}^\dagger = \frac{1}{\sqrt{2}} \sum_{\mathbf{k}} f_{m_4}(\mathbf{k}) \left(\hat{\pi}_{-\mathbf{k}, \uparrow}^\dagger \hat{\pi}_{\mathbf{k}, \downarrow}^\dagger - \hat{\pi}_{-\mathbf{k}, \downarrow}^\dagger \hat{\pi}_{\mathbf{k}, \uparrow}^\dagger \right). \quad (5)$$

Here, the function $f_{m_4}(\mathbf{k})$ transforms as $f_{m_4}(\mathbf{k}) \rightarrow e^{-im_4\pi/2} f_{m_4}(\mathbf{k})$ under C_4 rotations. Since only $m_4 = 0$ (*s*-wave) and $m_4 = 2$ (*d*-wave) lead to non-vanishing $\hat{\Delta}_{m_4}^\dagger$, we conclude from the derived selection rules that only couplings to closed channel (cc) states with *d*- or *s*-wave symmetry are allowed. In principle, our formalism allows us to include finite momentum Cooper pairs relevant for inter-pocket scattering and potentially relevant for going beyond BCS mean-field theory.

In the next step, we integrate out the closed (cc) channels, which yields mediated interactions that we can describe by the effective Hamiltonian

$$\hat{\mathcal{H}}_{\text{int}} = \sum_{\mathbf{k}, \mathbf{k}'} V_{\mathbf{k}, \mathbf{k}'} \hat{\pi}_{-\mathbf{k}, \uparrow}^\dagger \hat{\pi}_{\mathbf{k}, \downarrow}^\dagger \hat{\pi}_{-\mathbf{k}', \uparrow} \hat{\pi}_{\mathbf{k}', \downarrow}, \quad (6)$$

with scattering matrix elements $V_{\mathbf{k}, \mathbf{k}'}$ of the form

$$V_{\mathbf{k}, \mathbf{k}'} = \frac{1}{L^2} \sum_{m_4=0,2} \frac{1}{\Delta E_{m_4}} \mathcal{M}_{m_4}^*(\mathbf{k}) \mathcal{M}_{m_4}(\mathbf{k}'). \quad (7)$$

Here we sum over the two allowed closed channels, $m_4 = 0, 2$, whose energy above the scattering threshold is ΔE_{m_4} . The form factors $\mathcal{M}_{m_4}(\mathbf{k})$ will be calculated below from matrix elements coupling open and closed channels that we obtain within the effective string model. L^2 denotes the two-dimensional volume.

An emergent Feshbach resonance with divergent attractive interactions is realized when the closed channel approaches the scattering threshold from above, i.e. $\Delta E \rightarrow 0^+$. At the considered (cc) momentum $\mathbf{Q} = \mathbf{0}$, only the *d*-wave (cc) state has low energy ΔE_2 ; in contrast, the *s*-wave (cc) state has energy $\Delta E_0 = \mathcal{O}(t)$ owing to its strong center-of-mass dispersion. This follows from string model calculations [71, 76] and has been confirmed by large-scale exact-diagonalization [73] and DMRG studies [50] in the *t-J* model. We show the corresponding energy distribution curves of the pair-spectral functions at $\mathbf{Q} = \mathbf{0}$ in Figure 2a (right column), where the large splitting is clearly visible.

This leads to the important conclusion that low-energy scattering of magnetic polarons is dominated by couplings to the *d*-wave (cc) channel; namely, since $\Delta E_0 \approx t$, couplings to the *s*-wave channel can be safely neglected in $V_{\mathbf{k}, \mathbf{k}'}$, Eq. (7). This justifies the simplified two-channel model underlying the Feshbach hypothesis formulated earlier in our article. Accurate numerical calculations of the (cc) gap ΔE_2 are extremely challenging: since it is defined as the distance of the bare (cc) energy from the two-particle scattering threshold, it constitutes a small difference of two much larger quantities and becomes sensitive to details. Nevertheless we note that numerous studies have concluded that tightly-bound *d*-wave pairs, i.e. with (cc) character, exist at low energies close to the scattering threshold, see e.g. [50, 73, 75, 76]. This justifies our conjecture that strongly interacting doped Hubbard models at low doping are close to an emergent *d*-wave Feshbach resonance.

Now we use the truncated string basis to calculate the form factors $\mathcal{M}_2(\mathbf{k})$ characterizing the open-closed channel coupling. From the underlying *t-t'-J* model we find (see [109]) two contributions corresponding to the different recombination processes illustrated in Figure 2b,

$$\mathcal{M}_2(\mathbf{k}) = J_\perp \mathcal{M}_2^{J_\perp}(\mathbf{k}) - \text{sgn}(\delta) |t'| \mathcal{M}_2^{t'}(\mathbf{k}). \quad (8)$$

This result assumes perturbative $|t'| \ll t$, such that the effective string model remains valid. Moreover we

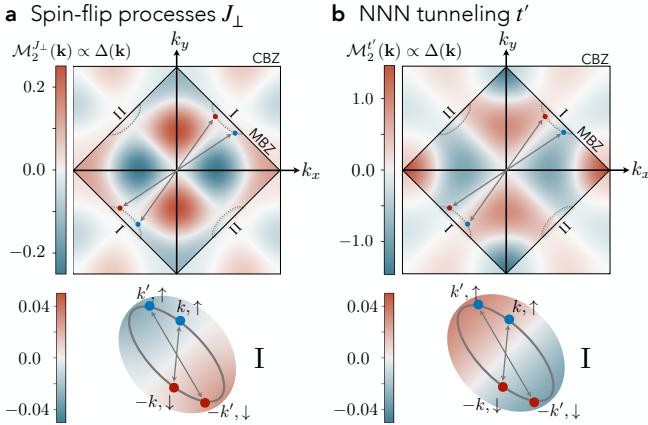


FIG. 3. Symmetry of the pairing interaction. We plot the dimensionless open-closed channel form factors $\mathcal{M}_2^{J_\perp}(\mathbf{k})$ from spin-flip processes **a**, and $\mathcal{M}_2^{t'}(\mathbf{k})$ from NNN tunneling processes **b**, as calculated within the two-channel model of the emergent Feshbach resonance. They directly reflect the sign structure of the resulting superconducting order parameter $\Delta(\mathbf{k})$, and show a strong momentum dependence. Outside the MBZ we used reduced opacity for clarity. Upon doping, charge carriers fill up the two hole pockets I and II, realizing scattering of total momentum $\mathbf{Q} = \mathbf{0}$ pairs on the Fermi surfaces (bottom). The mediated interactions, and hence the pairing gap, vanish along the white nodal lines, featuring a dominant $d_{x^2-y^2}$ nodal structure in the CBZ.

generalized our description to include hole and electron doping δ , characterized by $\text{sgn}(\delta) = +1$ (holes) and $\text{sgn}(\delta) = -1$ (electrons) respectively; in deriving Eq. (8) we further assumed $t' < 0$ in Eq. (2). A typical value used to model cuprates is $t'/|t| = -0.2$ [110, 111]. In the following, we extend the two-body scattering description to a many-body problem of weakly interacting magnetic polarons and discuss implications of the effective model at finite doping.

We show the two contributions to the form factor separately in Figure 3a and b and find a rich momentum dependence with a sign structure reflecting the underlying d -wave symmetry of (cc) mesons. Notably, within a weak coupling BCS description of the (sc) Fermi sea, the superconducting order parameter $\Delta(\mathbf{k}) \propto \mathcal{M}_2(\mathbf{k})$ follows directly from the BCS gap equation for Eq. (6), see [109]. Therefore, Figure 3 reveals the structure of the pairing gap. In particular, we find for both recombination processes that the form factor (and hence the pairing gap) is dominated by the ubiquitous $d_{x^2-y^2}$ nodal structure observed in hole doped cuprate compounds.

Beyond the $d_{x^2-y^2}$ structure dominating around the hole pockets we find additional nodal lines in the CBZ originating from a superimposed extended s-wave structure of the interactions. This rich momentum-dependence of the induced interactions reflects the extended spatial structure of the closed-channel (cc) state mediating the attractive interaction. Nevertheless, within our theory, combining J_\perp and t' processes,

pairing is dominated by $d_{x^2-y^2}$ structure in the entire low hole doping regime $\delta < 15\%$, with only small deviations [109] from the ideal $\Delta_{x^2-y^2}(\mathbf{k}) \simeq |\cos(k_x) - \cos(k_y)|$ structure; therefore the additional nodal lines are outside the immediately relevant experimental regime. In fact, the gap structure we find is consistent with ARPES measurements of the pairing gap in cuprate compounds [52, 112, 113], which indicate that the quasiparticle gap differs from the simple d -wave form $\Delta(\mathbf{k}) \propto \cos(2\phi_{\mathbf{k}})$ by the addition of a small $\delta\Delta(\mathbf{k}) \propto \cos(6\phi_{\mathbf{k}})$ component (see Methods).

Now we turn to possible experimental signatures of the Feshbach hypothesis. The key ingredient of the proposed pairing mechanism is the existence of a tightly bound (cc) channel at low excitation energies above the Fermi energy. At this point it is important to contrast the (cc) mesons to pre-formed Cooper pairs expected above the superconducting critical T_c where phase-coherence rather than pairing disappears at low doping [40, 41]. From our perspective, pre-formed Cooper pairs should be of (sc)²-type and exist just above T_c , whereas (cc) pairs can exist separately at higher energies and potentially well above T_c .

While the (cc) channel gives rise to a doping-dependent ARPES feature in single-particle spectroscopy, we find the signal to be very weak (see Methods and Ref. [109]). Therefore, we turn our attention to two-hole (correlation) spectroscopy, where numerical studies [50, 73] found the pronounced (cc) peaks shown in Figure 2a (right column). A direct measurement of such two-hole spectra requires removal of a tightly-bound pair, with or without well-defined C_4 angular momentum, at a well-defined energy ω and momentum \mathbf{k} . Theoretical proposals have been made how this can be achieved in coincidence ARPES spectroscopy, in a one-photon-in-two-electron-out [114, 115] or a two-photon-in-two-electron-out [116] configuration. While the former needs high-energy photons, the latter requires low-intensity light in order to distinguish the coincidence signal from the one-particle ARPES background [117], making both challenging. In Figure 4a we illustrate the correlated ARPES process, which removes adjacent electrons and creates a hole pair having overlap with all angular momentum m_4 channels of the (cc) bound state if $\mathbf{k} \neq \mathbf{0}$. The energy onset of the signal relative to the Fermi energy E_F and at $\mathbf{Q} = \mathbf{0}$ would directly measure the detuning ΔE_{m_4} from the (cc) resonance in our proposed Feshbach scenario.

Further, we suggest two potential experiments based on the coherent tunneling of pairs. First, if a sample with $T > T_c$ is brought in contact with a superconductor, the Cooper pairs from the latter can tunnel through the junction into the (cc) channel, similar to Anderson-Goldman pair tunneling [118]. Such experiments have already revealed some signatures of enhanced pairing fluctuations above T_c [44]. By adding an in-plane magnetic field and a voltage across the junction, the pair spectra could be directly probed with combined en-

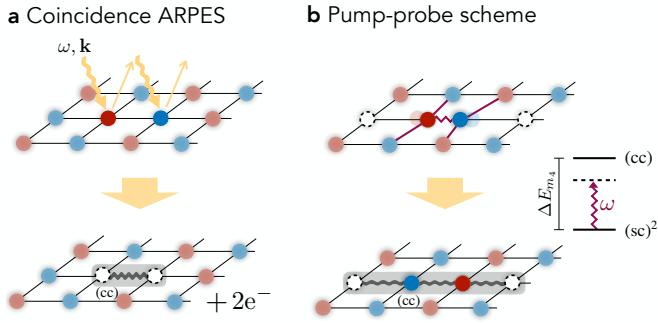


FIG. 4. Experimental signatures of the closed channel (cc) state. **a** Two photons with energy and momentum (ω, \mathbf{k}) remove two adjacent electrons from the system, which can be detected in the correlations of the photoelectrons (coincidence ARPES). This gives direct access to the dispersion relation of the (cc) meson as shown for $\mathbf{Q} = \mathbf{0}$ in Figure 2a (right). **b** We propose a pump-probe protocol, in which a Raman active phonon-mode is driven at frequency ω (purple). This modulates the microscopic couplings and drives a transition between the open channel (sc)² and closed channel (cc) states such that the energy difference ΔE_{m_4} in the proposed Feshbach model can be overcome, potentially allowing to reach a transient state with resonant interactions.

ergy and momentum resolution [50, 119]. Second, scanning tunneling noise spectroscopy can directly probe local pairs by analyzing autocorrelations of the current fluctuations [120, 121]. We expect an onset of enhanced pairing fluctuations at an energy ΔE_{m_4} above E_F as a direct signature of the near-resonant (cc) state, which should be present even above $T > T_c$. This is in line with recent noise-spectroscopy experiments performed on LSCO [45] which reported an onset of enhanced pairing fluctuations around an energy scale of 10 meV.

Finally, we propose to verify the existence of the tightly-bound (cc) state in pump-probe experiments, in which the properties of the transient state are modified, see Figure 4b. By off-resonantly driving a Raman-active phonon mode, the microscopic parameters t , t' and J can be modulated in time by the pump pulse, with frequency ω . From our microscopic model we predict that this can drive the transition between the open (sc)² and closed channel (cc), achieving tunable interactions in the transient state which become resonant for $\omega = \Delta E_{m_4}$. On resonance we can expect creating a large population of long lived metastable (cc) pairs. This transient state can exhibit optical properties similar to systems with strong superconducting correlations. This scenario is potentially relevant for understanding light-induced superconductivity [122].

To summarize, we propose a new perspective on the pairing mechanism potentially underlying high-temperature superconductivity as observed in the cuprate compounds. It is based on the idea that an emergent Feshbach resonance between magnetic polaron-like constituents, with spinon-chargon character, of the low-doping normal state may arise when a near-resonant

tightly bound bi-polaronic state of two holes exists at low excitation energies ΔE_2 . Using a truncated string basis we derive robust $d_{x^2-y^2}$ attractive interactions between the fermionic charge carriers in the open channel, inherited from the structure of the light bi-polaronic chargon-chargon state constituting the closed channel. Comparison to experiments in cuprate compounds [8, 113] as well as DMRG simulations of the t - J model [50] lead us to the Feshbach hypothesis: We conjecture that cuprates remain on the BCS side of an emergent Feshbach resonance, but realize near-resonant interactions, i.e. $\Delta E_2 \lesssim J$.

The Feshbach pairing mechanism we introduce here for cuprates, or the square lattice Hubbard model, is distinct from other proposed scenarios. In contrast to the spin-bag mechanism [22, 23], we assume a pronounced internal structure of the emergent charge carriers sustaining a long-lived chargon-chargon resonance that mediates attractive interactions. Our proposal is also different from glue-based mechanisms as in conventional phonon-based superconductors where weak retarded attraction appears, or exchange-based mechanisms where collective excitations – such as (para-) magnons – realize attractive interactions. For example, field-theoretic work [21] suggests intra-pocket d_{xy} pairing, whereas we find intra-pocket $d_{x^2-y^2}$ pairing (notably Ref. [21] found inter-pocket $d_{x^2-y^2}$ pairing, however). Nevertheless, we also conclude that magnetic interactions, in conjunction with kinetic effects, are ultimately responsible for pairing, in agreement with a large body of analytical and numerical work [12, 13, 16, 17] and experiments [11]. Although in our calculations we assumed a long-range ordered AFM, our ideas directly extend to disordered normal states such as fractionalized Fermi liquids [36, 123–126].

The Feshbach scenario we suggest may provide a long-sought common perspective on pairing in a whole range of strongly correlated systems, ranging from two-dimensional semiconductors [83, 84] to bilayer nickelate superconductors [85, 86, 127, 128]. We expect that our microscopic considerations will also provide a valuable perspective on pairing in a broader class of doped antiferromagnets, such as infinite-layer nickelates or heavy fermion superconductors. A direct application of our theory is to analyze electron-doped cuprates, where the topology of the magnetic polaron Fermi surface changes [129] and the realized pairing symmetry remains subject of debate.

To reveal direct signatures of the Feshbach pairing mechanism in cuprates, we propose to use spectroscopic probes for pairs, such as coincidence ARPES. These will allow to look for spectral features ubiquitous to the chargon-chargon excitations which we argue to be responsible for the appearance of strong attractive interactions. Additionally, we suggest pump-probe experiments, which may enable to bring the system closer to resonance, potentially resulting in higher transition temperatures. Numerical studies as well as quantum simulation experiments [127] provide further possibilities to test our hy-

pothesis. On one hand, advances in calculating one- and two-particle spectral functions numerically [130] will allow to search for more direct signatures of the emergent Feshbach resonance. On the other hand, ultracold atoms in optical lattices [127] or tweezer arrays [131] allow to study clean systems with widely tunable parameters, in and out-of equilibrium, and including higher-order correlation functions [132]. A possible application of the latter would be to look for direct signatures of the strings defining the structure of spinon-chargon and chargon-chargon pairs, in a wide range of dopings.

Acknowledgments.— We thank Pit Bermes, Roderich Moessner, Lode Pollet, Tizian Blatz, Timothy Harris, Immanuel Bloch, Markus Greiner, Ulrich Schollwöck, Atac Imamoglu, Assa Auerbach, Matteo Mitrano and Walter Metzner for fruitful discussions. This research was funded by the Deutsche Forschungsgemeinschaft (DFG, German Research Foundation) under Germany’s Excellence Strategy – EXC-2111 – 390814868 and has received funding from the European Research Council (ERC) under the European Union’s Horizon 2020 research and innovation programm (Grant Agreement no 948141) — ERC Starting Grant SimUcQuam. L.H. was supported by the Studienstiftung des deutschen Volkes. H.L. acknowledges support by the International Max Planck Research School. E.D. received funding by the SNSF (project 200021_212899), the Swiss State Secretariat for Education, Research and Innovation (contract number UeM019-1), and the ARO grant W911NF-20-1-0163.

Author contributions.— L.H. performed all calculations. F.G. supervised the work. L.H., A.B. and F.G. devised the conceptual idea. All authors jointly analyzed the results and proposed possible experimental tests. L.H. and F.G. wrote the manuscript, with input from H.L., E.D. and A.B.

Competing interests.— The authors declare no competing interests.

Data and materials availability.— The data is available from the authors upon request.

METHODS

Geometric string theory

In the proposed Feshbach scenario two meson-like parton bound states virtually recombine from an open channel (sc)² into the closed channel (cc). Hereby, the spatial structure of the meson bound states is crucial to determine the properties of the scattering channels and recombination processes. A semi-analytical description of the bound state wavefunction for $t \gg J$ can be obtained in a truncated basis (geometric string) approach [76, 97, 108] spanning the basis states of the open and closed channel Hilbert spaces, $\mathcal{H} = \mathcal{H}_{\text{open}} \oplus \mathcal{H}_{\text{closed}}$, with exactly two holes. The strategy is to determine the properties of the emergent Feshbach resonance in the few-body set-

ting of two holes, for which we can apply the geometric string theory to derive the effective interactions $V_{\mathbf{k}, \mathbf{k}'}$, see Eq. (6). Since the effective interactions describe the leading order two-body interactions between magnetic polarons, it allows us to elevate the few-body problem to a many-body Hamiltonian in the low-doping regime with weakly interacting (sc)²s/magnetic polarons.

The truncated basis states in the open channel are given by $\mathcal{H}_{\text{open}} = \{|\mathbf{j}_{\downarrow}, \Sigma_{\downarrow}\rangle \otimes |\mathbf{j}_{\uparrow}, \Sigma_{\uparrow}\rangle\}$ and are defined as follows. Starting from the undoped AFM Néel background, holes are inserted at position \mathbf{j}_{σ} ($\sigma = \downarrow, \uparrow$) but not on adjacent sites; further the fermionic two hole states have to be antisymmetrized. In the limit $t \gg J$, we assume the spin background to be frozen such that the individual holes can tunnel on NN sites and disturb the AFM spin background. The path of the holes, excluding self-retracing paths, is encoded in the string Σ_{σ} with length ℓ_{σ} and thus the string object contains information about the displacement of the AFM ordered background. Further, the string connects the spinon σ at position \mathbf{j}_{σ} with the corresponding chargon, see Figure 2a (inset). For distant holes, i.e. for the asymptotic free states in the scattering problem, the strings give rise to a linear confining potential $V_{\Sigma} \propto J_z \cdot \ell_{\sigma}$ resulting in parton bound states with a discrete spectrum; these asymptotic parton wavefunctions correspond to the wavefunctions obtained for single holes [108, 133]. Due to the increasing potential energy with the length of the strings, the basis states can be truncated in a controlled way.

A good parametrization of the internal states is given by the string length ℓ_{σ} and the angles between string segments of length ℓ_{σ} and $\ell_{\sigma} + 1$; thus, the eigenstates can be labeled by vibrational and rotational quantum numbers, respectively, which become particularly good quantum numbers around C_4 invariant momenta \mathbf{k}_{σ} . The internal ground state of these bound states are the magnetic polarons $\hat{\pi}_{\sigma}^{\dagger}$ or (sc) meson bound states in our model. Refined theoretical modeling and including the spin-flip terms J_{\perp} can accurately describe the (sc) dispersion relation $\epsilon_{\text{sc}}(\mathbf{k})$ [97, 108, 133].

Similarly, the truncated basis states for the closed channel are given by $\mathcal{H}_{\text{closed}} = \{|\mathbf{x}_c, \Sigma_{cc}\rangle\}$ [71, 76]. Here, the basis is constructed in the following way: we insert a pair of (distinguishable) holes on adjacent sites and label the site of the first hole by \mathbf{x}_c , which is connected by the string Σ_{cc} of length ℓ_{cc} to the second hole. Now, both holes can tunnel while remaining connected by the string tracing their paths’ through the spin background. The length of the string is associated with a confining potential. Again, at the C_4 -invariant momenta $\mathbf{Q} = \mathbf{0}, \pi$ the quantum numbers of the bound state are given by the vibrational and rotational modes; the former are energetically gapped $\mathcal{O}(t^{1/3} J^{2/3})$ and we assume the vibrational ground state. Importantly, the eigenstates have to be antisymmetrized in order to describe fermionic two-hole bound states. In this procedure we assume a total spin singlet. Hence, the bound state does not carry any spinon degree-of-freedom and can be described by its chargon-

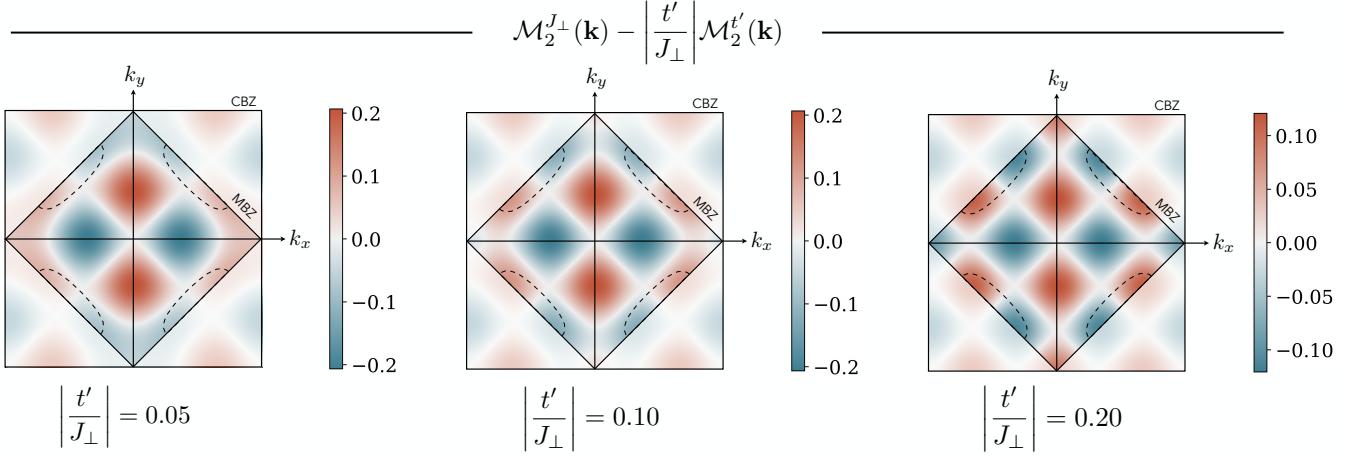


FIG. 5. **Combined t' and J_\perp form factors.** We show the form factor $\mathcal{M}_2(\mathbf{k})$ for hole doping in cuprate superconductors ($t'/|t| < 0$) for $|t'/J_\perp| = 0.05, 0.1, 0.2$. The hole pockets (dashed lines) correspond to the single hole magnetic polaron dispersion with $t/J = 10/3$ [134] at relatively large doping $\delta = 15\%$.

chargon (cc) content. The (cc) bound states $\hat{b}_{\mathbf{Q},\alpha,m_4}^\dagger$ can have different rotational eigenvalues $m_4 = 0, \dots, 3$. In contrast to the spinon positions \mathbf{j}_σ in the open channel, the position \mathbf{x}_c is defined on the crystal lattice. Therefore, we can either (i) describe momenta in the CBZ or (ii) introduce a band index α that is acquired from band folding into the MBZ, see main text. The (cc) bound state has substantial overlap with a state, where two adjacent electrons are removed from an AFM Mott insulator (see section on cARPES) corresponding to a string length $\ell_{cc} = 1$ state in our description. This gives rise to an ARPES-type two-hole spectrum with spectral weight at energies E as plotted in Figure 2a (right) for $\mathbf{Q} = \mathbf{0}$ in the MBZ obtained from geometric string theory [76] in the t - J_z model and state-of-the-art DMRG calculations of the t - J model on 40×4 cylinders [50].

The bare energy difference between the open and closed channel states ΔE_{m_4} determines the distance in energy from the Feshbach resonance and, hence, controls the scattering length. The previous DMRG studies [50] have also determined the dispersion relations of the (cc) bound states revealing a strong m_4 dependence consistent with geometric string calculations [76]. While the s-wave (cc) state is highly mobile $\propto t$, the d-wave band is flat in the t - J_z limit and only disperses by including spin flip-flop terms J_\perp . At the relevant scattering momenta $\mathbf{Q} = \mathbf{0}, \pi$, the (cc)'s internal ground state has d-wave symmetry with gap $\mathcal{O}(t)$ to internal rotational excitations. Therefore, the near-resonant low-lying closed channel state is of d-wave symmetry with the (fitted) dispersion $\varepsilon_{cc}(\mathbf{k}) = -J(\cos(k_x) + \cos(k_y) - 2) + \Delta E_{m_4=2}$.

Scattering form factors

The form factor $\mathcal{M}_{m_4}(\mathbf{k})$ is proportional to the coupling matrix elements between open (sc) and closed (cc)

channel states. Specifically, we consider open-closed channel couplings given by

$$\begin{aligned}\hat{\mathcal{H}}_{oc} &= \hat{\mathcal{H}}_{J_\perp} + \hat{\mathcal{H}}_{t'} \\ \hat{\mathcal{H}}_{J_\perp} &= \frac{J_\perp}{2} \sum_{\langle \mathbf{i}, \mathbf{j} \rangle} (\hat{S}_i^+ \hat{S}_j^- + \text{H.c.}) \\ \hat{\mathcal{H}}_{t'} &= -t' \sum_{\langle \langle \mathbf{i}, \mathbf{j} \rangle \rangle} \sum_{\sigma} (\hat{c}_{\mathbf{i},\sigma}^\dagger \hat{c}_{\mathbf{j},\sigma} + \text{H.c.}).\end{aligned}\quad (9)$$

Note that we include the NNN tunneling t' in a perturbative description, i.e. we assume the wavefunction and band structure of the (sc) and (cc) bound state for $t' = 0$ and calculate their coupling for small NNN tunneling t' .

As argued in the main text, the zero momentum scattering ($\mathbf{Q} = \mathbf{0}$) is relevant for low-energy intra-pocket scattering of magnetic polarons. In the MBZ, this also allows for closed channel states with $\mathbf{Q} = \mathbf{0}$ and antisymmetric band index. Therefore, the relevant form factor is related to the matrix elements by

$$\mathcal{M}_2(\mathbf{k}) = J_\perp \mathcal{M}_2^{J_\perp}(\mathbf{k}) + t' \mathcal{M}_2^{t'}(\mathbf{k}) \quad (10a)$$

$$\frac{\kappa}{\sqrt{L^2}} \mathcal{M}_2^\kappa(\mathbf{k}) = \langle 0 | \hat{b}_{\mathbf{Q}=\pi, m_4=2} \hat{\mathcal{H}}_\kappa \hat{\pi}_{-\mathbf{k}, \uparrow}^\dagger \hat{\pi}_{\mathbf{k}, \downarrow}^\dagger | 0 \rangle, \quad (10b)$$

with $\kappa = J_\perp, t'$. These matrix elements can be used in a full BEC-BCS crossover description, which captures strong hybridization between the two channels.

Here, we integrate out the closed channel, i.e. the closed channel is only virtually occupied in the scattering process, yielding the scattering Eq. (7). We emphasize that the structure of the (cc) bound state is inherited through the coupling matrix elements. To calculate the matrix elements, we expand the mesons' bound state wavefunctions in their string length. Since the bulk of the meson wavefunctions only span across a few lattice sites, the largest contribution to the form factors are given by short string length states, where two magnetic

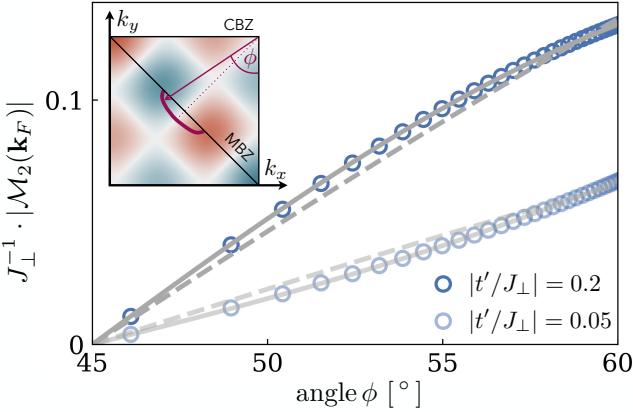


FIG. 6. Gap anisotropy. The form factor $\mathcal{M}_2(\mathbf{k})$ is directly related to the pairing gap $\Delta(\mathbf{k})$. We assume an elliptical Fermi surface of magnetic polarons, i.e. hole pockets, at $\delta = 10\%$ doping. The Fermi surface is parameterized by the angle $\phi_{\mathbf{k}}$ (inset). The blue circles show the pairing gap, calculated from our two channel model, along the Fermi surface for exemplary values $|t'/J_{\perp}| = 0.05, 0.2$. We fit the pairing gap using a plain vanilla $d_{x^2-y^2}$ gap symmetry (dashed gray) and a refined gap function including $\cos 6\phi_{\mathbf{k}}$ terms (solid gray). The latter is an excellent fit function for an entire range of parameters $|t'/J_{\perp}|$.

polarons of length $\ell_{\sigma} \approx 1 - 2$ recombine with a (cc) state of length $\ell_{cc} \approx 3 - 4$; the convergence of the form factor in the string length is confirmed in Ref. [109]. In Figure 3, we show the resulting form factors for (cc) strings up to length $\ell_{cc} = 5$ using the meson wavefunctions for $t/J = 3$ determined in Refs. [76, 133].

The form factors $\mathcal{M}_2(\mathbf{k})$ we consider in our model are constituted by spin-flip J_{\perp} and NNN tunneling t' processes. Further, the string description gives rise to an effective sign difference between electron ($\delta < 0$) and hole ($\delta > 0$) doping, see Eq. (8), that originates from a broken particle-hole symmetry for $t' \neq 0$. In the main text in Figure 3 we plot the two contributions $\mathcal{M}_2^{J_{\perp}}(\mathbf{k})$ and $\mathcal{M}_2^{t'}(\mathbf{k})$ separately.

In Figure 5, we additionally provide the combined form factors $\mathcal{M}_2(\mathbf{k})$ for various t'/J_{\perp} ; note that we do not take into account the attributed change in the (sc) and (cc) wavefunctions by the NNN tunneling. We find that the nodal ring of the spin-flip form factor moves away from the hole pockets and towards the center of the Brillouin zone as t' is increased. Further, we sketch the hole pockets for $t/J = 10/3$ and $\delta = 15\%$ [134], which – for realistic values of t' in cuprates – do not touch the nodal ring. Our findings are consistent with ARPES gap measurements in cuprate superconductors.

Gap anisotropy

In our phenomenological string model we find additional extended s-wave structure, which occurs from be-

yond point-like interactions, i.e. from the finite extend of the meson wavefunctions. Similarly, precise measurements of the superconducting gap in underdoped Bi-2212 indicate an anisotropy in momentum space that cannot be explained by the plain vanilla $d_{x^2-y^2}$ symmetry as argued by Mesot et al [112]. Instead, it was found that the function

$$\Delta(\phi_{\mathbf{k}}) \propto B \cos(2\phi_{\mathbf{k}}) + (1 - B) \cos(6\phi_{\mathbf{k}}) \quad (11)$$

captures the gap structure in underdoped samples, where B is used as a fit parameter. In ARPES measurements the pairing gap is determined along the Fermi surface, conveniently parameterized by the angle $\phi_{\mathbf{k}}$, see Figure 6b (inset) for definition. To model the cuprates in our calculations, we assume a Fermi surface of magnetic polarons for $t' = 0$ [134] as shown in Figure 6 (inset). Next, we calculate the BCS pairing gap $\Delta(\mathbf{k}) \propto \mathcal{M}_2(\mathbf{k})$ (see main text) for different parameters $|t'/J_{\perp}| = 0.05, 0.2$ and extract its features along the magnetic polaron's Fermi surface. To this end, we fit to (i) $\cos(2\phi_{\mathbf{k}})$ (i.e. $B = 1$) and (ii) to the refined gap function Eq. (11) with $B \in [0, 1]$. The fitted curves are shown by the dashed and solid gray lines in Figure 6. We find excellent agreement of our calculations to the fit for the second case (ii), consistent with ARPES measurements [112].

Coincidence ARPES (cARPES)

Coincidence ARPES, where two correlated photoelectrons are emitted, gives access to the (cc) channel with different angular momentum m_4 . This can be realized in both a one-photon-in-two-electron-out and a two-photon-in-two-electron-out scheme. The former requires high energy photons and therefore places an additional experimental challenge, while for the latter the typical ARPES photon energies can be used [117] and will be considered in the following.

The two in-coming photons have momentum \mathbf{k}_1 and \mathbf{k}_2 (out-going photonelectrons have momentum \mathbf{k}_3 and \mathbf{k}_4). Here, we consider the special case with $\mathbf{k}_1 = \mathbf{k}_2 \equiv \mathbf{k}$, and $\mathbf{k}_3 = \mathbf{k} + \delta\mathbf{k}$ and $\mathbf{k}_4 = \mathbf{k} - \delta\mathbf{k}$. In this sector, there is no momentum transfer to the sample and thus we probe (cc) states with $\mathbf{Q} = \mathbf{0}, \pi$ in the MBZ.

In the main text, we argue that for $\delta\mathbf{k} \neq 0$ the coupling matrix elements or spectral weight of coincidence ARPES is non-zero for any angular momentum m_4 . To show this, we consider the matrix elements $\mathcal{R}(\delta\mathbf{k})$ for removing two adjacent electrons at distance \mathbf{r}_n , given by four individual processes on the square lattice:

$$\mathcal{R}(\delta\mathbf{k}) \propto \sum_{n=0}^3 e^{i\frac{\pi}{2}nm_4} e^{-i\mathbf{r}_n \cdot \delta\mathbf{k}}. \quad (12)$$

The matrix elements are momentum dependent ($\delta\mathbf{k}$) and admit the rotational symmetry m_4 of the (cc) channel. Since the low-energy channel has d -wave symmetry

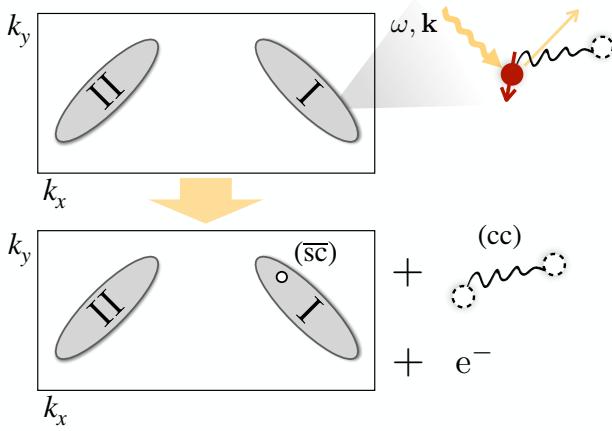


FIG. 7. Single-hole ARPES. In the low-doping regime, the Fermi sea of charge carriers forms two hole pockets I and II [52]. We consider photoemission processes, where the photoelectron is removed in the vicinity of an already existing magnetic polaron. This process can couple to the (cc) channel by leaving behind a hole-type excitation ($\bar{\text{sc}}$) in the Fermi sea; the two-body nature gives rise to broad spectral continuum.

($m_4 = 2$), the matrix elements vanish along the nodal directions, and in particular at $\delta \mathbf{k} = 0$. However, for $\delta \mathbf{k} \neq 0$ we find non-zero matrix elements to the (cc) bound state.

Single-hole ARPES

Alternatively to coincidence ARPES, one can – in principle – obtain a less-direct signature of (cc) states in single-hole ARPES spectroscopy. However we find the signal to be very weak, as we will show in the following. Nevertheless, high resolution ARPES in ultra-clean samples or quantum simulation may enable to measure signatures of the (cc) bound state in the future.

In order to extract two-hole properties from the

ARPES spectrum, involving the removal of just one electron, we make use of the non-zero density of already existing charge carriers. In addition to the low-energy one-hole excitations of the normal state directly probed in ARPES, we predict a broad and doping-dependent feature associated with the low-energy tightly-bound (cc) pair. Namely, if the additional hole created by the photo-electron is in the vicinity of an existing magnetic polaron, i.e. (sc), this state is generically expected to overlap with the tightly bound (cc) pair, see Figure 7. Owing to the two-body nature of the created excitation, constituted by the (cc) pair and a hole-type excitation ($\bar{\text{sc}}$) in the normal state, energy and momentum can be distributed and give rise to a two-body $(\bar{\text{sc}}) + (\text{cc})$ continuum.

The shape of the broad $(\bar{\text{sc}}) + (\text{cc})$ feature follows from the known dispersion relations $\varepsilon_{\text{sc}}(\mathbf{p})$ (see e.g. [134]) of the (sc) and $\varepsilon_{\text{cc}}(\mathbf{p}) = -J(\cos(p_x) + \cos(p_y) - 2) + \Delta E_{m_4}$ [50] of the (cc) constituents. Using momentum conservation we predicted a contribution to the ARPES spectrum at momentum \mathbf{k} and energy ω ,

$$A_{\bar{\text{sc}}+\text{cc}}(\mathbf{k}, \omega) = \int \frac{d^2 \mathbf{p}}{(2\pi)^2} n^F(\varepsilon_{\text{sc}}(\mathbf{p}) - \mu) \mathcal{R}(\mathbf{k}, \mathbf{p}) \times \delta(\omega + \varepsilon_{\text{sc}}(\mathbf{p}) - \mu - \varepsilon_{\text{cc}}(\mathbf{k} + \mathbf{p})), \quad (13)$$

where $n^F(\varepsilon)$ is the Fermi-Dirac distribution and $\mathcal{R}(\mathbf{k}, \mathbf{p})$ includes matrix elements reflecting the microscopic structure of (sc) and (cc) constituents. The matrix elements $\mathcal{R}(\mathbf{k}, \mathbf{p})$ can be approximated using the truncated basis technique of the (sc) and (cc) channel.

Altogether, the combination of several factors lead to a very weak, estimated signal of about 10^{-3} relative to the quasiparticle peak at the Fermi energy: (i) The signal depends on the hole density, which is small in the regime of interest, (ii) the coupling matrix elements are suppressed for the momenta \mathbf{k} , which probe (cc) state at total momentum $\mathbf{Q} = \mathbf{0}, \mathbf{\pi}$, and (iii) the dispersion relation of the (cc) channel yields a broad and flat signal distributing the spectral weight.

-
- [1] C. Chin, R. Grimm, P. Julienne, and E. Tiesinga, “Feshbach resonances in ultracold gases,” *Reviews of Modern Physics* **82**, 1225–1286 (2010).
 - [2] M. Sidler, P. Back, O. Cotlet, A. Srivastava, T. Fink, M. Kroner, E. Demler, and A. Imamoglu, “Fermi polaron-polaritons in charge-tunable atomically thin semiconductors,” *Nature Physics* **13**, 255–261 (2016).
 - [3] I. Schwartz, Y. Shimazaki, C. Kuhlenkamp, K. Watanabe, T. Taniguchi, M. Kroner, and A. Imamoglu, “Electrically tunable Feshbach resonances in twisted bilayer semiconductors,” *Science* **374**, 336–340 (2021).
 - [4] J. G. Bednorz and K. A. Müller, “Possible highTc superconductivity in the Ba-La-Cu-O system,” *Zeitschrift für Physik B Condensed Matter* **64**, 189–193 (1986).
 - [5] P. A. Lee, N. Nagaosa, and X.-G. Wen, “Doping a Mott insulator: Physics of high-temperature superconductivity,” *Rev. Mod. Phys.* **78**, 17–85 (2006).
 - [6] E. Fradkin, S. A. Kivelson, and J. M. Tranquada, “Colloquium: Theory of intertwined orders in high temperature superconductors,” *Reviews of Modern Physics* **87**, 457–482 (2015).
 - [7] B. Keimer, S. A. Kivelson, M. R. Norman, S. Uchida, and J. Zaanen, “From quantum matter to high-temperature superconductivity in copper oxides,” *Nature* **518**, 179–186 (2015).
 - [8] C. Proust and L. Taillefer, “The Remarkable Underlying Ground States of Cuprate Superconductors,” *Annual Review of Condensed Matter Physics* **10**, 409–429 (2019).
 - [9] J. Bardeen, L. N. Cooper, and J. R. Schrieffer, “Theory of Superconductivity,” *Physical Review* **108**, 1175–1204 (1957).
 - [10] P. W. Anderson, “Is There Glue in Cuprate Superconductors?” *Science* **316**, 1705–1707 (2007).

- [11] S. M. O'Mahony, W. Ren, W. Chen, Y. X. Chong, X. Liu, H. Eisaki, S. Uchida, M. H. Hamidian, and J. C. S. Davis, "On the electron pairing mechanism of copper-oxide high temperature superconductivity," *Proceedings of the National Academy of Sciences* **119** (2022).
- [12] D. J. Scalapino, "The case for $d_{x^2-y^2}$ pairing in the cuprate superconductors," *Physics Reports* **250**, 329–365 (1995).
- [13] W. Metzner, M. Salmhofer, C. Honerkamp, V. Meden, and K. Schönhammer, "Functional renormalization group approach to correlated fermion systems," *Reviews of Modern Physics* **84**, 299–352 (2012).
- [14] J. W. Loram, K. A. Mirza, J. M. Wade, J. R. Cooper, and W. Y. Liang, "The electronic specific heat of cuprate superconductors," *Physica C: Superconductivity* **235–240**, 134–137 (1994).
- [15] D. A. Wollman, D. J. V. Harlingen, W. C. Lee, D. M. Ginsberg, and A. J. Leggett, "Experimental determination of the superconducting pairing state in YBCO from the phase coherence of YBCO-Pb dc SQUIDS," *Physical Review Letters* **71**, 2134–2137 (1993).
- [16] C. J. Halboth and W. Metzner, "d-Wave Superconductivity and Pomeranchuk Instability in the Two-Dimensional Hubbard Model," *Physical Review Letters* **85**, 5162–5165 (2000).
- [17] D. Vilardi, C. Taranto, and W. Metzner, "Antiferromagnetic and d-wave pairing correlations in the strongly interacting two-dimensional Hubbard model from the functional renormalization group," *Physical Review B* **99**, 104501 (2019).
- [18] K. Miyake, S. Schmitt-Rink, and C. M. Varma, "Spin-fluctuation-mediated even-parity pairing in heavy-fermion superconductors," *Physical Review B* **34**, 6554–6556 (1986).
- [19] D. J. Scalapino, E. Loh, and J. E. Hirsch, "d-wave pairing near a spin-density-wave instability," *Physical Review B* **34**, 8190–8192 (1986).
- [20] P. Monthoux, A. V. Balatsky, and D. Pines, "Toward a theory of high-temperature superconductivity in the antiferromagnetically correlated cuprate oxides," *Physical Review Letters* **67**, 3448–3451 (1991).
- [21] C. Brügger, F. Kämpfer, M. Moser, M. Pepe, and U.-J. Wiese, "Two-hole bound states from a systematic low-energy effective field theory for magnons and holes in an antiferromagnet," *Physical Review B* **74**, 224432 (2006).
- [22] J. R. Schrieffer, X.-G. Wen, and S.-C. Zhang, "Spin-gap mechanism of high-temperature superconductivity," *Physical Review Letters* **60**, 944–947 (1988).
- [23] W. P. Su, "Spin polarons in the two-dimensional Hubbard model: A numerical study," *Physical Review B* **37**, 9904–9906 (1988).
- [24] A. J. Millis, H. Monien, and D. Pines, "Phenomenological model of nuclear relaxation in the normal state of $\text{YBa}_2\text{Cu}_3\text{O}_7$," *Physical Review B* **42**, 167–178 (1990).
- [25] J. Schmalian, D. Pines, and B. Stojković, "Weak pseudogap behavior in the underdoped cuprate superconductors," *Journal of Physics and Chemistry of Solids* **59**, 1764–1768 (1998).
- [26] A. Abanov, A. V. Chubukov, and J. Schmalian, "Quantum-critical theory of the spin-fermion model and its application to cuprates: Normal state analysis," *Advances in Physics* **52**, 119–218 (2003).
- [27] E. Dagotto, "Correlated electrons in high-temperature superconductors," *Reviews of Modern Physics* **66**, 763–840 (1994).
- [28] B.-X. Zheng, C.-M. Chung, P. Corboz, G. Ehlers, M.-P. Qin, R. M. Noack, H. Shi, S. R. White, S. Zhang, and G. K.-L. Chan, "Stripe order in the underdoped region of the two-dimensional Hubbard model," *Science* **358**, 1155–1160 (2017).
- [29] T. Schäfer, N. Wentzell, F. Šimkovic, Y.-Y. He, C. Hille, M. Klett, C. J. Eckhardt, B. Arzhang, V. Harkov, F.-M. L. Régent, A. Kirsch, Y. Wang, A. J. Kim, E. Kozik, E. A. Stepanov, A. Kauch, S. Andergassen, P. Hansmann, D. Rohe, Y. M. Vilk, J. P. LeBlanc, S. Zhang, A.-M. Tremblay, M. Ferrero, O. Parcollet, and A. Georges, "Tracking the Footprints of Spin Fluctuations: A Multi-Method, MultiMessenger Study of the Two-Dimensional Hubbard Model," *Physical Review X* **11**, 011058 (2021).
- [30] M. Qin, C.-M. Chung, H. Shi, E. Vitali, C. Hubig, U. Schollwöck, S. R. White, and S. Z. and, "Absence of Superconductivity in the Pure Two-Dimensional Hubbard Model," *Physical Review X* **10** (2020).
- [31] S. Jiang, D. J. Scalapino, and S. R. White, "Ground-state phase diagram of the t - t' - J model," *Proceedings of the National Academy of Sciences* **118** (2021).
- [32] A. Wietek, Y.-Y. He, S. R. White, A. Georges, and E. M. Stoudenmire, "Stripes, Antiferromagnetism, and the Pseudogap in the Doped Hubbard Model at Finite Temperature," *Physical Review X* **11**, 031007 (2021).
- [33] M. Qin, T. Schäfer, S. Andergassen, P. Corboz, and E. Gull, "The Hubbard Model: A Computational Perspective," *Annual Review of Condensed Matter Physics* **13**, 275–302 (2022).
- [34] H. Xu, C.-M. Chung, M. Qin, U. Schollwöck, S. R. White, and S. Zhang, "Coexistence of superconductivity with partially filled stripes in the Hubbard model," (2023), arXiv:2303.08376.
- [35] P. W. Anderson, "The Resonating Valence Bond State in La_2CuO_4 and Superconductivity," *Science* **235**, 1196–1198 (1987).
- [36] T. Senthil, S. Sachdev, and M. Vojta, "Fractionalized Fermi Liquids," *Physical Review Letters* **90**, 216403 (2003).
- [37] S. Sachdev, "Colloquium: Order and quantum phase transitions in the cuprate superconductors," *Reviews of Modern Physics* **75**, 913–932 (2003).
- [38] S. Sachdev and D. Chowdhury, "The novel metallic states of the cuprates: Topological Fermi liquids and strange metals," *Progress of Theoretical and Experimental Physics* **2016**, 12C102 (2016).
- [39] S. Sachdev, "Topological order, emergent gauge fields, and Fermi surface reconstruction," *Rep. Prog. Phys.* **82**, 014001 (2019).
- [40] Y. J. Uemura, L. P. Le, G. M. Luke, B. J. Sternlieb, W. D. Wu, J. H. Brewer, T. M. Riseman, C. L. Seaman, M. B. Maple, M. Ishikawa, D. G. Hinks, J. D. Jorgensen, G. Saito, and H. Yamochi, "Basic similarities among cuprate, bismuthate, organic, Chevrel-phase, and heavy-fermion superconductors shown by penetration-depth measurements," *Physical Review Letters* **66**, 2665–2668 (1991).
- [41] V. J. Emery and S. A. Kivelson, "Importance of phase fluctuations in superconductors with small superfluid density," *Nature* **374**, 434–437 (1995).
- [42] J. Corson, R. Mallozzi, J. Orenstein, J. N. Eckstein, and I. Bozovic, "Vanishing of phase coherence in underdoped

- $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$,” *Nature* **398**, 221–223 (1999).
- [43] J. Stajic, A. Iyengar, K. Levin, B. R. Boyce, and T. R. Lemberger, “Cuprate pseudogap: Competing order parameters or precursor superconductivity,” *Physical Review B* **68**, 024520 (2003).
- [44] N. Bergeal, J. Lesueur, M. Aprili, G. Faini, J. P. Contour, and B. Leridon, “Pairing fluctuations in the pseudogap state of copper-oxide superconductors probed by the Josephson effect,” *Nature Physics* **4**, 608–611 (2008).
- [45] P. Zhou, L. Chen, Y. Liu, I. Sochnikov, A. T. Bollinger, M.-G. Han, Y. Zhu, X. He, I. Božović, and D. Natelson, “Electron pairing in the pseudogap state revealed by shot noise in copper oxide junctions,” *Nature* **572**, 493–496 (2019).
- [46] P. Nozières and S. Schmitt-Rink, “Bose condensation in an attractive fermion gas: From weak to strong coupling superconductivity,” *Journal of Low Temperature Physics* **59**, 195–211 (1985).
- [47] A. J. Leggett, “Diatomc molecules and cooper pairs,” in *Modern Trends in the Theory of Condensed Matter*, edited by A. Pękalski and J. A. Przystawa (Springer Berlin Heidelberg, Berlin, Heidelberg, 1980) pp. 13–27.
- [48] M. Randeria, J.-M. Duan, and L.-Y. Shieh, “Bound states, Cooper pairing, and Bose condensation in two dimensions,” *Physical Review Letters* **62**, 981–984 (1989).
- [49] Q. Chen, Z. Wang, and R. B. K. Levin, “When Superconductivity Crosses Over: From BCS to BEC,” (2022), arXiv:2208.01774.
- [50] A. Bohrdt, E. Demler, and F. Grusdt, “Dichotomy of heavy and light pairs of holes in the t-J model,” *Nature Communications* **14** (2023).
- [51] K. M. Shen, F. Ronning, D. H. Lu, F. Baumberger, N. J. C. Ingle, W. S. Lee, W. Meevasana, Y. Kohsaka, M. Azuma, M. Takano, H. Takagi, and Z.-X. Shen, “Nodal Quasiparticles and Antinodal Charge Ordering in $\text{Ca}_{2-x}\text{Na}_x\text{CuO}_2\text{Cl}_2$,” *Science* **307**, 901–904 (2005).
- [52] K. Kurokawa, S. Isono, Y. Kohama, S. Kunisada, S. Sakai, R. Sekine, M. Okubo, M. D. Watson, T. K. Kim, C. Cacho, S. Shin, T. Tohyama, K. Tokiwa, and T. Kondo, “Unveiling phase diagram of the lightly doped high-Tc cuprate superconductors with disorder removed,” *Nature Communications* **14** (2023).
- [53] S. Badoux, W. Tabis, F. Laliberté, G. Grissonnanche, B. Vignolle, D. Vignolles, J. Béard, D. A. Bonn, W. N. Hardy, R. Liang, N. Doiron-Leyraud, L. Taillefer, and C. Proust, “Change of carrier density at the pseudogap critical point of a cuprate superconductor,” *Nature* **531**, 210–214 (2016).
- [54] L. Bulaevski, É. Nagaev, and D. Khomskii, “A New Type of Auto-localized State of a Conduction Electron in an Antiferromagnetic Semiconductor,” *Journal of Experimental and Theoretical Physics - J EXP THEOR PHYS* **27** (1968).
- [55] W. F. Brinkman and T. M. Rice, “Single-Particle Excitations in Magnetic Insulators,” *Physical Review B* **2**, 1324–1338 (1970).
- [56] S. A. Trugman, “Interaction of holes in a Hubbard antiferromagnet and high-temperature superconductivity,” *Phys. Rev. B* **37**, 1597–1603 (1988).
- [57] C. L. Kane, P. A. Lee, and N. Read, “Motion of a single hole in a quantum antiferromagnet,” *Phys. Rev. B* **39**, 6880–6897 (1989).
- [58] S. Sachdev, “Hole motion in a quantum Néel state,” *Physical Review B* **39**, 12232–12247 (1989).
- [59] J. van den Brink and O. P. Sushkov, “Single-hole Green’s functions in insulating copper oxides at nonzero temperature,” *Physical Review B* **57**, 3518–3524 (1998).
- [60] S. A. Trugman, “Spectral function of a hole in a Hubbard antiferromagnet,” *Physical Review B* **41**, 892–895 (1990).
- [61] K. J. von Szczepanski, P. Horsch, W. Stephan, and M. Ziegler, “Single-particle excitations in a quantum antiferromagnet,” *Physical Review B* **41**, 2017–2029 (1990).
- [62] C.-H. Chen, H.-B. Schüttler, and A. J. Fedro, “Hole excitation spectra in cuprate superconductors: A comparative study of single- and multiple-band strong-coupling theories,” *Physical Review B* **41**, 2581–2584 (1990).
- [63] M. D. Johnson, C. Gros, and K. J. von Szczepanski, “Geometry-controlled conserving approximations for the t - J model,” *Physical Review B* **43**, 11207–11239 (1991).
- [64] D. Poilblanc, T. Ziman, H. J. Schulz, and E. Dagotto, “Dynamical properties of a single hole in an antiferromagnet,” *Physical Review B* **47**, 14267–14279 (1993).
- [65] D. Poilblanc, H. J. Schulz, and T. Ziman, “Single-hole spectral density in an antiferromagnetic background,” *Physical Review B* **47**, 3268–3272 (1993).
- [66] E. Dagotto, R. Joynt, A. Moreo, S. Bacci, and E. Gagliano, “Strongly correlated electronic systems with one hole: Dynamical properties,” *Physical Review B* **41**, 9049–9073 (1990).
- [67] Z. Liu and E. Manousakis, “Spectral function of a hole in t - J model,” *Physical Review B* **44**, 2414–2417 (1991).
- [68] B. O. Wells, Z.-X. Shen, A. Matsuura, D. M. King, M. A. Kastner, M. Greven, and R. J. Birgeneau, “ E versus k Relations and Many Body Effects in the Model Insulating Copper Oxide $\text{Sr}_2\text{CuO}_2\text{Cl}_2$,” *Physical Review Letters* **74**, 964–967 (1995).
- [69] J. Koepsell, J. Vijayan, P. Sompét, F. Grusdt, T. A. Hilker, E. Demler, G. Salomon, I. Bloch, and C. Gross, “Imaging magnetic polarons in the doped Fermi-Hubbard model,” *Nature* **572**, 358–362 (2019).
- [70] M. M. Mohan and N. Kumar, “Spin singlet d wave hole pairing in the new high-Tc superconductors,” *Journal of Physics C: Solid State Physics* **20**, L527–L531 (1987).
- [71] B. I. Shraiman and E. D. Siggia, “Two-particle excitations in antiferromagnetic insulators,” *Physical Review Letters* **60**, 740–743 (1988).
- [72] E. Dagotto, J. Riera, and A. P. Young, “Dynamical pair susceptibilities in the t - J and Hubbard models,” *Physical Review B* **42**, 2347–2352 (1990).
- [73] D. Poilblanc, J. Riera, and E. Dagotto, “d-wave bound state of holes in an antiferromagnet,” *Physical Review B* **49**, 12318–12321 (1994).
- [74] S. R. White and D. J. Scalapino, “Hole and pair structures in the t - J model,” *Physical Review B* **55**, 6504–6517 (1997).
- [75] L. Vidmar and J. Bonča, “Two Holes in the t - J Model Form a Bound State for Any Nonzero J/t ,” *Journal of Superconductivity and Novel Magnetism* **26**, 2641–2645 (2013).
- [76] F. Grusdt, E. Demler, and A. Bohrdt, “Pairing of holes by confining strings in antiferromagnets,” *SciPost Physics* **14** (2023).
- [77] N. Doiron-Leyraud, C. Proust, D. LeBoeuf, J. Levallois, J.-B. Bonnemaison, R. Liang, D. A. Bonn, W. N. Hardy, and L. Taillefer, “Quantum oscillations and the Fermi

- surface in an underdoped high-T_c superconductor,” *Nature* **447**, 555–568 (2007).
- [78] J. Sous, Y. He, and S. A. Kivelson, “Absence of a BCS-BEC crossover in the cuprate superconductors,” *npj Quantum Materials* **8** (2023).
- [79] H. Feshbach, “A unified theory of nuclear reactions. II,” *Annals of Physics* **19**, 287–313 (1962).
- [80] U. Fano, “Effects of Configuration Interaction on Intensities and Phase Shifts,” *Physical Review* **124**, 1866–1878 (1961).
- [81] S. Inouye, M. R. Andrews, J. Stenger, H.-J. Miesner, D. M. Stamper-Kurn, and W. Ketterle, “Observation of Feshbach resonances in a Bose-Einstein condensate,” *Nature* **392**, 151–154 (1998).
- [82] K. Slagle and L. Fu, “Charge transfer excitations, pair density waves, and superconductivity in moiré materials,” *Physical Review B* **102**, 235423 (2020).
- [83] V. Crépel and L. Fu, “New mechanism and exact theory of superconductivity from strong repulsive interaction,” *Science Advances* **7** (2021).
- [84] V. Crépel, D. Guerci, J. Cano, J. Pixley, and A. Millis, “Topological Superconductivity in Doped Magnetic Moiré Semiconductors,” *Physical Review Letters* **131**, 056001 (2023).
- [85] H. Lange, L. Homeier, E. Demler, U. Schollwöck, A. Bohrdt, and F. Grusdt, “Pairing dome from an emergent Feshbach resonance in a strongly repulsive bilayer model,” (2023), arXiv:2309.13040.
- [86] H. Yang, H. Oh, and Y.-H. Zhang, “Strong pairing from doping-induced feshbach resonance and second fermi liquid through doping a bilayer spin-one mott insulator: application to la₃ni₂O₇,” (2023), arXiv:2309.15095 [cond-mat.str-el].
- [87] J. von Milczewski, X. Chen, A. Imamoglu, and R. Schmidt, “Superconductivity induced by strong electron-exciton coupling in doped atomically thin semiconductor heterostructures,” (2023), arXiv:2310.10726.
- [88] C. Zerba, C. Kuhlenkamp, A. Imamoglu, and M. Knap, “Realizing Topological Superconductivity in Tunable Bose-Fermi Mixtures with Transition Metal Dichalcogenide Heterostructures,” (2023), arXiv:2310.10720.
- [89] D. M. Newns and N. Read, “Mean-field theory of intermediate valence/heavy fermion systems,” *Advances in Physics* **36**, 799–849 (1987).
- [90] P. Coleman, “New approach to the mixed-valence problem,” *Physical Review B* **29**, 3035–3044 (1984).
- [91] P. Coleman, “Mixed valence as an almost broken symmetry,” *Physical Review B* **35**, 5072–5116 (1987).
- [92] G. Kotliar and J. Liu, “Superexchange mechanism and d-wave superconductivity,” *Phys. Rev. B* **38**, 5142–5145 (1988).
- [93] P. Bérard, D. Poilblanc, and R. Laughlin, “Evidence for composite nature of quasiparticles in the 2D $t - J$ model,” *Nuclear Physics B* **473**, 707–720 (1996).
- [94] A. Bohrdt, E. Demler, F. Pollmann, M. Knap, and F. Grusdt, “Parton theory of angle-resolved photoemission spectroscopy spectra in antiferromagnetic Mott insulators,” *Physical Review B* **102** (2020).
- [95] M. Brunner, F. F. Assaad, and A. Muramatsu, “Single-hole dynamics in the $t-J$ model on a square lattice,” *Physical Review B* **62**, 15480–15492 (2000).
- [96] A. S. Mishchenko, N. V. Prokof’ev, and B. V. Svistunov, “Single-hole spectral function and spin-charge separation in the $t-J$ model,” *Physical Review B* **64**, 033101 (2001).
- [97] E. Manousakis, “String excitations of a hole in a quantum antiferromagnet and photoelectron spectroscopy,” *Physical Review B* **75**, 035106 (2007).
- [98] A. Bohrdt, E. Demler, and F. Grusdt, “Rotational Resonances and Regge-like Trajectories in Lightly Doped Antiferromagnets,” *Physical Review Letters* **127** (2021).
- [99] L. F. Feiner, J. H. Jefferson, and R. Raimondi, “Effective single-band models for the high-T_c cuprates. I. Coulomb interactions,” *Physical Review B* **53**, 8751–8773 (1996).
- [100] Q.-H. Wang, J. H. Han, and D.-H. Lee, “Pairing near the Mott insulating limit,” *Physical Review B* **65**, 054501 (2001).
- [101] A. Greco, H. Yamase, and M. Bejas, “Plasmon excitations in layered high-T_c cuprates,” *Physical Review B* **94**, 075139 (2016).
- [102] A. Greco, H. Yamase, and M. Bejas, “Origin of high-energy charge excitations observed by resonant inelastic X-ray scattering in cuprate superconductors,” *Communications Physics* **2** (2019).
- [103] L. Zinni, M. Bejas, and A. Greco, “Superconductivity with and without glue and the role of the double-occupancy forbidding constraint in the $t-J-V$ model,” *Physical Review B* **103**, 134504 (2021).
- [104] M. Hepting, T. D. Boyko, V. Zimmermann, M. Bejas, Y. E. Suyolcu, P. Puphal, R. J. Green, L. Zinni, J. Kim, D. Casa, M. H. Upton, D. Wong, C. Schulz, M. Bartkowiak, K. Habicht, E. Pomjakushina, G. Cristiani, G. Logvenov, M. Minola, H. Yamase, A. Greco, and B. Keimer, “Evolution of plasmon excitations across the phase diagram of the cuprate superconductor la_{2-x}sr_xcuo₄,” *Physical Review B* **107**, 214516 (2023).
- [105] I. Battisti, V. Fedoseev, K. M. Bastiaans, A. de la Torre, R. S. Perry, F. Baumberger, and M. P. Allan, “Poor electronic screening in lightly doped Mott insulators observed with scanning tunneling microscopy,” *Physical Review B* **95**, 235141 (2017).
- [106] Q. Chen, Z. Wang, and R. B. K. Levin, “Test for BCS-BEC Crossover in the Cuprate Superconductors,” (2023), arXiv:2307.08611.
- [107] A. Auerbach, *Interacting Electrons and Quantum Magnetism* (Springer New York, 1994).
- [108] F. Grusdt, M. Kánsz-Nagy, A. Bohrdt, C. S. Chiu, G. Ji, M. Greiner, D. Greif, and E. Demler, “Parton Theory of Magnetic Polarons: Mesonic Resonances and Signatures in Dynamics,” *Phys. Rev. X* **8**, 011046 (2018).
- [109] L. Homeier, P. Bermes, and F. Grusdt, “Scattering theory of mesons in doped antiferromagnetic Mott insulators: Multichannel perspective and Feshbach resonance,” (*in preparation*, 2023).
- [110] O. K. Andersen, A. I. Liechtenstein, O. Jepsen, and F. Paulsen, “LDA energy bands, low-energy hamiltonians, t' , t'' , t_{\perp} (k), and J_{\perp} ,” *Journal of Physics and Chemistry of Solids* **56**, 1573–1591 (1995).
- [111] M. Hirayama, Y. Yamaji, T. Misawa, and M. Imada, “*Ab initio* effective Hamiltonians for cuprate superconductors,” *Physical Review B* **98**, 134501 (2018).
- [112] J. Mesot, M. R. Norman, H. Ding, M. Randeria, J. C. Campuzano, A. Paramekanti, H. M. Fretwell, A. Kaminski, T. Takeuchi, T. Yokoya, T. Sato, T. Takahashi, T. Mochiku, and K. Kadokawa, “Superconducting Gap Anisotropy and Quasiparticle Interactions: A

- Doping Dependent Photoemission Study," *Physical Review Letters* **83**, 840–843 (1999).
- [113] M. Hashimoto, I. M. Vishik, R.-H. He, T. P. Devereaux, and Z.-X. Shen, "Energy gaps in high-transition-temperature cuprate superconductors," *Nature Physics* **10**, 483–495 (2014).
- [114] J. Berakdar, "Emission of correlated electron pairs following single-photon absorption by solids and surfaces," *Physical Review B* **58**, 9808–9816 (1998).
- [115] F. Mahmood, T. Devereaux, P. Abbamonte, and D. K. Morr, "Distinguishing finite-momentum superconducting pairing states with two-electron photoemission spectroscopy," *Physical Review B* **105**, 064515 (2022).
- [116] Y. Su and C. Zhang, "Coincidence angle-resolved photoemission spectroscopy: Proposal for detection of two-particle correlations," *Physical Review B* **101**, 205110 (2020).
- [117] J. A. Sobota, Y. He, and Z.-X. Shen, "Angle-resolved photoemission studies of quantum materials," *Reviews of Modern Physics* **93**, 025006 (2021).
- [118] J. T. Anderson, R. V. Carlson, and A. M. Goldman, "Pair tunneling as a probe of order-parameter fluctuations in superconductors: Zero magnetic field effects," *Journal of Low Temperature Physics* **8**, 29–46 (1972).
- [119] D. J. Scalapino, "Pair Tunneling as a Probe of Fluctuations in Superconductors," *Physical Review Letters* **24**, 1052–1055 (1970).
- [120] K. M. Bastiaans, D. Cho, T. Benschop, I. Battisti, Y. Huang, M. S. Golden, Q. Dong, Y. Jin, J. Zaanen, and M. P. Allan, "Charge trapping and super-Poissonian noise centres in a cuprate superconductor," *Nature Physics* **14**, 1183–1187 (2018).
- [121] K. M. Bastiaans, D. Chatzopoulos, J.-F. Ge, D. Cho, W. O. Tromp, J. M. van Ruitenbeek, M. H. Fischer, P. J. de Visser, D. J. Thoen, E. F. C. Driessens, T. M. Klapwijk, and M. P. Allan, "Direct evidence for Cooper pairing without a spectral gap in a disordered superconductor above T_c ," *Science* **374**, 608–611 (2021).
- [122] D. Fausti, R. I. Tobey, N. Dean, S. Kaiser, A. Dienst, M. C. Hoffmann, S. Pyon, T. Takayama, H. Takagi, and A. Cavalleri, "Light-Induced Superconductivity in a Stripe-Ordered Cuprate," *Science* **331**, 189–191 (2011).
- [123] E. G. Moon and S. Sachdev, "Underdoped cuprates as fractionalized Fermi liquids: Transition to superconductivity," *Physical Review B* **83**, 224508 (2011).
- [124] S. Chatterjee and S. Sachdev, "Fractionalized Fermi liquid with bosonic chargons as a candidate for the pseudogap metal," *Physical Review B* **94**, 205117 (2016).
- [125] M. Punk, A. Allais, and S. Sachdev, "Quantum dimer model for the pseudogap metal," *Proceedings of the National Academy of Sciences* **112**, 9552–9557 (2015).
- [126] M. Christos, Z.-X. Luo, H. Shackleton, Y.-H. Zhang, M. S. Scheurer, and S. Sachdev, "A model of d-wave superconductivity, antiferromagnetism, and charge order on the square lattice," *Proceedings of the National Academy of Sciences* **120** (2023).
- [127] A. Bohrdt, L. Homeier, C. Reinmoser, E. Demler, and F. Grusdt, "Exploration of doped quantum magnets with ultracold atoms," *Annals of Physics* **435**, 168651 (2021).
- [128] H. Lange, L. Homeier, E. Demler, U. Schollwöck, F. Grusdt, and A. Bohrdt, "Feshbach resonance in a strongly repulsive bilayer model: a possible scenario for bilayer nickelate superconductors," (2023), arXiv:2309.15843.
- [129] N. P. Armitage, F. Ronning, D. H. Lu, C. Kim, A. Damascelli, K. M. Shen, D. L. Feng, H. Eisaki, Z.-X. Shen, P. K. Mang, N. Kaneko, M. Greven, Y. Onose, Y. Taguchi, and Y. Tokura, "Doping Dependence of an n-Type Cuprate Superconductor Investigated by Angle-Resolved Photoemission Spectroscopy," *Physical Review Letters* **88**, 257001 (2002).
- [130] S. Paeckel, T. Köhler, A. Swoboda, S. R. Manmana, U. Schollwöck, and C. Hubig, "Time-evolution methods for matrix-product states," *Annals of Physics* **411**, 167998 (2019).
- [131] L. Homeier, T. J. Harris, T. Blatz, U. Schollwöck, F. Grusdt, and A. Bohrdt, "Antiferromagnetic bosonic t - J models and their quantum simulation in tweezer arrays," (2023), arXiv:2305.02322.
- [132] A. Bohrdt, Y. Wang, J. Koepsell, M. Kánašz-Nagy, E. Demler, and F. Grusdt, "Dominant Fifth-Order Correlations in Doped Quantum Antiferromagnets," *Physical Review Letters* **126** (2021).
- [133] F. Grusdt, A. Bohrdt, and E. Demler, "Microscopic spinon-chargon theory of magnetic polarons in the t - J model," *Phys. Rev. B* **99**, 224422 (2019).
- [134] G. Martinez and P. Horsch, "Spin polarons in the t - J model," *Physical Review B* **44**, 317–331 (1991).