

# **In-Field Transport Critical Currents in Superhydride Superconductors: Highly-Compressed CeH<sub>9</sub>**

Evgeny F. Talantsev<sup>1,2</sup>

<sup>1</sup>M.N. Miheev Institute of Metal Physics, Ural Branch, Russian Academy of Sciences,  
18, S. Kovalevskoy St., Ekaterinburg, 620108, Russia

<sup>2</sup>NANOTECH Centre, Ural Federal University, 19 Mira St., Ekaterinburg, 620002,  
Russia

## **Abstract**

Experimental discovery of near-room-temperature superconductivity in highly compressed hydrogen sulphate started a new era in superconductivity. To date, researchers have made the discovery of dozens of superconducting hydride phases with transition temperatures above LN<sub>2</sub>. While the primary focus of the research in this field is to determine fundamental superconducting parameters of these superconductors, here we revealed primary applied property of these superconductors which is the field dependence of transport critical current,  $I_c(B,T)$ . We analysed reported  $V(I)$  curves for a highly compressed CeH<sub>9</sub> sample with  $T_c = 70$  K, and showed that this hydride exhibits practically identical  $I_c(B,T)$  to HTS 1G-wire (Bi,Pb)<sub>2</sub>Sr<sub>2</sub>Ca<sub>2</sub>Cu<sub>3</sub>O<sub>11</sub>. Additionally, we demonstrated that the n-value in CeH<sub>9</sub> superhydride follows a nearly identical dependence on critical current, as observed in Nb<sub>3</sub>Sn conductors.

# In-Field Transport Critical Currents in Superhydride Superconductors: Highly-Compressed CeH<sub>9</sub>

## I. Introduction

Experimental studies of near-room-temperature superconductors started after pivotal discovery of the superconducting state above 200 K in highly-compressed sulfur hydride by Drozdov *et al* [1] in 2015. To date, dozens of highly-compressed high-temperature superconducting hydrides have been discovered [2]–[12]. While fundamental properties/parameters of the superconducting state of the superhydrides (which are the lower critical field [1], [13], the upper critical field [14]–[17], the charge carriers density [14], [16], the London penetration depth [1], [13], [18], the coherence length [14], [16], [17], the Ginzburg-Landau parameter [13], [18]–[20], the Ginzburg-Levanyuk number [18], the energy gap [16], [21], [22], specific heat jump at the transition temperature [21], [22], the self-field critical current density [16] have been measured/extracted from experimental data), primary applied property of any superconductors, which is in-field transport critical current,  $I_c(B, T)$ , and its density,  $J_c(B, T)$ , are remaining to be practically unknown.

It should be noted that many experimental techniques utilized to measure temperature dependent superconducting gap,  $\Delta(T)$ , in low-temperature and high-temperature superconductors [23] are not applicable for highly compressed materials. However, the amplitude of the ground state energy gap,  $\Delta(0)$ , can be extracted from the self-field critical current density,  $J_c(sf, T)$  [24]–[27], and the upper critical field  $B_{c2}(T)$  [22], [28]. Until recent report by Semenok *et al* [15], available  $I_c(B, T)$  and  $J_c(B, T)$  data for superhydrides were limited by the values measured at  $T \sim T_c$  [7], [9].

CeH<sub>9</sub> phase exhibits maximal transition temperature of  $T_c = 102$  K at applied pressure of  $P = 130$  GPa [15]. In this study we analyzed  $V(I)$  curves measured in highly compressed CeH<sub>9</sub> sample ( $P = 125$  GPa,  $T_c = 70$  K) by Semenok *et al* [15]. It should be noted that

Semenok *et al* [14] used four-probe AC method with the excitation current of 5-10 mA to measure  $V(I)$  curves, while in the applied superconductivity many research groups utilize DC transport current measurements to study HTS 2G-wires [29]. We made a comparison of the derived  $I_c(B,T)$  data based on the electric field criterion of  $E_c = 1 \mu\text{V}/\text{cm}$  with the field dependent critical current measured in well-studied superconductors.

In this study we showed that:

1. Reduced critical currents,  $I_c(B,T)/I_c(B=1 \text{ Tesla}, T)$ , in CeH<sub>9</sub> ( $P = 125 \text{ GPa}$ ) and 1G-wire (Bi,Pb)<sub>2</sub>Sr<sub>2</sub>Ca<sub>2</sub>Cu<sub>3</sub>O<sub>11</sub> are practically identical;
2. The dependence of  $n$ -values from critical current,  $n(I_c)$ , in CeH<sub>9</sub> ( $P = 125 \text{ GPa}$ ) and Nb<sub>3</sub>Sn are nearly identical.

## II. Utilized model

Critical currents can be derived by the fit of measured  $V(I)$  (or  $E(I)$ ) curves to the power law[30]–[32]:

$$E(I) = E_c \times \left(\frac{I}{I_c}\right)^n, \quad (1)$$

where  $E_c$  is the electric field criterion, and  $n$  is the so-called  $n$ -value which is one of the characteristics of the transition from dissipative-less to dissipative regimes of the transport current flow in superconductors. To utilize widely used the electric field criterion value of  $E_c = 1 \mu\text{V}/\text{cm}$  [33]–[35] for CeH<sub>9</sub>, the following approach was used.

Considering geometrical arrangements of experiments in the report by Semenok *et al* [15], we approximated the distance between voltage taps (electrodes) in diamond anvil cell (DAC) as  $l = 50 \mu\text{m}$ . At the same time, the noise of electronics of the measured  $V(I)$  curves [15] was at the same level ( $< 10^{-7} \text{ V}$ ) as it is in many other transport critical current measuring systems [36]–[42]. Based on that, we fitted measured  $V(I)$  curves [15] to the equation:

$$V(I) = V_0 + V_c \times \left(\frac{I}{I_{c,V}}\right)^n, \quad (2)$$

where  $V_0$  is an instrumental offset, and  $V_c = 1 \mu V$ . Derived  $I_{c,V}$  was recalculated to the  $I_c$  by the equation:

$$I_c = \left(\frac{50 \mu m}{1 cm}\right)^{\frac{1}{n}} \times I_{c,V}. \quad (3)$$


Theoretical interpretation of  $n$ -value in polycrystalline superconductors can be found elsewhere [30]–[32], [43].

### III. Results and Discussion

Fits of several  $V(I)$  curves of CeH<sub>9</sub> ( $P = 125$  GPa) reported by Semenok *et al* [15] to Eq. 2 are shown in Fig. 1. We analyzed reported  $V(I)$  curves measured for CeH<sub>9</sub> sample with  $T_c = 70$  K. All performed fits (included fits which are not shown in Fig. 1) have a high quality (the coefficient of determination ( $R$ -Squared)) for each curve is better than  $R = 0.972$ , and for majority of the fits  $R > 0.99$ ).


Derived  $I_c(B, T=55K)$  dataset (in the reduced  $I_c(B, T)/I_c(B=0.95 \text{ Tesla}, T)$  form) are shown in Fig. 2.

It should be noted that CeH<sub>9</sub> samples studied by Semenok *et al* [15] were polycrystalline samples (which can be confirmed by XRD data presented in the study [15]) with  $T_c = 70$ -102 K. Based on that, it is useful to make a comparison of the deduced  $I_c(B, T)/I_c(B=0.95 \text{ Tesla}, T)$  with the  $I_c(B, T)/I_c(B=1.0 \text{ Tesla}, T)$  measured in HTS 1G-wires (Bi,Pb)<sub>2</sub>Sr<sub>2</sub>Ca<sub>2</sub>Cu<sub>3</sub>O<sub>11</sub>, which are also polycrystalline samples with  $T_c$  in the same ballpark ( $I_c(B, T)$  data for 1G-wires reported by Wimbush and Strickland [29]). This comparison is shown in Fig. 2, where nearly identical in-field transport current dependence CeH<sub>9</sub> ( $P = 125$  GPa) and two HTS 1G-wires can be seen.

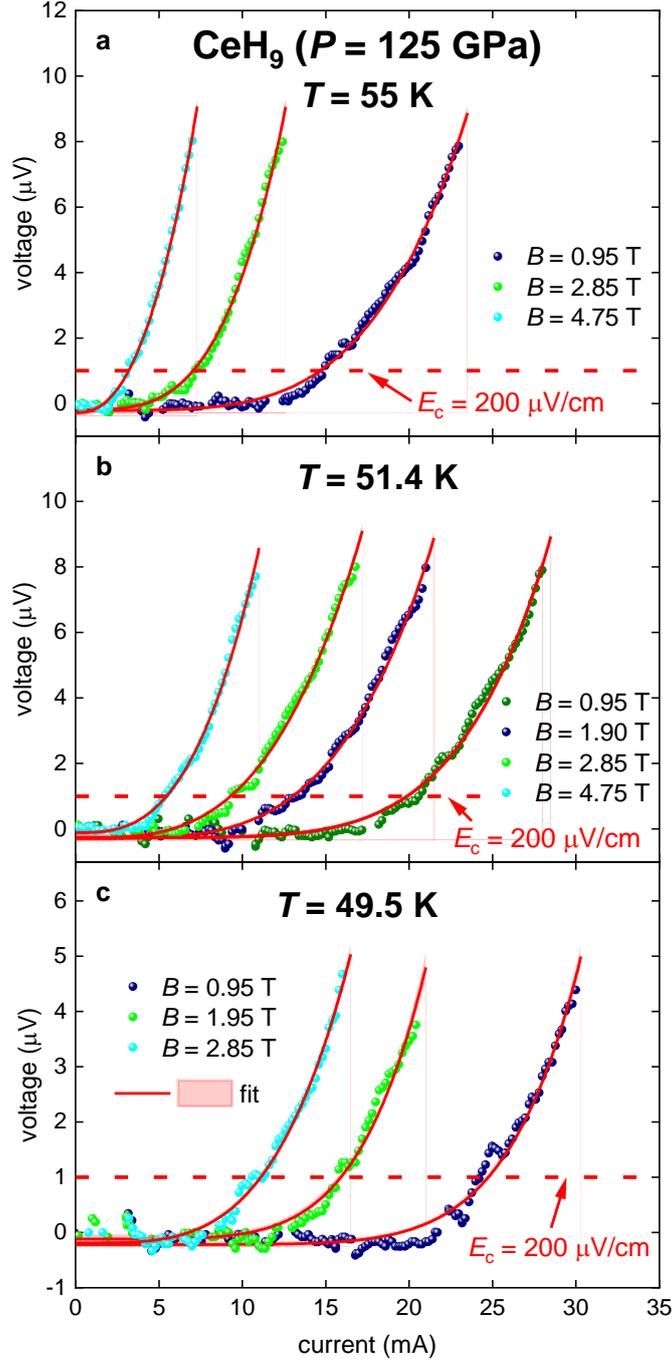


**Figure 1.** Fits of the  $V(I)$  curves measured in  $\text{CeH}_9$  ( $P = 125$  GPa) by Semenok *et al* [15] to Eq. 2. Raw  $V(I)$  datasets are from Figure S6 [15]. Utilized voltage criterion of  $V_c = 1$  mV (or field criterion  $E_c = 200$  mV/cm) is shown. The pink shadow areas indicate 95% confidence bands for the fit to Eq. 2.

The analysis of  $n$ -value (Eq. 1) this is a standard practice [44]–[46] in superconductors characterization. In Fig. 3 we showed field dependence of the  $n$ -values for  $\text{CeH}_9$  ( $P = 125$  GPa) and two HTS 1G-wires.

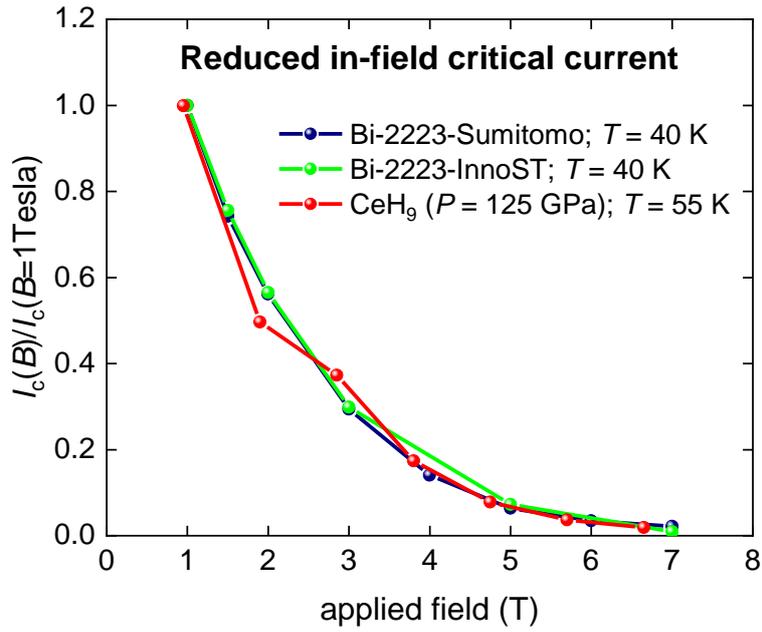

**Figure 2.** Reduced transport in-field critical currents (defined by  $E_c = 1 \mu\text{V}/\text{cm}$  criterion) for polycrystalline superconductors. Blue – Sumitomo 1G-HTS wire (data by Wimbush and Strickland [29]). Green – InnoST 1G-HTS wire (data by Wimbush and Strickland [29]). Red - CeH<sub>9</sub> ( $P = 125$  GPa), raw  $V(I)$  datasets reported by Semenok *et al* [15] in their Figure S6.

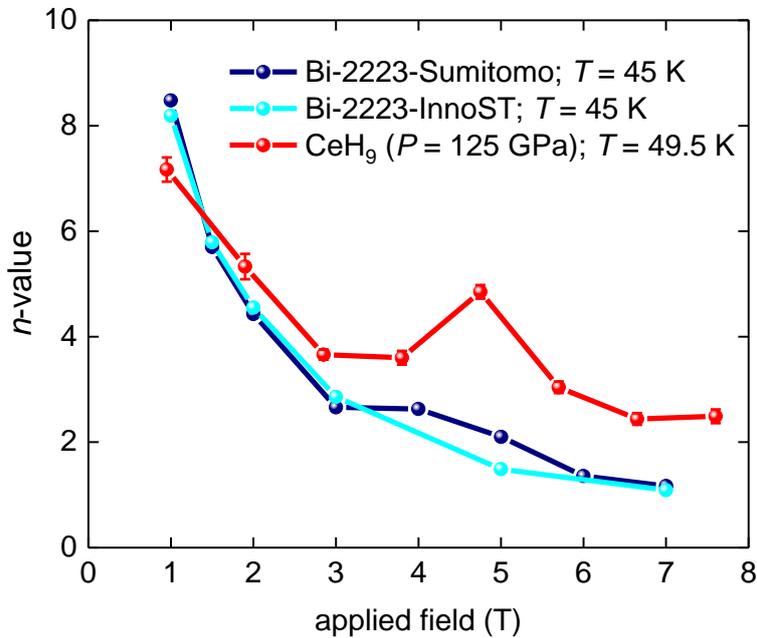


**Figure 3.** Field dependence of  $N$ -values for 1G-HTS wires (data by Wimbush and Strickland [29]) and CeH<sub>9</sub> ( $P = 125$  GPa) (raw  $V(I)$  datasets reported by Semenok *et al* [15]).

Further analysis is shown in Fig. 4, where the  $n(I_c)$  dependences were fitted to the power law [45]:

$$n(I_c) = 1 + a \times (I_c)^s \quad (4)$$

where  $a$  and  $s$  are free-fitting parameters. More details about parameter  $s$  can be found elsewhere [47].

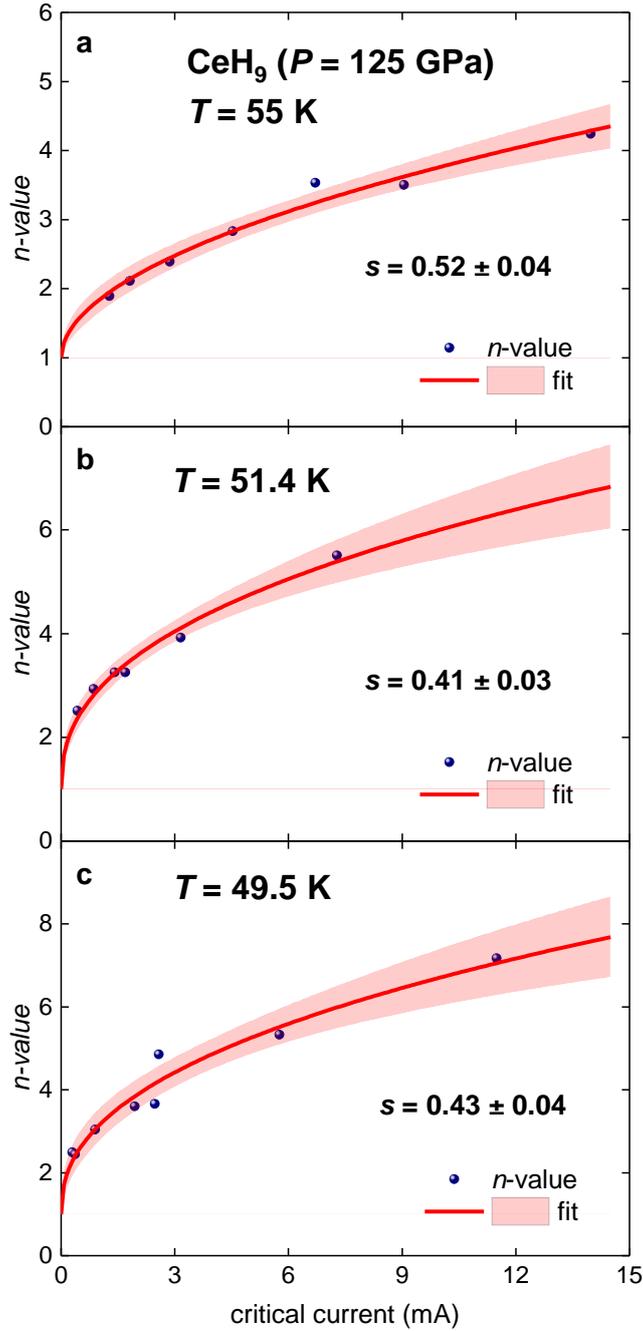

**Figure 4.**  $n(I_c)$  dependences and data fits to Eq. 4 for  $\text{CeH}_9$  ( $P = 125$  GPa) (raw  $V(I)$  datasets reported by Semenok *et al* [15]). The pink shadow areas indicate 95% confidence bands for the fit to Eq. 4.

It is important to note that deduced  $0.41 \leq s \leq 0.52$  (Fig. 4) for CeH<sub>9</sub> ( $P = 125$  GPa) are in the same ballpark values for reported by Taylor and Hampshire [45] for polycrystalline Nb<sub>3</sub>Sn wires ( $0.38 \leq s \leq 0.44$ ).

#### **IV. Conclusions**

In this study we analyzed the only available in-field high-current  $V(I)$  curves measured in highly-compressed hydrides. In the result, we derived the in-field transport critical current  $I_c(B,T)$  for CeH<sub>9</sub> ( $P = 125$  GPa) hydride and showed that its field dependence is similar to one measured in polycrystalline HTS 1G-wires (Bi,Pb)<sub>2</sub>Sr<sub>2</sub>Ca<sub>2</sub>Cu<sub>3</sub>O<sub>11</sub>. We also showed that the power-law exponent  $s$  in the dependence of the  $n$ -value vs the critical current is close to the power-law exponent in Nb<sub>3</sub>Sn.

#### **Acknowledgement**

The author thanks D. V. Semenov (Center for High Pressure Science and Technology Advanced Research, Beijing, PRC) and all co-workers of Ref. [15] for making their experimental data on CeH<sub>9</sub> superconductor freely available online prior the publication of their paper.

The author thanks financial support provided by the Ministry of Science and Higher Education of Russia (theme “Pressure” No. 122021000032-5). The research funding from the Ministry of Science and Higher Education of the Russian Federation (Ural Federal University Program of Development within the Priority-2030 Program) is gratefully acknowledged by the author.

#### **Data availability statement**

The data that support the findings of this study are available from the author upon reasonable request.

## Declaration of interests

The author declares that he has no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

## References

- [1] A. P. Drozdov, M. I. Erements, I. A. Troyan, V. Ksenofontov, and S. I. Shylin, “Conventional superconductivity at 203 kelvin at high pressures in the sulfur hydride system,” *Nature*, vol. 525, no. 7567, pp. 73–76, Sep. 2015, doi: 10.1038/nature14964.
- [2] A. P. Drozdov *et al.*, “Superconductivity at 250 K in lanthanum hydride under high pressures,” *Nature*, vol. 569, no. 7757, pp. 528–531, May 2019, doi: 10.1038/s41586-019-1201-8.
- [3] M. Somayazulu *et al.*, “Evidence for Superconductivity above 260 K in Lanthanum Superhydride at Megabar Pressures,” *Phys Rev Lett*, vol. 122, no. 2, p. 027001, Jan. 2019, doi: 10.1103/PhysRevLett.122.027001.
- [4] D. V. Semenov *et al.*, “Superconductivity at 161 K in thorium hydride ThH<sub>10</sub>: Synthesis and properties,” *Materials Today*, vol. 33, no. xx, pp. 36–44, Mar. 2020, doi: 10.1016/j.mattod.2019.10.005.
- [5] D. Sun *et al.*, “High-temperature superconductivity on the verge of a structural instability in lanthanum superhydride,” *Nat Commun*, vol. 12, no. 1, p. 6863, Nov. 2021, doi: 10.1038/s41467-021-26706-w.
- [6] P. Kong *et al.*, “Superconductivity up to 243 K in the yttrium-hydrogen system under high pressure,” *Nat Commun*, vol. 12, no. 1, p. 5075, Aug. 2021, doi: 10.1038/s41467-021-25372-2.
- [7] I. A. Troyan *et al.*, “Anomalous High-Temperature Superconductivity in YH<sub>6</sub>,” *Advanced Materials*, vol. 33, no. 15, p. 2006832, Apr. 2021, doi: 10.1002/adma.202006832.
- [8] W. Chen *et al.*, “High-Temperature Superconducting Phases in Cerium Superhydride with a  $T_c$  up to 115 K below a Pressure of 1 Megabar,” *Phys Rev Lett*, vol. 127, no. 11, p. 117001, Sep. 2021, doi: 10.1103/PhysRevLett.127.117001.
- [9] D. V. Semenov *et al.*, “Superconductivity at 253 K in lanthanum–yttrium ternary hydrides,” *Materials Today*, vol. 48, no. xx, pp. 18–28, Sep. 2021, doi: 10.1016/j.mattod.2021.03.025.
- [10] J. Bi *et al.*, “Giant enhancement of superconducting critical temperature in substitutional alloy (La,Ce)H<sub>9</sub>,” *Nat Commun*, vol. 13, no. 1, p. 5952, Oct. 2022, doi: 10.1038/s41467-022-33743-6.
- [11] Y. Song *et al.*, “Stoichiometric Ternary Superhydride LaBeH<sub>8</sub> as a New Template for High-Temperature Superconductivity at 110 K under 80 GPa,” *Phys Rev Lett*, vol. 130, no. 26, p. 266001, Jun. 2023, doi: 10.1103/PhysRevLett.130.266001.
- [12] W. Cai *et al.*, “Superconductivity above 180 K in Ca-Mg Ternary Superhydrides at Megabar Pressures,” Dec. 2023. *arXiv:2312.06090* (2023); <https://doi.org/10.48550/arXiv.2312.06090>
- [13] V. S. Minkov *et al.*, “Magnetic field screening in hydrogen-rich high-temperature superconductors,” *Nat Commun*, vol. 13, no. 1, p. 3194, Jun. 2022, doi: 10.1038/s41467-022-30782-x.
- [14] S. Mozaffari *et al.*, “Superconducting phase diagram of H<sub>3</sub>S under high magnetic fields,” *Nat Commun*, vol. 10, no. 1, p. 2522, Jun. 2019, doi: 10.1038/s41467-019-10552-y.
- [15] D. Semenov *et al.*, “Evidence for Pseudogap Phase in Cerium Superhydrides: CeH<sub>10</sub> and CeH<sub>9</sub>,” Jul. 2023. *arXiv:2307.11742* (2023); <https://doi.org/10.48550/arXiv.2307.11742>
- [16] I. A. Troyan *et al.*, “Non-Fermi-Liquid Behavior of Superconducting SnH<sub>4</sub>,” *Advanced Science*, Aug. 2023, doi: 10.1002/advs.202303622.
- [17] D. V. Semenov *et al.*, “Effect of Magnetic Impurities on Superconductivity in LaH<sub>10</sub>,” *Advanced Materials*, vol. 34, no. 42, p. 2204038, Oct. 2022, doi: 10.1002/adma.202204038.
- [18] V. S. Minkov, V. Ksenofontov, S. L. Bud’ko, E. F. Talantsev, and M. I. Erements, “Magnetic flux trapping in hydrogen-rich high-temperature superconductors,” *Nat Phys*, Jun. 2023, doi: 10.1038/s41567-023-02089-1.

- [19] E. F. Talantsev, W. P. Crump, J. G. Storey, and J. L. Tallon, “London penetration depth and thermal fluctuations in the sulphur hydride 203 K superconductor,” *Ann Phys*, vol. 529, no. 3, pp. 1–5, 2017, doi: 10.1002/andp.201600390.
- [20] E. Talantsev, W. P. Crump, and J. L. Tallon, “Thermodynamic Parameters of Single- or Multi-Band Superconductors Derived from Self-Field Critical Currents,” *Ann Phys*, vol. 529, no. 12, pp. 1–18, 2017, doi: 10.1002/andp.201700197.
- [21] E. F. Talantsev, “Classifying superconductivity in compressed H<sub>3</sub>S,” *Modern Physics Letters B*, vol. 33, no. 17, p. 1950195, Jun. 2019, doi: 10.1142/S0217984919501951.
- [22] E. F. Talantsev, “Electron–phonon coupling constant and BCS ratios in LaH<sub>10-y</sub> doped with magnetic rare-earth element,” *Supercond Sci Technol*, vol. 35, no. 9, p. 095008, Sep. 2022, doi: 10.1088/1361-6668/ac7d78.
- [23] C. P. Poole, H. Farach, R. Creswick, and R. Prozorov, *Superconductivity*, 2nd ed. London, UK: Academic Press, 2007.
- [24] E. F. Talantsev and J. L. Tallon, “Universal self-field critical current for thin-film superconductors,” *Nat Commun*, vol. 6, no. 1, p. 7820, Aug. 2015, doi: 10.1038/ncomms8820.
- [25] J. L. Tallon and E. F. Talantsev, “Compressed H<sub>3</sub>S, superfluid density and the quest for room-temperature superconductivity,” *J Supercond Nov Magn*, vol. 31, no. 3, pp. 619–624, 2018, doi: 10.1007/s10948-017-4419-4.
- [26] E. F. Talantsev, W. P. Crump, and J. L. Tallon, “Universal scaling of the self-field critical current in superconductors: from sub-nanometre to millimetre size,” *Sci Rep*, vol. 7, no. 1, p. 10010, Aug. 2017, doi: 10.1038/s41598-017-10226-z.
- [27] I. A. Troyan *et al.*, “Non-Fermi-Liquid Behavior of Superconducting SnH<sub>4</sub>,” *Advanced Science*, Aug. 2023, doi: 10.1002/advs.202303622.
- [28] E. F. Talantsev, “Classifying superconductivity in compressed H<sub>3</sub>S,” *Modern Physics Letters B*, vol. 33, no. 17, p. 1950195, Jun. 2019, doi: 10.1142/S0217984919501951.
- [29] S. C. Wimbush and N. M. Strickland, “A Public Database of High-Temperature Superconductor Critical Current Data,” *IEEE Transactions on Applied Superconductivity*, vol. 27, no. 4, pp. 1–5, Jun. 2017, doi: 10.1109/TASC.2016.2628700.
- [30] A. K. Ghosh, “V–I transition and n-value of multifilamentary LTS and HTS wires and cables,” *Physica C Supercond*, vol. 401, no. 1–4, pp. 15–21, Jan. 2004, doi: 10.1016/j.physc.2003.09.006.
- [31] J. Lehtonen, R. Mikkonen, and R. Perälä, “Temperature dependent self-field effect in measured V(I,B)-characteristics of Bi-2223/Ag tapes,” *Physica C Supercond*, vol. 401, no. 1–4, pp. 151–154, Jan. 2004, doi: 10.1016/j.physc.2003.09.027.
- [32] P. Bruzzone, “The index n of the voltage–current curve, in the characterization and specification of technical superconductors,” *Physica C Supercond*, vol. 401, no. 1–4, pp. 7–14, Jan. 2004, doi: 10.1016/j.physc.2003.09.005.
- [33] E. F. Talantsev, “On the fundamental definition of critical current in superconductors,” Jul. 2017. doi: 10.48550/arXiv.1707.07395.
- [34] E. F. Talantsev, N. M. Strickland, S. C. Wimbush, and W. P. Crump, “The onset of dissipation in high-temperature superconductors: Self-field experiments,” *AIP Adv*, vol. 7, no. 12, Dec. 2017, doi: 10.1063/1.4997261.
- [35] S. B. L. Chislett-McDonald, L. Bullock, A. Turner, F. Schoofs, Y. Dieudonne, and A. Reilly, “In-situ critical current measurements of REBCO coated conductors during gamma irradiation,” *Supercond Sci Technol*, vol. 36, no. 9, p. 095019, Sep. 2023, doi: 10.1088/1361-6668/aceab8.
- [36] N. M. Strickland, C. Hoffmann, and S. C. Wimbush, “A 1 kA-class cryogen-free critical current characterization system for superconducting coated conductors,” *Review of Scientific Instruments*, vol. 85, no. 11, Nov. 2014, doi: 10.1063/1.4902139.
- [37] N. M. Strickland *et al.*, “Cryogen-free 1kA-class I<sub>c</sub> measurement system featuring an 8 T HTS magnet,” *J Phys Conf Ser*, vol. 507, no. 2, p. 022037, May 2014, doi: 10.1088/1742-6596/507/2/022037.
- [38] M. H. Sohn *et al.*, “Design and Manufacturing of a Conduction-Cooled Sample Holder for a Superconducting Property Measurement System,” *IEEE Transactions on Applied Superconductivity*, vol. 25, no. 3, pp. 1–4, Jun. 2015, doi: 10.1109/TASC.2014.2384533.

- [39] P. Sunwong, J. S. Higgins, and D. P. Hampshire, "Probes for investigating the effect of magnetic field, field orientation, temperature and strain on the critical current density of anisotropic high-temperature superconducting tapes in a split-pair 15 T horizontal magnet," *Review of Scientific Instruments*, vol. 85, no. 6, Jun. 2014, doi: 10.1063/1.4881235.
- [40] M. Lao *et al.*, "High current variable temperature electrical characterization system for superconducting wires and tapes with continuous sample rotation in a split coil magnet," *Review of Scientific Instruments*, vol. 90, no. 1, Jan. 2019, doi: 10.1063/1.5078447.
- [41] H. Ma *et al.*, "Critical current measurements of high-temperature superconducting short samples at a wide range of temperatures and magnetic fields," *Review of Scientific Instruments*, vol. 89, no. 1, Jan. 2018, doi: 10.1063/1.4996057.
- [42] N. M. Strickland, A. Choquette, E. F. Talantsev, and S. C. Wimbush, "High-current superconductor transport critical-current measurement option for the Quantum Design Physical Property Measurement System," Aug. 2019, doi: 10.48550/arXiv.1908.09416.
- [43] J. W. Ekin, *Experimental Techniques for Low-Temperature Measurements*. Oxford, UK: Oxford University Press, 2006.
- [44] J. Hänisch *et al.*, "Anisotropy of flux pinning properties in superconducting (Li,Fe)OHFeSe thin films," *Supercond Sci Technol*, vol. 33, no. 11, p. 114009, Nov. 2020, doi: 10.1088/1361-6668/abb118.
- [45] D. M. J. Taylor and D. P. Hampshire, "Relationship between the  $n$ -value and critical current in Nb<sub>3</sub>Sn superconducting wires exhibiting intrinsic and extrinsic behaviour," *Supercond Sci Technol*, vol. 18, no. 12, pp. S297–S302, Dec. 2005, doi: 10.1088/0953-2048/18/12/012.
- [46] E. F. Talantsev and R. C. Mataira, "Polar projections for big data analysis in applied superconductivity," *AIP Adv*, vol. 8, no. 7, Jul. 2018, doi: 10.1063/1.5038040.
- [47] P. Branch, K. Osamura, and D. Hampshire, "Weak emergence in the angular dependence of the critical current density of the high temperature superconductor coated conductor REBCO," *Supercond Sci Technol*, vol. 33, no. 10, p. 104006, Oct. 2020, doi: 10.1088/1361-6668/abaebe.