

Common behavior of the scaled condensation energy for both high- T_c and conventional superconductors

V. R. Shaginyan,^{1,2,*} A. Z. Msezane,² and S. A. Artamonov¹

¹*Petersburg Nuclear Physics Institute, NRC Kurchatov Institute, Gatchina, 188300, Russia*

²*Department of Physics, Clark Atlanta University, Atlanta, GA 30314, USA*

We analyze the scaling of the condensation energy E_Δ divided by γ , $E_\Delta/\gamma \simeq N(0)\Delta_1^2/\gamma$, of both conventional superconductors and unconventional high- T_c one, where $N(0)$ is the density of states, Δ_1 is the maximum value of the superconducting gap and γ is the Sommerfeld coefficient. For the first time, we show that the universal scaling of $E_\Delta/\gamma \propto T_c^2$ applies equally to conventional superconductors and unconventional high- T_c ones. Our consideration is based on both facts: Bogoliubov quasiparticles act in conventional and unconventional superconductors, and the corresponding flat band is deformed by the unconventional superconducting state. As a result, our theoretical observations based on the fermion condensation theory are in good agreement with experimental facts.

PACS numbers: 74.25.Bt; 74.72.-h; 64.70.Tg

I. INTRODUCTION

It is generally accepted that conventional superconductors have nothing in common with unconventional superconductors, since unconventional superconductors are strange metals with flat bands [1] in the absence of quasiparticles, see e.g. [2]. On the other hand, experimental facts show that both types of superconductors have common properties, have quasiparticles and exhibit common scaling behavior, see, for example, [3–6]; while the corresponding flat bands of high- T_c superconductors are deformed by superconducting state, which makes high- T_c superconductors similar to ordinary superconductors [7, 8]. Thus, these contradictions pose a challenging puzzle for condensed matter researchers.

The flat band problem described above could have been solved many years ago when Landau's Fermi liquid (LFL) theory was developed [9]. As known, it deals with energy functionals $E_0[n(\mathbf{p})]$ in the functional space $[n]$ of quasiparticle distributions $n(\mathbf{p})$ located in $[n]$ between 0 and 1. This theory is based on assumption that the single particle spectrum of a normal Fermi liquid is similar to that of an ideal Fermi gas, differing from the latter in the value of the effective mass M^* . At temperature $T = 0$, in a homogeneous isotropic matter, the LFL ground state quasiparticle distribution is the Fermi step function $n_F(p) = \theta(p - p_F)$. Quasiparticles fill the Fermi sphere up to the same radius $p_F = (3\pi^2\rho)^{1/3}$ (ρ is the number density and p_F is the Fermi momentum) as noninteracting particles do (the Landau-Luttinger theorem [9]). From the mathematical point of view, in the LFL, the minimum of $E_0[n]$ is supposed to always lie at a boundary point n_F of the space $[n]$. This assumption

remains valid as long as the necessary stability condition

$$\delta E_0 = \int (\varepsilon[\mathbf{p}, n(\mathbf{p}, T = 0)] - \mu) \delta n(\mathbf{p}, T = 0) \frac{d^3p}{(2\pi)^3} > 0, \quad (1)$$

is fulfilled. Here $\varepsilon[\mathbf{p}, n(\mathbf{p})] = \delta E_0[n]/\delta n(\mathbf{p})$ is the quasiparticle energy, $n(\mathbf{p})$ is the quasiparticle distribution function, and μ is the chemical potential. The stability condition requires that the change of $E_0[n]$ for any admissible variations of n_F holds. Thus, it is the violation of the condition given by Eq. (1) that results in the rearrangement of the distribution $n_F(\mathbf{p})$. The quasiparticle distribution function $n(\mathbf{p})$ is constrained by the Pauli principle $1 \geq n(\mathbf{p}) \geq 0$. As a result, there are two classes of solutions of Eq. (1). One class forming flat bands is

$$\varepsilon(p) = \mu; \text{ if } 1 > n_0(\mathbf{p}) > 0 \text{ in } p_i < p < p_f, \quad (2)$$

which is valid if the special solution $n_0(\mathbf{p})$ becomes $1 > n_0(\mathbf{p}) > 0$ in some region $p_i < p_F < p_f$ [10–14]. The other conventional class is defined by $\delta n(\mathbf{p}) = 0$ with $n(\mathbf{p}) = 0$ or $n(\mathbf{p}) = 1$, that is $n(\mathbf{p}) = n_F(\mathbf{p})$ [9].

Flat bands, now observed in many strongly correlated Fermi systems [1], first emerged as a mathematical curiosity [10, 11] and now represent a rapidly expanding and dynamic field with countless applications, see e.g. [1, 13–18]. High- T_c superconductors represent a wide class of strongly correlated Fermi systems, exhibiting the non-Fermi liquid (NFL) behavior defined by flat bands, see e.g. [13, 14, 16–18]. As a result, one can expect that superconductors with high- T_c have nothing in common with conventional superconductors. For example, in case of high- T_c superconductors the critical temperature [10, 11, 14, 16–18]

$$T_c \propto \Delta_1 \propto \lambda_0, \quad (3)$$

rather than being $T_c \propto \exp(-1/gN(0))$, where λ_0 is the superconducting coupling constant, Δ_1 is the maximum value of the superconducting gap and $N(0)$ is the density of states at the Fermi surface [19, 20]. However,

*Electronic address: vrshag@thd.pnpi.spb.ru

in both conventional and unconventional high- T_c superconductors, the condensation energy exhibits universal scaling behavior: $E_\Delta/\gamma \simeq N(0)\Delta_1^2/\gamma \propto T_c^2$, as it follows from experimental facts [4].

In our paper we analyze both unconventional high- T_c superconductors and conventional ones, and demonstrate that both of them exhibit the common universal scaling of the condensation energy E_Δ/γ , $E_\Delta/\gamma \simeq N(0)\Delta_1^2/\gamma$. For the first time, we explain that the universal scaling of $E_\Delta/\gamma \propto T_c^2$ applies equally to conventional and unconventional high- T_c superconductors. Our results are in good agreement with experimental facts [4]. This observation suggests that the FC superconducting state is BCS-like and suggests the fundamental applicability of the BCS formalism to describe some properties of the superconducting state, as predicted in [13, 21]. Our analysis is made within the framework of the fermion condensation (FC) theory based on the topological fermion condensation quantum phase transition (FCQPT) that forms flat bands and leads to the universal scaling behavior of the thermodynamic and transport properties of HF metals [10, 11, 13, 15].

II. SUPERCONDUCTING SYSTEMS WITH THE FC STATE

Here we consider the superconducting state of high- T_c superconductors within the framework of the FC theory [10, 13]. It was experimentally shown that in HF metals the quasiparticles are well-defined excitations [5] and in the superconducting state of high- T_c superconductors the elementary excitations are Bogoliubov quasiparticle (BQ), that is the excitations are Bardeen-Cooper-Schrieffer like [3, 6, 19, 20]. Therefore, as we shall see, unconventional superconductors exhibit the same scaling behavior of the condensation energy E_Δ/γ as conventional superconductors do [9].

The energy dispersion of single-particle excitations and the corresponding coherence factors as a function of momentum were measured on high- T_c cuprates ($\text{Bi}_2\text{Sr}_2\text{Ca}_2\text{Cu}_3\text{O}_{10+\delta}$, $T_c=108$ K) by using high-resolution angle-resolved photoemission spectroscopy [3]. All the observed features qualitatively and quantitatively agree with the behavior of BQ in conventional superconductors predicted by the BCS theory [3, 5, 19, 20]. This observation shows that the superconducting state of high- T_c superconductors is BCS-like with BQ, and implies the basic validity of the BCS formalism in describing the superconducting state, and is closely related to the deformation of flat band by the superconducting phase transition [8, 21–24]. On the other hand, a number of the properties as the maximum value of the superconducting gap Δ_1 , the high density of states and the other exotic properties are beyond the BCS theory [13, 15, 21].

Below we shall call electron (hole) liquids as electron one. At $T < T_c$, the thermodynamic potential Ω of an

electron liquid is given by the Equation (see, e.g. [9, 20])

$$\Omega = E_{gs} - \mu N - TS, \quad (4)$$

In Eq. (4) N is the number density of quasiparticles, S denotes the entropy, and μ is the chemical potential. The ground state energy $E_{gs}[\kappa(\mathbf{p}), n(\mathbf{p})]$ of electron liquid is the exact functional of the order parameter of the superconducting state $\kappa(\mathbf{p})$ and of the quasiparticle occupation numbers $n(\mathbf{p})$ [13, 25]. Here we assume that the electron system is two-dimensional in order to describe the results of Ref. [3], while all results can be transported to the case of three-dimensional system. This energy is determined by the known equation of the weak-coupling theory of superconductivity

$$E_{gs} = E[n(\mathbf{p})] + \delta E_s. \quad (5)$$

Here $E[n(\mathbf{p})]$ is the exact Landau functional determining the ground-state energy of normal Fermi liquid [9, 13], and δE_s is given by

$$\delta E_s = \int \lambda_0 V(\mathbf{p}_1, \mathbf{p}_2) \kappa(\mathbf{p}_1) \kappa^*(\mathbf{p}_2) \frac{d\mathbf{p}_1 d\mathbf{p}_2}{(2\pi)^4}. \quad (6)$$

Here $\lambda_0 V(\mathbf{p}_1, \mathbf{p}_2)$ is the pairing interaction. The quasiparticle occupation numbers

$$n(\mathbf{p}) = v^2(\mathbf{p})(1 - f(\mathbf{p})) + u^2(\mathbf{p})f(\mathbf{p}), \quad (7)$$

and at finite temperatures the order parameter κ reads

$$\kappa(\mathbf{p}) = v(\mathbf{p})u(\mathbf{p})(1 - 2f(\mathbf{p})). \quad (8)$$

While at $T = 0$ the order parameter reduces to [11]

$$\kappa(\mathbf{p}) = \sqrt{n_0(\mathbf{p})(1 - n_0(\mathbf{p}))}. \quad (9)$$

Here the coherence factors $v(\mathbf{p})$ and $u(\mathbf{p})$ are obeyed the normalization condition

$$v^2(\mathbf{p}) + u^2(\mathbf{p}) = 1. \quad (10)$$

The distribution function $f(\mathbf{p})$ of BQ defines the entropy

$$S = -2 \int [f(\mathbf{p}) \ln f(\mathbf{p}) + (1 - f(\mathbf{p})) \ln(1 - f(\mathbf{p}))] \frac{d\mathbf{p}}{4\pi^2}. \quad (11)$$

We assume that the pairing interaction $\lambda_0 V(\mathbf{p}_1, \mathbf{p}_2)$ is weak and produced, for instance, by electron—phonon interaction. Minimizing Ω with respect to $\kappa(\mathbf{p})$ and using the definition $\Delta(\mathbf{p}) = -\delta\Omega/\kappa(\mathbf{p})$, we obtain the equation connecting the single-particle energy $\varepsilon(\mathbf{p})$ to the superconducting gap $\Delta(\mathbf{p})$,

$$\varepsilon(\mathbf{p}) - \mu = \Delta(\mathbf{p}) \frac{1 - 2v^2(\mathbf{p})}{2v(\mathbf{p})u(\mathbf{p})}. \quad (12)$$

The single-particle energy $\varepsilon(\mathbf{p})$ is determined by the Landau equation

$$\varepsilon(\mathbf{p}) = \frac{\delta E[n(\mathbf{p})]}{\delta n(\mathbf{p})}. \quad (13)$$

Note that $E[n(\mathbf{p})]$, $\varepsilon[n(\mathbf{p})]$, and the Landau amplitude

$$F(\mathbf{p}, \mathbf{p}_1) = \frac{\delta E^2[n(\mathbf{p})]}{\delta n(\mathbf{p})\delta(\mathbf{p}_1)} \quad (14)$$

implicitly depend on the number density x which defines the strength of F . Minimizing Ω with respect to $f(\mathbf{p})$ and after some algebra, we obtain the equation for the superconducting gap $\Delta(\mathbf{p})$

$$\Delta(\mathbf{p}) = -\frac{1}{2} \int \lambda_0 V(\mathbf{p}, \mathbf{p}_1) \frac{\Delta(\mathbf{p}_1)}{E(\mathbf{p}_1)} (1 - 2f(\mathbf{p}_1)) \frac{d\mathbf{p}_1}{4\pi^2}. \quad (15)$$

Here the excitation energy $E(\mathbf{p})$ represented by BQ is given by

$$E(\mathbf{p}) = \frac{\delta(E_{gs} - \mu N)}{\delta f(\mathbf{p})} = \sqrt{(\varepsilon(\mathbf{p}) - \mu)^2 + \Delta^2(\mathbf{p})}. \quad (16)$$

The coherence factors $v(\mathbf{p})$, $u(\mathbf{p})$, and the distribution function $f(\mathbf{p})$ are given by the ordinary relations

$$v^2(\mathbf{p}) = \frac{1}{2} \left(1 - \frac{\varepsilon(\mathbf{p}) - \mu}{E(\mathbf{p})} \right); u^2(\mathbf{p}) = \frac{1}{2} \left(1 + \frac{\varepsilon(\mathbf{p}) - \mu}{E(\mathbf{p})} \right), \quad (17)$$

$$f(\mathbf{p}) = \frac{1}{1 + \exp(E(\mathbf{p})/T)}. \quad (18)$$

Equations (12)–(18) are the conventional equations of the BCS theory [19, 20], determining the superconducting state with BQ and the maximum value of the superconducting gap $\Delta_1 \sim 10^{-3}\varepsilon_F$ provided that one assumes that the system in question has not undergone FCQPT.

Now we consider a superconducting state with FC which takes place after the FCQPT point. At $T = 0$ and $\lambda_0 \rightarrow 0$ the maximum value of the superconducting gap $\Delta_1 \rightarrow 0$, as well as the critical temperature $T_c \rightarrow 0$, and Eq. (12) converts into Eq. (2) [10, 11, 13]. At $T \rightarrow 0$, Eq. (2) defines the new state of Fermi liquid with FC [10, 12] which is characterized by flat part of the spectrum in the $(p_f - p_i)$ region and has a strong impact on the system's properties up to temperature T_f^0 [10, 13, 23, 24]. It is seen from Eq. (2) that the entropy $S(T \rightarrow 0) \rightarrow S_0$, where $S_0 > 0$ is given by

$$S_0 = - \int [n_0(p) \ln n_0(p) + (1 - n_0(p)) \ln(1 - n_0(p))] \frac{d\mathbf{p}}{(2\pi)^2}. \quad (19)$$

At $T \rightarrow 0$, Eq. (2) defines the particular state of a Fermi liquid with FC, for which the modulus of the order parameter $|\kappa(\mathbf{p})|$ has finite values in the $(p_f - p_i)$ region, whereas $\Delta_1 \rightarrow 0$ in this region. Observe that $f(\mathbf{p}, T \rightarrow 0) \rightarrow 0$, and it follows from Eqs. (7) and (8) that if $0 < n(\mathbf{p}) < 1$ then $|\kappa(\mathbf{p})| \neq 0$ in the region $(p_f - p_i)$. Such a state can be considered as superconducting, with an infinitely small value of Δ_1 , so that the entropy of this state is equal to zero. At any finite $T > 0$ the entropy $S \geq S_0$, thus the topological FCQPT is of the first order [13]. The FC state is formed by the Landau

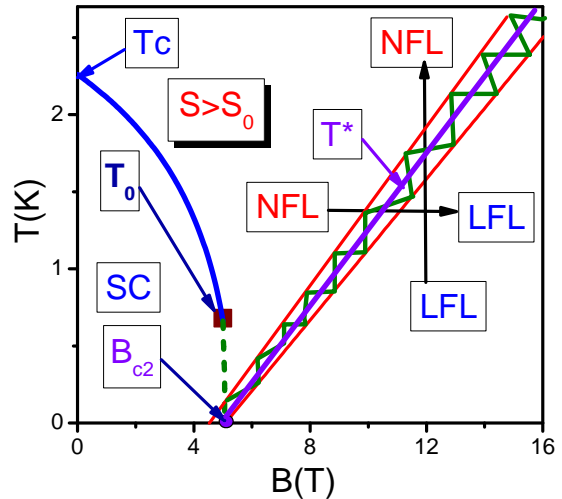


FIG. 1: Schematic $T-B$ phase diagram of a superconducting HF metal, with the upper critical field B_{c2} . The vertical and horizontal arrows crossing the transition region are marked by the line depicting the LFL-NFL and NFL-LFL transitions at fixed B and T , respectively. The hatched area indicates the crossover from the LFL state, with $\rho(T) \propto T^2$, to the NFL one, with $\rho(T) \propto T$. The median line T^* of the crossover is shown by the solid line. As shown by the solid curve, at $B < B_{c2}$ the system is in its superconducting (SC) state. The superconducting critical field B_{c2} is shown by the violet circle. Superconducting-normal phase boundary is displayed by the solid and dashed curves. The solid square shows the point at $T = T_0$ where the superconducting phase transition T_c changes from the second order phase transition to the first one.

interaction $F(p = p_F, p_1 = p_F)$ being relatively strong as compared with the pairing interaction $\lambda_0 V$, therefore $\lambda_0 V$ does not noticeably disturb the occupation numbers n_0 , but does disturb the corresponding flat band [8, 13]. If the Landau interaction as a function of the number density x is sufficiently small, the flat part vanishes, and at $T \rightarrow 0$ Eq. (2) has the only trivial solution $\varepsilon(p = p_F) = \mu$, and the quasiparticle occupation numbers are given by the step function, $n(\mathbf{p}) = \theta(p_F - p)$ [10, 11].

Consider the schematic phase diagram of unconventional high- T_c superconductor. It is seen from the schematic phase diagram 1, that at temperatures $T \lesssim T_c$ the superconducting-normal phase transition shown by the solid line in Fig. 1 is of the second order and entropy S is a continuous function of its variable T at $T_c(B)$. At temperatures $T \rightarrow 0$, the normal state can be recovered by the application of magnetic field B , that is approximately equal to the critical field $B \simeq B_{c2}$, and this state can be viewed as the LFL one induced by the magnetic field. When the system in its NFL state, under the application of magnetic field $B > T^*$, HF metal

transits to its LFL state, as seen from Fig. 1. At $T \rightarrow 0$ the entropy of the superconducting state $S_{SC} \rightarrow 0$ and the entropy of the NFL state tends to some finite value $S_{NFL} \geq S_0$, see Eq. (19) [11]. Thus, at temperatures $T_0 \geq T$ the equality $S_{SC}(T) = S_{NFL}(T)$ cannot be satisfied [13, 26]. Thus, the second-order phase transition becomes the first below a certain temperature $T_0(B)$, as it happens in CeCoIn₅ and as shown by the arrow in Fig. 1 [26–28]. We note that the topological FCQPT is also of the first order. This first-order phase transition is determined both by the entropy jump mentioned above and by the topological charge of FCQPT, which also changes abruptly [12, 14]. As a result, possible fluctuations of the order parameter κ are suppressed at $T \leq T_0$ [13, 26].

III. COMMON SCALING OF CONVENTIONAL AND HIGH- T_c SUPERCONDUCTORS

It follows from Eqs. (2) and (12) that the system becomes divided into two quasiparticle subsystems: the first subsystem in the $(p_f - p_i)$ range is characterized by the quasiparticles with the effective mass $M_{FC}^* \propto 1/\Delta_1$, while the second one is occupied by quasiparticles with finite mass M_L^* and momenta $p < p_i$ [13]. If $\lambda_0 \neq 0$, then Δ_1 becomes finite. It is seen from Eq. (15) that the superconducting gap depends on the single-particle spectrum $\varepsilon(\mathbf{p})$. On the other hand, it follows from Eq. (12) that $\varepsilon(\mathbf{p})$ depends on $\Delta(\mathbf{p})$, since at $\Delta_1 \rightarrow 0$ the spectrum becomes flat. Let us assume that λ_0 is small so that the particle-particle interaction $\lambda_0 V(\mathbf{p}, \mathbf{p}_1)$ can only lead to a small perturbation of the order parameter $\kappa(\mathbf{p})$ determined by Eq. (9). Upon differentiation both parts of Eq. (12) with respect to the momentum p , we obtain that the effective mass $M_{FC}^* = d\varepsilon(p)/dp|_{p=p_F}$ becomes finite [8]

$$M_{FC}^* \sim p_F \frac{p_f - p_i}{2\Delta_1}. \quad (20)$$

It follows from Eq. (20) that the effective mass and the density of states $N(0) \propto M_{FC}^* \propto 1/\Delta_1$ are finite and constant at $T < T_c$ [8, 24]. At $T \rightarrow 0$ and $\lambda_0 \rightarrow 0$ the density of states near the Fermi level tends to infinity. Thus, we arrive at the result that contradicts the BCS theory, and follows from Eq. (20)

$$N(0) \propto M_{FC}^* \propto 1/\Delta_1 \propto 1/T_c \propto 1/V_F, \quad (21)$$

where $V_F \propto p_F/M_{FC}^*$ is the Fermi velocity [7, 24], see Fig. 2.

Measurements of V_F as a function of T_c [7] are depicted in Fig. 2. These observations are in good agreement with Eq. (21). Thus, our theoretical prediction [13, 22, 24] agrees very well with the experimental results [7]. It is worth noting that $V_F \rightarrow 0$, as well as $T_c \rightarrow 0$, as can be seen from Fig. 2. This result shows that the flat band is disturbed by the finite value of Δ_1 , and possesses a finite slope that makes $V_F \propto T_c$, as seen

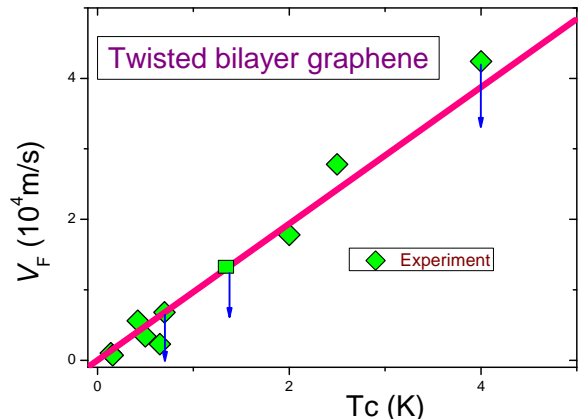


FIG. 2: Experimental results for the average Fermi velocity V_F as a function of the critical temperature T_c for MATBG [7]. The downward arrows show that $V_F \leq V_0$, with V_0 is the maximal shown value. Theory is shown by the solid line that demonstrates $V_F \propto T_c \propto 1/N(0)$, see Eq. (21), [8].

from Fig. 2. Indeed, from Fig. 2, the experimental critical temperatures T_c do not correspond to the minima of the Fermi velocity V_F as they would in any BCS-like theory [7]. This extraordinary behavior is explained within the framework of the FC theory based on the topological FCQPT, forming flat bands [8, 13]. As we will see below, another unusual behavior, i.e., the general universal scaling of E_Δ/γ of both conventional and high- T_c superconductors [4], is also associated with Eq. (21) and explained within the framework of the FC theory.

We are led to the conclusion that in contrast to the conventional theory of superconductivity the single-particle spectrum $\varepsilon(\mathbf{p})$ strongly depends on the superconducting gap and we have to solve Eqs. (13) and (15) in a self-consistent way. On the other hand, let us assume that Eqs. (13) and (15) are solved, and the effective mass M_{FC}^* is determined. Now one can fix the dispersion $\varepsilon(\mathbf{p})$ by choosing the effective mass M^* of system in question equal to M_{FC}^* and then solve Eq. (15) as it is done in the case of the conventional theory of superconductivity [19]. As a result, one observes that the superconducting state is characterized by BQ with the dispersion given by Eq. (16), the coherence factors v, u are given by Eq. (17), and the normalization condition (10) is held. We conclude that the observed features agree with the behavior of BQ in accordance with experimental facts [3, 29]. This observation suggests that the superconducting state with FC is BCS-like and implies the basic validity of BCS formalism in describing the superconducting state in terms of BQ. It is exactly the case that was observed experimentally in high- T_c cuprates like Bi₂Sr₂Ca₂Cu₃O_{10+ δ} , see e.g. [3, 6].

We now analyze other relationships between the conventional superconducting state and the superconducting state with FC. We consider the case when $T_c \ll T_f^0$. This means that the order parameter $\kappa(\mathbf{p})$ is slightly perturbed by the pairing interaction because the particle-particle interaction $\lambda_0 V$ is small comparatively to the Landau amplitude F and the order parameter $\kappa(\mathbf{p})$ is governed mainly by F [10, 13]. We can solve Eq. (15) analytically taking the BCS approximation for the particle-particle interaction: $\lambda_0 V(\mathbf{p}, \mathbf{p}_1) = \lambda_0$ if $|\varepsilon(\mathbf{p}) - \mu| \leq \omega_D$, i.e. the interaction is zero outside this region, with ω_D being the characteristic phonon energy. As a result, the maximum value of the superconducting gap is given by [13]

$$\begin{aligned} \Delta_1 &\simeq \frac{\lambda_0 p_F (p_f - p_F)}{2\pi} \ln(1 + \sqrt{2}) \\ &\simeq 2\beta \varepsilon_F \frac{p_f - p_F}{p_F} \ln(1 + \sqrt{2}). \end{aligned} \quad (22)$$

Here, the Fermi energy $\varepsilon_F = p_F^2/2M_L^*$, and the dimensionless coupling constant β is given by the relation $\beta = \lambda_0 M_L^*/2\pi$. Taking the usual values of β as $\beta \simeq 0.3$, and assuming $(p_f - p_F)/p_F \simeq 0.2$, we get from Eq. (22) a large value of $\Delta_1 \sim 0.1\varepsilon_F$, while for normal metals one has $\Delta_1 \sim 10^{-3}\varepsilon_F$. Now we determine the energy scale E_0 which defines the region occupied by quasiparticles with the effective mass M_{FC}^*

$$E_0 = \varepsilon(\mathbf{p}_f) - \varepsilon(\mathbf{p}_i) \simeq 2 \frac{(p_f - p_F)p_F}{M_{FC}^*} \simeq 2\Delta_1. \quad (23)$$

We have returned back to the Landau Fermi liquid theory since the high energy degrees of freedom are eliminated and the quasiparticles are introduced. The only difference between LFL, which serves as a basis when constructing the superconducting state, and Fermi liquid with FC is that we have to expand the number of relevant low energy degrees of freedom by introducing the new type of quasiparticles with the effective mass M_{FC}^* given by Eq. (20) and the energy scale E_0 given by Eq. (23). Therefore, the dispersion $\varepsilon(\mathbf{p})$ is characterized by two effective masses M_L^* and M_{FC}^* and by the scale E_0 , which define the low temperature properties including the line shape of quasiparticle excitations [24], while the dispersion of BQ is given by Eq. (21). We note that both the effective mass M_{FC}^* and the scale E_0 are temperature independent at $T < T_c$, where T_c is the critical temperature of the superconducting phase transition [13]. Obviously, we cannot directly relate these new BQ quasiparticle excitations with the quasiparticle excitations of an ideal Fermi gas because the system in question has undergone the topological FCQPT. However, the basic properties of the LFL theory remains in FCQPT: low-energy excitations of a strongly correlated liquid with FC are quasiparticles, whereas in the superconducting state they are represented by BQ [13]. As it was shown above,

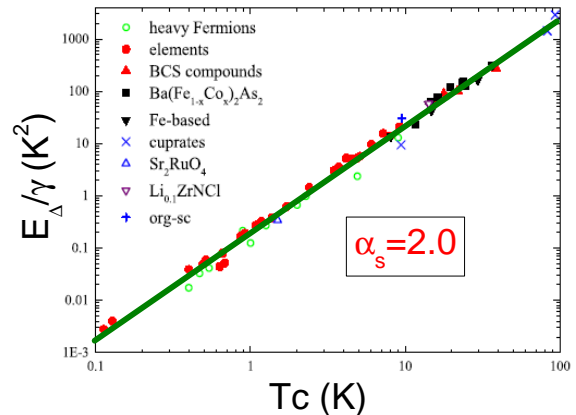


FIG. 3: Condensation energy $E_{\Delta}/\gamma \propto T_c^2$ divided by the specific heat γ as a function of T_c for a wide range of superconductors, with the slope $\alpha_s = 2$ [4], see Eq. (26). Deviations from the line of best fit, spanning six orders of magnitude for E_{Δ}/γ and almost three orders of magnitude for T_c , are relatively small.

properties of these new quasiparticles are closely related to the properties of the superconducting state with the order parameter at $T = 0$ being given by Eq. (9) We may say that the quasiparticle system in the range $(p_f - p_i)$ becomes very ‘soft’, that is it should be adjusted to the superconducting state, see Eqs. (20) and Eq. (21), and is to be considered as a strongly correlated liquid.

At the same time, one could expect serious deviations from the BCS results when calculating the pairing correction ΔE_{FC} to $E_0[n]$. Applying the Landau formula for the change of $E_0[n]$ due to the variation $\delta n(\mathbf{p}, T) = n(\mathbf{p}, T) - n_0(\mathbf{p})$ of the occupation numbers [9] and adding the superfluid term (6) we arrive at the following result

$$\Delta E_{FC} = \int (\varepsilon(\mathbf{p}) - \mu) \delta n(\mathbf{p}) \frac{d^3 p}{(2\pi)^3} + \delta E_s. \quad (24)$$

Here δE_s is given by Eqs. (3), (6) and (9)

$$\delta E_s = -\frac{1}{2} \int_{p_i}^{p_f} \Delta_0(p) \sqrt{n_0(p)(1 - n_0(p))} \frac{p^2 dp}{2\pi^2}. \quad (25)$$

In the usual BCS case the first term and the second one become proportional $\sim \Delta^2/\varepsilon_F^0$ so that $\Delta E_{FC} \sim \Delta^2/\varepsilon_F^0$ [9]. One could suspect that in the system with the FC the first term in Eq. (24) turns out to be zero, for $\varepsilon(\mathbf{p}) - \mu = 0$ in the region $p_f - p_i$, see Eq. (2). This is not true, since both the Fermi velocity V_F and the effective mass M_{FC}^* become finite under the influence of the superconducting state [8], see Eq. (21). Considering also that we are dealing with BQ, we are left with the usual BCS result for the superconducting condensation energy E_{Δ} , which is

valid for both conventional superconductors and unconventional superconductors with high- T_c ,

$$\Delta E_{FC}/\gamma \sim E_{\Delta}/\gamma \sim \frac{N(T)\Delta_1^2}{\gamma(T)} \sim \Delta_1^2 \sim T_c^2. \quad (26)$$

Here $N(T)$ and $\gamma(T)$ are the density of states and the Sommerfeld coefficient, correspondingly. $N(T)$ and $\gamma(T)$ strongly depend on temperature T in the FC theory, and Δ_1 is the maximum value of the superconducting gap. However, $M^*(T) \propto N(T) \propto \gamma(T)$ [13], and we obtain $E_{\Delta}/\gamma \sim T_c^2$. It is seen from Fig. 3 that Eq. (26) is in accordance with experimental facts [4]. Indeed, taking into account that BQ of unconventional high- T_c superconductors within the framework of the FC theory coincide with BQ of conventional superconductors and Eq. (20), we conclude that the condensation energy E_{Δ}/γ given by Eq. (26) has the universal form valid in the case of both conventional superconductors and high- T_c ones. To check this conclusion, we compare our theoretical result with experimental facts [4]. Figure 3 shows the scaling of the condensation energy E_{Δ} versus T_c^2 on log-log scale. It is seen from Fig. 3 that the universal scaling $E_{\Delta}/\gamma \propto T_c^2$ is valid for all superconductors, both the conventional and the unconventional high- T_c ones. This universal scaling behavior takes place over almost seven orders of magnitude for E_{Δ}/γ and three orders of magnitude for T_c [4]. This observation is not surprising, for, as we have seen above, high- T_c superconductors have the same BQ as conventional one, since the shape of the corresponding band is correlated with their T_c , as it follows from Eq. (21). Note that due to the strong influence of the pseudo-

gap state on the properties of unconventional superconductors, such as the density of states, heat capacity, and even the real meaning of T_c is not clear, only optimally doped samples were considered [4, 30]. Thus, the FC theory allows one to justify Eq. (26) that describes the superconductivity extending far beyond the weak coupling regime, and applies to both the conventional and the unconventional strongly correlated superconductors.

IV. SUMMARY

We have analyzed the common behavior of unconventional high- T_c and conventional superconductors and demonstrated that the universal scaling of the condensation energy $E_{\Delta}/\gamma = N(0)\Delta_1^2/\gamma$ applies equally to conventional and unconventional high- T_c superconductors. Our explanation is based on the general property of superconductors: Bogoliubov quasiparticles act in conventional and unconventional superconductors, while the corresponding band is only deformed by the unconventional superconducting state. These observations suggest that the unconventional superconducting state can be considered BCS-like in some cases, as predicted in [13, 21, 24]. Our theoretical observations are in good agreement with experimental facts.

We thank V.A. Khodel for fruitful discussions. This work was supported by U.S. DOE, Division of Chemical Sciences, Office of Basic Energy Sciences, Office of Energy Research, AFOSR.

-
- [1] N. Regnault, Y. Xu, M.-R. Li, D.-Sh. Ma, M. Jovanovic *et al.*, Nature **603**, 824 (2022).
- [2] L. Chen, D. T. Lowder, E. Bakali, A. M. Andrews, W. Schrenk, *et al.*, Science **382**, 907 (2023).
- [3] H. Matsui, T. Sato, T. Takahashi, S.-C. Wang, H.-B. Yang, H. Ding, T. Fujii, T. Watanabe, and A. Matsuda, Phys. Rev. Lett. **90**, 217002 (2003).
- [4] J.S. Kim, G.N. Tam, and G.R. Stewart, Phys. Rev. B **92**, 224509 (2015).
- [5] A. Hunter, S. Beck, E. Cappelli, F. Margot, M. Straub *et al.*, Phys. Rev. Lett. **131**, 236502 (2023).
- [6] K.-J. Xu, Qinda Guo, M. Hashimoto, Z.-X. Li, S.-D. Chen *et al.*, Nat. Phys. **19**, 1834 (2023).
- [7] W. Qin, B. Zou, and A.H. MacDonald, Phys. Rev. B **107**, 024509 (2023).
- [8] V.R. Shaginyan, A.Z. Msezane, M.Ya. Amusia, and G.S. Japaridze, EPL, **138**, 16004 (2022).
- [9] E. M. Lifshitz, L. Pitaevskii, *Statistical Physics. Part 2.* (Butterworth-Heinemann, Oxford, 2002).
- [10] V.A. Khodel and V.R. Shaginyan, JETP Lett. **51**, 553 (1990).
- [11] V.A. Khodel, V.R. Shaginyan, and V.V. Khodel, Phys. Rep. **249**, 1 (1994).
- [12] G.E. Volovik, JETP Lett. **53**, 222 (1991).
- [13] V.R. Shaginyan, M.Ya. Amusia, A.Z. Msezane, and K.G. Popov, Phys. Rep. **492**, 31 (2010).
- [14] T.T. Heikkila and G.E. Volovik, Flat bands as a route to high-temperature superconductivity in graphite. Springer Series in Materials Science, Vol. **244** (Springer Nature Switzerland AG, Cham, 2016).
- [15] M.Ya. Amusia and V.R. Shaginyan, *Strongly Correlated Fermi Systems: A New State of Matter*, Springer Tracts in Modern Physics Vol. **283** (Springer Nature Switzerland AG, Cham, 2020).
- [16] P. Rosenzweig, H. Karakachian, D. Marchenko, and K. Küster, and U. Starke, Phys. Rev. Lett. **125**, 176403 (2020).
- [17] P. Törmä, S. Peotta, and B.A. Bernevig, Nat. Rev. Phys. **4**, 528 (2022).
- [18] V. Peri, Z.D. Song, B.A. Bernevig, and S.D. Huber, Phys. Rev. Lett. **126**, 027002 (2021).
- [19] J. Bardeen, L.N. Cooper, and J.R. Schriffer, Phys. Rev. **108**, 1175 (1957).
- [20] K.H. Bennemann and J.B. Ketterson, *Superconductivity*, (Springer-Verlag Berlin Heidelberg, 2008).
- [21] M.Ya. Amusia and V.R. Shaginyan, JETP Lett. **77**, 671 (2003).
- [22] V.R. Shaginyan, JETP Lett. **77**, 99 (2003).
- [23] J. Dukelsky, V.A. Khodel, P. Schuck, and V.R. Shaginyan, Z. Phys. B **102**, 245 (1997).

- [24] M.Ya. Amusia and V.R. Shaginyan, Phys. Rev. B **63**, 224507 (2001).
- [25] V.R. Shaginyan, Phys. Lett. A**249**, 237 (1998).
- [26] V.R. Shaginyan, A.Z. Msezane, V.A. Stephanovich, and E.V. Kirichenko, EPL **76**, 898 (2006).
- [27] A. Bianchi, R. Movshovich, N. Oeschler, P. Gegenwart, F. Steglich *et al.*, Phys. Rev. Lett. **89**, 137002 (2002).
- [28] K. Izawa, H. Yamaguchi, Y. Matsuda, H. Shishido, R. Settai, and Y. Onuki, Phys. Rev. Lett. **87**, 057002 (2001).
- [29] S. Nakamae, K. Behnia, N. Mangkorntong, M. Nohara, H. Takagi, S. J. C. Yates, and N. E. Hussey, Phys. Rev. B **68**, 100502(R) (2003).
- [30] J.W. Loram, K.A. Mirza, J.M. Wade, J.R. Cooper, and W.Y. Liang, Physica C **235-240**, 134 (1994).