

# Multipolar magnetism in $5d^2$ vacancy-ordered halide double perovskites

Koushik Pradhan,<sup>1</sup> Arun Paramakanti,<sup>2</sup> and Tanusri Saha-Dasgupta<sup>1,\*</sup>

<sup>1</sup>*Department of Condensed Matter Physics and Materials Science,  
S.N. Bose National Centre for Basic Sciences, Kolkata 700098, India.*

<sup>2</sup>*Department of Physics, University of Toronto, 60 St. George Street, Toronto, ON, M5S 1A7 Canada  
(Dated: March 12, 2024)*

Vacancy-ordered halide double perovskites hosting 4d/5d transition metals have emerged as a distinct platform for investigating unconventional magnetism arising out of the interplay of strong atomic spin-orbit coupling (SOC) and Coulomb interactions. Focusing on the  $d^2$  system  $\text{Cs}_2\text{WCl}_6$ , our *ab initio* electronic structure calculation reveals very narrow electronic bands, fulfilling the necessary condition to realize exotic orders. Using this input, we solve the many-body spin-orbit coupled single-site problem by exact diagonalization and show that the multiplet structure of  $\text{Cs}_2\text{WCl}_6$  hosts ground non-Kramers doublets on W, with vanishing dipole moment and a small gap to an excited magnetic triplet. Our work provides the rationale for the observed strong deviation from the classic Kotani behaviour in  $\text{Cs}_2\text{WCl}_6$  for the measured temperature dependence of the magnetic moment. The non-Kramers doublets on W exhibit non-zero quadrupolar and octupolar moments, and our calculated two-site exchange supports the dominance of inter-site octupolar exchange over quadrupolar interactions. We predict ferro-octupolar order with  $T_c \sim 5$  K, which may get somewhat suppressed by quantum fluctuations and disorder; this could be tested in future low-temperature experiments.

PACS numbers: 75.25.aj, 75.40.Gb, 75.70.Tj

Compounds crystallizing in the perovskite structure of general formula  $\text{ABX}_3$ , where A is an alkali or alkaline metal, B is a transition metal, and X is oxygen, nitrogen or halogen, are among the most intensely studied materials by condensed matter physicists and solid state chemists, due to their fascinating physical and chemical properties [1–6]. Ordered double perovskites  $\text{A}_2\text{BB}'\text{X}_6$  have structures derived from perovskite structure, formed when exactly half of B site cations is replaced by another B' cation, and a rock salt ordering between these two is achieved [7]. Oxide-based double perovskites (DPs) with 3d transition metal at B site and 4d/5d transition metal at B' site have been studied for the intriguing properties arising out of the interplay of strong correlation and strong spin-orbit coupling (SOC) [8]. To realize unconventional properties in such systems, it is desirable to reduce the electronic bandwidth, thereby pushing them closer to atomic limit which amplifies the role of local correlations as well as SOC effects. In this context, for instance,  $5d^4$  compounds like  $\text{Ba}_2\text{YIrO}_6$  with  $\text{Ir}^{5+}$  have been studied [9] by putting a nonmagnetic cation like Y at B site which leads to a reduced bandwidth compared with perovskites such as  $\text{SrIrO}_3$ . Nevertheless, the properties of such DPs remain debated; while some studies have argued for a nonmagnetic insulator in  $\text{Ba}_2\text{YIrO}_6$ , with proximity to excitonic magnetism or impurity-induced magnetism [10–12], *ab initio* and dynamical mean field theory studies instead find evidence for a considerable bandwidth, which can lead to long-range magnetic order [13] or at the very least to fluctuating local moments in the ground state [14]. Experiments on  $5d^1$  DPs, such as  $\text{Ba}_2\text{NaOsO}_6$  with  $\text{Os}^{7+}$  [15, 16] and

$\text{Ba}_2\text{MgReO}_6$  with  $\text{Re}^{6+}$  [17–20] have also revealed unusual forms of multipolar magnetism, reflecting the role of atomic SOC and the correlation effect at single site level. While multipolar magnetism has also been proposed and actively investigated in certain cubic  $5d^2$  osmate DPs [21–27], such as  $\text{Ba}_2\text{MgOsO}_6$  and  $\text{Ba}_2\text{ZnOsO}_6$ , conclusive evidence of multipolar order in these  $5d^2$  oxide DPs is lacking.

In this backdrop, vacancy-ordered DPs in which the second B' site is vacant, resulting in isolated  $\text{BX}_6$  octahedra bound electrostatically by A-site cations appear to be an ideal platform to investigate unconventional forms of magnetism. Vacancy-ordered DPs with  $\text{K}_2\text{PtCl}_6$  structure type were discovered way back in 1834 [28–30]. In recent times, vacancy-ordered DPs with monovalent cation at the A site and halide anion at the X site along with transition metal ions at the B site have been synthesized [31]. These halide DPs can also incorporate organic ligands and are of potential interest as photovoltaics [28]. The creation of vacant site at B' as well as the introduction of a halogen instead of oxygen leads to the expansion of lattice parameter by  $\sim 20$ -25%. One would then expect these compounds to be as close to the atomic limit as possible for a crystalline system. Transition metal-based vacancy ordered DPs may thus be thought of as model narrow-bandwidth systems to study exotic properties arising from strong correlation and atomic spin-orbit coupling (SOC). The vacancy-ordered DPs with  $\text{Os}^{4+}$  or  $\text{Ir}^{4+}$  ions at the B site tend to support this conjecture [32, 33]. In addition to  $d^4$  and  $d^5$  compounds, based on late transition metals, vacancy-ordered DPs with early transition metals like W, Mo or Ta have also been reported, which makes compounds with  $d^1$ ,  $d^2$  filling also accessible for investigation [34–36]. Compounds with  $d^2$  filling with the possible formation of  $J = 2$  moment are

\* corresponding author: tanusri@bose.res.in

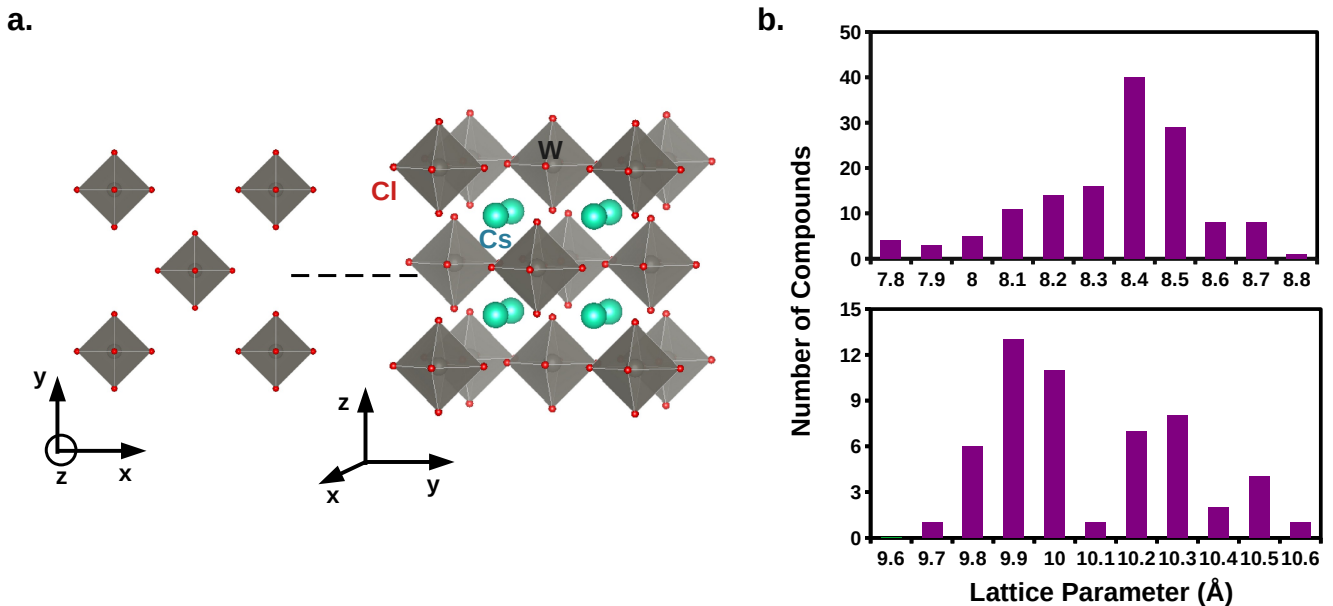


FIG. 1. **a.** Structure of  $\text{Cs}_2\text{WCl}_6$  vacancy ordered double perovskite halide in the  $\text{Fm}\bar{3}\text{m}$  (225) cubic spacegroup. **b.** Distribution of lattice parameters of double perovskite oxides (top) and vacancy ordered double perovskite chlorides (bottom) showing the significant lattice expansion in the latter class of compounds. For fair comparison only double perovskite oxides with spacegroup  $\text{Fm}\bar{3}\text{m}$  are included.

special since this is isomorphic to a d-orbital state with angular momentum  $L = 2$ .

DPs such as  $\text{Cs}_2\text{WCl}_6$  which have been synthesized through solid-state route [37] and hydrothermal synthesis [38] have been reported to show differing colours, suggesting that its properties show strong sample dependence and dependence on the synthesis method. A recent report claims to have synthesized phase pure  $\text{Cs}_2\text{WCl}_6$  under anaerobic and anhydrous conditions [39]. Remarkably, the magnetic characterization of this compound revealed peculiar temperature dependence of its magnetic susceptibility, at odds with the well-known Kotani model [40]. In this study, we focus on  $\text{Cs}_2\text{WCl}_6$ , with  $5d^2$  filling on W, and show that such vacancy-ordered DPs are ideal candidates to host multipolar magnetism, with the unusual nature of magnetic susceptibility arising from non-Kramers doublets on W. We make predictions for future experiments to verify our conclusions.

## I. CRYSTAL STRUCTURE

Vacancy ordered halide DP  $\text{Cs}_2\text{WCl}_6$  crystallizes in a face centered cubic crystal structure [39] with space group  $\text{Fm}\bar{3}\text{m}$  (225). Cs and W occupy the high symmetry 8c and 4a Wyckoff positions with coordinates (0.25, 0.25, 0.25) and (0, 0, 0), while Cl atoms sit at 24e Wyckoff positions with coordinates  $(x, 0, 0)$ ,  $x$  being a free parameter. Each W atom is surrounded by Cl atoms in perfect octahedra, and Cs atoms reside in the hollow between the  $[\text{WCl}_6]$  octahedra, with 12-fold coordination of Cl atoms, as shown in Fig. 1a.

Full geometry optimization, with fixed crystal symmetry, shows the important role of exchange-correlation functional in density functional theory (DFT). With the choice of PBE and PBEsol exchange-correlation functionals, the optimized volume is found to show a deviation of  $\sim 9.5\%$  and  $\sim 1\%$  from the experimentally measured volume, respectively, indicating the superiority of PBEsol over PBE. In subsequent DFT calculations, we have thus used PBEsol exchange-correlation functional. For DFT computational details see Appendix A. The W-Cl bond length in optimized geometry turned out to be  $2.377 \text{ \AA}$ , in comparison to W-O bond length of  $1.955 \text{ \AA}$  in  $\text{Sr}_2\text{CrWO}_6$ . The optimized lattice parameter turned out to be  $10.32 \text{ \AA}$ , significantly larger compared to that of that of  $\text{Sr}_2\text{CrWO}_6$  ( $7.8200 \text{ \AA}$ ) [41]. In this context, it is interesting to note that generally studied oxide DPs have substantially smaller lattice parameters compared to that of chlorides due to the smaller ionic radius of the O atom. This is evident from Fig. 1b, where the distribution of lattice parameters of known oxide DPs and vacancy-ordered chloride DPs, both having spacegroup symmetry  $\text{Fm}\bar{3}\text{m}$ , is plotted. While the lattice parameter values for oxides lie in the range  $7.8\text{-}8.8 \text{ \AA}$ , the corresponding values for vacancy-ordered chloride DPs lie in the range  $9.6\text{-}10.6 \text{ \AA}$ .

## II. ELECTRONIC STRUCTURE

Fig. 2 shows the non-spin polarized band structure and the corresponding orbital projected density of states in the wide energy range of  $-0.5$  to  $4 \text{ eV}$  around the Fermi

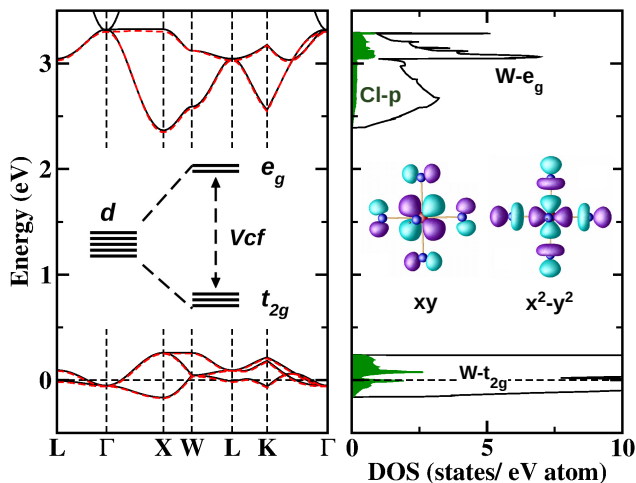


FIG. 2. (Left) Non spin-polarized bandstructure (solid black) together with the tight binding bands (dashed red) plotted along the high symmetry path of Brillouin zone. Inset shows the  $t_{2g}$ - $e_g$  crystal field splitting; (Right) The density of states projected on W- $d$  (solid black) and Cl- $p$  (shaded green) states. Inset shows the  $t_{2g}(x^2-y^2)$  and  $e_g(xy)$  Wannier functions with their lobes having different signs being colored differently.

energy ( $E_F$ ). The W- $d$  states are crystal field split into triply degenerate  $t_{2g}(xy, yz, zx)$  and doubly degenerate  $e_g(3z^2-r^2, x^2-y^2)$  states in the octahedral crystal field of Cl atoms. With  $d^2$  occupancy of  $W^{4+}$ , the Fermi level is crossed by  $t_{2g}$  states, admixed with Cl- $p$  due to finite W-Cl hybridization. The Cl- $p$  dominated states lie far below  $E_F$ , outside the range of the plot. W- $t_{2g}$  bands are found to possess a very narrow bandwidth of  $\sim 1$  eV, compared W bandwidth of  $\sim 2$  eV in  $Sr_2CrWO_6$  [42].

Starting from this DFT electronic structure, we obtain the W  $d$  only model through NMTO downfolding [43] in which all degrees of freedom other than W  $d$  are downfolded. The real space representation of this Hamiltonian in the Wannier basis of W  $d$  provides information on the onsite matrix and thus the  $t_{2g}$ - $e_g$  crystal field splitting, and on the W-W hopping integrals. The  $t_{2g}(xy)$  and  $e_g(x^2-y^2)$  W Wannier functions constructed through NMTO-downfolding is shown in the inset of Fig. 2. While the central part of the Wannier functions are shaped according to the respective symmetries of W  $d$  orbitals, the tails residing in the Cl atoms are shaped like  $p$ , showing formation of W-Cl  $\pi$  and  $\sigma$  bonding for  $t_{2g}$  and  $e_g$  Wannier functions, respectively.

The  $t_{2g}$ - $e_g$  crystal field ( $V_{cf}$ ) splitting turned out to be  $\sim 3.0$  eV, significantly smaller compared that found for corresponding 5d TM oxides, which is about 5 eV [12], arising from significant smaller W-Cl bond length vis-a-vis than in oxides. The resultant smaller value of the  $V_{cf}$  can further enhance the role of  $t_{2g}$ - $e_g$  interactions in determining the low energy physics, as discussed in Sec III. The narrow bandwidth of W- $d$  suffices the nearest neighbour (NN) tight-binding W  $d$  only Hamiltonian to faithfully represent the full DFT electronic structure as

Orbital	xy	xz	yz	$z^2$	$x^2-y^2$
xy	-0.0458	0.0	0.0	-0.0223	0.0
xz	0.0	0.0109	0.0111	0.0	0.0
yz	0.0	0.0111	0.0109	0.0	0.0
$z^2$	-0.0233	0.0	0.0	-0.0337	0.0
$x^2-y^2$	0.0	0.0	0.0	0.0	0.1089

TABLE I. Hopping matrix, obtained by NMTO downfolding calculation, between two nearest neighbour W atoms with a connecting vector  $(0.5, 0.5, 0)$ . All the energies are in eV unit.

shown in Fig. 2. by superimposing the NN tight binding bands (red) with the full band structure (black). Table 1 lists the hopping matrix, obtained by NMTO downfolding calculation, between two nearest neighbour W atoms with a connecting vector  $(0.5, 0.5, 0)$  in the  $xy$  plane. With the cubic symmetry, the corresponding matrices in the other planes can be obtained via  $C_3$  transformations about the  $[111]$  axis.

### III. PSEUDOSPIN HAMILTONIAN

Armed with this DFT input, we next solve the many-body spin-orbit entangled W  $d$  Hamiltonian in terms of its multiplet structure and pseudo spin representation.

#### A. Single-site model

The local single-site Hamiltonian for the  $d^2$  configuration is given by

$$H_{loc} = H_{CEF} + H_{SOC} + H_{int} \quad (1)$$

where  $H_{CEF}$  incorporates the octahedral  $t_{2g}$ - $e_g$  crystal field splitting,  $H_{SOC}$  captures the atomic SOC, and  $H_{int}$  encapsulates electron-electron interactions.

We work in the orbital basis, labelling the  $t_{2g}$  orbitals by  $\ell \equiv \{1, 2, 3\}$  and  $e_g$  orbitals by  $\ell = 4, 5$ . The octahedral CEF term is then given by:

$$H_{CEF} = V_{cf} \sum_{\ell=4,5} \sum_s n_{\ell,s} \quad (2)$$

where  $s = \uparrow, \downarrow$  is the spin. The SOC term is

$$H_{SOC} = \frac{\lambda}{2} \sum_{\ell, \ell'} \sum_{s, s'} \langle \ell | \mathbf{L} | \ell' \rangle \cdot \langle s | \boldsymbol{\sigma} | s' \rangle c_{\ell s}^\dagger c_{\ell' s'} \quad (3)$$

where  $\boldsymbol{\sigma}$  is the vector of Pauli matrices, and  $\mathbf{L}$  are the  $d$ -orbital angular momentum matrices. The Kanamori interaction is given by

$$H_{int} = U \sum_{\ell} n_{\ell\uparrow} n_{\ell\downarrow} + \left( U' - \frac{J_H}{2} \right) \sum_{\ell > \ell'} n_{\ell} n_{\ell'} \quad (4)$$

$$- J_H \sum_{\ell \neq \ell'} \mathbf{S}_{\ell} \cdot \mathbf{S}_{\ell'} + J_H \sum_{\ell \neq \ell'} c_{\ell\uparrow}^\dagger c_{\ell\downarrow}^\dagger c_{\ell'\downarrow} c_{\ell'\uparrow}$$

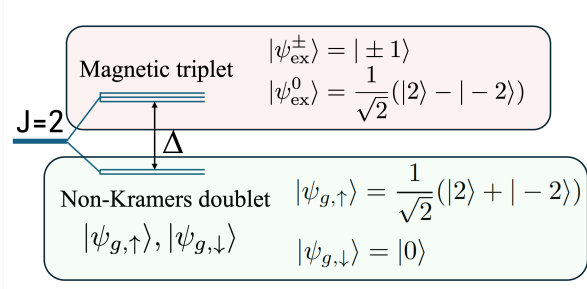


FIG. 3. Schematic diagram of  $J = 2$  multiplet weakly split into a non-Kramers doublet and gapped magnetic triplet. The weak splitting  $\Delta$  is induced by  $t_{2g}-e_g$  interactions which can be captured by a Stevens operator (see text).

where  $U$  and  $U'$  are the intra-orbital and inter-orbital Hubbard interactions respectively,  $J_H$  is the Hund's coupling.  $\mathbf{S}_\ell = (1/2)c_{\ell s}^\dagger \boldsymbol{\sigma}_{s,s'} c_{\ell s'}$  denotes the spin operator for orbital  $\ell$ , while the number operator  $n_\ell \equiv n_{\ell\uparrow} + n_{\ell\downarrow}$  counts the total number of electrons in orbital  $\ell$ . Assuming spherical symmetry of the Coulomb interaction,  $U' = U - 2J_H$  [44].

Diagonalizing  $H_{\text{loc}}$ , we find a low energy manifold with five states. These five low energy states form part of a  $J = 2$  total angular momentum manifold, which is weakly split in the octahedral environment: a ground state non-Kramers doublet and an excited triplet which is split from the doublet by a small energy gap  $\Delta \sim \lambda^2 J_H / V_{cf}$  [23]. This is schematically depicted in Fig. 3. The next set of excited levels,  $J = 0$  and  $J = 1$ , are split by a large energy gap  $\sim \lambda$ ; we ignore these high energy states for discussing the spin susceptibility and entropy at moderate temperatures. In the limit of  $t_{2g}-e_g$  crystal field splitting  $V_{cf} \rightarrow \infty$ , the gap  $\Delta \rightarrow 0$ , and the two-electron ground state of  $H_{\text{loc}}$  is a five-fold degenerate  $J = 2$  multiplet obtained from spin-orbit coupling of  $L_{\text{eff}} = 1$  and  $S_{\text{eff}} = 1$  of two electrons in the  $t_{2g}$  orbital.

We fix parameters  $\lambda = 0.35$  eV,  $U = 2.5$  eV, and  $J_H = 0.25$  eV; this choice of  $\lambda$ ,  $J_H$  reproduces the peaks seen in resonant inelastic X-ray scattering (RIXS) measurements on closely related  $d^4$  osmium halide  $\text{K}_2\text{OsCl}_6$  upto a scale  $\sim 1.2$  eV [45]. Remarkably, this choice is also very similar to that obtained in previous work on  $5d$  oxides [12, 46]. Using our *ab initio* estimate of  $V_{cf} \approx 3.0$  eV, a single-site exact diagonalization yields  $\Delta \approx 7$  meV. However, the single-site model, as used in present study is only an *effective* model for the low energy physics of the  $\text{WCl}_6$  octahedra with seven sites. Thus, the DFT estimated  $V_{cf}$  can get renormalized in the context of single-site model [45], and it may be considered as a tuning parameter. Decreasing  $V_{cf} = 1.7$  eV, for example, increases the low energy doublet-triplet splitting of the  $J = 2$  multiplet to  $\Delta \approx 15$  meV while leaving the rest of the spectrum upto  $\sim 1.2$  eV nearly unchanged. Indeed, the correct thing to do at low energy is to write an effective Hamiltonian for the  $J = 2$  multiplet in terms of Stevens operators [47]

with

$$H_S = -\frac{\Delta}{120}(O_{40} + 5O_{44}) \quad (5)$$

$$O_{40} = 35J_z^4 - (30J(J+1) - 25)J_z^2 + 3J^2(J+1)^2 - 6J(J+1) \quad (6)$$

$$O_{44} = \frac{1}{2}(J_+^4 + J_-^4), \quad (7)$$

which splits the  $J = 2$  multiplet, leading to the doublet-triplet gap  $\Delta$  [23, 25]. Following this spirit, in the following, we will use  $\Delta$  as a fitting parameter to explore the consequences for the spin susceptibility and entropy.

In terms of  $J_z$  eigenstates, the wavefunctions of the pseudospin-1/2 non-Kramers doublet ground state are given by (see Fig. 3):

$$|\psi_{g,\uparrow}\rangle = \frac{1}{\sqrt{2}}(|2\rangle + |-2\rangle); \quad |\psi_{g,\downarrow}\rangle = |0\rangle \quad (8)$$

while the excited state triplet wavefunctions are given by

$$|\psi_{e,\pm 1}\rangle = |\pm 1\rangle; \quad |\psi_{e,0}\rangle = \frac{1}{\sqrt{2}}(|2\rangle - |-2\rangle) \quad (9)$$

### B. Spin susceptibility and effective moment: Breakdown of the Kotani result

Using these wavefunctions, and the energy gap  $\Delta$ , the spin susceptibility, as given below, can be computed;

$$\chi(T) = (g\mu_B)^2 \left[ \frac{\frac{8}{\Delta} + (\frac{2}{T} - \frac{8}{\Delta})e^{-\Delta/T}}{2 + 3e^{-\Delta/T}} \right] \quad (10)$$

We define  $\mu_{\text{eff}}^2(T) = \frac{1}{g^2} \chi(T)T$ , which leads to

$$\mu_{\text{eff}}^2(T) = \mu_B^2 T \left[ \frac{\frac{8}{\Delta} + (\frac{2}{T} - \frac{8}{\Delta})e^{-\Delta/T}}{2 + 3e^{-\Delta/T}} \right] \quad (11)$$

To compare with the published experimental data [39], we plot this in units of  $\mu_B^2$ , setting  $y_{\text{eff}} = \mu_{\text{eff}}/\mu_B$ , so that

$$y_{\text{eff}}^2(T) = T \left[ \frac{\frac{8}{\Delta} + (\frac{2}{T} - \frac{8}{\Delta})e^{-\Delta/T}}{2 + 3e^{-\Delta/T}} \right] \quad (12)$$

We note that our result in Eq. 12 is only valid for  $T/\lambda \ll 1$  since we do not account for higher spin-orbit levels which are split off by scales comparable to  $\lambda$ . These high energy states will give rise to a background van Vleck contribution [40, 48]. We can account for such a constant background susceptibility via a phenomenological additional constant  $\alpha$ , which leads to

$$y_{\text{eff}}^2(T) = T \left[ \frac{\frac{8}{\Delta} + (\frac{2}{T} - \frac{8}{\Delta})e^{-\Delta/T}}{2 + 3e^{-\Delta/T}} \right] + \alpha T \quad (13)$$

We will use this functional form to fit the experimental data assuming that single-site physics dominates, with

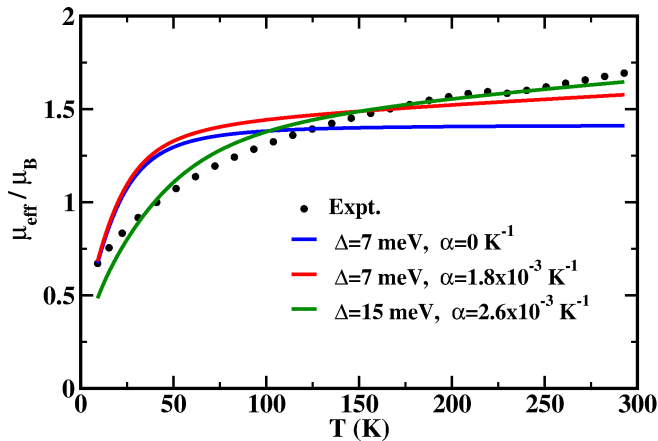


FIG. 4. Comparison of experimental and calculated temperature dependence of effective magnetic moment ( $\mu_{\text{eff}}$ ) in unit of  $\mu_B$  for  $\text{Cs}_2\text{WCl}_6$ . The black filled circles represent experimental data while the blue, red, green curves are obtained using Eqn.13 for different values of  $\Delta$  and  $\alpha$  as indicated.

$\Delta, \alpha$  being treated as fit parameters. We ignore residual impurity effects arising from traces of O in place of Cl [39] which might lead to an additional Curie contribution to  $\chi(T)$  at the lowest temperatures.

Fig. 4 shows the effective magnetic moment (in units of  $\mu_B$ ) corresponding to various values of  $\Delta, \alpha$ , plotted as a function of temperature, in comparison to the experimental data [39]. In all cases, we find that the low temperature moment drops to zero, consistent with the experimental trend, and at odds with the Kotani result [39, 40]. To choose  $\Delta$  and  $\alpha$ , we first used  $\Delta=7$  meV, obtained based on our *ab initio* estimate of  $V_{cf}$  with  $\alpha = 0$  which ignores all higher energy levels split off by a scale  $\sim \lambda$  as well as possible contribution of impurities. To explain the linear slope at higher temperatures, we find it is important to include the van Vleck contribution, given by non-zero value of  $\alpha$ . We show the case with  $\Delta=7$  meV and  $\alpha=1.8 \times 10^{-3} \text{ K}^{-1}$  as an example, where  $\Delta$  is still constrained. The best fit to experimental data is obtained employing  $\Delta=15$  meV and  $\alpha=2.6 \times 10^{-3} \text{ K}^{-1}$ . The computed data captures the measured temperature variation almost over the entire temperature range. We note that, upto factors, the scale of  $\alpha$  is  $\mathcal{O}(1/\lambda)$ .

### C. Single site entropy

In the low energy limit, the single-site entropy from the non-Kramers and gapped triplet is given by

$$\frac{S}{k_B} = \frac{3(\Delta/T)}{3 + 2e^{\Delta/T}} + \ln(2 + 3e^{-\Delta/T}). \quad (14)$$

This exhibits a plateau at  $S = k_B \ln 2$  for  $T \lesssim \Delta/4$ . To estimate numbers for  $\text{Cs}_2\text{WCl}_6$ , if we set  $\Delta \approx 15$  meV which fits the effective moment data reasonably well as shown above, this entropy plateau should occur for

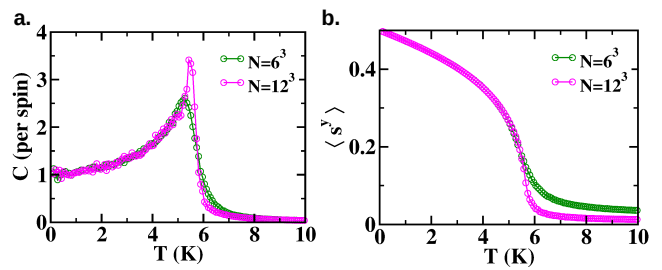


FIG. 5. Classical Monte Carlo simulation results for (a) the specific heat per spin ( $C$ ) as a function of temperature showing a phase transition at  $T_c \approx 5.5 \text{ K}$ , and (b) the ferro-octupolar order parameter  $\langle s^y \rangle$  as a function of temperature showing its onset for  $T < T_c$ . Simulations are for the model Hamiltonian  $H_{\text{spin}}$  with parameters given in the text, and system sizes  $N = 6^3, 12^3$  spins.

$T \lesssim 40 \text{ K}$ . This entropy will get quenched at low temperature once the non-Kramers develop inter-site correlations and form a long-range ordered state. We next estimate these inter-site interactions between the non-Kramers doublets.

### D. Pseudospin interactions and multipolar order

We define the pseudospin-1/2 operators which act on the non-Kramers doublet in terms of the  $J = 2$  angular momentum operators as

$$s^x \equiv (J_x^2 - J_y^2)/4\sqrt{3}, \quad (15)$$

$$s^y \equiv \overline{J_x J_y J_z}/2\sqrt{3}, \quad (16)$$

$$s^z \equiv (3J_z^2 - J(J+1))/12, \quad (17)$$

with overline denoting symmetrization. On symmetry grounds, the most general pseudospin-1/2 exchange Hamiltonian for nearest neighbors is given by

$$\begin{aligned} H_{\text{spin}} = \sum_{(i,j)} & [K_y s_i^y s_j^y + (K_x \cos^2 \phi_{ij} + K_z \sin^2 \phi_{ij}) s_i^x s_j^x \\ & + (K_x - K_z) \sin \phi_{ij} \cos \phi_{ij} (s_i^x s_j^z + s_i^z s_j^x) \\ & + (K_x \sin^2 \phi_{ij} + K_z \cos^2 \phi_{ij}) s_i^z s_j^z] \end{aligned} \quad (18)$$

where  $\phi_{ij} = \{0, 2\pi/3, 4\pi/3\}$  correspond to nearest neighbors  $(i, j)$  in the  $\{xy, yz, zx\}$  planes. Here,  $K_x, K_z$  are quadrupolar couplings,  $K_y$  is the octupolar coupling, and the spin operators ( $s^x, s^y, s^z$ ) act within the non-Kramers doublet space [24, 25, 27, 49]. Using the single-site Hamiltonian and hopping matrices from our *ab initio* calculations, with Hubbard  $U = 2.5$  eV in the Kanamori interaction, we have employed an exact Schrieffer-Wolff method to extract the two-site exchange couplings [24]; we find  $(K_x, K_y, K_z) \approx (-0.04, -0.56, 0.24)$  meV. The dominant ferro-octupolar exchange  $K_y$  suggests that the ground state of  $\text{Cs}_2\text{WCl}_6$  should have ferro-octupolar order.

Fig. 5 shows results from the classical Monte Carlo simulations of  $H_{\text{spin}}$ , treating the pseudospin-1/2 operators

as classical vectors (of length=1/2) with anisotropic and bond-dependent interactions; we have used  $4 \times 10^4$  sweeps for equilibration and measurements on system sizes with  $N = 6^3$  and  $N = 12^3$  spins. The specific heat peak in Fig. 5(a) signals a phase transition at  $T_c \approx 5.5\text{K}$ , and from Fig. 5(b) we find the development of ferrooctupolar order for  $T < T_c$ . In experiments,  $T_c$  may be somewhat suppressed by the effects of quantum fluctuations and possible weak disorder.

#### IV. SUMMARY AND DISCUSSION

The vacancy ordered halide DPs having 4d or 5d transition metals at B site are a unique class of compounds where a small bandwidth and strong SOC can lead to interesting physics. Understanding the local physics of this class of materials is the first step in exploring the wide range of phenomena which might be realized in future experiments. Taking this first step, we have shown that the  $d^2$  DPs in this category can realize multipolar magnetism. In particular, the low energy physics of these materials may be described in terms of a non-Kramers doublet split off from a gapped magnetic triplet. At the single-site level, this explains the puzzling strong deviation from the Kotani plot, as found in recent experiment.[39] We find that there are weak interactions between the non-Kramers doublets which stems from the very flat bands and weak intersite hopping found in our *ab initio* calculations. Such inter-site interactions, which we have computed, are expected to lead to long-range ferro-octupolar order with  $T_c \approx 5.5\text{K}$ . The existence of non-Kramers doublets and their consequences for magnetism have previously been proposed and partially explored in the  $5d^2$  osmate DPs such as  $\text{Ba}_2\text{MgOsO}_6$  and  $\text{Ba}_2\text{ZnOsO}_6$ , but there is yet to be conclusive evidence on this [21–25, 27]. Our findings on  $\text{Cs}_2\text{WCl}_6$  thus add an important step forward by expanding the set of candidate  $5d$  quantum materials which may exhibit unconventional multipolar magnetism.

While this work was being written up, we came across a recently submitted preprint by Li et al [50] which explores these halide DP compounds using a combination of DFT, exact diagonalization, and cluster diagonalization. At the single-site level, their theory for  $\text{Cs}_2\text{WCl}_6$  finds results which are largely in agreement with the Kotani plot, and at odds with our results. We attribute this to the fact that the original Kotani work [40] as well as the work by Li et al [50] consider a  $t_{2g}$  only model, ignoring completely the effect of  $e_g$  orbitals, while we show that taking into account the effect of the  $e_g$  orbitals either in microscopics or via effective Stevens operators is important in splitting the five-fold  $J = 2$  multiplet, and, thereby stabilizing a non-Kramers doublet as ground state. It is to be noted that due to the substantially larger metal-ligand bond length in vacancy-ordered halides in comparison to oxides, the crystal field splitting is generally smaller than that in commonly considered oxides, which might

be further renormalized to smaller values within an effective single-site metal-only model. Such renormalization of high energy parameters in single-site models versus full octahedral cluster was also noted for modelling RIXS in  $\text{K}_2\text{OsCl}_6$  [45].

The implications of this difference are quite important. For instance, the paper by Li, *et al* [50], only finds effective moments  $\mu_{\text{eff}}(T)$  which are in agreement with experiments when they study a two-site model. However, such a two-site cluster kills the magnetic moment by forming a nearest-neighbor singlet. It is unclear if this picture of valence bond singlet formation is the appropriate description of magnetism on the full lattice. In our work, by contrast, the effective moment vanishes due to the formation of a single site non-Kramers doublet which has no magnetic dipole moment degrees of freedom. Furthermore, our computed exchange interactions show that this material might host ferro-octupolar order on the FCC lattice rather than the Li, *et al* [50] proposed scenario of singlets formed from  $J = 2$  moments on neighboring sites.

Turning to concrete proposals which can serve to experimentally distinguish our proposal from the proposal by Li *et al* [50], we suggest specific heat and inelastic neutron scattering measurements. The proposed ferro-octupolar transition temperature is  $T_c \approx 5.5\text{K}$  which though may be somewhat suppressed by disorder and quantum fluctuations. In light of this, low-temperature measurements like specific heat and muon spin resonance measurements [23, 51–55] may be able used to explore this hidden phase, albeit the fact that further probes would be needed to distinguish such a transition from ordinary magnetic order. Inelastic neutron scattering measurements [21] could be used to detect a spin-gap  $\sim \Delta$  in the intermediate temperature regime  $T_c \ll T \ll \Delta$  which would bolster the case for our scenario and also serve to extract  $\Delta$ . We expect that the magnetic entropy per spin should show a plateau  $S \sim k_B \ln 2$  at intermediate temperatures in the window  $T_c \ll T \lesssim \Delta/4$  where the uncorrelated non-Kramers doublet physics is expected to survive. Finally,  $^{35}\text{Cl}$ ,  $^{37}\text{Cl}$ , and  $^{133}\text{Cs}$  NMR measurements could be potentially used to look for more detailed local signatures of magnetism at low temperatures as has been done using  $^{23}\text{Na}$  in certain oxide-based DPs [15, 16, 26, 27].

#### ACKNOWLEDGMENTS

TS-D acknowledges discussions with Tony Cheetham and Pratap Vishnoi. This research was funded by DST India (KP and TS-D) and NSERC of Canada (AP). We acknowledge funding from a SERB-India Vajra Fellowship VJR/2019/000076 (AP, TS-D) which enabled this collaboration. TS-D acknowledges a J.C.Bose National Fellowship (grant no. JCB/2020/000004) for support.

## Appendix A: Computational Details

The first principles DFT calculations were performed using projector augmented-wave [56] pseudo-potential method in plane wave basis, as implemented within the Vienna Ab-initio simulation package [57]. We considered the exchange correlation functionals within generalised gradient approximation of PBE [58] and PBEsol [59]. A plane-wave energy cutoff of 600 eV and Brillouin Zone sampling with  $8 \times 8 \times 8$  Monkhorst-Pack grids were found to be sufficient for the convergence of energies and forces. For structural relaxations, ions were allowed to move until atomic forces became less than  $0.0001 \text{ eV/\text{Å}}^0$ .

For the extraction of a few band tight binding Hamiltonian out of full GGA calculation which can be used

as the input to the many-body Hamiltonian, N-th orbital muffin-tin orbital (NMTO) downfolding calculations were carried out [43]. The consistency of results obtained in plane wave and LMTO basis was cross-checked in terms of density of states and band structures. Starting from a full DFT calculation, it arrives at a few-orbital Hamiltonian in an energy-selected, effective Wannier function basis, by integrating out the degrees of freedom that are not of interest. The NMTO technique, which is not yet available in its self-consistent form, relies on the self-consistent potential parameters obtained out of linear muffin-tin orbital (LMTO) calculations [60]. The obtained tight-binding parameters were found in good agreement with maximally localized Wannier function calculations [61].

- 
- [1] M. B. Salamon and M. Jaime, The physics of manganites: Structure and transport, *Rev. Mod. Phys.* **73**, 583 (2001).
- [2] J. M. D. Coey, M. Viret and S. von Molnár, Mixed-valence manganites, *Advances in Physics* **48**, 167 (1999).
- [3] A. K. Jena, A. Kulkarni, and T. Miyasaka, Halide perovskite photovoltaics: Background, status, and future prospects, *Chemical Reviews* **119**, 3036 (2019).
- [4] W.-J. Yin, J.-H. Yang, J. Kang, Y. Yan, and S.-H. Wei, Halide perovskite materials for solar cells: a theoretical review, *J. Mater. Chem. A* **3**, 8926 (2015).
- [5] M. A. Pena and J. L. G. Fierro, Chemical structures and performance of perovskite oxides, *Chemical Reviews* **101**, 1981 (2001).
- [6] C. N. R. Rao, A. K. Cheetham, and R. Mahesh, Giant magnetoresistance and related properties of rare-earth manganates and other oxide systems, *Chemistry of Materials* **8**, 2421 (1996).
- [7] S. Vasala and M. Karppinen,  $A_2B'B''O_6$  perovskites: A review, *Progress in Solid State Chemistry* **43**, 1 (2015).
- [8] T. Saha-Dasgupta, Double perovskites with 3d and 4d/5d transition metals: compounds with promises, *Materials Research Express* **7**, 014003 (2020).
- [9] T. Dey, A. Maljuk, D. V. Efremov, O. Kataeva, S. Gass, C. G. F. Blum, F. Steckel, D. Gruner, T. Ritschel, A. U. B. Wolter, J. Geck, C. Hess, K. Koepernik, J. van den Brink, S. Wurmehl, and B. Büchner,  $Ba_2YrO_6$ : A cubic double perovskite material with  $ir^{5+}$  ions, *Phys. Rev. B* **93**, 014434 (2016).
- [10] G. Khaliullin, Excitonic magnetism in van Vleck-type  $d^4$  Mott insulators, *Phys. Rev. Lett.* **111**, 197201 (2013).
- [11] O. N. Meetei, W. S. Cole, M. Randeria, and N. Trivedi, Novel magnetic state in  $d^4$  Mott insulators, *Phys. Rev. B* **91**, 054412 (2015).
- [12] A. Paramekanti, D. J. Singh, B. Yuan, D. Casa, A. Said, Y.-J. Kim, and A. D. Christianson, Spin-orbit coupled systems in the atomic limit: rhenates, osmates, iridates, *Phys. Rev. B* **97**, 235119 (2018).
- [13] S. Bhowal, S. Baidya, I. Dasgupta, and T. Saha-Dasgupta, Breakdown of  $j = 0$  nonmagnetic state in  $d^4$  iridate double perovskites: A first-principles study, *Phys. Rev. B* **92**, 121113 (2015).
- [14] H. Schnait, D. Bauernfeind, T. Saha-Dasgupta, and M. Aichhorn, Small moments without long-range magnetic ordering in the zero-temperature ground state of the double perovskite iridate  $Ba_2YrO_6$ , *Phys. Rev. B* **106**, 035132 (2022).
- [15] L. Lu, M. Song, W. Liu, A. P. Reyes, P. Kuhns, H. O. Lee, I. R. Fisher, and V. F. Mitrović, Magnetism and local symmetry breaking in a Mott insulator with strong spin orbit interactions, *Nat. Comm.* **8**, 14407 (2017).
- [16] W. Liu, R. Cong, E. Garcia, A. Reyes, H. Lee, I. Fisher, and V. Mitrović, Phase diagram of  $Ba_2NaOsO_6$ , a Mott insulator with strong spin orbit interactions, *Physica B: Condensed Matter* **536**, 863 (2018).
- [17] D. Hirai and Z. Hiroi, Successive symmetry breaking in a  $j_{\text{eff}} = 3/2$  quartet in the spin-orbit coupled insulator  $Ba_2MgReO_6$ , *J. Phys. Soc. Jpn.* **88**, 064712 (2019).
- [18] D. Hirai, H. Sagayama, S. Gao, H. Ohsumi, G. Chen, T. Arima, and Z. Hiroi, Detection of multipolar orders in the spin-orbit-coupled  $5d$  Mott insulator  $Ba_2MgReO_6$ , *Phys. Rev. Research* **2**, 022063 (2020).
- [19] J.-R. Soh, M. E. Merkel, L. Pourousskii, I. Zivkovic, O. Malanyuk, J. Pasztorova, S. Francoual, D. Hirai, A. Urru, D. Tolj, D. Fiore-Mosca, O. Yazyev, N. A. Spaldin, C. Ederer, and H. M. Ronnow, Spectroscopic signatures and origin of a hidden order in  $Ba_2MgReO_6$  (2023), [arXiv:2312.01767 \[cond-mat.str-el\]](https://arxiv.org/abs/2312.01767).
- [20] D. F. Mosca, C. Franchini, and L. V. Pourovskii, Interplay of superexchange and vibronic effects in the hidden order of  $Ba_2MgReO_6$  unravelled from first principles (2024), [arXiv:2402.15564 \[cond-mat.str-el\]](https://arxiv.org/abs/2402.15564).
- [21] D. D. Maharaj, G. Sala, M. B. Stone, E. Kermarrec, C. Ritter, F. Fauth, C. A. Marjerrison, J. E. Greedan, A. Paramekanti, and B. D. Gaulin, Octupolar versus néel order in cubic  $5d^2$  double perovskites, *Phys. Rev. Lett.* **124**, 087206 (2020).
- [22] A. Paramekanti, D. D. Maharaj, and B. D. Gaulin, Octupolar order in  $d$ -orbital Mott insulators, *Phys. Rev. B* **101**, 054439 (2020).
- [23] S. Voleti, D. D. Maharaj, B. D. Gaulin, G. Luke, and A. Paramekanti, Multipolar magnetism in  $d$ -orbital systems: Crystal field levels, octupolar order, and orbital loop currents, *Phys. Rev. B* **101**, 155118 (2020).
- [24] S. Voleti, A. Haldar, and A. Paramekanti, Octupolar order and Ising quantum criticality tuned by strain and dimensionality: Application to  $d$ -orbital Mott insulators,

- Phys. Rev. B* **104**, 174431 (2021).
- [25] G. Khaliullin, D. Churchill, P. P. Stavropoulos, and H.-Y. Kee, Exchange interactions, Jahn-Teller coupling, and multipole orders in pseudospin one-half  $5d^2$  Mott insulators, *Phys. Rev. Research* **3**, 033163 (2021).
- [26] R. Cong, E. Garcia, P. C. Forino, A. Tasseti, G. Allodi, A. P. Reyes, P. M. Tran, P. M. Woodward, C. Franchini, S. Sanna, and V. F. Mitrović, Effects of charge doping on Mott insulator with strong spin-orbit coupling,  $\text{Ba}_2\text{Na}_{1-x}\text{Ca}_x\text{OsO}_6$ , *Phys. Rev. Mater.* **7**, 084409 (2023).
- [27] S. Voleti, K. Pradhan, S. Bhattacharjee, T. Saha-Dasgupta, and A. Paramekanti, Probing octupolar hidden order via Janus impurities, *npj Quantum Materials* **8**, 42 (2023).
- [28] A. E. Fedorovskiy, N. A. Drigo, and M. K. Nazeeruddin, The role of Goldschmidt's tolerance factor in the formation of  $\text{A}_2\text{BX}_6$  double halide perovskites and its optimal range, *Small Methods* **4**, 1900426 (2020).
- [29] B. Lee, C. C. Stoumpos, N. Zhou, F. Hao, C. Malliakas, C.-Y. Yeh, T. J. Marks, M. G. Kanatzidis, and R. P. H. Chang, Air-stable molecular semiconducting iodosalts for solar cell applications:  $\text{Cs}_2\text{SnI}_6$  as a hole conductor, *Journal of the American Chemical Society* **136**, 15379 (2014), PMID: 25299304.
- [30] A. E. Maughan, A. M. Ganose, D. O. Scanlon, and J. R. Neilson, Perspectives and design principles of vacancy-ordered double perovskite halide semiconductors, *Chemistry of Materials* **31**, 1184 (2019).
- [31] W. Rahim, A. Cheng, C. Lyu, T. Shi, Z. Wang, D. O. Scanlon, and R. G. Palgrave, Geometric analysis and formability of the cubic  $\text{A}_2\text{BX}_6$  vacancy-ordered double perovskite structure, *Chemistry of Materials* **32**, 9573 (2020).
- [32] M. Saura-Múzquiz, M. Avdeev, H. E. A. Brand, and B. J. Kennedy, Structural and magnetic properties of some vacancy-ordered osmium halide perovskites, *Inorganic Chemistry* **61**, 15961 (2022).
- [33] S.-S. Bao, D. Wang, X.-D. Huang, M. Etter, Z.-S. Cai, X. Wan, R. E. Dinnebier, and L.-M. Zheng,  $\text{Na}_2\text{Ir}^{\text{IV}}\text{Cl}_6$ : Spin-orbital-induced semiconductor showing hydration-dependent structural and magnetic variations, *Inorganic Chemistry* **57**, 13252 (2018).
- [34] H. Ishikawa, T. Yajima, A. Matsuo, and K. Kindo, Ligand dependent magnetism of the  $J_{\text{eff}} = 3/2$  Mott insulator  $\text{Cs}_2\text{MX}_6$  ( $M = \text{Ta}, \text{Nb}$ ,  $X = \text{Br}, \text{Cl}$ ), *Journal of Physics: Condensed Matter* **33**, 125802 (2021).
- [35] H. Ishikawa, T. Takayama, R. K. Kremer, J. Nuss, R. Dinnebier, K. Kitagawa, K. Ishii, and H. Takagi, Ordering of hidden multipoles in spin-orbit entangled  $5d^1$  Ta chlorides, *Phys. Rev. B* **100**, 045142 (2019).
- [36] A. Mansouri Tehrani, J.-R. Soh, J. Pásztorová, M. E. Merkel, I. Živković, H. M. Ronnow, and N. A. Spaldin, Charge multipole correlations and order in  $\text{Cs}_2\text{TaCl}_6$ , *Phys. Rev. Res.* **5**, L012010 (2023).
- [37] C. D. Kennedy and R. D. Peacock, 629. complex chlorides and bromides of quadrivalent tungsten, *J. Chem. Soc.* , 3392 (1963).
- [38] Z. Liu, X. Qin, Q. Chen, Q. Chen, Y. Jing, Z. Zhou, Y. S. Zhao, J. Chen, and X. Liu, Highly stable lead-free perovskite single crystals with NIR emission beyond 1100nm, *Advanced Optical Materials* **10**, 2201254 (2022).
- [39] E. E. Morgan, G. T. Kent, A. Zohar, A. O'Dea, G. Wu, A. K. Cheetham, and R. Seshadri, Hybrid and inorganic vacancy-ordered double perovskites  $\text{A}_2\text{WCl}_6$ , *Chemistry of Materials* **35**, 7032 (2023).
- [40] M. Kotani, On the magnetic moment of complex ions. (i), *Journal of the Physical Society of Japan* **4**, 293 (1949).
- [41] J. B. Philipp, P. Majewski, L. Alff, A. Erb, R. Gross, T. Graf, M. S. Brandt, J. Simon, T. Walther, W. Mader, D. Topwal, and D. D. Sarma, Structural and doping effects in the half-metallic double perovskite  $\text{A}_2\text{CrWO}_6$  ( $A = \text{Sr}, \text{Ba}$ , and  $\text{Ca}$ ), *Phys. Rev. B* **68**, 144431 (2003).
- [42] H. Das, M. De Raychaudhury, and T. Saha-Dasgupta, Moderate to large magneto-optical signals in high Tc double perovskites, *Applied Physics Letters* **92**, 201912 (2008).
- [43] O. K. Andersen and T. Saha-Dasgupta, Muffin-tin orbitals of arbitrary order, *Phys. Rev. B* **62**, R16219 (2000).
- [44] A. Georges, L. d. Medici, and J. Mravlje, Strong correlations from Hund's coupling, *Annual Review of Condensed Matter Physics* **4**, 137 (2013).
- [45] P. Warzanowski, M. Magnaterra, P. Stein, G. Schlicht, Q. Faure, C. J. Sahle, T. Lorenz, P. Becker, L. Bohatý, M. Moretti Sala, G. Monaco, P. H. M. van Loosdrecht, and M. Grüninger, Electronic excitations in  $5d^4 j = 0$   $\text{Os}^{4+}$  halides studied by resonant inelastic x-ray scattering and optical spectroscopy, *Phys. Rev. B* **108**, 125120 (2023).
- [46] B. Yuan, J. P. Clancy, A. M. Cook, C. M. Thompson, J. Greedan, G. Cao, B. C. Jeon, T. W. Noh, M. H. Upton, D. Casa, T. Gog, A. Paramekanti, and Y.-J. Kim, Determination of Hund's coupling in  $5d$  oxides using resonant inelastic x-ray scattering, *Phys. Rev. B* **95**, 235114 (2017).
- [47] K. W. H. Stevens, Matrix elements and operator equivalents connected with the magnetic properties of rare earth ions, *Proceedings of the Physical Society. Section A* **65**, 209 (1952).
- [48] J. H. Van Vleck, On dielectric constants and magnetic susceptibilities in the new quantum mechanics part iii—application to dia- and paramagnetism, *Phys. Rev.* **31**, 587 (1928).
- [49] D. Churchill and H.-Y. Kee, Competing multipolar orders in a face-centered cubic lattice: Application to the osmium double perovskites, *Phys. Rev. B* **105**, 014438 (2022).
- [50] Y. Li, R. Seshadri, S. D. Wilson, A. K. Cheetham, and R. Valenti, *Origins of temperature-dependent magnetism in open-shell  $4d$  and  $5d$  halide perovskites* (2024), arXiv:2402.14064 [cond-mat.str-el].
- [51] C. M. Thompson, C. A. Marjerrison, A. Z. Sharma, C. R. Wiebe, D. D. Maharaj, G. Sala, R. Flacau, A. M. Hallas, Y. Cai, B. D. Gaulin, G. M. Luke, and J. E. Greedan, Frustrated magnetism in the double perovskite  $\text{La}_2\text{LiOsO}_6$ : A comparison with  $\text{La}_2\text{LiRuO}_6$ , *Phys. Rev. B* **93**, 014431 (2016).
- [52] K. M. Kojima, Y. Fudamoto, M. Larkin, G. M. Luke, J. Merrin, B. Nachumi, Y. J. Uemura, M. Hase, Y. Sasago, K. Uchinokura, Y. Ajiro, A. Revcolevschi, and J.-P. Renard, Antiferromagnetic order with spatially inhomogeneous ordered moment size of Zn- and Si-doped  $\text{CuGeO}_3$ , *Phys. Rev. Lett.* **79**, 503 (1997).
- [53] C. A. Marjerrison, C. M. Thompson, A. Z. Sharma, A. M. Hallas, M. N. Wilson, T. J. S. Munsie, R. Flacau, C. R. Wiebe, B. D. Gaulin, G. M. Luke, and J. E. Greedan, Magnetic ground states in the three  $\text{Os}^{6+}$  ( $5d^2$ ) double perovskites  $\text{Ba}_2\text{MOsO}_6$  ( $M = \text{Mg}, \text{Zn}$ , and  $\text{Cd}$ ) from Néel order to its suppression, *Phys. Rev. B* **94**, 134429



- (2016).
- [54] C. M. Thompson, J. P. Carlo, R. Flacau, T. Aharen, I. A. Leahy, J. R. Pollicemi, T. J. S. Munsie, T. Medina, G. M. Luke, J. Munevar, S. Cheung, T. Goko, Y. J. Uemura, and J. E. Greedan, Long-range magnetic order in the  $5d^2$  double perovskite  $\text{Ba}_2\text{CaOsO}_6$ : comparison with spin-disordered  $\text{Ba}_2\text{YReO}_6$ , *J. Phys. Cond. Matt.* **26**, 306003 (2014).
- [55] T. Aharen, J. E. Greedan, C. A. Bridges, A. A. Aczel, J. Rodriguez, G. MacDougall, G. M. Luke, V. K. Michaelis, S. Kroeker, C. R. Wiebe, H. Zhou, and L. M. D. Cranswick, Structure and magnetic properties of the  $S = 1$  geometrically frustrated double perovskites  $\text{La}_2\text{LiReO}_6$  and  $\text{Ba}_2\text{YReO}_6$ , *Phys. Rev. B* **81**, 064436 (2010).
- [56] G. Kresse and D. Joubert, From ultrasoft pseudopotentials to the projector augmented-wave method, *Phys. Rev. B* **59**, 1758 (1999).
- [57] G. Kresse and J. Hafner, Ab initio molecular dynamics for liquid metals, *Phys. Rev. B* **47**, 558 (1993).
- [58] J. P. Perdew, K. Burke, and M. Ernzerhof, Generalized gradient approximation made simple, *Phys. Rev. Lett.* **77**, 3865 (1996).
- [59] J. P. Perdew, A. Ruzsinszky, G. I. Csonka, O. A. Vydrov, G. E. Scuseria, L. A. Constantin, X. Zhou, and K. Burke, Restoring the density-gradient expansion for exchange in solids and surfaces, *Phys. Rev. Lett.* **100**, 136406 (2008).
- [60] O. K. Andersen, Linear methods in band theory, *Phys. Rev. B* **12**, 3060 (1975).
- [61] N. Marzari, A. A. Mostofi, J. R. Yates, I. Souza, and D. Vanderbilt, Maximally localized wannier functions: Theory and applications, *Rev. Mod. Phys.* **84**, 1419 (2012).