

Antiferromagnetic domains in a single crystal of the A-type spin-7/2 trigonal topological insulator EuSn_2As_2

Santanu Pakhira^{1,2} and D. C. Johnston^{1,3}

¹*Ames National Laboratory, Iowa State University, Ames, Iowa 50011, USA*

²*Present Address: Institute for Quantum Materials and Technologies,
Karlsruhe Institute of Technology, 76131, Karlsruhe, Germany.*

³*Department of Physics and Astronomy, Iowa State University, Ames, Iowa 50011, USA*

(Dated: March 29, 2024)

EuSn_2As_2 is a trigonal A-type antiferromagnetic topological insulator with the moments aligned in the ab plane and with a Néel temperature $T_N = 23.5$ K. Here we report that an EuSn_2As_2 crystal exhibits a broad peak at $H_{c1} = 1100$ Oe in the field derivative dM_{ab}/dH of the ab -plane magnetization $M_{ab}(H)$ at temperature $T = 2$ K, demonstrating the presence of trigonal antiferromagnetic domains. We model these $M_{ab}(H, T = 2$ K) data and obtain the trigonal anisotropy-energy coefficient K_3 that is 13.3 and 3.7 times larger than those we previously reported for single crystals of the trigonal compounds EuMg_2Sb_2 and EuMg_2Bi_2 , respectively.

I. INTRODUCTION

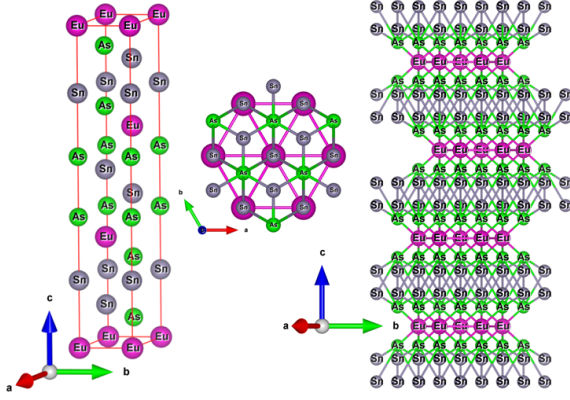


FIG. 1. Trigonal crystal structure of EuSn_2As_2 [2]. The Eu atoms are colored dark purple, the Sn atoms blue, and the As atoms green. The Eu atoms form a hexagonal (triangular) layer situated between two buckled SnAs honeycomb layers, with four Eu layers within each c -axis height. The Eu magnetic structure is A-type with the Eu^{2+} moments aligned in the ab plane [2]. The height of the magnetic unit cell is twice the c -axis lattice parameter.

EuSn_2As_2 is a topological insulator that has been reported to exhibit Dirac surface states at energies within the bulk band gap from angle-resolved photoemission spectroscopy (ARPES) measurements [1]. The compound crystallizes in the trigonal NaSn_2As_2 -type structure with space group $R\bar{3}m$ shown in Fig. 1 [2]. It orders antiferromagnetically below its Néel temperature $T_N \approx 23.5$ K [2, 3]. Neutron-diffraction measurements [2] showed that the antiferromagnetic (AFM) structure is A-type, where the Eu^{2+} moments have spin $S = 7/2$, spectroscopic splitting factor $g = 2$, and ordered moment $\mu = gS\mu_B = 7\mu_B$, where μ_B is the Bohr magneton. The Eu moments are aligned ferromagnetically in an ab plane layer with the Eu moments in adjacent layers along the c axis aligned antiferromagnetically [2]. Other

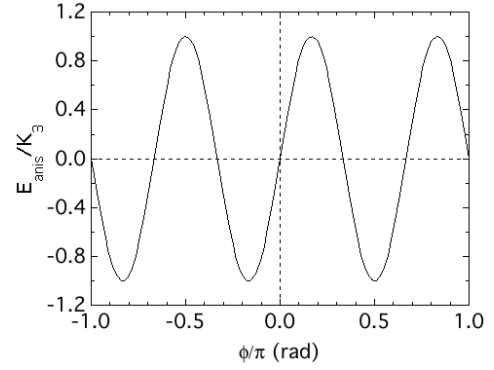


FIG. 2. Magnetic anisotropy free energy E_{anis} of ferromagnetic moments aligned at an angle ϕ with the positive x axis, normalized by the trigonal anisotropy constant K_3 in Eq. (1).

studies of the magnetic and thermodynamic properties of EuSn_2As_2 single crystals were also presented in Ref. [2].

The related topological compounds EuMg_2Sb_2 and EuMg_2Bi_2 crystallize in the trigonal CaAl_2Si_2 -type crystal structure with space group $P\bar{3}m1$ and order antiferromagnetically at $T_N = 8.2$ and 6.7 K, respectively. Neutron-diffraction measurements demonstrated that both compounds exhibit A-type AFM order with the Eu moments aligned in the ab plane [4, 5]. Remarkably, crystals of both compounds showed a distinct positive curvature in $M(H_{ab})$ isotherms at low fields $0 \leq H_{ab} \lesssim H_{c1}$ at $T = 1.8$ K, where $H_{c1} \approx 220$ and ≈ 465 Oe for EuMg_2Sb_2 and EuMg_2Bi_2 , respectively [6]. At higher fields up to the respective saturation critical fields which were $H_c^c = 3.4$ T for EuMg_2Sb_2 at 1.8 K [4] and 4.0 T at 2 K for EuMg_2Bi_2 [7], it was found that $M_{ab} = \chi(T_N)H_{ab}$ as expected from molecular-field theory [8] since the moments were initially nearly perpendicular to \mathbf{H}_{ab} at the respective critical field H_{c1} .

These observations motivated us to consider the presence of equally-populated trigonal AFM domains below the respective T_N of EuMg_2Bi_2 and EuMg_2Sb_2 . These

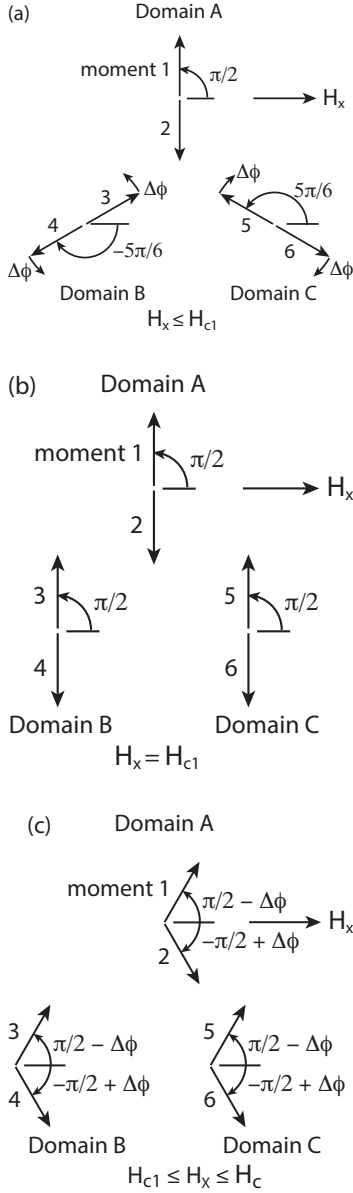


FIG. 3. (a) Domain model for trigonal A-type antiferromagnets in $H_x = 0$ [6]. Moments 1, 4, and 6 are the magnetic moments in a central layer in zero field according to Fig. 2, whereas moments 2, 3, and 5 represent moments in adjacent layers in the collinear A-type AFM structure. The arrows and $\Delta\phi$ indicate the direction of rotation of the moments in a domain for $H_x \leq H_{c1}$. (b) Orientation of the moments when $H = H_{c1}$, apart from a slight canting toward H_x that gives rise to the measured magnetization. (c) Rotation of the moments in each domain towards H_x for $H_{c1} < H_x < H_{ab}^c$, where H_{ab}^c is the ab -plane saturation (critical) field.

domains result from the existence of a trigonal anisotropy free energy of the form

$$F(\phi) = K_3 \cos(3\phi), \quad (1)$$

where K_3 is the anisotropy energy amplitude and ϕ is the angle between moments in an A-type AFM domain and

the x axis, which is assumed to be the axis in which a magnetic field H_x is applied. A plot of $F(\phi)$ is shown in Fig. 2, where three minima in $F(\phi)$ are at $\phi/\pi = -5/6, -1/6,$ and $1/2$.

The critical field $H_x = H_{c1}$ is the ab -plane field at which all moments in each domains become nearly perpendicular to H_{ab} , apart from a small canting $\lesssim 1^\circ$ toward the field that gives rise to the observed magnetization. The $M(0 \leq H_{ab} \leq H_{c1})$ data for both EuMg_2Sb_2 and EuMg_2Bi_2 were successfully fitted by a model in which the positive curvature in $M(H_{ab})$ below H_{c1} arose from the field response of the Eu spins in trigonal domains in Fig. 3 [6]. These fits allowed the respective ab -plane trigonal anisotropy parameters K_3 to be determined.

II. THEORY

Here we analyze the low-field $M(H_{ab}, T = 2 \text{ K})$ data for EuSn_2As_2 [2] in Fig. 4(b) by our model [6] for the magnetic response of the moments in isolated trigonal domains at $T = 0 \text{ K}$ and derive therefrom the value of its trigonal anisotropy constant K_3 . We will then compare this value with the values of K_3 previously obtained for trigonal domains in EuMg_2Sb_2 and EuMg_2Bi_2 [6].

With increasing ab -plane field H_x at $T = 2 \text{ K}$, the three AFM domains initially at 120° to each other as shown in Fig. 3(a) begin to align nearly perpendicular to H_x , which according to Fig. 4(c) occurs at $H_x \approx 1100 \text{ Oe}$. Then with a further increase in H_x the collinear spins in each domain progressively cant towards $H_x = H_{ab}$ until they reach FM alignment at the critical field $H_{ab}^c \approx 3.7 \text{ T}$ according to Fig. 4(a).

Following Ref. [6], the anisotropy energy (1) averaged over the three domains and then normalized by K_3 is

$$\frac{E_{\text{anis ave}}}{K_3} = -\frac{1}{3}[1 + 2 \cos(3\Delta\phi)], \quad (2)$$

and the magnetic energy normalized by K_3 is

$$\frac{E_{\text{mag ave}}}{K_3} = -\frac{\chi_\perp H_x^2}{3K_3} \left[1 + 2 \sin^2 \left(\frac{\pi}{6} + \Delta\phi \right) \right], \quad (3)$$

where $\Delta\phi$ in Fig. 3(c) is the rotation angle of the moments due to a particular H_x and $\chi_\perp = \chi_c$ is the magnetic susceptibility perpendicular to the ab plane, which according to molecular-field theory [8] is $\chi_c = \chi(T_N)$. Then setting

$$h_x = \chi_\perp H_x^2 / K_3 \quad (4)$$

gives

$$\frac{E_{\text{mag ave}}}{K_3} = -\frac{h_x}{3} \left[1 + 2 \sin^2 \left(\frac{\pi}{6} + \Delta\phi \right) \right]. \quad (5)$$

Thus the total average energy $E_{\text{tot ave}}$ normalized by K_3 is

$$\frac{E_{\text{tot ave}}}{K_3} = \frac{E_{\text{anis ave}}}{K_3} + \frac{E_{\text{mag ave}}}{K_3}. \quad (6)$$

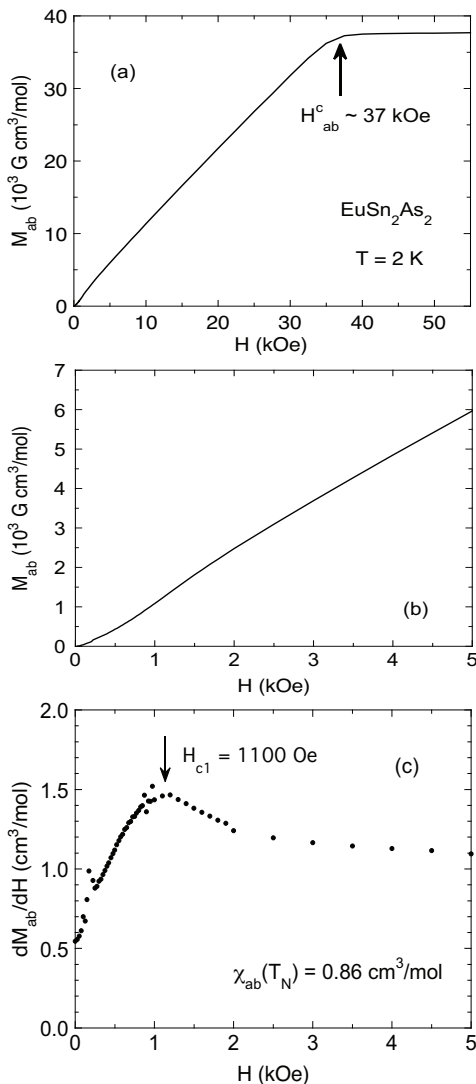


FIG. 4. (a) Magnetization versus x -axis field H_x up to 55 kOe. The critical field for the ab -plane field is ≈ 37 kOe. (b) Expansion of $M_{ab}(H)$ for $H \leq 5$ kOe. (c) Low-field slope dM_{ab}/dH , yielding $H_{c1} \approx 1100$ Oe. The small peak at $H \approx 200$ Oe was also observed to occur for dM_{ab}/dH with $\mathbf{H} \parallel c$ [2] and was postulated to arise from the presence of magnetic defects.

Then using Eqs. (2) and (5) and minimizing $E_{\text{tot ave}}/K_3$ in Eq. (6) with respect to $\Delta\phi$ gives a simple solution for h_x in terms of $\Delta\phi$ as

$$h_x(\phi) = 3 \csc[(\pi + 6\Delta\phi)/3] \sin(3\Delta\phi). \quad (7)$$

From Figs. 3(a) and 3(b), we have $\Delta\phi = \pi/3$ when $H_x = H_{c1}$, *i.e.*, when all moments are approximately perpendicular to H_x . Then Eqs. (4) and (7) and give

$$h_x(\pi/3) = \frac{9}{2} = \frac{\chi_{\perp} H_{c1}^2}{K_3}. \quad (8)$$

This value is per Eu^{2+} ion, whereas the measured $\chi_{\perp} = \chi(T_N)$ is per mole of Eu ions, so Eq. (8) becomes

$$\frac{9}{2} = \frac{\chi_{\perp} H_{c1}^2}{N_A K_3}, \quad (9)$$

where N_A is Avogadro's number. Then using $H_{c1} = 1100$ Oe from Fig. 4(c), the anisotropy-corrected $\chi_{\perp} = \chi(T_N) = 0.86 \text{ cm}^3/\text{mol}$ [2], and solving for K_3 gives

$$\begin{aligned} K_3 &= \frac{\chi_{\perp} H_{c1}^2}{(9/2)N_A} \\ &= 2.4 \times 10^{-7} \text{ eV/Eu}. \end{aligned} \quad (10)$$

This K_3 value is 13.3 and 3.7 times larger than those found for single crystals of the two previously-studied trigonal A-type antiferromagnets EuMg_2Sb_2 and EuMg_2Bi_2 , respectively [6].

III. CONCLUDING REMARKS

The present work is part of an ongoing effort to characterize the ab -plane magnetic-field dependence of Eu^{2+} and Gd^{3+} spin $S = 7/2$ trigonal and tetragonal A-type antiferromagnets with the moments aligned in the ab plane. In addition to the present study of EuSn_2As_2 , these compounds have so far included trigonal EuMg_2Sb_2 and EuMg_2Bi_2 [6] as noted in the text, and also trigonal EuAl_2Ge_2 [9] and tetragonal EuGa_4 [10]. In future work, it would be interesting to determine if the ab -plane magnetic-field-induced changes in the domain structure also affects the topological properties of relevant A-type antiferromagnets.

ACKNOWLEDGMENTS

The research at Ames National Laboratory was supported by the U.S. Department of Energy, Office of Basic Energy Sciences, Division of Materials Sciences and Engineering. Ames National Laboratory is operated for the U.S. Department of Energy by Iowa State University under Contract No. DE-AC02-07CH11358.

[1] H. Li, S.-Y. Gao, S.-F. Duan, Y.-F. Xu, K.-J. Zhu, S.-J. Tian, J.-C. Gao, W.-H. Fan, Z.-C. Rao, J.-R. Hugang, J.-J. Li, D.-Y. Yan, Z.-T. Liu, W.-L. Liu, Y.-

B. Huang, Y.-L. Li, Y. Liu, G.-B. Zhang, P. Zhang, T. Kondo, S. Shin, H.-C. Lei, Y.-G. Shi, W.-T. Zhang, H.-M. Weng, T. Qian, and H. Ding, Dirac Surface States in

- Intrinsic Magnetic Topological Insulators EuSn_2As_2 and $\text{MnBi}_{2n}\text{Te}_{3n+1}$, *Phys. Rev. X* **9**, 041039 (2019).
- [2] S. Pakhira, M. A. Tanatar, T. Heitmann, D. Vaknin, and D. C. Johnston, A-type antiferromagnetic order and magnetic phase diagram of the trigonal Eu Spin-7/2 triangular-lattice compound EuSn_2As_2 , *Phys. Rev. B* **104**, 174427 (2021).
- [3] M. Q. Arguilla, N. D. Cultrara, Z. J. Baum, S. Jiang, R. D. Ross and J. E. Goldberger, EuSn_2As_2 : An Exfoliatable Magnetic Layered Zintl-Klemm Phase, *Inorg. Chem. Front.* **4**, 378 (2017).
- [4] S. Pakhira, F. Islam, E. O’Leary, M. A. Tanatar, T. Heitmann, L.-L. Wang, R. Prozorov, A. Kaminski, D. Vaknin, and D. C. Johnston, A-type antiferromagnetic order in semiconducting EuMg_2Sb_2 single crystals, *Phys. Rev. B* **106**, 024418 (2022).
- [5] S. Pakhira, T. Heitmann, S. X. M. Riberolles, B. G. Ueland, R. J. McQueeney, D. C. Johnston, and D. Vaknin, Zero-field magnetic ground state of EuMg_2Bi_2 , *Phys. Rev. B* **103**, 024408 (2021).
- [6] S. Pakhira, Y. Lee, L. Ke, and D. C. Johnston, Magnetic field induced *ab*-plane rotation of the Eu magnetic moments in trigonal EuMg_2Bi_2 and EuMg_2Sb_2 single crystals below their Néel temperatures, *Phys. Rev. B* **106**, 184423 (2022).
- [7] S. Pakhira, M. A. Tanatar, and D. C. Johnston, Magnetic, thermal, and electronic-transport properties of EuMg_2Bi_2 single crystals, *Phys. Rev. B* **101**, 214407 (2020).
- [8] D. C. Johnston, Unified molecular field theory for collinear and noncollinear Heisenberg antiferromagnets, *Phys. Rev. B* **91**, 064427 (2015).
- [9] S. Pakhira, A. K. Kundu, F. Islam, M. A. Tanatar, T. Roy, T. Heitmann, T. Yilmaz, E. Vescovo, M. Tsujikawa, M. Shirai, R. Prozorov, D. Vaknin, and D. C. Johnston, Anisotropic magnetism and electronic structure of trigonal EuAl_2Ge_2 single crystals, *Phys. Rev. B* **107**, 134439 (2023).
- [10] S. Pakhira and D. C. Johnston, Low-field magnetic anomalies in single crystals of the A-type square-lattice antiferromagnet EuGa_4 , *Phys. Rev. B* **107**, 024421 (2023).