

Enhancing Critical Current Density in Thin Superconductor Layers by Moiré Pinning Centers

Z. Owjifard¹, A. Tavana^{1*}, and M. Hosseini^{2*}

¹*AMDM Lab., Department of Physics, University of Mohaghegh Ardabili, Ardabil, Iran.*

²*Department of Physics, Shiraz University of Technology, Shiraz, Iran.*

**Corresponding author*

Abstract

One important factor affecting the critical current density in type-II superconductors is the formation of artificial pinning centers. Hence, the engineering of pinning centers in superconducting systems has garnered considerable attention. In this study, the effect of moiré patterned pinning centers on the critical current density of superconducting tapes is investigated. The Langevin equation is solved by taking into account the prominent forces within the superconductor medium, using the appropriate boundary conditions for vortices. The vortices dynamics are investigated by performing molecular dynamics simulations, which are used to calculate the corresponding critical current densities. Results show a significant enhancement in the critical current density at particular angles of the relative rotation of the primary lattices. It is also revealed that for stronger pinning forces, the calculated critical current densities are higher in the moiré lattices compared to the primary lattices of pinning centers.

Keywords: Superconducting tapes; moiré pattern; vortex dynamics

I- Introduction

Superconductors have attracted considerable attention due to their remarkable ability to conduct electric current without any energy dissipation [1,2]. However, they are more than just perfect conductors and repel magnetic flux, regardless of their history, i.e., the Meissner effect. In type-II superconductors, when specimens are subjected to an external magnetic field lower than B_{c2} , they exhibit a characteristic phase known as the vortex or Abrikosov phase, where magnetic vortices partially penetrate the material [3,4]. These vortices organize themselves into a hexagonal triangular lattice structure, commonly referred to as the Shubnikov phase [4,5].

Indeed, the motion of vortices leads to the dissipation of energy, due to the displacement of the normal-phase vortex cores. Therefore, restricting the mobility of vortices is essential in improving the performance of superconductors, as it results in an increase in the dissipation-free current carrying capacity [6]. Hence, studying the dynamics of vortices in the presence of the pinning centers on various types of patterned substrates is crucial in type-II superconductors [7].

Numerous investigations have successfully studied the effect of various geometries of pinning center patterns in superconductor tapes, including triangular [8-23], square [8,9,16,24-37], rectangular [38-43], conformal crystal [44, 45], Kagome [11, 15-17, 21, 46-52], honeycomb [11,19, 46-48,51], and other [53-55] arrays of pinning centers. In practice, these different geometries have been achieved through meticulous experimental techniques and have provided valuable insights into the behavior of vortices in superconducting materials. Through the manipulation of these pinning center patterns, researchers aim to advance the comprehension of

vortex dynamics, improve the existing applications, and explore new applications for superconductors.

One class of pinning center arrangements can be obtained from the moiré patterns. The moiré patterns emerge from the interference effects between two overlaid lattices when one of them is shifted or twisted with respect to the other one [56,57]. These patterns can occur on a large scale and are often observed when two regular patterns, such as grids or lines, are combined. They have found interesting applications in various areas, including optics, imaging, and twistrionics [56,58].

In this study, the effect of the twist angle of moiré patterns, resulting from the rotation of two triangular pinning center lattices, on the dynamics of vortex lines is investigated. We calculate the critical current density for a range of twist angles θ , and for different strengths of the pinning force, based on molecular dynamics simulations. Results indicate that for certain optimum values of θ , there is a significant enhancement in the critical current density.

I- Simulation details

Calculations are performed based on the molecular dynamics method. The system comprises magnetic vortices interacting with each other and with the pinning center situated on a moiré pattern. Then, the overdamped equation of motion governing the movement of the i -th vortex is [9,30,46, 59-62]:

$$\eta v_i = f_i = f_i^{vv} + f_i^{vp} + f_i^T \quad (1)$$

where η , is the damping coefficient or viscosity and f_i represents the total force acting on the i -th vortex. In this equation, f_i^{vv} is the vortex-vortex interaction force that can be expressed as [11,30,46, 59-63]:

$$f_i^{vv} = f_0 K_1 \left(\frac{|\mathbf{r}_i - \mathbf{r}_j|}{\lambda} \right) \hat{\mathbf{r}}_{ij}, \quad (2)$$

where, f_0 represents the amplitude of the vortex-vortex force, K_1 is the modified Bessel function, λ is the magnetic field penetration depth, and r_i is the position of the i -th vortex, such that [30,46, 59-62]:

$$\hat{\mathbf{r}}_{ij} = \frac{(\mathbf{r}_i - \mathbf{r}_j)}{|\mathbf{r}_i - \mathbf{r}_j|}, \quad (3)$$

$$\phi_0 = \frac{hc}{2e} \quad (4)$$

and

$$f_0 = \frac{\phi_0^2}{8\pi^2 \lambda^3}. \quad (5)$$

In equation (4), $\phi_0 = hc/2e$ is the quantum of magnetic flux, where h is Planck's constant, e is the electron charge, and c is the velocity of light.

In equation (1), f_i^{vp} is the pinning force described as [64, 66]:

$$f_i^{vp} = \left(\frac{f_p}{r_p} \right) |\mathbf{r}_i - \mathbf{r}_k^{(p)}| \Theta \left(\frac{r_p - |\mathbf{r}_i - \mathbf{r}_k^{(p)}|}{\lambda} \right) \hat{\mathbf{r}}_{ik}^{(p)}, \quad (6)$$

where f_p is the amplitude of the pinning force, r_p is the effective range of the pinning potential,

and Θ is the Heaviside step function. $\hat{\mathbf{r}}_{ik}^{(p)}$ is defined as:

$$\hat{\mathbf{r}}_{ik}^{(p)} = (\mathbf{r}_i - \mathbf{r}_k^{(p)}) / |\mathbf{r}_i - \mathbf{r}_k^{(p)}| \quad (7)$$

The lateral dimensions of the system are $L \times L$, where L is set equal to 10λ . Periodic boundary conditions are assumed for both x and y directions. Without loss of generality, we also set $\eta=1$ and $\lambda=1$.

f_i^T in equation (1), is the force resulting from the thermal fluctuations and is treated as a random function that meets the following conditions [67]:

$$\langle f_i^T(t) \rangle = 0 \quad (8)$$

$$\langle f_i^T(t) f_i^T(t') \rangle = 2\eta k_B T \delta_{ij} \delta(t-t') \quad (9)$$

In this approximation, the normalized critical current density, J_c , is defined as the ratio of the number of pinned vortices, N_v^p to the total number of vortices, N_v , [64,65] i.e.:

$$J_c(\phi) \propto \frac{N_v^p(\phi)}{N_v(\phi)}, \quad (10)$$

For the geometry of the pinning centers, the initial configuration comprises two triangular lattices placed exactly on top of each other with a relative twist angle equal to zero ($\theta = 0$). By increasing the value of θ , these two lattices become detached from each other and moiré patterns emerge. The resulting moiré patterns of two triangular lattices with twist angles $\theta = 0, 2.5, 5,$ and 7.5 are shown in Figure 1.

Critical current densities are calculated for the emerged moiré patterns with different θ values, ranging from zero to 60 degrees. As a result of the inherent symmetry of the triangular lattice, rotating the lattice by 60 degrees brings it back to its original state. This means that a twist angle of $\theta = 60$ degrees is equivalent to having no twist at all ($\theta = 0$). When $\theta = 0$, the pinning sites in two triangular lattices overlap, resulting in a doubled pinning force. However, upon exiting from

the $\theta = 0$ state, the pinning sites no longer overlap and each pinning site has a pinning force that is half of its value in comparison with the $\theta = 0$ state.

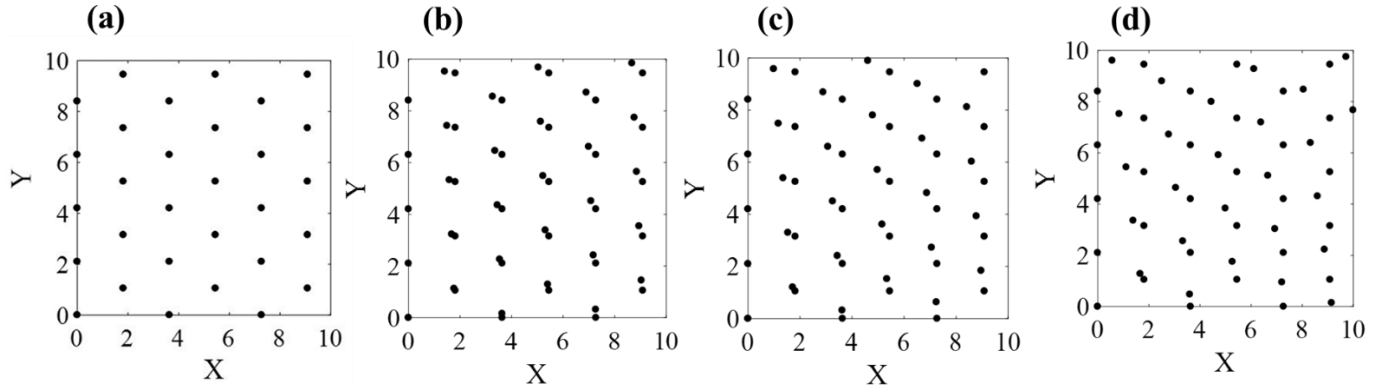


Figure1: The moiré pinning array patterns for twist angles (a) $\theta = 0$, (b) $\theta = 2.5$, (c) $\theta = 5$, and (d) $\theta = 7.5$. X and Y are in units of λ .

III- Results and Discussion

Figure 2 illustrates the normalized J_c versus the number of vortices for $\theta = 0$ and for pinning forces equal to 0.5, 1, 2, and 3. As expected, for $f_p = 3$, the critical current density is larger than the other cases. Pinning centers act as barriers hindering the movement of vortices. So, stronger pinning forces suppress the vortex motion more effectively, which consequently leads to an increase in the critical current density.

The figure shows that when $\theta = 0$, in addition to the initial peak, there are other peaks for $f_p=2$ and $f_p=3$. The appearance of these peaks has captured the interest of scientists due to their intriguing nature and wide range of applications [68-71].

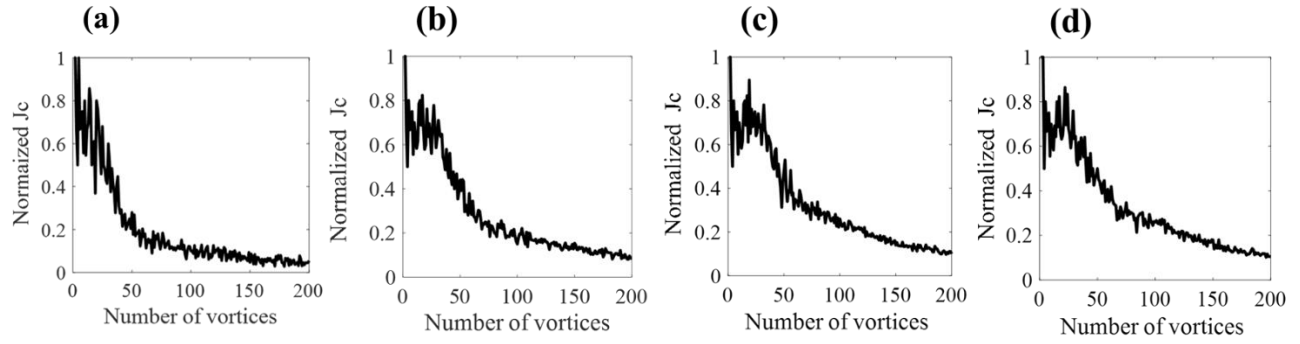


Figure 2: Normalized critical current density, J_c , versus the number of vortices for (a) $\theta = 0, f_p = 0.5$, (b) $\theta = 0, f_p = 1$, (c) $\theta = 0, f_p = 2$, and (d) $\theta = 0, f_p = 3$.

In Figure 3, diagrams of the normalized J_c versus twist angles, θ , are depicted for $f_p = 0.5, 1, 2$, and 3, respectively, for high, intermediate, and low magnetic fields. High fields refer to the range of vortex numbers between 180 and 200, intermediate fields span the range between 90 and 110, and low fields indicate the range between 40 and 60 number of vortices. The pinning sites are located at the points of two triangular lattices that are co-centered and twisted relative to each other by the twist angle θ .

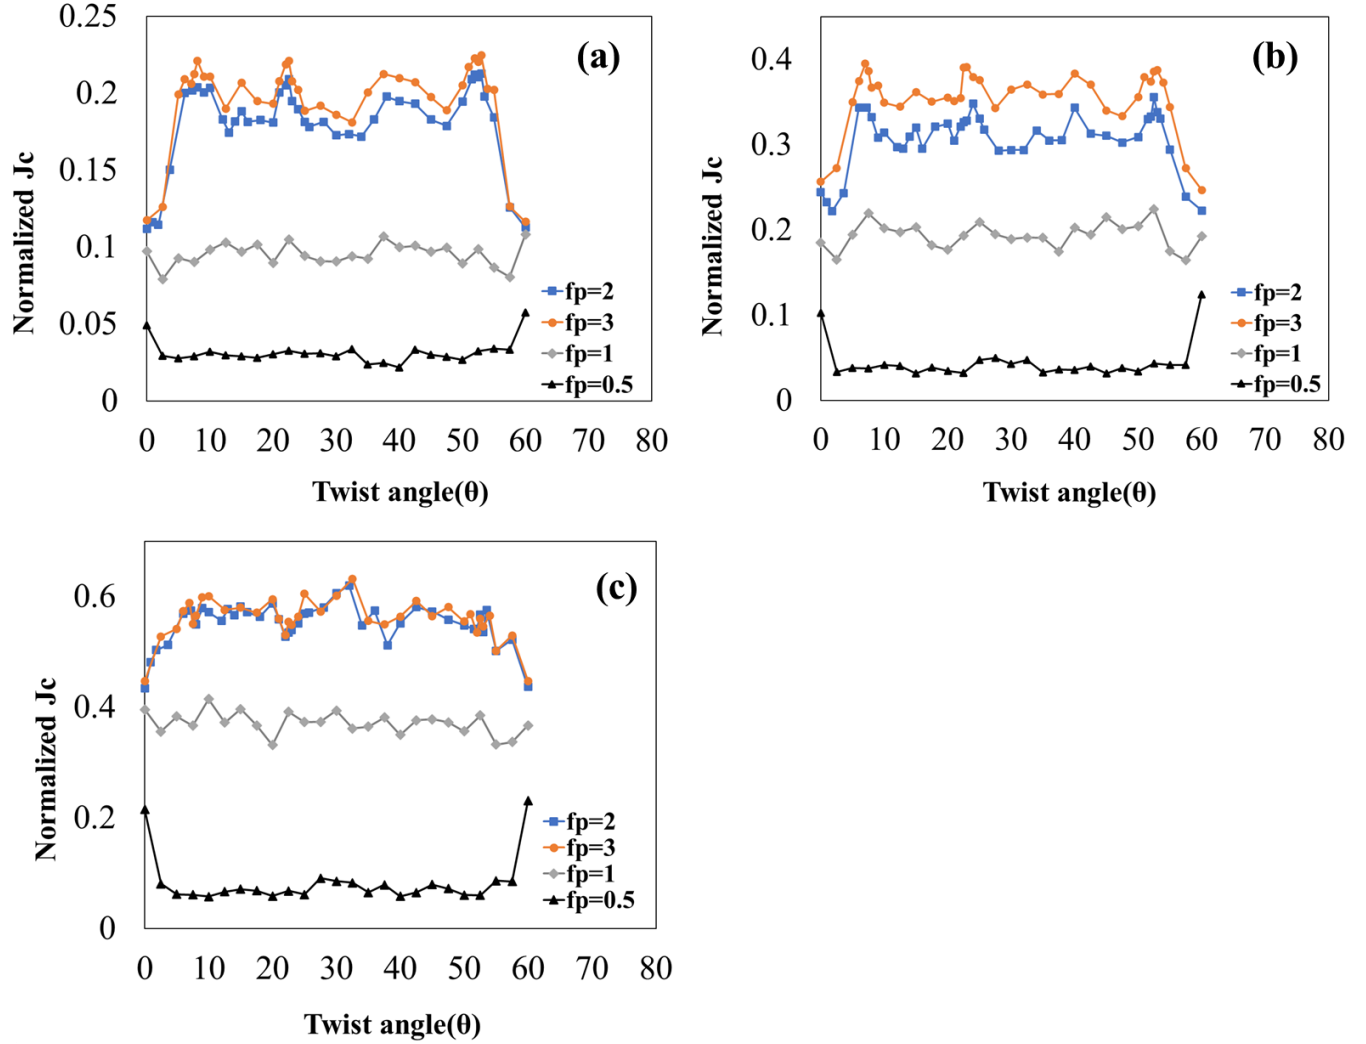


Figure 3: Normalized critical current density, J_c , as a function of twist angle θ , for high (a), intermediate (b), and low (c) magnetic fields.

Figure 3(a), illustrates the normalized J_c versus θ for high magnetic fields. From this figure, it can be seen that for $f_p = 3$, the normalized J_c has the largest value for all twist angles in comparison to other pinning force strengths. Also, for $f_p = 3$, a noticeable increase in the critical current density can be observed by increasing the value of θ from zero. Furthermore, we observe that for the θ values of 8, 22.5, 37.5, and 53 degrees, the critical current density is maximized, with the absolute maximum value occurring at $\theta = 53$ degrees. The behavior of the critical current density for $f_p = 2$ is similar to that of $f_p = 3$, except for a slight decrease in its value for most of the θ values. For

$f_p = 1$, the critical current density shows a significant decrease compared to the $f_p = 2$ and $f_p = 3$ cases and does not change with the variations in θ significantly, and only minor fluctuations are observed.

For $f_p = 0.5$, the critical current densities are smaller compared to the $f_p = 1$ case. Increasing the value of θ from zero leads to a reduction in the critical current density, similar to the $f_p = 1$ situation. As θ increases, the normalized J_c remains almost constant and at $\theta = 60$, returns to its initial value.

In Figure 3(b), the critical current density is depicted as a function of θ for four different values of f_p equal to 0.5, 1, 2, and 3, in intermediate magnetic fields. Within this range of magnetic field strengths, J_c demonstrates a pattern similar to that observed in high fields. Comparing the critical current density plots for intermediate and high magnetic fields, we observe a noticeable enhancement in the critical current density, going from the $f_p = 2$ to the $f_p = 3$ case.

Figure 3(c) illustrates the relationship between the normalized critical current density and the twist angle for four values of f_p equal to 0.5, 1, 2, and 3, in low magnetic fields. Within this range of magnetic field strengths, there is no noticeable difference between $f_p=2$ and $f_p=3$ values in the normalized J_c diagrams.

Determination of the normalized critical current density involves a competition between two key factors; the regularity of the lattice and the degree of the overlap between the pinning sites. When θ is equal to zero, the pinning centers exhibit an initial arrangement characterized by triangular ordering. Comparing the cases $\theta = 0$ and $\theta \neq 0$, it can be observed that in the $\theta = 0$ case, the pinning force is doubled due to the overlapping of two lattices. However, the number of pinning sites is also halved relative to the non-zero θ case.

On the other hand, for $\theta = 0$, there is a triangular ordering, whereas for non-zero θ , short-range ordering is lost. Consequently, when θ is non-zero, by the alteration of the initial ordering of pinning centers, a noticeable increase in the critical current density can be observed for pinning forces equal to 2 and 3.

When the vortex-pinning forces are greater than the vortex-vortex forces, the impact of the overlapping between pinning centers becomes more important than the lattice regularity. Therefore, as the angle θ increases, the critical current density increases due to the doubling of the number of pinning sites. The reason for this is the larger magnitude of the vortex-pinning forces, compared to the vortex-vortex forces.

As a general trend, as θ increases, for pinning forces greater than one, where the vortex-pinning forces surpass the vortex-vortex forces, the effect of increased number of pinning sites becomes more significant compared to the increased disorder in the spatial distribution of the pinning centers. Hence, increasing the number of pinning centers leads to an enhancement in the critical current density.

For $f_p = 1$, the vortex-pinning force is equal to the vortex-vortex force. Therefore, with an increase in θ , no significant change in the critical current density is observed. For $f_p = 0.5$, since the vortex-pinning forces are smaller than the vortex-vortex forces, with an increase in the value of θ from zero, the impact of lattice irregularity becomes more prominent compared to the increased number of pinning centers. This results in a decrease in the normalized critical current density.

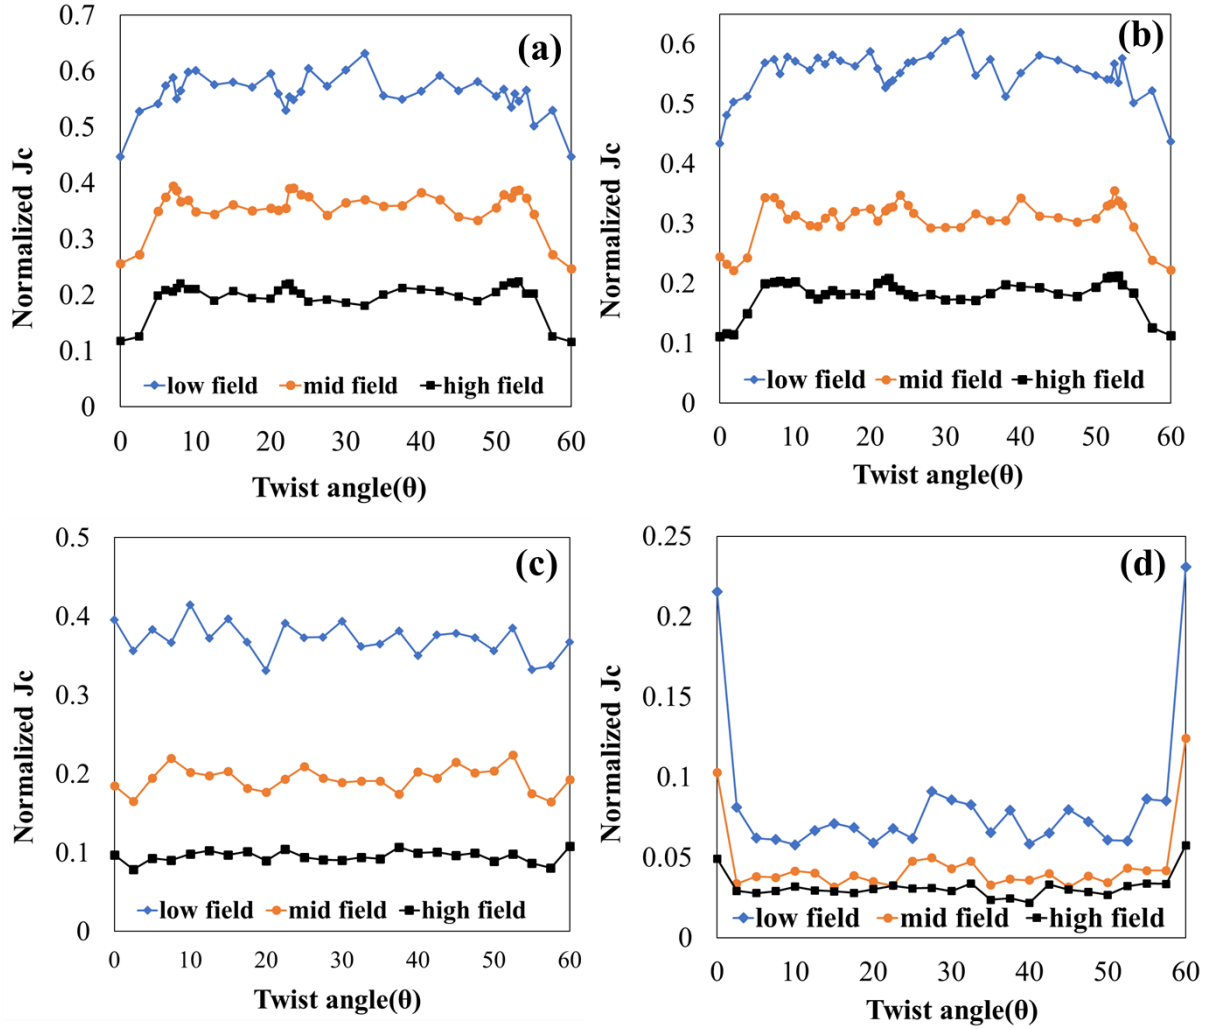


Figure 4: Normalized critical current density, J_c , as a function of twist angle θ , for $f_p = 3$ (a), $f_p = 2$ (b), $f_p = 1$ (c), and $f_p = 0.5$ (d), in high, intermediate, and low magnetic fields.

In Figures 4(a) to (d), the normalized critical current densities are depicted as a function of the twist angle θ , respectively for pinning forces f_p equal to 0.5, 1, 2, and 3, respectively in high, intermediate, and low magnetic fields. In Figure 4(a), when $f_p = 3$, the maximum critical current density occurs approximately at the same twist angle for the both high and the intermediate fields. An increase in J_c at specific twist angles has also been reported in previous research [72].

In Figure 4(b), the critical current density as a function of angle is shown for $f_p = 2$ in the low, intermediate, and high magnetic fields. As it can be seen, the behavior of J_c resembles that of the $f_p = 3$ case. In Figure 4(c), when $f_p = 1$, J_c remains almost constant for all magnetic field strengths, despite small fluctuations.

Figure 4(d) shows the relationship between the critical current density and twist angle for the pinning force $f_p = 0.5$. In this case, as we exit from the $\theta = 0$ state, the critical current density decreases, initially, then shows fluctuations at higher twist angles, and finally returns to its initial value at $\theta = 60$ degrees. By increasing the pinning force, the difference in the critical current densities corresponding to different magnetic fields decreases.

Comparing the critical current densities at $\theta = 0$ with larger twist angles for $f_p = 0.5$, we observe that a smaller vortex-pinning force leads to a smaller critical current density. For $f_p = 2$ and $f_p = 3$, the critical current density shows an increasing trend by increasing the value of θ , because, the vortex-pinning forces become larger than the vortex-vortex forces. For $f_p = 1$, the critical current density remains almost constant at all θ values, with minor fluctuations.

IV- Conclusion

In summary, we have investigated the normalized critical current density in a superconducting tape with pinning centers forming moiré patterns, obtained from twisting two triangular pinning lattices relative to each other. We have studied the effect of twist angle, different pinning forces, and different magnetic field strengths on J_c . Results show that for pinning forces greater than one, because of the larger vortex-pinning forces in comparison with the vortex-vortex forces, the critical current density significantly increases. In addition, the specific twist angles for which the critical

current density reaches its maximum values are inspected. When the vortex-pinning forces are smaller than the vortex-vortex forces, and for pinning forces smaller than one, increasing the twist angle results in a decrease in the critical current density. This decrease can be attributed to the lattice ordering and to the pinning sites overlapping.

References

- [1] Foltyn, S.R., Civale, L., MacManus-Driscoll, J.L., Jia, Q.X., Maiorov, B., Wang, H. and Maley, M., “Materials science challenges for high-temperature superconducting wire”. *Nature materials*, 6(9), pp.631-642 (2007).
- [2] Anders, S., Blamire, M.G., Buchholz, F.I., Cr  t  , D.G., Cristiano, R., Febvre, P., Fritzsche, L., Herr, A., Il’ichev, E., Kohlmann, J. and Kunert, J., “European roadmap on superconductive electronics–status and perspectives”, *Physica C: Superconductivity*, 470(23-24), pp.2079-2126 (2010).
- [3] Ginzburg, V.L., V.L. Ginzburg, and L. Landau, “On the theory of superconductivity”: Springer (2009).
- [4] Abrikosov, A.A., “On the magnetic properties of superconductors of the second group”, *Soviet Physics-JETP*, 5: p. 1174-1182 (1957).
- [5] Fossheim, K. and A. Sudb  , “Superconductivity: physics and applications”, John Wiley & Sons (2004).
- [6] Tinkham, M., “Introduction to Superconductivity, volume Second Edition”, Dover Publications Inc., Mineola, New York (2004).
- [7] Wang, Y.L., Thoutam, L.R., Xiao, Z.L., Shen, B., Pearson, J.E., Divan, R., Ocola, L.E., Crabtree, G.W. and Kwok, W.K., “Enhancing superconducting critical current by randomness”, *Physical Review B*, 93(4): p. 045111 (2016).
- [8] Berdiyev, G., M. Milo  evi  , and F. Peeters, “Novel commensurability effects in superconducting films with antidot arrays”, *Physical review letters*, 96(20): p. 207001 (2006).
- [9] Reichhardt, C., C. Olson, and F. Nori, “Commensurate and incommensurate vortex states in superconductors with periodic pinning arrays”, *Physical Review B*, 57(13): p. 7937 (1998).
- [10] Martin, J.I., V  lez, M., Nogu  s, J. and Schuller, I.K., “Flux pinning in a superconductor by an array of submicrometer magnetic dots”, *Physical review letters*, 79(10): p. 1929 (1997).

- [11] Reichhardt, C. and C.O. Reichhardt, “Transport anisotropy as a probe of the interstitial vortex state in superconductors with artificial pinning arrays”, *Physical Review B*, 79(13): p. 134501 (2009).
- [12] Reichhardt, C. and N. Grønbech-Jensen, “Critical currents and vortex states at fractional matching fields in superconductors with periodic pinning”, *Physical Review B*, 63(5): p. 054510 (2001).
- [13] Ooi, S., T. Mochiku, and K. Hirata, “Fractional matching effect in single-crystal films of $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+y}$ with antidot lattice”. *Physica C: Superconductivity*, 469(15-20): p. 1113-1115 (2009).
- [14] Bothner, D., Seidl, R., Misko, V.R., Kleiner, R., Koelle, D. and Kemmler, M., “Unusual commensurability effects in quasiperiodic pinning arrays induced by local inhomogeneities of the pinning site density”, *Superconductor Science and Technology*, 27(6): p. 065002 (2014).
- [15] Verga, L.G., Da Silva, M.C., Simões, R.P., Mello, D.F.D. and Venegas, P.A., “Anisotropy in the transport properties of type II superconducting films with periodic pinning. *Journal of superconductivity and novel magnetism*”, 26: p. 351-359 (2013).
- [16] Morgan, D.J. and J. Ketterson, “Asymmetric flux pinning in a regular array of magnetic dipoles. *Physical review letters*”, 80(16): p. 3614 (1998).
- [17] Vizarim, N.P., Carlone, M., Verga, L.G. and Venegas, P.A., “Commensurability effects in the critical forces of a superconducting film with Kagomé pinning array at submatching fields”, *The European Physical Journal B*, 90: p. 1-8 (2017).
- [18] Sadovskyy, I.A., Wang, Y.L., Xiao, Z.L., Kwok, W.K. and Glatz, A., “Effect of hexagonal patterned arrays and defect geometry on the critical current of superconducting films”, *Physical Review B*, 95(7): p. 075303 (2017).
- [19] Cao, R., Horng, L., Wu, T.C., Wu, J.C. and Yang, T.J., “Temperature dependent pinning phenomenon in superconducting Nb films with triangular and honeycomb pinning arrays”, *Journal of Physics: Condensed Matter*, 21(7): p. 075705 (2009).
- [20] Cao, R., Wu, T.C., Kang, P.C., Wu, J.C., Yang, T.J. and Horng, L., “Anisotropic pinning in Nb thin films with triangular pinning arrays. *Solid state communications*”, 143(3): p. 171-175 (2007).
- [21] Laguna, M.F., Balseiro, C.A., Domínguez, D. and Nori, F., “Vortex structure and dynamics in kagomé and triangular pinning potentials”. *Physical Review B*, 64(10): p. 104505 (2001).
- [22] Vizarim, N.P., Carlone, M., Verga, L.G. and Venegas, P.A., “Critical forces at fractional matching fields in superconducting thin films with triangular pinning lattice”, *Materials Research*, 20: p. 899-903 (2017).

- [23] Wu, T.C., Kang, P.C., Horng, L., Wu, J.C. and Yang, T.J., “Anisotropic pinning effect on a Nb thin film with triangular arrays of pinning sites”. *Journal of applied physics*, 95(11): p. 6696-6698 (2004).
- [24] Baert, M., Metlushko, V.V., Jonckheere, R., Moshchalkov, V.V. and Bruynseraede, Y., “Composite flux-line lattices stabilized in superconducting films by a regular array of artificial defects”, *Physical review letters*, 74(16): p. 3269 (1995).
- [25] Metlushko, V., Welp, U., Crabtree, G.W., Osgood, R., Bader, S.D., DeLong, L.E., Zhang, Z., Brueck, S.R.J., Ilic, B., Chung, K. and Hesketh, P.J., “Interstitial flux phases in a superconducting niobium film with a square lattice of artificial pinning centers”, *Physical Review B*, 60(18): p. R12585 (1999).
- [26] Harada, K., Kamimura, O., Kasai, H., Matsuda, T., Tonomura, A. and Moshchalkov, V.V., “Direct observation of vortex dynamics in superconducting films with regular arrays of defects. *Science*”, 274(5290): p. 1167-1170 (1996).
- [27] Grigorenko, A.N., Bending, S.J., Van Bael, M.J., Lange, M., Moshchalkov, V.V., Fangohr, H. and De Groot, P.A.J., “Symmetry locking and commensurate vortex domain formation in periodic pinning arrays”, *Physical review letters*, 90(23): p. 237001 (2003).
- [28] Crassous, A., Bernard, R., Fusil, S., Bouzehouane, K., Le Bourdais, D., Enouz-Vedrenne, S., Briatico, J., Bibes, M., Barthélémy, A. and Villegas, J.E., “Nanoscale electrostatic manipulation of magnetic flux quanta in ferroelectric/superconductor BiFeO₃/YBa₂Cu₃O_{7- δ} heterostructures”, *Physical review letters*, 107(24): p. 247002 (2011).
- [29] Grigorenko, A.N., Howells, G.D., Bending, S.J., Bekaert, J., Van Bael, M.J., Van Look, L., Moshchalkov, V.V., Bruynseraede, Y., Borghs, G., Kaya, I.I. and Stradling, R.A., “Direct imaging of commensurate vortex structures in ordered antidot arrays”, *Physical review b*, 63(5): p. 052504 (2001).
- [30] Reichhardt, C., C. Olson, and F. Nori, “Dynamic phases of vortices in superconductors with periodic pinning”, *Physical Review Letters*, 78(13): p. 2648 (1997).
- [31] Ren, Q.-B. and M.-B. Luo, “Dynamics of two-dimensional vortex system in a strong square pinning array at the second matching field”, *Physics Letters A*, 377(31-33): p. 1966-1969 (2013).
- [32] Martin, J.I., Vélez, M., Hoffmann, A., Schuller, I.K. and Vicent, J.L., “Temperature dependence and mechanisms of vortex pinning by periodic arrays of Ni dots in Nb films”, *Physical Review B*, 62(13): p. 9110 (2000).

- [33] Moshchalkov, V.V., Baert, M., Metlushko, V.V., Rosseel, E., Van Bael, M.J., Temst, K., Bruynseraede, Y. and Jonckheere, R., “Pinning by an antidot lattice: The problem of the optimum antidot size”, *Physical Review B*, 57(6): p. 3615 (1998).
- [34] García-Santiago, A., Hernandez, J.M., Tejada, J., Vanacken, J. and Moshchalkov, V.V., “Observation of commensurability effects in a patterned thin superconducting Pb film using microwave reflection spectrometry”, *Physical Review B*, 89(5): p. 054517 (2014).
- [35] Yetis, H., “Transport properties of the multiple vortices in superconductors with square pinning arrays”, *The European Physical Journal B*, 88: p. 1-6 (2015).
- [36] Reichhardt, C. and F. Nori, “Phase locking, devil's staircases, Farey trees, and Arnold tongues in driven vortex lattices with periodic pinning”, *Physical review letters*, 82(2): p. 414 (1999).
- [37] Field, S.B., James, S.S., Barentine, J., Metlushko, V., Crabtree, G., Shtrikman, H., Ilic, B. and Brueck, S.R.J., “Vortex configurations, matching, and domain structure in large arrays of artificial pinning centers”, *Physical review letters*, 88(6): p. 067003 (2002).
- [38] Karapetrov, G., Fedor, J., Iavarone, M., Rosenmann, D. and Kwok, W.K., “Direct observation of geometrical phase transitions in mesoscopic superconductors by scanning tunneling microscopy”, *Physical review letters*, 95(16): p. 167002 (2005).
- [39] Martín, J.I., Vélez, M., Hoffmann, A., Schuller, I.K. and Vicent, J.L., “Artificially induced reconfiguration of the vortex lattice by arrays of magnetic dots”, *Physical review letters*, 83(5): p. 1022 (1999).
- [40] Reichhardt, C.O., A. Libál, and C. Reichhardt, “Vortex configurations and dynamics in elliptical pinning sites for high matching fields”, *Physical Review B*, 73(18): p. 184519 (2006).
- [41] Reichhardt, C., G. Zimányi, and N. Grønbech-Jensen, “Complex dynamical flow phases and pinning in superconductors with rectangular pinning arrays”, *Physical Review B*, 64(1): p. 014501 (2001).
- [42] Velez, M., Jaque, D., Martin, J.I., Montero, M.I., Schuller, I.K. and Vicent, J.L., “Vortex lattice channeling effects in Nb films induced by anisotropic arrays of mesoscopic pinning centers”, *Physical Review B*, 65(10): p. 104511 (2002).
- [43] Vélez, M., Martin, J.I., Villegas, J.E., Hoffmann, A., González, E.M., Vicent, J.L. and Schuller, I.K., “Superconducting vortex pinning with artificial magnetic nanostructures”, *Journal of Magnetism and Magnetic Materials*, 320(21): p. 2547-2562 (2008).

- [44] Ray, D., Reichhardt, C.O., Janko, B. and Reichhardt, C., “Strongly enhanced pinning of magnetic vortices in type-II superconductors by conformal crystal arrays”, *Physical review letters*, 110(26): p. 267001 (2013).
- [45] Wang, Y.L., Latimer, M.L., Xiao, Z.L., Divan, R., Ocola, L.E., Crabtree, G.W. and Kwok, W.K., “Enhancing the critical current of a superconducting film in a wide range of magnetic fields with a conformal array of nanoscale holes”, *Physical Review B*, 87(22): p. 220501 (2013).
- [46] Reichhardt, C. and C.O. Reichhardt, “Vortex molecular crystal and vortex plastic crystal states in honeycomb and kagome pinning arrays”, *Physical Review B*, 76(6): p. 064523 (2007).
- [47] Cuppens, J., Ataklti, G.W., Gillijns, W., Van de Vondel, J., Moshchalkov, V.V. and Silhanek, A.V., “Vortex dynamics in a superconducting film with a kagomé and a honeycomb pinning landscape”, *Journal of superconductivity and novel magnetism*, 24: p. 7-11 (2011).
- [48] He, S.K., Zhang, W.J., Wen, Z.C., Xiao, H., Han, X.F., Gu, C.Z. and Qiu, X.G., “Interstitial vortex in superconducting film with periodic hole arrays”, *Chinese Physics B*, 21(8): p. 087401 (2012).
- [49] Simões, R.P., Venegas, P.A. and Mello, D.F.D., “The effects of pinning on critical currents of superconducting films”, *Journal of superconductivity and novel magnetism*, 26: p. 2281-2284 (2013).
- [50] Simoes, R.P., Venegas, P.A. and Mello, D.F.D., “Role of interstitial pinning in the dynamical phases of vortices in superconducting films”, *Journal of superconductivity and novel magnetism*, 26: p. 2277-2279 (2013).
- [51] He, S.K., Zhang, W.J., Liu, H.F., Xue, G.M., Li, B.H., Xiao, H., Wen, Z.C., Han, X.F., Zhao, S.P., Gu, C.Z. and Qiu, X.G., “Wire network behavior in superconducting Nb films with diluted triangular arrays of holes”, *Journal of Physics: Condensed Matter*, 24(15): p. 155702 (2012).
- [52] Xue, C., Ge, J.Y., He, A., Zharinov, V.S., Moshchalkov, V.V., Zhou, Y.H., Silhanek, A.V. and Van de Vondel, J., “Mapping degenerate vortex states in a kagome lattice of elongated antidots via scanning Hall probe microscopy”, *Physical Review B*, 96(2): p. 024510 (2017).
- [53] Sadovskyy, I.A., Koshelev, A.E., Kwok, W.K., Welp, U. and Glatz, A., “Targeted evolution of pinning landscapes for large superconducting critical currents”, *Proceedings of the National Academy of Sciences*, 116(21): p. 10291-10296 (2019).
- [54] Zoveydavi, S., Hosseini, M., Owjifard, Z., Moftakharzadeh, A., “Investigation of the Effect of Conformal Pinning Array on Critical Current Density in Infinitely Long Superconductors”, *Physica C: Superconductivity and its Applications*, p.1354498 (2024).

- [55] Shadkamfar, A., Hosseini, M. , Moftakharzadeh, A., “Effect of column-ordered pinning centers on the critical current density of superconducting tape”, *Physica C: Superconductivity and its Applications*, 606, p.1354225 (2023).
- [56] Kobayashi, K., “Moiré pattern in scanning tunneling microscopy: Mechanism in observation of subsurface nanostructures”, *Physical Review B*, 1996. 53(16): p. 11091 (1996).
- [57] Miao, H., Panna, A., Gomella, A.A., Bennett, E.E., Znati, S., Chen, L. and Wen, H., “A universal moiré effect and application in X-ray phase-contrast imaging”, *Nature physics*, 12(9): p. 830-834 (2016).
- [58] S. Carr, D. Massatt, S. Fang, P. Cazeaux, M. Luskin, and E. Kaxiras, “Twistronics: Manipulating the electronic properties of two-dimensional layered ”, *Phys. Rev. B*, vol. 95, p. 075420 (2017).
- [59] Misko, V. R., Savel’ev, S., , Nori, F. “Critical currents in superconductors with quasiperiodic pinning arrays: One-dimensional chains and two-dimensional Penrose lattices” ,*Phys. Rev B*, 74(2), 024522 (2006).
- [60] Reichhardt C., Olson C. J., Groth J., Field S., Nori F., “Vortex plastic flow, local flux density, magnetization hysteresis loops, and critical current, deep in the bose-glass and mott-insulator regimes” *Phys. Rev. B.*, 53(14) (1996).
- [61] Reichhardt C., Olson C. J., Groth J., Field S., Nori F., “Microscopic derivation of magnetic-flux-density profiles, magnetization hysteresis loops, and critical currents in strongly pinned superconductors”, *Phys. Rev. B.*, 52(14) (1995).
- [62] Misko V. R., Savel’ev S., Rakhmanov A. L. , Nori F., “Nonuniform self-organized dynamical states in superconductors with periodic pinning” *Phy. Rev. Lett.*, 96(12) (2006).
- [63] Reichhardt, C. and Reichhardt, C.O., “Transport anisotropy as a probe of the interstitial vortex state in superconductors with artificial pinning arrays”, *Physical Review B*, 79(13), p.134501 (2009).
- [64] Reichhardt, C., Zimányi, G.T., Scalettar, R.T., Hoffmann, A. and Schuller, I.K., “Individual and multiple vortex pinning in systems with periodic pinning arrays”, *Physical Review B*, 64(5): p. 052503 (2001).
- [65] Misko, V.R., S. Savel’ev, F. Nori, “ Enhancement of the critical current in quasiperiodic pinning arrays: One-dimensional chains and Penrose lattices”, *Physica C: Superconductivity and its applications.*, 437: p. 213-216 (2006).
- [66] Reichhardt, C., Zimányi, G.T., Scalettar, R.T., Hoffmann, A. and Schuller, I.K., “ Individual and multiple vortex pinning in systems with periodic pinning arrays”, *Physical Review B*, 64(5), p.052503 (2001).
- [67] Sadovskyy, I.A., et al., “Toward superconducting critical current by design”, *Advanced Materials*, 28(23): p. 4593-4600 (2016).

- [68] Wang, C., Hirota, Y., Wang, L., Sakagami, R., Li, Y., Yi, X., Li, W., Chen, Y., Yu, C., Wang, Z. and Tamegai, T., “Peak effects in the kagome superconductors CsV₃Sb₅ and Cs(V_{0.93}Nb_{0.07})₃Sb₅”, *Physical Review B*, 109(2), p.024514 (2024).
- [69] Jung, S.G., Jang, H., Kim, J., Park, J.H., Lee, S., Seo, S., Bauer, E.D., Park, T., “A Quenched Disorder in the Quantum-Critical Superconductor CeCoIn₅”, *Advanced Science*, 11(1), p.2304837 (2024).
- [70] Sharma, H., Wen, Z. and Mizuguchi, M., “Spin Seebeck effect mediated reversal of vortex-Nernst effect in superconductor-ferromagnet bilayers”, *Scientific Reports*, 13(1), p.4425 (2023).
- [71] Song, X., Suresh Babu, S., Bai, Y., Golubev, D.S., Burkova, I., Romanov, A., Ilin, E., Eckstein, J.N., Bezryadin, A., “Interference, diffraction, and diode effects in superconducting array based on bismuth antimony telluride topological insulator”, *Communications Physics*, 6(1), p.177 (2023).
- [72] Li, W., Reichhardt, C.J.O., Jankó, B., Reichhardt, C., “Vortex dynamics, pinning, and angle-dependent motion on moiré patterns”, *Physical Review B*, 104(2), p.024504 (2021).