

Decoupled static and dynamical charge correlations in $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$

L. Martinelli,^{1,*} I. Bialo,^{1,†} X. Hong,¹ J. Oppliger,¹ C. Lin,¹ T. Schaller,¹ J. Küspert,¹ M. H. Fischer,¹ T. Kurosawa,^{2,3} N. Momono,^{2,3} M. Oda,² J. Choi,⁴ S. Agrestini,⁴ M. Garcia-Fernandez,⁴ Ke-Jin Zhou,⁴ Q. Wang,⁵ and J. Chang^{1,‡}

¹Physik-Institut, Universität Zürich, Winterthurerstrasse 190, CH-8057 Zürich, Switzerland

²Department of Physics, Hokkaido University - Sapporo 060-0810, Japan

³Department of Applied Sciences, Muroran Institute of Technology, Muroran 050-8585, Japan

⁴Diamond Light Source, Harwell Campus, Didcot, Oxfordshire OX11 0DE, United Kingdom

⁵Department of Physics, The Chinese University of Hong Kong, Shatin, Hong Kong, China

(Dated: June 24, 2024)

The relation between charge order, its quantum fluctuations and optical phonon modes in cuprate superconductors remains an unsolved problem. The exploration of these excitations is however complicated by the presence of twinned domains. Here, we use uniaxial strain in combination with ultra-high-resolution Resonant Inelastic X-ray Scattering (RIXS) at the oxygen K - and copper L_3 -edges to study the excitations stemming from the charge ordering wave vector in $\text{La}_{1.875}\text{Sr}_{0.125}\text{CuO}_4$. By detwining stripe ordering, we demonstrate that the optical phonon anomalies do not show any stripe anisotropy. The low-energy charge excitations also retain an in-plane four-fold symmetry. As such, we find that both phonon and charge excitations are decoupled entirely from the strength of static charge ordering. The almost isotropic character of charge excitations remains a possible source for the strange metal properties found in the normal state of cuprate superconductors.

Excitation spectra often entail fingerprints of their underlying ground state. In the context of high-temperature cuprate superconductors, this has motivated numerous studies of phonon and charge excitations. In particular excitations with momenta matching charge stripe ordering are at the center of the debate. While the presence of modulations of the electron/spin density is a common feature of the Hubbard model [1, 2], many aspects of this order are still unexplained, including the different phenomenology displayed by La-based cuprates and the other families [3]. A lingering question is whether the stripe/charge order is driven by a purely electronic mechanism, or if instead a phononic contribution is also present. The problem is complicated by the presence of dynamic excitations that precede the formation of static charge order [4–9]. The predominant interpretation is that they constitute quantum fluctuations of the electronic “crystal” created by charge-density waves. Such strong fluctuations could signal the proximity to a quantum critical point, which is sometimes identified with the putative pseudogap endpoint at $p \sim 0.19$ [10, 11]. It was proposed that the short-range character of such excitations could provide an almost-isotropic scattering in momentum space, which in turn might explain the strange-metal behaviour in the transport properties [12–14]. Little is known yet, however, about the symmetry of such excitations. The presence of twinned charge-order domains in the tetragonal CuO_2 planes precludes an easy investigation of their properties.

We design an experiment to test these interpretations. Employing a novel *in-situ* strain device, we achieve substantial detwining of the charge-stripe order in the prototypical cuprate $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ with $x = 0.125$, where the strength of charge order is maximum. We investigate the inelastic excitations using ultra-high-resolution RIXS at both the oxygen- K and copper- L_3 edge. No changes in the energy and intensity of optical phonon excitations are observed. The absence of any sizeable effect in the bond-buckling and bond-stretching phonon response demonstrates that the phonon intensity and dispersion anomalies are not primarily correlated with the strength of the static order. Consequently, we prove that charge-stripe order is driven, at least in La-based compounds, primarily by electronic correlations. The simultaneous use of ultra-high-resolution at two resonant edges allows us to disentangle the quantum fluctuations associated to charge order that broadly peak around the charge order wavevector. Our measurements demonstrate that these excitations remain unaffected by the strain application both around the a - and b - axis ordering wavevectors, and retain a four-fold symmetry. Our observations resolve the apparent discrepancy observed in the RIXS response at Cu L_3 and O K edges [4, 9, 15] and provide a clear proof of the existence of dynamical charge density fluctuations in the phase diagram of cuprates. We show that these excitations are insensitive to strain application, suggesting that they are associated to a very short-range interaction between electrons, decoupled from static charge-stripe order. Our observations have implications for the theory of charge fluctuations and strange metal properties.

* leonardo.martinelli@physik.uzh.ch

† izabela.bialo@uzh.ch

‡ johan.chang@physik.uzh.ch

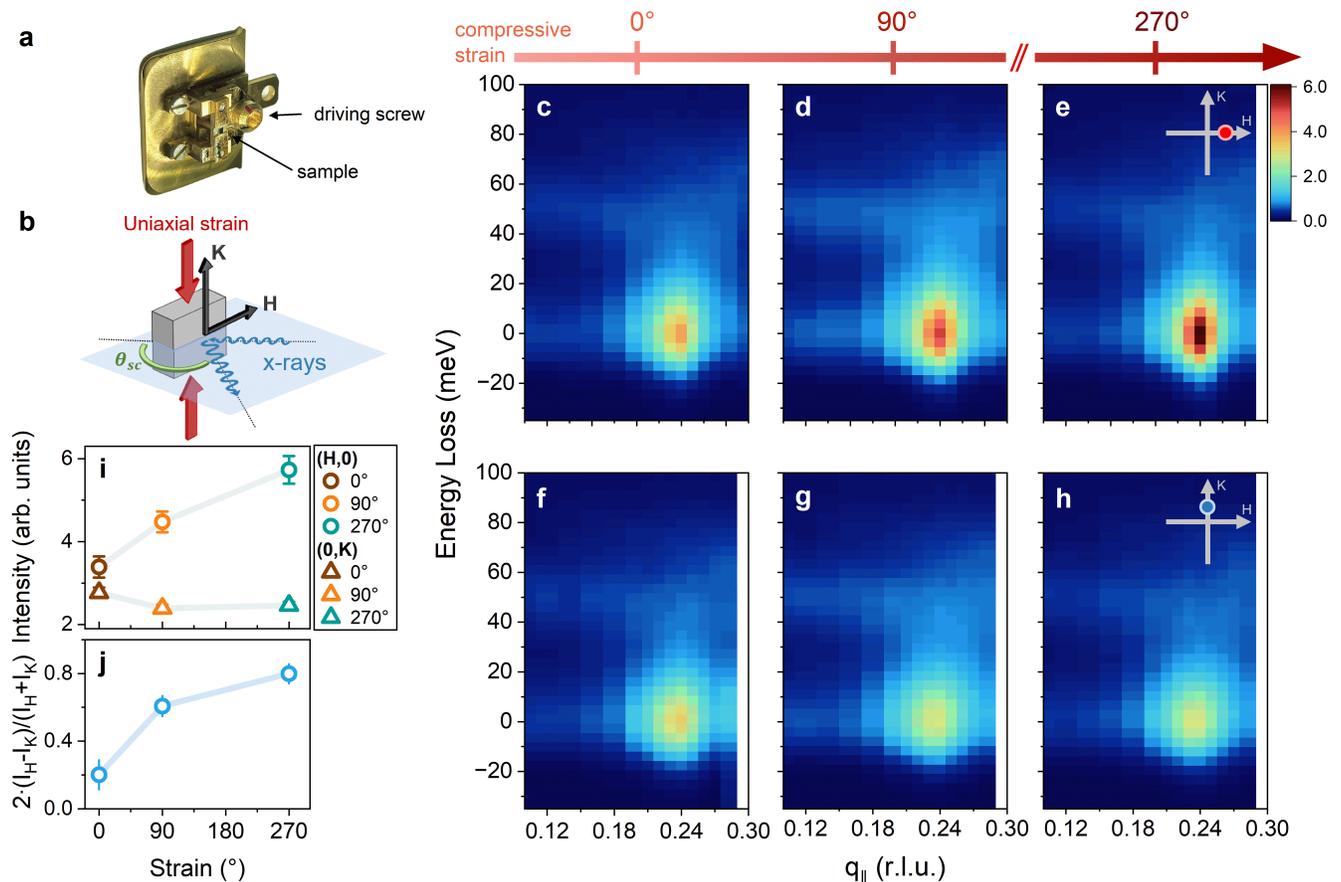


FIG. 1. RIXS spectra at oxygen K -edge under uniaxial pressure application. (a) Photograph and (b) sketch of respectively the *in-situ* strain device and the experimental (scattering) geometry. Incident and scattered x-rays are indicated by blue wavy arrows. The reciprocal H and K directions are indicated with black arrows. The direction of application of uniaxial strain (K) is indicated with thick red arrows. (c-e) Low-energy RIXS spectra as a function of momentum along the $(H,0)$ and (f-h) $(0,K)$ directions. (i) Intensity of static CO along $(H,0)$ (circles) and $(0,K)$ (triangles) directions as a function of applied strain, quantified by screw angle rotation – see Supplementary Materials [16]. (j) Difference between CO intensity along $(H,0)$ and $(0,K)$ directions divided by the mean value.

I. RESULTS

Charge order anisotropy – Our RIXS scattering geometry is illustrated in Fig. 1(a,b). The sample stage can be rotated such that scans along both $q_{\parallel} = (H,0)$ and $(0,K)$ directions are possible under application of b -axis strain. We start by discussing oxygen K -edge results. RIXS maps along the two high-symmetry directions are shown for three pressure points in Fig. 1(c-h). Elastic scattering from charge order (CO) is observed at $q_{co} = (\delta,0)$ and $(0,\delta)$ with $\delta \sim 0.235$ r.l.u. – consistent with previous reports [17, 18].

Our strain device applies uniaxial strain through a screw mechanism, see Fig. 1(a). The applied strain is quantified in terms of the rotation screw angle. By comparison with diffraction measurements [19], we can estimate a maximum applied strain of $\sim 0.1\%$ (see Methods and the Supplementary Materials) [16]. To quantify the CO intensity versus applied strain, we fit the RIXS spec-

tra with a model comprising an elastic peak, three inelastic excitations, and a smooth function for the electron-hole continuum (Fig. 2(a)). Our fitting procedure is elaborated in the Supplementary Material. Intensity of CO is quantified by the area of the elastic line as a function of in-plane momentum. The analysis of the charge order peak intensity is shown in Fig. 1(i,j). In the absence of strain application, a - and b -axis charge order is nearly equally strong. The small difference may originate from a small residual compressive strain induced by thermal contraction of the device. With application of b -axis strain, the a -axis charge order intensity I_H is enhanced roughly linearly in the investigated range of strain values (Fig. 1(i)). Simultaneously, b -axis CO intensity I_K decreases, in agreement with Ref. [19]. The correlation length, extracted as $\xi = \frac{1}{\text{HWHM}}$ [20] with HWHM being the half-width at half-maximum of the CO peak), slightly increases with strain along the a -axis, from (9 ± 1) to (12 ± 1) unit cells. No significant changes are observed

along the b -axis. These correlation lengths are consistent with the existing literature [21, 22]. The domain population factor $2(I_H - I_K)/(I_H + I_K)$, plotted in Fig. 1(j), increases by more than a factor of four in the applied strain interval. We note that, in our RIXS measurements, the magnitude of the reduction of CO along b -axis is less than the enhancement along the perpendicular direction. The fact that the volume of CO is not conserved is consistent with previous resonant scattering measurements on $\text{YBa}_2\text{Cu}_3\text{O}_{6+x}$ [23, 24].

Fundamental excitations – The high energy resolution of RIXS spectra (23 meV at the oxygen K -edge) allows us to scrutinize the charge excitations visible in the 0 – 100 meV-energy range. A typical RIXS spectrum near the charge ordering vector is shown in Fig. 2(a). Elastic scattering from the charge ordering is the most intense feature in the spectrum. RIXS maps with the elastic component subtracted are therefore shown in Fig. 2(b-d). The low-energy part of the spectra contains three excitation branches – with energy scales of about 20, 50 and 70 meV. The two highest-energy modes are identified with the oxygen bond-buckling (BB) and bond-stretching (BS) modes by comparison with inelastic neutron and x-ray scattering experiments [25–27].

From the abovementioned fitting model (see also Supplementary Material [16]) the dispersion relations and excitation amplitudes are extracted. The LE excitation has a pronounced intensity maximum centered approximately at the CO wavevector. The width in momentum is ~ 0.1 r.l.u. which corresponds to a real-space correlations length of roughly 6 unit cells. Its energy shows a minimum close to q_{co} and a dispersion of ~ 5 meV (Fig. 2(b)). The energy of the BS phonon is in excellent agreement with neutron scattering measurements on La-based cuprates [28–30] and shows a softening of ~ 10 meV around the same wavevector (Fig. 2(b,e)). The dispersion relations, as well as the intensities versus momentum is – within our instrumental sensitivity – independent of the applied uniaxial pressure. In particular, as shown in Fig. 2(e), the anomalous softening of the BS phonons is independent of strain, and is equal along the $(H, 0)$ and $(0, K)$ directions. The intensity of the LE mode also shows the same behavior – see Fig. 2(f)-(h). These observations are simultaneous with the uniaxial-strain-induced detwinning of the static CO.

All these observations are confirmed and reproduced at the copper L -edge (Fig. 3). In particular, the ratio of the intensities of CO along the H and K directions is consistent at the two edges. With the assumption that the measured excitations have the same energy at the two edges, we are able to give a unified description of the RIXS response. The momentum dependence of the intensity observed on the LE mode is identical to that extracted at the oxygen K -edge, as highlighted in panel (d) of Fig. 3. The intensity of the bond-stretching mode is, in particular, identical along the a - and b -axis along the entire direction, and independent of strain within our experimental sensitivity. These observations reinforce the

results at the oxygen K -edge and prove that the same excitations are observed on both resonances. Our observations at the Cu- L and O- K edges are schematically visualized in Fig. 4.

II. DISCUSSION

Acquisition of high-resolution RIXS spectra allowed us to extract three low-energy excitations. The bond-buckling oxygen mode, at 50 meV, despite being possibly involved in an enhancement of superconductivity [31], does not show a substantial coupling to charge order and its fluctuations. Our analysis, consistently with previous results, shows that its energy and intensity do not display any relevant anomalies in the proximity of q_{co} (see Supplemental Material Fig. S4-S5). We will therefore concentrate our discussion on the other two modes.

A fundamental question revolves around the relationship between the softening of the BS mode and charge order. The softening of the dispersion from the $\cos(\pi k_{x,y})$ behaviour expected from LDA calculations [32] (dotted line in panel (e) Fig. 2), as well as anomalies in the linewidth and intensity of the mode, have been reported in many cuprate families by several spectroscopic techniques [4, 8, 15, 25, 33, 34]. This effect could be interpreted as a self-energy effect stemming from the presence of stripe order exhibiting two-fold (C_2) symmetry. In this scenario, bond-stretching phonons should split into two branches, one propagating parallel to the stripe modulation (showing the anomalous softening) and one moving perpendicular to them [35]. Establishing this experimentally has been complicated by the presence of twinned domains with a perpendicular orientation of charge order, as well as the insufficient momentum resolution of neutron scattering experiments. Our results suggest no connection between self-energy effects and static charge ordering. Indeed, we do not detect any change in the intensity and dispersion of phonons as a function of applied strain, despite a two-fold change in the intensity of static charge-order, see Fig. 2. The softening persists unaltered along both in-plane directions. Moreover, no double-peak structure is evident in the experimental spectra (Fig. 2a). In the case of a double-peak structure, the asymmetry in the number of twinned domains induced by uniaxial strain should reflect in a slightly different energy of the BS mode when fitted with a single peak. Such a shift is not observed within our sensitivity.

RIXS also provides a direct measure of electron-phonon coupling (EPC) [36–38]. In systems where the photo-excited electrons are strongly localized, like at the copper L_3 -edge in cuprates, the RIXS phonon cross section is indeed to first order proportional to the EPC [39]. Even when this approximation breaks down, as at the oxygen K -edge, still a positive correlation persists [38]. Our measurements on LSCO do not support a connection between electron-phonon coupling of oxygen BS modes and static charge ordering. In fact, we do not detect any

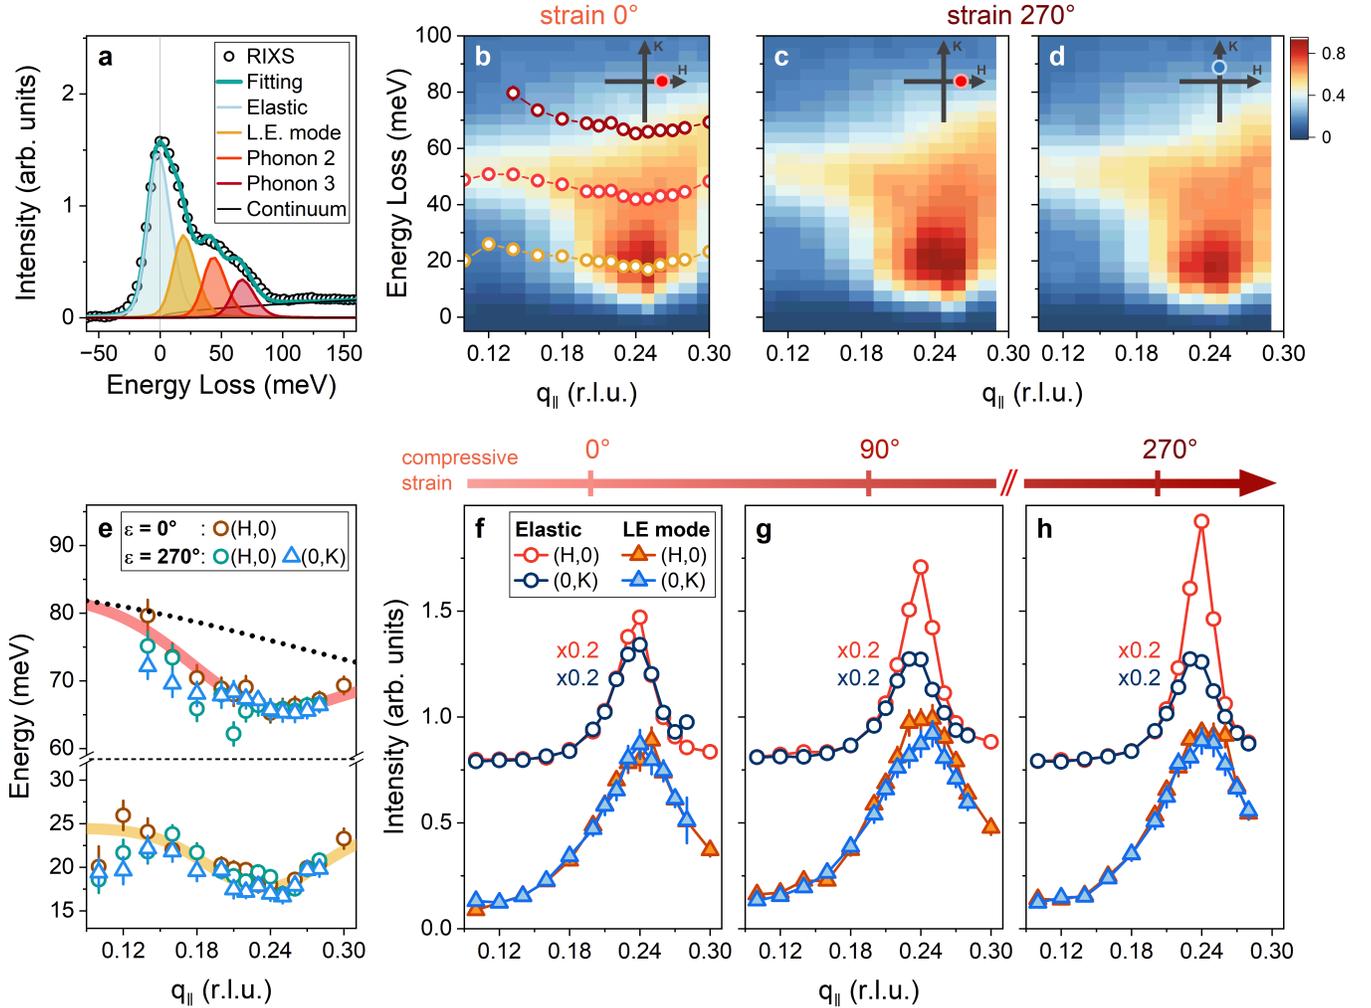


FIG. 2. **Oxygen K -edge resonant x-ray scattering.** (a) Example spectrum at $Q=(0.26,0)$, including our fitting model (green line). The elastic component is shown in light blue, the low-energy mode in yellow, and the buckling (bond-stretching) phonon mode is displayed in orange (red). Weak continuum of electron-hole excitations is shown in black. (b)-(d) RIXS spectra as a function of momentum $q_{||}$ after subtraction of the elastic signal. Applied strain values and directions are indicated above the panels and in the insets, respectively. (e) Energy of the bond-stretching mode and of the low-energy mode as a function of momentum for two different values of applied strain, for both H (circles) and K (triangles) directions. The black dotted line is a cosine function, while the red solid line is a guide to the eye. The solid yellow line is a guide to the eye. (f)-(h) Intensity of elastic peak (empty circles) and low-energy mode (filled triangles) for both $(H,0)$ (red and orange symbols) and $(0,K)$ (blue and light-blue symbols) directions, for increasing strain application.

strain effect on the RIXS BS phonon cross-section, which displays no anisotropy along the $(H,0)$ and $(0,K)$ directions (see panel (c) of Fig. 3). This implies that the EPC is identical along the a - and b -axis, despite a two-fold increase in the intensity of CDW.

The root cause of the softening of the BS mode must therefore be searched elsewhere. Previous works suggested that dynamical fluctuations of finite energy could be a source of phonon energy renormalization [40, 41]. The dispersion of the LE mode, at energies of ~ 20 meV, shows a distinct softening at the CO wavevector, where the spectral weight is simultaneously enhanced. This excitation has been measured recently in RIXS experiments

on different cuprate materials, and has been linked to charge ordering because of a peculiar doping and temperature dependence. A loss of spectral weight has been reported in the low-energy RIXS spectra upon heating [5, 9, 10, 15, 42], a behaviour incompatible with a pure phonon mode. Similarly when going to the strongly underdoped and overdoped regime [10, 15]. Both observations rule out any description of this excitation in terms of a pure phonon mode. Its nature is, however, not conclusively established. RIXS literature on copper- L and [4, 8] and oxygen- K [9, 15] edges suggested divergent interpretations. The low-energy spectra are assigned to either strong softening of bond-stretching modes [4, 8]

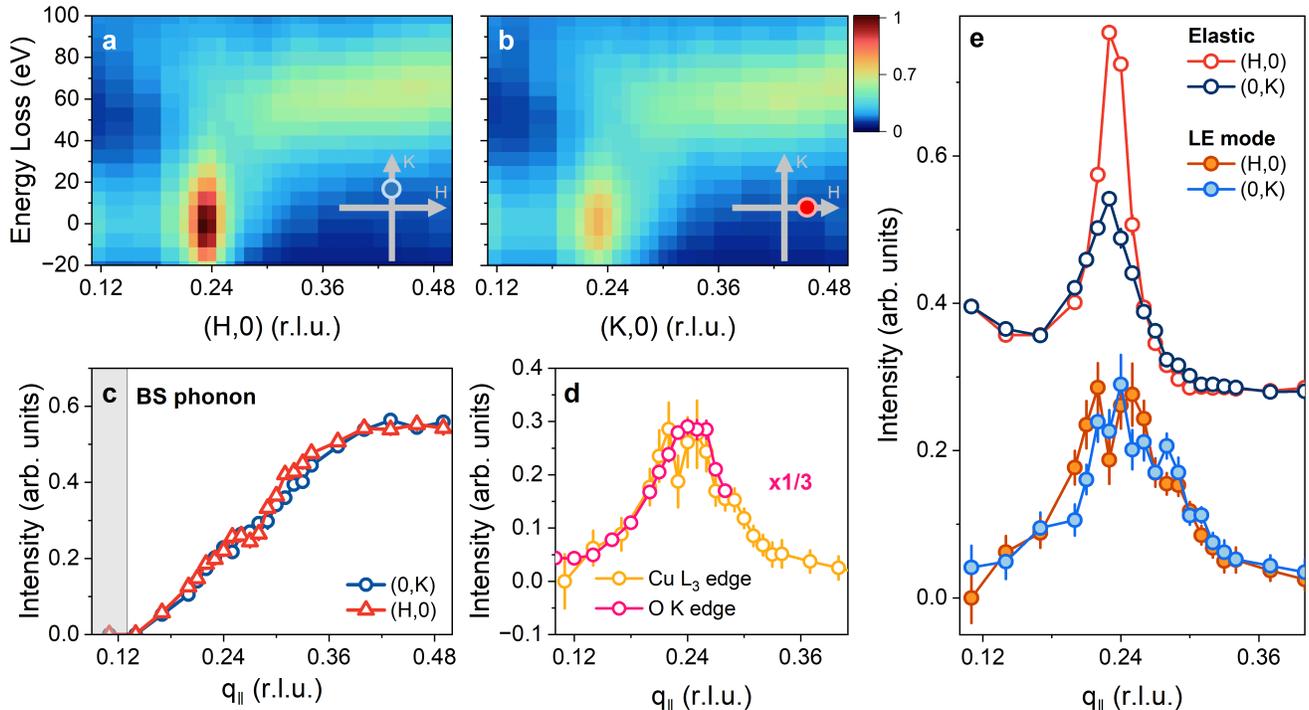


FIG. 3. **Copper L -edge resonant x-ray scattering.** (a-b) RIXS maps along the $(H,0)$ and $(0,K)$ high symmetry directions. (c) Intensity of the bond-stretching phonon along the $(H,0)$ and $(0,K)$ directions at the maximum applied strain (270° screw rotation). (d) Comparison of the phonon peak amplitude obtained at the oxygen and copper edges and plotted versus momentum. (e) Elastic and LE excitation intensities along the $(H,0)$ and $(0,K)$. Solid lines in (c-e) are guides to the eye. All error bars reflect confidence intervals on fitting parameters.

or a low-energy electronic excitation [9, 15]. The latter scenario is commonly used in terms of a continuum quantum fluctuations associated with charge ordering [4, 5, 9]. This point of view builds on the existence of a quantum critical point in the doping-temperature phase diagram of cuprates [14, 43].

By combining measurements at the two edges, we provide consistent results of the low-energy RIXS excitations. This resolves the discrepancies in the existing literature and provide a solid ground for interpretation. More importantly, we demonstrate a clear connection between the softening of the BS mode and the intensity of the LE mode, while excluding any substantial effect from the static order (Fig. 4). Our measurements, therefore, provide a proof that static charge order is, in the cuprates, unconventional in its origin, ruling out a scenario in which electron-phonon coupling plays a significant contribution.

Our results show that the quantum fluctuations of the charge order parameter retain a C_4 symmetry despite the evident one-dimensional character of the static modulation [19, 44, 45]. It is interesting to note that recent results have suggested the presence of electronic excitations in spectra of cuprates with an almost circular symmetry

[46, 47]. This suggests that electronic excitations are determined by a quasi-circular long-range Coulomb interaction. As such, weaker influence of the lattice symmetry is expected on these excitations. Our measurements are compatible with this scenario. Furthermore, recent diffraction measurements on LSCO were interpreted with the existence of two different types of charge order [48], one of which is linked to the spin order. It is not inconceivable that only one of the two orders is affected by the strain. Our measurements are however acquired at T_c , where spin order should not be present [49].

Our uniaxial pressure experiments show no in-plane anisotropy of the electron-phonon coupling and phonon self-energy (Fig. 4). As such, we conclude that EPC is not the main driving mechanism for charge stripe order in the cuprates. An unconventional electronic ordering mechanism is more plausible. Interestingly, the dynamical charge excitations within the detwinned charge ordered phase retain rotational symmetry. It is possible that uniaxial-pressure induced detwinning of charge stripe order is a degeneracy lifting of ground states within a few milli-electron volt. As the observed charge excitations are an order of magnitude more energetic, a decoupling would be possible. In outlook, it would be of

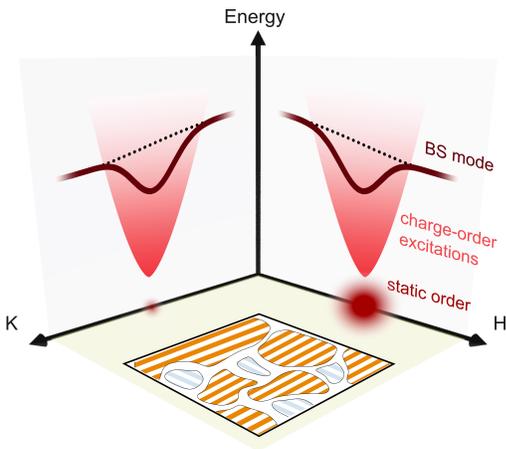


FIG. 4. **Sketch summarizing our experimental results.** The intensity of static charge order shows a substantial detuning upon strain application. The energy and intensity of charge fluctuations, as well as the softening of the BS mode, retain tetragonal symmetry. The square at the bottom sketches the situation in real space, with an imbalance of charge order domains.

great interest for future experiments to completely resolve charge fluctuations, precisely measuring their energy and width as a function of momentum and temperature.

III. METHODS

Samples - A single crystal rod of LSCO $x = 0.125$ was grown by floating zone methodology [50]. Assisted by X-ray LAUE, rectangular pieces with facets defined by the tetragonal a -, b -, and c -axes were cut down to $1 \times 0.4 \times 0.7 \text{ mm}^3$ in size and glued inside the strain cell. Samples were cleaved ex-situ right before RIXS measurements.

Resonant scattering measurements - RIXS experiments were carried out at the I21 beamline of the Diamond Light Source (DLS) [51]. The energy resolutions – estimated from elastic scattering on an amorphous carbon tape – were 23 and 43 meV full-width-at-half-maximum

(FWHM) respectively at the oxygen- K and copper- L_3 edge. With this resolution, it was not possible to extract the life times (intrinsic linewidths) of the charge fluctuations in our experiment. To optimize the RIXS cross section, data were recorded using linear vertical (σ) incident light polarisation in grazing incidence scattering geometry. Consistent with existing literature, we describe the charge ordering vector(s) in tetragonal notation even the low temperature structure of LSCO $x = 0.12$ is orthorhombic or monoclinic [52]. Wave vectors $Q = (q_x, q_y, q_z)$ are thus labelled in reciprocal lattice units (r.l.u.) of $(2\pi/a, 2\pi/b, 2\pi/c)$, with $a = b = 3.78 \text{ \AA}$, and $c = 13.2 \text{ \AA}$. Temperature was kept at $T_c \sim 28 \text{ K}$ during the measurements, to ensure maximum intensity of CO [21, 50].

Uniaxial pressure cell - Our uniaxial pressure cell is an adaptation of the design described in Ref. [53, 54]. Compressive strain is applied ex situ through a screw mechanism. As RIXS does not provide a direct pressure gauge, our strain estimation relies on comparison with previous diffraction measurements [19]. For a comprehensive discussion of design and strain calibration, see Supplementary Material [16].

Data availability

Data supporting the findings of this study are available from the corresponding authors upon request.

Author contributions

L.M. and I.B. have contributed equally to this work. Q.W. and I.B. conceived the project. T.K., N.M., and M.O. grew and characterized the $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ single crystals. L.M., I.B. and X.H. aligned, cut, prepared, and glued the crystals inside the strain cell. L.M., I.B., X.H., J.O., T.S., J.Choi, S.A., M.G-F. and K-J.Z. carried out the RIXS experiments. L.M. analysed the RIXS data with the help from I.B., and J.C.. C.L. designed the uniaxial pressure cell. All authors contributed to the writing of the manuscript.

Competing interests

The authors declare no competing interests.

-
- [1] Luca Fausto Tocchio, Arianna Montorsi, and Federico Becca, “Metallic and insulating stripes and their relation with superconductivity in the doped Hubbard model,” *SciPost Physics* **7**, 021 (2019).
- [2] Hong-Chen Jiang and Thomas P. Devereaux, “Superconductivity in the doped Hubbard model and its interplay with next-nearest hopping t' ,” *Science* **365**, 1424–1428 (2019).
- [3] R. Comin, A. Frano, M. M. Yee, Y. Yoshida, H. Eisaki, E. Schierle, E. Weschke, R. Sutarto, F. He, A. Soumyanarayanan, Y. He, M. Le Tacon, I. S. Elfimov, J. E. Hoffman, G. A. Sawatzky, B. Keimer, and A. Damascelli, “Charge order driven by Fermi-arc instability in $\text{Bi}_2\text{Sr}_{2-x}\text{La}_x\text{CuO}_{6+\delta}$,” *Science* **343**, 390–392 (2014).
- [4] L. Chaix, G. Ghiringhelli, Y. Y. Peng, M. Hashimoto, B. Moritz, K. Kummer, N. B. Brookes, Y. He, S. Chen, S. Ishida, Y. Yoshida, H. Eisaki, M. Salluzzo, L. Braicovich, Z.-X. Shen, T. P. Devereaux, and W.-S. Lee, “Dispersive charge density wave excitations in $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$,” *Nat. Phys.* **13**, 952–956 (2017).

- [5] R. Arpaia, S. Caprara, R. Fumagalli, G. De Vecchi, Y. Y. Peng, E. Andersson, D. Betto, G. M. De Luca, N. B. Brookes, F. Lombardi, M. Salluzzo, L. Braicovich, C. Di Castro, M. Grilli, and G. Ghiringhelli, “Dynamical charge density fluctuations pervading the phase diagram of a Cu-based high- T_c superconductor,” *Science* **365**, 906–910 (2019).
- [6] H. Miao, J. Lorenzana, G. Seibold, Y. Y. Peng, A. Amorese, F. Yakhou-Harris, K. Kummer, N. B. Brookes, R. M. Konik, V. Thampy, G. D. Gu, G. Ghiringhelli, L. Braicovich, and M. P. M. Dean, “High-temperature charge density wave correlations in $\text{La}_{1.875}\text{Ba}_{0.125}\text{CuO}_4$ without spin-charge locking,” *Proc. Natl. Acad. Sci.* **114**, 12430–12435 (2017).
- [7] H. Miao, R. Fumagalli, M. Rossi, J. Lorenzana, G. Seibold, F. Yakhou-Harris, K. Kummer, N. B. Brookes, G. D. Gu, L. Braicovich, G. Ghiringhelli, and M. P. M. Dean, “Formation of incommensurate charge density waves in cuprates,” *Phys. Rev. X* **9**, 031042 (2019).
- [8] W. S. Lee, Ke-Jin Zhou, M. Hepting, J. Li, A. Nag, A. C. Walters, M. Garcia-Fernandez, H. C. Robarts, M. Hashimoto, H. Lu, B. Noszarzewski, D. Song, H. Eisaki, Z. X. Shen, B. Moritz, J. Zaanen, and T. P. Devereaux, “Spectroscopic fingerprint of charge order melting driven by quantum fluctuations in a cuprate,” *Nature Physics* **17**, 53–57 (2021).
- [9] H. Y. Huang, A. Singh, C. Y. Mou, S. Johnston, A. F. Kemper, J. van den Brink, P. J. Chen, T. K. Lee, J. Okamoto, Y. Y. Chu, J. H. Li, S. Komiya, A. C. Komarek, A. Fujimori, C. T. Chen, and D. J. Huang, “Quantum Fluctuations of Charge Order Induce Phonon Softening in a Superconducting Cuprate,” *Physical Review X* **11**, 041038 (2021).
- [10] Riccardo Arpaia, Leonardo Martinelli, Marco Moretti Sala, Sergio Caprara, Abhishek Nag, Nicholas B. Brookes, Pietro Camisa, Qizhi Li, Qiang Gao, Xingjiang Zhou, Mirian Garcia-Fernandez, Ke-Jin Zhou, Enrico Schierle, Thilo Bauch, Ying Ying Peng, Carlo Di Castro, Marco Grilli, Floriana Lombardi, Lucio Braicovich, and Giacomo Ghiringhelli, “Signature of quantum criticality in cuprates by charge density fluctuations,” *Nature Communications* **14**, 7198 (2023).
- [11] Sergio Caprara, Carlo Di Castro, Giovanni Mirarchi, Götz Seibold, and Marco Grilli, “Dissipation-Driven Strange Metal Behavior,” *Communications Physics* **5**, 1–7 (2022), publisher: Nature Publishing Group.
- [12] Gaël Grissonnanche, Yawen Fang, Anaëlle Legros, Simon Verret, Francis Laliberté, Clément Collignon, Jian-shi Zhou, David Graf, Paul A. Goddard, Louis Taillefer, and B. J. Ramshaw, “Linear-in temperature resistivity from an isotropic Planckian scattering rate,” *Nature* **595**, 667–672 (2021).
- [13] S. Caprara, C. Di Castro, G. Seibold, and M. Grilli, “Dynamical charge density waves rule the phase diagram of cuprates,” *Phys. Rev. B* **95**, 224511 (2017).
- [14] Götz Seibold, Riccardo Arpaia, Ying Ying Peng, Roberto Fumagalli, Lucio Braicovich, Carlo Di Castro, Marco Grilli, Giacomo Claudio Ghiringhelli, and Sergio Caprara, “Strange metal behaviour from charge density fluctuations in cuprates,” *Communications Physics* **4**, 1–6 (2021).
- [15] Jiemin Li, Abhishek Nag, Jonathan Pellicciari, Hannah Robarts, Andrew Walters, Mirian Garcia-Fernandez, Hiroshi Eisaki, Dongjoon Song, Hong Ding, Steven Johnston, Riccardo Comin, and Ke-Jin Zhou, “Multiorbital charge-density wave excitations and concomitant phonon anomalies in $\text{Bi}_2\text{Sr}_2\text{LaCuO}_{4+\delta}$,” *Proc. Natl. Acad. Sci. USA* **117**, 16219–16225 (2020).
- [16] See Supplemental Material for details on experimental configurations, fitting of RIXS spectra, data normalization and background subtraction, which includes Refs. [11, 12, 22, 24, 37, 38, 42–45].
- [17] Qisi Wang, K. von Arx, D. G. Mazzone, S. Mustafi, M. Horio, J. Küspert, J. Choi, D. Bucher, H. Wo, J. Zhao, W. Zhang, T. C. Asmara, Y. Sassa, M. Månsson, N. B. Christensen, M. Janoschek, T. Kurosawa, N. Momono, M. Oda, M. H. Fischer, T. Schmitt, and J. Chang, “Uniaxial pressure induced stripe order rotation in $\text{La}_{1.88}\text{Sr}_{0.12}\text{CuO}_4$,” *Nature Communications* **13** (2022), 10.1038/s41467-022-29465-4.
- [18] V. Thampy, M. P. M. Dean, N. B. Christensen, L. Steinke, Z. Islam, M. Oda, M. Ido, N. Momono, S. B. Wilkins, and J. P. Hill, “Rotated stripe order and its competition with superconductivity in $\text{La}_{1.88}\text{Sr}_{0.12}\text{CuO}_4$,” *Phys. Rev. B* **90**, 100510(R) (2014).
- [19] J. Choi, Q. Wang, S. Jöhr, N. B. Christensen, J. Küspert, D. Bucher, D. Biscette, M. H. Fischer, M. Hücker, T. Kurosawa, N. Momono, M. Oda, O. Ivashko, M. v. Zimmermann, M. Janoschek, and J. Chang, “Unveiling unequivocal charge stripe order in a prototypical cuprate superconductor,” *Phys. Rev. Lett.* **128**, 207002 (2022).
- [20] S. B. Wilkins, M. P. M. Dean, Jörg Fink, Markus Hücker, J. Geck, V. Soltwisch, E. Schierle, E. Weschke, G. Gu, S. Uchida, N. Ichikawa, J. M. Tranquada, and J. P. Hill, “Comparison of stripe modulations in $\text{La}_{1.875}\text{Ba}_{0.125}\text{CuO}_4$ and $\text{La}_{1.48}\text{Nd}_{0.4}\text{Sr}_{0.12}\text{CuO}_4$,” *Phys. Rev. B* **84**, 195101 (2011).
- [21] T. P. Croft, C. Lester, M. S. Senn, A. Bombardi, and S. M. Hayden, “Charge density wave fluctuations in $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ and their competition with superconductivity,” *Phys. Rev. B* **89**, 224513 (2014).
- [22] N. B. Christensen, J. Chang, J. Larsen, M. Fujita, M. Oda, M. Ido, N. Momono, E. M. Forgan, A. T. Holmes, J. Mesot, M. Huecker, and M. v. Zimmermann, “Bulk charge stripe order competing with superconductivity in $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ ($x=0.12$),” [arXiv:1404.3192](https://arxiv.org/abs/1404.3192).
- [23] H.-H. Kim, E. Lefrançois, K. Kummer, R. Fumagalli, N. B. Brookes, D. Betto, S. Nakata, M. Tortora, J. Porras, T. Loew, M. E. Barber, L. Braicovich, A. P. Mackenzie, C. W. Hicks, B. Keimer, M. Minola, and M. Le Tacon, “Charge density waves in $\text{YBa}_2\text{Cu}_3\text{O}_{6.67}$ probed by resonant x-ray scattering under uniaxial compression,” *Phys. Rev. Lett.* **126**, 037002 (2021).
- [24] H.-H. Kim, S. M. Souliou, M. E. Barber, E. Lefrançois, M. Minola, M. Tortora, R. Heid, N. Nandi, R. A. Borzi, G. Garbarino, A. Bosak, J. Porras, T. Loew, M. König, P. J. W. Moll, A. P. Mackenzie, B. Keimer, C. W. Hicks, and M. Le Tacon, “Uniaxial pressure control of competing orders in a high-temperature superconductor,” *Science* **362**, 1040–1044 (2018), publisher: American Association for the Advancement of Science.
- [25] L. Pintschovius and M. Braden, “Anomalous Dispersion of LO Phonons in $\text{La}_{1.85}\text{Sr}_{0.15}\text{CuO}_4$,” *Physical Review B* **60**, R15039–R15042 (1999).
- [26] R. J. McQueeney, Y. Petrov, T. Egami, M. Yethiraj, G. Shirane, and Y. Endoh, “Anomalous Dispersion of LO Phonons in $\text{La}_{1.85}\text{Sr}_{0.15}\text{CuO}_4$ at Low Temperatures,”

- Phys. Rev. Lett.* **82**, 628–631 (1999), publisher: American Physical Society.
- [27] X. J. Zhou, Junren Shi, T. Yoshida, T. Cuk, W. L. Yang, V. Brouet, J. Nakamura, N. Mannella, Seiki Komiyama, Yoichi Ando, F. Zhou, W. X. Ti, J. W. Xiong, Z. X. Zhao, T. Sasagawa, T. Kakeshita, H. Eisaki, S. Uchida, A. Fujimori, Zhenyu Zhang, E. W. Plummer, R. B. Laughlin, Z. Hussain, and Z.-X. Shen, “Multiple Bosonic Mode Coupling in the Electron Self-Energy of $(\text{La}_{2-x}\text{Sr}_x)\text{CuO}_4$,” *Phys. Rev. Lett.* **95**, 117001 (2005), publisher: American Physical Society.
- [28] D. Reznik, L. Pintschovius, M. Ito, S. Iikubo, M. Sato, H. Goka, M. Fujita, K. Yamada, G. D. Gu, and J. M. Tranquada, “Electron–phonon coupling reflecting dynamic charge inhomogeneity in copper oxide superconductors,” *Nature* **440**, 1170–1173 (2006).
- [29] D. Reznik, “Giant Electron-Phonon Anomaly in Doped La_2CuO_4 and other cuprates,” *Advances in Condensed Matter Physics* **2010**, e523549 (2010).
- [30] S. R. Park, T. Fukuda, A. Hamann, D. Lamago, L. Pintschovius, M. Fujita, K. Yamada, and D. Reznik, “Evidence for a Charge Collective Mode Associated with Superconductivity in Copper Oxides from Neutron and X-Ray Scattering Measurements of $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$,” *Physical Review B* **89**, 020506 (2014).
- [31] S. Johnston, F. Vernay, B. Moritz, Z.-X. Shen, N. Nagaosa, J. Zaanen, and T. P. Devereaux, “Systematic study of electron-phonon coupling to oxygen modes across the cuprates,” *Phys. Rev. B* **82**, 064513 (2010).
- [32] Feliciano Giustino, Marvin L. Cohen, and Steven G. Louie, “Small phonon contribution to the photoemission kink in the copper oxide superconductors,” *Nature* **452**, 975–978 (2008), publisher: Springer Science and Business Media LLC.
- [33] L. Pintschovius, D. Reznik, W. Reichardt, Y. Endoh, H. Hiraka, J. M. Tranquada, H. Uchiyama, T. Masui, and S. Tajima, “Oxygen Phonon Branches in $\text{YBa}_2\text{Cu}_3\text{O}_7$,” *Physical Review B* **69**, 214506 (2004).
- [34] J. Graf, M. d’Astuto, C. Jozwiak, D. R. Garcia, N. L. Saini, M. Krisch, K. Ikeuchi, A. Q. R. Baron, H. Eisaki, and A. Lanzara, “Bond Stretching Phonon Softening and Kinks in the Angle-Resolved Photoemission Spectra of Optimally Doped $\text{Bi}_2\text{Sr}_{1.6}\text{La}_{0.4}\text{Cu}_2\text{O}_{6+\delta}$ Superconductors,” *Physical Review Letters* **100**, 227002 (2008).
- [35] Eiji Kaneshita, Masanori Ichioka, and Kazushige Machida, “Phonon anomalies due to collective stripe modes in high T_c cuprates,” *Phys. Rev. Lett.* **88**, 115501 (2002).
- [36] T. P. Devereaux, A. M. Shvaika, K. Wu, K. Wohlfield, C. J. Jia, Y. Wang, B. Moritz, L. Chaix, W.-S. Lee, Z.-X. Shen, G. Ghiringhelli, and L. Braicovich, “Directly characterizing the relative strength and momentum dependence of electron-phonon coupling using resonant inelastic x-ray scattering,” *Phys. Rev. X* **6**, 041019 (2016).
- [37] Andrey Geondzhian and Keith Gilmore, “Demonstration of resonant inelastic x-ray scattering as a probe of exciton-phonon coupling,” *Phys. Rev. B* **98**, 214305 (2018).
- [38] Krzysztof Bieniasz, Steven Johnston, and Mona Berciu, “Beyond the single-site approximation modeling of electron-phonon coupling effects on resonant inelastic X-ray scattering spectra,” *SciPost Phys.* **11**, 062 (2021).
- [39] Lucio Braicovich, Matteo Rossi, Roberto Fumagalli, Yingying Peng, Yan Wang, Riccardo Arpaia, Davide Betto, Gabriella M. De Luca, Daniele Di Castro, Kurt Kummer, Marco Moretti Sala, Mattia Pagetti, Giuseppe Balestrino, Nicholas B. Brookes, Marco Salluzzo, Steven Johnston, Jeroen van den Brink, and Giacomo Ghiringhelli, “Determining the electron-phonon coupling in superconducting cuprates by resonant inelastic x-ray scattering: Methods and results on $\text{Nd}_{1+x}\text{Ba}_{2-x}\text{Cu}_3\text{O}_{7-\delta}$,” *Phys. Rev. Research* **2**, 023231 (2020).
- [40] D. Reznik, “Giant Electron-Phonon Anomaly in Doped La_2CuO_4 and other cuprates,” *Advances in Condensed Matter Physics* **2010**, e523549 (2010), publisher: Hindawi.
- [41] S. R. Park, T. Fukuda, A. Hamann, D. Lamago, L. Pintschovius, M. Fujita, K. Yamada, and D. Reznik, “Evidence for a Charge Collective Mode Associated with Superconductivity in Copper Oxides from Neutron and X-Ray Scattering Measurements of $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$,” *Physical Review B* **89**, 020506 (2014).
- [42] B. Yu, W. Tabis, I. Bialo, F. Yakhou, N. B. Brookes, Z. Anderson, Y. Tang, G. Yu, and M. Greven, “Unusual dynamic charge correlations in simple-tetragonal $\text{HgBa}_2\text{CuO}_{4+\delta}$,” *Phys. Rev. X* **10**, 021059 (2020).
- [43] S. Caprara, C. Di Castro, G. Seibold, and M. Grilli, “Dynamical charge density waves rule the phase diagram of cuprates,” *Phys. Rev. B* **95**, 224511 (2017), publisher: American Physical Society.
- [44] A. J. Achkar, M. Zwiebler, Christopher McMahon, F. He, R. Sutarto, Isaiah Djianto, Zhihao Hao, Michel J. P. Gingras, M. Hücker, G. D. Gu, A. Revcolevschi, H. Zhang, Y.-J. Kim, J. Geck, and D. G. Hawthorn, “Nematicity in stripe-ordered cuprates probed via resonant x-ray scattering,” *Science* **351**, 576–578 (2016).
- [45] Jaewon Choi, Jiemin Li, Abhishek Nag, Jonathan Pellicciari, Hannah Robarts, Charles C. Tam, Andrew Walters, Stefano Agrestini, Mirian García-Fernández, Dongjoon Song, Hiroshi Eisaki, Steve Johnston, Riccardo Comin, Hong Ding, and Ke-Jin Zhou, “Universal Stripe Symmetry of Short-Range Charge Density Waves in Cuprate Superconductors,” *Advanced Materials* **n/a**, 2307515 (2023).
- [46] Kirsty Scott, Elliot Kisiel, Timothy J. Boyle, Rourav Basak, Gaëtan Jargot, Sarmistha Das, Stefano Agrestini, Mirian Garcia-Fernandez, Jaewon Choi, Jonathan Pellicciari, Jiemin Li, Yi-De Chuang, Ruidan Zhong, John A. Schneeloch, Genda Gu, François Légaré, Alexander F. Kemper, Ke-Jin Zhou, Valentina Bisogni, Santiago Blanco-Canosa, Alex Frano, Fabio Boschini, and Eduardo H. da Silva Neto, “Low-energy quasi-circular electron correlations with charge order wavelength in $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$,” *Science Advances* **9**, eadg3710 (2023).
- [47] F. Boschini, M. Minola, R. Sutarto, E. Schierle, M. Bluschke, S. Das, Y. Yang, M. Michiardi, Y. C. Shao, X. Feng, S. Ono, R. D. Zhong, J. A. Schneeloch, G. D. Gu, E. Weschke, F. He, Y. D. Chuang, B. Keimer, A. Damascelli, A. Frano, and E. H. da Silva Neto, “Dynamic electron correlations with charge order wavelength along all directions in the copper oxide plane,” *Nature Communications* **12**, 597 (2021).
- [48] J. J. Wen, H. Huang, S. J. Lee, H. Jang, J. Knight, Y. S. Lee, M. Fujita, K. M. Suzuki, S. Asano, S. A. Kivelson, C. C. Kao, and J. S. Lee, “Observation of two types of charge-density-wave orders in superconducting

- La_{2-x}Sr_xCuO₄,” *Nat. Commun.* **10**, 3269 (2019), iISBN: 2041-1723.
- [49] J. Chang, Ch. Niedermayer, R. Gilardi, N. B. Christensen, H. M. Rønnow, D. F. McMorrow, M. Ay, J. Stahn, O. Sobolev, A. Hiess, S. Pailhes, C. Baines, N. Momono, M. Oda, M. Ido, and J. Mesot, “Tuning competing orders in La_{2-x}Sr_xCuO₄ cuprate superconductors by the application of an external magnetic field,” *Phys. Rev. B* **78**, 104525 (2008), publisher: American Physical Society.
- [50] J. Chang, Ch. Niedermayer, R. Gilardi, N. B. Christensen, H. M. Rønnow, D. F. McMorrow, M. Ay, J. Stahn, O. Sobolev, A. Hiess, S. Pailhes, C. Baines, N. Momono, M. Oda, M. Ido, and J. Mesot, “Tuning competing orders in La_{2-x}Sr_xCuO₄ cuprate superconductors by the application of an external magnetic field,” *Phys. Rev. B* **78**, 104525 (2008).
- [51] Ke-Jin Zhou, Andrew Walters, Mirian Garcia-Fernandez, Thomas Rice, Matthew Hand, Abhishek Nag, Jiemin Li, Stefano Agrestini, Peter Garland, Hongchang Wang, Simon Alcock, Ioana Nistea, Brian Nutter, Nicholas Rubies, Giles Knap, Martin Gaughran, Fajin Yuan, Peter Chang, John Emmins, and George Howell, “I21: an advanced high-resolution resonant inelastic x-ray scattering beamline at diamond light source,” *Journal of Synchrotron Radiation* **29**, 563–580 (2022).
- [52] R. Frison, J. Küspert, Qisi Wang, O. Ivashko, M. v. Zimmermann, M. Meven, D. Bucher, J. Larsen, Ch. Niedermayer, M. Janoschek, T. Kurosawa, N. Momono, M. Oda, N. B. Christensen, and J. Chang, “Crystal symmetry of stripe-ordered La_{1.88Sr_{0.12}CuO₄,” *Phys. Rev. B* **105**, 224113 (2022).}
- [53] Chun Lin, Masayuki Ochi, Ryo Noguchi, Kenta Kuroda, Masahito Sakoda, Atsushi Nomura, Masakatsu Tsubota, Peng Zhang, Cedric Bareille, Kifu Kurokawa, Yosuke Arai, Kaishu Kawaguchi, Hiroaki Tanaka, Koichiro Yaji, Ayumi Harasawa, Makoto Hashimoto, Donghui Lu, Shik Shin, Ryotaro Arita, Satoshi Tanda, and Takeshi Kondo, “Visualization of the strain-induced topological phase transition in a quasi-one-dimensional superconductor TaSe₃,” *Nature Materials* **20**, 1093–1099 (2021).
- [54] Chun Lin, Armando Consiglio, Ola Kenji Forsslund, Julia Kuspert, M. Michael Denner, Hechang Lei, Alex Louat, Matthew D. Watson, Timur K. Kim, Cephise Cacho, Dina Carbone, Mats Leandersson, Craig Polley, Thiagarajan Balasubramanian, Domenico Di Sante, Ronny Thomale, Zurab Guguchia, Giorgio Sangiovanni, Titus Neupert, and Johan Chang, “Giant Strain Response of Charge Modulation and Singularity in a Kagome Superconductor,” (2024), arXiv:2402.16089 [cond-mat].