

# Real-space $d$ -wave superconductivity from weak attraction

Pavel Kornilovitch\*

Department of Physics, Oregon State University, Corvallis, Oregon 97331, USA

(Dated: July 11, 2024)

It is shown that even a weak out-of-plane attraction,  $V \rightarrow 0$ , can form real-space pairs in the body-centered tetragonal lattice despite the presence of a Hubbard repulsion and a fully developed three-dimensional kinetic energy. In the hole channel, the pairs have  $d$  orbital symmetry which, following Bogoliubov's argument, translates into a  $d$ -symmetric macroscopic superconducting order parameter. The findings help to understand key features of  $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$  and further support the real-space mechanism of superconductivity in cuprates. The rules of real-space superconductivity are formulated at the end.

*Introduction.* In BCS superconductivity [1, 2], Cooper pairs can form because the Fermi sea reduces kinetic energy [3] while slow ions effectively reduce Coulomb repulsion [4–6]. In BEC superconductivity [7–16], real-space pairs can form if a non-retarded attraction  $V$  overcomes repulsion  $U$  and kinetic energy  $K$ . Pair formation threshold,  $V_{\text{cr}}$ , is of the order of several hopping integrals  $t$  for a broad range of lattice geometries [17].  $V_{\text{cr}}$  remains finite even in the absence of repulsion as long as  $K$  is three-dimensional. In hole-doped cuprates near half filling,  $t \approx 0.1$  eV [18], which means a  $V_{\text{cr}}$  of several tenths of eV is needed to form pairs. This may be challenging to achieve with phonon [16], Jahn-Teller [19–21], or spin wave [22] mediation. One approach to lower  $V_{\text{cr}}$  is to spread attraction over several unit cells trading the depth of an attractive potential for its width [23]. In this paper, we describe a realistic 3D system where an *infinitesimal* out-of-plane attraction  $V \ll t$  produces real-space pairs despite the presence of a Hubbard repulsion and fully developed 3D kinetic energy. In the *hole* channel of the body-centered tetragonal (BCT) lattice,  $q_z$ -independent dispersion near  $q_x, q_y = \pm\pi$  renders hole movement near the band edges effectively two-dimensional. A nonlocal  $V$  neutralizes Hubbard repulsion  $U$ . As a result, pairs are formed with zero threshold,  $V_{\text{cr}} \rightarrow 0$ , even for finite  $U$  and interlayer hopping  $t_{\perp}$ . The BCT lattice serves as a prototype structure of  $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$  (LSCO) where each BCT site represents one  $\text{CuO}_6$  octahedron. Thus formed real-space hole pairs have  $d$  orbital symmetry, which naturally leads to macroscopic  $d$ -wave superconductivity.

*Bogoliubov's argument.* We begin by outlining the relation between macroscopic order parameter  $\Delta$  and real-space pair wave function  $\psi$  derived by Bogoliubov [13]. The four-point equal-time correlation function

$$\begin{aligned} F(\mathbf{r}_1, \mathbf{r}_2; \mathbf{r}'_1, \mathbf{r}'_2) &= \langle c_{\mathbf{r}_1}^\dagger c_{\mathbf{r}_2}^\dagger c_{\mathbf{r}'_2} c_{\mathbf{r}'_1} \rangle \\ &= \sum_{\nu} N_{\nu} \Psi_{\nu}^*(\mathbf{r}_1, \mathbf{r}_2) \Psi_{\nu}(\mathbf{r}'_1, \mathbf{r}'_2), \end{aligned} \quad (1)$$

can be expanded in a complete set of normalized solutions of a two-body Schrödinger equation  $\Psi_{\nu}$ . Quantum number  $\nu$  includes pair's total momentum and a discrete index of relative motion of the two particles forming the

pair. In Eq. (1),  $c$  are fermion operators, and  $\langle \dots \rangle$  is understood as quasi-averaging, i.e., quantum-statistical averaging is performed with a fixed phase angle of the superconducting condensate and averaging over the phase angle is not performed. If  $N$  is the total number of particles then  $N(N-1)$  is the total number of pairs. By setting  $\mathbf{r}'_1 = \mathbf{r}_1, \mathbf{r}'_2 = \mathbf{r}_2$  and integrating over  $\mathbf{r}_{1,2}$ , it follows from Eq. (1) that  $\langle N(N-1) \rangle = \sum_{\nu} N_{\nu}$  [13]. Thus, coefficient  $N_{\nu}$  is the average number of pairs in a state with wave function  $\Psi_{\nu}$ . To describe superconducting state, one assumes a condensate of pairs in the ground state, i.e.,  $N_0$  is macroscopically large.

Next, the four coordinates in Eq. (1) are combined in two groups,  $\{\mathbf{r}_1, \mathbf{r}_2\}$  and  $\{\mathbf{r}'_1, \mathbf{r}'_2\}$ , and are infinitely separated. The four-point correlation function splits into a product of two-point correlation functions:

$$\langle c_{\mathbf{r}_1}^\dagger c_{\mathbf{r}_2}^\dagger c_{\mathbf{r}'_2} c_{\mathbf{r}'_1} \rangle = \langle c_{\mathbf{r}_1}^\dagger c_{\mathbf{r}_2}^\dagger \rangle \langle c_{\mathbf{r}'_2} c_{\mathbf{r}'_1} \rangle \equiv \Delta^*(\mathbf{r}_1, \mathbf{r}_2) \Delta(\mathbf{r}'_1, \mathbf{r}'_2). \quad (2)$$

Because of quasi-averaging,  $\Delta \neq 0$ . The right-hand side of Eq. (1) receives contributions from unpaired  $\Psi_{\nu}$  as well as from paired  $\Psi_{\nu}$  not in the condensate. Bogoliubov showed that in the dilute limit, the main contribution comes from the condensate pair state with a relative wave function  $\psi_0(\mathbf{r}_1 - \mathbf{r}_2)$ . The final result is

$$\Delta(\mathbf{r}_1, \mathbf{r}_2) = \sqrt{N_0} \psi_0(\mathbf{r}_1 - \mathbf{r}_2). \quad (3)$$

This formula has an important practical implication: *orbital symmetry of the superconducting order parameter is the same as that of the pair wave function.* The latter can be deduced from a two-body lattice Schrödinger equation which is exactly solvable [17]. Later in the paper, this is done for the body-centered tetragonal lattice.

*BCT lattice as a prototype model structure for LSCO.* We approach cuprate superconductivity as an anisotropic but *three-dimensional* phenomenon. Superconductivity is a phase-coherent Bose condensation of anisotropic real-space pairs formed above  $T_c$ . This viewpoint is supported by the phenomenology of anisotropic Bose gas applied to cuprates [15, 16, 24–30], as well as by measurements of magnetic fluctuations [31] and of the inter-plane coherence length [32]. Real-space pairs above  $T_c$  have been

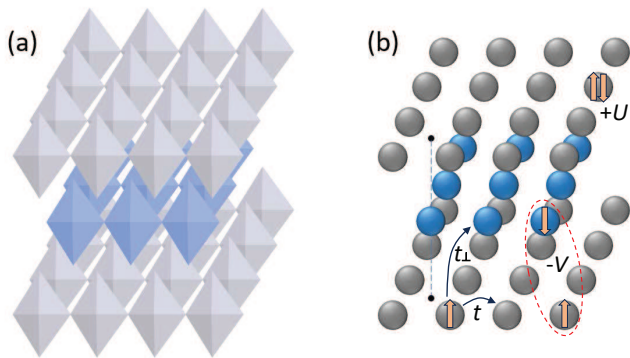


FIG. 1. (a) CuO<sub>6</sub> octahedra in a BCT arrangement. (b) An effective one-orbital BCT lattice. The middle layer is shown in blue for visual purposes.

observed in cuprates [33] and in iron-based superconductors [34, 35].

Theoretical description of cuprate superconductivity should thus be based on three-dimensional models. We focus on the well-studied compound La<sub>2-x</sub>Sr<sub>x</sub>CuO<sub>4</sub>. Its main structural elements are CuO<sub>6</sub> octahedra arranged in a BCT lattice, see Fig. 1(a). (The weak orthorhombic distortion that occurs at low temperatures is disregarded here.) In a commonly held view, the most important orbitals are  $d_{x^2-y^2}$  of copper ions and  $p_x, p_y$  of in-plane oxygen ions [36]. We expand this set by including  $p_z$  orbitals of apical oxygen ions [37, 38] that facilitate hole hopping between layers,  $t_{\perp}$ . We also assume that a multi-orbital model can be downfolded to an effective one-orbital model using one of the several available reduction schemes [39–42]. An essential feature of such reductions is checkerboard arrangement of orbital phases in the ground state of the effective model, which is a consequence of the odd symmetry of  $p_x, p_y$  oxygen orbitals. It results in overall  $d_{x^2-y^2}$  symmetry of in-plane holes. In order to preserve this feature in the effective model built of  $s$  orbitals, in-plane nearest-neighbor hopping must be positive,  $t > 0$ . (We leave aside the powerful idea that in-plane hopping can be doping-dependent which may help explain the superconducting dome [17, 18].) In physical units,  $t \approx 0.1$  eV [18]. One should add that both  $t$  and  $t_{\perp}$  can be affected by electron-phonon interaction and formation of polarons [43–45].

Inter-hole interaction is discussed next. First, there is a Hubbard repulsion  $U \approx 5 - 6$  eV between two holes occupying the same site [46, 47]. Second, quantum-chemical calculations predict a negative excess energy between two *static* holes, one on an in-plane oxygen and another on an apical oxygen, of about 0.12 eV [48, 49]. This is interpreted as an out-of-plane attractive potential  $V \approx (1 - 2)t$ . The involvement of apical oxygens in hole pairing is strongly supported by terahertz excitation experiments [50, 51]. A similar-scale near-neighbor attractive potential,  $V \approx 1.0t$ , was inferred from spec-

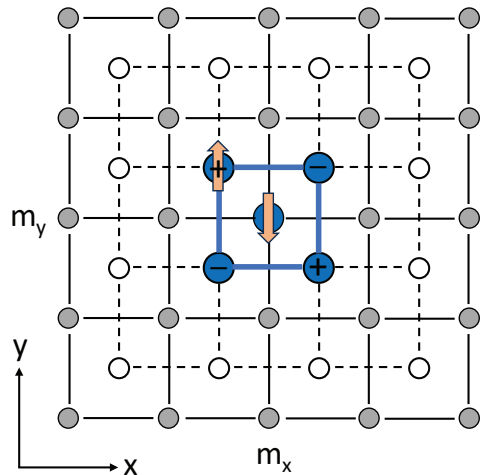


FIG. 2. Origin of  $d$  symmetry in Eq. (4). Shown are two BCT layers in top view. The layer of open circles is shifted out-of-plane (in the  $z$  direction) from the layer of filled circles. The hole marked with a down orange arrow is a source of attractive interaction for its pair partner. The latter is confined to the four sites connected by thick blue lines. If  $t > 0$ , the ground state wave function alternates sign as shown by the pluses and minuses.

troscopic analysis of 1D cuprates [52, 53]. In our model, both in-plane and apical oxygens belong to the same effective BCT site. To preserve out-of-plane nature of  $V$ , we include attraction between two adjacent BCT layers.

We have arrived at the following effective model, see Fig. 1(b):

$$H = t \sum_{\mathbf{m}\mathbf{b}\sigma} c_{\mathbf{m}\sigma}^{\dagger} c_{\mathbf{m}+\mathbf{b},\sigma} + t_{\perp} \sum_{\mathbf{m}\mathbf{b}'\sigma} c_{\mathbf{m}\sigma}^{\dagger} c_{\mathbf{m}+\mathbf{b}',\sigma} + \frac{U}{2} \sum_{\mathbf{m}} \hat{n}_{\mathbf{m}}(\hat{n}_{\mathbf{m}} - 1) - \frac{V}{2} \sum_{\mathbf{m}\mathbf{b}'} \hat{n}_{\mathbf{m}} \hat{n}_{\mathbf{m}+\mathbf{b}'} . \quad (4)$$

Here,  $\mathbf{m}$  numbers BCT lattice sites,  $\sigma$  is spin projection, and  $\hat{n}_{\mathbf{m}} = \sum_{\sigma} c_{\mathbf{m}\sigma}^{\dagger} c_{\mathbf{m}\sigma}$  is the density operator.  $\mathbf{b}$  and  $\mathbf{b}'$  are in-plane and out-of-plane nearest-neighbor vectors, respectively.  $t$  and  $t_{\perp}$  are in-plane and out-of-plane hopping amplitudes. In this paper, we focus on the hole sector,  $t > 0$ . We propose Eq. (4) as an effective model for underdoped LSCO. The model is consistent with a small Fermi surface on the  $x$  side of  $x$  vs.  $1+x$  reconstruction [54], and with the positive Hall sign near half-filling [55]. The model, Eq. (4), possesses several unique properties discussed below.

$d$ -symmetry of the order parameter is a hallmark of cuprate superconductivity [56] and is one reason the latter is called “unconventional”. The experimental situation, however, remains unclear [57]. Sometimes,  $d$ -symmetry is argued to support purely repulsive mechanisms because the node at  $\mathbf{r}_1 = \mathbf{r}_2$  minimizes Hubbard energy. However, the same argument applies to an extended  $s$  wave function that has an even lower energy since it lacks

nodes along the angular coordinate. Such reasoning in its simple form is unable to support Hubbard-based mechanisms. Another way to obtain  $d$ -symmetry within effective models is by introducing a second-neighbor, hole-like (positive) hopping in addition to the first-neighbor, electron-like (negative) hopping [58, 59].  $d$ -wave superconductivity within the more conventional Eliashberg theory with only electron-phonon interaction has also been reported [60–62].

Equation (4) explains the  $d$ -symmetry with only nearest-neighbor in-plane hole hopping. The physics is illustrated in Fig. 2. Consider relative motion of two holes in the strong coupling limit,  $V \gg t, t_\perp$ . One pair member resides in an upper BCT layer and is a source of attraction for the second member. The latter is confined within four sites of the lower BCT layer. The problem is isomorphic to a particle on a four-site ring with  $t > 0$ . The ground state has energy  $-V - 2t$  and a wave function that alternates signs as one goes along the ring. It implies a  $d$ -symmetric pair wave function. This qualitative argument is supported by exact solution of the two-body problem [63], and remains valid in the weak-coupling limit,  $V \rightarrow 0$ . Then, by Bogoliubov's reasoning, a  $d$ -symmetric hole pair implies a  $d$ -symmetric order parameter. The effective BCT model, Eq. (4), explains  $d$ -wave superconductivity quite naturally. Physical origin of the  $d$ -symmetry can be traced back to the positivity of  $t$  and, eventually, to the  $d_{x^2-y^2}$  and  $p_x, p_y$  orbitals of the underlying copper-oxygen plane.

*Zero binding threshold.* One-particle dispersion of Eq. (4) reads:

$$\varepsilon_{\mathbf{q}} = 2t (\cos q_x + \cos q_y) + 8t_\perp \cos \frac{q_x}{2} \cos \frac{q_y}{2} \cos \frac{q_z}{2}, \quad (5)$$

where we have set BCT lattice parameters,  $a = c = 1$ . When  $t > 0$  and  $|t_\perp| < \frac{1}{2}t$ , minimum energy ( $\varepsilon_0 = -4t$ ) occurs at  $q_x, q_y = \pm\pi$  and *all*  $q_z$ . Band minimum is not a single point but an entire line. In the ground state,  $z$ -axis band mass is infinite, and the hole is confined to  $(xy)$  plane. Hole motion is effectively two-dimensional, and density of states is constant near the band bottom. This is the physical origin of the zero binding threshold.

The two-fermion sector of Eq. (4) is exactly solvable by methods developed in Ref. [17]. Full analysis will be published elsewhere but key pointers are given in Ref. [63]. Main findings are summarized here. We assume a positive Hubbard potential,  $U > 0$ , and limit consideration to  $\Gamma$  point of the pair Brillouin zone, i.e., zero total pair momentum. (i) At  $V \gg t, t_\perp$ , there are eight bound pair states. In the spin-singlet sector, they are: extended  $s$ , degenerate doublet ( $d_{xz}, d_{yz}$ ), and a separate  $d_{xy}$ . In the spin-triplet sector, they are: degenerate doublet ( $p_x, p_y$ ) and two separate states:  $p_z$  and  $f$ . Only the extended  $s$  depends on  $U$  while the rest are  $U$  independent. (ii) The eight states combine into three groups with close energies, depending on the number of sign changes un-

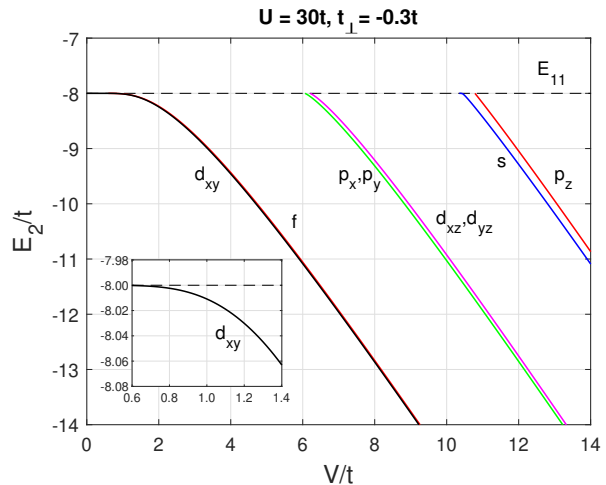


FIG. 3. Pair energies  $E_2$  vs. out-of-plane attraction  $V$  in the BCT model, Eq. (4), for  $U = 30t$  and  $t_\perp = -0.3t$ . The dispersion equations that define  $E_2(V)$  are listed in Ref. [63]. Notice how the eight states form three groups with close energies.  $E_{11} = -8t$  is the lowest energy of two unpaired holes. Pair formation thresholds for these  $U$  and  $t_\perp$  are:  $V_{p_x, p_y} = 6.066t$ ,  $V_{d_{xz}, d_{yz}} = 6.211t$ ,  $V_s = 10.350t$ ,  $V_{p_z} = 10.786t$ .  $d_{xy}$  and  $f$  pair states have zero formation thresholds. Inset: energy of the lowest pair state,  $d_{xy}$ , at small  $V$ .

der  $z$  rotations: the low-energy group ( $d_{xy}, f$ ), the mid-energy group ( $p_x, p_y, d_{xz}, d_{yz}$ ), and the high-energy group ( $s, p_z$ ). (iii) The top two groups have finite thresholds that depend on the ratio  $t_\perp/t$ . As  $V$  decreases, the top six states disappear into the free-particle continuum. Typical pair energies are shown in Fig. 3. (iv) Both low-energy states have  $d_{xy}$  symmetry under  $z$  rotations. Additionally,  $f$  state is odd under  $(xy)$  plane reflections while  $d_{xy}$  is even. Out of the two states,  $d_{xy}$  has a slightly lower energy defined by equation

$$1 = \frac{V}{2} \int_{-\pi}^{\pi} \int_{-\pi}^{\pi} \int_{-\pi}^{\pi} \frac{d^3 \mathbf{q}}{(2\pi)^3} \frac{(1 - \cos q_x)(1 - \cos q_y)(1 + \cos q_z)}{|E_{d_{xy}}| + 2\varepsilon_{\mathbf{q}}}. \quad (6)$$

When  $E_{d_{xy}} \rightarrow -4t - 0$ , the integral diverges logarithmically near  $q_x, q_y = \pm\pi$ , signaling a zero  $V$  threshold.

This property is very unusual. Usually, three-dimensional systems require finite attraction to form a bound state. The BCT lattice may be predisposed to low binding thresholds and to real-space superconductivity in general. This finding may contain hints for better understanding of superconductivity in LSCO. The model is also self-consistent. Using the Zhang and Catlow value of  $V = 0.12$  eV [48, 49] and assuming, for example,  $t = 600$  K, one obtains from Fig. 3 a binding energy of 210 K, which is the right order of magnitude for the pseudogap in underdoped LSCO [54, 56].

*Pair properties and close-packed  $T_c$ .* Real-space superconductivity is a Bose-Einstein condensation of pre-

formed pairs [9–11, 14, 15]. The anisotropic BEC temperature is

$$k_B T_{\text{BEC}} = \frac{3.3 \hbar^2 n_p^{2/3}}{(m_x^* m_y^* m_z^*)^{1/3}}. \quad (7)$$

Continuous-space approximation is unnecessary [64] but it nicely illustrates the qualitative point to be discussed here. According to Eq. (7),  $T_{\text{BEC}}$  increases with pair density until pairs begin to overlap.  $T_{\text{BEC}}$  reaches maximum at *close-packing*, i.e. when pair density  $n_p$  equals inverse pair volume  $\Omega_p$  [17, 64–67]:

$$k_B T_{\text{BEC}}^* = \frac{3.3 \hbar^2}{(m_x^* m_y^* m_z^*)^{1/3} \Omega_p^{2/3}}. \quad (8)$$

To maximize  $T_{\text{BEC}}^*$ , light and compact pairs are needed. In some models, including the *attractive* Hubbard model, there is a contradiction: compact pairs (small  $\Omega_p$ ) require large  $V$ 's whereas low  $m^*$  require small  $V$ 's. Remarkably, it is not the case in the BCT lattice. Let us look at the constituents of Eq. (8) as a function of  $V$ . The pair volume diverges at weak coupling but monotonically decreases with  $V$  and approaches unit cell volume as  $V \rightarrow \infty$ . The in-plane mass  $m_{x,y}^*$  is weakly  $V$ -dependent because of the *light pairs* mechanism: the pair can move in the first order in  $t$  while never breaking the attractive bond [17, 67–72]. Even in the strong-attraction limit, the mass is limited to  $m_{x,y}^* < 4m_0$  [17]. The out-of-plane mass,  $m_z^*$ , shows the most interesting behavior. At weak coupling, the pair wave function is composed of partial waves close to the band minimum  $q_x, q_y = \pm\pi$ . According to Eq. (5), for these  $q_{x,y}$  the dispersion is flat in the  $z$ -direction. It implies that  $m_z^*$  is infinite at  $V \rightarrow 0$ . As  $V$  increases, the pair wave function becomes more compact in real space and spread out in momentum space. Since partial waves away from the band minimum are  $z$ -dispersive, the pair becomes increasingly mobile in the out-of-plane direction. This is similar to how a bound pair can become mobile in a flat-band system [73]. Two factors out of four in the denominator of Eq. (8) ( $\Omega_p$  and  $m_z^*$ ) decrease with  $V$  while the other two ( $m_{x,y}^*$ ) stay approximately constant. As a result,  $T_{\text{BEC}}^*$  monotonically grows with  $V$ . Representative curves are shown in Fig. 4.

Thus, the maximal attainable  $T_c$  in a given system increases with  $V$  because pairs become increasingly compact, hence allowing for larger packing densities, while remaining relatively mobile. The above mechanism of boosting  $T_c$  works until  $V$  becomes large enough to cause phase separation [17, 74]. This suggests that *the highest critical temperatures are observed near charge-ordering instabilities*. This observation helps to understand proliferation of charge density waves, stripes and nematic phases experimentally detected in cuprates [77–81].

*Rules of real-space superconductivity.* Based on the above considerations, three rules of real-space supercon-

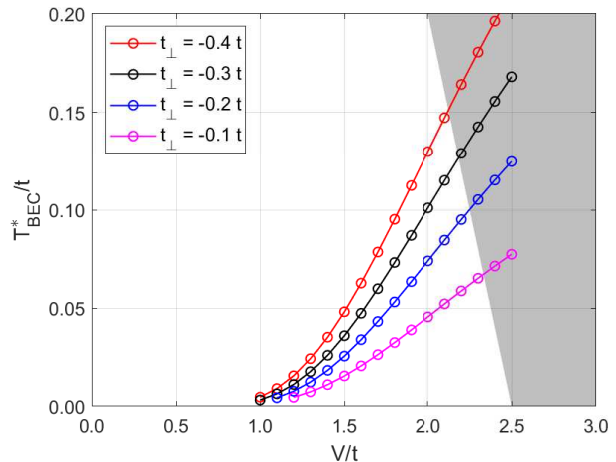


FIG. 4. Close-packed  $T_{\text{BEC}}^*$ , Eq. (8), in the hole-type BCT UV model ( $t > 0$ ) as a function of  $V$  and  $t_{\perp}$ .  $U = 30t$ . The ground state has  $d_{xy}$  orbital symmetry. The shaded area schematically indicates the region of clustering and phase separation. Note that  $T_{\text{BEC}}^*$  systematically increases with  $V$  until phase separation takes place [74]. The highest  $T_{\text{BEC}}^*$  occurs near clustering and other charge instabilities.

ductivity are now formulated. (i) A material must possess at least one nonzero attractive  $V$  that can be orbital specific [75]. (ii)  $V$  must not exceed the phase separation threshold. (iii) The highest critical temperature is achieved for those  $V$ ,  $U$ , and kinetic energy terms that maximize  $T_{\text{BEC}}^*$  given by Eq. (8).  $T_c$  differences between materials of similar crystal structures, for example  $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$  and  $\text{HgBa}_2\text{CuO}_{4+\delta}$ , should be explainable by differences in attractive potential  $V$ . One should expect a correlation of this rule with other  $T_c$  predictors [76]. In general, larger  $V$ 's result in higher  $T_{\text{BEC}}^*$ , which suggests a route to room-temperature superconductivity.

*Summary.* The main goal of this work has been to show that a  $d$ -symmetric order parameter is naturally explainable by real-space superconductivity. All it takes is an out-of-plane attraction and hole-like in-plane hopping, both of which are present in LSCO [48, 49]. Additionally, it is found that the body-centered tetragonal lattice (BCT), the underlying crystal structure of LSCO, is particularly conducive to real-space pairing due to specifics of its hole dispersion. The findings further support the real-space mechanism of superconductivity in cuprates.

\* pavel.kornilovich@gmail.com

- [1] J. Bardeen, L. N. Cooper, and J. R. Schrieffer, Theory of superconductivity, *Physical Review* **108**, 1175 (1957).
- [2] J.R. Schrieffer, *Theory of superconductivity*, 1st edition (Perseus Books, 1999).
- [3] L. N. Cooper, Bound electron pairs in a degenerate Fermi gas, *Physical Review* **104**, 1189-1190 (1956).

- [4] N.N. Bogoliubov, V.V. Tolmachev, and D. V. Shirkov, *A new method in the theory of superconductivity* (1958), (translation: Consultants Bureau, Inc., New York, 1959); Fortschritte der Physik (Progress of Physics) **6**, issue 11-12, pp. 605-682 (1958).
- [5] V.V. Tolmachev, Logarithmic criterion for superconductivity, Dokl. Akad. Nauk SSSR **140:3**, 563-566 (1961).
- [6] P. Morel and P.W. Anderson, Calculation of the superconducting state parameters with retarded electron-phonon interaction, Physical Review **125**, 1263-1271 (1962).
- [7] R.A. Ogg Jr., Bose-Einstein condensation of trapped electron pairs. Phase separation and superconductivity of metal-ammonia solutions, Physical Review **69**, 243-244 (1946); Physical Review **69**, 544 (1946).
- [8] M.R. Schafroth, Superconductivity of a charged Bose gas, Physical Review **96**, 1149 (1954).
- [9] M.R. Schafroth, Theory of superconductivity, Physical Review **96**, 1442 (1954).
- [10] M.R. Schafroth, S.T. Butler, and J.M. Blatt, Quasichemical equilibrium approach to superconductivity, Helvetica Physica Acta **30**, 93-134 (1957).
- [11] J.M. Blatt, *Theory of superconductivity* (Academic Press, 1964).
- [12] D.M. Eagles, Possible pairing without superconductivity at low carrier concentrations in bulk and thin-film superconducting semiconductors, Physical Review **186**, 456-463 (1969).
- [13] N.N. Bogoliubov, Quasi-averages in problems of statistical mechanics. In *Lectures on Quantum Statistics*, vol. 2, Quasi-averages, pp. 34-41 (Gordon and Breach, Science Publishers, Inc., 1970).
- [14] A. Alexandrov and J. Ranninger, Bipolaronic superconductivity, Physical Review B **24**, 1164 (1981).
- [15] R. Micnas, J. Ranninger, and S. Robaszkiewicz, Superconductivity in narrow-band systems with local nonretarded attractive interactions, Reviews of Modern Physics **62**, 113-171 (1990).
- [16] A.S. Alexandrov and N.F. Mott, *High Temperature Superconductors and other Superfluids* (Taylor & Francis, London, 1994).
- [17] P.E. Kornilovitch, Two-particle bound states on a lattice, Annals of Physics **460**, 169574 (2024).
- [18] N. Harrison and M.K. Chan, Thermodynamic evidence for electron correlation-driven flattening of the quasiparticle bands in the high- $T_c$  cuprates, arXiv:2303.12956.
- [19] J.G. Bednorz and K.A. Müller, Perovskite-type oxides — The new approach to high- $T_c$  superconductivity, Reviews of Modern Physics **60**, 585 (1988).
- [20] D. Mihailovic and V.V. Kabanov, Finite wave vector Jahn-Teller pairing and superconductivity in the cuprates, Physical Review B **63**, 054505 (2001).
- [21] V.V. Kabanov and D. Mihailovic, Manifestations of mesoscopic Jahn-Teller real-space pairing and clustering in  $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ , Physical Review B **65**, 212508 (2002).
- [22] D.J. Scalapino, A common thread: The pairing interaction for unconventional superconductors, Reviews of Modern Physics **84**, 1383-1417 (2012).
- [23] P.E. Kornilovitch, Exact estimates of inter-polaron coupling constants resulting in bipolaron formation. In *Polarons and Bipolarons in High- $T_c$  Superconductors and Related Materials*, edited by E.K.H. Salje, A.S. Alexandrov, and W.Y. Liang (Cambridge University Press, 1995), pp. 367-374.
- [24] Y.J. Uemura, G.M. Luke, B.J. Sternlieb, J.H. Brewer, J.F. Carolan, W.N. Hardy, R. Kadono, J.R. Kempton, R.F. Kiefl, S.R. Kreitzman, P. Mulhern, T.M. Riseman, D.L.L. Williams, B.X. Yang, S. Uchida, H. Takagi, J. Gopalakrishnan, A.W. Sleight, M.A. Subramanian, C.L. Chien, M.Z. Cieplak, Gang Xiao, V.Y. Lee, B.W. Statt, C.E. Stronach, W.J. Kossler, and X.H. Yu, Universal Correlations between  $T_c$  and  $n_s/m^*$  (Carrier Density over Effective Mass) in High- $T_c$  Cuprate Superconductors, Physical Review Letters **62**, 2317-2320 (1989).
- [25] Y.J. Uemura, L.P. Le, G.M. Luke, B.J. Sternlieb, W. D. Wu, J.H. Brewer, T.M. Riseman, C.L. Seaman, M.B. Maple, M. Ishikawa, D.G. Hinks, J.D. Jorgensen, G. Saito, and H. Yamochi, Basic similarities among cuprate, bismuthate, organic, Chevrel-phase, and heavy-fermion superconductors shown by penetration-depth measurements, Physical Review Letters **66**, 2665-2668 (1991).
- [26] A.S. Alexandrov and N.F. Mott, Do pairs exist above  $T_c$ ?, Supercond. Sci. Technol. **6**, 215-224 (1993).
- [27] V.B. Geshkenbein, L.B. Ioffe, and A.I. Larkin, Superconductivity in a system with preformed pairs, Physical Review B **55**, 3173-3180 (1997).
- [28] A.S. Alexandrov and V.V. Kabanov, Parameter-free expression for superconducting  $T_c$  in cuprates, Physical Review B **59**, 13628-13631 (1999).
- [29] Q. Chen, J. Stajic, S. Tan, and K. Levin, BCS-BEC crossover: From high temperature superconductors to ultracold superfluids, Physics Reports **412**, 1 (2005).
- [30] Qijin Chen, Zhiqiang Wang, Rufus Boyack, and K. Levin, Test for BCS-BEC crossover in the cuprate superconductors, npj Quantum Mater. **9**, 27 (2024).
- [31] A.-E. Tüçüoğlu, M.E. Kamminga, T.B. Tejsner, H. Jacobsen, H.W. Hansen, M.-E. Lăcătușu, J. Baas, K.L. Eliassen, J.-C. Grivel, Y. Sassa, N.B. Christensen, P. Steffens, M. Boehm, A. Piovano, K. Lefmann, and Astrid T. Rømer, Gradual emergence of superconductivity in underdoped  $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ , Physical Review B **107**, 174514 (2023).
- [32] I. Mangel and A. Keren, The ground-state inter-plane superconducting coherence length of  $\text{La}_{1.875}\text{Sr}_{0.125}\text{CuO}_4$  measured by a “xiometer”, arXiv:2308.06757.
- [33] Panpan Zhou, Liyang Chen, Yue Liu, Ilya Sochnikov, Anthony T. Bollinger, Myung-Geun Han, Yimei Zhu, Xi He, Ivan Božović, and Douglas Natelson, Electron pairing in the pseudogap state revealed by shot noise in copper oxide junctions. Nature **572**, 493-496 (2019).
- [34] Y.I. Seo, W.J. Choi, Shin-ichi Kimura, and Yong Seung Kwon, Evidence for a preformed Cooper pair model in the pseudogap spectra of a  $\text{Ca}_{10}(\text{Pt}_4\text{As}_8)(\text{Fe}_2\text{As}_2)_5$  single crystal with a nodal superconducting gap, Scientific Reports **9**, 3987 (2019).
- [35] B.L. Kang, M.Z. Shi, S.J. Li, H.H. Wang, Q. Zhang, D. Zhao, J. Li, D.W. Song, L.X. Zheng, L.P. Nie, T. Wu, and X.H. Chen, Preformed Cooper pairs in layered FeSe-based superconductors, Physical Review Letters **125**, 097003 (2020).
- [36] V.J. Emery, Theory of high- $T_c$  superconductivity in oxides, Physical Review Letters **58**, 2794 (1987).
- [37] E. Pavarini, I. Dasgupta, T. Saha-Dasgupta, O. Jepsen, and O.K. Andersen, Band-structure trend in hole-doped cuprates and correlation with  $T_{c\text{max}}$ , Physical Review Letters **87**, 047003 (2001).
- [38] N. Barišić and D.K. Sunko, High- $T_c$  cuprates: a story of two electronic subsystems, J. Supercond. Nov. Magn. **35**, 1781-1799 (2022).



- [39] F.C. Zhang and T.M. Rice, Effective Hamiltonian for the superconducting Cu oxides, *Physical Review B* **37**, 3759 (1988).
- [40] H. Sakakibara, H. Usui, K. Kuroki, R. Arita, and H. Aoki, Two-orbital model explains the higher transition temperature of the single-layer Hg-cuprate superconductor compared to that of the La-cuprate superconductor, *Physical Review Letters* **105**, 057003 (2010).
- [41] M. Hirayama, Y. Yamaji, T. Misawa, and M. Imada, *Ab initio* effective Hamiltonians for cuprate superconductors, *Physical Review B* **98**, 134501 (2018).
- [42] Sh. Jiang, D.J. Scalapino, and S.R. White, Density matrix renormalization group based downfolding of the three-band Hubbard model: Importance of density-assisted hopping, *Physical Review B* **108**, L161111 (2023).
- [43] A.S. Alexandrov and N.F. Mott, *Polarons and Bipolarons* (World Scientific Publishing, 1995).
- [44] P.E. Kornilovitch, Giant enhancement of anisotropy by electron-phonon interaction, *Physical Review B* **59**, 13531–13534 (1999).
- [45] Benjamin K. Chang, Iurii Timrov, Jinsoo Park, Jinjian Zhou, Nicola Marzari, and Marco Bernardi, First-principles electron-phonon interactions and polarons in the parent cuprate  $\text{La}_2\text{CuO}_4$ , arXiv:2401.11322.
- [46] M.R. Ramadhan, B. Adiperdana, I. Ramli, D.P. Sari, A.E. Putri, U. Widyaiswari, H. binti Rozak, W.N. Zaharim, A. Manaf, B. Kurniawan, M.I. Mohamed-Ibrahim, Sh. Sulaiman, T. Kawamata, T. Adachi, Y. Koike, and I. Watanabe, Estimation of the on-site Coulomb potential and covalent state in  $\text{La}_2\text{CuO}_4$  by muon spin rotation and density functional theory calculations, *Physical Review Research* **4**, 033044 (2022).
- [47] A. Chainani, M. Horio, C.-M. Cheng, D. Malterre, K. Sheshadri, M. Kobayashi, K. Horiba, H. Kumigashira, T. Mizokawa, M. Oura, M. Taguchi, Y. Mori, A. Takahashi, T. Konno, T. Ohgi, H. Sato, T. Adachi, Y. Koike, T. Mochiku, K. Hirata, S. Shin, M.K. Wu, and A. Fujimori, Oxygen on-site Coulomb energy in  $\text{Pr}_{1.3-x}\text{La}_{0.7}\text{Ce}_x\text{CuO}_4$  and  $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$  and its relation with Heisenberg exchange, *Physical Review B* **107**, 195152 (2023).
- [48] X. Zhang and C.R.A. Catlow, Elastic and Coulombic contributions to real-space hole pairing in doped  $\text{La}_2\text{CuO}_4$ , *J. Mater. Chem.* **1**, 233 (1991).
- [49] C.R.A. Catlow, M.S. Islam, and X. Zhang, The structure and energies of peroxy bipolarons in  $\text{La}_2\text{CuO}_4$ , *J. Phys.: Condens. Matter* **10**, L49 (1998).
- [50] W. Hu, S. Kaiser, D. Nicoletti, C.R. Hunt, I. Gierz, M.C. Hoffmann, M. Le Tacon, T. Loew, B. Keimer, and A. Cavalleri, Optically enhanced coherent transport in  $\text{YBa}_2\text{Cu}_3\text{O}_{6.5}$  by ultrafast redistribution of interlayer coupling, *Nature Materials* **13**, 705–711 (2014).
- [51] K. Ishioka, A. Pashkin, Ch. Bernhard, H. Petek, Xin Yao, and J. Demsar, Selective coupling of coherent optical phonons in  $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$  with electronic transitions, *Physical Review B* **107**, 184302 (2023).
- [52] Zhuoyu Chen, Yao Wang, Slavko N. Rebec, Tao Jial, Makoto Hashimoto, Donghui Lu, Brian Moritz, Robert G. Moore, Thomas P. Devereaux, and Zhi-Xun Shen, Anomalously strong near-neighbor attraction in doped 1D cuprate chains, *Science* **373**, 1235–1239 (2021).
- [53] Yao Wang, Zhuoyu Chen, Tao Shi, Brian Moritz, Zhi-Xun Shen, and Thomas P. Devereaux, Phonon-mediated long-range attractive interaction in one-dimensional cuprates, *Physical Review Letters* **127**, 197003 (2021).
- [54] Cyril Proust and Louis Taillefer, The remarkable underlying ground states of cuprate superconductors, *Annual Review of Condensed Matter Physics*, **10**, 409–429 (2019).
- [55] I. Khait, S. Bhattacharyya, A. Samanta, and A. Auerbach, Hall anomalies of the doped Mott insulator, *npj Quantum Materials* **8**, 75 (2023).
- [56] C.C. Tsuei and J.R. Kirtley, Pairing symmetry in cuprate superconductors, *Reviews of Modern Physics* **72**, 969 (2000).
- [57] Yuying Zhu, Heng Wang, Zechao Wang, Shuxu Hu, Genda Gu, Jing Zhu, Ding Zhang, and Qi-Kun Xue, Persistent Josephson tunneling between  $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+x}$  flakes twisted by  $45^\circ$  across the superconducting dome, *Physical Review B* **108**, 174508 (2023).
- [58] M. Bak and R. Micnas, Extended bound states of fermions on 2D square lattice beyond the nn hopping and interactions. Proceedings of XXII International School of Theoretical Physics: “Quantum Coherence in Superconductors and Nanostructures”, Ustron 1998, *Molecular Physics Reports* **24**, 168–176 (1999); arXiv:cond-mat/9909089.
- [59] D.K. Singh, S. Kadge, Y. Bang, and P. Majumdar, Fermi arcs and pseudogap phase in a minimal microscopic model of  $d$ -wave superconductivity, *Physical Review B* **105**, 054501 (2022).
- [60] J.P. Hague,  $d$ -wave superconductivity from electron-phonon interactions, *Physical Review B* **73**, 060503(R) (2006).
- [61] T.M. Hardy, J.P. Hague, J.H. Samson, and A.S. Alexandrov, Superconductivity in a Hubbard-Fröhlich model and in cuprates, *Physical Review B* **79**, 212501 (2009).
- [62] F. Schrodi, P.M. Oppeneer, and A. Aperis, Unconventional superconductivity mediated solely by isotropic electron-phonon interaction, *Physical Review B* **104**, L140506 (2021).
- [63] Supplemental Material to this paper.
- [64] P.E. Kornilovitch and J.P. Hague, Optimal interlayer hopping and high temperature Bose-Einstein condensation of local pairs in quasi 2D superconductors, *J. Phys.: Condens. Matter* **27**, 075602 (2015).
- [65] V.A. Ivanov, P.E. Kornilovitch, and V.V. Bobryshev, Possible enhancement of the phonon pairing mechanism by a staggered magnetic field, *Physica C* **235-240**, 2369–2370 (1994).
- [66] C. Zhang, N.V. Prokof'ev, and B.V. Svistunov, Bond bipolarons: Sign-free Monte Carlo approach, *Physical Review B* **105**, L020501 (2022).
- [67] G.D. Adebajo, J.P. Hague, and P.E. Kornilovitch, Ubiquitous light real-space pairing from long-range hopping and interactions, *Physics Letters A* **507**, 129474 (2024).
- [68] A.S. Alexandrov and P.E. Kornilovitch, The Fröhlich-Coulomb model of high-temperature superconductivity and charge segregation in the cuprates, *J. Phys.: Condens. Matter* **14**, 5337–5348 (2002).
- [69] J.P. Hague, P.E. Kornilovitch, J.H. Samson, and A.S. Alexandrov, Superlight small bipolarons, *J. Phys.: Condens. Matter* **19**, 255214 (2007).
- [70] J.P. Hague, P.E. Kornilovitch, J.H. Samson, and A.S. Alexandrov, Long-range electron-phonon interactions lead to superlight small bipolarons, *J. Phys.: Conference Series* **92**, 012118 (2007).
- [71] J.P. Hague, P.E. Kornilovitch, J.H. Samson, and A.S. Alexandrov, Singlet and triplet bipolarons on the triangular lattice, *Journal of Physics and Chemistry of Solids* **69**, 3304–3306 (2008).

- [72] G.D. Adebajo, P.E. Kornilovitch, and J.P. Hague, Superlight pairs in face-centred-cubic extended Hubbard models with strong Coulomb repulsion, *J. Phys.: Condens. Matter* **34**, 135601 (2022).
- [73] P. Törmä, L. Liang, and S. Peotta, Quantum metric and effective mass of a two-body bound state in a flat band, *Physical Review B* **98**, 220511(R) (2018).
- [74] Pavel Kornilovitch, A stable pair liquid phase in fermionic systems, *Physical Review B* **107**, 115135 (2023).
- [75] P.P. Edwards, N.C. Pyper, X. Jie, D.R. Slocombe, C.R.A. Catlow, M.S. Islam, and P.J. Dobson, Orbital selective hole- and hole-pair formation and Bose condensation in high-temperature superconductors, *J. Solid State Chem.* **317**, 123529 (2023).
- [76] Jakša Vučičević and Michel Ferrero, Simple predictors of  $T_c$  in superconducting cuprates and the role of interactions between effective Wannier orbitals in the  $d-p$  three-band model, *Physical Review B* **109**, L081115 (2024).
- [77] J.M. Tranquada, B.J. Sternlieb, J.D. Axe, Y. Nkamura, and S. Uchida, Evidence for stripe correlations of spins and holes in copper oxide superconductors, *Nature* **375**, 561-563 (1995).
- [78] J. Chang, E. Blackburn, A.T. Holmes, N.B. Christensen, J. Larsen, J. Mesot, R. Liang, D.A. Bonn, W.N. Hardy, A. Watenphul, M. v. Zimmermann, E.M. Forgan, and S.M. Hayden, Direct observation of competition between superconductivity and charge density wave order in  $\text{YBa}_2\text{Cu}_3\text{O}_{6.67}$ , *Nature Physics* **8**, 871-876 (2012).
- [79] G. Ghiringhelli, M. Le Tacon, M. Minola, S. Blanco-Canosa, C. Mazzoli, N.B. Brookes, G.M. De Luca, A. Frano, D.G. Hawthorn, F. He, T. Loew, M. Moretti Sala, D.C. Peets, M. Salluzzo, E. Schierle, R. Sutarto, G.A. Sawatzky, E. Weschke, B. Keimer, and L. Braicovich, Long-range incommensurate charge fluctuations in  $(\text{Y,Nd})\text{Ba}_2\text{Cu}_3\text{O}_{6+x}$ , *Science* **337**, 821-825 (2012).
- [80] R. Comin, R. Sutarto, F. He, E.H. da Silva Neto, L. Chauviere, A. Fraño, R. Liang, W.N. Hardy, D.A. Bonn, Y. Yoshida, H. Eisaki, A.J. Achkar, D.G. Hawthorn, B. Keimer, G.A. Sawatzky, and A. Damascelli, Symmetry of charge order in cuprates, *Nature Materials* **14**, 796-800 (2015).
- [81] H. Miao, G. Fabbris, R.J. Koch, D.G. Mazzone, C.S. Nelson, R. Acevedo-Esteves, G.D. Gu, Y. Li, T. Yilimaz, K. Kaznatcheev, E. Vescovo, M. Oda, T. Kurosawa, N. Momono, T. Assefa, I.K. Robinson, E.S. Bozin, J.M. Tranquada, P.D. Johnson, and M.P.M. Dean, Charge density waves in cuprate superconductors beyond the critical doping, *npj Quantum Mater.* **6**, 31 (2021).

---

**SUPPLEMENTAL MATERIAL FOR:  
REAL-SPACE  $d$ -WAVE SUPERCONDUCTIVITY FROM WEAK ATTRACTION**

Here we provide sufficient information to derive the basic properties of Eq. (4) and Fig. 3 of the main text. A complete analysis of the body-centered-tetragonal (BCT)  $UV$  model, Eq. (4), including its electron sector, will be published elsewhere. Here, we limit consideration to  $\Gamma$ -point of the pair Brillouin zone, i.e., zero total pair momentum,  $\mathbf{P} = 0$ . The solution follows the methodology developed in Ref. [1].

**Spin singlets**

In accordance with the general methodology [1], we introduce four out-of-plane nearest neighbor vectors:

$$\mathbf{b}'_1 = \frac{1}{2}(\mathbf{x} + \mathbf{y} + \mathbf{z}); \quad \mathbf{b}'_2 = \frac{1}{2}(\mathbf{x} - \mathbf{y} + \mathbf{z}); \quad \mathbf{b}'_3 = \frac{1}{2}(-\mathbf{x} + \mathbf{y} + \mathbf{z}); \quad \mathbf{b}'_4 = \frac{1}{2}(-\mathbf{x} - \mathbf{y} + \mathbf{z}). \quad (9)$$

The singlet pair energy  $E_2$  is defined from the consistency condition of the following system of 5 linear equations:

$$\Phi_0^+ = -UM_{00}^+ \Phi_0^+ + VM_{0\mathbf{b}'_1}^+ \Phi_{\mathbf{b}'_1}^+ + VM_{0\mathbf{b}'_2}^+ \Phi_{\mathbf{b}'_2}^+ + VM_{0\mathbf{b}'_3}^+ \Phi_{\mathbf{b}'_3}^+ + VM_{0\mathbf{b}'_4}^+ \Phi_{\mathbf{b}'_4}^+ \quad (10)$$

$$\Phi_{\mathbf{b}'_1}^+ = -UM_{\mathbf{b}'_1 0}^+ \Phi_0^+ + VM_{\mathbf{b}'_1 \mathbf{b}'_1}^+ \Phi_{\mathbf{b}'_1}^+ + VM_{\mathbf{b}'_1 \mathbf{b}'_2}^+ \Phi_{\mathbf{b}'_2}^+ + VM_{\mathbf{b}'_1 \mathbf{b}'_3}^+ \Phi_{\mathbf{b}'_3}^+ + VM_{\mathbf{b}'_1 \mathbf{b}'_4}^+ \Phi_{\mathbf{b}'_4}^+ \quad (11)$$

$$\Phi_{\mathbf{b}'_2}^+ = -UM_{\mathbf{b}'_2 0}^+ \Phi_0^+ + VM_{\mathbf{b}'_2 \mathbf{b}'_1}^+ \Phi_{\mathbf{b}'_1}^+ + VM_{\mathbf{b}'_2 \mathbf{b}'_2}^+ \Phi_{\mathbf{b}'_2}^+ + VM_{\mathbf{b}'_2 \mathbf{b}'_3}^+ \Phi_{\mathbf{b}'_3}^+ + VM_{\mathbf{b}'_2 \mathbf{b}'_4}^+ \Phi_{\mathbf{b}'_4}^+ \quad (12)$$

$$\Phi_{\mathbf{b}'_3}^+ = -UM_{\mathbf{b}'_3 0}^+ \Phi_0^+ + VM_{\mathbf{b}'_3 \mathbf{b}'_1}^+ \Phi_{\mathbf{b}'_1}^+ + VM_{\mathbf{b}'_3 \mathbf{b}'_2}^+ \Phi_{\mathbf{b}'_2}^+ + VM_{\mathbf{b}'_3 \mathbf{b}'_3}^+ \Phi_{\mathbf{b}'_3}^+ + VM_{\mathbf{b}'_3 \mathbf{b}'_4}^+ \Phi_{\mathbf{b}'_4}^+ \quad (13)$$

$$\Phi_{\mathbf{b}'_4}^+ = -UM_{\mathbf{b}'_4 0}^+ \Phi_0^+ + VM_{\mathbf{b}'_4 \mathbf{b}'_1}^+ \Phi_{\mathbf{b}'_1}^+ + VM_{\mathbf{b}'_4 \mathbf{b}'_2}^+ \Phi_{\mathbf{b}'_2}^+ + VM_{\mathbf{b}'_4 \mathbf{b}'_3}^+ \Phi_{\mathbf{b}'_3}^+ + VM_{\mathbf{b}'_4 \mathbf{b}'_4}^+ \Phi_{\mathbf{b}'_4}^+. \quad (14)$$

Here:

$$M_{\mathbf{00}}^+ = M_{000}, \quad (15)$$

$$M_{\mathbf{0b}'_1}^+ = M_{\mathbf{0b}'_2}^+ = M_{\mathbf{0b}'_3}^+ = M_{\mathbf{0b}'_4}^+ = 2M_{\frac{1}{2}\frac{1}{2}1}, \quad (16)$$

$$M_{\mathbf{b}'_1\mathbf{0}}^+ = M_{\mathbf{b}'_2\mathbf{0}}^+ = M_{\mathbf{b}'_3\mathbf{0}}^+ = M_{\mathbf{b}'_4\mathbf{0}}^+ = M_{\frac{1}{2}\frac{1}{2}1}, \quad (17)$$

$$M_{\mathbf{b}'_1\mathbf{b}'_1}^+ = M_{\mathbf{b}'_2\mathbf{b}'_2}^+ = M_{\mathbf{b}'_3\mathbf{b}'_3}^+ = M_{\mathbf{b}'_4\mathbf{b}'_4}^+ = M_{000} + M_{112}, \quad (18)$$

$$M_{\mathbf{b}'_1\mathbf{b}'_2}^+ = M_{\mathbf{b}'_2\mathbf{b}'_1}^+ = M_{\mathbf{b}'_3\mathbf{b}'_4}^+ = M_{\mathbf{b}'_4\mathbf{b}'_3}^+ = M_{010} + M_{102}, \quad (19)$$

$$M_{\mathbf{b}'_1\mathbf{b}'_3}^+ = M_{\mathbf{b}'_3\mathbf{b}'_1}^+ = M_{\mathbf{b}'_2\mathbf{b}'_4}^+ = M_{\mathbf{b}'_4\mathbf{b}'_2}^+ = M_{100} + M_{012}, \quad (20)$$

$$M_{\mathbf{b}'_1\mathbf{b}'_4}^+ = M_{\mathbf{b}'_4\mathbf{b}'_1}^+ = M_{\mathbf{b}'_2\mathbf{b}'_3}^+ = M_{\mathbf{b}'_3\mathbf{b}'_2}^+ = M_{110} + M_{002}, \quad (21)$$

where

$$M_{nml} \equiv \int_{-\pi}^{\pi} \int_{-\pi}^{\pi} \int_{-\pi}^{\pi} \frac{dq_x dq_y dq_z}{(2\pi)^3} \frac{\cos nq_x \cos mq_y \cos lq_z}{|E_2| + 4t(\cos q_x + \cos q_y) + 16t_{\perp} \cos \frac{q_x}{2} \cos \frac{q_y}{2} \cos q_z}. \quad (22)$$

Additionally,  $M_{100} = M_{010}$  and  $M_{102} = M_{012}$ . Introducing a new basis:

$$\Phi_0 = \Phi_0^+ \quad (23)$$

$$\Phi_s = \frac{1}{2} \left( \Phi_{\mathbf{b}'_1}^+ + \Phi_{\mathbf{b}'_2}^+ + \Phi_{\mathbf{b}'_3}^+ + \Phi_{\mathbf{b}'_4}^+ \right) \quad (24)$$

$$\Phi_{d_{xz}} = \frac{1}{2} \left( \Phi_{\mathbf{b}'_1}^+ + \Phi_{\mathbf{b}'_2}^+ - \Phi_{\mathbf{b}'_3}^+ - \Phi_{\mathbf{b}'_4}^+ \right) \quad (25)$$

$$\Phi_{d_{yz}} = \frac{1}{2} \left( \Phi_{\mathbf{b}'_1}^+ - \Phi_{\mathbf{b}'_2}^+ + \Phi_{\mathbf{b}'_3}^+ - \Phi_{\mathbf{b}'_4}^+ \right) \quad (26)$$

$$\Phi_{d_{xy}} = \frac{1}{2} \left( \Phi_{\mathbf{b}'_1}^+ - \Phi_{\mathbf{b}'_2}^+ - \Phi_{\mathbf{b}'_3}^+ + \Phi_{\mathbf{b}'_4}^+ \right), \quad (27)$$

the system, Eqs. (10)-(14), is diagonalized into the following blocks.

Extended s:

$$\Phi_0 = -UM_{000}\Phi_0 + 4VM_{\frac{1}{2}\frac{1}{2}1}\Phi_s \quad (28)$$

$$\Phi_s = -2UM_{\frac{1}{2}\frac{1}{2}1}\Phi_0 + V(M_{000} + M_{112} + 2M_{100} + 2M_{102} + M_{110} + M_{002})\Phi_s. \quad (29)$$

Twice-degenerate doublet ( $d_{xz}, d_{yz}$ ):

$$\Phi_{d_{xz}} = V(M_{000} + M_{112} - M_{110} - M_{002})\Phi_{d_{xz}} \quad (30)$$

$$\Phi_{d_{yz}} = V(M_{000} + M_{112} - M_{110} - M_{002})\Phi_{d_{yz}}. \quad (31)$$

A separate  $d_{xy}$  state:

$$\Phi_{d_{xy}} = V(M_{000} + M_{112} - 2M_{100} - 2M_{102} + M_{110} + M_{002})\Phi_{d_{xy}}. \quad (32)$$

The above equations define pair energies  $E_2$  vs.  $U, V, t, t_{\perp}$  for their respective symmetries. An example  $E_2(V)$  is plotted in Fig. 3 of the main text.

### Spin triplets

The general spin-triplet pair solution is described by the linear system of four equations:

$$\Phi_{\mathbf{b}'_1}^- = +VM_{\mathbf{b}'_1\mathbf{b}'_1}^- \Phi_{\mathbf{b}'_1}^- + VM_{\mathbf{b}'_1\mathbf{b}'_2}^- \Phi_{\mathbf{b}'_2}^- + VM_{\mathbf{b}'_1\mathbf{b}'_3}^- \Phi_{\mathbf{b}'_3}^- + VM_{\mathbf{b}'_1\mathbf{b}'_4}^- \Phi_{\mathbf{b}'_4}^- \quad (33)$$

$$\Phi_{\mathbf{b}'_2}^- = +VM_{\mathbf{b}'_2\mathbf{b}'_1}^- \Phi_{\mathbf{b}'_1}^- + VM_{\mathbf{b}'_2\mathbf{b}'_2}^- \Phi_{\mathbf{b}'_2}^- + VM_{\mathbf{b}'_2\mathbf{b}'_3}^- \Phi_{\mathbf{b}'_3}^- + VM_{\mathbf{b}'_2\mathbf{b}'_4}^- \Phi_{\mathbf{b}'_4}^- \quad (34)$$

$$\Phi_{\mathbf{b}'_3}^- = +VM_{\mathbf{b}'_3\mathbf{b}'_1}^- \Phi_{\mathbf{b}'_1}^- + VM_{\mathbf{b}'_3\mathbf{b}'_2}^- \Phi_{\mathbf{b}'_2}^- + VM_{\mathbf{b}'_3\mathbf{b}'_3}^- \Phi_{\mathbf{b}'_3}^- + VM_{\mathbf{b}'_3\mathbf{b}'_4}^- \Phi_{\mathbf{b}'_4}^- \quad (35)$$

$$\Phi_{\mathbf{b}'_4}^- = +VM_{\mathbf{b}'_4\mathbf{b}'_1}^- \Phi_{\mathbf{b}'_1}^- + VM_{\mathbf{b}'_4\mathbf{b}'_2}^- \Phi_{\mathbf{b}'_2}^- + VM_{\mathbf{b}'_4\mathbf{b}'_3}^- \Phi_{\mathbf{b}'_3}^- + VM_{\mathbf{b}'_4\mathbf{b}'_4}^- \Phi_{\mathbf{b}'_4}^-. \quad (36)$$



Here

$$M_{\mathbf{b}'_1\mathbf{b}'_1}^- = M_{\mathbf{b}'_2\mathbf{b}'_2}^- = M_{\mathbf{b}'_3\mathbf{b}'_3}^- = M_{\mathbf{b}'_4\mathbf{b}'_4}^- = M_{000} - M_{112}, \quad (37)$$

$$M_{\mathbf{b}'_1\mathbf{b}'_2}^- = M_{\mathbf{b}'_2\mathbf{b}'_1}^- = M_{\mathbf{b}'_3\mathbf{b}'_4}^- = M_{\mathbf{b}'_4\mathbf{b}'_3}^- = M_{010} - M_{102}, \quad (38)$$

$$M_{\mathbf{b}'_1\mathbf{b}'_3}^- = M_{\mathbf{b}'_3\mathbf{b}'_1}^- = M_{\mathbf{b}'_2\mathbf{b}'_4}^- = M_{\mathbf{b}'_4\mathbf{b}'_2}^- = M_{100} - M_{012}, \quad (39)$$

$$M_{\mathbf{b}'_1\mathbf{b}'_4}^+ = M_{\mathbf{b}'_4\mathbf{b}'_1}^+ = M_{\mathbf{b}'_2\mathbf{b}'_3}^+ = M_{\mathbf{b}'_3\mathbf{b}'_2}^+ = M_{110} - M_{002}. \quad (40)$$

Additionally,  $M_{100} = M_{010}$  and  $M_{102} = M_{012}$ . Introducing a new basis:

$$\Phi_{p_x} = \frac{1}{2} \left( \Phi_{\mathbf{b}'_1}^- + \Phi_{\mathbf{b}'_2}^- - \Phi_{\mathbf{b}'_3}^- - \Phi_{\mathbf{b}'_4}^- \right) \quad (41)$$

$$\Phi_{p_y} = \frac{1}{2} \left( \Phi_{\mathbf{b}'_1}^- - \Phi_{\mathbf{b}'_2}^- + \Phi_{\mathbf{b}'_3}^- - \Phi_{\mathbf{b}'_4}^- \right) \quad (42)$$

$$\Phi_{p_z} = \frac{1}{2} \left( \Phi_{\mathbf{b}'_1}^- + \Phi_{\mathbf{b}'_2}^- + \Phi_{\mathbf{b}'_3}^- + \Phi_{\mathbf{b}'_4}^- \right) \quad (43)$$

$$\Phi_f = \frac{1}{2} \left( \Phi_{\mathbf{b}'_1}^- - \Phi_{\mathbf{b}'_2}^- - \Phi_{\mathbf{b}'_3}^- + \Phi_{\mathbf{b}'_4}^- \right), \quad (44)$$

the system, Eqs. (33)-(36), is diagonalized into the following blocks.

Twice-degenerate doublet ( $p_x, p_y$ ):

$$\Phi_{p_x} = V (M_{000} - M_{112} - M_{110} + M_{002}) \Phi_{p_x} \quad (45)$$

$$\Phi_{p_y} = V (M_{000} - M_{112} - M_{110} + M_{002}) \Phi_{p_y}. \quad (46)$$

A separate  $p_z$  state:

$$\Phi_{p_z} = V (M_{000} - M_{112} + 2M_{100} - 2M_{102} + M_{110} - M_{002}) \Phi_{p_z}. \quad (47)$$

A separate  $f$  state:

$$\Phi_f = V (M_{000} - M_{112} - 2M_{100} + 2M_{102} + M_{110} - M_{002}) \Phi_f. \quad (48)$$

The above equations define triplet pair energies  $E_2$  vs.  $U, V, t, t_\perp$  for their respective symmetries. An example  $E_2(V)$  is plotted in Fig. 3 of the main text.

### Pair radius

In this section, an efficient method of calculating pair radius is described. Consideration is limited to spin singlets at  $\mathbf{P} = 0$ . The effective radius is defined as

$$(r_\alpha^*)^2 \equiv \langle m_\alpha^2 \rangle = \frac{\sum_{\mathbf{m}} m_\alpha^2 \Psi^{+*}(\mathbf{m}, \mathbf{0}) \Psi^+(\mathbf{m}, \mathbf{0})}{\sum_{\mathbf{m}} \Psi^{+*}(\mathbf{m}, \mathbf{0}) \Psi^+(\mathbf{m}, \mathbf{0})} \equiv \frac{J_\alpha}{J_0}. \quad (49)$$

Here,  $\Psi^+$  is the real-space wave function [1]

$$\Psi^+(\mathbf{m}, \mathbf{0}) = \frac{1}{2N} \sum_{\mathbf{k}} (e^{i\mathbf{k}\mathbf{m}} + e^{-i\mathbf{k}\mathbf{m}}) \phi_{\mathbf{k}, -\mathbf{k}}^+. \quad (50)$$

The momentum-space wave function is expressible via  $\Phi_{\mathbf{b}}^+$  [1]

$$\phi_{\mathbf{k}_1, \mathbf{k}_2}^+ = \frac{U}{E - \varepsilon_{\mathbf{k}_1} - \varepsilon_{\mathbf{k}_2}} \Phi_0^+(\mathbf{k}_1 + \mathbf{k}_2) + \sum_{\mathbf{b}'} V_{\mathbf{b}'} \frac{e^{-\mathbf{k}_1\mathbf{b}'} + e^{-\mathbf{k}_2\mathbf{b}'}}{E - \varepsilon_{\mathbf{k}_1} - \varepsilon_{\mathbf{k}_2}} \Phi_{\mathbf{b}'}^+(\mathbf{k}_1 + \mathbf{k}_2). \quad (51)$$

In our problem,  $V_{\mathbf{b}'} = -V$  for all four  $\mathbf{b}'$  defined in Eq. (9). Substitution of Eq. (50) into the denominator of Eq. (49) yields

$$J_0 = \frac{1}{N} \sum_{\mathbf{k}} \phi_{\mathbf{k}, -\mathbf{k}}^{+*} \phi_{\mathbf{k}, -\mathbf{k}}^+ = \frac{1}{N} \sum_{\mathbf{k}} |\phi_{\mathbf{k}, -\mathbf{k}}^+|^2. \quad (52)$$

In the numerator of Eq. (49),  $m_\alpha$  can be represented as a derivative of  $e^{\pm i\mathbf{k}\mathbf{m}}$ . After transformations, and utilizing  $\phi_{\mathbf{k}_1\mathbf{k}_2}^+ = \phi_{\mathbf{k}_2\mathbf{k}_1}^+$ , one obtains

$$J_\alpha = \frac{1}{N^2} \sum_{\mathbf{m}} \left( \sum_{\mathbf{k}} \phi_{\mathbf{k},-\mathbf{k}}^+ \frac{\partial}{\partial k_\alpha} e^{i\mathbf{k}\mathbf{m}} \right) \left( \sum_{\mathbf{k}'} \phi_{\mathbf{k}',-\mathbf{k}'}^{+*} \frac{\partial}{\partial k'_\alpha} e^{-i\mathbf{k}'\mathbf{m}} \right). \quad (53)$$

One can apply the Green's theorem for periodic functions to both sums over  $\mathbf{k}$  [2]. Integration by parts leads to

$$J_\alpha = \frac{1}{N} \sum_{\mathbf{k}} \frac{\partial}{\partial k_\alpha} \left( \phi_{\mathbf{k},-\mathbf{k}}^+ \right) \frac{\partial}{\partial k_\alpha} \left( \phi_{\mathbf{k},-\mathbf{k}}^{+*} \right). \quad (54)$$

Utilizing Eq. (51) for  $\mathbf{k}_1 + \mathbf{k}_2 = \mathbf{P} = 0$ , one obtains

$$\frac{\partial}{\partial k_\alpha} \left( \phi_{\mathbf{k},-\mathbf{k}}^+ \right) = \left[ \frac{2U}{(E - 2\varepsilon_{\mathbf{k}})^2} \frac{\partial \varepsilon_{\mathbf{k}}}{\partial k_\alpha} \right] \Phi_{\mathbf{0}}^+(\mathbf{0}) + \sum_{\mathbf{b}'} V_{\mathbf{b}'} \left[ -\frac{2b_\alpha \sin(\mathbf{k}\mathbf{b}')}{E - 2\varepsilon_{\mathbf{k}}} + \frac{4 \cos(\mathbf{k}\mathbf{b}')}{(E - 2\varepsilon_{\mathbf{k}})^2} \frac{\partial \varepsilon_{\mathbf{k}}}{\partial k_\alpha} \right] \Phi_{\mathbf{b}'}^+(\mathbf{0}). \quad (55)$$

The second factor in Eq. (54) is a complex conjugate of Eq. (55). All together, Eqs. (49), (51), (52), (54) and (55) provide a general recipe of calculating pair radius. Once pair energy  $E$  and eigenvector  $\{\Phi_{\mathbf{0}}^+, \Phi_{\mathbf{b}}^+\}$  are known from the main linear system,  $r_\alpha$  only requires calculation of two momentum integrals.

In some situations, the general procedure simplifies significantly. As an example, consider  $d_{xy}$  pair state which energy is defined by Eq. (32). Inverting the basis transformation, Eqs. (24)-(27), one obtains

$$\Phi_{\mathbf{0}}^+ = 0; \quad \Phi_{\mathbf{b}'_1}^+ = -\Phi_{\mathbf{b}'_2}^+ = -\Phi_{\mathbf{b}'_3}^+ = \Phi_{\mathbf{b}'_4}^+ = \frac{1}{2} \Phi_{d_{xy}}. \quad (56)$$

The momentum-space wave function now follows from Eq. (51):

$$\begin{aligned} \phi_{\mathbf{k},-\mathbf{k};d_{xy}}^+ &= -|V| \frac{2}{E - 2\varepsilon_{\mathbf{k}}} [\cos(\mathbf{k}\mathbf{b}'_1) - \cos(\mathbf{k}\mathbf{b}'_2) - \cos(\mathbf{k}\mathbf{b}'_3) + \cos(\mathbf{k}\mathbf{b}'_4)] \frac{1}{2} \Phi_{d_{xy}} \\ &= 4|V| \Phi_{d_{xy}} \frac{\sin \frac{k_x a}{2} \sin \frac{k_y a}{2} \sin \frac{k_z c}{2}}{E - 2\varepsilon_{\mathbf{k}}}. \end{aligned} \quad (57)$$

The constant factor ( $4|V|\Phi_{d_{xy}}$ ) drops out of the ratio of two integrals and can be disregarded. Thus, only pair energy  $E_2$  is needed for radius calculation in this case. Utilizing this expression for  $\phi_{\mathbf{k},-\mathbf{k}}^+$ , the derivatives needed in Eq. (54) can be explicitly derived. Then everything is substituted in Eqs. (52) and (54) for numerical integration.

---


\* pavel.kornilovich@gmail.com

[1] P.E. Kornilovitch, Two-particle bound states on a lattice, *Annals of Physics* **460**, 169574 (2024).

[2] N.W. Ashcroft and N.D. Mermin, *Solid State Physics* (Saunders, Philadelphia, 1976), Appendix I.

---

(a)

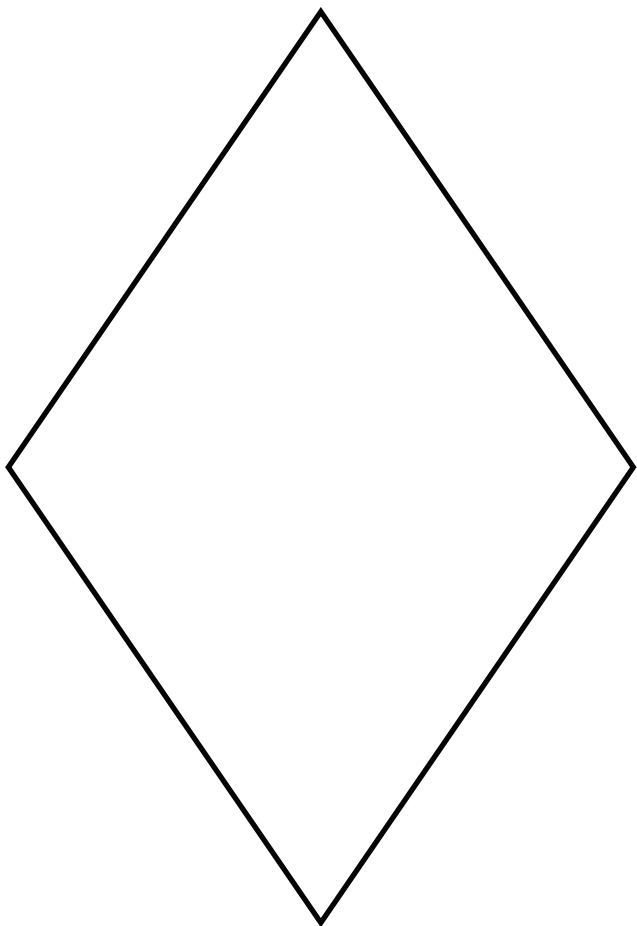

(b)

