

DFT+DMFT study of correlated electronic structure in the monolayer-trilayer phase of $\text{La}_3\text{Ni}_2\text{O}_7$

Zhenfeng Ouyang,^{1,2} Rong-Qiang He,^{1,2,*} and Zhong-Yi Lu^{1,2,3,†}

¹*Department of Physics and Beijing Key Laboratory of Opto-electronic Functional Materials & Micro-nano Devices, Renmin University of China, Beijing 100872, China*

²*Key Laboratory of Quantum State Construction and Manipulation (Ministry of Education), Renmin University of China, Beijing 100872, China*

³*Hefei National Laboratory, Hefei 230088, China*

(Dated: July 12, 2024)

By performing DFT+DMFT calculations, we systematically investigate the correlated electronic structure in the newly discovered monolayer-trilayer (ML-TL) phase of $\text{La}_3\text{Ni}_2\text{O}_7$ (1313-La327). Our calculated Fermi surfaces are in good agreement with the angle-resolved photoemission spectroscopy (ARPES) results. We find that 1313-La327 is a multiorbital correlated metal. An orbital-selective Mott behavior is found in ML. The ML Ni- $3d_{z^2}$ orbitals exhibit a Mott behavior, while the ML Ni- $3d_{x^2-y^2}$ orbitals are metallic due to self-doping. And the ML also shows features of heavy fermions, which indicates that there may be Kondo physics in 1313-La327. We also find a large static local spin susceptibility of ML Ni, suggesting that there is large spin fluctuation in 1313-La327. The TL Ni- e_g orbitals possess similar electronic correlation to those in $\text{La}_4\text{Ni}_3\text{O}_{10}$ (La4310). The e_g orbitals of the outer-layer Ni in TL (TL-outer Ni) show non-Fermi liquid behaviors. Besides, large weight of high-spin states are found in TL-outer Ni and ML Ni, implying Hundness. Under 16 GPa, a Lifshitz transition is revealed by our calculations and a La-related band crosses the Fermi level. Our work provides a theoretical reference for studying other potential mixed-stacked nickelate superconductors.

I. INTRODUCTION

The discovery of superconductivity with transition temperature (T_c) about 80 K in Ruddlesden-Ropper (RP) bilayer perovskite $\text{La}_3\text{Ni}_2\text{O}_7$ (2222-La327) under pressure [1] has attracted extensive attention. Before that, the only nickelate superconductor was doped infinite-layer $\text{R}_{0.8}\text{Sr}_{0.2}\text{NiO}_2$ thin films (R = La, Nd) [2]. Differed from the nominal $3d^9$ electronic configuration in infinite-layer RNiO_2 , RP series of nickelates $\text{La}_{n+1}\text{Ni}_n\text{O}_{3n+1}$ have higher chemical valence. With a chemical valence of Ni^{2+} , La_2NiO_4 ($n = 1$) [3] is isostructural to superconducting $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ and was once regarded as a platform to reproduce high- T_c superconductivity like cuprates. The undoped La_2NiO_4 is an antiferromagnetic (AFM) insulator. With hole doping, the system shows a transition from AFM insulator to metal [4–7]. However, no signatures of superconductivity were observed.

For $n = 2$, with a higher average valence of $\text{Ni}^{2.5+}$, superconductivity transition was observed in 2222-La327 above 15 GPa [1]. The x-ray-diffraction patterns show that the space group of the high-pressurized superconducting 2222-La327 is $I4/mmm$ with 180° Ni-O-Ni bonding angle along c axis [8, 9]. Although a magnetic long-range order has not been experimentally observed, some theoretical research suggested that there are interlayer AFM superexchange interactions between the half-filled $3d_{z^2}$ orbitals [10, 11]. Our previous DFT+DMFT calculation [12] has confirmed that the normal state of 2222-La327 is a Hund metal. The interlayer AFM superexchange interactions can be transmitted to the $3d_{x^2-y^2}$ orbitals by Hund's coupling and then provide glue for superconducting pairing [10, 11, 13]. Both model studies of func-

tional renormalization group method [14] and cluster dynamical mean-field theory [11] predicted an s_{\pm} -wave pairing.

Soon after, superconductivity transition in La4310 ($n = 3$) was experimentally reported [15–18]. The maximal superconducting T_c of La4310 is ~ 20 K under high pressure. A structural transition from monoclinic $P21/a$ to tetragonal $I4/mmm$ space group happens above 12 GPa [16]. Similar to 2222-La327, superconducting phase only emerges in high pressure phase without Ni-O octahedra distortions. Some theoretical studies also predicted a possible s_{\pm} -wave pairing [19–21]. Our previous DFT+DMFT study [22] suggests that inner-layer Ni in La4310 has a higher chemical valence than that of outer-layer Ni, which leads to weak electronic correlation in the inner layer. This may explain the lower superconducting T_c of La4310. According to Wu *et al.* [23], the occupations of the Ni- $3d_{z^2}$ orbitals in La4310 are not half-filled, which weakens the effective interlayer couplings and causes the lower superconducting T_c than that of 2222-La327. It seems that RP bilayer structure becomes the most promising candidate for realizing high- T_c superconductivity in the family of nickelates.

However, a hidden phase of $\text{La}_3\text{Ni}_2\text{O}_7$ was experimentally observed recently [24]. Distinguished from the previously reported 2222-La327, this hidden phase exhibits a distinctive long-range structural order, stacking with monolayer and trilayer of NiO_6 blocks in a “1313” sequence. And this structure has been subsequently reported by some other groups [25–27]. Among them, Pupal *et al.* [25] claimed that they obtained single crystals of 1313-La327 as primary bulk phase and superconductivity was observed under high pressures. Other groups obtained samples including other competing phases such as 2222-La327, La4310, or La_2NiO_4 [26, 27]. These findings bring some controversy to the origin of superconductivity in $\text{La}_3\text{Ni}_2\text{O}_7$ compounds. Hence, it is urgent to study the correlated electronic structure in 1313-La327, which may provide clues about the possible superconductivity.

In this paper, we perform the density functional theory plus

* rqhe@ruc.edu.cn

† zlu@ruc.edu.cn

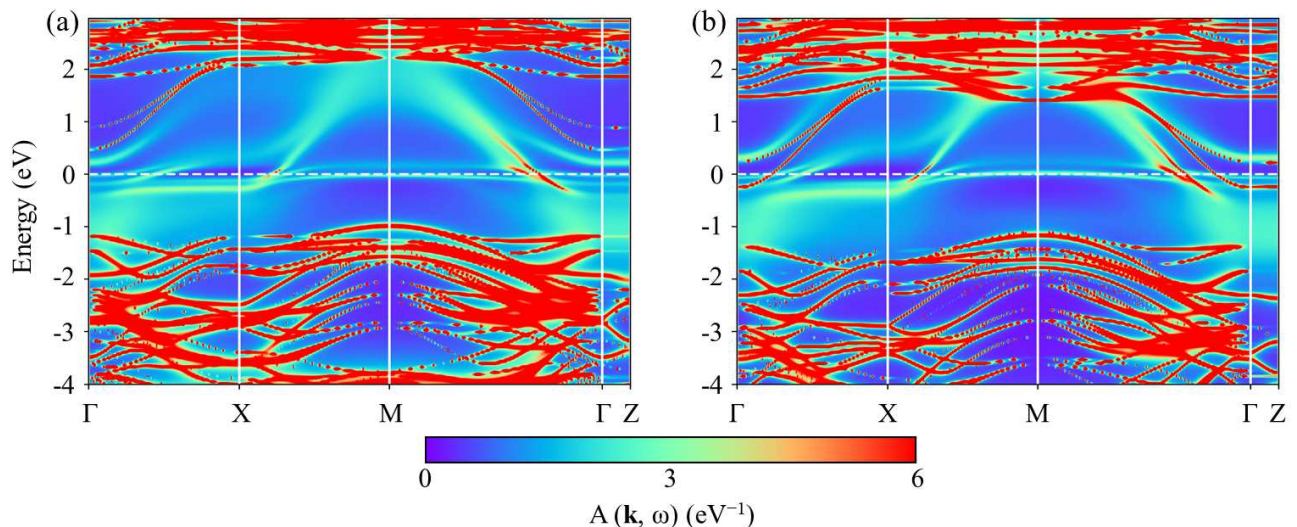


FIG. 1. Momentum-resolved spectral functions $A(\mathbf{k}, \omega)$ obtained by DFT+DMFT calculations for ambient pressure (a) and 16 GPa (b), respectively. The Fermi level is set to zero. Under 16 GPa, a La-related band with large quasi-particle weight crosses the Fermi level around the Γ point. But in the case of ambient pressure, this band lays at ~ 0.5 eV above the Fermi level.

dynamical mean-field theory (DFT+DMFT) calculations to study the correlated electronic structure in 1313-La327. Our calculated Fermi surfaces are in good agreement with the ARPES results. We find that 1313-La327 is a multiorbital correlated metal and a Lifshitz transition is observed under 16 GPa. Furthermore, our results suggest that 1313-La327 is a unique platform, which may include Mott, Kondo, and Hund physics. Specifically, the calculated self-energy functions and orbital-resolved spectral functions show that the ML Ni- $3d_{z^2}$ orbitals exhibit a Mott behavior, while the ML Ni- $3d_{x^2-y^2}$ orbitals are metallic due to the self-doping between ML and TL. Large mass enhancements of the ML Ni- e_g orbitals suggest that there may Kondo physics. Besides, we find large weights of high-spin states in TL-outer Ni and ML Ni, which indicates Hundness. The calculated static local spin susceptibility suggests that there is a complicated magnetic property in 1313-La327.

II. RESULTS AND ANALYSIS

A. Electronic structure

We first focus the momentum-resolved spectral functions $A(\mathbf{k}, \omega)$ of 1313-La327. As shown in Fig. 1(a), we find that the bands around the Fermi level are strongly renormalized. According to previous DFT results [24, 28], the bandwidth of the Ni- e_g orbital is about 4 eV. After considering electronic correlation, the bandwidth reduces to about 2 eV. Especially for those bands near the Fermi level, the bandwidth shrinks to be ~ 0.5 eV. In addition, the quasi-particle spectral weight also reflects the electronic correlation in 1313-La327. At the M point, the spectral weights around the Fermi level obviously reduce, which makes those bands almost invisible compared with the previous DFT result [24]. All these findings are sim-

ilar to those in 2222-La327 [12] and La4310 [22]. This shows that 1313-La327 is a multiorbital correlated metal.

As shown in Fig. 1(b), the features of multiorbital correlated physics are still observed under high pressure of 16 GPa. Although it seems that pressure brings tiny effects on those Ni- e_g related bands, a La-related band crosses the Fermi level. To further determine this finding, we show the Fermi surfaces of 1313-La327 in Fig. 2. Figures 2(b) and (c) show the Fermi surfaces at $k_z = 0$ plane under ambient pressure and 16 GPa pressure, respectively. And the Fermi surfaces determined by ARPES under ambient pressure [27] are exhibited in Fig. 2(a). Our DFT+DMFT calculated Fermi surfaces under ambient pressure are in good agreement with the ARPES results (Details of the calculations are presented in Appendix A). Besides the α , β , and γ pockets which are similar to those in 2222-La327, a newly discovered ϵ pocket in 1313-La327

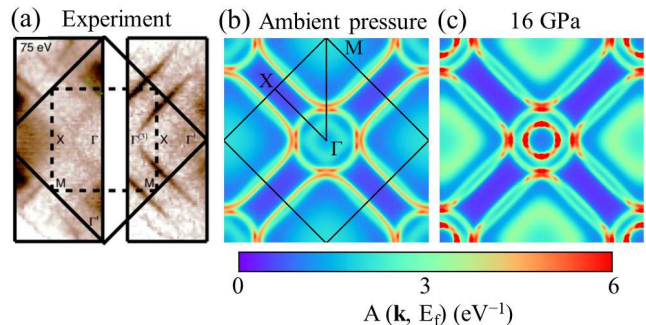


FIG. 2. (a) The Fermi surfaces at $k_z = 0$ determined by the ARPES at ambient pressure from Ref. [27]. The DFT+DMFT calculated Fermi surfaces at $k_z = 0$ plane for ambient pressure (b) and 16 GPa (c), respectively. The first Brillouin zone and the high-symmetry paths are denoted by black solid lines in (b).

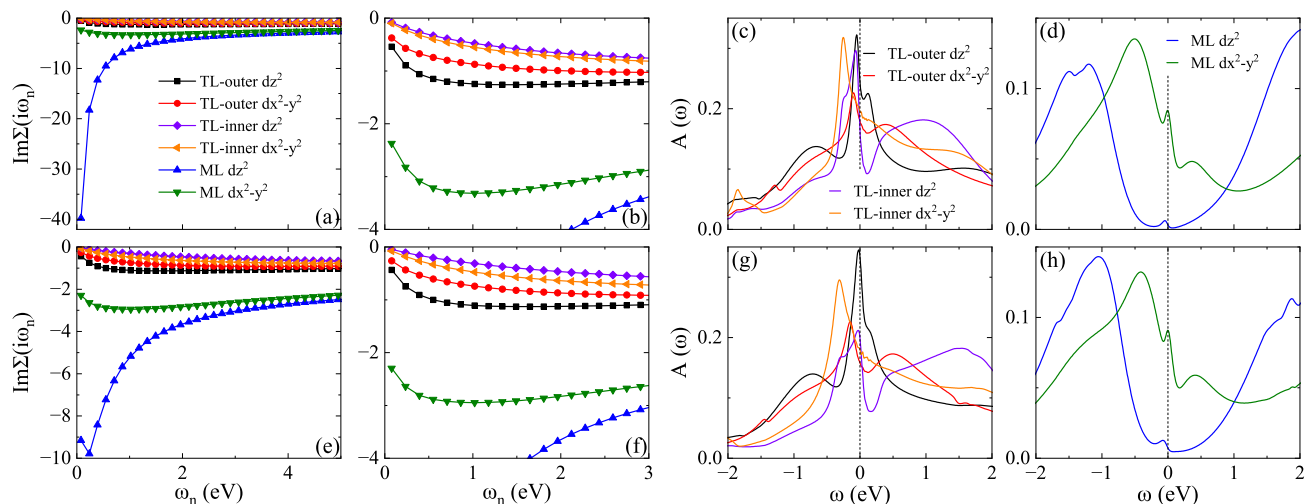


FIG. 3. The imaginary parts of self-energy functions at Matsubara axis $\text{Im}\Sigma(i\omega_n)$ and orbital-resolved spectral functions $A(\omega)$ obtained by DFT+DMFT calculations for ambient pressure (a-d) and 16 GPa (e-h).

has also been well reproduced in our theoretical calculations. This ε pocket shows a diamond-like pattern around the Γ point in Fig. 2(b). However, in Fig. 2(c), it is clearly seen that there is a ring-like Fermi surface with large quasi-particle weight, which is quite close to the ε pocket. This is the La-related band, which crosses the Fermi level around the Γ point. This phenomenon has not been found in our previous studies about 2222-La327 [12] or La4310 [22]. For example, the La-related bands in 2222-La327 have no contribution to the Fermi surfaces. But it is reminiscent of the self-doping in infinite-layer nickelates $\text{La}_{1-x}\text{Sr}_x\text{NiO}_2$, where La-related band crosses the Fermi level [29, 30].

In Fig. 3, we show the orbital-resolved Matsubara self-energy functions $\text{Im}\Sigma(i\omega_n)$ and local spectral functions $A(\omega)$ of 1313-La327 under ambient pressure and 16 GPa, respectively. Under ambient condition, an obvious orbital difference is found in Fig. 3(a). The self-energy function $\text{Im}\Sigma(i\omega_n)$ of the ML Ni- $3d_{z^2}$ orbital exhibits a divergent behavior in low-frequency region, which is totally different from the others. This is a signal of Mott physics. A Mott gap is observed in the local spectral function $A(\omega)$ of the ML Ni- $3d_{z^2}$ orbital in Fig. 3(d). As for the ML Ni- $3d_{x^2-y^2}$ orbital, a large intercept of low-frequency $\text{Im}\Sigma(i\omega_n)$ in Fig. 3(b) indicates its strong electronic correlation. It should be noted that both the ML Ni- $3d_{z^2}$ and $3d_{x^2-y^2}$ orbitals show a small quasi-particle resonance peak at the Fermi level in our room-temperature calculations [Fig. 3(d)]. It is expected that these quasi-particle resonance peaks will become higher when decreasing temperatures. Anyway, the characteristic of the energy gap is clear. Under 16 GPa, similar behaviors are observed. In Fig. 3(e), a large and finite intercept of $\text{Im}\Sigma(i\omega_n)$ of the ML Ni- $3d_{z^2}$ orbital appears. But the local spectral function $A(\omega)$ of the ML Ni- $3d_{z^2}$ orbital still shows a Mott behavior [Fig. 3(h)], which is similar to the ambient case. As for the TL Ni- e_g orbitals, the $\text{Im}\Sigma(i\omega_n)$ of the TL-outer Ni- e_g orbitals at low-frequency region show nonlinear behaviors. And finite intercepts of $\text{Im}\Sigma(i\omega_n)$ can be found around zero frequency. These

suggest that the TL-outer Ni- e_g orbitals show non-Fermi liquid behaviors. But the $\text{Im}\Sigma(i\omega_n)$ of the TL-inner Ni- e_g orbitals show linear behaviors at low frequencies, which is consistent with a Fermi liquid behavior [Figs. 3(b) and (f)]. Similar results have also been found in La4310 [22].

B. Spin susceptibility

According to the above results, a significant difference of physical properties between the TL and ML in 1313-La327 is observed. In Table I, we show the DFT+DMFT calculated static local spin susceptibility χ_{spin} of the three kinds of Ni in 1313-La327, which further shows the difference between TL and ML. The spin susceptibility of ML Ni is much larger than that of TL Ni, which suggests a local moment may exist on ML Ni. Although there lack experimental reports about magnetic order in 1313-La327, this finding is very easy to associate with La_2NiO_4 , which shares the same chemical formula with the ML in 1313-La327. It is known that the undoped La_2NiO_4 is an AFM Mott insulator. When applying hole doping, an insulator-metal transition occurs [4–7]. In 1313-La327, the average chemical valence of Ni cation

TABLE I. The DFT+DMFT calculated static local spin susceptibility χ_{spin} of TL-outer Ni, TL-inner Ni, and ML Ni under ambient pressure (AP) and 16 GPa, respectively. The χ_{spin} of La4310 (44.3 GPa) [22] is also exhibited.

	TL-outer Ni	TL-inner Ni	ML Ni
1313-La327 (AP)	6.99	1.36	27.72
1313-La327 (16 GPa)	5.34	0.87	25.66
La4310 (44.3 GPa)	1.92	0.98	–

TABLE II. The DFT+DMFT calculated mass enhancement m^*/m and the local occupation number N_{e_g} of Ni- e_g orbitals in 1313-La327 under ambient pressure (AP) and 16 GPa and La4310 (44.3 GPa) [22], respectively.

	Orbital	TL-outer		TL-inner		ML	
		$3d_{z^2}$	$3d_{x^2-y^2}$	$3d_{z^2}$	$3d_{x^2-y^2}$	$3d_{z^2}$	$3d_{x^2-y^2}$
m^*/m	1313-La327 (AP)	5.374	4.098	2.255	2.264	1325	9.727
	1313-La327 (16GPa)	4.345	2.966	1.684	1.508	92.95	8.106
	La4310 (44.3 GPa)	2.578	2.296	2.018	1.986	—	—
N_{e_g}	1313-La327 (AP)	1.115	1.049	1.021	1.043	1.082	1.083
	1313-La327 (16GPa)	1.110	1.053	0.962	1.063	1.104	1.083
	La4310 (44.3 GPa)	1.088	1.060	1.060	1.017	—	—

is $\text{Ni}^{2.5+}$. ML and TL have chemical formulas of La_2NiO_4 and $\text{La}_4\text{Ni}_3\text{O}_{10}$, respectively, where the average chemical valence of Ni cations are Ni^{2+} and $\text{Ni}^{2.67+}$, respectively. Hence, in order to make the chemical valence of ML Ni and TL Ni cations get closer to $\text{Ni}^{2.5+}$, it is natural to speculate that there is a self-doping between ML and TL, where electrons transfer from ML to TL and holes are doped in ML. And according to Refs. [24, 25], the in-plane Ni-O distance is shorter than the out-of plane Ni-O distance in 1313-La327, so the self-doping affects the high-lying Ni- $3d_{x^2-y^2}$ orbitals. This is consistent with our result in Figs. 3(d) and (h), where the ML Ni- $3d_{x^2-y^2}$ orbital exhibits a metallic behavior. As for the TL Ni in 1313-La327, the χ_{spin} of TL-outer Ni is larger than that of TL-inner Ni. All these findings suggest that there may be a more complicated magnetic property in 1313-La327, which is vital for superconducting pairing and needs more experimental and theoretical investigations.

C. Electronic correlation

Here, we investigate the electronic correlation in 1313-La327 and make systematic comparisons with those previous nickelate superconductors, for example 2222-La327 [12] and La4310 [22]. In Table II, we show the mass enhancement m^*/m and the local occupation number N_{e_g} of 1313-La327 and La4310. The mass enhancement is defined as

$$m^*/m = Z^{-1} = 1 - \left. \frac{\partial \text{Re}\Sigma(\omega)}{\partial \omega} \right|_{\omega=0}. \quad (1)$$

Z is the renormalization factor, which is a key factor to characterize band renormalization and electronic correlation. As for the TL in 1313-La327 under ambient pressure, the TL-outer Ni- e_g orbitals possess larger mass enhancement than that of the inner Ni- e_g orbitals, which is similar to the case of La4310 [22]. And for the ML Ni- $3d_{z^2}$ orbitals, an extremely large $m^*/m \sim 1300$ indicates a quite small quasi-particle weight Z . It is reminiscent of heavy fermion systems, which have a large mass enhancement. The Kondo hybridization between the localized ML Ni- $3d_{z^2}$ and delocalized ML Ni- $3d_{x^2-y^2}$ orbitals may explain the quasi-particle peaks in

Figs. 3(d) and (h). This finding suggests that there may be Kondo physics in 1313-La327. And Kondo physics has already been discussed in those previous 2222-La327 [31] and infinite-layer $\text{La}_{1-x}\text{Sr}_x\text{NiO}_2$ [30]. It should be noted that the heavy fermion in 1313-La327 is special because the conduction electrons are strongly correlated. In addition, we also find that pressure weakens the electronic correlation in 1313-La327, and the e_g orbitals of TL-outer Ni possess stronger renormalization than that of TL-inner Ni.

As for the local occupation number N_{e_g} of the Ni- e_g orbitals in 1313-La327, due to orbital hybridization, our calculated N_{e_g} is larger than the nominal value estimated from chemical valence. It should be noted that a strong d - p hybridization between the Ni- $3d_{z^2}$ and inner apical O- $2p_z$ orbitals, as well as between the Ni- $3d_{x^2-y^2}$ and in-plane O- $2p_x/p_y$ orbitals in 2222-La327 have been experimentally confirmed recently [32]. The holes transfer from Ni cations to O anions, hence the exact local occupation number of the Ni- $3d$ orbitals is larger than the nominal value of 7.5. This result shows good consistency with our previous theoretical calculations about 2222-La327 [12] and La4310 [22]. And a previous theoretical report also predicted an approximate Ni- $3d^8$ occupation in 1313-La327 [33]. Our finding about the local occupation number of the Ni- e_g orbitals in 1313-La327 once again suggests that strong d - p hybridization may be a common feature in these RP series of nickelates.

D. Hundness from high-spin state

In Table III, we show the weights of the Ni- e_g orbital local multiplets in 1313-La327 and make comparisons with those in 2222-La327 and La4310. According to our previous study, 2222-La327 is a Hund metal and the high-spin $S_z = 1$ state possesses a larger weight [12]. And Hund correlation plays an important role in superconducting pairing in 2222-La327. Specifically, the AFM interactions between the interlayer Ni- $3d_{z^2}$ orbitals are shared to the Ni- $3d_{x^2-y^2}$ orbitals by Hund's correlation. Then these AFM interactions provide glue for the superconducting pairing [10, 11, 13]. Besides, Hund's correlation has also been found in infinite-layer LaNiO_2 [34].

TABLE III. The DFT+DMFT calculated weights (%) of the Ni- e_g orbital local multiplets in 1313-La327 under ambient pressure (AP) and 16 GPa, La4310 (44.3 GPa) [22], and 2222-La327 (29.5 GPa) [12], respectively.

	N_{Γ}	0	1	2	2	3	4
	S_z	0	1/2	0	1	1/2	0
	2222-La327 (29.5 GPa)	0.4	12.4	23.6	33.3	28.1	2.3
TL-outer Ni	1313-La327 (AP)	0.3	11.4	19.9	41.7	25.1	1.6
	1313-La327 (16 GPa)	0.4	12.5	21.7	37.7	25.9	1.9
	La4310 (44.3 GPa)	0.6	14.7	24.8	31.5	26.1	2.1
TL-inner Ni	1313-La327 (AP)	0.9	18.1	26.9	29.3	23.1	1.6
	1313-La327 (16 GPa)	1.3	20.9	28.1	25.5	22.5	1.8
	La4310 (44.3 GPa)	1.0	18.3	27.1	27.6	24.1	1.9
ML Ni	1313-La327 (AP)	0.0	3.3	4.7	72.8	18.7	0.5
	1313-La327 (16 GPa)	0.0	3.8	5.9	68.5	21.1	0.8

Here, we find large weights of high-spin states of the TL-outer Ni and ML Ni in 1313-La327. These findings suggest that Hund's correlation may be a common property in nickelates. In addition, it should be noticed that the high-spin $S_z = 1$ state of ML Ni has a very large weight of $\sim 70\%$. This finding supports the previous analysis of the results about χ_{spin} in Table I and once again emphasizes that there may be a complex magnetic property in 1313-La327.

III. DISCUSSION AND CONCLUSION

Although the superconducting transition in 1313-La327 still needs to be further experimentally confirmed, our theoretical calculations indeed reveal some unique features.

(i) We find a self-doping in 1313-La327 between ML and TL. Note that this should not be confused with the self-doping revealed in 2222-La327 from a recent experiment [32], where the self-doped ligand holes mainly resides on the inner apical O and in-plane O atoms.

(ii) The localized ML Ni- $3d_{z^2}$ orbitals in 1313-La327 show features of heavy fermions. The hybridization between the localized ML Ni- $3d_{z^2}$ and the hole-doped delocalized ML Ni- $3d_{x^2-y^2}$ orbitals suggests that 1313-La327 may be a platform for Kondo physics. And Kondo physics has been discussed in other nickelates [30, 31, 35]. For example in largely doped infinite-layer nickelates, superconducting pairing is predicted to be s -wave for small t_c/K or to be d -wave pairing state for large t_c/K , where t_c and K describe the effective hopping amplitude of conduction electrons and Kondo exchange interaction, respectively [30, 35].

(iii) Some previous works claimed that doping electrons is beneficial for achieving a higher superconducting T_c in La4310 [36, 37]. From this aspect, the self-doping provides a potential support for the possible realization of a higher superconducting T_c in the TL of 1313-La327. This may explain the high- T_c superconducting transition under pressures, which

was reported by Puphal *et al.* [25].

(iv) A Lifshitz transition is found in 1313-La327 under 16 GPa and a La-related band crosses the Fermi level. This is similar to the self-doped infinite-layer $\text{La}_{1-x}\text{Sr}_x\text{NiO}_2$ [29, 30].

(v) A very large $\text{Im}\Sigma(i\omega_n)$ of the ML Ni- $3d_{x^2-y^2}$ orbitals and nonlinear $\text{Im}\Sigma(i\omega_n)$ of the TL-outer Ni- e_g orbitals indicate their strong correlation [Figs. 3(a-b) and (e-f)]. Refs. [22] and [11] show that Hund's correlation can significantly enhance electronic correlation and give rise to a non-Fermi liquid behavior. Here for 1313-La327, the Hund's correlation is manifest through Ni local high-spin state and should account for the strong correlation as well as the non-Fermi liquid behavior. And we suggest that Hund's correlation may be a common property of nickelates.

All these should be further both experimentally and theoretically investigated.

In Summary, we have systematically studied the correlated electronic structure in the newly discovered 1313-La327. Our calculated Fermi surfaces are in good agreement with the ARPES results. We find that 1313-La327 is a multiorbital correlated metal. Due to the self-doping from ML to TL, the ML Ni- $3d_{x^2-y^2}$ orbitals are metallic and show a non-Fermi liquid behavior. But the ML Ni- $3d_{z^2}$ orbitals show a Mott behavior. In addition, the ML Ni- $3d_{z^2}$ orbitals also exhibit features of heavy fermions. Our calculations about the static local spin susceptibility suggest that there may be large spin fluctuation in ML Ni and 1313-La327 may have a more complicated magnetic property. As for the TL in 1313-La327, the TL-outer Ni- e_g orbitals a non-Fermi liquid behavior, which is similar to the case of La4310. The large weights of high-spin states of ML Ni and TL-outer Ni indicate Hundness in 1313-La327. Under 16 GPa, a Lifshitz transition is observed and a La-related band crosses the Fermi level. Our studies give a new perspective to understand this ML-TL stacking structure and provide a theoretical reference for studying other potential mixed-stacked nickelate superconductors.

ACKNOWLEDGMENTS

This work was supported by the National Natural Science Foundation of China (under Grant No. 11934020). Z.Y.L. was also supported by Innovation Program for Quantum Science and Technology (Grant No. 2021ZD0302402). Computational resources were provided by the Physical Laboratory of High Performance Computing at Renmin University of China.

Appendix A: DETAILS OF THE METHOD

The DFT parts of our DFT+DMFT calculations were performed by WIEN2K code with the full-potential linearized augmented plane-wave method [38]. The experimental crystal structures under ambient pressure and high pressure were chosen in our calculations according to Refs. [24] and [25], respectively. The cutoff parameter was $R_{\text{MT}}K_{\text{max}} = 7.0$. The generalized gradient approximation with Perdew-Burke-Ernzerhof functional was chosen as the exchange and correlation potential [39]. The k -point mesh for the Brillouin zone integration was $13 \times 13 \times 2$. The EDMFTF software package was used to perform the charge fully self-consistent

DFT+DMFT calculations [40]. Each DFT+DMFT cycle contained one-shot DMFT calculation and maximum 100 DFT iterations. Within about 40 DFT+DMFT cycles, we obtained a good convergence. The convergence criteria for charge and total energy were 10^{-7} eV and 10^{-7} Ry, respectively. The systems were enforced to be paramagnetic and calculated at 290 K. Only Ni- e_g orbitals were treated as correlated. A three-impurity problem was considered in our calculations because there are three different kinds of Ni atoms in 1313-La327. They are TL-outer Ni, TL-inner Ni, and ML Ni, respectively. The Hund's exchange parameter J_H was set to be 1.0 eV. We chose the Coulomb interaction parameter $U = 5.0$ (8.0) eV for the Ni atoms in TL (ML) structure. And the experimentally determined Fermi surfaces were well reproduced in our calculations. The density-density form of the Coulomb repulsion was used. We used the projectors with an energy window from -10 to 10 eV with respect to the Fermi level to construct the correlated orbitals. The impurity problem was solved by hybridization expansion continuous-time quantum impurity solver [41] with exact double-counting scheme [42] for the self-energy function. Utilizing the maximum entropy method analytical continuation [43], we obtained the real-frequency self-energy function, which was used to calculate the momentum-resolved spectral function and the other related physical quantities.

-
- [1] H. Sun, M. Huo, X. Hu, J. Li, Z. Liu, Y. Han, L. Tang, Z. Mao, P. Yang, B. Wang, J. Cheng, D.-X. Yao, G.-M. Zhang, and M. Wang, Signatures of superconductivity near 80 K in a nickelate under high pressure, *Nature* **621**, 493 (2023).
- [2] D. Li, K. Lee, B. Y. Wang, M. Osada, S. Crossley, H. R. Lee, Y. Cui, Y. Hikita, and H. Y. Hwang, Superconductivity in an infinite-layer nickelate, *Nature* **572**, 624 (2019).
- [3] C. Rao, D. Buttrey, N. Otsuka, P. Ganguly, H. Harrison, C. Sandberg, and J. Honig, Crystal structure and semiconductor-metal transition of the quasi-two-dimensional transition metal oxide, La_2NiO_4 , *J. Solid State Chem.* **51**, 266 (1984).
- [4] R. J. Cava, B. Batlogg, T. T. Palstra, J. J. Krajewski, W. F. Peck, A. P. Ramirez, and L. W. Rupp, Magnetic and electrical properties of $\text{La}_{2-x}\text{Sr}_x\text{NiO}_{4+\delta}$, *Phys. Rev. B* **43**, 1229 (1991).
- [5] C. H. Chen, S.-W. Cheong, and A. S. Cooper, Charge modulations in $\text{La}_{2-x}\text{Sr}_x\text{NiO}_{4+y}$: Ordering of polarons, *Phys. Rev. Lett.* **71**, 2461 (1993).
- [6] S.-W. Cheong, H. Y. Hwang, C. H. Chen, B. Batlogg, L. W. Rupp, and S. A. Carter, Charge-ordered states in $(\text{La},\text{Sr})_2\text{NiO}_4$ for hole concentrations $n_h=1/3$ and $1/2$, *Phys. Rev. B* **49**, 7088 (1994).
- [7] G. Wu and J. J. Neumeier, Small polaron transport and pressure dependence of the electrical resistivity of $\text{La}_{2-x}\text{Sr}_x\text{NiO}_4$ ($0 < x < \sim 1.2$), *Phys. Rev. B* **67**, 125116 (2003).
- [8] J. Li, P. Ma, H. Zhang, X. Huang, C. Huang, M. Huo, D. Hu, Z. Dong, C. He, J. Liao, X. Chen, T. Xie, H. Sun, and M. Wang, Pressure-driven right-triangle shape superconductivity in bilayer nickelate $\text{La}_3\text{Ni}_2\text{O}_7$, [arXiv:2404.11369](https://arxiv.org/abs/2404.11369).
- [9] L. Wang, Y. Li, S.-Y. Xie, F. Liu, H. Sun, C. Huang, Y. Gao, T. Nakagawa, B. Fu, B. Dong, Z. Cao, R. Yu, S. I. Kawaguchi, H. Kadobayashi, M. Wang, C. Jin, H.-k. Mao, and H. Liu, Structure responsible for the superconducting state in $\text{La}_3\text{Ni}_2\text{O}_7$ at high-pressure and low-temperature conditions, *J. Am. Chem. Soc.* **146**, 7506 (2024).
- [10] C. Lu, Z. Pan, F. Yang, and C. Wu, Interlayer-coupling-driven high-temperature superconductivity in $\text{La}_3\text{Ni}_2\text{O}_7$ under pressure, *Phys. Rev. Lett.* **132**, 146002 (2024).
- [11] Y.-H. Tian, Y. Chen, J.-M. Wang, R.-Q. He, and Z.-Y. Lu, Correlation effects and concomitant two-orbital s_{\pm} -wave superconductivity in $\text{La}_3\text{Ni}_2\text{O}_7$ under high pressure, *Phys. Rev. B* **109**, 165154 (2024).
- [12] Z. Ouyang, J.-M. Wang, J.-X. Wang, R.-Q. He, L. Huang, and Z.-Y. Lu, Hund electronic correlation in $\text{La}_3\text{Ni}_2\text{O}_7$ under high pressure, *Phys. Rev. B* **109**, 115114 (2024).
- [13] H. Oh and Y.-H. Zhang, Type-II $t - J$ model and shared superexchange coupling from Hund's rule in superconducting $\text{La}_3\text{Ni}_2\text{O}_7$, *Phys. Rev. B* **108**, 174511 (2023).
- [14] Q.-G. Yang, D. Wang, and Q.-H. Wang, Possible s_{\pm} -wave superconductivity in $\text{La}_3\text{Ni}_2\text{O}_7$, *Phys. Rev. B* **108**, L140505 (2023).
- [15] Y. Zhu, E. Zhang, B. Pan, X. Chen, D. Peng, L. Chen, H. Ren, F. Liu, N. Li, Z. Xing, J. Han, J. Wang, D. Jia, H. Wo, Y. Gu, Y. Gu, L. Ji, W. Wang, H. Gou, Y. Shen, T. Ying, X. Chen, W. Yang, C. Zheng, Q. Zeng, J. gang Guo, and J. Zhao, Superconductivity in trilayer nickelate $\text{La}_4\text{Ni}_3\text{O}_{10}$ single crystals, [arXiv:2311.07353](https://arxiv.org/abs/2311.07353).
- [16] J. Li, C.-Q. Chen, C. Huang, Y. Han, M. Huo, X. Huang, P. Ma, J. Qiu, Zhengyang and Chen, X. Hu, L. Chen, T. Xie, B. Shen, H. Sun, D.-X. Yao, and M. Wang, Structural transition, electric transport, and electronic structures in the compressed trilayer nickelate $\text{La}_4\text{Ni}_3\text{O}_{10}$, *Sci. China Phys. Mech. Astron.* **67**, 117403 (2024).

- [17] Q. Li, Y.-J. Zhang, Z.-N. Xiang, Y. Zhang, X. Zhu, and H.-H. Wen, Signature of superconductivity in pressurized $\text{La}_4\text{Ni}_3\text{O}_{10}$, *Chinese Physics Letters* **41**, 017401 (2024).
- [18] M. Zhang, C. Pei, X. Du, W. Hu, Y. Cao, Q. Wang, J. Wu, Y. Li, H. Liu, C. Wen, Y. Zhao, C. Li, W. Cao, S. Zhu, Q. Zhang, N. Yu, P. Cheng, L. Zhang, Z. Li, J. Zhao, Y. Chen, H. Guo, C. Wu, F. Yang, S. Yan, L. Yang, and Y. Qi, Superconductivity in trilayer nickelate $\text{La}_4\text{Ni}_3\text{O}_{10}$ under pressure, [arXiv:2311.07423](https://arxiv.org/abs/2311.07423).
- [19] Q.-G. Yang, K.-Y. Jiang, D. Wang, H.-Y. Lu, and Q.-H. Wang, Effective model and s_{\pm} -wave superconductivity in trilayer nickelate $\text{La}_4\text{Ni}_3\text{O}_{10}$, [arXiv:2402.05447](https://arxiv.org/abs/2402.05447).
- [20] Y. Zhang, L.-F. Lin, A. Moreo, T. A. Maier, and E. Dagotto, Prediction of s_{\pm} -wave superconductivity enhanced by electronic doping in trilayer nickelates $\text{La}_4\text{Ni}_3\text{O}_{10}$ under pressure, [arXiv:2402.05285](https://arxiv.org/abs/2402.05285).
- [21] M. Zhang, H. Sun, Y.-B. Liu, Q. Liu, W.-Q. Chen, and F. Yang, The s_{\pm} -wave superconductivity in the pressurized $\text{La}_4\text{Ni}_3\text{O}_{10}$, [arXiv:2402.07902](https://arxiv.org/abs/2402.07902).
- [22] J.-X. Wang, Z. Ouyang, R.-Q. He, and Z.-Y. Lu, Non-Fermi liquid and Hund correlation in $\text{La}_4\text{Ni}_3\text{O}_{10}$ under high pressure, *Phys. Rev. B* **109**, 165140 (2024).
- [23] C. Lu, Z. Pan, F. Yang, and C. Wu, Superconductivity in $\text{La}_4\text{Ni}_3\text{O}_{10}$ under pressure, [arXiv:2402.06450](https://arxiv.org/abs/2402.06450).
- [24] X. Chen, J. Zhang, A. S. Thind, S. Sharma, H. LaBollita, G. Pettersson, H. Zheng, D. P. Phelan, A. S. Botana, R. F. Klie, and J. F. Mitchell, Polymorphism in the Ruddlesden–Popper nickelate $\text{La}_3\text{Ni}_2\text{O}_7$: Discovery of a hidden phase with distinctive layer stacking, *J. Am. Chem. Soc.* **146**, 3640 (2024).
- [25] P. Puphal, P. Reiss, N. Enderlein, Y.-M. Wu, G. Khalullin, V. Sundaramurthy, T. Priessnitz, M. Knauff, L. Richter, M. Isobe, P. A. van Aken, H. Takagi, B. Keimer, Y. E. Sulyolcu, B. Wehinger, P. Hansmann, and M. Hepting, Unconventional crystal structure of the high-pressure superconductor $\text{La}_3\text{Ni}_2\text{O}_7$, [arXiv:2312.07341](https://arxiv.org/abs/2312.07341).
- [26] H. Wang, L. Chen, A. Rutherford, H. Zhou, and W. Xie, Long-range structural order in a hidden phase of Ruddlesden–Popper bilayer nickelate $\text{La}_3\text{Ni}_2\text{O}_7$, *Inorg. Chem.* **63**, 5020 (2024).
- [27] S. N. Abadi, K.-J. Xu, E. G. Lomeli, P. Puphal, M. Isobe, Y. Zhong, A. V. Fedorov, S.-K. Mo, M. Hashimoto, D.-H. Lu, B. Moritz, B. Keimer, T. P. Devereaux, M. Hepting, and Z.-X. Shen, Electronic structure of the alternating monolayer-trilayer phase of $\text{La}_3\text{Ni}_2\text{O}_7$, [arXiv:2402.07143](https://arxiv.org/abs/2402.07143).
- [28] Y. Zhang, L.-F. Lin, A. Moreo, T. A. Maier, and E. Dagotto, Electronic structure, self-doping, and superconducting instability in the alternating single-layer trilayer stacking nickelates $\text{La}_3\text{Ni}_2\text{O}_7$, [arXiv:2404.16600](https://arxiv.org/abs/2404.16600).
- [29] Q. Gu and H.-H. Wen, Superconductivity in nickel-based 112 systems, *The Innovation* **3**, 100202 (2022).
- [30] Y.-f. Yang and G.-M. Zhang, Self-doping and the Mott-Kondo scenario for infinite-layer nickelate superconductors, *Front. Phys.* **9** (2022).
- [31] Y. Cao and Y.-f. Yang, Flat bands promoted by Hund’s rule coupling in the candidate double-layer high-temperature superconductor $\text{La}_3\text{Ni}_2\text{O}_7$ under high pressure, *Phys. Rev. B* **109**, L081105 (2024).
- [32] Z. Dong, M. Huo, J. Li, L. Jingyuan, P. Li, H. Sun, L. Gu, Y. Lu, M. Wang, Y. Wang, and Z. Chen, Visualization of oxygen vacancies and self-doped ligand holes in $\text{La}_3\text{Ni}_2\text{O}_{7-\delta}$, *Nature* **10.1038/s41586-024-07482-1** (2024).
- [33] F. Lechermann, S. Bötzel, and I. M. Eremin, Electronic instability, layer selectivity and Fermi arcs in $\text{La}_3\text{Ni}_2\text{O}_7$, [arXiv:2403.12831](https://arxiv.org/abs/2403.12831).
- [34] Y. Wang, C.-J. Kang, H. Miao, and G. Kotliar, Hund’s metal physics: From SrNiO_2 to LaNiO_2 , *Phys. Rev. B* **102**, 161118(R) (2020).
- [35] Z. Wang, G.-M. Zhang, Y.-f. Yang, and F.-C. Zhang, Distinct pairing symmetries of superconductivity in infinite-layer nickelates, *Phys. Rev. B* **102**, 220501 (2020).
- [36] Y. Zhang, L.-F. Lin, A. Moreo, T. A. Maier, and E. Dagotto, Prediction of s_{\pm} -wave superconductivity enhanced by electronic doping in trilayer nickelates $\text{La}_4\text{Ni}_3\text{O}_{10}$ under pressure, [arXiv:2402.05285](https://arxiv.org/abs/2402.05285).
- [37] C. Lu, Z. Pan, F. Yang, and C. Wu, Superconductivity in $\text{La}_4\text{Ni}_3\text{O}_{10}$ under pressure (), [arXiv:2402.06450](https://arxiv.org/abs/2402.06450).
- [38] P. Blaha, K. Schwarz, F. Tran, R. Laskowski, G. K. H. Madsen, and L. D. Marks, WIEN2k: An APW+lo program for calculating the properties of solids, *J. Chem. Phys.* **152**, 074101 (2020).
- [39] J. P. Perdew, K. Burke, and M. Ernzerhof, Generalized gradient approximation made simple, *Phys. Rev. Lett.* **77**, 3865 (1996).
- [40] K. Haule, C.-H. Yee, and K. Kim, Dynamical mean-field theory within the full-potential methods: Electronic structure of CeIrIn_5 , CeCoIn_5 , and CeRhIn_5 , *Phys. Rev. B* **81**, 195107 (2010).
- [41] K. Haule, Quantum Monte Carlo impurity solver for cluster dynamical mean-field theory and electronic structure calculations with adjustable cluster base, *Phys. Rev. B* **75**, 155113 (2007).
- [42] K. Haule, Exact Double Counting in Combining the Dynamical Mean Field Theory and the Density Functional Theory, *Phys. Rev. Lett.* **115**, 196403 (2015).
- [43] M. Jarrell and J. Gubernatis, Bayesian inference and the analytic continuation of imaginary-time quantum monte carlo data, *Phys. Rep.* **269**, 133 (1996).