

The design, verification, and applications of Hotspice: a Monte Carlo simulator for artificial spin ice

Jonathan Maes¹,¹ Diego De Gusem¹,¹ Ian Lateur¹,¹ Jonathan Leliaert¹,¹ Aleksandr Kurenkov^{2,3},^{2,3} and Bartel Van Waeyenberge¹

¹*DyNaMat, Department of Solid State Sciences, Ghent University, 9000 Ghent, Belgium*

²*Laboratory for Mesoscopic Systems, Department of Materials, ETH Zurich, 8093 Zurich, Switzerland*

³*Laboratory for Multiscale Materials Experiments, PSI Center for Neutron and Muon Sciences, Forschungsstrasse 111, 5232 Villigen PSI, Switzerland*

(Dated: September 10, 2024)

We present Hotspice, a Monte Carlo simulation software designed to capture the dynamics and equilibrium states of Artificial Spin Ice (ASI) systems with both in-plane (IP) and out-of-plane (OOP) geometries. An Ising-like model is used where each nanomagnet is represented as a macrospin, with switching events driven by thermal fluctuations, magnetostatic interactions, and external fields. To improve simulation accuracy, we explore the impact of several corrections to this model, concerning for example the calculation of the dipole interaction in IP and OOP ASI, as well as the impact of allowing asymmetric rather than symmetric energy barriers between stable states. We validate these enhancements by comparing simulation results with experimental data for pinwheel and kagome ASI lattices, demonstrating how these corrections enable a more accurate simulation of the behavior of these systems. We finish with a demonstration of ‘clocking’ in pinwheel and OOP square ASI as an example of reservoir computing.

Keywords: Artificial Spin Ice; Monte Carlo simulation; Metropolis-Hastings; Néel-Arrhenius; Reservoir computing

I. INTRODUCTION

Artificial Spin Ice (ASI) are arrays of magnetostatically coupled nanomagnets arranged on a lattice. [1, 2] These nanomagnets are made sufficiently small – usually a few tens of nanometers thick with lateral dimensions of the order of 100 nm [3] – such that it is energetically favorable for them to have an almost homogeneous magnetization. [4–7] Nanomagnets are designed to exhibit uniaxial anisotropy, meaning their magnetic moment prefers to align along the so-called “easy axis”. [3] They typically have a flat geometry, which causes the magnetization to prefer an in-plane orientation. [5] Out-of-plane (OOP) magnets can be made by using interfacial anisotropy to counteract this shape anisotropy, while in-plane (IP) magnets are typically given an elongated shape to align the easy axis with the long axis of the magnet.

Thus, each nanomagnet behaves as a bistable macrospin, with the magnetic moment pointing in either direction along the easy axis. Transitions between these stable states can occur spontaneously at elevated temperatures if the energy barrier posed by shape anisotropy is not too high. [4, 8] Switching can also be facilitated by a magnetic field (of external origin or originating from neighboring magnets), or by more intricate methods such as current-induced torques. [9, 10]

ASI systems were originally inspired by the magnetic frustration – the presence of competing interactions which cannot simultaneously all be satisfied – observed in natural spin ices found in certain crystal structures. Spin ices, in turn, got their name from water ice, which is the prototypical system exhibiting geometrical frustra-

tion. [3, 11–13] Frustration can lead to correlations and collective behavior that the individual elements would not exhibit by themselves, resulting in nontrivial dynamics and complex magnetic orderings. [14–16]

ASI is very attractive in comparison to its natural spin ice counterpart. Modern nanofabrication methods such as electron beam lithography allow any arbitrary geometry to be realized and many other aspects of the system to be engineered, offering enormous freedom to the designer. [14, 15] Furthermore, the mesoscopic size of ASI (a few hundred nanometers) enables direct observation of their magnetic degrees of freedom through a variety of microscopy techniques, in contrast to natural spin ices where imaging individual spins is not feasible. [3, 17] Hence, the controlled, tunable and easily measurable environment offered by ASI has enabled the study of complex phenomena such as phase transitions with ordered domains [16, 18–23] or glasslike behavior [11, 24], vertex-based frustration [25] leading to emergent topological structures such as monopoles and Dirac strings [26, 27], chiral dynamics... [23, 28] ASI also holds significant potential for computational applications [29], both in conventional logic [30–32] and neuromorphic computing. [15, 33]

The dynamics of ASI can be simulated using micromagnetic codes, such as the finite-difference-based `mumax3` [34] and `OOMMF` [35] or the finite-element-based `Nmag` [36], which capture the magnetization dynamics of individual nanomagnets in great detail. However, the time between successive switches of a nanomagnet is not necessarily similar to the timescale of micromagnetics: when the simulated time extends beyond several microseconds, simulating even a modest number

of magnets – on the order of several dozen – becomes computationally unfeasible. [37]

To address these limitations, specialized ASI simulation tools have been developed, such as the flatspin simulator [2], which implements deterministic spin flipping via a Stoner-Wohlfarth model. [38] Using such higher-level approximations enables the study of collective behavior in much larger systems and over far longer timescales than is feasible with micromagnetic codes, though at the cost that the internal magnetization structure of individual nanomagnets is no longer simulated in detail. Additionally, Monte Carlo methods are often used to simulate spin ices, including ASI, but these are typically specialized to a select few lattice geometries and often only account for nearest-neighbor interactions, whose strength is often arbitrarily set or calculated separately using micromagnetic codes. [18, 19, 39, 40]

Our goal was to blend these two approaches, resulting in Hotspice: a versatile Monte Carlo simulator meant to capture ASI physics with minimal arbitrary parameters, allowing various lattice configurations to be evaluated. This software approximates each single-domain nanomagnet as a single Ising spin, associating energies with its various states and accounting for the magnetostatic interaction between all magnets. Throughout this paper, we investigate several model variants to assess their accuracy in simulating the behavior of ASI. These variants differ in their calculation of the magnetostatic interactions, the use of symmetric versus asymmetric energy barriers, and their choice of update algorithms.

II. DESIGN

Hotspice is a Monte Carlo simulation software implemented as a Python package, designed to model both in-plane (IP) and out-of-plane (OOP) ASI systems containing thousands of magnets over arbitrary timescales. It was developed to explore reservoir computing in ASI, as discussed in Section IV C. Simulations can be performed on either CPU or GPU, with the optimal hardware choice depending on the size of the ASI and the update scheme used. Both open and periodic boundary conditions (PBC) are possible.

In this section, we describe the model implemented in Hotspice and discuss several variants of this model.

A. Model

Because the magnetization prefers to align along the fixed easy axis of a nanomagnet, it is natural to use an Ising-like approximation where the position \mathbf{r}_i , axis \mathbf{u}_i , and size of magnetic moment¹ μ_i of each magnet are

¹ The size of the magnetic moment μ_i corresponds to the total ground state magnetic moment $|\int_{\Omega_i} \mathbf{M}(\mathbf{r}) d\mathbf{r}|$, with Ω_i the shape

fixed, allowing the magnets to only switch between the ‘up’ and ‘down’ states. Thus, the total magnetic moment vector of magnet i can be expressed as $\boldsymbol{\mu}_i = s_i \mu_i \mathbf{u}_i$, where $s_i = \pm 1$ and $|\mathbf{u}_i| = 1$.

The switching rate between these states is determined by the temperature T and the effective energy barrier \widetilde{E}_B separating them. For an isolated nanomagnet, the energy barrier $E_B = K_u V^2$ originates from its uniaxial shape anisotropy K_u . Interactions with other magnets or external fields modify the energy landscape, leading to an effective barrier \widetilde{E}_B . [37] Hotspice allows each magnet to have a unique magnetic moment size μ_i , temperature T_i and energy barrier $E_{B,i}$. This enables, for instance, modelling some of the disorder due to lithographic variations by assigning a different shape anisotropy to each magnet, typically sampled from a Gaussian distribution with mean E_B and standard deviation $\sigma(E_B)$.

Due to the periodic nature of many ASI lattices, Hotspice chooses to perform the simulation on a rectangular grid, the benefits of which will be discussed in Section II D. Each grid point may or may not contain a magnet, and the magnets must either all be IP or OOP. Many popular ASI lattices can be constructed in this manner, as showcased in Fig. 1. Some lattices in this figure are related to each other: the magnets of the OOP lattices (i)-(l) are positioned at the vertices where magnets meet in the respective IP lattices (e)-(h), and the pinwheel lattices (a) and (b) are equal to the square lattices (c) and (d), respectively, but with each magnet rotated 45° .

B. Energy calculation

1. Energy terms

Hotspice considers three energy terms³: the magnetostatic interaction energy $E_{MS,i,j}$ between magnets i and j , the Zeeman energy $E_{Z,i}$ of an external field \mathbf{B}_{ext} interacting with magnet i , and the exchange coupling energy $E_{\text{exch},i,j}$ between nearest neighbors (NN) i and j . By default, only the magnetostatic interaction is nonzero. For magnetic dipoles, they are calculated as follows:

$$E_{MS,i,j} = \frac{\mu_0}{4\pi} \left(\frac{\boldsymbol{\mu}_i \cdot \boldsymbol{\mu}_j}{|\mathbf{r}_{ij}|^3} - \frac{3(\boldsymbol{\mu}_i \cdot \mathbf{r}_{ij})(\boldsymbol{\mu}_j \cdot \mathbf{r}_{ij})}{|\mathbf{r}_{ij}|^5} \right), \quad (1)$$

$$E_{Z,i} = -\boldsymbol{\mu}_i \cdot \mathbf{B}_{\text{ext}}, \quad (2)$$

$$E_{\text{exch},i,j} = J \frac{\boldsymbol{\mu}_i \cdot \boldsymbol{\mu}_j}{\mu_i \mu_j}, \quad (3)$$

of magnet i and $\mathbf{M}(\mathbf{r})$ its magnetization in the twofold degenerate ground state. Due to edge relaxation effects, this value is slightly smaller than $M_{\text{sat}} V_i$.

² This is valid for switching by coherent rotation. Similar to the calculation of μ , edge relaxation effects may cause the effective volume to be slightly smaller.

³ Additional energy terms can be defined by the user by inheriting from the `Energy` class.

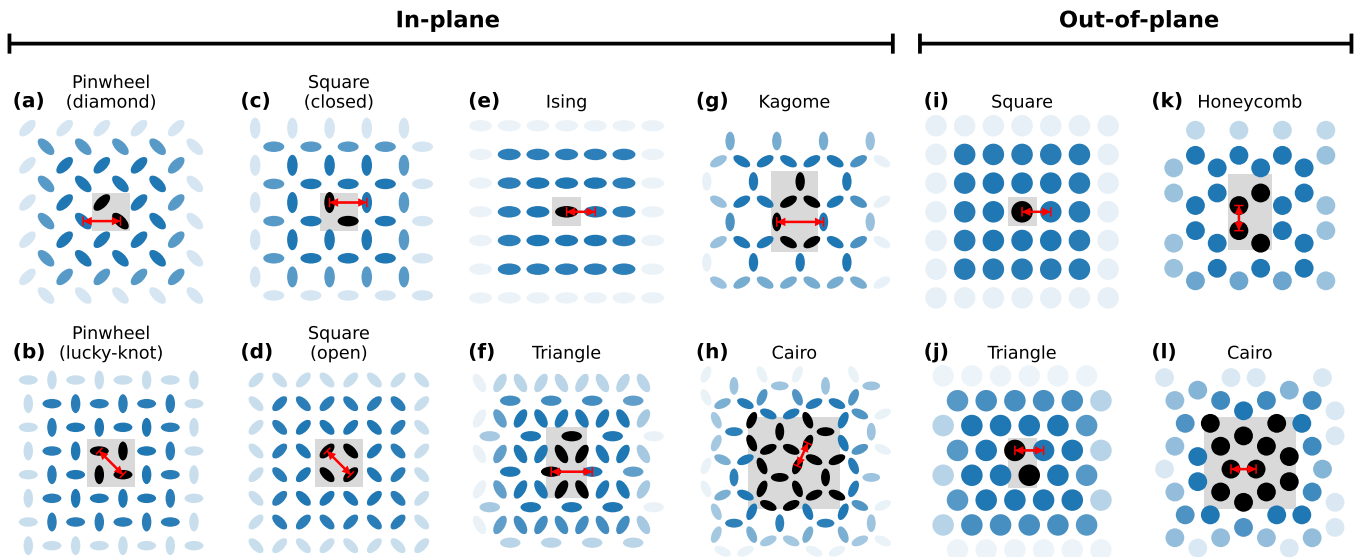


FIG. 1. Predefined artificial spin ice (ASI) lattices available in Hotspice. The unit cell of each lattice is delineated by a central grey rectangle. The red indicator defines the lattice parameter a . In the Ising approximation, the magnetization of in-plane magnets (top) aligns along the major axis of the depicted ellipses. Out-of-plane magnets (bottom) are illustrated as circles.

with \mathbf{r}_{ij} the vector connecting the two magnetic dipoles $\boldsymbol{\mu}_i$ and $\boldsymbol{\mu}_j$, μ_0 the vacuum permeability and J the exchange coupling constant. The exchange interaction is usually not present in ASI ($J = 0$), but can be relevant in cases such as interconnected ASI (whether by design or by lithographic inaccuracies); this was for example the case in Ref. [41], where one sample required accounting for the exchange interaction to achieve a proper fit.

The combined interaction energy E_i of a single magnet i is then given by

$$E_i = E_{Z,i} + \sum_j E_{\text{MS},i,j} + \sum_{j \in \mathcal{N}_i} E_{\text{exch},i,j}, \quad (4)$$

with \mathcal{N}_i the nearest neighbors of i . Note that, due to the absence of self-energy in Eq. (4), E_i simply changes sign when magnet i switches, and hence its switching energy $\Delta E_{i,1 \rightarrow 2} = -2E_i$.

2. Finite-size corrections to the magnetostatic energy

Eqs. (1) to (3) approximate each nanomagnet as a point dipole, but real nanomagnets have finite spatial extent. This does not affect the Zeeman and exchange energy since they are position-independent, and any shape-related effects can be captured by an appropriately chosen \mathbf{B}_{ext} and J . The magnetostatic interaction, however, depends on the relative position, orientation, and shape of all magnets. This may result in inadequate simulation of closely spaced ASI where the real magnetostatic coupling can be significantly stronger than predicted by a point dipole approximation. Therefore, two (mutually exclusive) improvements are proposed, which rescale the magnetostatic interaction energy between magnets.

a. Second-order correction for dipoles In Ref. [7], *Politi and Pini* present a multipole expansion of the magnetostatic interaction, to account for the finite size of 2D nanomagnets (i.e., lateral dimensions \gg thickness), assuming a uniform magnetization. This results in a second-order correction

$$E_{\text{MS},i,j} = E_{\text{MS},i,j}^{(0)} + E_{\text{MS},i,j}^{(2)}, \quad (5)$$

where $E_{\text{MS},i,j}^{(0)}$ is the original point dipole magnetostatic interaction given by Eq. (1). The second-order correction is

$$E_{\text{MS},i,j}^{(2)} = \frac{\mu_0}{4\pi} \frac{3\mathcal{I}_{ij}}{2} \left[3 \frac{\boldsymbol{\mu}_i^{\text{OOP}} \cdot \boldsymbol{\mu}_j^{\text{OOP}}}{r_{ij}^5} + \frac{\boldsymbol{\mu}_i^{\text{IP}} \cdot \boldsymbol{\mu}_j^{\text{IP}}}{r_{ij}^5} - 5 \frac{(\boldsymbol{\mu}_i^{\text{IP}} \cdot \mathbf{r}_{ij})(\boldsymbol{\mu}_j^{\text{IP}} \cdot \mathbf{r}_{ij})}{r_{ij}^7} \right], \quad (6)$$

where $\boldsymbol{\mu}_i$ was split into its IP and OOP components. The shape of the nanomagnets is encapsulated in the single scalar $\mathcal{I}_{ij} = \frac{\mathcal{I}_i + \mathcal{I}_j}{2}$, which is calculated similar to a moment of inertia: $\mathcal{I}_i = \int_{\Omega_i} |\mathbf{r} - \mathbf{r}_{0,i}|^2 d\mathbf{r}$ with $\mathbf{r}_{0,i} = \int_{\Omega_i} \mathbf{r} d\mathbf{r}$ the center of mass of magnet i . Assuming all magnets are elliptical cylinders with semi-major axis a and semi-minor axis b , this reduces to $\mathcal{I}_{ij} = (a^2 + b^2)/4$. While this correction can be applied to both IP and OOP magnetic dipoles, it is most effective for OOP systems as can be seen in Fig. 2.

b. Dumbbell model Instead of representing a magnet as a point dipole, one may instead represent it as a pair of magnetic monopoles. [42, 43] This introduces a new parameter d : the effective distance between the north and south poles of a magnet, with respective positions $\mathbf{r}_{\mathbf{N}_i} =$

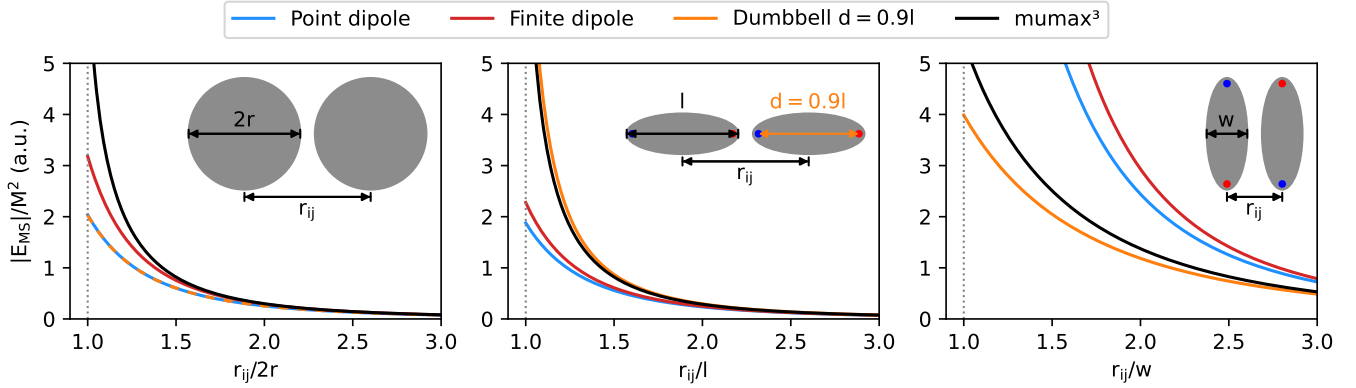


FIG. 2. Magnitude of the magnetostatic interaction between two magnets as a function of their normalized center-to-center distance, for the three Hotspice calculation methods (point dipole, second-order correction for dipoles, and dumbbell) compared to a micromagnetic `mumax3` calculation. OOP magnets are assumed to be circular with diameter $2r$, IP magnets are ellipses with length l and width $w = 4l/11$. Positions of north and south monopoles used for the dumbbell calculation in IP magnets are shown as red \bullet and blue \bullet dots and are a distance $d = 0.9l$ apart within a magnet. The energy on the vertical axis was divided by M^2 to be independent of magnet volume.

$\mathbf{r}_i + s_i \frac{d_i}{2} \mathbf{u}_i$ and $\mathbf{r}_s = \mathbf{r}_i - s_i \frac{d_i}{2} \mathbf{u}_i$. An appropriate choice of d_i (slightly smaller than the physical length l of the nanomagnet [44]) allows this dumbbell model to emulate the spatial extent of a real nanomagnet. The north and south monopoles are assigned magnetic charges $+q_i$ and $-q_i$, respectively, with $q_i = \mu_i/d_i$. [42]

The interaction energy between two magnetic charges q and q' can be derived from the magnetic version of Coulomb's law [45] as

$$E = - \int_{\infty}^{\mathbf{r}} \frac{\mu_0}{4\pi} \frac{qq'}{|\mathbf{r}'|^3} \hat{\mathbf{r}} \cdot d\mathbf{r} = \frac{\mu_0}{4\pi} \frac{qq'}{|\mathbf{r}|}. \quad (7)$$

The magnetostatic interaction energy between two nanomagnets is then the sum of their four mutual monopole interactions, resulting in

$$E_{\text{MS},i,j} = \frac{\mu_0 \mu_i \mu_j}{4\pi d_i d_j} \left(\frac{1}{|\mathbf{r}_{\mathbf{N}_i} - \mathbf{r}_{\mathbf{N}_j}|} + \frac{1}{|\mathbf{r}_{\mathbf{S}_i} - \mathbf{r}_{\mathbf{S}_j}|} - \frac{1}{|\mathbf{r}_{\mathbf{N}_i} - \mathbf{r}_{\mathbf{S}_j}|} - \frac{1}{|\mathbf{r}_{\mathbf{S}_i} - \mathbf{r}_{\mathbf{N}_j}|} \right). \quad (8)$$

The minus sign in the equation appears because the north and south poles have opposite charge.

c. Comparison The effect these two methods have on the magnetostatic interaction is illustrated in Fig. 2, as a function of the normalized distance between magnets. For out-of-plane (OOP) systems, the dumbbell model is inadequate due to the small fringe fields and the limited thickness of the magnets. Instead, the second-order dipole correction is more appropriate, yielding a significant improvement towards the ideal `mumax3` curve.

For IP systems, the dumbbell model constitutes a vast improvement over the standard point dipole treatment. The best correspondence with `mumax3` is found when the monopole-monopole distance d is set slightly shorter than

the length l of a magnet, typically around $d/l \approx 0.9$. This adjustment accounts for the curvature at the ends of most nanomagnets; similar values for d/l were previously found in Ref. [44] for typical nanomagnet shapes like ellipses and stadiums. In contrast, the second-order dipole correction has little effect in IP systems and can even increase the discrepancy from `mumax3`: it emulates increased spatial extent and therefore always increases the interaction, but in the anti-parallel configuration ($\uparrow\downarrow$) the point dipole model already overestimates the interaction.

Thus, the dumbbell model is preferred for IP systems, while the second-order dipole correction is most suitable for OOP systems.

3. Effective energy barrier

To simulate ASI dynamics and hysteresis, it is crucial to know the height of the effective energy barrier \widetilde{E}_B which separates the two magnetization states of each magnet.⁴ It can be calculated at varying levels of accuracy, which may result in different switching rates or even a different switching order. [37]

Recall that Eq. (4) is written in such a way that the interaction energy E_i changes sign if the magnetization of either magnet is reversed: say i reverses at time t , then $E_i(t^+) = -E_i(t^-)$. This formulation allows Hotspice to easily calculate the energy change $\Delta E_i = -2E_i$ of magnet i if it would switch (called its switching energy).

We will omit the subscript i for the remainder of this section; it is implied that the following equations apply

⁴ The effective barrier \widetilde{E}_B is distinct from the shape anisotropy E_B : \widetilde{E}_B is a modification of E_B caused by the interaction with other magnets.

to each magnet individually.

a. Mean-barrier approximation The simplest way to approximate the effective energy barrier \widetilde{E}_B is to assume that the highest-energy state lies halfway between the two stable states. This means the barrier height changes at half the rate at which the switching energy ΔE changes, leading to the approximation $\widetilde{E}_B = E_B + \Delta E/2$. [46, 47] However, this does not account for the extreme cases where the interactions are so strong that the energy barrier effectively disappears. This happens when $|\Delta E|$ exceeds twice the shape anisotropy E_B , leaving only one global minimum. To handle these situations, Hotspice calculates the effective energy barrier \widetilde{E}_B as follows:

$$\widetilde{E}_B = \begin{cases} E_B + \frac{\Delta E}{2} & \text{if } |\frac{\Delta E}{2}| < E_B, \\ \Delta E & \text{otherwise.} \end{cases} \quad (9)$$

This way, ΔE serves as the barrier when the original energy barrier disappears.

b. Asymmetric barrier (IP only) The simple approximation above is insufficient for many in-plane ASI. In real nanomagnets, the magnetization must rotate for switching to occur: either clockwise (\odot) or anticlockwise (\ominus). [47] In an asymmetrical environment (when the effective field has a nonzero component perpendicular to the easy axis) one of these two rotation directions will be preferred. [37, 47] Take for example the pinwheel ASI: any two neighboring magnets form a T-shape, so the magnet pointing into the side of the other will greatly influence whether the other prefers \odot or \ominus rotation. [47] Accounting for the existence of these separate chiral switching channels profoundly affects the switching rates and transition kinetics, since switching will occur predominantly via the more favorable pathway. [37]

In the dipole model, this can be accounted for by keeping track of the energy of each magnet in these transitional ‘perpendicular’ states. We therefore introduce E_\perp , which represents the energy of a magnet if it would point 90° counterclockwise from its normal magnetization direction, but without taking into account the shape anisotropy (E_B) associated with that orientation. (Note: the bistability of the magnets does not change; we are simply putting ‘test dipoles’ in the perpendicular orientation, but the magnets are never actually put in these states.) The equation for the effective barrier along the two rotation pathways (\pm) then becomes

$$\widetilde{E}_B = \begin{cases} E_B \pm \rho E_\perp + \frac{\Delta E}{2} & \text{if } |\frac{\Delta E}{2}| < E_B \pm \rho E_\perp, \\ \Delta E & \text{otherwise,} \end{cases} \quad (10)$$

which results in two different barriers if $E_\perp \neq 0$. Note that the value of each term in this equation can differ for each magnet in the ASI. The parameter $\rho = \mu_\perp/\mu_\parallel > 0$ was introduced to account for non-coherent magnetization reversal processes like domain wall nucleation and propagation, which result in an effective reduction of the magnetic moment during reversal. [37, 48] Using a value

$\rho < 1$ improves correspondence with experimental observations, as we will show in Section IV A.

c. Exact solution (OOP only) If an analytical expression for the energy as a function of magnetization angle θ relative to the magnet’s easy axis is known, then \widetilde{E}_B can be calculated exactly. The shape anisotropy creates a basic energy profile with two minima at $\theta = 0$ and $\theta = \pi$, but the exact form of this profile depends on the magnet’s shape; for ellipsoidal magnets, it is $-\frac{E_B}{2} \cos 2\theta$. [5] Assuming a uniform magnetization in each magnet⁵, the magnetostatic and Zeeman interactions add a term proportional to $\cos(\theta - \phi)$, with ϕ the angle of their combined effective field. Thus, the total profile is a sum of two sines and can be fully characterized if E and E_\perp are known. However, in the general case, this results in a transcendental equation requiring numerical approximation to solve, which is not done in Hotspice for performance reasons.

In OOP ASI, an explicit expression can still be obtained because the effective field aligns with the easy axis, making $E_\perp = 0$. This leads to a quadratic relation as described in Ref. [38]:

$$\widetilde{E}_B = \begin{cases} E_B \left(\frac{\Delta E}{4E_B} + 1 \right)^2 & \text{if } |\frac{\Delta E}{2}| < E_B, \\ \Delta E & \text{otherwise.} \end{cases} \quad (11)$$

C. Dynamics

A magnet may spontaneously switch to the opposite magnetization state due to thermal fluctuations. The time evolution of the ASI is evaluated in a stepwise manner by an update algorithm that determines which magnet should switch next. The two distinct types of kinetic Monte Carlo (KMC) algorithms—rejection-free KMC and rejection KMC—were both implemented in Hotspice. In the context of ASI, we refer to these as *Néel-Arrhenius switching* and *Metropolis-Hastings*, respectively. [51] The former is more suitable for simulating the temporal evolution of the system, while the latter can be used to sample the equilibrium distribution of the state space. For a broader overview of Monte Carlo methods, we refer to Ref. [52], which may also clarify the at times confusing naming present throughout literature.

1. Néel relaxation: temporal evolution

Néel relaxation theory [5] states that, for an isolated nanomagnet, the switching rate ν is given by the Néel-Arrhenius equation

$$\nu = \nu_0 \exp\left(-\frac{E_B}{k_B T}\right), \quad (12)$$

⁵ Only perfectly ellipsoidal magnets have uniform magnetization in a uniform external field. [49, 50]

with $k_B T$ the thermal energy and ν_0 the attempt frequency. An estimate of ν_0 for coherent magnetization reversal can be obtained from the limit $E_B \rightarrow 0$. The gyromagnetic precession frequency of the magnetization of a nanomagnet is on the order of 10^9 Hz to 10^{10} Hz. [4, 53] As $E_B \rightarrow 0$, the switching rate ν should approach this value, and in this limit Eq. (12) implies that $\nu \rightarrow \nu_0$, so we use $\nu_0 = 10^{10}$ Hz. [54] An order-of-magnitude estimate of ν_0 suffices, because any small (i.e., $\sim k_B T$) change of E_B will translate to an exponential change in switching rate.

For mutually interacting magnets, an adjusted version of Eq. (12) can be used where E_B is replaced by the effective energy barrier \widetilde{E}_B . In the general case where the energy barriers for clockwise and anticlockwise rotation during switching differ, these two switching channels ($\circlearrowleft, \circlearrowright$) will separately follow Eq. (12), so their switching frequencies must be combined. This yields the total switching rate presented in [47]:

$$\nu = \nu_{\circlearrowleft} + \nu_{\circlearrowright} = \frac{\nu_0}{2} \left[\exp\left(-\frac{\widetilde{E}_{B,\circlearrowleft}}{k_B T}\right) + \exp\left(-\frac{\widetilde{E}_{B,\circlearrowright}}{k_B T}\right) \right], \quad (13)$$

where we assigned a halved attempt frequency $\nu_0/2$ to either switching channel such that Eq. (13) reduces to Eq. (12) in the case of $\widetilde{E}_{B,\circlearrowleft} = \widetilde{E}_{B,\circlearrowright}$. [37]

One iteration of the algorithm is as follows:

1. Calculate the switching rate ν_i of all magnets (i.e., $\forall i$) based on the interaction energies E_i , and hence effective energy barriers $E_{B,i}$, present in the current magnetization state.
2. Generate a random switching time interval Δt_i for each magnet i , sampled from an exponential distribution with mean value $1/\nu_i$.
3. Determine which magnet j has the smallest such time $\Delta t_j = \min_i \Delta t_i$.
4. To prevent excessively long switching times, a parameter t_{\max} was introduced.
 - If $t + \Delta t_j \leq t_{\max}$: increment the elapsed time t by t_j and switch magnet j .
 - If $t + \Delta t_j > t_{\max}$: increment the elapsed time t by t_{\max} without switching a magnet.

The maximum time t_{\max} (default value of one second) prevents the simulation from advancing too far into the future, as the exponential character of the Néel-Arrhenius law can cause switching times to become much longer than what could ever be observed experimentally. It can also be used to apply time-dependent external fields: for example, when a sinusoidal signal of frequency f is applied to the lattice $t_{\max} = 20/f$ ensures the waveform is captured in sufficient detail.

2. Metropolis-Hastings: sampling equilibrium states

Metropolis-Hastings (MH) is a rejection-based kinetic Monte Carlo (KMC) method designed to sample the state space at thermal equilibrium, where the probability of each state appearing is proportional to their Boltzmann factor. [52, 55] Hence, in contrast to Néel-Arrhenius switching, MH is not intended to accurately model the system's transient dynamics and is instead more suitable for examining equilibrium statistical quantities in ASI, like the average magnetization, heat capacity, correlation... [16]

The algorithm repeats the following steps:

1. Select a magnet i at random (with all magnets equally likely to be chosen).
2. Calculate the energy change ΔE_i if this magnet were to switch.
3. Switch the magnet with probability

$$P_i = \begin{cases} \exp(-\Delta E_i/k_B T), & \text{if } \Delta E_i > 0, \\ 1 & \text{otherwise.} \end{cases} \quad (14)$$

4. *Optional*: Increment the elapsed time t by

$$\Delta t = -\frac{\exp(\widetilde{E}_B/k_B T) \ln \chi}{N\nu}, \quad (15)$$

with N the number of magnets in the system and χ a uniformly distributed random variable in $(0, 1]$. [51]

This algorithm satisfies detailed balance and ergodicity, thus ensuring equilibrium is eventually reached, though the rate of convergence may vary as noted in Section III A. [56] For enhanced performance, multiple sufficiently distant magnets can be selected simultaneously, see Section II D 2.

Whereas Néel relaxation relies on an explicit calculation of the elapsed time, Metropolis-Hastings does not strictly require this knowledge. Hence, the last step of the algorithm where the elapsed time is calculated, is optional. For a long time, the notion of a well-defined elapsed time in rejection KMC was controversial. [57–59] Often, the number of MC steps per site was used as a crude measure of ‘elapsed time’, but eventually a formal derivation for the physical time scale in rejection KMC was presented in Ref. [51] (Eq. (15)). Note that the effective energy barrier \widetilde{E}_B only appears in the elapsed time: it does not influence the switching probability in the Metropolis algorithm because it has no effect on the equilibrium state.

D. Implementation details

Hotspice represents an ASI as a rectilinear grid of non-uniform unit cells, with magnets positioned at selected

grid points. In simulating an ASI, we faced a trade-off between the freedom to place magnets arbitrarily and the efficiency of calculation. We opted to prioritize efficiency and accept the geometrical restriction, as most ASI research focuses on periodic lattices. Despite the seemingly restrictive nature of the rectilinear grid, Fig. 1 illustrates its versatility in forming various periodic lattices, with only the Cairo lattices requiring grid non-uniformity. Real-time visualization is simple and efficient for a rectilinear grid, as the underlying matrix can directly be cast to a pixel image.

By leveraging the unit cell concept in periodic lattices and the efficient indexation of a rectilinear grid in computer memory, several aspects of the calculation can be performed more efficiently than for free-form ASI. The unit cell of each lattice in Fig. 1 is depicted as a grey rectangle. Although non-rectilinear unit cells with fewer magnets could be identified for some lattices, Hotspice does not consider these to reduce complexity and maintain a clear connection to the underlying rectilinear grid of the ASI implementation.

1. Kernels

Pre-calculated “kernels” are used to efficiently update the magnetostatic interaction after each switch. For each magnet i , a kernel $\mathbf{K}_i(j)$ stores the strength of this interaction between itself and all other magnets j , enabling the quick calculation of their magnetostatic interaction energy as $E_{MS,i,j} = \mathbf{K}_i(j)s_i s_j$ by precalculating all $\mathbf{K}_i(j)$ values once when the ASI is created. However, for large arrays, this approach becomes impractical due to the need to store $\mathcal{O}(N^2)$ elements $\mathbf{K}_i(j)$ if the underlying rectangular grid has size $N = L_x \times L_y$.

By leveraging unit cells, this storage requirement can be reduced to $\mathcal{O}(N)$. Labeling each spot in the unit cell by an index q , each magnet in the lattice corresponds to an index q . The surrounding magnets of a magnet at spot q will always have the same layout, except for a different cutoff at the border if PBC are disabled. Thus, all possible interactions a magnet at site q experiences can be stored in a single $(2L_x - 1) \times (2L_y - 1)$ matrix \mathbf{K}_q , with the magnet q at the center of the matrix and the element $\mathbf{K}_q(L_x + x, L_y + y)$ representing the interaction between a magnet with index q at site (v, w) and the magnet at site $(v+x, w+y)$. This method requires storing only a few kernels—one for each magnet in the unit cell—rather than one for each magnet in the entire lattice, thereby reducing the number of stored kernels by $\mathcal{O}(N)$.

Note that, if the asymmetric energy barrier is to be accounted for, two additional kernels are needed for each magnet in the unit cell: one where the central magnet is rotated 90° (for initial calculation of E_\perp), and one where all other magnets are rotated 90° (for updating E_\perp when a magnet switches).

The grid allows the straightforward implementation of first-order PBC by adjusting these kernels (adding eight

offset versions of a kernel to itself), which does not impact performance.

2. Multi-switching in Metropolis

Since the Metropolis-Hastings algorithm is designed primarily for sampling equilibrium states rather than capturing the temporal evolution of the system, a straightforward performance improvement can be achieved by selecting multiple magnets simultaneously rather than sequentially. This allows for better usage of the parallel processing capabilities of the GPU, as the magnetostatic energy can then be updated using a convolution. However, to avoid issues with simultaneous switching of nearby magnets, we enforce a minimum distance r between selected magnets. The criterion we use is that two simultaneously sampled magnets should never affect each other’s switching probability by more than a user-adjustable factor $Q \in]0, 1[$ (commonly set to 0.01). This leads to the following expression for r :

$$r \geq \sqrt[3]{\frac{2\mu_0 \max_i \mu_i^2}{\pi Q k_B T}}, \quad (16)$$

valid for the Metropolis-Hastings switching probability $P(\Delta E) = \min(1, \exp(-\Delta E/k_B T))$ and with $\max_i \mu_i^2$ the square of the largest magnetic moment in the lattice.

For magnet selection, we employed a modified “Stratified Jittered Grid” algorithm. The simulation domain is divided into subregions of $R_x \times R_y$ grid cells, with $R_x \geq 2$ and $R_y \geq 2$ chosen such that each subregion has a physical size of at least $r \times r$. A quarter of these subregions are chosen such that they are non-adjacent, and a single magnet is sampled from each of them. [60] This ensures that sampled magnets are at least a distance r apart, though their average distance will be $2r$. Although this method is less random, dense and versatile than Poisson Disk Sampling [60–62], it is efficient to compute in parallel⁶ and synergizes well with our grid-based ASI implementation.

The “supergrid” of subregions is slightly smaller than the ASI to prevent PBC from violating the minimal distance requirement and is randomly shifted over the simulation domain to ensure uniform coverage and proper behavior near the edges. Note that PBC can make it impossible to maintain a spacing $> r$ in very small systems, or with small Q values; in such cases, we resort to selecting a single magnet.

⁶ Ref. [63] presents a parallel Poisson Disk algorithm which generates samples over only a few iterations, though it is nontrivial to restrict the samples to a non-uniform grid without violating the minimal distance constraint.

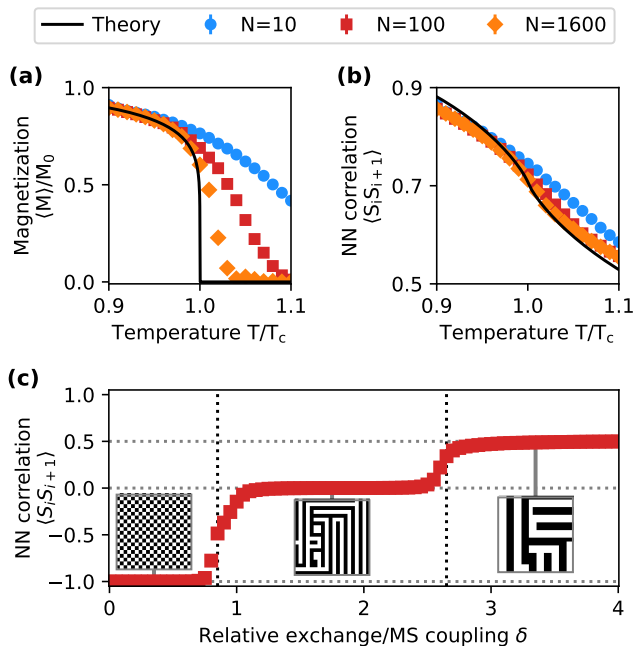


FIG. 3. Hotspice simulation of a square-lattice exchange-coupled Ising system. (a) Average magnetization and (b) nearest-neighbor (NN) correlation as a function of temperature. Discrepancies due to critical slowing down above T_c improve with more Monte Carlo steps per site N . (c) NN correlation when including long-range magnetostatic interactions, as a function of relative magnetostatic/exchange coupling δ . Transitions occur at $\delta = 0.85$ and 2.65 , indicated by dotted lines. Insets show the magnetization state with growing stripe domains: white corresponds to spin ‘up’, black to ‘down’.

III. VERIFICATION

A. Exchange-coupled OOP square system

The 2D square-lattice exchange-coupled Ising model is one of few exactly solvable systems in statistical physics. [64] Its average magnetization M is temperature-dependent:

$$M = \sqrt[8]{1 - \sinh^{-4}(2J/k_B T)}, \quad (17)$$

with J the exchange coupling constant. [65–67] This system exhibits a second-order phase transition at the critical temperature $T_c = \frac{2J}{k_B \ln(1+\sqrt{2})}$. [64] The nearest-neighbor correlation can also be calculated analytically:

$$\langle \sigma_1 \sigma_2 \rangle = \begin{cases} \sqrt{1+k} \left[\frac{1-k}{\pi} K(k) + \frac{1}{2} \right] & \text{for } T < T_c, \\ \sqrt{1+k} \left[\frac{1-k}{\pi k} K(1/k) + \frac{1}{2} \right] & \text{for } T > T_c. \end{cases} \quad (18)$$

with K the complete elliptic integral of the first kind and $k = 1/\sinh^2(2J/k_B T)$. [65]

The result from the Hotspice simulation of this Ising system is shown in Fig. 3a-b, as calculated for an

800×800 lattice on GPU with maximal Metropolis multi-sampling ($Q = +\infty$). The system was not reset between successive temperature steps because the theoretical curves are monotonously decreasing. [68] The Hotspice result corresponds well to theory below T_c and in the high-temperature limit. Just above T_c , however, the average magnetization only slowly evolves to the expected value. This is a symptom of the well-known phenomenon called “critical slowing down”, which originates from a divergence in the autocorrelation time τ near the critical point, causing subsequent Monte Carlo configurations to be highly correlated. [69–71] As a result, the system explores the phase space very slowly, particularly with single-spin flip algorithms like Metropolis. [71] Although cluster algorithms like the Wolff algorithm [72] can mitigate this effect, they are not intended for application beyond the 2D Ising system.

B. Exchange- and magnetostatically coupled OOP square system

Including long-range magnetostatic interactions into an exchange-coupled square-lattice Ising system significantly alters its behavior, which is then determined by the ratio $\delta = E_{\text{exch},i,j}/E_{\text{MS},i,j}$ ($j \in \mathcal{N}_i$) representing the balance between the exchange coupling and magnetostatic interaction. Analytical predictions remain possible: for $\delta < 0.85$, the magnetostatic coupling dominates, leading to a checkerboard state. As δ increases, the ever-stronger exchange coupling leads to the formation of ferromagnetic domains, which organize into stripes due to the magnetostatic interaction, with the stripe width determined by δ . [73]

The average stripe width is reflected in the NN correlation $\langle S_i S_{i+1} \rangle$, as shown in Fig. 3c for a Hotspice simulation. Consistent with the theoretical predictions of Ref. [73], for $\delta < 0.85$ a checkerboard state exists with $\langle S_i S_{i+1} \rangle = -1$. In the range $0.85 < \delta < 2.65$, stripe domains with a width of 1 row are preferred, leading to $\langle S_i S_{i+1} \rangle = 0$. Beyond $\delta = 2.65$, a 2-row width becomes preferable with $\langle S_i S_{i+1} \rangle = 0.5$. Increasing δ further leads to ever wider stripe domains, and in the limit $\delta \rightarrow +\infty$, the correlation approaches $\langle S_i S_{i+1} \rangle \rightarrow 1$.

IV. APPLICATIONS

To explore the accuracy of the various model variants, we compare simulations to several specific experiments. The pinwheel hysteresis highlights the importance of the asymmetric energy barrier, while the kagome reversal is an example where the dumbbell model captures a key detail of the reversal process which could not be reproduced by dipole models. We finish with a demonstration of “clocking” in pinwheel ASI, which has applications in reservoir computing. [74] Python codes for these simulations are provided in the supplementary information.

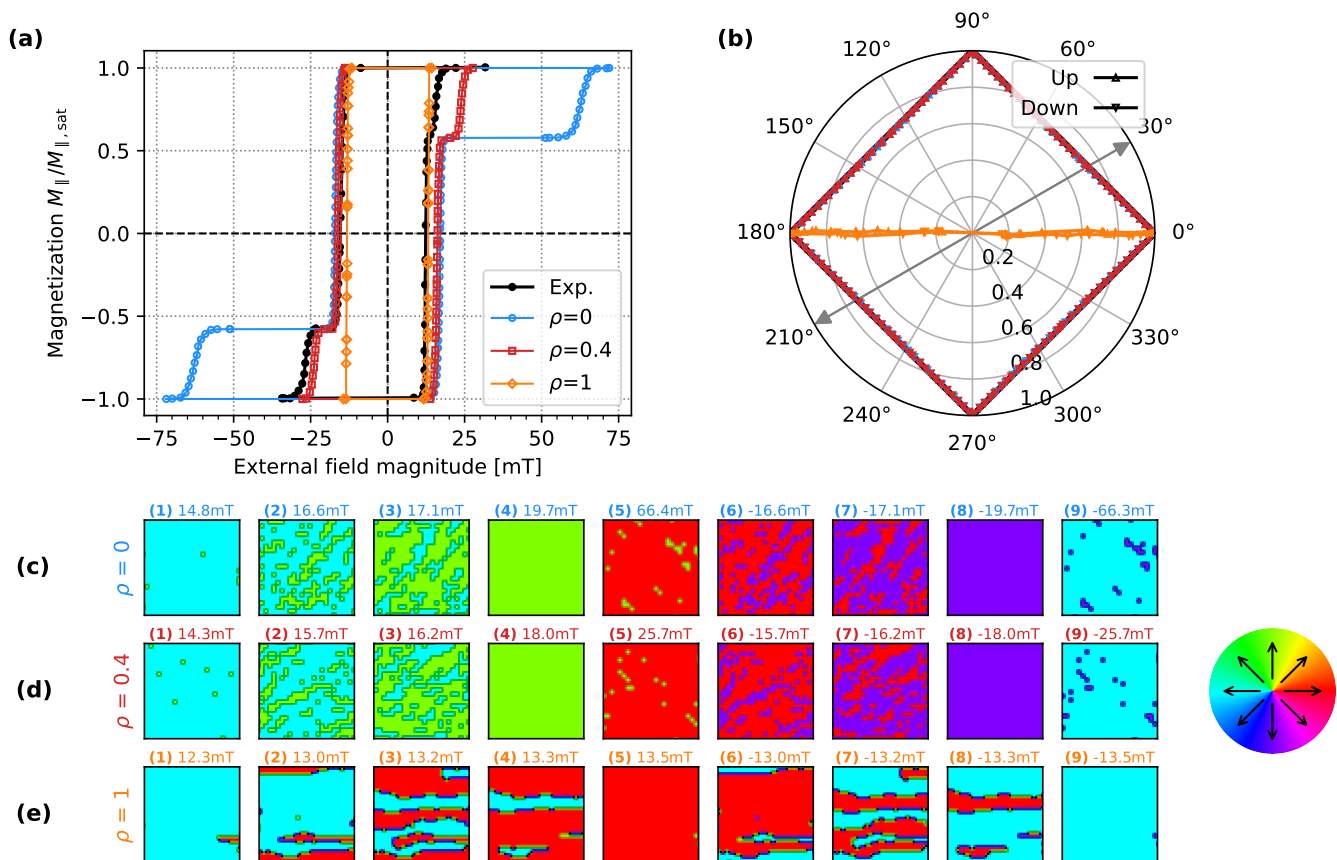


FIG. 4. Hysteresis of the pinwheel ASI for an applied field at 30° with respect to the system edges. The parameter $\rho = \mu_{\perp}/\mu_{\parallel}$ modulates the effect of the asymmetric barrier described in Section II B 3. (a) Component of the average magnetization along the direction of the external magnetic field. The hysteresis observed in experiment by Li *et al.* [75] is shown in black. (b) Path of the average magnetization in-plane. Upward (downward) pointing triangles correspond to the ramp-up (down) of the external field. The external field direction is indicated by the double-headed arrow. (c-e) Snapshots of the system, upon approaching or passing through certain values of $M_{\parallel}/M_{\parallel,\text{sat}}$, in chronological order through the hysteresis loop. The color of each pixel shows the average magnetization angle of the magnets in a small area of the system, encoded according to the color wheel shown on the right. Snapshots (1,5,9) are taken near the saturated $M_{\parallel}/M_{\parallel,\text{sat}} \approx \pm 1$ state, (3) and (7) at the zero-average $M_{\parallel}/M_{\parallel,\text{sat}} = 0$, and (2,4,6,8) at $M_{\parallel}/M_{\parallel,\text{sat}} = \pm \frac{\sqrt{3}}{3} \approx 0.58$, which is the magnetization at the plateau between the two steps for $\rho = 0$ and $\rho = 0.4$.

A. Pinwheel reversal

Pinwheel ASI (Fig. 1a-b) can be seen as consisting of two intertwined sublattices whose magnets are perpendicular to each other. The ground state of this system consists of superferromagnetic domains, where all magnets within each sublattice are magnetized in the same direction. [1, 16, 28]

Li *et al.* [75] performed an experimental study to observe the reversal of ‘diamond’-edge pinwheel ASI (Fig. 1a) under an applied external field. A strong field drives the system towards a uniform state, and since this is also the superferromagnetic ground state of pinwheel ASI, the system will remain in this state when the field is removed, resulting in hysteresis. Notably, when Li *et al.* applied the field at an oblique angle (30°) to the

ASI edges, the reversal occurred in two distinct steps: the sublattice which was more aligned with the field (15° to the easy axis) reversed first, followed by the second sublattice for which the field was at 75° . Accurate simulation of the second reversal step will require accounting for the asymmetry in the energy barrier between clockwise and counterclockwise switching, due to this near-perpendicular field for the second sublattice.

We replicated this experiment using Hotspice for a few values of $\rho = \mu_{\perp}/\mu_{\parallel}$ to clearly observe the effect of the asymmetric barrier, resulting in the hysteresis loops shown in Fig. 4. The Néel update algorithm was used, because the Metropolis-Hastings algorithm samples the equilibrium state space and therefore would not capture the hysteresis observed experimentally – a hysteresis only exists because the equilibrium is not reached within the

timescale of the observation. We used parameters derived from the experimental configuration when possible: an ASI of 25×25 unit cells with a NN center-to-center distance of 420 nm was used, at room temperature (300 K). The magnetic moment and energy barrier of each magnet can be derived from the geometry of the $470 \times 170 \times 10$ nm stadium-shaped magnets and the permalloy ($\text{Ni}_{80}\text{Fe}_{20}$) saturation magnetization $M_{\text{sat}} = 800 \text{ kA m}^{-1}$. This yields a magnetic moment $\mu = M_{\text{sat}}V = 5.9 \times 10^{-16} \text{ A m}^2$, and a mumax³ [34] simulation reveals that the energy barrier of such magnets is $\approx 60 \text{ eV}$. These values result in a good match with the experimental field magnitude for the first reversal step.

In the experiment, the two reversal steps occurred gradually over a range of fields, resembling more of an S-curve rather than a sharp step. This is due to a random spread on the coercive field of each nanomagnet due to imperfections in lithography. [76] We modelled this in the simulation by introducing a random Gaussian variation on the energy barrier, with $\sigma(E_B)/\langle E_B \rangle = 7\%$ yielding the closest agreement to the experiment. Note that the experimental hysteresis curve is not symmetric, in contrast to our simulations, which Li *et al.* attributed to a small sample movement during their measurement which changed the applied field angle with respect to the array.

As can be noted from the figure, the resulting hysteresis, and particularly the field magnitude for the second reversal step, is highly dependent on the choice of $\rho = \mu_{\perp}/\mu_{\parallel}$. When the asymmetry of the energy barrier is neglected ($\rho = 0$), the field magnitude required for the second step is significantly overestimated, as seen in the blue curve of Fig. 4a ($\approx 60 \text{ mT}$ vs. experiment $\approx 25 \text{ mT}$). Increasing ρ reduces the field magnitude at which the second step occurs but has little effect on the first. Notably, for $\rho \gtrsim 0.6$, the second step disappears entirely, and the reversal instead occurs by domain nucleation at the edges of the ASI, as shown in Fig. 4e.

Thus, $\rho \approx 0.4$ yields the best correspondence to the experiment. A possible explanation for this is that the switching of magnets in the experimental ASI does not occur by uniform rotation, as assumed by the Néel-Arrhenius switching law (Eq. (12)). Indications of non-uniform rotation or domain wall-mediated reversal were previously noticed by Morley *et al.* [77]

B. Kagome reversal

The in-plane kagome ASI (Fig. 1g) is a typical example of a frustrated system: every vertex is formed by three magnets that must obey the two-out/one-in or two-in/one-out ice rule. Each magnet has four NN located near its endpoints, making this lattice an interesting testing ground for the dumbbell model. The point dipole model tends to significantly underestimate the NN interaction, while the dumbbell model increases the magnetostatic interaction energy between closely spaced magnets, potentially affecting the dynamics of the system.

We therefore expect the dumbbell model to provide a more accurate simulation of the kagome lattice than the point dipole model. [2, 27]

To illustrate this, we used Hotspice to reproduce the reversal process of kagome ASI as observed by Mengotti *et al.* [27] They studied the hysteresis loop using XMCD to image the evolution of the system’s microstate during a gradual increase of the external field near the coercive field. In the Hotspice simulation shown in Fig. 5a, we applied an increasing magnetic field \mathbf{B}_{ext} to a saturated kagome lattice, at an angle of -93.6° relative to the horizontal axis. This corresponds to a reverse field in the negative y-direction with a slight -3.6° offset to break symmetry between sloped magnets, resulting in the creation of “Dirac strings” of flipped magnets.

As the field strength increases, the Zeeman energy of the magnets rises, with the energy of vertical magnets increasing faster than for the sloped ones. However, the magnetostatic energy is lowest for the vertical magnets in the initial state. The balance between these contributions results in a critical energy barrier E_B^c : when the energy barrier E_B is lower (higher) than this value, a sloped (vertical) magnet will flip first, as shown in Fig. 5b. Therefore, the dynamics may depend on the simulation method, as the dumbbell model increases the magnetostatic interaction energy between nearest neighbors.

We simulated a kagome ASI consisting of 173 magnets whose energy barrier $E_B = 120 \text{ eV}$ with a standard deviation $\sigma(E_B)/\langle E_B \rangle = 5\%$. The results, shown in Fig. 5a, reveal a qualitative difference between the dumbbell and dipole models. In the dumbbell model, sloped magnets on the boundaries of the ASI flip first, while for the dipole method vertical magnets in the bulk flip first. [44] In the experiment of Mengotti *et al.* [27], Dirac strings were observed to originate from sloped magnets, which is in agreement with the dumbbell simulation. Additionally, researchers using the ‘flatspin’ ASI simulator, which employs a dipole-based model, observed Dirac strings to originate from vertical magnets, similar to our results with a dipole model, highlighting the dumbbell model’s ability to capture distinct dynamics. [2]

C. Reservoir computing by “clocking”

Hotspice was developed to explore the potential of reservoir computing (RC) in ASI. RC is a machine learning framework where an input signal is applied to a nonlinear dynamical system, known as the “reservoir”. [33, 78] The reservoir generates a high-dimensional nonlinear response, enabling linear separation without the need to train the reservoir itself. [1, 79] The essential characteristics of reservoirs – short-term memory and high dimensionality – are inherent to many physical systems, including ASI, making them suitable for direct use as a reservoir. [33] This capability has already been demonstrated numerically for various ASI lattices. [1, 15, 41, 80] To optimize the RC capability of ASI,

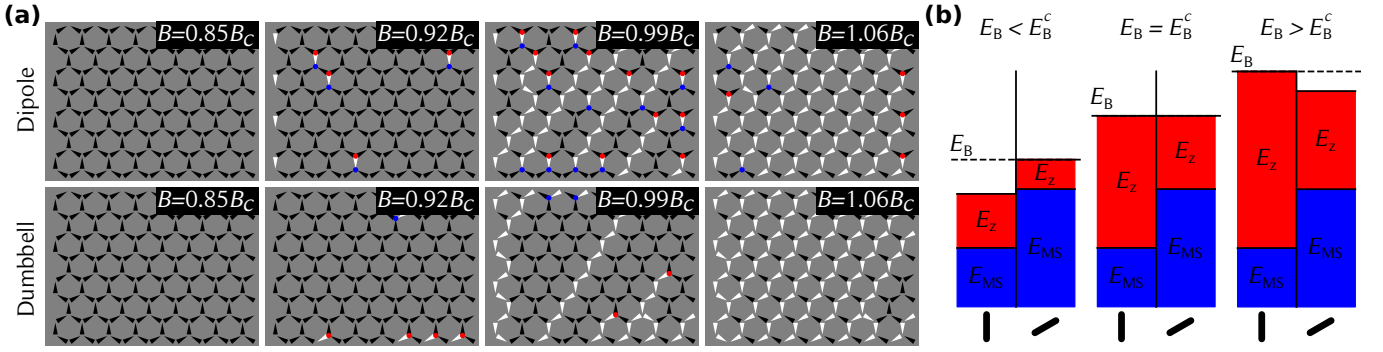


FIG. 5. Reversal of a kagome ASI under an external field applied at -93.6° relative to the horizontal axis. (a) Comparison between the dumbbell and dipole simulations at different external field magnitudes B . Note that the critical field B_C differs between the models: $B_C = 26.7$ mT for the dumbbell model and $B_C = 23.9$ mT for the dipole model. The NN center-to-center distance is 500 nm, with a length $d = 470$ nm used in the dumbbell model. The magnets have a magnetic moment $\mu = 1.1$ fAm², and their energy barrier is normally distributed with a mean of 120 eV and 5% standard deviation. Arrows represent the magnetic moment of the magnets, and the blue and red points (\bullet and \bullet) represent the net change in charge of a vertex. (b) The effect of an externally applied magnetic field on a vertical and sloped magnet for different values of the energy barrier. E_{MS} is the same for each E_B , however it is higher for the sloped magnets compared to the vertical ones. When $E_B < E_B^c$ ($E_B > E_B^c$), the sloped (vertical) magnet will flip first since the Zeeman energy E_z increases faster for the vertical magnets.

it can be advantageous to manipulate the system in small, discrete steps without triggering a global magnetization reversal or “avalanche”, a process that can be achieved through “clocking” protocols. [74]

1. Clocking in pinwheel ASI

A clocked input encoding scheme for pinwheel ASI has been proposed by Jensen *et al.* [74]. They applied an external magnetic field in a well-chosen direction to selectively affect one of the two pinwheel sublattices at a time. The field magnitude was carefully tuned such that only the magnets with the lowest effective energy barrier \tilde{E}_B – typically those at the boundary of a superferromagnetic domain – would switch. The field direction was then changed to affect the other sublattice. This two-step clocking scheme allows domain wall boundaries to advance one step at a time, thereby enabling intermediate magnetic states.

Furthermore, the pinwheel lattice can be modified to enhance NN interactions, and therefore inter-sublattice interactions, by slightly rotating all magnets by an angle α . However, α should remain below a certain threshold to avoid the formation of anti-ferromagnetic domains instead of superferromagnetic ones. [16] This threshold varies depending on the model used; for the point dipole model used here, α should not exceed $\pm 10^\circ$. [81]

We performed a simple test to visualize the behavior of pinwheel ASI under clocking, as shown in Fig. 6a. All magnets were initially magnetized to the right (red). Clocking cycle A is defined by applying a magnetic field at 49° for 0.5 s, then at -41° for another 0.5 s. Since the switching occurs on nanosecond timescales, this duration is effectively infinite. After applying clocking cycle A six

times, the reverse cycle B was applied six times as well.

Our results are comparable to both experimental and numerical results achieved by Jensen *et al.* [74] for “AB clocking”. Each time cycle A or B is applied, a well-defined effect is visible, though the impact of subsequent B cycles diminishes as the system approaches its initial state. Note that, even though cycle B applies the opposite fields to cycle A , it is not the inverse: the system does not return to the same states previously visited by cycles A . Because of this nonlinear behavior which stores information in the state of the system by avoiding avalanches, this setup has the potential to perform well for reservoir computing purposes. [82]

In summary, two key factors are necessary for controlled domain wall movement. First, the degeneracy between the ground states must be lifted, which is straightforward in pinwheel ASI as the four types of superferromagnetic domains respond differently to an in-plane field. Second, two independently addressable sublattices should exist to prevent avalanches; in pinwheel ASI, magnets of the two sublattices are perpendicular to each other, enabling their selective manipulation via in-plane fields.

2. Clocking in OOP square ASI

The concept of clocking can be extended to other ASI lattices that form domains, provided they contain multiple sublattices that can be addressed separately to avoid avalanches. As an example, we devised a clocking protocol for OOP square ASI based on the lessons learnt from pinwheel ASI.

In this system, neighboring magnets prefer anti-parallel alignment, resulting in two degenerate checker-

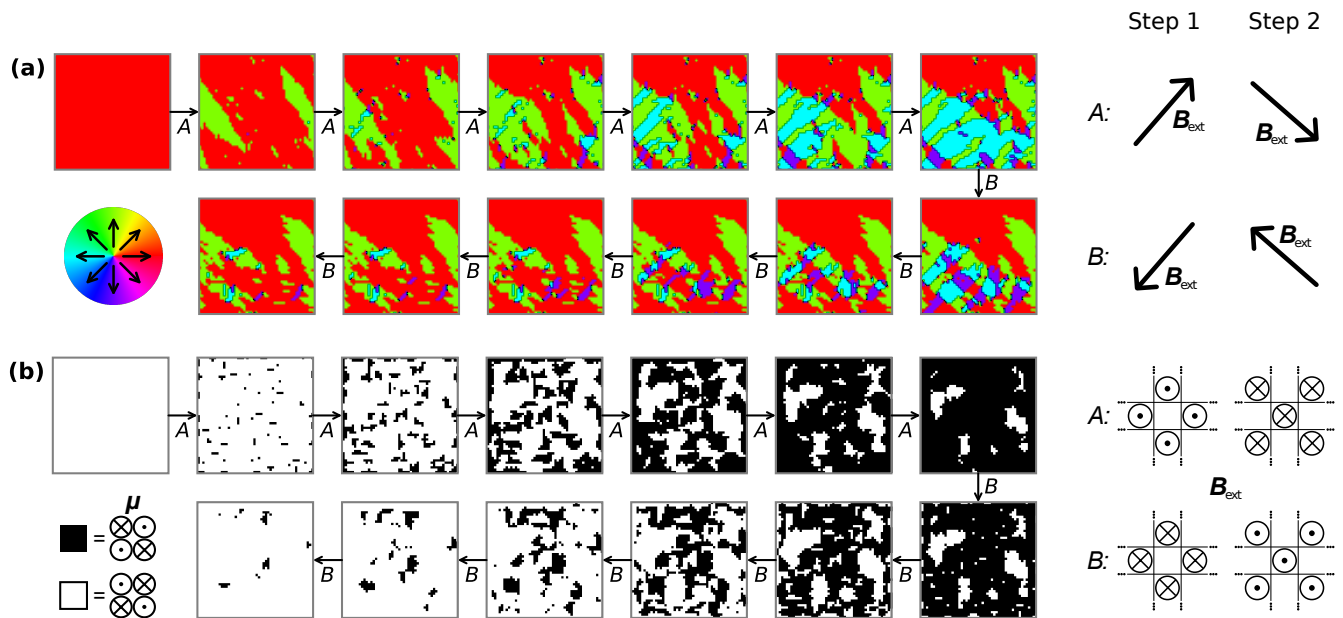


FIG. 6. (a) The clocking behavior of a 101×101 ‘diamond’-edge pinwheel ASI (containing 5100 magnets), with a lattice spacing $a = 248$ nm. Each magnet was rotated by $\alpha = 4^\circ$, has a magnetic moment $\mu = 3 \times 10^{-16}$ A m², and an energy barrier $E_B = 110$ eV with $\sigma(E_B)/\langle E_B \rangle = 5\%$ standard deviation. The asymmetric energy barrier was accounted for with $\rho = 0.4$. All magnets are initially magnetized to the right (red). Clocking cycle *A* is applied six times, defined by applying a magnetic field with magnitude $B_{\text{ext}} = 60.5$ mT at 49° for 0.5 s, then at -41° for another 0.5 s. Afterwards, the reverse cycle *B* is applied six times, with angles 229° and 139° . (b) A similar simulation for a 50×50 OOP square ASI, with circular magnets of radius 85 nm and a lattice spacing $a = 200$ nm. Each magnet has a magnetic moment $\mu = 1.6 \times 10^{-16}$ A m² and energy barrier $E_B = 60$ eV $\pm 5\%$, similar to the OOP magnets used in Ref. [41]. All magnets are initially magnetized in one of the antiferromagnetic ground states (black). The magnetic field used in the clocking cycles has a magnitude $B_{\text{ext}} = 48$ mT, and each step is applied for 0.5 s.

board ground states. One can therefore consider two sublattices – akin to the black and white squares on a chess board. A uniform external field cannot move the domain walls because the domains have net zero magnetization. Instead, by applying opposite magnetic fields to each sublattice, domains of one type can be made to grow while the other shrinks. However, clocking also requires that only one sublattice is affected at a time. This can be achieved by first applying the field to one sublattice, removing it, and then applying an opposite field to the other sublattice. This procedure causes the domain walls to shift by up to two magnets per cycle, as demonstrated in Fig. 6b, where the gradual expansion of the desired domain type is clearly visible.

Implementing this procedure requires the use of local fields, which is more challenging than the global fields used for clocking pinwheel ASI. One potential solution is to use spin-orbit torque to flip the magnets, using current lines placed diagonally across the ASI to selectively affect one sublattice at a time. This clocking scheme benefits from disorder in the system (e.g., $\sigma(E_B) > 0$ or vacancies), as this provides nucleation sites within the bulk.

V. CONCLUSION

We have presented in detail the underlying models used by Hotspice, an open-source and easily extensible Monte Carlo simulator designed to simulate ASI dynamics. In particular, we focused on the evaluation of several model variants extending beyond the basic Ising model typically used for ASI simulations.

Firstly, we considered more accurate calculations for magnetostatic interactions: OOP systems were found to benefit from a second-order correction, while IP systems achieve far more accurate results with a dumbbell model. Secondly, accounting for asymmetric switching channels proved key to correctly reproduce coercive fields in pinwheel ASI, for example, provided the reduced magnetization during non-coherent reversal processes was also accounted for. Finally, we provided two algorithms for handling switching events: the Néel-Arrhenius approach, best suited for simulating the temporal evolution of the system, including out-of-equilibrium dynamics, and the Metropolis-Hastings algorithm, which efficiently explores equilibrium configurations, especially when multiple magnets switch simultaneously. These methods were compared to experimental and theoretical results for pinwheel, kagome, and OOP square ASI.

This approach makes Hotspice complementary to traditional micromagnetic simulations: its higher-level approximations enable the study of complex ASI dynamics in much larger systems and over significantly longer timescales, though this comes at the cost of sacrificing the detailed simulation of the internal magnetization structure of individual nanomagnets. This opens new opportunities to use ASI for applied machine learning tasks, such as reservoir computing (RC). The software's ability to quickly sweep parameters and evaluate RC metrics facilitates the optimization of ASI configurations and identification of suitable input protocols, as demonstrated by our simulation of clocking protocols in pinwheel and OOP square ASI.

In conclusion, Hotspice's combination of speed, flexibility, and accuracy makes it a powerful platform to explore the rich physics of ASI systems and advance their use in innovative applications like reservoir computing.

ACKNOWLEDGMENTS

The authors acknowledge funding from the SpinENGINE EU FET-Open Horizon 2020 RIA project (No. 861618) and the SHAPEme project (EOS ID 400077525) from the FWO and F.R.S.-FNRS under the Excellence of Science (EOS) program. J. L. is supported by the Research Foundation – Flanders (FWO) through senior postdoctoral research fellowship No. 12W7622N.

CODE AVAILABILITY

Hotspice is open-source and available on GitHub.

-
- [1] *Reservoir Computing in Artificial Spin Ice*, ALIFE 2021: The 2021 Conference on Artificial Life, Vol. ALIFE 2020: The 2020 Conference on Artificial Life (2020) https://direct.mit.edu/isal/proceedings-pdf/isal2020/32/376/1908630/isal_a_00268.pdf.
- [2] J. H. Jensen, A. Strømberg, O. R. Lykkebø, A. Penty, J. Leliaert, M. Sjölander, E. Folven, and G. Tufte, *Physical Review B* **106**, 064408 (2022).
- [3] C. Nisoli, R. Moessner, and P. Schiffer, *Reviews of Modern Physics* **85**, 1473 (2013).
- [4] W. F. Brown, *Phys. Rev.* **130**, 1677 (1963).
- [5] L. Néel, in *Annales de géophysique*, Vol. 5 (1949) pp. 99–136.
- [6] C. Kittel, *Phys. Rev.* **70**, 965 (1946).
- [7] P. Politi and M. G. Pini, *Physical Review B* **66**, 214414 (2002).
- [8] V. Zayets, Thermally activated magnetization reversal in a fecob nanomagnet. high-precision measurement method of coercive field, delta, retention time and size of nucleation domain (2019).
- [9] A. Manchon, J. Železný, I. M. Miron, T. Jungwirth, J. Sinova, A. Thiaville, K. Garello, and P. Gambardella, *Rev. Mod. Phys.* **91**, 035004 (2019).
- [10] A. Brataas, A. D. Kent, and H. Ohno, *Nature materials* **11**, 372 (2012).
- [11] A. P. Ramirez, A. Hayashi, R. J. Cava, R. Siddharthan, and B. Shastri, *Nature* **399**, 333 (1999).
- [12] L. J. Heyderman and R. L. Stamps, *Journal of Physics: Condensed Matter* **25**, 363201 (2013).
- [13] S. Lendinez and M. Jungfleisch, *Journal of Physics: Condensed Matter* **32**, 013001 (2019).
- [14] S. H. Skjærø, C. H. Marrows, R. L. Stamps, and L. J. Heyderman, *Nature Reviews Physics* **2**, 13 (2020).
- [15] *Computation in artificial spin ice*, ALIFE 2021: The 2021 Conference on Artificial Life, Vol. ALIFE 2018: The 2018 Conference on Artificial Life (2018) https://direct.mit.edu/isal/proceedings-pdf/alife2018/30/15/1904940/isal_a_00011.pdf.
- [16] R. Macêdo, G. Macauley, F. Nascimento, and R. Stamps, *Physical Review B* **98**, 014437 (2018).
- [17] M. Freeman and B. Choi, *Science* **294**, 1484 (2001).
- [18] J. Sklenar, Y. Lao, A. Albrecht, J. D. Watts, C. Nisoli, G.-W. Chern, and P. Schiffer, *Nature Physics* **15**, 191 (2019).
- [19] V. Kapaklis, U. B. Arnalds, A. Harman-Clarke, E. T. Papaioannou, M. Karimipour, P. Korelis, A. Taroni, P. C. Holdsworth, S. T. Bramwell, and B. Hjörvarsson, *New Journal of Physics* **14**, 035009 (2012).
- [20] K. Hofhuis, S. H. Skjærø, S. Parchenko, H. Arava, Z. Luo, A. Kleibert, P. M. Derlet, and L. J. Heyderman, *Nature Physics* , 1 (2022).
- [21] O. Sendetskyi, V. Scagnoli, N. Leo, L. Anghinolfi, A. Alberca, J. Lüning, U. Staub, P. M. Derlet, and L. J. Heyderman, *Physical Review B* **99**, 214430 (2019).
- [22] H. Lou, W.-C. Yue, Z. Yuan, P. Huang, Y. Chen, Y.-L. Wang, S. Zhang, and D. Shi, *Physical Review B* **108**, 184433 (2023).
- [23] W. Branford, S. Ladak, D. E. Read, K. Zeissler, and L. Cohen, *Science* **335**, 1597 (2012).
- [24] . R. Wang, C. Nisoli, R. Freitas, J. Li, W. McConville, B. Cooley, M. Lund, N. Samarth, C. Leighton, V. Crespi, *et al.*, *Nature* **439**, 303 (2006).
- [25] M. J. Morrison, T. R. Nelson, and C. Nisoli, *New Journal of Physics* **15**, 045009 (2013).
- [26] S. Ladak, D. Read, G. Perkins, L. Cohen, and W. Branford, *Nature Physics* **6**, 359 (2010).
- [27] E. Mengotti, L. J. Heyderman, A. F. Rodríguez, F. Noltling, R. V. Hügli, and H.-B. Braun, *Nature Physics* **7**, 68 (2011).
- [28] S. Gliga, G. Hrkac, C. Donnelly, J. Büchi, A. Kleibert, J. Cui, A. Farhan, E. Kirk, R. V. Chopdekar, Y. Masaki, *et al.*, *Nature materials* **16**, 1106 (2017).
- [29] L. J. Heyderman, *Nature Nanotechnology* , 1 (2022).
- [30] H. Arava, P. M. Derlet, J. Vijayakumar, J. Cui, N. S. Bingham, A. Kleibert, and L. J. Heyderman, *Nanotechnology* **29**, 265205 (2018).
- [31] P. Gypens, J. Leliaert, and B. Van Waeyenberge, *Physical Review Applied* **9**, 034004 (2018).
- [32] H. Arava, N. Leo, D. Schildknecht, J. Cui, J. Vijayakumar, P. M. Derlet, A. Kleibert, and L. J. Heyderman,

- Phys. Rev. Appl. **11**, 054086 (2019).
- [33] G. Tanaka, T. Yamane, J. B. Héroux, R. Nakane, N. Kanazawa, S. Takeda, H. Numata, D. Nakano, and A. Hirose, *Neural Networks* **115**, 100 (2019).
- [34] A. Vansteenkiste, J. Leliaert, M. Dvornik, M. Helsen, F. Garcia-Sanchez, and B. Van Waeyenberge, *AIP Advances* **4**, 107133 (2014).
- [35] M. J. Donahue and D. G. Porter, *Oommf user's guide*, version 1.0 (1999).
- [36] T. Fischbacher, M. Franchin, G. Bordignon, and H. Fangohr, *IEEE Transactions on Magnetics* **43**, 2896 (2007).
- [37] N. Leo, M. Pancaldi, S. Koraltan, P. V. González, C. Abert, C. Vogler, F. Slanovc, F. Bruckner, P. Heistracher, K. Hofhuis, *et al.*, *New Journal of Physics* **23**, 033024 (2021).
- [38] C. Tannous and J. Gieraltowski, *European Journal of Physics* **29**, 475 (2008).
- [39] I. Gilbert, G.-W. Chern, S. Zhang, L. O'Brien, B. Fore, C. Nisoli, and P. Schiffer, *Nature Physics* **10**, 670 (2014).
- [40] S. Zhang, I. Gilbert, C. Nisoli, G.-W. Chern, M. J. Erickson, L. O'Brien, C. Leighton, P. E. Lammert, V. H. Crespi, and P. Schiffer, *Nature* **500**, 553 (2013).
- [41] A. Kurenkov, J. Maes, A. Pac, G. M. Macauley, B. V. Waeyenberge, A. Hrabec, and L. J. Heyderman, Perpendicular-anisotropy artificial spin ice with spontaneous ordering: a platform for neuromorphic computing with flexible timescales (2024), arXiv:2408.12182 [cond-mat.mes-hall].
- [42] C. Castelnuovo, R. Moessner, and S. L. Sondhi, *Nature* **451**, 42 (2008).
- [43] L. D. C. Jaubert and P. C. W. Holdsworth, *Journal of Physics: Condensed Matter* **23**, 164222 (2011).
- [44] D. De Gusem, *Multiscale Modelling of Artificial Spin Ice*, Master's thesis, Ghent University (2024).
- [45] T. H. Boyer *et al.*, *American Journal of Physics* **56**, 688 (1988).
- [46] A. Jansen, *Physical Review B* **69**, 035414 (2004).
- [47] S. Koraltan, M. Pancaldi, N. Leo, C. Abert, C. Vogler, K. Hofhuis, F. Slanovc, F. Bruckner, P. Heistracher, M. Menniti, *et al.*, *Physical Review B* **102**, 064410 (2020).
- [48] M. Baumgartner, K. Garello, J. Mendil, C. O. Avci, E. Grimaldi, C. Murer, J. Feng, M. Gabureac, C. Stamm, Y. Acremann, *et al.*, *Nature nanotechnology* **12**, 980 (2017).
- [49] J. A. Osborn, *Phys. Rev.* **67**, 351 (1945).
- [50] J. C. Maxwell, *Electricity and magnetism*, Vol. 2 (Dover New York, 1954).
- [51] S. A. Serebrinsky, *Physical Review E* **83**, 037701 (2011).
- [52] J.-C. Walter and G. Barkema, *Physica A: Statistical Mechanics and its Applications* **418**, 78 (2015).
- [53] C. Bean and u. D. Livingston, *Journal of Applied Physics* **30**, S120 (1959).
- [54] J. Maes, J. Leliaert, and B. Van Waeyenberge, *Biaxial nanomagnets as building block for balanced half-adders*, Master's thesis, Ghent University (2021).
- [55] E.-A. Kyimba *et al.*, *Comparison of Monte Carlo Metropolis, Swendsen-Wang, and Wolff Algorithms in the Critical Region for the 2-dimensional Ising Model*, Master's thesis, North Carolina State University, Raleigh, North Carolina (2006).
- [56] H. Jang, M. J. Grimson, and T. B. Woolf, *Physical Review E* **70**, 047101 (2004).
- [57] A. Bortz, M. Kalos, and J. Lebowitz, *Journal of Computational Physics* **17**, 10 (1975).
- [58] A. Sadiq, *Journal of Computational Physics* **55**, 387 (1984).
- [59] K. Binder, D. W. Heermann, and K. Binder, *Monte Carlo simulation in statistical physics*, Vol. 8 (Springer, 1992).
- [60] V. Ostromoukhov, in *ACM SIGGRAPH 2007 papers* (2007) pp. 78–es.
- [61] A. Lagae and P. Dutré, in *Computer Graphics Forum*, Vol. 27 (Wiley Online Library, 2008) pp. 114–129.
- [62] R. Bridson, *SIGGRAPH sketches* **10** (2007).
- [63] L.-Y. Wei, *Acm Transactions On Graphics (tog)* **27**, 1 (2008).
- [64] R. J. Baxter, *Exactly solved models in statistical mechanics* (Courier Corporation, 2007).
- [65] E. W. Montroll, R. B. Potts, and J. C. Ward, *Journal of Mathematical Physics* **4**, 308 (1963).
- [66] C. N. Yang, *Physical Review* **85**, 808 (1952).
- [67] J. M. Coey, *Magnetism and magnetic materials* (Cambridge university press, 2010).
- [68] M. E. Newman and G. T. Barkema, *Monte Carlo methods in statistical physics* (Clarendon Press, 1999).
- [69] D. Girardi and N. Branco, *Journal of Statistical Mechanics: Theory and Experiment* **2010**, P04012 (2010).
- [70] L. Böttcher and H. J. Herrmann, *Computational Statistical Physics* (Cambridge University Press, 2021).
- [71] W. Krauth, *Statistical mechanics: algorithms and computations*, Vol. 13 (OUP Oxford, 2006).
- [72] U. Wolff, *Phys. Rev. Lett.* **62**, 361 (1989).
- [73] A. B. MacIsaac, J. P. Whitehead, M. C. Robinson, and K. De'Bell, *Phys. Rev. B* **51**, 16033 (1995).
- [74] J. H. Jensen, A. Strømberg, I. Breivik, A. Penty, M. A. Niño, M. W. Khaliq, M. Foerster, G. Tufte, and E. Folven, *Nature Communications* **15**, 964 (2024).
- [75] Y. Li, G. W. Paterson, G. M. Macauley, F. S. Nascimento, C. Ferguson, S. A. Morley, M. C. Rosamond, E. H. Linfield, D. A. MacLaren, R. Macedo, *et al.*, *ACS nano* **13**, 2213 (2018).
- [76] R. D. Fraleigh, S. Kempinger, P. E. Lammert, S. Zhang, V. H. Crespi, P. Schiffer, and N. Samarth, *Physical Review B* **95**, 144416 (2017).
- [77] S. A. Morley, D. Alba Venero, J. M. Porro, S. T. Riley, A. Stein, P. Steadman, R. L. Stamps, S. Langridge, and C. H. Marrows, *Phys. Rev. B* **95**, 104422 (2017).
- [78] D. Verstraeten, B. Schrauwen, M. D'Haene, and D. Stroobandt, *Neural Networks and Liquid State Machines*, **20**, 391 (2007), echo State Networks and Liquid State Machines.
- [79] W. Maass, T. Natschläger, and H. Markram, *Neural Computation* **14**, 2531 (2002).
- [80] K. Hon, Y. Kuwabiraki, M. Goto, R. Nakatani, Y. Suzuki, and H. Nomura, *Applied Physics Express* **14**, 033001 (2021).
- [81] A. Strømberg, E. Digernes, R. V. Chopdekar, J. Grepstad, and E. Folven, On the antiferromagnetic-ferromagnetic phase transition in pinwheel artificial spin ice (2024), arXiv:2404.03973 [cond-mat.mes-hall].
- [82] I. Lateur, *Modelling Artificial Spin Ice for Reservoir Computing*, Master's thesis, Ghent University (2023).

The design, verification, and applications of Hotspice: a Monte Carlo simulator for artificial spin ice

Jonathan Maes¹,²,³ Diego De Gusem¹,²,³ Ian Lateur¹, Jonathan Leliaert¹, Aleksandr Kurenkov^{2,3} and Bartel Van Waeyenberge¹

¹DyNaMat, Department of Solid State Sciences, Ghent University, 9000 Ghent, Belgium

²Laboratory for Mesoscopic Systems, Department of Materials, ETH Zurich, 8093 Zurich, Switzerland

³Laboratory for Multiscale Materials Experiments, PSI Center for Neutron and Muon Sciences, Forschungsstrasse 111, 5232 Villigen PSI, Switzerland

(Dated: September 10, 2024)

SUPPLEMENTARY INFORMATION

S1. CODE EXAMPLES

The code used for the simulations presented in the main text is provided below. These are cleaned versions without plotting code, and not all `run()` functions return all the data shown in the figure. The full scripts, including plotting functions, can be found in the GitHub repository.

A. Exchange-coupled OOP square system

The following code was used for the simulation shown in Fig. 3a and 3b of the main text. It calculates the temperature-dependence of the average magnetization $\langle M \rangle / M_0 = \sum_i s_i / N$ and the nearest-neighbor correlation $\langle S_i S_{i+1} \rangle$ in an exchange-coupled OOP square ASI. Due to the absence of magnetostatic interactions, this simulation can significantly benefit from multi-switching using the Metropolis algorithm. Therefore, the simulation is performed on the GPU by setting the environment variable "HOTSPICE_USE_GPU" to "True".

```
1 import numpy as np
2
3 import os
4 os.environ["HOTSPICE_USE_GPU"] = "True" # We use Metropolis for multi-sampling on GPU
5 import hotspice
6
7
8 def run(T_range=np.linspace(0.9, 1.1, 21), N: int = 100, size: int = 800):
9     """ 'T_range' specifies the examined temperature range in multiples of T_c.
10         At each step, 'N' Monte Carlo steps per site are performed.
11         There will be <size>*<size> magnets.
12     """
13     a = 1 # Choose large spacing to get many simultaneous Metropolis switches
14     T_c = 1 # T_c = 2*J/(k_B*np.log(1+np.sqrt(2))), or the other way around:
15     J = T_c*hotspice.kB*np.log(1 + np.sqrt(2))/2
16
17     N_saved_iters = int(np.ceil(N/2)) # Half of N iters gets saved
18     observable_shape = (T_range.size, N_saved_iters)
19     m_avg = np.empty(observable_shape)
20     NNcorr_avg = np.empty(observable_shape)
21
22     mm = hotspice.ASI.OOP_Square(a, size, energies=[hotspice.ExchangeEnergy(J=J)],
23                                 pattern='uniform', PBC=True, T=1)
24     mm.params.UPDATE_SCHEME = hotspice.Scheme.METROPOLIS
25     for i, T in enumerate(T_range):
26         mm.T = T*T_c
27         mm.progress(t_max=np.inf, MCsteps_max=N/2) # Equilibrate for N/2 steps
28         for j in range(N_saved_iters):
29             mm.progress(t_max=np.inf, MCsteps_max=1)
30             m_avg[i,j] = mm.m_avg
```

```

31         NNcorr_avg[i,j] = mm.correlation_NN()
32     return m_avg, NNcorr_avg
33
34
35 if __name__ == "__main__":
36     size = 800 # With GPU+Metropolis, there is no reason to use size<800 here
37     for N in [10, 100, 1600]:
38         run(N=N, size=size)

```

B. Exchange- and magnetostatically coupled OOP square system

The following code was used for the simulation shown in Fig. 3c of the main text. It calculates the nearest-neighbor correlation $\langle S_i S_{i+1} \rangle$ in an OOP square ASI, where magnets are both magnetostatically and exchange-coupled. The effect of varying the relative strength of the exchange coupling with respect to the nearest-neighbor magnetostatic coupling: $\delta = E_{\text{exch},i,j}/E_{\text{MS},i,j} (j \in \mathcal{N}_i)$.

```

1 import numpy as np
2
3 import os
4 os.environ["HOTSPICE_USE_GPU"] = "True" # We use Metropolis for multi-sampling on GPU
5 import hotspice
6
7
8 def run(delta_range=np.linspace(0, 4, 81), N: float = 100, size: int = 200):
9     """ 'T_range' specifies the examined temperature range in multiples of T_c.
10         At each step, 'N' calls of 'Magnets.update()' are performed.
11         There will be <size>*<size> magnets.
12     """
13     T, a = 50, 1e-6 # A combination that is NOT in the paramagnetic state
14
15     corr_avg, corr_std = np.empty_like(delta_range), np.empty_like(delta_range)
16     states = np.empty(shape=(delta_range.size, size, size), dtype=bool)
17
18     energyDD, energyExch = hotspice.DipolarEnergy(), hotspice.ExchangeEnergy()
19     mm = hotspice.ASI.OOP_Square(a, size, E_B=0, T=T, energies=[energyDD, energyExch],
20                               pattern='AFM', PBC=True)
21     mm.params.UPDATE_SCHEME = hotspice.Scheme.METROPOLIS
22     for i, delta in enumerate(delta_range):
23         energyExch.J = delta*energyDD.get_NN_interaction()/2 # Set delta by changing J
24         corrs = [mm.correlation_NN()
25                 for _ in mm.progress(t_max=np.inf, MCsteps_max=N, Q=np.inf)]
26         half = len(corrs) // 2
27         corr_avg[i], corr_std[i] = np.mean(corrs[half:]), np.std(corrs[half:])
28         states[i,:,:] = (hotspice.utils.asnumpy(mm.m) + 1).astype(bool)
29     return corr_avg, corr_std, states
30
31
32 if __name__ == "__main__":
33     run()

```

C. Pinwheel reversal

The following code was used for the simulation shown in Fig. 4 of the main text. It performs a hysteresis on pinwheel ASI, for a range of the parameter $\rho = m_{\perp}/m_{\parallel}$, illustrating the importance of this parameter. The nanomagnet parameters were derived from the experimental setup in [?].

```

1 import numpy as np
2 import hotspice
3
4

```



```

5 def run(size: int = 50, m_perp_factor: float = 1,
6         monopoles: bool = False, angle: float = np.pi/6):
7     """ A system size of 50 gives the exact same geometry as in the experiment, but
8         with the x- and y-axes flipped. However, the experiment also defines the angle
9         clockwise from the y-axis, which is therefore the same as our 'B_angle'.
10    """
11    ## Basic system: 50x50 system of 470x170x10nm magnets, 420nm NN spacing
12    l, d, t, Msat = 470e-9, 170e-9, 10e-9, 800e3
13    moment = Msat*((d*d*np.pi/4) + (1-d)*d)*t # [Am^2] moment of stadium-shaped magnet
14    a = 420e-9*np.sqrt(2) # [m] Lattice spacing (for 420nm NN spacing in Pinwheel)
15    T = 300 # [K] Assume room temperature
16    E_B = hotspice.utils.eV_to_J(71) # [J] Energy barrier, calculated with mumax3
17    E_B_std = 0.07
18
19    ## CREATE ASI
20    if monopoles: energyDD = hotspice.energies.DiMonopolarEnergy(d=0.9*l, small_d=0.9*d)
21    else: energyDD = hotspice.energies.DipolarEnergy()
22    energyZ = hotspice.ZeemanEnergy()
23    mm = hotspice.ASI.IP_Pinwheel(a, size, moment=moment, E_B=E_B, E_B_std=E_B_std,
24                                T=T, PBC=False, m_perp_factor=m_perp_factor,
25                                energies=[energyDD, energyZ])
26    mm.params.UPDATE_SCHEME = hotspice.Scheme.NEEL
27
28    ## PERFORM HYSTERESIS
29    B_max = 0.1 # [T] The hysteresis occurs between '-B_max' -> 'B_max' -> '-B_max'.
30    _N = 20000 # Number of 'mm.update()' steps between 'B_max' and '-B_max'.
31    B_fields = np.linspace(-B_max, B_max, _N) # One sweep to opposite fields (N steps)
32    B_fields = np.append(B_fields, np.flip(B_fields)) # Sweep both ways (2*N steps)
33    m_avg, m_angle = np.zeros_like(B_fields), np.zeros_like(B_fields)
34
35    mm.initialize_m(pattern='uniform', angle=angle+np.pi) # Initialize along field
36    for i, B in enumerate(B_fields):
37        energyZ.set_field(angle=angle, magnitude=B)
38        mm.progress()
39        m_avg[i], m_angle[i] = mm.m_avg, mm.m_avg_angle
40    return B_fields, m_avg, m_angle
41
42 if __name__ == "__main__":
43     for m_perp_factor in [0, 0.4, 1]:
44         run(m_perp_factor=m_perp_factor)

```

D. Kagome reversal

The following code was used for the simulation shown in Fig. 5 of the main text. It performs a reversal of kagome ASI, using both the point dipole and monopole representations, which affect the calculation of the magnetostatic energy. The nanomagnet parameters were derived from the experimental setup in [?].

```

1 import numpy as np
2 import hotspice
3
4
5 def run(size: int = 30, monopoles: bool = True, angle: float = np.pi/2 - 3.6*np.pi/180,
6         E_B: float = hotspice.utils.eV_to_J(120), E_B_std: float = 0.05):
7     """ Mumax upper bound for the energy barrier is 250eV,
8         for the magnet geometry used in the experiment.
9     """
10    a = 1e-6 # Gives 500nm NN center-to-center distance
11    d = 470e-9 # Must be <577.35e-9, otherwise neighbors touch
12    moment = 1.1e-15
13
14    _N = 2000 # Number of 'mm.update()' steps between 'B_max' and '-B_max'.
15    B_max = 0.06 # [T] The hysteresis occurs between '-B_max' -> 'B_max' -> '-B_max'.

```

```

16 B_fields = np.linspace(B_max, -B_max, _N) # One sweep to opposite fields (N steps)
17 B_fields = np.append(B_fields, np.flip(B_fields)) # Sweep both ways (2*N steps)
18
19 if monopoles: energyDD = hotspice.energies.DiMonopolarEnergy(d=d)
20 else: energyDD = hotspice.energies.DipolarEnergy()
21 energyZ = hotspice.ZeemanEnergy(angle=angle)
22 mm = hotspice.ASI.IP_Kagome(a, size, moment=moment, energies=[energyDD, energyZ],
23                             E_B=E_B, E_B_std=E_B_std, m_perp_factor=0)
24 mm.params.UPDATE_SCHEME = hotspice.Scheme.NEEL
25
26 ## Perform the reversal
27 mm.initialize_m("uniform", angle=angle)
28 M_S = mm.m_avg_y
29
30 M_y = np.zeros_like(B_fields)
31 for i, B in enumerate(B_fields):
32     energyZ.magnitude = B
33     mm.progress()
34     M_y[i] = mm.m_avg_y/M_S
35
36 ## Identify the critical field magnitude
37 for i, _ in enumerate(M_y): # Identify the critical field magnitude
38     if (M_y[i] <= 0 < M_y[i + 1]) or (M_y[i] >= 0 > M_y[i + 1]):
39         B_C = np.abs(B_fields[i] - (M_y[i]*(B_fields[i+1] - B_fields[i]))
40                     /(M_y[i+1] - M_y[i]))
41         break
42
43 ## Save states at certain field magnitudes
44 states, fields = [], [-0.85, -0.92, -0.99, -1.06]
45 for B in fields:
46     energyZ.magnitude = B*B_C
47     mm.progress()
48     states.append(np.where(mm.occupation == 0, np.nan, mm.m))
49 return states, fields
50
51 if __name__ == "__main__":
52     run(monopoles=False)
53     run(monopoles=True)

```

E. Pinwheel clocking

The following code was used for the simulation shown in Fig. 6a of the main text. It demonstrates the use of the `hotspice.io` module to apply clocked input to pinwheel ASI by defining a custom `Datastream` and `Inputter`. These are then used to apply the clocking cycles A and B as described in the main text. The nanomagnet parameters were derived from the experimental setup in [?].

```

1 import numpy as np
2 import hotspice
3
4
5 class BinaryListDatastream(hotspice.io.BinaryDatastream):
6     """ Returns values from a given list. """
7     def __init__(self, binary_list: list[int] = [0]):
8         self.binary_list = binary_list
9         self.len_list = len(binary_list) # will be used often, no need to recalculate
10        self.index = 0 # start at the beginning
11        super().__init__()
12
13    def get_next(self, n=1) -> np.ndarray:
14        """ Returns next 'n' values as xp.ndarray. Loops back to start at the end. """
15        values = [self.binary_list[(self.index + i) % self.len_list] for i in range(n)]
16        self.index += n

```

```

17     return np.array(values)
18
19
20 class ClockingFieldInputter(hotspice.io.FieldInputter):
21     def __init__(self, datastream: hotspice.io.BinaryDatastream, magnitude=1,
22                 angle=0, spread=np.pi/8, n=2, frequency=1):
23         """ Applies an external field at 'angle+spread' rad for 0.5/frequency seconds,
24             then at 'angle-spread' rad for bit 0. It does the same +180deg for bit 1.
25             This avoids avalanches by only affecting one sublattice at a time.
26         """
27         self.spread = spread
28         super().__init__(datastream, magnitude=magnitude,
29                         angle=angle, n=n, frequency=frequency)
30
31     def bit_to_angles(self, bit):
32         if not bit:
33             return (self.angle + self.spread, self.angle - self.spread)
34         return (self.angle + self.spread + np.pi, self.angle - self.spread + np.pi)
35
36     def input_single(self, mm: hotspice.ASI.IP_ASI, value: bool|int):
37         if self.frequency and mm.params.UPDATE_SCHEME != hotspice.Scheme.NEEL:
38             raise AttributeError("Can only use frequency if UPDATE_SCHEME is NEEL.")
39         if not mm.in_plane:
40             raise AttributeError("Can only use ClockingFieldInputter on in-plane ASI.")
41
42         Zeeman: hotspice.ZeemanEnergy = mm.get_energy('Zeeman')
43         if Zeeman is None: mm.add_energy(Zeeman := hotspice.ZeemanEnergy(0, 0))
44         angle1, angle2 = self.bit_to_angles(value)
45         Zeeman.set_field(magnitude=self.magnitude, angle=angle1)
46         mm.progress(t_max=0.5/self.frequency, MCsteps_max=self.n)
47         Zeeman.set_field(magnitude=self.magnitude, angle=angle2)
48         mm.progress(t_max=0.5/self.frequency, MCsteps_max=self.n)
49
50
51 def run(N: int = 13, size: int = 101, E_B_std: float = 0.05,
52        m_perp_factor: float = 0.4, magnitude: float = 53e-3):
53     """ A system size of 101 gives the same geometry as the experimental system used
54         in the original clocking paper "Clocked dynamics in Artificial Spin Ice".
55     """
56     ## Basic 101x101 system
57     a = 248e-9 # Lattice spacing
58     moment = 3e-16
59     T = 1 # For deterministic switching
60     E_B = hotspice.utils.eV_to_J(110)
61     np.random.seed(2) # 2 gives a nice result.
62
63     spread = np.pi/4 # We use 45deg instead of the 22.5deg used in the Clocking paper.
64     bits = [None] + [1]*(N//2) + [0]*(N//2)
65     datastream = BinaryListDatastream(bits)
66     inputter = ClockingFieldInputter(datastream, magnitude=magnitude, spread=spread)
67     lattice_angle = np.deg2rad(4) # Rotate all magnets by 4deg
68     mm = hotspice.ASI.IP_Pinwheel(a, size, moment=moment, E_B=E_B, E_B_std=E_B_std,
69                                  T=T, pattern="uniform", angle=lattice_angle,
70                                  m_perp_factor=m_perp_factor)
71     mm.params.UPDATE_SCHEME = hotspice.Scheme.NEEL # NEEL is best at low T and high E_B
72     mm.add_energy(hotspice.ZeemanEnergy())
73
74     states = []
75     for bit in datastream.binary_list:
76         if bit is not None: inputter.input(mm, values=[bit])
77         states.append(np.copy(mm.m))
78     return states
79
80 if __name__ == "__main__":

```

```
81 | run(m_perp_factor=0.4)
```

F. OOP square clocking

The following code was used for the simulation shown in Fig. 6b of the main text. It demonstrates a clocking protocol for OOP square ASI, available in the standard Hotspice distribution. The code applies the clocking cycles A and B as described in the main text.

```

1 | import numpy as np
2 | import hotspice
3 |
4 |
5 | def run(N: int = 13, magnitude: float = 0.05, E_B_std: float = 0.05,
6 |         E_B: float = hotspice.utils.eV_to_J(60), moment: float = 2.37e-16,
7 |         a: float = 230e-9, d: float = 0, vacancy_fraction: float = 0., size: int = 50):
8 |     mm = hotspice.ASI.OOP_Square(a, size, E_B=E_B, E_B_std=E_B_std,
9 |                                moment=moment, major_axis=d, minor_axis=d)
10 |    mm.params.UPDATE_SCHEME = hotspice.Scheme.NEEL
11 |    mm.add_energy(hotspice.ZeemanEnergy())
12 |    vacancies = int(mm.n*vacancy_fraction)
13 |    mm.occupation[np.random.randint(mm.ny, size=vacancies),
14 |                 np.random.randint(mm.nx, size=vacancies)] = 0
15 |    ds = hotspice.io.RandomBinaryDatastream()
16 |    inputter = hotspice.io.OOPSquareChessStepsInputter(ds, magnitude=magnitude)
17 |
18 |    states, domains = [], []
19 |    values = []
20 |    mm.initialize_m('AFM', angle=np.pi)
21 |    for i in range(N):
22 |        if i == 0: values.append(None)
23 |        else: values.append(inputter.input(mm, values=(i < (N//2 + 1)))[0])
24 |        states.append(np.where(mm.occupation == 0, np.nan, mm.m))
25 |        domains.append(np.where(mm.occupation == 0, np.nan, mm.get_domains()))
26 |    return states, domains
27 |
28 | if __name__ == "__main__":
29 |     run(magnitude=0.048, a=200e-9, d=170e-9)

```