

Elementary theory of Magnetoferrons: bringing magnons and ferrons together in multiferroic systems

Mario A. Castro¹, Carlos Saji¹, Guidobeth Saez¹, Patricio Vergara¹, Sebastian Allende^{2,3}, and Alvaro S. Nunez¹

¹*Departamento de Física, FCFM, Universidad de Chile, Santiago, Chile.*

²*Departamento de Física, Universidad de Santiago de Chile, 9170124, Santiago, Chile. and*

³*Centro de Nanociencia y Nanotecnología CEDENNA, Avda. Ecuador 3493, Santiago, Chile.*

(Dated: December 23, 2024)

The collective excitations of a multiferroic material are analyzed. We show that these excitations also exhibit magnetoelectric behavior, leading to the hybridization of magnons, oscillations of the magnetization field, and ferrons, which are oscillations of the electric dipolar density field. We term these emergent entities 'magnetoferrons', study their main properties, and discuss their potential applications. Additionally, we provide a phenomenological framework for these systems, which will be invaluable for describing the dynamics of the multiferromagnetic state.

Introduction.- The multiferromagnetic phases of matter present excellent prospects for realizing several novel physical effects that could be pivotal for new technological developments[1–4]. One such effect is the magnetoelectric effect[5], in which electric stimuli produce magnetic responses and vice versa[6]. Such a coupling is often regarded as a signature of profound microscopic mechanisms dictating quantum mechanical electronic behavior and, therefore, has received much attention. In this work, we analyze the collective excitations of a multiferroic material and show that they, too, display this magnetoelectric behavior that results in a hybridization of the magnons, oscillations of the magnetization field, and the ferrons, oscillations of the electric dipolar density field. We call these emergent entities magnetoferrons, study their main properties, and discuss their potential applications.

The appearance of massless or gapless Goldstone modes characterizes the phenomenon of spontaneous breaking of continuous symmetries. These modes are related to slow, symmetry-restoring, long-wavelength fluctuations in the order parameter. In crystals, for instance, the vibrational modes known as acoustic phonons[7] are connected to slow fluctuations in the density of the crystal's atoms. Magnons are quantum particles corresponding to Goldstone modes associated with the rotational symmetry destroyed by the ferromagnetic order[8]. They are elementary excitations with a gapless dispersion relation $\omega \sim k^2$, which transport momentum, energy, and magnetization currents. Magnonics[9–17] is an emerging field of research that focuses on the study and manipulation of magnons. These spin waves can carry and process information, making them promising candidates for developing novel, energy-efficient devices and technologies for information processing and communication.

The field of magnonics explores ways to generate, detect, and manipulate magnons and their associated spin waves. The purpose of this endeavor is to understand the fundamental physics of magnonic phenomena and to develop practical applications, such as magnonic circuits[18–21], logic devices[22, 23], and

Josephson interferometers[24–27], which can operate at high speeds with low power consumption.

Ferrons, theoretically proposed as quantum particles related to the elementary excitations of electric polarization in ferroelectric materials, do not follow this pattern. For ferroelectric, these particles follow a dispersion $k \sim \omega^2 \epsilon(\omega)$, where ϵ corresponds to the dynamic permittivity [28, 29]. Bosonic excitations in ferroelectrics that carry electric dipoles are identified from the phenomenological Landau-Ginzburg-Devonshire theory[30]. Ferrons are shown to exist from the simultaneous action of anharmonicity and broken inversion symmetry. Unlike magnon excitations, which are transverse perturbations of the magnetic order, ferron quasiparticles in displacive ferroelectrics are of the longitudinal kind. Based on the predicted ferron spectrum, temperature-dependent pyroelectric and electrocaloric properties, electric-field-tunable heat and polarization transport, and ferron-photon hybridization are predicted in [29].

In multiferroics[1, 2, 31, 32], magnons and ferrons naturally hybridize, giving rise to magnetoferrons. Magnetoferrons might become handy in several contexts, such as when exploiting the sensitivity of multiferroic materials to electric and magnetic fields. In this sense, they can be used to develop susceptible sensors and actuators that respond to multiple stimuli. Magnetoferrons are different from electromagnons[33, 34], i.e., magnon excitation by oscillatory electric fields of electromagnetic wave perturbations.

From a spintronics point of view, storage devices based on multiferroic components can be envisioned. The dual magnetoelectric properties of multiferroic materials can be leveraged to develop nonvolatile data storage devices where information is encoded in electric polarization and magnetization. In this context, magnetoferrons could provide low-dissipation mechanisms to retrieve written information nondestructively. Finally, magnetoelectric waves can be used to design new types of devices for signal transmission and processing, especially in the microwave frequency range.

Phenomenological theory.- Our selected model is based

on previous work [35–37], where a novel mechanism for multiferroicity was proposed relying on a well-established time reversal (\mathcal{T}) breaking antiferromagnetic model. This model was enhanced by intentionally breaking the space inversion (\mathcal{P}) while keeping the symmetry \mathcal{PT} . Such symmetry breaking gave rise to magnetoelectric features readily interpreted as multiferroic behavior. In this section, we will provide a phenomenological account of those systems that will prove invaluable in addressing the dynamic description of the multiferroic state.

In the Landau theory of ferroelectrics, symmetry requirements are crucial for determining the system's possible phases and properties. Ferroelectrics must break the inversion symmetry to exhibit spontaneous polarization. This means that the crystal structure of the ferroelectric phase lacks a symmetry center. The order parameter in Landau theory is usually the polarization vector \mathbf{P} . The free energy expansion must be invariant under the symmetry operations of the high-symmetry (paraelectric) phase. Given that the free energy of the ferroelectric part can be written as $\mathcal{F}_e(\mathbf{P}) = \left(\frac{A}{2}(\partial_i \mathbf{P})^2 + \frac{\alpha}{2}\mathbf{P}^2 + \frac{\beta}{4}\mathbf{P}^4 + \frac{\gamma}{6}\mathbf{P}^6\right) - \mathbf{E} \cdot \mathbf{P}$. Here, α , β , and γ represent the Landau coefficients that will be regarded as positive. This locates our isolated electric system in the paraelectric phase. In external fields (electric, stress, etc.), additional coupling terms in the free energy expansion can express the Landau-Ginzburg-Devonshire Lagrangian expansion[38].

The Landau theory of ferroelectrics requires that the free energy expansion and all related terms respect the symmetry of the paraelectric phase. This includes considerations of inversion symmetry breaking, proper treatment of the order parameter, and appropriate coupling terms for external fields and mechanical strain. These symmetry requirements are essential for accurately describing ferroelectric materials' phase transitions and properties.

In the Landau theory of antiferromagnets, the description includes both the magnetization field \mathbf{m} and the Néel field \mathbf{n} . The order parameters in antiferromagnets are the magnetization field \mathbf{m} and the Néel field \mathbf{n} . The Néel field \mathbf{n} represents the staggered magnetization, indicating the difference in magnetization between sublattices, while the magnetization field \mathbf{m} represents the net magnetic moment per unit volume.

Just like for the ferroelectric part, symmetry plays a crucial role in the Landau theory of antiferromagnet degrees of freedom. The antiferromagnet order parameter maintains the inversion symmetry, which means that the order parameter \mathbf{n} changes sign under inversion, while \mathbf{m} remains unchanged. This inversion symmetry is essential to define the free energy expansion and the interactions between the order parameters and the external fields[39–41]. The free energy of the antiferromagnetic system can be customarily expressed, up to the lowest

order in the order parameter fields, as $\mathcal{F}_m(\mathbf{n}, \mathbf{m}) = \left(\frac{a}{2}\mathbf{m}^2 + \frac{b}{4}\mathbf{m}^4 + \frac{A}{2}(\partial_i \mathbf{n})^2 - \frac{K}{2}(\mathbf{n} \cdot \mathbf{z})^2 - \mathbf{H} \cdot \mathbf{m}\right)$, where $a > 0$ and $b > 0$ are Landau parameters, A is a Ginzburg-like parameter, K and anisotropy related constant, and \mathbf{H} and external magnetic field. The Lagrangian \mathcal{L} is expanded as a function of both \mathbf{m} and \mathbf{n} , ensuring that all terms respect the symmetry of the crystal[42–44]. The collective Lagrangian density becomes:

$$\mathcal{L} = \frac{\rho}{2}\dot{\mathbf{P}}^2 - \mathcal{F}_e(\mathbf{P}) + s \mathbf{m} \cdot \mathbf{n} \times \dot{\mathbf{n}} - \mathcal{F}_m(\mathbf{n}, \mathbf{m}) - g \mathbf{P} \cdot \mathbf{m} \quad (1)$$

where $s = S/\gamma$, is the spin density over the gyromagnetic ratio. The last term, proportional to g , breaks the system's time-reversal invariance (\mathcal{T}) while simultaneously breaking its inversion-reversal symmetry \mathcal{P} . However, the coupling is \mathcal{PT} invariant. In this sense, it is related to the axion electrodynamics in topological materials[45]. It constitutes a coupling between the ferroelectric and magnetic degrees of freedom, as shown in Fig. (1). When large enough, this coupling introduces a second-order symmetry-breaking transition to a multiferroic state, showing ferroelectricity and magnetism[46]. Needless to say, the specific details of our calculations do not depend on the specific form of this coupling; similar calculations can be achieved for a coupling of the more familiar form $\sim (\mathbf{m} \cdot \mathbf{P})^2$ [32].

The equations of motion can be written as:

$$\begin{aligned} s\dot{\mathbf{n}} &= (\mathbf{f}_m - g \mathbf{P}) \times \mathbf{n} \\ s\dot{\mathbf{m}} &= \mathbf{f}_n \times \mathbf{n} + \mathbf{f}_m \times \mathbf{m} \\ \rho\dot{\mathbf{P}} &= \mathbf{f}_P - g \mathbf{m}, \end{aligned} \quad (2)$$

where $\mathbf{f}_n = -\delta\mathcal{F}_m(\mathbf{n}, \mathbf{m})/\delta\mathbf{n}$ and $\mathbf{f}_P = -\delta\mathcal{F}_e(\mathbf{P})/\delta\mathbf{P}$. These equations constitute the basic mathematical framework for describing the basic magnetoelectric phenomena to be addressed in the remaining work.

Equilibrium conditions.- The energy minimum is attained for $\mathbf{n}_0 = \mathbf{z}$. Depending on the value of g we have $\mathbf{m} = \mathbf{P} = 0$ for $|g| < g_c$ and $\mathbf{m} = m_0 \hat{\mathbf{m}}$ and $\mathbf{P} = P_0 \hat{\mathbf{P}}$ for $|g| > g_c$. In the latter case $\hat{\mathbf{m}} = \text{sign}(g)\hat{\mathbf{P}}$. This transition corresponds to a phase transition from an antiferromagnetic state towards a multiferroic phase. An analysis of the equilibrium conditions, $g m_0 = \alpha P_0 + \beta P_0^2$ and $g P_0 = a m_0 + b m_0^2$, in the vicinity of the transition leads to a critical value $g_c = \sqrt{a\alpha}$. Furthermore, we found that the transition to the multiferroic state is a second-order one. We obtain for $g \gtrsim g_c$: $P_0 = \sqrt{\frac{2\alpha g_c}{a^2\beta + \alpha^2 b}} (g - g_c)^{1/2}$ and $m_0 = \sqrt{\frac{2\alpha g_c}{a^2\beta + \alpha^2 b}} (g - g_c)^{1/2}$.

We add coupling of the electromagnetic field to the energy of the system with $\mathbf{E} \parallel \mathbf{H} \parallel \hat{\mathbf{m}}$. This leads to a contribution of the form $\delta\mathcal{F} = -E P_0 - B m_0$, the susceptibilities of the system can be readily written as:

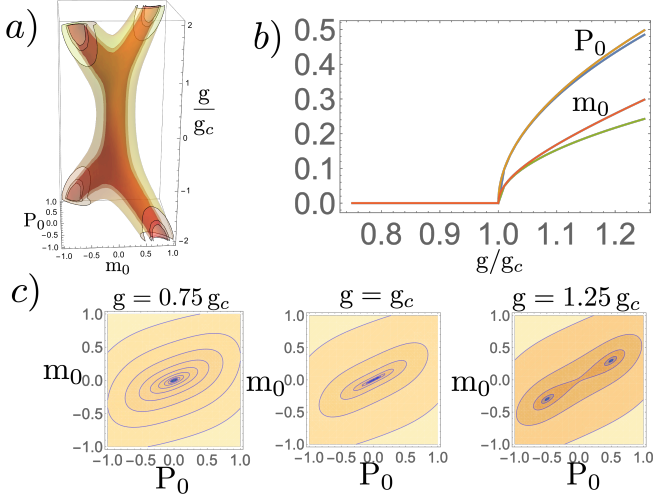


FIG. 1. Stability analysis of the multiferroic state in terms of the coupling parameter g . *a)* Energy levels, in the (m, p, g) -space of the functional energy $\mathcal{F}(m, p, g) - \mathcal{F}_{\min}(g)$. It vividly illustrates the nature of the bifurcation and the origin of the multiferroic state. *b)* Zoom at the bifurcation displaying the pitchfork-like behavior for both polarization and magnetization. Along with the exact numerical results, we attach the results of the Landau analysis that are in great agreement. *c)* Snapshots of the energy levels in (m, p) -space at different values of g , $g < g_c$, $g = g_c$, and $g > g_c$. They illustrate how the transition unfolds.

$$\begin{aligned}\chi_e &= \left(\frac{\partial P_0}{\partial E} \right) = \frac{\mathcal{S}(g/g_c)}{2\alpha|g/g_c - 1|} \\ \chi_m &= \left(\frac{\partial m_0}{\partial B} \right) = \frac{\mathcal{S}(g/g_c)}{2a|g/g_c - 1|} \\ \chi_{me} &= \left(\frac{\partial P_0}{\partial B} \right) = \left(\frac{\partial m_0}{\partial E} \right) = \frac{\mathcal{S}(g/g_c)}{2g_c|g/g_c - 1|},\end{aligned}\quad (3)$$

donde $\mathcal{S}(x) = \begin{cases} 1, & \text{if } x < 1 \\ \frac{1}{2}, & \text{if } x > 1 \end{cases}$. We note that $\chi_{me} = \sqrt{\chi_e \chi_m}$. This is the maximum allowable magneto-electric susceptibility. This bound is achieved through thermodynamical stability requirements[47]. The multiferroic transition displays a divergent magneto-electric susceptibility.

A significant magneto-electric response, where electric and magnetic fields strongly interact, has several key applications in advanced technologies. It enables the de-

velopment of more efficient data storage devices, such as magneto-electric random access memory[48], sensitive sensors for medical and industrial use, and precise actuators for micromachines. In telecommunications, it facilitates the manipulation of compact and energy-efficient RF signals, while in spintronics, it allows faster and more efficient control of electronic devices by using electric fields to manipulate magnetic states[49]. In addition,

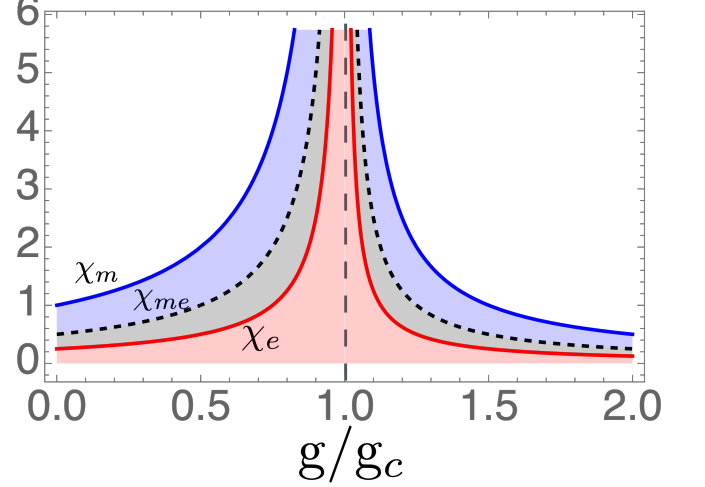


FIG. 2. Susceptibilities from Eq. (3) as a function of g . The chosen parameters are $\alpha = 2$ and $a = 1/2$. The magneto-electric susceptibility, χ_{me} , is the geometric mean of χ_e and χ_m . This corresponds to the highest magneto-electric effect compliant with thermodynamic requirements.

magneto-electric materials can convert mechanical energy into electrical energy, making them valuable for energy harvesting technologies[50].

Spin wave spectrum.- We expand the action around the equilibrium state $\mathbf{m} = m_0 \hat{\mathbf{m}} + \delta \mathbf{m}$ and $\mathbf{P} = P_0 \hat{\mathbf{P}} + \delta \mathbf{p}$. We can write an effective action for the system with the $\delta \mathbf{m}$ fluctuations integrated out:

$$\begin{aligned}\mathcal{L}^{(2)} &= \frac{\rho}{2} \delta \dot{\mathbf{p}}^2 - \frac{A}{2} (\nabla \delta \mathbf{p})^2 + \frac{1}{2} \mathcal{K} \delta \mathbf{p}^2 \\ &+ \frac{\chi_{\perp}}{2} \left(\left(s \mathbf{n} \times \dot{\mathbf{n}} + \mathbf{f} - \frac{\mathbf{m}_0}{\chi_{\perp}} \right)^2 - (\mathbf{f} \cdot \mathbf{n})^2 \right) \\ &+ s \mathbf{m}_0 \cdot (\mathbf{n} \times \dot{\mathbf{n}}) - \frac{A}{2} (\nabla \mathbf{n})^2 - \frac{K}{2} (\mathbf{n} \cdot \mathbf{z})^2\end{aligned}\quad (4)$$

where we have defined $\mathbf{f} = (\mathbf{H} - g \delta \mathbf{p} + \frac{\mathbf{m}_0}{\chi_{\perp}})$ and $\mathcal{K} = (\alpha + 3\beta P_0^2)$, $\chi_{\perp} = (a + 3b m_0^2)^{-1}$. This leads to the following equations of motion:

$$\begin{aligned}\rho \delta \ddot{\mathbf{p}} &= A \nabla^2 \delta \mathbf{p} - \mathcal{K} \delta \mathbf{p} - \chi_{\perp} g (\mathbf{f} + s \mathbf{n} \times \dot{\mathbf{n}} - \frac{\mathbf{m}_0}{\chi_{\perp}}) + \chi_{\perp} g (\mathbf{f} \cdot \mathbf{n}) \mathbf{n} \\ \chi_{\perp} s^2 \mathbf{n} \times \ddot{\mathbf{n}} &= 2 \chi_{\perp} s \mathbf{n} \times (\dot{\mathbf{n}} \times \mathbf{f}) - \chi_{\perp} s \mathbf{n} \times (\dot{\mathbf{f}} \times \mathbf{n}) + A \mathbf{n} \times \nabla^2 \mathbf{n} + K (\mathbf{n} \cdot \mathbf{z}) \mathbf{n} \times \mathbf{z} - \chi_{\perp} (\mathbf{f} \cdot \mathbf{n}) \mathbf{n} \times \mathbf{f}\end{aligned}\quad (5)$$

The solutions to the wave equation can be expressed as $\delta \mathbf{n}(x, t) = e^{i\mathbf{k}\cdot\mathbf{x} - \omega t} (\varepsilon_1 n_1 + \varepsilon_2 n_2)$. The equation of motion unfolds into two coupled equations for n_1 and n_2 that can only be fulfilled by choosing a phase shift $\pm\pi/2$ between them. The waves are, therefore, circularly polarized. Due to the magnetic field, there is a splitting between the two circular polarizations. We have,

$$\delta \dot{\mathbf{n}} \times \mathbf{n}_0 = \sigma \omega \delta \mathbf{n},$$

with $\sigma = +1(-1)$ for right-polarized (left-polarized) waves. In the paraelectric regime, the equations for small deviations from equilibrium, $\mathbf{n}_0 = \mathbf{z}$ and $\mathbf{H} = H_z \mathbf{z}$, are:

$$-\rho\omega^2 \delta \mathbf{p}_\perp = -Ak^2 \delta \mathbf{p}_\perp - \mathcal{K} \delta \mathbf{p}_\perp + \chi_\perp g (g \delta \mathbf{p}_\perp + s\sigma\omega \delta \mathbf{n}_\perp) + gH_z \chi_\perp \delta \mathbf{n}_\perp \quad (6)$$

$$\begin{aligned} -\rho\omega^2 \delta \mathbf{p}_z &= -Ak^2 \delta \mathbf{p}_z - \mathcal{K} \delta \mathbf{p}_z + g\mathbf{m}_0 \cdot \delta \mathbf{n}_\perp \\ -\omega^2 s^2 \chi_\perp \delta \mathbf{n}_\perp &= 2s\sigma\omega H_z \chi_\perp \delta \mathbf{n}_\perp + g\chi_\perp s\sigma\omega \delta \mathbf{p}_\perp - K \delta \mathbf{n}_\perp \\ &\quad - Ak^2 \delta \mathbf{n}_\perp - \mathbf{m}_0 \left[\frac{1}{\chi_\perp} \mathbf{m}_0 \cdot \delta \mathbf{n}_\perp - g \delta \mathbf{p}_z \right] \\ &\quad + H_z^2 \chi_\perp \delta \mathbf{n}_\perp + gH_z \chi_\perp \delta \mathbf{p}_\perp, \end{aligned} \quad (7)$$

where the external field induces displacements in the ground state magnetic configuration: $\mathbf{m}_0^{eq} = \mathbf{m}_0 + \Delta \mathbf{m}$ and $\mathbf{n}_0^{eq} = \mathbf{n}_0 + \Delta \mathbf{n}$. In the linear field regime, these displacements can be approximated as $\Delta \mathbf{m} = \frac{H_z \mathbf{m}_0^2}{K} \hat{z}$ and $\Delta \mathbf{n} = -\frac{H_z \mathbf{m}_0}{K}$. Additionally, the electric polarization experiences a displacement given by $\Delta \mathbf{P} = -\frac{g\chi_\perp H_z^2 \mathbf{m}_0}{K(\mathcal{K} - g^2 \chi_\perp)} + \mathcal{O}(H_z^3)$.

In the limit $\mathbf{P}_0 = \delta \mathbf{p} = \mathbf{m}_0 = 0$, the equations reduce to standard antiferromagnetic dynamics[51–53]. For $|\mathbf{m}_0| \ll 1$, two distinct branches emerge. In the first branch $\delta \mathbf{p}$ aligns with \mathbf{n}_0 and decouples from the magnons, exhibiting a dispersion relation $\rho\omega^2 = Ak^2 + \mathcal{K}$, see green line in Figs. (3).(a-c). The second branch corresponds to $\delta \mathbf{p}$ forming vector waves that share its circular polarization in the plane perpendicular to \mathbf{n}_0 . The spectrum can be readily found

$$\begin{aligned} -g^2 \mathbf{m}_0^2 P + (P - g^2 \chi_\perp) (P[M + H_z \chi_\perp (H_z + 2\sigma s\omega)]) \\ -g^2 \chi_\perp^2 (H_z + s\sigma\omega)^2 = 0 \end{aligned} \quad (8)$$

where $P = \rho\omega^2 - Ak^2 - \mathcal{K} + \chi_\perp g^2$ and $M = -Ak^2 - K - \frac{\mathbf{m}_0^2}{\chi_\perp}$.

The main features of the dispersion relations are depicted in Figs.(3) and (4). The multiferroic phase transition ($g = g_c$) is related to a vanishing of the gap as can be seen in Figs.(3c) and (4d).

The above account allows us to use a magnetoferron-based device specially tuned to sense electric or magnetic fields. The critical element of such a device is a

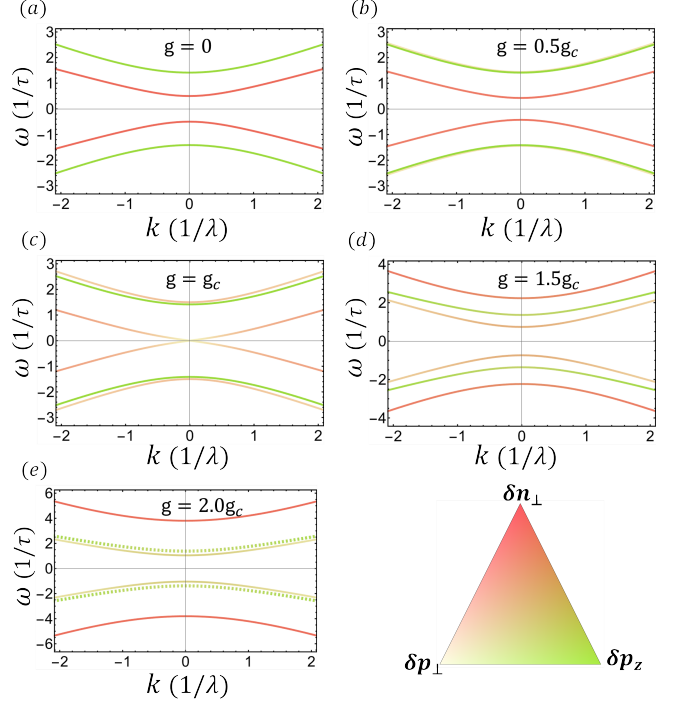


FIG. 3. Magnetoferrons dispersion relation for $a = 1/2$, $\alpha = 2$, $K = 0.5$, $H_z = 0$ and different values of the magnetoelectric coupling constant g . The remaining parameters are taken as unity. The color of each band indicates the relative contributions of the components $\delta \mathbf{n}_\perp$ (red), $\delta \mathbf{p}_z$ (green) and $\delta \mathbf{p}_\perp$ (light yellow), as illustrated in the triangular color map. For $g = 0$, the bands shown in figure (a) are not hybridized. The magnetoferrons are independent for the electric and magnetic parts. For low coupling (b), the degeneracy of the $\delta \mathbf{p}$ -bands is lifted and slight hybridization is observed. However, the middle bands (green), associated with $\delta \mathbf{p}_z$ remain non-hybridized since $\mathbf{m}_0 = 0$. For $g = g_c$ (c), a multiferroic phase transition occurs, characterized by a vanishing gap. In this limit, we observe that the bands exhibit significant hybridization near $k = 0$. The hybridization of the bands is also observed for (d) $g = 1.5g_c$ and (e) $g = 2g_c$.

high-Q cavity with the magnetoelectric material as an active substance. Magnetoferrons will be excited at specific resonances that will sharply depend on the values of the electric and magnetic fields.

Conclusion and outlook.— The collective excitations of a multiferroic material were analyzed. We showed that they, too, display this magnetoelectric behavior that results in a hybridization of the magnons, oscillations of the magnetization field, and the ferrons, oscillating the electric dipolar density field. We call these emergent entities magnetoferrons and discuss their potential applications. We also provided a phenomenological account of those systems that will prove invaluable in addressing the dynamic description of the multiferroic state. In principle,

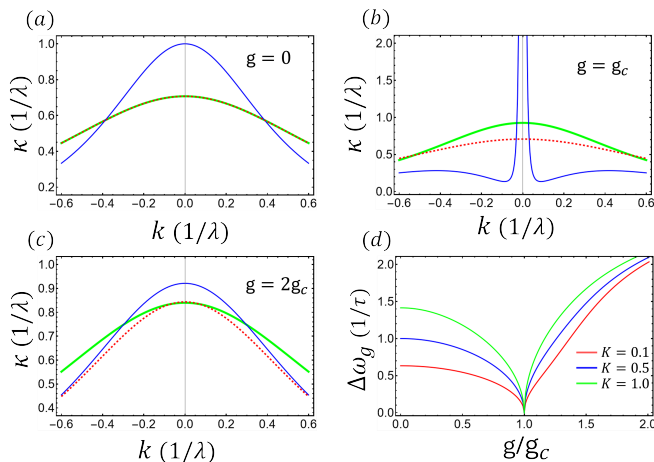


FIG. 4. Panels (a), (b), and (c) show the curvature of the magnetoferron dispersion relation for the three lowest-frequency bands. A divergence in the curvature is observed at the multiferroic phase transition ($g = g_c$). (d) show the frequency gap of the magnetoferrons dispersion as a function of the magnetolectric constant for three different values of magnetic anisotropy $K = 0.1$, $K = 0.5$, and $K = 1.0$. We consider that $a = 1/2$, $\alpha = 2$, $H_z = 0$, and the remaining parameters are taken as unity.

these excitations are quantized in the form:

$$\delta s_\ell(\mathbf{R}) = \sum_{\mathbf{q}, \nu} \left(t_{\mathbf{q}, \ell, \nu} \mathbf{a}_{\mathbf{q}, \nu} \frac{e^{i\mathbf{q} \cdot \mathbf{R}}}{\sqrt{\omega_{\mathbf{q}, \nu}}} + t_{\mathbf{q}, \ell, \nu}^* \mathbf{a}_{\mathbf{q}, \nu}^\dagger \frac{e^{-i\mathbf{q} \cdot \mathbf{R}}}{\sqrt{\omega_{\mathbf{q}, \nu}}} \right),$$

where $\delta s_\ell(\mathbf{R}) = (\delta \mathbf{n}_\perp, \delta \mathbf{p}_\perp, \delta p_z)$, $\mathbf{a}_{\mathbf{q}, \nu}^\dagger$ ($\mathbf{a}_{\mathbf{q}, \nu}$) is a creation (annihilation) operator for a magnetoferron in band ν with momentum \mathbf{q} and $t_{\mathbf{q}, \ell, \nu}$ corresponds to the suitably normalized eigenvectors of Eq. (6). This equation opens the doors to quantum phenomena, such as [54–58], in the context of quantized magnetoferrons.

Additional symmetry-respecting coupling of the polarization to the strain field will likely open the way to magnetoelastic phenomena such as piezomagnetism[59] or the piezospintronic effect[60–62].

The unique properties of magnetolectric waves in multiferroic materials shall lead to the development of various applications. The propagation and control of the magnetoferrons entail the possibility of controlling spin (\vec{j}_S)[63], polarization (\vec{j}_P)[64], and heat (\vec{j}_Q)[65] currents with great control, especially near the critical region. The first idea that comes to mind is a magnetolectric sensor that detects weak magnetic fields. These sensors might utilize the interferometry of magnetoferrons and their dependence on electric and magnetic properties in multiferroic materials to detect changes in magnetic fields by measuring the induced electric polarization. These sensors might find applications in fields as different as biomagnetic sensing, geophysical exploration, and non-destructive testing. The second is a neuromorphic memory device that stores data in both the electric polar-

ization and magnetization states of multiferroics. This could be implemented by the design of magnetoferroic-based memristors[66]. Information is customarily written and read using electric and magnetic fields. The emergence of magnetoferroics and the coupling between them and these fields in multiferroic materials allows efficient data manipulation. This opens the way for data storage solutions that offer faster access times and lower power consumption than traditional memory devices. Third, a spintronic device that uses magnetolectric coupling to control the spin current. The device exploits the magnetolectric effect to control the spin orientation of electrons, which is crucial for developing advanced spintronics applications: next-generation transistors, magnetic random access memory (MRAM), and other spin-based electronic devices. Finally, magnetoferroics can be used to envision a microwave signal processor utilizing magnetolectric waves for frequency modulation and filtering. Magnetolectric materials are used to create components such as filters and modulators that operate at microwave frequencies, taking advantage of their unique dispersion properties in telecommunications, radar systems, and wireless communication technologies.

Acknowledgements.— Funding is acknowledged from Fondecyt Regular 1230515 and DICYT regular 042431AP. G.S. thanks the financial support provided by ANID Subdirección de Capital Humano/Doctorado, Chile Nacional/2022-21222167. M. A. C. acknowledges Proyecto ANID Fondecyt de Postdoctorado 3240112.

-
- [1] N. A. Spaldin and R. Ramesh, Advances in magnetolectric multiferroics, *Nature Materials* **18**, 203–212 (2019).
 - [2] Q. Song, C. A. Occhialini, E. Ergezen, B. Ilyas, D. Amoroso, P. Barone, J. Kapteghian, K. Watanabe, T. Taniguchi, A. S. Botana, S. Picozzi, N. Gedik, and R. Comin, Evidence for a single-layer van der waals multiferroic, *Nature* **602**, 601–605 (2022).
 - [3] D. Bennett, G. Martínez-Carracedo, X. He, J. Ferrer, P. Ghosez, R. Comin, and E. Kaxiras, Stacking-engineered ferroelectricity and multiferroic order in van der waals magnets, *Physical Review Letters* **133**, 10.1103/physrevlett.133.246703 (2024).
 - [4] M. Castro, G. Saéz, P. Vergara Apaz, S. Allende, and A. S. Nunez, Toward fully multiferroic van der waals spinfets: Basic design and quantum calculations, *Nano Letters* **24**, 7911–7918 (2024).
 - [5] M. Mostovoy, Multiferroics: different routes to magnetolectric coupling, *npj Spintronics* **2**, 10.1038/s44306-024-00021-8 (2024).
 - [6] T. Kimura, T. Goto, H. Shintani, K. Ishizaka, T. Arima, and Y. Tokura, Magnetic control of ferroelectric polarization, *Nature* **426**, 55–58 (2003).
 - [7] W. S. Gan, Spontaneous symmetry breaking and phonon as the goldstone mode, in *Gauge Invariance Approach to Acoustic Fields* (Springer Singapore, 2019) p. 59–62.

- [8] P. W. Anderson, [Basic Notions of Condensed Matter Physics](#), [25] edited by P. W. Anderson (CRC Press, 2018).
- [9] A. V. Chumak, V. Vasyuchka, A. Serga, and B. Hillebrands, Magnon spintronics, *Nature Physics* **11**, 453–461 (2015).
- [10] P. Pirro, V. I. Vasyuchka, A. A. Serga, and B. Hillebrands, Advances in coherent magnonics, *Nature Reviews Materials* **6**, 1114–1135 (2021).
- [11] H. Yuan, Y. Cao, A. Kamra, R. A. Duine, and P. Yan, Quantum magnonics: When magnon spintronics meets quantum information science, *Physics Reports* **965**, 1–74 (2022).
- [12] B. Flebus, D. Grundler, B. Rana, Y. Otani, I. Barsukov, A. Barman, G. Gubbiotti, P. Landeros, J. Akerman, U. Ebels, P. Pirro, V. E. Demidov, K. Schultheiss, G. Csaba, Q. Wang, F. Ciubotaru, D. E. Nikonov, P. Che, R. Hertel, T. Ono, D. Afanasiev, J. Mentink, T. Rasing, B. Hillebrands, S. V. Kusminskiy, W. Zhang, C. R. Du, A. Finco, T. van der Sar, Y. K. Luo, Y. Shiota, J. Skleinar, T. Yu, and J. Rao, The 2024 magnonics roadmap, *Journal of Physics: Condensed Matter* **36**, 363501 (2024).
- [13] J. S. Harms, H. Y. Yuan, and R. A. Duine, Antimagnonics, *AIP Advances* **14**, 10.1063/5.0151652 (2024).
- [14] C. Saji, R. E. Troncoso, V. L. Carvalho-Santos, D. Altbir, and A. S. Nunez, Hopfion-driven magnonic hall effect and magnonic focusing, *Physical Review Letters* **131**, 10.1103/physrevlett.131.166702 (2023).
- [15] Z. Jiang, J. Lim, Y. Li, W. Pfaff, T.-H. Lo, J. Qian, A. Schleife, J.-M. Zuo, V. Novosad, and A. Hoffmann, Integrating magnons for quantum information, *Applied Physics Letters* **123**, 10.1063/5.0157520 (2023).
- [16] E. Aguilera, R. Jaeschke-Ubiergo, N. Vidal-Silva, L. E. F. F. Torres, and A. S. Nunez, Topological magnonics in the two-dimensional van der waals magnet CrI_3 , *Physical Review B* **102**, 10.1103/physrevb.102.024409 (2020).
- [17] Y. M. Bunkov, Quantum magnonics, *Journal of Experimental and Theoretical Physics* **131**, 18–28 (2020).
- [18] A. V. Chumak, A. A. Serga, and B. Hillebrands, Magnon transistor for all-magnon data processing, *Nature Communications* **5**, 10.1038/ncomms5700 (2014).
- [19] J. Cramer, F. Fuhrmann, U. Ritzmann, V. Gall, T. Nizeki, R. Ramos, Z. Qiu, D. Hou, T. Kikkawa, J. Sinova, U. Nowak, E. Saitoh, and M. Kläui, Magnon detection using a ferroic collinear multilayer spin valve, *Nature Communications* **9**, 10.1038/s41467-018-03485-5 (2018).
- [20] H. Wu, L. Huang, C. Fang, B. Yang, C. Wan, G. Yu, J. Feng, H. Wei, and X. Han, Magnon valve effect between two magnetic insulators, *Physical Review Letters* **120**, 10.1103/physrevlett.120.097205 (2018).
- [21] L. Cornelissen, J. Liu, B. van Wees, and R. Duine, Spin-current-controlled modulation of the magnon spin conductance in a three-terminal magnon transistor, *Physical Review Letters* **120**, 10.1103/physrevlett.120.097702 (2018).
- [22] M. P. Kostylev, A. A. Serga, T. Schneider, B. Leven, and B. Hillebrands, Spin-wave logical gates, *Applied Physics Letters* **87**, 10.1063/1.2089147 (2005).
- [23] K. Ganzhorn, S. Klingler, T. Wimmer, S. Geprägs, R. Gross, H. Huebl, and S. T. B. Goennenwein, Magnon-based logic in a multi-terminal yig/pt nanostructure, *Applied Physics Letters* **109**, 10.1063/1.4958893 (2016).
- [24] R. E. Troncoso and A. S. Núñez, Dynamics and spontaneous coherence of magnons in ferromagnetic thin films, *Journal of Physics: Condensed Matter* **24**, 036006 (2011).
- [25] R. E. Troncoso and Álvaro S. Núñez, Josephson effects in a bose-einstein condensate of magnons, *Annals of Physics* **346**, 182–194 (2014).
- [26] K. Nakata, K. A. van Hoogdalem, P. Simon, and D. Loss, Josephson and persistent spin currents in bose-einstein condensates of magnons, *Physical Review B* **90**, 10.1103/physrevb.90.144419 (2014).
- [27] K. Nakata, J. Zou, J. Klinovaja, and D. Loss, Magnonic φ josephson junctions and synchronized precession, *Physical Review Research* **6**, 10.1103/physrevresearch.6.033207 (2024).
- [28] M. Born, K. Huang, and M. Lax, Dynamical theory of crystal lattices, *American Journal of Physics* **23**, 474–474 (1955).
- [29] P. Tang, R. Iguchi, K.-i. Uchida, and G. E. W. Bauer, Excitations of the ferroelectric order, *Physical Review B* **106**, 10.1103/physrevb.106.1081105 (2022).
- [30] A. P. Levanyuk, I. Burc Misirlioglu, and M. Baris Okatan, Landau, ginzburg, devonshire and others, *Ferroelectrics* **569**, 310–323 (2020).
- [31] N. A. Spaldin, S.-W. Cheong, and R. Ramesh, Multiferroics: Past, present, and future, *Physics Today* **63**, 38–43 (2010).
- [32] J. Wang, [Multiferroic Materials](#) (CRC Press, 2016).
- [33] S. Kimura, T. Fujita, M. Hagiwara, H. Yamaguchi, T. Kashiwagi, N. Terada, Y. Sawada, and K. Watanabe, Electromagnon by chiral spin dynamics in the triangular lattice antiferromagnet, *Physical Review B* **90**, 10.1103/physrevb.90.060413 (2014).
- [34] T. Kubacka, J. A. Johnson, M. C. Hoffmann, C. Vicario, S. de Jong, P. Beaud, S. Grübel, S.-W. Huang, L. Huber, L. Patthey, Y.-D. Chuang, J. J. Turner, G. L. Dakovski, W.-S. Lee, M. P. Minitti, W. Schlotter, R. G. Moore, C. P. Hauri, S. M. Koochpayeh, V. Scagnoli, G. Ingold, S. L. Johnson, and U. Staub, Large-amplitude spin dynamics driven by a thz pulse in resonance with an electromagnon, *Science* **343**, 1333–1336 (2014).
- [35] G. Saez, M. A. Castro, S. Allende, and A. S. Nunez, Model for nonrelativistic topological multiferroic matter, *Phys. Rev. Lett.* **131**, 226801 (2023).
- [36] P. Vergara, G. Sáez, M. Castro, S. Allende, and Álvaro S. Núñez, Emerging topological multiferroics from the 2d rice-mele model, *npj 2D Materials and Applications* **8**, 10.1038/s41699-024-00478-5 (2024).
- [37] G. Saez, P. Vergara, M. Castro, S. Allende, and A. S. Nunez, Ferromagnetic order in noncentrosymmetric antiferromagnets: An avenue toward spintronic-based computing, data storage, and energy harvesting, *physica status solidi (RRL) – Rapid Research Letters* , 2400292 (2024).
- [38] K. Rabe, C. Ahn, and J. Triscone, [Physics of Ferroelectrics: A Modern Perspective](#), Topics in Applied Physics (Springer Berlin Heidelberg, 2007).
- [39] A. Auerbach, [Interacting Electrons and Quantum Magnetism](#) (Springer New York, 1994).
- [40] K. Borejsza and N. Dupuis, Antiferromagnetism and single-particle properties in the two-dimensional half-filled hubbard model: A nonlinear sigma model approach, *Physical Review B* **69**, 10.1103/physrevb.69.085119 (2004).
- [41] S. Sachdev, [Quantum Phase Transitions](#), 2nd ed. (Cambridge University Press, Cambridge, England, 2011).
- [42] S. M. Rezende, A. Azevedo, and R. L. Rodríguez-Suárez,

- Introduction to antiferromagnetic magnons, *Journal of Applied Physics* **126**, [10.1063/1.5109132](https://doi.org/10.1063/1.5109132) (2019).
- [43] A. El Kanj, O. Gomonay, I. Boventer, P. Bortolotti, V. Cros, A. Anane, and R. Lebrun, Antiferromagnetic magnon spintronic based on nonreciprocal and nondegenerated ultra-fast spin-waves in the canted antiferromagnet α -Fe₂O₃, *Science Advances* **9**, [10.1126/sciadv.adh1601](https://doi.org/10.1126/sciadv.adh1601) (2023).
- [44] L. Huang, L. Liao, H. Qiu, X. Chen, H. Bai, L. Han, Y. Zhou, Y. Su, Z. Zhou, F. Pan, B. Jin, and C. Song, Antiferromagnetic magnonic charge current generation via ultrafast optical excitation, *Nature Communications* **15**, [10.1038/s41467-024-48391-1](https://doi.org/10.1038/s41467-024-48391-1) (2024).
- [45] A. Sekine and K. Nomura, Axion electrodynamics in topological materials, *Journal of Applied Physics* **129**, [10.1063/5.0038804](https://doi.org/10.1063/5.0038804) (2021).
- [46] E. O. Kamenetskii, Magnetolectric energy in electrodynamics: Magnetolectricity, bi(an)isotropy, and magnetolectric meta-atoms, *Annalen der Physik* **535**, [10.1002/andp.202300287](https://doi.org/10.1002/andp.202300287) (2023).
- [47] T. H. O'Dell, The field invariants in a magneto-electric medium, *Philosophical Magazine* **8**, 411–418 (1963).
- [48] T. Kosub, M. Kopte, R. Hühne, P. Appel, B. Shields, P. Maletinsky, R. Hübner, M. O. Liedke, J. Fassbender, O. G. Schmidt, and D. Makarov, Purely antiferromagnetic magnetolectric random access memory, *Nature Communications* **8**, [10.1038/ncomms13985](https://doi.org/10.1038/ncomms13985) (2017).
- [49] S. Fusil, V. Garcia, A. Barthélémy, and M. Bibes, Magnetolectric devices for spintronics, *Annual Review of Materials Research* **44**, 91–116 (2014).
- [50] M. Suárez-Rodríguez, B. Martín-García, W. Skowroński, K. Staszek, F. Calavalle, A. Fert, M. Gobbi, F. Casanova, and L. E. Hueso, Microscale chiral rectennas for energy harvesting, *Advanced Materials* **36**, [10.1002/adma.202400729](https://doi.org/10.1002/adma.202400729) (2024).
- [51] V. Baltz, A. Manchon, M. Tsoi, T. Moriyama, T. Ono, and Y. Tserkovnyak, Antiferromagnetic spintronics, *Rev. Mod. Phys.* **90**, 015005 (2018).
- [52] R. E. Troncoso, C. Ulloa, F. Pesce, and A. S. Nunez, Antiferromagnetic magnonic crystals, *Phys. Rev. B* **92**, [224424](https://doi.org/10.1103/PhysRevB.92.224424) (2015).
- [53] S. M. Rezende, Magnons in antiferromagnets, in *Fundamentals of Magnonics* (Springer International Publishing, 2020) p. 187–222.
- [54] A. Tapia, C. Saji, A. Roldán-Molina, and A. S. Nunez, Stability enhancement by zero-point spin fluctuations: A quantum perspective on Bloch point topological singularities, *Advanced Functional Materials* **34**, [10.1002/adfm.202312721](https://doi.org/10.1002/adfm.202312721) (2024).
- [55] A. Roldán-Molina, M. J. Santander, A. S. Nunez, and J. Fernández-Rossier, Quantum fluctuations stabilize skyrmion textures, *Physical Review B* **92**, [10.1103/PhysRevB.92.245436](https://doi.org/10.1103/PhysRevB.92.245436) (2015).
- [56] A. Roldán-Molina, A. S. Nunez, and J. Fernández-Rossier, Topological spin waves in the atomic-scale magnetic skyrmion crystal, *New Journal of Physics* **18**, [045015](https://doi.org/10.1088/1751-8183/18/4/045015) (2016).
- [57] A. Roldán-Molina, A. S. Nunez, and R. Duine, Magnonic black holes, *Physical Review Letters* **118**, [10.1103/PhysRevLett.118.061301](https://doi.org/10.1103/PhysRevLett.118.061301) (2017).
- [58] R. J. Doornenbal, A. Roldán-Molina, A. S. Nunez, and R. A. Duine, Spin-wave amplification and lasing driven by inhomogeneous spin-transfer torques, *Physical Review Letters* **122**, [10.1103/PhysRevLett.122.037203](https://doi.org/10.1103/PhysRevLett.122.037203) (2019).
- [59] M. Jaime, A. Saul, M. Salamon, V. S. Zapf, N. Harrison, T. Durakiewicz, J. C. Lashley, D. A. Andersson, C. R. Stanek, J. L. Smith, and K. Gofryk, Piezomagnetism and magnetoelastic memory in uranium dioxide, *Nature Communications* **8**, [10.1038/s41467-017-00096-4](https://doi.org/10.1038/s41467-017-00096-4) (2017).
- [60] A. S. Núñez, Theory of the piezo-spintronic effect, *Solid State Communications* **198**, 18–21 (2014).
- [61] C. Ulloa, R. E. Troncoso, S. A. Bender, R. A. Duine, and A. S. Nunez, Piezospintronic effect in honeycomb antiferromagnets, *Physical Review B* **96**, [10.1103/PhysRevB.96.104419](https://doi.org/10.1103/PhysRevB.96.104419) (2017).
- [62] H. Guo, Z. Feng, H. Yan, J. Liu, J. Zhang, X. Zhou, P. Qin, J. Cai, Z. Zeng, X. Zhang, X. Wang, H. Chen, H. Wu, C. Jiang, and Z. Liu, Giant piezospintronic effect in a noncollinear antiferromagnetic metal, *Advanced Materials* **32**, [10.1002/adma.202002300](https://doi.org/10.1002/adma.202002300) (2020).
- [63] J. Harms, H. Yuan, and R. A. Duine, Enhanced magnon spin current using the bosonic Klein paradox, *Physical Review Applied* **18**, [10.1103/PhysRevApplied.18.064026](https://doi.org/10.1103/PhysRevApplied.18.064026) (2022).
- [64] G. Bauer, P. Tang, R. Iguchi, J. Xiao, K. Shen, Z. Zhong, T. Yu, S. Rezende, J. Heremans, and K. Uchida, Polarization transport in ferroelectrics, *Physical Review Applied* **20**, [10.1103/PhysRevApplied.20.050501](https://doi.org/10.1103/PhysRevApplied.20.050501) (2023).
- [65] B. L. Wooten, R. Iguchi, P. Tang, J. S. Kang, K.-i. Uchida, G. E. Bauer, and J. P. Heremans, Electric field-dependent phonon spectrum and heat conduction in ferroelectrics, *Science Advances* **9**, [10.1126/sciadv.add7194](https://doi.org/10.1126/sciadv.add7194) (2023).
- [66] R. Tetzlaff, ed., *Memristors and Memristive Systems*, 1st ed. (Springer, New York, NY, 2013).