

Berezinskii-Kosterlitz-Thouless region and magnetization plateaus in easy-axis triangular weak-dimer antiferromagnet $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$

Ying Fu,^{1,2} Han Ge,² Jian Chen,² Jie Xiao,² Yi Tan,² Le Wang,³ Junfeng Wang,⁴ Chao Dong,⁴ Zhe Qu,⁵ Miao He,⁵ Chuanying Xi,⁵ Langsheng Ling,⁵ Bin Xi,^{6,*} and Jia-Wei Mei^{2,†}

¹Quantum Science Center of Guangdong-Hong Kong-Macao Greater Bay Area (Guangdong), Shenzhen, China

²Department of Physics, Southern University of Science and Technology, Shenzhen 518055, China

³International Quantum Academy, Shenzhen, 518048, China.

⁴Wuhan National High Magnetic Field Center & School of Physics, Huazhong University of Science and Technology, Wuhan 430074, China

⁵Anhui Key Laboratory of Low-Energy Quantum Materials and Devices,

High Magnetic Field Laboratory, HFIPS, Chinese Academy of Sciences, Hefei, Anhui 230031, China

⁶College of Physics Science and Technology, Yangzhou University, Yangzhou 225002, China

(Dated: January 17, 2025)

We investigate the magnetic phase diagram of the bilayer triangular antiferromagnet $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$, unveiling a rich interplay between geometric frustration, bilayer coupling, and symmetry-driven phenomena. High-field magnetization measurements reveal fractional magnetization plateaus at $1/3$, $1/2$, $2/3$, and $5/6$ of the saturation magnetization. To elucidate the experimental magnetic phase diagram at low fields, we propose that $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$ can be described as an easy-axis triangular weak-dimer antiferromagnet. We emphasize the critical role of the emergent $U(1) \otimes S_3$ symmetry, where $S_3 = \mathbb{Z}_3 \otimes \mathbb{Z}_2^d$, in determining the magnetic phases at low fields. The remarkable agreement between the experimental and theoretical phase diagrams suggests that the phase transitions are governed by this symmetry. Notably, our combined experimental and theoretical results identify a Berezinskii-Kosterlitz-Thouless (BKT) phase region at finite fields. These findings provide new insights into the phase structure of frustrated magnets and establish $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$ as a compelling platform for exploring unconventional quantum phenomena in $U(1) \otimes S_3$ systems.

Introduction. – The triangular lattice system serves as a paradigmatic platform for investigating the interplay of geometric frustration and quantum fluctuations in magnetic systems[1]. The inherent geometric frustration in triangular lattices prevents all spins from aligning antiferromagnetically, leading to a highly degenerate ground state and amplifying quantum fluctuations [2]. This unique interplay has been extensively studied in various $3d$ transition-metal compounds, including Cs_2CuBr_4 [3, 4], $\text{Ba}_3\text{CoSb}_2\text{O}_9$ [5, 6], $\text{Ba}_3\text{MnNb}_2\text{O}_9$ [7], $\text{Na}_2\text{BaCo}(\text{PO}_4)_2$ [8–10], $\text{Na}_2\text{BaNi}(\text{PO}_4)_2$ [11, 12], $\text{K}_2\text{Co}(\text{SeO}_3)_2$ [13–15], and $\text{Rb}_4\text{Mn}(\text{MoO}_4)_3$ [16]. Recent research has also highlighted the significance of bilayer triangular lattices, such as $A'_3\text{Cr}_2\text{O}_8$ ($A'=\text{Sr}, \text{Ba}$)[17, 18], $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$ [19], and $\text{K}_2\text{Ni}_2(\text{SeO}_3)_3$ [20, 21], which offer additional opportunities to explore the effects of interlayer interactions and symmetry-induced phenomena in frustrated quantum magnetism.

One of the most striking features of triangular lattice systems is the $1/3$ magnetization plateau, characterized by the up-up-down (*uud*) spin configuration. This phase exemplifies a spontaneous breaking of the threefold sublattice permutation symmetry \mathbb{Z}_3 (Fig. 1(a)) [22–24], which falls into the universality class of the three-state clock model[25, 26]. Quantum fluctuations further enhance the stability of this plateau phase[4, 27, 28]. At zero magnetic field, the time-reversal symmetry enlarges \mathbb{Z}_3 to \mathbb{Z}_6 [24] (Fig. 1(b)), which stabilizes an intermediate Berezinskii-Kosterlitz-Thouless (BKT) phase with quasi-long-range spin correlations with algebraic decay $\langle S(0)S(r) \rangle \sim r^{-\eta}$ [25, 29], where the anomalous dimension η quantifies deviation from the classical mean-field dimension.

The symmetry connection between the $1/3$ plateau and the intermediate BKT phase highlights the critical role of symmetry in shaping phase transitions[30–32]. However, the intermediate BKT phase is fragile in the presence of a magnetic field [33], and its experimental observation remains elusive.

In this work, we propose that the bilayer triangular antiferromagnet $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$ exemplifies the weak-dimer regime in bilayer systems. The bilayer dimer symmetry (\mathbb{Z}_2^d) enriches the triangular lattice’s \mathbb{Z}_3 symmetry, extending it to $S_3 = \mathbb{Z}_3 \otimes \mathbb{Z}_2^d$ (Fig. 1(c)), while preserving a continuous $U(1)$ symmetry associated with c -axis spin rotations. By combining experimental measurements and theoretical modeling, we construct the magnetic phase diagram with a particular focus on the low-field regime. In addition to the “Y” phase, associated with $U(1)$ symmetry breaking of the c -axis spin rotation symmetry, our study reveals three distinct phases driven

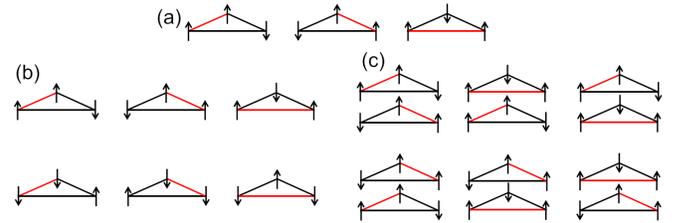


FIG. 1. (a) Spin configurations illustrating \mathbb{Z}_3 symmetry in an antiferromagnetic triangle. (b) Spin configurations demonstrating \mathbb{Z}_6 symmetry in a single-layer triangle with time-reversal symmetry. (c) Spin configurations corresponding to $S_3 = \mathbb{Z}_3 \otimes \mathbb{Z}_2^d$ symmetry in a weak-dimer bilayer triangle system.

by the breaking of the discrete S_3 symmetry: the S_3 -broken (triplet-singlet-singlet tss) phase, the \mathbb{Z}_3 -broken (uud) phase, and an intermediate Berezinskii-Kosterlitz-Thouless (BKT) phase. These findings depart from prior investigations on strong-dimer systems [17, 18, 34]. Notably, the theoretical phase diagram aligns closely with experimental observations, underscoring the critical role of symmetry in governing the phase transitions. At higher fields, our experimental measurements uncover a series of magnetization plateaus at $1/3$, $1/2$, $2/3$, and $5/6$ of the saturation magnetization.

Methods. – The synthesis of $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$ single crystals was performed using the flux method, as detailed in previous reports [19]. Magnetization, heat capacity, and magnetocaloric effect measurements were conducted using the Quantum Design Magnetic Property Measurement System (up to 7 T) and the Physical Property Measurement System (up to 14 T). High-field magnetization measurements up to 35 T were carried out using a Vibratory Sample Magnetometer (VSM) on a water-cooled magnet (WM5) at the High Magnetic Field Laboratory (HMFL). The Monte Carlo (MC) simulations were executed employing a combination of the parallel tempering method [35] and the heat-bath algorithm [36].

Weak dimer interaction and multiple magnetization plateaus in $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$. – In addition to its monolayer counterpart $\text{K}_2\text{Co}(\text{SeO}_3)_2$ [8, 14, 15], the bilayer triangular antiferromagnet $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$, characterized by Co_2O_9 spin

dimers (Fig. 2(a)), has attracted considerable attention [19, 34]. The intra-dimer exchange interaction in $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$ arises from a combination of ferromagnetic superexchange via shared oxygen atoms (as per the Goodenough-Kanamori rules[37] for an 85° Co-O-Co bond angle) and antiferromagnetic direct exchange between Co^{2+} ions. Unlike systems such as $\text{Cs}_3\text{V}_2\text{Cl}_9$ [38] and $\text{Cs}_3\text{Fe}_2\text{Cl}_9$ [39, 40], where ferromagnetic superexchange is predominant, the direct exchange interaction in $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$ plays a significant role. Contrary to the strong dimer assumption previously proposed[34], we suggest that $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$ is more accurately described as a weak-dimer bilayer triangular antiferromagnet, due to the competing exchanges, despite the short Co-Co bonds within the Co_2O_9 dimers indicating dominant intra-dimer interactions.

The weak intra-dimer interaction in $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$ is evidenced by its similarity to the magnetic properties of the single-layer compound $\text{K}_2\text{Co}(\text{SeO}_3)_2$ at high temperatures. This is supported by the comparative study of magnetic susceptibilities for the two compounds, shown in Fig. 2(b). In the relevant temperature range $40 \text{ K} < T < 100 \text{ K}$, where the effective spin-1/2 state of Co^{2+} ions emerges, both $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$ and $\text{K}_2\text{Co}(\text{SeO}_3)_2$ exhibit paramagnetic behavior. Their effective Curie-Weiss temperatures can be used to estimate the exchange interactions, $\Theta_{\text{CW}} = 1.5(J + J_\perp + J_\perp^0/6)$ for $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$ and $\Theta_{\text{CW}} = 1.5J$ for $\text{K}_2\text{Co}(\text{SeO}_3)_2$. As indicated in Fig. 2(b), both compounds share comparable magnetic characteristics. With $\Theta_{\text{CW}}^e = -43 \text{ K}$ for $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$ and -49 K for $\text{K}_2\text{Co}(\text{SeO}_3)_2$, these values are remarkably close, suggesting an effectively weak dimer interaction ($J_\perp^{\text{eff}} = J_\perp + J_\perp^0/6$).

Figure 2(c) compares the magnetization curves of $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$ and $\text{K}_2\text{Co}(\text{SeO}_3)_2$ at 2 K. Despite the large Curie-Weiss temperatures (exceeding 40 K), the critical fields for the onset of the $1/3$ magnetization plateau are relatively small, a behavior attributed to the strong magnetic anisotropy in both systems. The close proximity of the critical fields, with their difference being significantly smaller than the Curie-Weiss temperature scale, further supports the classification of $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$ as a weak-dimer system. Notably, the absence of an obvious spin gap near zero field in the magnetization of $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$ underscores its weak intra-dimer interaction, contrasting sharply with the pronounced spin gaps observed in field-dependent magnetization curves of strong-dimer systems such as $\text{Sr}_3\text{Cr}_2\text{O}_8$ [41] and $\text{SrCu}_2(\text{BO}_3)_2$ [42].

High-field magnetization measurements along the c -axis at 1.8 K, shown in Fig. 2(d), reveal a series of distinct magnetization plateaus. The derivative curve (blue line) highlights the precise locations of these plateaus, which occur at fractional values of the saturation magnetization: $1/3$, $1/2$, $2/3$, and $5/6$. The compound reaches saturation at approximately 25 T with a magnetic moment of $\sim 3.7 \mu_B$, closely matching the saturation field ($\sim 22 \text{ T}$) and moment ($\sim 3.9 \mu_B$) of its monolayer counterpart $\text{K}_2\text{Co}(\text{SeO}_3)_2$. Despite being in the weak-dimer regime, the spin dimers in $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$ enhance the geometric frustration, as illustrated in Fig. 1. This

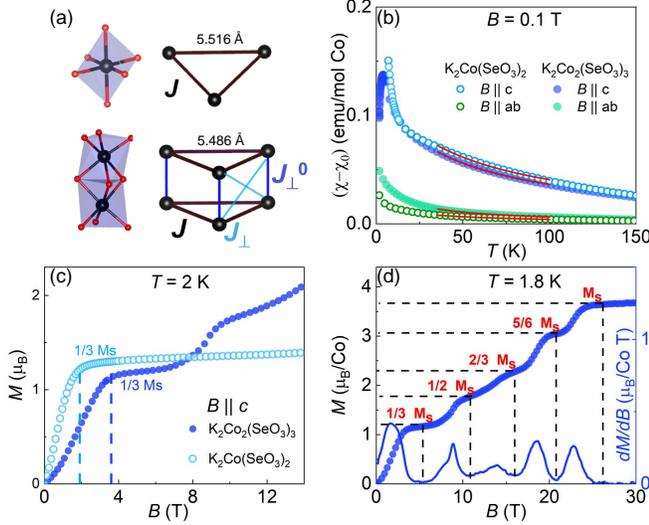


FIG. 2. (a) Schematic illustration of the bilayer triangular antiferromagnet $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$, featuring Co_2O_9 spin dimers on a triangular lattice. The dominant intralayer interaction J is present in both $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$ and its monolayer counterpart $\text{K}_2\text{Co}(\text{SeO}_3)_2$, while $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$ additionally exhibits interlayer interactions J_\perp and J_\perp^0 . (b) Magnetic susceptibilities $\chi = M/H$ for $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$ and $\text{K}_2\text{Co}(\text{SeO}_3)_2$, with Curie-Weiss fits shown as red lines. (c) Comparison of field-dependent magnetization between $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$ and $\text{K}_2\text{Co}(\text{SeO}_3)_2$ along the c axis at 2 K. (d) High-field magnetization of $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$ along the c axis at 1.8 K, revealing a series of magnetization plateaus. The blue line represents the derivative curve.

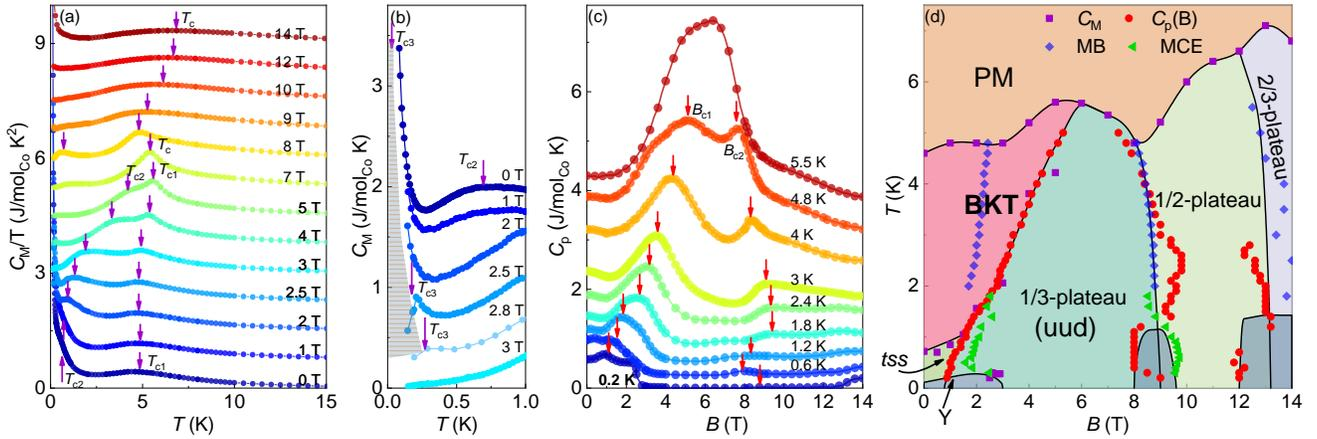


FIG. 3. (a) The magnetic specific heat divided by temperature $C_m(T)/T$ (offset of 0.75) of $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$ for $B \parallel c$ axis. (b) Zoomed-in view of $C_m(T)$ (offset of 0.25) in (a) to resolve the phase transition at low field and temperature. (c) Field-dependent heat capacity C_p (offset of 0.25). (d) Magnetic phase diagram of $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$ for $B \parallel c$ axis. The lines for the phase boundaries are guides for the eye. The transition points are extracted from thermodynamic measurements.

enhanced frustration is likely responsible for the emergence of multiple magnetization plateaus.

Phase diagram below 14 T in $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$. – Figure 3(a) presents the specific heat $C_m(T)$ of $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$ as a function of temperature for magnetic fields applied along the c -axis ($B \parallel c$). The phonon contribution has been subtracted using Debye and Einstein fitting. Given the effective interaction around 40 K, as indicated by the Curie-Weiss fitting, the peak features observed between 5 K and 10 K likely represent phase transitions rather than mere correlations. The broad nature of these transitions reflects the two-dimensional characteristics of the system.

To better resolve these transitions, we first examine the specific heat at $B = 7$ T, where the sharpest feature is observed, indicating a single phase transition at $T_c = 5.4$ K. For fields above 7 T and up to 14 T, only one phase transition persists, though it becomes increasingly broad and challenging to pinpoint precisely.

Below 7 T, the specific heat peak splits into two, indicating the presence of two distinct phase transitions at T_{c1} and T_{c2} . As the magnetic field decreases, the position of T_{c1} decreases slightly but broadens, while T_{c2} decreases more rapidly and remains broad. At even lower fields, below 3 T, an additional phase transition T_{c3} emerges around 0.1 K, the lowest temperature accessible in our experiments. To provide a clearer view of this low-temperature behavior, Fig. 3(b) zooms in on the specific heat data between 0.1 K and 1.0 K, highlighting the transition at T_{c3} .

Figure 3(c) presents field-dependent specific heat $C_p(B)$ measurements for $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$ at various fixed temperatures. For instance, at $T = 0.6$ K, the specific heat curves exhibit two concave regions in the ranges of 3–9 T and 9–13 T, corresponding to the 1/3 and 1/2 plateaus, respectively, as shown in Fig. 2(d). Around 13 T with increasing fields, the heat capacity increases and then begins to drop around 14 T, signaling the approach to the 2/3 plateau, corroborated by the

high-field magnetization curve in Fig. 2(d). At lower temperatures, additional features near these transitions reveal the presence of extra phases between the 1/3- and 1/2-plateau phases and between the 1/2- and 2/3-plateau phases.

Focusing on the low-field region, below 6 T, the transition from the zero-field phase to the 1/3-plateau phase is observed at the critical field $B_c(T)$. For $T > 1$ K, $B_c(T)$ aligns well with the phase boundary $T_{c2}(B)$ identified in Fig. 3(a), validating the consistency of temperature- and field-dependent results. In contrast, for $T < 1$ K, $B_c(T)$ deviates from $T_{c2}(B)$, with $B_c(T)$ falling below 1 T. This discrepancy suggests the emergence of a new low-temperature phase.

Figure 3(d) presents the magnetic phase diagram of $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$, meticulously constructed from field-dependent measurements of heat capacity, magnetization, and magnetocaloric effect (MCE), with detailed data available in the supplementary materials. Besides the key features of the 1/3-, 1/2-, and 2/3-plateau phases, the low-field region ($B < 6$ T) reveals a remarkably intricate phase structure, which is the primary focus of our study.

At higher temperatures, the system transitions from the paramagnetic phase to the 1/3-plateau phase through an intermediate phase. By integrating experimental observations with theoretical insights, we identify this intermediate phase as the Berezinskii-Kosterlitz-Thouless (BKT) phase, characterized by algebraic spin correlations. As the magnetic field decreases further, another transition occurs below 3 T and around 0.1 K, leading to the emergence of the "Y" phase, associated with $U(1)$ symmetry breaking. In the low field and temperature regime ($B < 1$ T, 0.1 K $< T < 1$ K), we identify a distinct phase, termed the *tss* (triplet-singlet-singlet) phase, based on theoretical simulation below.

Theoretical phase diagram for $U(1) \otimes S_3$ symmetry breaking. – To gain deeper insights into the rich and complex magnetic behavior observed in $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$, we turn to a theoretical model that captures the essential features of this bilayer

triangular antiferromagnet. The experimental phase diagram in Fig. 3(d) highlights the interplay of symmetry, frustration, and interlayer interactions, motivating a detailed theoretical investigation focused on the low-field region.

We begin with the Hamiltonian for $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$, given by:

$$\begin{aligned}
H = & \sum_{n\langle ij \rangle} J[(S_{ni}^x S_{nj}^x + S_{ni}^y S_{nj}^y)/\Delta + S_{ni}^z S_{nj}^z] \\
& + \sum_i J_{\perp}^0 [(S_{1i}^x S_{2i}^x + S_{1i}^y S_{2i}^y)/\Delta + S_{1i}^z S_{2i}^z] \\
& + \sum_{\langle ij \rangle'} J_{\perp} [(S_{1i}^x S_{2j}^x + S_{1i}^y S_{2j}^y)/\Delta + S_{1i}^z S_{2j}^z] \\
& - B \sum_i (S_{1i}^z + S_{2i}^z).
\end{aligned} \tag{1}$$

Here, $J > 0$ is the dominant antiferromagnetic interaction within each layer for nearest-neighbor bonds $\langle ij \rangle$. J_{\perp} represents the interlayer nearest-neighbor interaction across bonds $\langle ij \rangle'$, and J_{\perp}^0 accounts for the intra-dimer interaction. The anisotropy parameter Δ is assumed to be uniform across all bonds. To explore the phase diagram, we perform classical Monte Carlo simulations on $L \times L \times 2$ clusters ($L = 24, 36, 48, 60$) with periodic boundary conditions. The order parameters are defined as

$$\begin{aligned}
\psi_K^x &= \frac{1}{L} \sum_i (S_{1i}^x e^{i\mathbf{q}_K \cdot \mathbf{r}_i} - S_{2i}^x e^{i\mathbf{q}_K \cdot \mathbf{r}_i}), \\
\psi_{K,\Gamma}^z &= \frac{1}{L} \sum_i (S_{1i}^z e^{i\mathbf{q}_{K,\Gamma} \cdot \mathbf{r}_i} - S_{2i}^z e^{i\mathbf{q}_{K,\Gamma} \cdot \mathbf{r}_i}),
\end{aligned} \tag{2}$$

where $\mathbf{q}_K = (\frac{4\pi}{3}, 0)$ and $\mathbf{q}_{\Gamma} = (0, 0)$. The minus sign reflects the antiferromagnetic interlayer interaction. ψ_K^x corresponds to the $U(1)$ spin rotational symmetry, while ψ_K^z and ψ_{Γ}^z are related to the discrete \mathbb{Z}_3 permutation symmetry and \mathbb{Z}_2^d bilayer dimer symmetry, respectively. We measure the Binder ratio [43, 44] $U = \frac{\langle |\psi|^4 \rangle}{\langle |\psi|^2 \rangle^2}$ and the correlation length [45, 46] $\xi(\mathbf{q}) = \frac{1}{|\delta\mathbf{q}|} \sqrt{\frac{\langle |\psi(\mathbf{q})|^2 \rangle}{\langle |\psi(\mathbf{q} + \delta\mathbf{q})|^2 \rangle}} - 1$ with $\delta\mathbf{q} = (2\pi/L, 0)$ for the corresponding order parameters $\psi(\mathbf{q})$. At critical points, the Binder ratio U and correlation length ratio ξ/L become size-independent, enabling us to determine the critical temperatures T_c .

The phase diagram for $J_{\perp}/J = 0.2$, $J_{\perp}^0/J = 1$, and $\Delta = 3$, shown in Fig. 4(a), reveals a rich variety of magnetic phases. Beyond the "Y" phase, which exhibits Berezinskii-Kosterlitz-Thouless (BKT)-like behavior and arises from $U(1)$ symmetry breaking of the c -axis spin rotation, three additional phases emerge due to S_3 symmetry breaking: the S_3 -broken tss phase, the \mathbb{Z}_3 -broken (uud) phase, and an intermediate BKT phase. While the exact experimental parameters of $\text{K}_2\text{Co}_2(\text{SeO}_3)_2$ remain undetermined, the theoretical phase diagram at low fields aligns remarkably well with the experimental results in Fig. 3(d), highlighting the validity of the model.

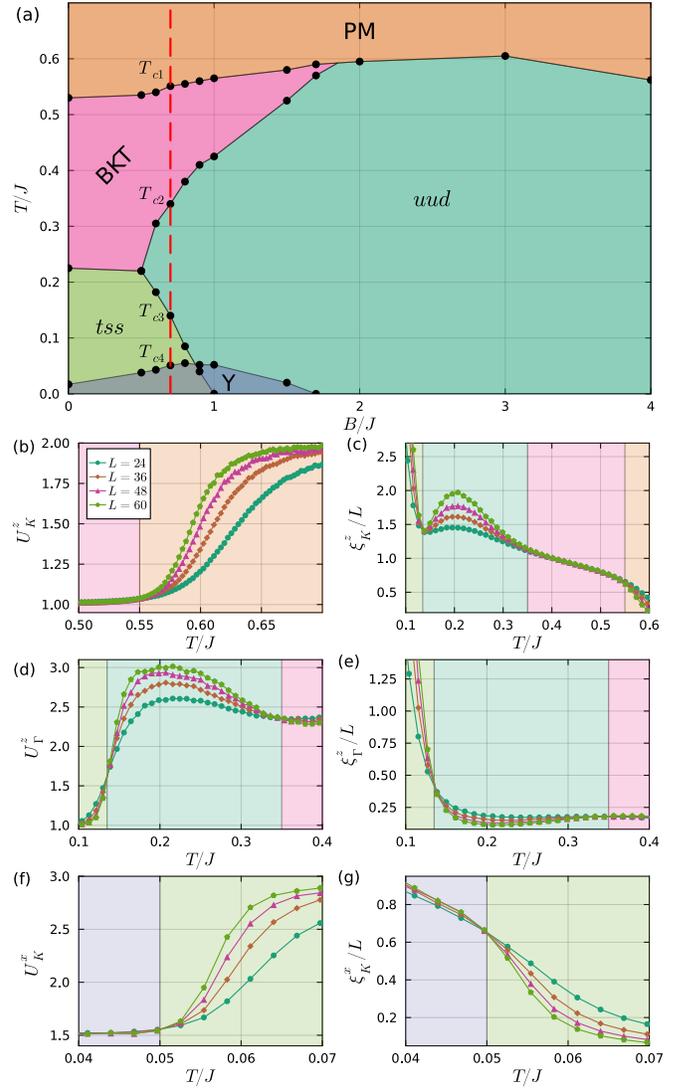


FIG. 4. (a) Phase diagram obtained from classical Monte Carlo simulations for the spin dimer system described by the model (1) with parameters $J_{\perp}^0 = J$, $J_{\perp} = 0.2J$, anisotropy $\Delta = 3$, and $J > 0$. The paramagnetic (PM) state preserves the $U(1) \otimes S_3$ symmetry. The "Y" phase is associated with $U(1)$ symmetry breaking. The uud state corresponds to the $1/3$ -magnetization plateau and is \mathbb{Z}_2^d -symmetric. The tss phase, representing the triplet-singlet-singlet configuration, corresponds to one of the six spin states shown in Fig. 1(c) and breaks S_3 symmetry. The BKT phase is characterized by intermediate algebraic spin correlations. (b)-(g) Binder ratio U and scaled correlation length ξ/L for various order parameters ψ_K^z , ψ_{Γ}^z , and ψ_K^x defined in Eq.(2) are shown for $B/J = 0.7$.

Figures 4(b)-(g) illustrate the determination of critical temperatures for a representative magnetic field $B/J = 0.7$. From high to low temperatures, the Binder ratio U for ψ_K^z [Fig. 4(b)] converges at $T_{c1} = 0.55J$ across different system sizes, signaling a BKT phase transition. This is further supported by the scaled correlation length ξ_K^z/L [Fig. 4(c)], which shows a size-independent behavior in the range $T_{c2} < T < T_{c1}$ ($T_{c2} = 0.35J$), confirming the BKT phase. At

$T_{c3} = 0.135J$, a transition related to the bilayer dimer \mathbb{Z}_2^d symmetry breaking is observed, as evidenced by the Binder ratio U_F^z [Fig. 4(d)] and the scaled correlation length ξ_F^z/L [Fig. 4(e)]. Finally, at $T_{c4} = 0.051J$, the Binder ratio U_K^x [Fig. 4(f)] and the scaled correlation length ξ_K^x/L [Fig. 4(g)] for ψ_K^x reveal a BKT-like transition driven by $U(1)$ symmetry breaking.

Discussions and Conclusions. – We have investigated the magnetic phases of the bilayer triangular antiferromagnet $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$, uncovering a rich interplay of geometric frustration, bilayer coupling, and symmetry-driven phase transitions. The remarkable agreement between theoretical and experimental phase diagrams at low fields validates the $U(1) \otimes S_3$ symmetry framework and highlights the pivotal role of $S_3 = \mathbb{Z}_3 \otimes \mathbb{Z}_2^d$ in shaping the phase structure. While holographic theory suggests the possibility of a continuous $S_3 \leftrightarrow \mathbb{Z}_1$ phase transition [32], our results reveal that this transition is not direct but proceeds via two steps, involving an intermediate \mathbb{Z}_2 -symmetric (*wud*) phase or a Berezinskii-Kosterlitz-Thouless (BKT) phase with algebraic spin correlations. Notably, the BKT phase forms a stable finite-field region in $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$, in contrast to the monolayer counterpart $\text{K}_2\text{Co}(\text{SeO}_3)_2$, where such behavior exists only at zero field. These findings establish $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$ as an ideal platform for exploring symmetry-driven phase transitions in frustrated magnets and open avenues for studying quantum phenomena and exotic spin dynamics stabilized by bilayer symmetry.

While the low-field phase diagram aligns well with experimental observations, high-field phases have received less attention in this work due to uncertainties in the magnetic exchange parameters. By fine-tuning parameters in the weak dimer limit, classical Monte Carlo simulations successfully reproduce the 1/3, 1/2, and 2/3 plateaus [47], but the experimentally observed 5/6 plateau suggests significant quantum effects or additional interactions beyond classical models. Future studies could further elucidate the role of bilayer coupling in enhancing frustration and stabilizing unconventional magnetic states in the whole phase diagram.

This work is supported by the National Natural Science Foundation of China (Grant No. 12474143), the National Key Research and Development Program of China (Grant No. 2021YFA1400400), and Shenzhen Fundamental Research Program (Grant No. JCYJ20220818100405013 and JCYJ20230807093204010). A portion of this work was carried out at the Steady High Magnetic Field Facilities, High magnetic Field Laboratory, CAS, Synergetic Extreme Condition User Facility (SECUF) and Wuhan National High Magnetic Field Center.

* xibin@yzu.edu.cn

† meijw@sustech.edu.cn

[1] V. Zapf, M. Jaime, and C. D. Batista, Bose-einstein condensa-

tion in quantum magnets, *Rev. Mod. Phys.* **86**, 563 (2014).

- [2] H. T. Diep, *Frustrated Spin Systems* (WORLD SCIENTIFIC, 2005) <https://www.worldscientific.com/doi/pdf/10.1142/5697>.
- [3] T. Ono, H. Tanaka, H. A. Katori, F. Ishikawa, H. Mitamura, and T. Goto, Magnetization plateau in the frustrated quantum spin system Cs_2CuBr_4 , *Phys. Rev. B* **67**, 104431 (2003).
- [4] J. Alicea, A. V. Chubukov, and O. A. Starykh, Quantum stabilization of the 1/3-magnetization plateau in Cs_2CuBr_4 , *Phys. Rev. Lett.* **102**, 137201 (2009).
- [5] H. D. Zhou, C. Xu, A. M. Hallas, H. J. Silverstein, C. R. Wiebe, I. Umegaki, J. Q. Yan, T. P. Murphy, J. H. Park, Y. Qiu, J. R. D. Copley, J. S. Gardner, and Y. Takano, Successive Phase Transitions and Extended Spin-Excitation Continuum in the $S=1/2$ Triangular-Lattice Antiferromagnet $\text{Ba}_3\text{CoSb}_2\text{O}_9$, *Phys. Rev. Lett.* **109**, 267206 (2012).
- [6] T. Susuki, N. Kurita, T. Tanaka, H. Nojiri, A. Matsuo, K. Kindo, and H. Tanaka, Magnetization Process and Collective Excitations in the $S=1/2$ Triangular-Lattice Heisenberg Antiferromagnet $\text{Ba}_3\text{CoSb}_2\text{O}_9$, *Phys. Rev. Lett.* **110**, 267201 (2013).
- [7] M. Lee, E. S. Choi, X. Huang, J. Ma, C. R. Dela Cruz, M. Matsuda, W. Tian, Z. L. Dun, S. Dong, and H. D. Zhou, Magnetic phase diagram and multiferroicity of $\text{Ba}_3\text{MnNb}_2\text{O}_9$: A spin- $5/2$ triangular lattice antiferromagnet with weak easy-axis anisotropy, *Phys. Rev. Lett.* **90**, 224402 (2014).
- [8] R. Zhong, S. Guo, G. Xu, Z. Xu, and R. J. Cava, Strong quantum fluctuations in a quantum spin liquid candidate with a Cobased triangular lattice, *Proceedings of the National Academy of Sciences* **116**, 14505 (2019).
- [9] N. Li, Q. Huang, X. Yue, W. Chu, Q. Chen, E. Choi, X. Zhao, H. Zhou, and X. Sun, Possible itinerant excitations and quantum spin state transitions in the effective spin- $1/2$ triangular-lattice antiferromagnet $\text{Na}_2\text{BaCo}(\text{PO}_4)_2$, *Nat. Commun.* **11**, 4216 (2020).
- [10] J. Sheng, L. Wang, A. Candini, W. Jiang, L. Huang, B. Xi, J. Zhao, H. Ge, N. Zhao, Y. Fu, *et al.*, Two-dimensional quantum universality in the spin- $1/2$ triangular-lattice quantum antiferromagnet $\text{Na}_2\text{BaCo}(\text{PO}_4)_2$, *Proceedings of the National Academy of Sciences* **119**, e2211193119 (2022).
- [11] N. Li, Q. Huang, A. Brassington, X. Yue, W. Chu, S. Guang, X. H. Zhou, P. Gao, E. X. Feng, H. B. Cao, *et al.*, Quantum spin state transitions in the spin-1 equilateral triangular lattice antiferromagnet $\text{Na}_2\text{BaNi}(\text{PO}_4)_2$, *Phys. Rev. B* **104**, 104403 (2021).
- [12] J. Sheng, J.-W. Mei, L. Wang, W. Jiang, L. Xu, H. Ge, N. Zhao, T. Li, A. Candini, B. Xi, J. Zhao, Y. Fu, J. Yang, Y. Zhang, G. Biasiol, S. Wang, J. Zhu, P. Miao, X. Tong, D. Yu, R. Mole, L. Ma, Z. Zhang, Z. Ouyang, W. Tong, A. Podlesnyak, L. Wang, F. Ye, D. Yu, L. Wu, and Z. Wang, Bose-einstein condensation of a two-magnon bound state in a spin-one triangular lattice (2023), [arXiv:2306.09695 \[cond-mat.str-el\]](https://arxiv.org/abs/2306.09695).
- [13] R. Zhong, S. Guo, and R. Cava, Frustrated magnetism in the layered triangular lattice materials $\text{K}_2\text{Co}(\text{SeO}_3)_2$ and $\text{Rb}_2\text{Co}(\text{SeO}_3)_2$, *Phys. Rev. Mat.* **4**, 084406 (2020).
- [14] M. Zhu, V. Romerio, N. Steiger, S. Nabi, N. Murai, S. Ohira-Kawamura, K. Y. Povarov, Y. Skourski, R. Sibille, L. Keller, *et al.*, Continuum excitations in a spin supersolid on a triangular lattice, *Phys. Rev. Lett.* **133**, 186704 (2024).
- [15] T. Chen, A. Ghasemi, J. Zhang, L. Shi, Z. Tagay, L. Chen, E.-S. Choi, M. Jaime, M. Lee, Y. Hao, *et al.*, Phase Diagram and Spectroscopic Evidence of Supersolids in Quantum Ising Magnet $\text{K}_2\text{Co}(\text{SeO}_3)_2$, [arXiv preprint arXiv:2402.15869](https://arxiv.org/abs/2402.15869) (2024).
- [16] R. Ishii, S. Tanaka, K. Onuma, Y. Nambu, M. Tokunaga, T. Sakakibara, N. Kawashima, Y. Maeno, C. Broholm, D. P. Gautreaux, J. Y. Chan, and S. Nakatsuji, Successive phase transitions and phase diagrams for the quasi-two-dimensional easy-axis triangular antiferromagnet $\text{Rb}_4\text{Mn}(\text{MoO}_4)_3$, *EPL (Euro-*

- physics Letters) **94**, 17001 (2009).
- [17] A. Aczel, Y. Kohama, M. Jaime, K. Niiyos, H. B. Chan, L. Balicas, H. Dabkowska, and G. Luke, Bose-einstein condensation of triplons in $\text{Ba}_3\text{Cr}_2\text{O}_8$, *Phys. Rev. B* **79**, 100409 (2009).
- [18] M. Kofu, J.-H. Kim, S. Ji, S.-H. Lee, H. Ueda, Y. Qiu, H.-J. Kang, M. Green, and Y. Ueda, Weakly coupled $s=1/2$ quantum spin singlets in $\text{Ba}_3\text{Cr}_2\text{O}_8$, *Phys. Rev. Lett.* **102**, 037206 (2009).
- [19] R. Zhong, S. Guo, L. T. Nguyen, and R. J. Cava, Frustrated spin-1/2 dimer compound $\text{K}_2\text{Co}_2(\text{SeO}_3)_3$ with easy-axis anisotropy, *Phys. Rev. B* **102**, 224430 (2020).
- [20] Z. Li, Z. Ouyang, J. Cao, L. Wang, Z. Wang, Z. Xia, and J. Wang, Magnetism in the $s=1$ triangular dimer lattice antiferromagnet $\text{K}_2\text{Ni}_2(\text{SeO}_3)_3$, *Phys. Rev. B* **109**, 224413 (2024).
- [21] L. Yue, Z. Lu, K. Yan, L. Wang, S. Guo, R. Guo, P. Chen, X. Chen, and J.-W. Mei, Magnetic phase transitions in the triangular-lattice spin-1 dimer compound $\text{K}_2\text{Ni}_2(\text{SeO}_3)_3$, *Phys. Rev. B* **109**, 214430 (2024).
- [22] S. Miyashita, Magnetic properties of ising-like heisenberg antiferromagnets on the triangular lattice, *Journal of the Physical Society of Japan* **55**, 3605 (1986).
- [23] S. Miyashita, Phase transition in spin systems with various types of fluctuations, *Proceedings of the Japan Academy, Series B* **86**, 643 (2010).
- [24] P.-E. Melchy and M. E. Zhitomirsky, Interplay of anisotropy and frustration: Triple transitions in a triangular-lattice antiferromagnet, *Phys. Rev. B* **80**, 064411 (2009).
- [25] J. V. José, L. P. Kadanoff, S. Kirkpatrick, and D. R. Nelson, Renormalization, vortices, and symmetry-breaking perturbations in the two-dimensional planar model, *Phys. Rev. B* **16**, 1217 (1977).
- [26] F. Y. Wu, The potts model, *Rev. Mod. Phys.* **54**, 235 (1982).
- [27] A. V. Chubukov and D. I. Golosov, Quantum theory of an antiferromagnet on a triangular lattice in a magnetic field, *Journal of Physics: Condensed Matter* **3**, 69 (1991).
- [28] Q. Sheng and C. L. Henley, Ordering due to disorder in a triangular Heisenberg antiferromagnet with exchange anisotropy, *Journal of Physics: Condensed Matter* **4**, 2937 (1992).
- [29] B. Nienhuis, Critical behavior of two-dimensional spin models and charge asymmetry in the coulomb gas, *Journal of Statistical Physics* **34**, 731 (1984).
- [30] L. D. Landau, On the theory of phase transitions, *Zh. Eksp. Teor. Fiz.* **7**, 19 (1937).
- [31] W. Ji and X.-G. Wen, Categorical symmetry and noninvertible anomaly in symmetry-breaking and topological phase transitions, *Phys. Rev. Res.* **2**, 033417 (2020).
- [32] A. Chatterjee and X.-G. Wen, Holographic theory for continuous phase transitions: Emergence and symmetry protection of gaplessness, *Phys. Rev. B* **108**, 075105 (2023).
- [33] Z. Hu, Z. Ma, Y.-D. Liao, H. Li, C. Ma, Y. Cui, Y. Shanguan, Z. Huang, Y. Qi, W. Li, *et al.*, Evidence of the Berezinskii-Kosterlitz-Thouless phase in a frustrated magnet, *Nat. Commun.* **11**, 5631 (2020).
- [34] G. V. Chen, Emergent Berezinskii-Kosterlitz-Thouless and Kugel-Khomskii Physics in the Triangular Lattice Bilayer Cobaltate, *Phys. Rev. Lett.* **133**, 136703 (2024).
- [35] K. Hukushima and K. Nemoto, Exchange Monte Carlo Method and Application to Spin Glass Simulations, *Journal of the Physical Society of Japan* **65**, 1604 (1996).
- [36] Y. Miyatake, M. Yamamoto, J. J. Kim, M. Toyonaga, and O. Nagai, On the implementation of the 'heat bath' algorithms for Monte Carlo simulations of classical Heisenberg spin systems, *Journal of Physics C: Solid State Physics* **19**, 2539 (1986).
- [37] J. B. Goodenough, Goodenough-Kanamori rule, *Scholarpedia* **3**, 7382 (2008), revision #122456.
- [38] B. Leuenberger, B. Briat, J. C. Canit, A. Furrer, P. Fischer, and H. U. Guedel, Synthesis, structural characterization, and magnetic properties of vanadium (3+) dimer compounds. neutron scattering and magnetic circular dichroism study of cesium chlorovanadate ($\text{Cs}_3\text{V}_2\text{Cl}_9$) and rubidium bromovanadate ($\text{Rb}_3\text{V}_2\text{Br}_9$), *Inorganic Chemistry* **25**, 2930 (1986).
- [39] Y. Ishii, Y. Narumi, Y. Matsushita, M. Oda, T. Kida, M. Hagiwara, and H. Yoshida, Field-induced successive phase transitions in the J_1 - J_2 buckled honeycomb antiferromagnet $\text{Cs}_3\text{Fe}_2\text{Cl}_9$, *Phys. Rev. B* **103**, 104433 (2021).
- [40] S. Gao, C. Pasco, O. Omar, Q. Zhang, D. M. Pajerowski, F. Ye, M. Frontzek, A. F. May, M. B. Stone, and A. D. Christianson, Codimension-two spiral spin-liquid in the effective honeycomb-lattice compound $\text{Cs}_3\text{Fe}_2\text{Cl}_9$, *arXiv preprint arXiv:2405.18973* (2024).
- [41] A. Aczel, Y. Kohama, C. Marcenat, F. Weickert, M. Jaime, O. Ayala-Valenzuela, R. McDonald, S. Selesnic, H. Dabkowska, and G. Luke, Field-induced Bose-Einstein condensation of triplons up to 8 K in $\text{Sr}_3\text{Cr}_2\text{O}_8$, *Phys. Rev. Lett.* **103**, 207203 (2009).
- [42] K. Onizuka, H. Kageyama, Y. Narumi, K. Kindo, Y. Ueda, and T. Goto, 1/3 magnetization plateau in $\text{SrCu}_2(\text{BO}_3)_2$ -stripe order of excited triplets, *Journal of the Physical Society of Japan* **69**, 1016 (2000).
- [43] K. Binder, Finite size scaling analysis of ising model block distribution functions, *Zeitschrift für Physik B Condensed Matter* **43**, 119 (1981).
- [44] K. Binder and D. Heermann, *Monte Carlo Simulation in Statistical Physics: An Introduction*, Graduate Texts in Physics (Springer Berlin Heidelberg, 2010).
- [45] D. X. Viet and H. Kawamura, Monte carlo studies of chiral and spin ordering of the three-dimensional heisenberg spin glass, *Phys. Rev. B* **80**, 064418 (2009).
- [46] L. Seabra, T. Momoi, P. Sindzingre, and N. Shannon, Phase diagram of the classical heisenberg antiferromagnet on a triangular lattice in an applied magnetic field, *Phys. Rev. B* **84**, 214418 (2011).
- [47] Supplementary Materials.