

Optical control of the crystal structure in the bilayer nickelate superconductor $\text{La}_3\text{Ni}_2\text{O}_7$ via nonlinear phononics

Shu Kamiyama,¹ Tatsuya Kaneko,¹ Kazuhiko Kuroki,¹ and Masayuki Ochi^{1,2}

¹*Department of Physics, Osaka University, Toyonaka, Osaka 560-0043, Japan*

²*Forefront Research Center, Osaka University, 1-1 Machikaneyama-cho, Toyonaka, Osaka 560-0043, Japan*

(Dated: January 22, 2025)

Superconductivity in the bilayer nickelate $\text{La}_3\text{Ni}_2\text{O}_7$ occurs when the interlayer Ni-O-Ni bond angle becomes straight under pressure, suggesting a strong relationship between the crystal structure and the emergence of superconductivity. In this study, we theoretically propose a way to control the crystal structure of $\text{La}_3\text{Ni}_2\text{O}_7$ toward the tetragonal symmetry via light irradiation instead of pressure using the idea of nonlinear phononics. Here, resonant optical excitation of an infrared-active (IR) lattice vibration induces a nonlinear Raman-mode displacement through the anharmonic phonon-phonon coupling. We calculate the light-induced phonon dynamics on the anharmonic lattice potential determined by first-principles calculation. We find that the interlayer Ni-O-Ni bond angle gets slightly closer to straight when an appropriate IR mode is selectively excited. Our study suggests that light irradiation can be a promising way for structural control of $\text{La}_3\text{Ni}_2\text{O}_7$.

I. INTRODUCTION

A recently discovered unconventional superconductor, bilayer nickel oxide $\text{La}_3\text{Ni}_2\text{O}_7$, with a maximum transition temperature T_c of 80 K at around 15–40 GPa has garnered significant attention [1–35]. This material is a member of the bilayer Ruddlesden-Popper compounds, where two NiO_2 planes are connected via inner apical oxygens. As pointed out in an earlier study by one of the present authors [36], $\text{La}_3\text{Ni}_2\text{O}_7$ is a system where a nearly half-filled $\text{Ni}-d_{3z^2-r^2}$ orbital hybridized with a $\text{Ni}-d_{x^2-y^2}$ orbital constitutes a bilayer square lattice, which is one of the promising playgrounds of high-temperature superconductivity [37–48]. While the origin of superconductivity is likely unconventional [49–51], a complicated role of the $\text{Ni}-d_{3z^2-r^2}$ and $d_{x^2-y^2}$ orbitals with strong hybridization remains under debate.

$\text{La}_3\text{Ni}_2\text{O}_7$ undergoes a structural transition from the orthorhombic *Amam* phase into the orthorhombic *Fmmm* phase or the tetragonal *I4/mmm* phase [52–54]. The Ni-O-Ni interlayer bond angle θ is around 168° [1] at ambient pressure [see, Fig. 1(a)], and becomes straight in the *Fmmm* or *I4/mmm* phases [see, Fig. 1(b)]. Superconductivity in $\text{La}_3\text{Ni}_2\text{O}_7$ emerges under high pressure where the crystal structure becomes tetragonal [52–54], which suggests a strong relationship between the tetragonal symmetry of the crystal structure and the emergence of superconductivity. It is also noteworthy that a trilayer nickelate $\text{La}_4\text{Ni}_3\text{O}_{10}$ also exhibits superconductivity by applying sufficient pressure where the tetragonal phase is realized [55–59].

From this perspective, one important direction in the study of bilayer nickelate superconductors is to realize the tetragonal structure at ambient pressure. Atomic substitution that stabilizes the tetragonal phase is a possible way. However, rather higher pressure is required to stabilize the tetragonal phase by replacing La with other lanthanoids because La has the largest ionic radius among them [22, 52]. Therefore, some previous studies

have proposed the replacement of La with actinium or alkaline-earth elements such as Sr and Ba, which have a larger ionic radius than La [60, 61]. Two of the present authors proposed that $\text{Sr}_3\text{Ni}_2\text{O}_5\text{Cl}_2$ is a promising candidate [62, 63] where a larger ionic radius of Sr^{2+} than La^{3+} and a smaller ionic radius of Ni^{3+} than $\text{Ni}^{2.5+}$ favor the tetragonal structure even at ambient pressure as shown by first-principles phonon calculation. Here, while the valence number of nickel is different from $\text{La}_3\text{Ni}_2\text{O}_7$, a crystal field of a NiO_5Cl octahedron lowers the $d_{3z^2-r^2}$ orbital energy and thus a nearly half-filled $d_{3z^2-r^2}$ is realized. It is also noteworthy that recent experiments reported ambient-pressure superconductivity in thin-film $\text{La}_3\text{Ni}_2\text{O}_7$ [64, 65], where the compressive strain likely reduces the octahedral tilting in the superconducting samples [66] while the atomic positions therein are at present unknown.

Another fascinating idea for approaching the tetragonal phase is to manipulate the crystal structure using light instead of applying pressure based on nonlinear phononics [67–83]. In nonlinear phononics, resonant optical excitation of an infrared-active (IR) lattice vibration induces a nonlinear Raman-mode displacement through the anharmonic phonon-phonon coupling. While a change in the crystal structure is transient, a sufficiently longer timescale of phonons than electrons allows us to investigate how structural changes affect electronic states of materials. The generation of intense pulses at mid-infrared and terahertz (THz) frequencies has made nonlinear phononics experimentally possible, and the development of probe techniques has enabled us to measure ultrafast dynamics of quantum materials [67, 82]. Nonlinear phononics has been applied to cuprate superconductors [68–70], ferroelectrics [71–74], magnetic materials [74–78], and topological materials [79, 80].

Based on the idea of nonlinear phononics, in this study, we theoretically investigate the possibility of controlling the crystal structure of $\text{La}_3\text{Ni}_2\text{O}_7$ toward the tetragonal phase by light irradiation. We demonstrate that Raman

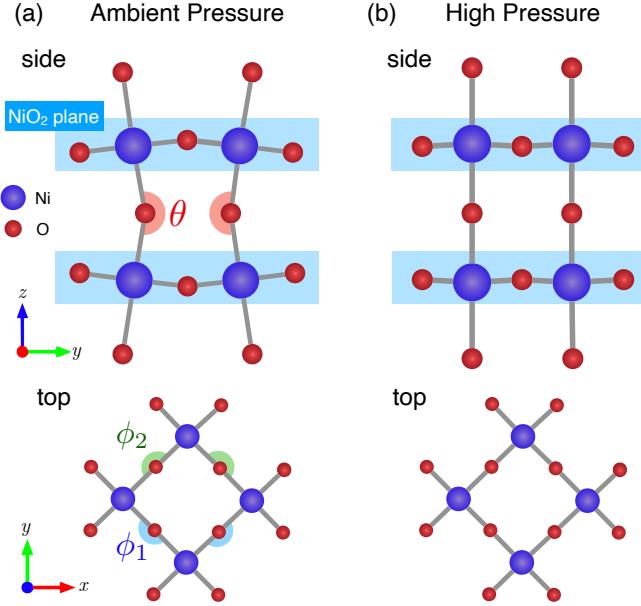


FIG. 1. Crystal structure of $\text{La}_3\text{Ni}_2\text{O}_7$ under (a) ambient pressure and (b) high pressure.

modes that can make the system closer to the tetragonal phase are activated through the anharmonic coupling with an IR mode resonantly excited by light. We calculate the optically driven phonon dynamics using the anharmonic lattice potential determined by first-principles calculation. We find that the interlayer Ni-O-Ni bond angle gets slightly closer to straight when an appropriate IR mode is selectively excited. Our study suggests that nonlinear phononics offers a promising pathway to approach the tetragonal crystal structures of the multilayer nickelate superconductors without applying pressure.

This paper is organized as follows. Methods for first-principles calculations and phonon dynamics are described in Secs. II A and II B, respectively. First-principles construction of the anharmonic lattice potential is described in Sec. III A. In Sec. III B, we present calculation results of phonon dynamics and specify the target IR mode for resonant optical excitation that can effectively modulate the crystal structure toward the tetragonal phase. The field-amplitude dependence of the structural modulation is discussed in Sec. III C. Other possible candidates for the target IR mode are suggested in Sec. III D. Discussions are shown in Sec. IV. Section V summarizes the study.

II. METHODS

A. First-principles calculation and anharmonic lattice potential

First-principles calculations based on the density functional theory (DFT) are performed by using the

PBEsol [84, 85] exchange-correlation functional as implemented in Vienna *ab initio* simulation package (VASP) [86–90]. We use a plane-wave cutoff energy of 600 eV for Kohn-Sham orbitals and an $8 \times 8 \times 8$ Monkhorst-Pack \mathbf{k} -mesh. We perform structural optimization until the Hellmann-Feynman force becomes less than 0.01 eV \AA^{-1} for each atom. Both the lattice parameters and atomic coordinates are optimized for the orthorhombic structure (space group: $Amam$). The optimized interlayer Ni-O-Ni angle is 170.4° , which is close to the experimental value [1], 168° . Phonon calculation is performed using the frozen-phonon method as implemented in Phonopy [91, 92]. To describe the optical response, we only calculate the Γ -point phonons [68, 69]. We analyze irreducible representation of each phonon mode for the point group mmm . The irreducible representations and frequencies of all eigenmodes are presented in Appendix A (Table II).

Next, we construct the anharmonic lattice potential based on our first-principles calculation. The anharmonic lattice potential for a pair of the IR and Raman modes are expressed with their amplitudes Q_{IR} and Q_{R} as follows:

$$\begin{aligned} V(Q_{\text{IR}}, Q_{\text{R}}) &= \frac{1}{2}\omega_{\text{IR}}^2 Q_{\text{IR}}^2 + \frac{1}{2}\omega_{\text{R}}^2 Q_{\text{R}}^2 - \frac{1}{2}g_{\text{IR}-\text{R}} Q_{\text{IR}}^2 Q_{\text{R}} \\ &\quad + a_{3;\text{R}} Q_{\text{R}}^3 + a_{4;\text{R}} Q_{\text{R}}^4 + b_{4;\text{IR}} Q_{\text{IR}}^4 - \frac{1}{2}h_{\text{IR}-\text{R}} Q_{\text{IR}}^2 Q_{\text{R}}^2, \end{aligned} \quad (1)$$

where ω_{IR} and ω_{R} are the phonon frequencies of the IR and Raman modes, respectively. The other coefficients are determined by fitting this equation to the DFT total energies in the way described in Sec. III A. Symmetry constraints on the lattice potential are as follows. First, due to the space inversion symmetry, an odd-order term of Q_{IR} is not allowed in Eq. (1). In addition, $g_{\text{IR}-\text{R}}$ is non-zero only for the A_g Raman modes because Q_{IR}^2 for any IR mode belongs to A_g for the present crystal symmetry. While $h_{\text{IR}-\text{R}}$ can be non-zero for the other Raman modes, $-\frac{1}{2}h_{\text{IR}-\text{R}} Q_{\text{IR}}^2 Q_{\text{R}}^2$ does not shift the potential minimum to $Q_{\text{R}} \neq 0$ unlike $-\frac{1}{2}g_{\text{IR}-\text{R}} Q_{\text{IR}}^2 Q_{\text{R}}$. Since the modulation of the crystal structure by shifting the potential minimum to $Q_{\text{R}} \neq 0$ for non-zero Q_{IR} is the central purpose of the study of nonlinear phononics, hereafter, we only consider A_g Raman modes, which have non-zero $g_{\text{IR}-\text{R}}$. The phonon frequency and the irreducible representation for all the IR and A_g Raman modes are listed in Table I. Eigenmodes for these phonons are presented in Appendix A. Several approximations adopted for our lattice potential are discussed in Sec. IV.

B. Equation of motion for phonon dynamics

In this study, we consider the case where a specific IR mode is resonantly excited by the optical pulse field, and Raman oscillations are induced through the IR-Raman coupling. Therefore, all the A_g Raman modes R_1, \dots, R_n

label	irr.	$\omega_R/2\pi$ (THz)	label	irr.	$\omega_{IR}/2\pi$ (THz)
9	A_g	2.709	29	B_{1u}	5.563
13	A_g	3.760	30	B_{2u}	6.188
19	A_g	4.643	34	A_u	7.259
28	A_g	5.552	36	B_{3u}	7.485
32	A_g	6.637	37	B_{1u}	7.526
33	A_g	6.730	40	B_{2u}	7.927
50	A_g	9.852	42	B_{2u}	8.548
57	A_g	11.218	43	A_u	8.635
58	A_g	11.595	44	B_{3u}	8.875
61	A_g	13.133	45	B_{3u}	9.337
label irr. $\omega_{IR}/2\pi$ (THz)		46	B_{1u}	9.495	
4	B_{1u}	1.959	48	B_{2u}	9.779
6	B_{2u}	2.207	53	B_{2u}	10.309
11	A_u	3.047	54	A_u	10.819
14	B_{3u}	3.846	55	B_{3u}	10.947
15	B_{1u}	3.993	59	B_{3u}	12.289
17	B_{2u}	4.307	62	B_{2u}	13.678
18	B_{2u}	4.552	63	B_{1u}	14.855
22	B_{3u}	4.755	66	B_{3u}	15.636
23	B_{3u}	4.844	67	B_{2u}	17.942
25	B_{1u}	4.895	70	B_{1u}	19.171
27	A_u	5.127	72	B_{2u}	19.274

TABLE I. Irreducible representation (irr.) and phonon frequency ω for all the IR and A_g Raman modes at the Γ point. A label runs from the lowest frequency mode.

are included in the following equation. We numerically solve the classical equation of motion for the anharmonic lattice potential,

$$\ddot{Q}_{IR} + \omega_{IR}^2 Q_{IR} = F(t) - 4b_{4;IR} Q_{IR}^3 \quad (2a)$$

$$+ \sum_R (g_{IR-R} Q_{IR} Q_R + h_{IR-R} Q_{IR} Q_R^2)$$

$$\ddot{Q}_R + \omega_R^2 Q_R = \frac{1}{2} g_{IR-R} Q_{IR}^2 + h_{IR-R} Q_{IR}^2 Q_R \quad (2b)$$

$$- 3a_{3;R} Q_R^2 - 4a_{4;R} Q_R^3 \quad (R = R_1, \dots, R_n),$$

where $F(t) = F_0 e^{-t^2/2\sigma^2} \cos \Omega t$ is the driving force generated by the external light pulse. The half-width of the Gaussian function is represented as $\tau = 2\sqrt{2 \ln 2} \sigma$. We set $F_0 = 20 \text{ meV}\text{\AA}^{-1} \text{amu}^{-1/2}$ and $\tau = 0.3 \text{ ps}$ unless otherwise noted. The field frequency Ω is set as $\Omega = \omega_{IR}$, where the IR phonon is resonantly excited. Note that damping factors are not considered in the equations of motions (see discussions in Sec. IV). A key feature of these equations is that a driving force of the Raman-mode oscillation in Eq. (2b) is proportional to Q_{IR}^2 , resulting in the nonlinear response of the Raman modes and the time-averaged crystal structure with net displacements [82].

After the light pulse irradiation (i.e., $F(t) \simeq 0$ for a sufficiently large t), the time-averaged crystal structure is modulated by A_g Raman modes while the time average of the IR oscillation becomes zero. Thus, the time-averaged crystal structure is analyzed based on the original *Amam* space group since A_g modes fully preserve the crystal symmetry. We focus on the Ni-O-Ni bond angles:

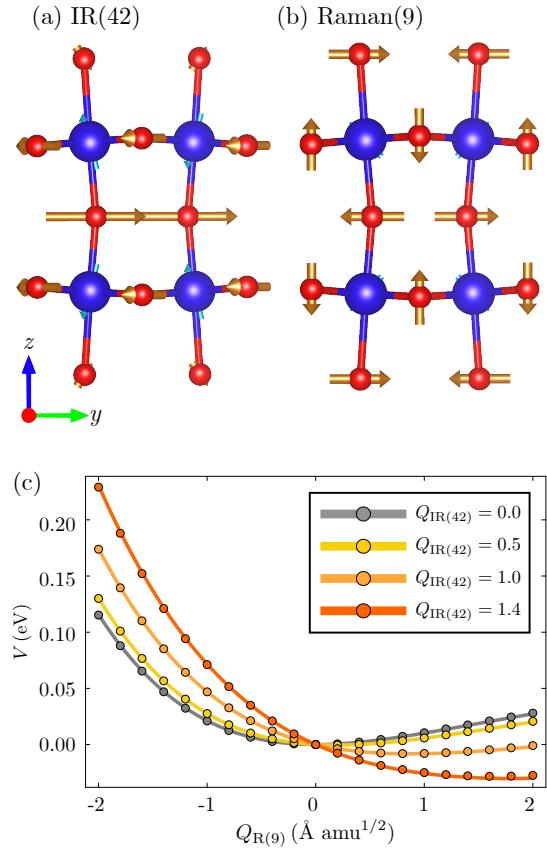


FIG. 2. Atomic displacements for the (a) IR(42) and (b) Raman(9) modes depicted using VESTA [93]. (c) Anharmonic lattice potential $V(Q_{IR}, Q_R)$ for the IR(42) and Raman(9) modes, where each circles represent DFT values and curves represent lattice potential fitted by Eq. (1), respectively.

interlayer angle θ and in-plane angles ϕ_1 and ϕ_2 as defined in Fig. 1(a). Here, there are only two inequivalent in-plane angles due to the reflection symmetry. We note that two NiO_2 planes can be transformed each other via the space inversion symmetry, and so there are no additional inequivalent in-plane angles. Since the octahedral rotation in the top view of the crystal structure is not allowed for the *Amam* space group, $\phi_1, \phi_2 \neq \pi$ represents the buckling of the NiO_2 plane partially caused by the octahedral tilting. The relationship between the phonon amplitude Q_α for mode α and the displacement vector $\mathbf{U}_{\alpha,j}$ for atom j is expressed as

$$\mathbf{U}_{\alpha,j} = \frac{Q_\alpha}{\sqrt{m_j}} \mathbf{e}_{\alpha,j}, \quad (3)$$

where m_j is the mass of atom j and $\mathbf{e}_{\alpha,j}$ is the dimensionless eigenvector of the phonon mode.

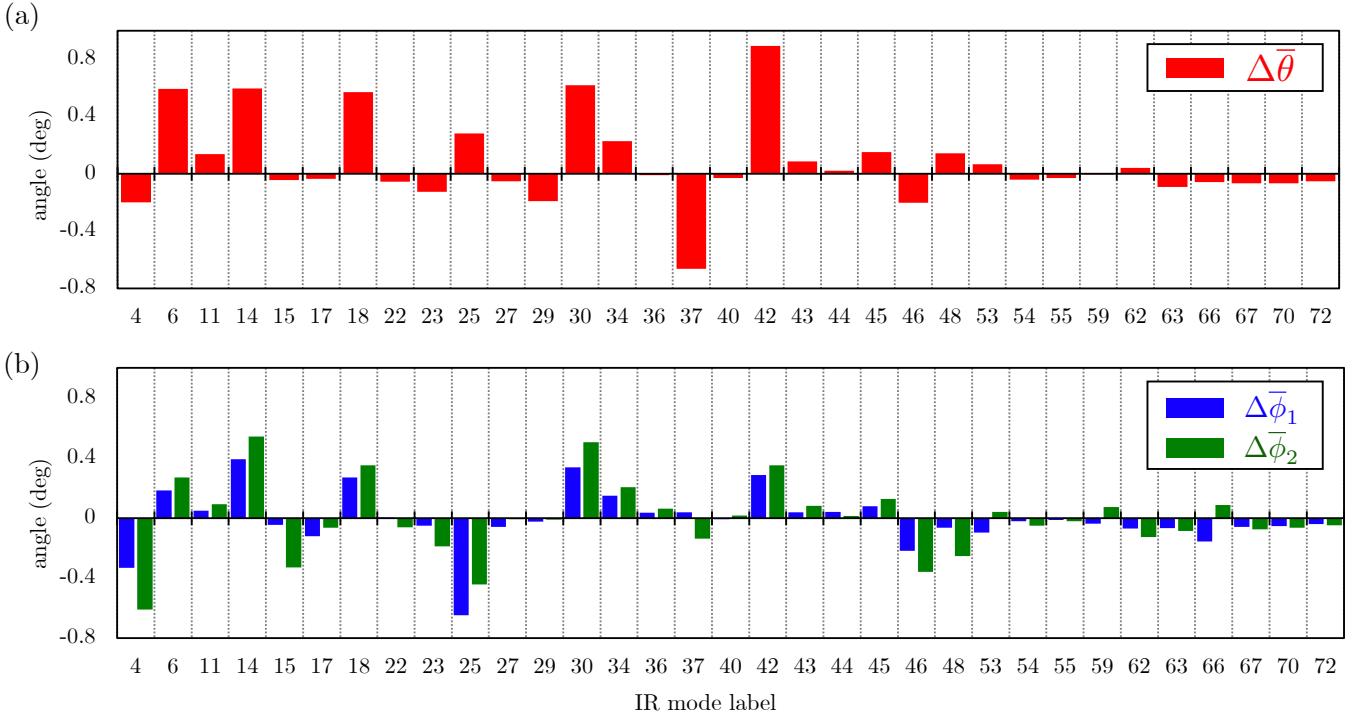


FIG. 3. Time-averaged change of the bond angles, (a) $\Delta\bar{\theta}$, (b) $\Delta\bar{\phi}_1$ and $\Delta\bar{\phi}_2$, from the original structure after light irradiation. The horizontal axis represents the label of the IR mode resonantly excited. Time-averaged angles correspond to the dotted lines in Figs. 4(b)–4(d).

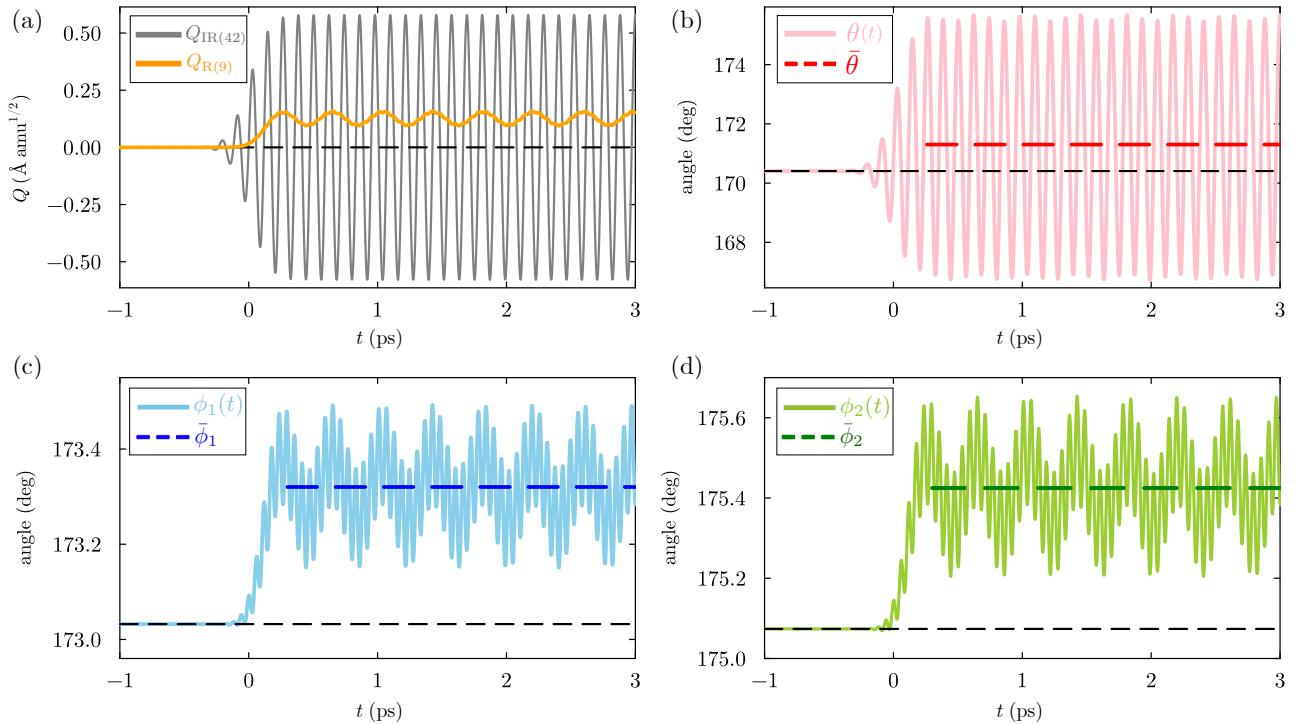


FIG. 4. Time evolution of (a) phonon amplitudes Q and (b)–(d) bond angles for the case where IR(42) is resonantly excited. In (a), $Q_{\text{IR}(42)}$ and $Q_{\text{R}(9)}$ are shown as representatives. In (b)–(d), the bond angles before light irradiation and the time-averaged angles after light pulse irradiation are shown with dashed lines together with the time evolution of each angle shown with a solid line.

III. RESULTS

A. First-principles construction of the anharmonic lattice potential

We determine the coefficients in the anharmonic lattice potential, Eq. (1), by fitting this equation to the DFT total energies in the following way. First, we use the phonon frequencies ω_{IR} and ω_{R} obtained by first-principles phonon calculation, which are listed in Table I. Next, $a_{3;\text{R}}$ and $a_{4;\text{R}}$ are determined by the fourth-order polynomial fitting using the DFT total energies for various $Q_{\text{R}} \in [-2.0, 2.0] \text{ \AA amu}^{1/2}$ with $Q_{\text{IR}} = 0$. The same fitting is performed for $b_{4;\text{IR}}$ using the DFT total energies for various $Q_{\text{IR}} \in [-2.0, 2.0] \text{ \AA amu}^{1/2}$ with $Q_{\text{R}} = 0$. Finally, we determine the IR-Raman coupling coefficients $g_{\text{IR-R}}$ and $h_{\text{IR-R}}$ by the second-order polynomial fitting as a function of Q_{R} using the DFT total energies of $Q_{\text{IR}} = 1.0$ and various $Q_{\text{R}} \in [-0.6, 0.6] \text{ \AA amu}^{1/2}$.

For example, the obtained $V(Q_{\text{IR}}, Q_{\text{R}})$ for IR(42) and Raman(9) eigenmodes, of which are shown in Figs. 2(a) and 2(b), is presented in Fig. 2(c) with curves for various Q_{IR} . Here, Raman(9) is a phonon mode that brings the crystal structure closer to the tetragonal structure. $V(Q_{\text{IR}}, Q_{\text{R}})$ agrees well with the DFT total energies shown with circles, which demonstrates that the fitting procedure described above works well. As is evident in Eq. (1), the minimum of the potential curve with respect to Q_{R} is shifted when Q_{IR} is non-zero in Fig. 2(c).

B. Nonlinear phonon dynamics and modulation of the crystal structure

A goal of this study is to modulate the crystal structure toward the tetragonal phase at ambient pressure via resonant optical excitation of a specific IR mode and induced Raman oscillations through phonon-phonon coupling. Therefore, we compare $\bar{\theta}$, $\bar{\phi}_1$, and $\bar{\phi}_2$ among the cases where each IR mode is excited, and identify which IR mode is a good target for optical excitation in the following way.

Figure 3 presents the time-averaged change in the bond angles, $\Delta\bar{\theta}$, $\Delta\bar{\phi}_1$, and $\Delta\bar{\phi}_2$, for each case where a specific IR mode is optically excited [94]. In Fig. 3(a), we find that the IR(42) mode with $\omega_{\text{IR}(42)} = 8.65 \text{ THz}$ is the most promising because $\Delta\bar{\theta} = 0.8^\circ$ is the largest, i.e., the interlayer Ni-O-Ni angle most effectively becomes close to straight. By calculating the band structure for the modulated crystal structure (see, Appendix B), we find that the bilayer splitting energy of Ni- $d_{3z^2-r^2}$ bands increases, i.e., the bilayer coupling becomes strong, in the dynamically modified crystal structure, likely due to the reduced octahedral tilting. In Fig. 3(b), we also find that the in-plane bond angles driven via IR(42) also increase, which indicates a suppressed buckling of the NiO_2 plane. Figure 4 presents the time evolution of phonon amplitudes Q and the bond angles when IR(42) is optically

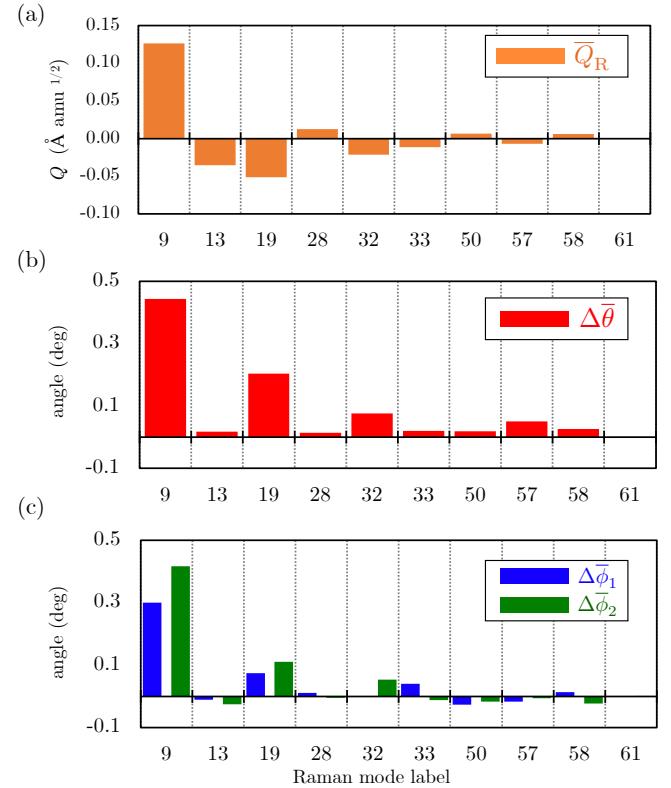


FIG. 5. (a) Time-averaged phonon amplitude after light irradiation for each Raman mode and (b)–(c) changes in the bond angles induced by each Raman mode, for the case where IR(42) is optically excited. For (b)–(c), bond angles are calculated for the crystal structure with atomic displacement of each \bar{Q}_{R} .

excited. As seen in Fig. 4(a), the centers of oscillation for Q_{R} and the bond angles are shifted by the optical pulse as the consequence of the nonlinear oscillation of Raman modes.

We further investigate the case where IR(42) is optically excited. Figure 5(a) presents a time-averaged phonon amplitude after light irradiation for each Raman mode. We find that the time-averaged shift, \bar{Q}_{R} , is the largest for Raman(9) among the A_g Raman modes. By calculating the bond angles for the crystal structure with the time-averaged modulation \bar{Q}_{R} for each Raman mode, we evaluate the contribution of each mode on the bond angles [see Figs. 5(b)–5(c)]. We find that $\Delta\bar{\theta}$ for Raman(9) is the largest among the A_g Raman modes, indicating that the octahedral tilting is efficiently alleviated by Raman(9). In fact, the crystal structure approaches the tetragonal phase by positive $Q_{\text{R}(9)}$ as shown in Fig. 2(b) presenting the Raman(9) phonon mode and Fig. 6(a) presenting the bond angles as a function of $Q_{\text{R}(9)}$. As shown in Fig. 2(b) and Fig. 5(c), the buckling of NiO_2 plane partially induced by the octahedral tilting is also alleviated for a positive $Q_{\text{R}(9)}$.

The IR-Raman(9) coupling coefficient $g_{\text{IR-R}(9)}$ is the largest for IR(42) among all the IR modes as shown in

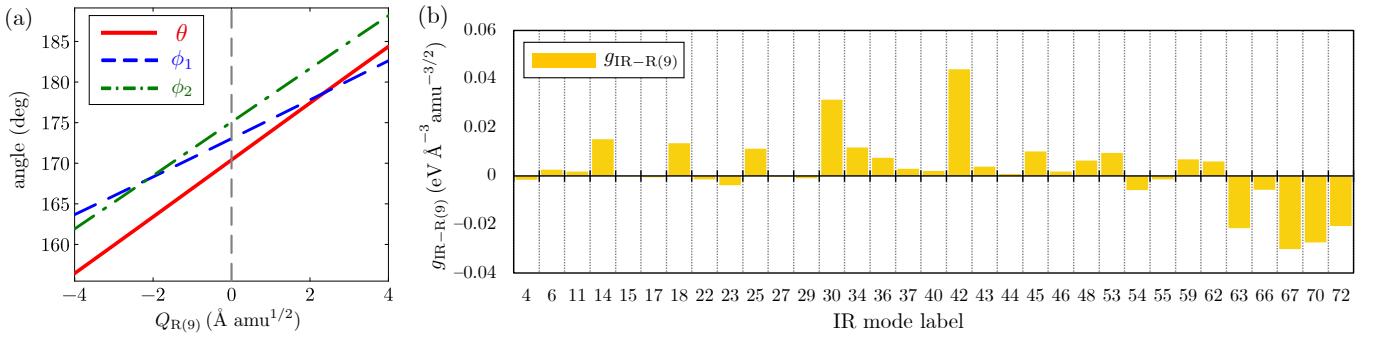


FIG. 6. (a) Bond angles defined in Fig. 1(a) plotted against the amplitude of Raman(9), $Q_{R(9)}$. (b) The IR-Raman coupling coefficient g_{IR-R} between Raman(9) and each IR mode.

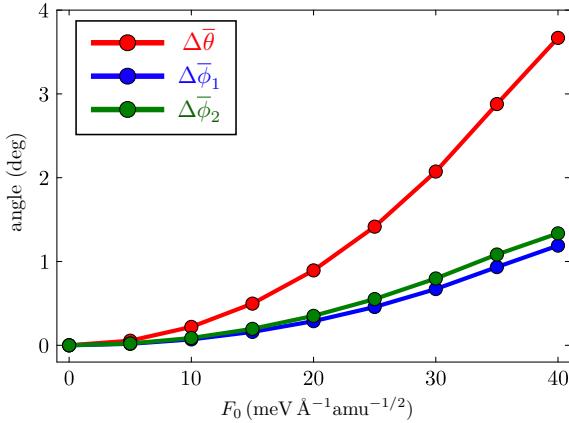


FIG. 7. Field-amplitude (F_0) dependence of $\Delta\bar{\theta}$, $\Delta\bar{\phi}_1$, and $\Delta\bar{\phi}_2$ for the case where IR(42) is optically excited.

Fig. 6(b). This can be naturally understood because atomic displacements for IR(42) and Raman(9) have a large amplitude on the inner apical oxygen atoms as shown in Figs. 2(a) and 2(b). The largest $\Delta\bar{\theta}$ for IR(42) in Fig. 3 is considered to be due to the strong coupling between IR(42) and Raman(9).

C. Field-amplitude dependence

Figure 7 shows $\Delta\bar{\theta}$, $\Delta\bar{\phi}_1$, and $\Delta\bar{\phi}_2$ as a function of the field amplitude F_0 for the case where IR(42) is optically excited. We find that the changes in the bond angles are roughly proportional to F_0^2 . This originates from approximate relationships, $Q_{IR} \propto F_0$ and $Q_R \propto Q_{IR}^2$, which is because the IR and Raman modes are mainly driven by the external field and the phonon-phonon coupling proportional to Q_{IR}^2 , respectively [see, Eq. (2)]. In other words, we here demonstrate the quadratic F_0 dependence of the structural changes as a consequence of the nonlinear Raman oscillation, which is a key aspect of nonlinear phononics for realizing a non-zero displacement of the time-averaged crystal structure after light irradia-

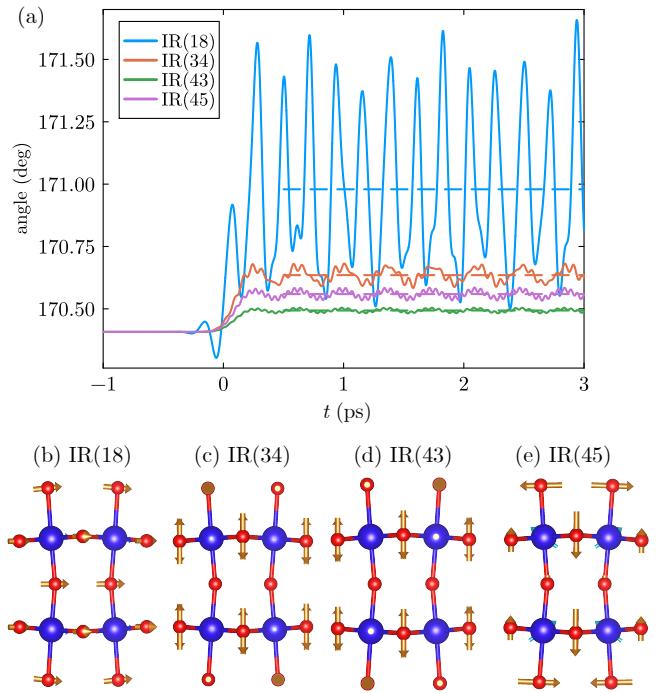


FIG. 8. (a) Time-evolution of interlayer bond angle θ for the cases where other IR modes than IR(42) are optically excited. Dashed lines present the time-averaged value of the interlayer bond angle, $\bar{\theta}$. (b)–(e) Phonon modes of IR(18), (34), (43), and (45) are shown, respectively.

tion. We also note that a change in the bond angle can be greatly increased by using high-intensity light.

D. Other IR modes

While IR(42) gives the largest increase in $\Delta\bar{\theta}$, $\theta(t)$ is strongly oscillating and $\Delta\theta(t)$ becomes even negative in its oscillation as shown in Fig. 4(b). This is because the linearly excited IR(42) phonon strongly contributes to the oscillation of the inner apical oxygen as shown in Fig. 2(a). Therefore, we also present the cases where

other IR modes are optically excited in Fig. 8(a). In particular, we show the cases where $\Delta\theta(t)$ is always positive, i.e., the interlayer bond angle is always increased after light irradiation. For these cases, IR(18), (34), (43), and (45) are optically excited, the eigenmodes of which are shown in Figs. 8(b)–8(e). Since the inner apical oxygen moves little in these IR modes, θ is less affected by the IR-mode oscillation, which gives the smaller oscillation of $\theta(t)$ compared to that for IR(42) as shown in Fig. 4(b). These IR modes can also be good candidates as a target state of light irradiation.

IV. DISCUSSIONS

In this study, we adopt several approximations for the anharmonic lattice potential, Eq. (1). First, we do not consider the Raman-Raman scattering. Reference [95] discussed that the role of Raman-Raman coupling terms like $h_{R_1-R_2}Q_{R_1}Q_{R_2}$ is to renormalize the light-induced phonon displacements. In fact, they evaluated $h_{R_1-R_2}$ for an actual material and found that their values are sufficiently smaller than a critical threshold against an unstable deformation of the lattice. Thus, we expect that our results are qualitatively kept unchanged even by including the Raman-Raman coupling while the size of the Raman displacements can be somewhat renormalized.

Second, we do not consider $\mathbf{q} \neq \mathbf{0}$ phonons, which are required when one considers higher-order potential coupling terms [96–98]. To include such coupling terms, we should consider intractably many phonon modes over the whole Brillouin zone. On the other hand, the nonlinear oscillation, which is an objective of our study, requires Q_{IR}^2 dependence of the potential term, and so the lowest-order term that can induce the nonlinear oscillation is $Q_{IR}^2Q_R$, where only phonons at the Γ point involve due to the translational invariance of the crystal (i.e., the total crystal momentum should be zero for each term). Thus, in the present study we ignore $\mathbf{q} \neq \mathbf{0}$ phonons for simplicity as many theoretical studies on nonlinear phononics do [68–71, 76–81].

Third, in our simulation of phonon dynamics, we do not explicitly consider the phonon lifetime, which can effectively represent several types of phonon-phonon coupling discarded in this study and electron-phonon coupling. However, in order to see the transient modulated crystal structure after light irradiation theoretically, damping effects are not necessarily included. We expect that a change in the crystal structure similar to our simulation can be observed within a short timescale following the field irradiation.

Finally, phonon dynamics is treated by the classical equation of motion rather than by the quantum theory of phonons. In the quantum treatment of phonon anharmonicity, one needs to consider the energy conservation of each scattering process [98–101]. From this perspective, $\mathbf{q} \neq \mathbf{0}$ phonons are necessary to satisfy the energy conservation together with the crystal momentum con-

servation. Considering anharmonic phonon dynamics in the quantum manner is important but very challenging, and so is a future objective. In addition, we have not considered the dynamics of electronic states associated with lattice motions, which would be one of the future tasks.

Our theoretical proposal of the structural control can be experimentally realizable by the pump-probe method using a terahertz or mid-infrared laser [67, 69, 73, 77, 80]. By examining the optical response in both equilibrium and pumped nonequilibrium states, one can reveal changes in electronic states [67, 77, 80]. In addition, using time-resolved X-rays during laser irradiation, it is possible to observe changes in the crystal structure [69, 73].

The external driving force $F(t)$ considered in this study and the actual electric field $\mathbf{E}(t)$ are related by $F(t) = \mathbf{E}(t) \cdot \mathbf{Z}_\alpha$, where \mathbf{Z}_α is the mode effective charge of the phonon mode α . Although first-principles evaluation of the effective charge requires the correct description of the metallicity and the screening effect in the material, $\text{La}_3\text{Ni}_2\text{O}_7$ hosts the non-trivial density wave resulting in the insulating states [1, 12, 14, 27, 28, 51, 102–114], which likely originates from strong electron correlation effects. While first-principles evaluation of the effective charge for metals has been recently proposed by a dynamical extension of the effective charge [115–118], it is still challenging to include the strong electron correlation effects into DFT calculation. Therefore, we do not evaluate \mathbf{Z}_α in this study, and hence we cannot show an explicit correspondence between the electric-field strength and F_0 . Nevertheless, by assuming a typical value of $|\mathbf{Z}_\alpha| \sim 0.1 \text{ e amu}^{-1/2}$ [77], the electric field strength is estimated to be $|\mathbf{E}| \sim 10 \text{ MV cm}^{-1}$ for $F_0 = 10 \text{ meV \AA}^{-1} \text{ amu}^{-1/2}$.

V. SUMMARY

In this study, we have investigated the possibility of controlling the crystal structure of the bilayer nickelate $\text{La}_3\text{Ni}_2\text{O}_7$ via light irradiation based on nonlinear phononics. We have constructed the anharmonic lattice potential using first-principle calculation and calculated phonon dynamics by solving the equation of motion for that potential. We have found that the interlayer Ni-O-Ni bond angle gets slightly closer to straight when an appropriate IR mode, which is identified in this study, is selectively excited. If structural control can be achieved through experiments, we expect that it will lead to hints for elucidating the relationship between the crystal structure of multi-layer nickelate superconductors and the mechanisms of superconductivity or density wave appearance. We expect our findings stimulate an experimental study on the structural control of $\text{La}_3\text{Ni}_2\text{O}_7$ using light.

ACKNOWLEDGMENTS

We thank Dr. S. Kitou, Dr. Y. Murotani, Dr. H. Sakakibara and Dr. A. Togo for fruitful discussions. This work was supported by Grants-in-Aid for Scientific Research from JSPS, KAKENHI Grants No. JP24K06939, No. JP24H00191 (T.K.), No. JP22K04907 (K.K.), and No. JP24K01333.

Appendix A: Eigenmodes for the Γ point phonons

We illustrate atomic displacements of all the A_g Raman modes at the Γ point in Fig. 9 and show irreducible representation and phonon frequency ω for all eigen phonon modes at the Γ point in Table. II.

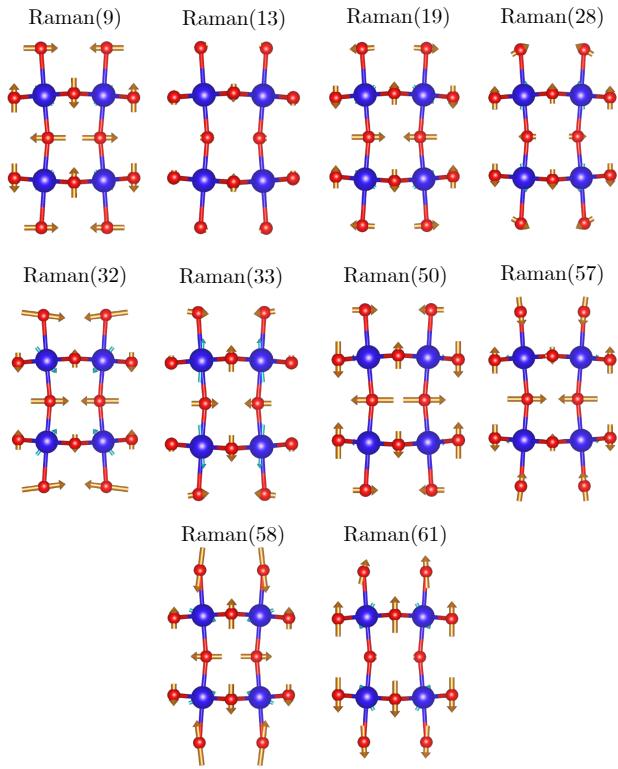


FIG. 9. Atomic displacements for all the A_g Raman modes. La atoms and their modulated vectors are omitted for simplicity

Appendix B: Electronic band dispersion for the modulated crystal structure

In Fig. 10, we present the electronic band dispersion for the original (unmodulated) crystal structure and that for the modulated crystal structure. To see how the electronic structure is affected by the structural modulation by light irradiation, we calculate the electronic

label	irr.	$\omega/2\pi$ (THz)	label	irr.	$\omega/2\pi$ (THz)
1	accostic	0	37	B_{1u}	7.526
2	accostic	0	38	B_{3g}	7.626
3	accostic	0	39	B_{1g}	7.875
4	B_{1u}	1.959	40	B_{2u}	7.927
5	B_{3g}	2.015	41	B_{3g}	8.546
6	B_{2u}	2.207	42	B_{2u}	8.548
7	B_{2g}	2.316	43	A_u	8.635
8	B_{1g}	2.447	44	B_{3u}	8.875
9	A_g	2.709	45	B_{3u}	9.337
10	B_{1g}	2.963	46	B_{1u}	9.495
11	A_u	3.047	47	B_{2g}	9.557
12	B_{3g}	3.561	48	B_{2u}	9.779
13	A_g	3.760	49	B_{1g}	9.810
14	B_{3u}	3.846	50	A_g	9.852
15	B_{1u}	3.993	51	B_{3g}	9.880
16	B_{2g}	4.023	52	B_{1g}	10.169
17	B_{2u}	4.307	53	B_{2u}	10.309
18	B_{2u}	4.552	54	A_u	10.819
19	A_g	4.643	55	B_{3u}	10.947
20	B_{1g}	4.717	56	B_{3g}	11.137
21	B_{3g}	4.718	57	A_g	11.218
22	B_{3u}	4.755	58	A_g	11.595
23	B_{3u}	4.844	59	B_{3u}	12.289
24	B_{2g}	4.862	60	B_{1g}	12.908
25	B_{1u}	4.895	61	A_g	13.133
26	B_{1g}	4.948	62	B_{2u}	13.678
27	A_u	5.127	63	B_{1u}	14.855
28	A_g	5.552	64	B_{1g}	14.859
29	B_{1u}	5.563	65	B_{2g}	15.099
30	B_{2u}	6.188	66	B_{3u}	15.636
31	B_{1g}	6.294	67	B_{2u}	17.942
32	A_g	6.637	68	B_{1g}	18.527
33	A_g	6.730	69	B_{2g}	19.066
34	A_u	7.259	70	B_{1u}	19.171
35	B_{2g}	7.451	71	B_{1g}	19.205
36	B_{3u}	7.485	72	B_{2u}	19.274

TABLE II. All phonon modes at the Γ point in $\text{La}_3\text{Ni}_2\text{O}_7$.

band dispersion for the time-averaged crystal structure after light irradiation, where IR(42) is optically excited with $F_0 = 40 \text{ meV}\text{\AA}^{-1} \text{amu}^{-1/2}$. A $12 \times 12 \times 12$ \mathbf{k} -mesh is used for determining the Fermi energy.

We find that the bilayer splitting energy for the $d_{3z^2-r^2}$ orbital is slightly increased. For example, at the Z point, the $d_{3z^2-r^2}$ bonding and anti-bonding bands reside around $E - E_F \simeq -0.3$ and $+1.1$ eV, respectively. At the R point, the $d_{3z^2-r^2}$ bonding and anti-bonding bands reside around $E - E_F \simeq -0.8$ and $+1.7$ eV, respectively. For both points, we can see that the energy difference between the bonding and anti-bonding states becomes larger for the modulated crystal structure. Here, we refer the readers to the previous study, e.g., Ref. [1], for the orbital-character assignment of the band dispersion. The increase in the bilayer splitting energy is likely due to the increase in the interlayer bond angle θ , which can enhance the interlayer hopping between the $d_{3z^2-r^2}$ orbitals. According to previous studies, the interlayer

hopping between the $d_{3z^2-r^2}$ orbitals is crucial for superconductivity since it determines the interlayer exchange coupling between spins of the $d_{3z^2-r^2}$ orbital.

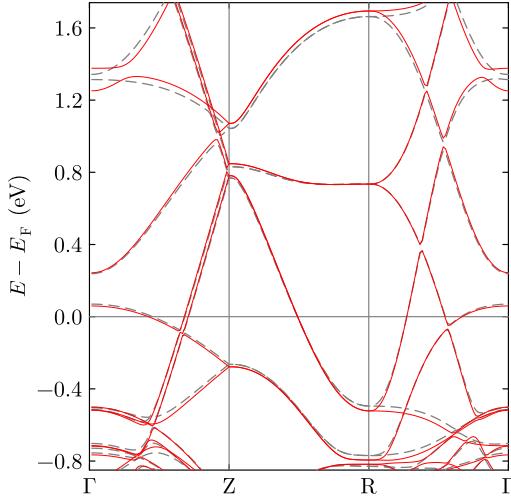


FIG. 10. Electronic band dispersion for the original crystal structure (gray dashed lines) and the modulated crystal structure for the case where IR(42) is optically excited with $F_0 = 40 \text{ meV\AA}^{-1} \text{ amu}^{-1/2}$ (red solid lines). The k -path is set to $\Gamma = (0, 0, 0) \rightarrow Z = (\pi/a, 0, 0) \rightarrow R = (\pi/a, \pi/2b, \pi/2c) \rightarrow \Gamma = (0, 0, 0)$ with the lattice constants b and c .

-
- [1] H. Sun, M. Huo, X. Hu, J. Li, Z. Liu, Y. Han, L. Tang, Z. Mao, P. Yang, B. Wang, J. Cheng, D.-X. Yao, G.-M. Zhang, and M. Wang, *Nature* **621**, 493 (2023).
- [2] Y. Zhang, L.-F. Lin, A. Moreo, and E. Dagotto, *Phys. Rev. B* **108**, L180510 (2023).
- [3] Q.-G. Yang, D. Wang, and Q.-H. Wang, *Phys. Rev. B* **108**, L140505 (2023).
- [4] F. Lechermann, J. Gondolf, S. Bötzel, and I. M. Eremin, *Phys. Rev. B* **108**, L201121 (2023).
- [5] H. Sakakibara, N. Kitamine, M. Ochi, and K. Kuroki, *Phys. Rev. Lett.* **132**, 106002 (2024).
- [6] Y. Gu, C. Le, Z. Yang, X. Wu, and J. Hu, Effective model and pairing tendency in bilayer ni-based superconductor $\text{La}_3\text{Ni}_2\text{O}_7$ (2023), arXiv:2306.07275.
- [7] Y. Shen, M. Qin, and G.-M. Zhang, *Chin. Phys. Lett.* **40**, 127401 (2023).
- [8] V. Christiansson, F. Petocchi, and P. Werner, *Phys. Rev. Lett.* **131**, 206501 (2023).
- [9] Z. Liu, M. Huo, J. Li, Q. Li, Y. Liu, Y. Dai, X. Zhou, J. Hao, Y. Lu, M. Wang, and H.-H. Wen, *Nat. Commun.* **15**, 7570 (2024).
- [10] W. Wú, Z. Luo, D.-X. Yao, and M. Wang, *Sci. China Phys. Mech. Astron.* **67**, 117402 (2024).
- [11] Y. Cao and Y.-f. Yang, *Phys. Rev. B* **109**, L081105 (2024).
- [12] J. Hou, P.-T. Yang, Z.-Y. Liu, J.-Y. Li, P.-F. Shan, L. Ma, G. Wang, N.-N. Wang, H.-Z. Guo, J.-P. Sun, Y. Uwatoko, M. Wang, G.-M. Zhang, B.-S. Wang, and J.-G. Cheng, *Chin. Phys. Lett.* **40**, 117302 (2023).
- [13] Y.-B. Liu, J.-W. Mei, F. Ye, W.-Q. Chen, and F. Yang, *Phys. Rev. Lett.* **131**, 236002 (2023).
- [14] Y. Zhang, D. Su, Y. Huang, Z. Shan, H. Sun, M. Huo, K. Ye, J. Zhang, Z. Yang, Y. Xu, Y. Su, R. Li, M. Smidman, M. Wang, L. Jiao, and H. Yuan, *Nat. Phys.* **20**, 1269 (2024).
- [15] C. Lu, Z. Pan, F. Yang, and C. Wu, *Phys. Rev. Lett.* **132**, 146002 (2024).
- [16] Y. Zhang, L.-F. Lin, A. Moreo, T. A. Maier, and E. Dagotto, *Nat. Commun.* **15**, 2470 (2024).
- [17] H. Oh and Y.-H. Zhang, *Phys. Rev. B* **108**, 174511 (2023).
- [18] Z. Liao, L. Chen, G. Duan, Y. Wang, C. Liu, R. Yu, and Q. Si, *Phys. Rev. B* **108**, 214522 (2023).
- [19] X.-Z. Qu, D.-W. Qu, J. Chen, C. Wu, F. Yang, W. Li, and G. Su, *Phys. Rev. Lett.* **132**, 036502 (2024).
- [20] Y.-f. Yang, G.-M. Zhang, and F.-C. Zhang, *Phys. Rev. B* **108**, L201108 (2023).
- [21] K. Jiang, Z. Wang, and F.-C. Zhang, *Chin. Phys. Lett.* **41**, 017402 (2024).
- [22] Y. Zhang, L.-F. Lin, A. Moreo, T. A. Maier, and E. Dagotto, *Phys. Rev. B* **108**, 165141 (2023).
- [23] Y.-H. Tian, Y. Chen, J.-M. Wang, R.-Q. He, and Z.-Y. Lu, *Phys. Rev. B* **109**, 165154 (2024).
- [24] R. Jiang, J. Hou, Z. Fan, Z.-J. Lang, and W. Ku, *Phys. Rev. Lett.* **132**, 126503 (2024).
- [25] Z. Luo, B. Lv, M. Wang, W. Wú, and D.-X. Yao, *npj*

- Quantum Mater.* **9**, 61 (2024).
- [26] J. Yang, H. Sun, X. Hu, Y. Xie, T. Miao, H. Luo, H. Chen, B. Liang, W. Zhu, G. Qu, C.-Q. Chen, M. Huo, Y. Huang, S. Zhang, F. Zhang, F. Yang, Z. Wang, Q. Peng, H. Mao, G. Liu, Z. Xu, T. Qian, D.-X. Yao, M. Wang, L. Zhao, and X. J. Zhou, *Nat. Commun.* **15**, 4373 (2024).
- [27] M. Zhang, C. Pei, Q. Wang, Y. Zhao, C. Li, W. Cao, S. Zhu, J. Wu, and Y. Qi, *J. Mater. Sci. Technol.* **185**, 147 (2024).
- [28] G. Wang, N. N. Wang, X. L. Shen, J. Hou, L. Ma, L. F. Shi, Z. A. Ren, Y. D. Gu, H. M. Ma, P. T. Yang, Z. Y. Liu, H. Z. Guo, J. P. Sun, G. M. Zhang, S. Calder, J.-Q. Yan, B. S. Wang, Y. Uwatoko, and J.-G. Cheng, *Phys. Rev. X* **14**, 011040 (2024).
- [29] T. Kaneko, H. Sakakibara, M. Ochi, and K. Kuroki, *Phys. Rev. B* **109**, 045154 (2024).
- [30] C. Lu, Z. Pan, F. Yang, and C. Wu, *Phys. Rev. B* **110**, 094509 (2024).
- [31] S. Ryee, N. Witt, and T. O. Wehling, *Phys. Rev. Lett.* **133**, 096002 (2024).
- [32] Z. Ouyang, J.-M. Wang, J.-X. Wang, R.-Q. He, L. Huang, and Z.-Y. Lu, *Phys. Rev. B* **109**, 115114 (2024).
- [33] Y. Zhou, J. Guo, S. Cai, H. Sun, P. Wang, J. Zhao, J. Han, X. Chen, Y. Chen, Q. Wu, Y. Ding, T. Xiang, H. kwang Mao, and L. Sun, Investigations of key issues on the reproducibility of high- T_c superconductivity emerging from compressed $\text{La}_3\text{Ni}_2\text{O}_7$ (2024), arXiv:2311.12361.
- [34] X.-Z. Qu, D.-W. Qu, X.-W. Yi, W. Li, and G. Su, Roles of hund's rule and hybridization in the two-orbital model for high- T_c superconductivity in the bilayer nickelate (2023), arXiv:2311.12769.
- [35] M. Kakoi, T. Kaneko, H. Sakakibara, M. Ochi, and K. Kuroki, *Phys. Rev. B* **109**, L201124 (2024).
- [36] M. Nakata, D. Ogura, H. Usui, and K. Kuroki, *Phys. Rev. B* **95**, 214509 (2017).
- [37] E. Dagotto, J. Riera, and D. Scalapino, *Phys. Rev. B* **45**, 5744 (1992).
- [38] N. Bulut, D. J. Scalapino, and R. T. Scalettar, *Phys. Rev. B* **45**, 5577 (1992).
- [39] R. T. Scalettar, J. W. Cannon, D. J. Scalapino, and R. L. Sugar, *Phys. Rev. B* **50**, 13419 (1994).
- [40] R. E. Hetzel, W. von der Linden, and W. Hanke, *Phys. Rev. B* **50**, 4159 (1994).
- [41] R. R. dos Santos, *Phys. Rev. B* **51**, 15540 (1995).
- [42] A. I. Liechtenstein, I. I. Mazin, and O. K. Andersen, *Phys. Rev. Lett.* **74**, 2303 (1995).
- [43] K. Kuroki, T. Kimura, and R. Arita, *Phys. Rev. B* **66**, 184508 (2002).
- [44] S. S. Kancharla and S. Okamoto, *Phys. Rev. B* **75**, 193103 (2007).
- [45] K. Bouadim, G. G. Batrouni, F. Hébert, and R. T. Scalettar, *Phys. Rev. B* **77**, 144527 (2008).
- [46] N. Lanatà, P. Barone, and M. Fabrizio, *Phys. Rev. B* **80**, 224524 (2009).
- [47] H. Zhai, F. Wang, and D.-H. Lee, *Phys. Rev. B* **80**, 064517 (2009).
- [48] T. A. Maier and D. J. Scalapino, *Phys. Rev. B* **84**, 180513 (2011).
- [49] Z. Ouyang, M. Gao, and Z.-Y. Lu, *npj Quantum Mater.* **9**, 80 (2024).
- [50] Y. D. Li, Y. T. Cao, L. Y. Liu, P. Peng, H. Lin, C. Y. Pei, M. X. Zhang, H. Wu, X. Du, W. X. Zhao, K. Y. Zhai, J. K. Zhao, M. L. Lin, P. H. Tan, Y. P. Qi, G. Li, H. J. Guo, L. Yang, and L. X. Yang, Ultrafast dynamics of bilayer and trilayer nickelate superconductors (2024), arXiv:2403.05012.
- [51] X.-W. Yi, Y. Meng, J.-W. Li, Z.-W. Liao, W. Li, J.-Y. You, B. Gu, and G. Su, *Phys. Rev. B* **110**, L140508 (2024).
- [52] B. Geisler, J. J. Hamlin, G. R. Stewart, R. G. Hennig, and P. J. Hirschfeld, *npj Quantum Mater.* **9**, 38 (2024).
- [53] L. Wang, Y. Li, S.-Y. Xie, F. Liu, H. Sun, C. Huang, Y. Gao, T. Nakagawa, B. Fu, B. Dong, Z. Cao, R. Yu, S. I. Kawaguchi, H. Kadobayashi, M. Wang, C. Jin, H.-k. Mao, and H. Liu, *J. Am. Chem. Soc.* **146**, 7506 (2024).
- [54] N. Wang, G. Wang, X. Shen, J. Hou, J. Luo, X. Ma, H. Yang, L. Shi, J. Dou, J. Feng, J. Yang, Y. Shi, Z. Ren, H. Ma, P. Yang, Z. Liu, Y. Liu, H. Zhang, X. Dong, Y. Wang, K. Jiang, J. Hu, S. Nagasaki, K. Kitagawa, S. Calder, J. Yan, J. Sun, B. Wang, R. Zhou, Y. Uwatoko, and J. Cheng, *Nature* **634**, 579 (2024).
- [55] H. Sakakibara, M. Ochi, H. Nagata, Y. Ueki, H. Sakurai, R. Matsumoto, K. Terashima, K. Hirose, H. Ohta, M. Kato, Y. Takano, and K. Kuroki, *Phys. Rev. B* **109**, 144511 (2024).
- [56] Q. Li, Y.-J. Zhang, Z.-N. Xiang, Y. Zhang, X. Zhu, and H.-H. Wen, *Chin. Phys. Lett.* **41**, 017401 (2024).
- [57] Y. Zhu, D. Peng, E. Zhang, B. Pan, X. Chen, L. Chen, H. Ren, F. Liu, Y. Hao, N. Li, Z. Xing, F. Lan, J. Han, J. Wang, D. Jia, H. Wo, Y. Gu, Y. Gu, L. Ji, W. Wang, H. Gou, Y. Shen, T. Ying, X. Chen, W. Yang, H. Cao, C. Zheng, Q. Zeng, J.-G. Guo, and J. Zhao, *Nature* **631**, 531 (2024).
- [58] M. Zhang, C. Pei, X. Du, W. Hu, Y. Cao, Q. Wang, J. Wu, Y. Li, H. Liu, C. Wen, Y. Zhao, C. Li, W. Cao, S. Zhu, Q. Zhang, N. Yu, P. Cheng, L. Zhang, Z. Li, J. Zhao, Y. Chen, H. Guo, C. Wu, F. Yang, S. Yan, L. Yang, and Y. Qi, Superconductivity in trilayer nickelate $\text{La}_4\text{Ni}_3\text{O}_{10}$ under pressure (2024), arXiv:2311.07423.
- [59] J. Li, C.-Q. Chen, C. Huang, Y. Han, M. Huo, X. Huang, P. Ma, Z. Qiu, J. Chen, X. Hu, L. Chen, T. Xie, B. Shen, H. Sun, D.-X. Yao, and M. Wang, *Sci. China Phys. Mech. Astron.* **67**, 117403 (2024).
- [60] L. C. Rhodes and P. Wahl, *Phys. Rev. Mater.* **8**, 044801 (2024).
- [61] S. Wu, Z. Yang, X. Ma, J. Dai, M. Shi, H.-Q. Yuan, H.-Q. Lin, and C. Cao, $\text{Ac}_3\text{Ni}_2\text{O}_7$ and $\text{La}_2\text{AeNi}_2\text{O}_6\text{F}$ ($\text{Ae} = \text{Sr}, \text{Ba}$): Benchmark materials for bilayer nickelate superconductivity (2024), arXiv:2403.11713.
- [62] M. Ochi, H. Sakakibara, H. Usui, and K. Kuroki, Theoretical study on the crystal structure of a bilayer nickel-oxychloride $\text{Sr}_3\text{Ni}_2\text{O}_5\text{Cl}_2$ and analysis on the occurrence of possible unconventional superconductivity (2024), arXiv:2409.06935.
- [63] K. Yamane, Y. Matsushita, S. Adachi, R. Matsumoto, K. Terashima, T. Hiroto, H. Sakurai, and Y. Takano, High-pressure synthesis of bilayer nickelate $\text{Sr}_3\text{Ni}_2\text{O}_5\text{Cl}_2$ with tetragonal crystal structure (2024), arXiv:2412.09093.
- [64] E. K. Ko, Y. Yu, Y. Liu, L. Bhatt, J. Li, V. Thampy, C.-T. Kuo, B. Y. Wang, Y. Lee, K. Lee, J.-S. Lee, B. H. Goodge, D. A. Muller, and H. Y. Hwang, *Nature* (2024).
- [65] G. Zhou, W. Lv, H. Wang, Z. Nie, Y. Chen,

- Y. Li, H. Huang, W. Chen, Y. Sun, Q.-K. Xue, and Z. Chen, Ambient-pressure superconductivity onset above 40 K in bilayer nickelate ultrathin films (2024), [arXiv:2412.16622](#).
- [66] Y.-F. Zhao and A. S. Botana, Electronic structure of Ruddlesden-Popper nickelates: strain to mimic the effects pressure (2024), [arXiv:2412.04391](#).
- [67] M. Först, C. Manzoni, S. Kaiser, Y. Tomioka, Y. Tokura, R. Merlin, and A. Cavalleri, *Nat. Phys.* **7**, 854 (2011).
- [68] A. Subedi, A. Cavalleri, and A. Georges, *Phys. Rev. B* **89**, 220301 (2014).
- [69] R. Mankowsky, A. Subedi, M. Först, S. O. Mariager, M. Chollet, H. T. Lemke, J. S. Robinson, J. M. Glownia, M. P. Minitti, A. Frano, M. Fechner, N. A. Spaldin, T. Loew, B. Keimer, A. Georges, and A. Cavalleri, *Nature* **516**, 71 (2014).
- [70] M. Fechner and N. A. Spaldin, *Phys. Rev. B* **94**, 134307 (2016).
- [71] A. Subedi, *Phys. Rev. B* **92**, 214303 (2015).
- [72] R. Mankowsky, A. von Hoegen, M. Först, and A. Cavalleri, *Phys. Rev. Lett.* **118**, 197601 (2017).
- [73] M. Fechner, M. Först, G. Orenstein, V. Krapivin, A. S. Disa, M. Buzzi, A. von Hoegen, G. de la Pena, Q. L. Nguyen, R. Mankowsky, M. Sander, H. Lemke, Y. Deng, M. Trigo, and A. Cavalleri, *Nat. Mater.* **23**, 363 (2024).
- [74] C. Paiva, M. Fechner, and D. M. Juraschek, Dynamically induced multiferroic polarization (2024), [arXiv:2404.16234](#).
- [75] D. M. Juraschek, M. Fechner, and N. A. Spaldin, *Phys. Rev. Lett.* **118** (2017).
- [76] M. Gu and J. M. Rondinelli, *Phys. Rev. B* **98**, 024102 (2018).
- [77] A. S. Disa, M. Fechner, T. F. Nova, B. Liu, M. Först, D. Prabhakaran, P. G. Radaelli, and A. Cavalleri, *Nat. Phys.* **16**, 937 (2020).
- [78] Y. Zeng, *Phys. Rev. B* **108**, 054308 (2023).
- [79] R. Tang, F. Boi, and Y.-H. Cheng, *npj Quantum Mater.* **8**, 78 (2023).
- [80] T. G. H. Blank, K. A. Grishunin, K. A. Zvezdin, N. T. Hai, J. C. Wu, S.-H. Su, J.-C. A. Huang, A. K. Zvezdin, and A. V. Kimel, *Phys. Rev. Lett.* **131**, 026902 (2023).
- [81] D. M. Juraschek, T. Neuman, J. Flick, and P. Narang, *Phys. Rev. Res.* **3**, L032046 (2021).
- [82] A. S. Disa, T. F. Nova, and A. Cavalleri, *Nat. Phys.* **17**, 1087 (2021).
- [83] A. Subedi, *C. R. Phys.* **22**, 161 (2021).
- [84] J. P. Perdew, A. Ruzsinszky, G. I. Csonka, O. A. Vydrov, G. E. Scuseria, L. A. Constantin, X. Zhou, and K. Burke, *Phys. Rev. Lett.* **100**, 136406 (2008).
- [85] J. P. Perdew, A. Ruzsinszky, G. I. Csonka, O. A. Vydrov, G. E. Scuseria, L. A. Constantin, X. Zhou, and K. Burke, *Phys. Rev. Lett.* **102**, 039902 (2009).
- [86] G. Kresse and J. Hafner, *Phys. Rev. B* **47**, 558 (1993).
- [87] G. Kresse and J. Hafner, *Phys. Rev. B* **49**, 14251 (1994).
- [88] G. Kresse and J. Furthmüller, *Comput. Mater. Sci.* **6**, 15 (1996).
- [89] G. Kresse and J. Furthmüller, *Phys. Rev. B* **54**, 11169 (1996).
- [90] G. Kresse and D. Joubert, *Phys. Rev. B* **59**, 1758 (1999).
- [91] A. Togo, L. Chaput, T. Tadano, and I. Tanaka, *J. Phys.: Condens. Matter* **35**, 353001 (2023).
- [92] A. Togo, *J. Phys. Soc. Jpn.* **92**, 012001 (2023).
- [93] K. Momma and F. Izumi, *J. Appl. Cryst.* **44**, 1272 (2011).
- [94] We evaluate a time average of $\theta(t)$ after light irradiation in the time domain $[t_{\min}, t_{\max}]$ as follows:
- $$\bar{\theta} = \frac{1}{t_{\max} - t_{\min}} \int_{t_{\min}}^{t_{\max}} dt' \int_{t_{\min}}^{t'} dt \frac{\theta(t)}{t' - t_{\min}},$$
- where the time average over $t \in [t_{\min}, t']$ is again time-averaged over $t' \in [t_{\min}, t_{\max}]$. While the first time average, $\int_{t_{\min}}^{t'} dt \frac{\theta(t)}{t' - t_{\min}}$, exhibits a decaying oscillation against t' , a center of that oscillation is efficiently obtained by the second average. We set $t_{\min} = 0.8$ ps, which is sufficiently larger than $\tau = 0.3$ ps so that $F(t_{\min}) \simeq 0$, and $t_{\max} = 25$ ps, which is sufficiently large to get a converged value for the time average.
- [95] M. Gu and J. M. Rondinelli, *Appl. Phys. Lett.* **113**, 112903 (2018).
- [96] P. G. Klemens, *Phys. Rev.* **148**, 845 (1966).
- [97] S. W. Teitelbaum, T. Henighan, Y. Huang, H. Liu, M. P. Jiang, D. Zhu, M. Chollet, T. Sato, E. D. Murray, S. Fahy, S. O'Mahony, T. P. Bailey, C. Uher, M. Trigo, and D. A. Reis, *Phys. Rev. Lett.* **121**, 125901 (2018).
- [98] T. Feng and X. Ruan, *Phys. Rev. B* **93**, 045202 (2016).
- [99] A. A. Maradudin and A. E. Fein, *Phys. Rev.* **128**, 2589 (1962).
- [100] A. A. Maradudin, A. E. Fein, and G. H. Vineyard, *Phys. Status Solidi B* **2**, 1479 (1962).
- [101] T. Feng and X. Ruan, *J. Nanomater.* **2014**, 206370 (2014).
- [102] Z. Liu, H. Sun, M. Huo, X. Ma, Y. Ji, E. Yi, L. Li, H. Liu, J. Yu, Z. Zhang, Z. Chen, F. Liang, H. Dong, H. Guo, D. Zhong, B. Shen, S. Li, and M. Wang, *Sci. China Phys. Mech. Astron.* **66**, 217411 (2023).
- [103] K. Chen, X. Liu, J. Jiao, M. Zou, C. Jiang, X. Li, Y. Luo, Q. Wu, N. Zhang, Y. Guo, and L. Shu, *Phys. Rev. Lett.* **132**, 256503 (2024).
- [104] M. Kakoi, T. Oi, Y. Ohshita, M. Yashima, K. Kuroki, T. Kato, H. Takahashi, S. Ishiwata, Y. Adachi, N. Hatada, T. Uda, and H. Mukuda, *J. Phys. Soc. Jpn.* **93**, 053702 (2024).
- [105] T. Xie, M. Huo, X. Ni, F. Shen, X. Huang, H. Sun, H. C. Walker, D. Adroja, D. Yu, B. Shen, L. He, K. Cao, and M. Wang, *Science Bulletin* **69**, 3221 (2024).
- [106] X. Chen, J. Choi, Z. Jiang, J. Mei, K. Jiang, J. Li, S. Agrestini, M. Garcia-Fernandez, H. Sun, X. Huang, D. Shen, M. Wang, J. Hu, Y. Lu, K.-J. Zhou, and D. Feng, *Nat. Commun.* **15**, 9597 (2024).
- [107] Y. Wang, K. Jiang, Z. Wang, F.-C. Zhang, and J. Hu, *Phys. Rev. B* **110**, 205122 (2024).
- [108] Z. Dan, Y. Zhou, M. Huo, Y. Wang, L. Nie, M. Wang, T. Wu, and X. Chen, Spin-density-wave transition in double-layer nickelate $\text{La}_3\text{Ni}_2\text{O}_7$ (2024), [arXiv:2402.03952](#).
- [109] R. Khasanov, T. J. Hicken, D. J. Gawryluk, L. P. Sorel, S. Böttzel, F. Lechermann, I. M. Eremin, H. Luetkens, and Z. Guguchia, Pressure-induced split of the density wave transitions in $\text{La}_3\text{Ni}_2\text{O}_{7-\delta}$ (2024), [arXiv:2402.10485](#).
- [110] Y. Meng, Y. Yang, H. Sun, S. Zhang, J. Luo, L. Chen, X. Ma, M. Wang, F. Hong, X. Wang, and X. Yu, *Nat. Commun.* **15**, 10408 (2024).
- [111] H. LaBollita, V. Pardo, M. R. Norman, and A. S. Botana, Assessing the formation of spin and charge

- stripes in $\text{La}_3\text{Ni}_2\text{O}_7$ from first-principles (2024), [arXiv:2407.14409](#).
- [112] B. Zhang, C. Xu, and H. Xiang, Emergent spin-charge-orbital order in superconductor $\text{La}_3\text{Ni}_2\text{O}_7$ (2024), [arXiv:2407.18473](#).
- [113] X.-S. Ni, Y. Ji, L. He, T. Xie, D.-X. Yao, M. Wang, and K. Cao, Spin density wave in the bilayered nickelate $\text{La}_3\text{Ni}_2\text{O}_{7-\delta}$ at ambient pressure (2024), [arXiv:2407.19213](#).
- [114] L.-F. Lin, Y. Zhang, N. Kaushal, G. Alvarez, T. A. Maier, A. Moreo, and E. Dagotto, *Phys. Rev. B* **110**, 195135 (2024).
- [115] O. Bistoni, P. Barone, E. Cappelluti, L. Benfatto, and F. Mauri, *2D Mater.* **6**, 045015 (2019).
- [116] L. Binci, P. Barone, and F. Mauri, *Phys. Rev. B* **103**, 134304 (2021).
- [117] C. E. Dreyer, S. Coh, and M. Stengel, *Phys. Rev. Lett.* **128**, 095901 (2022).
- [118] C.-Y. Wang, S. Sharma, E. K. U. Gross, and J. K. Dewhurst, *Phys. Rev. B* **106**, L180303 (2022).