

# Uniaxial Pressure Effects, Phase Diagram, and Tricritical Point in the Centrosymmetric Skyrmion Lattice Magnet $\text{GdRu}_2\text{Si}_2$

L. Gries,<sup>1</sup> T. Kleinbeck,<sup>1</sup> D.A. Mayoh,<sup>2</sup> G.D.A. Wood,<sup>2</sup> G. Balakrishnan,<sup>2</sup> and R. Klingeler<sup>1,\*</sup>

<sup>1</sup>*Kirchhoff Institute of Physics, Heidelberg University, INF 227, D-69120 Heidelberg, Germany*

<sup>2</sup>*Department of Physics, University of Warwick, Coventry, West Midlands CV4 7AL, United Kingdom*

(Dated: February 20, 2025)

The magnetic phase diagram, magnetoelastic coupling, and uniaxial pressure effects of centrosymmetric magnetic skyrmion-hosting  $\text{GdRu}_2\text{Si}_2$  are investigated by means of high-resolution capacitance dilatometry in fields up to 15 T supported by specific heat and magnetisation studies. In addition to the previously reported phases in the  $H$ - $T$  phase diagram, we observe a third antiferromagnetic phase in zero magnetic field. We present the magnetic phase diagram and find two unreported phases, one of which features a comparably giant uniaxial pressure dependence. Our dilatometric measurements show magnetoelastic effects associated with the various magnetic ordering phenomena. We determine the uniaxial pressure dependencies of the various phases, in particular of the skyrmion lattice phase which is enhanced at higher fields and temperatures and also widens at a rate of 0.07 T/GPa when uniaxial pressure is applied along the  $c$  axis. The relevance of fluctuations is further highlighted by the presence of tricritical point indicated by our thermodynamic data at the phase boundary separating two double- $Q$  magnetic configurations between which the skyrmion pocket phase evolves upon further cooling.

## I. INTRODUCTION

Magnetic skyrmions are a class of topologically protected non-collinear spin structures which exhibit a variety of particle-like properties [1–6]. The nanometric scale of magnetic skyrmions and emergence of interesting phenomena like the topological Hall effect [7–9] and non-linear tunneling magneto-resistance [10] lead to the proposition of novel skyrmion based technological applications including neuromorphic computation systems [11–13], non-volatile memory [14–16] and logical gates [17–19]. Since the initial experimental finding of magnetic skyrmions in MnSi in 2009 by Mühlbauer *et al.* [20] a plethora of systems hosting a skyrmion lattice have been discovered, e.g.,  $\text{Cu}_2\text{OSeO}_3$  [21],  $\text{GaV}_4\text{S}_8$  [22] and thin film  $\text{Fe}_{0.5}\text{Co}_{0.5}\text{Si}$  [23]. In these non-centrosymmetric systems the Dzyaloshinskii–Moriya interaction is an integral part of the skyrmion formation process. However this is not the case in selected centrosymmetric systems such as  $\text{Gd}_2\text{PdSi}_3$  [24],  $\text{Gd}_3\text{Ru}_4\text{Al}_{12}$  [25],  $\text{EuAl}_4$  [26] and  $\text{GdRu}_2\text{Si}_2$  [27, 28] where various stabilisation mechanisms from geometric frustration [29, 30] to multiple spin interactions [31] have been proposed. These centrosymmetric system are interesting for the aforementioned technological applications due to their small skyrmion diameter on the order of  $\sim 2$  nm [14, 25, 28].

$\text{GdRu}_2\text{Si}_2$  crystallises in centrosymmetric tetragonal structure in the spacegroup  $I4/mmm$  [32–34]. It consists of square layers of  $\text{Gd}^{3+}$  ions ( $S = 7/2$ ,  $L = 0$ ) and  $\text{Ru}_2\text{Si}_2$  layers stacked alternately along the  $c$  axis. In

zero magnetic field, two distinct magnetic phases have been reported: phase IV (magnetic phases are labeled in accordance with [35]) which evolves at  $T_N \simeq 46$  K and phase I below  $T_t \simeq 40$  K [27, 36]. Neutron diffraction experiments reveal that phase IV assumes a sinusoidal or helical spin structure [37], while phase I, the ground state, forms a double- $Q$  constant moment structure [35]. Applying magnetic fields parallel to the  $c$  axis induces a first order phase transition at about 2 T below 20 K [36]. It features a double- $Q$  magnetic structure consisting of the superposition of two orthogonal helices creating a skyrmion lattice (SKL) in this field-induced phase II [27, 28]. By further increasing  $B||c$ , the SKL phase is replaced by a double- $Q$  magnetic structure in phase III above 2.4 T while full polarisation of the spin structure is achieved for  $B||c \gtrsim 10$  T [27]. The origin of the observed magnetic structures has been mainly attributed to a combination of RKKY and multiple spin interactions [28, 38–40].

Here we report magneto-elastic coupling and the initial uniaxial pressure dependencies on the various phases in  $\text{GdRu}_2\text{Si}_2$  as well as the discovery of two new magnetic phases VI and VII. We achieve this by means of high-resolution capacitance dilatometry studies to determine thermal expansion and magnetostriction in fields up to  $B||c = 14$  T which are supported by magnetisation and specific heat measurements. In addition to further completing the magnetic phase diagram, we report the thermodynamic properties at the phase boundaries including evidence of a tricritical point and widening of the SKL phase upon application of uniaxial pressure  $p||c$ . Specifically, the onset temperature of the SKL phase, at  $B||c = 2.1$  T, increases by  $\partial T_{\text{II-III}}/\partial p_c = 8.5(1.2)$  K/GPa and the field range where it is present at 2 K widens as  $\Delta B_{\text{skyr}}/p_c \approx 0.07$  T/GPa.

\* klingeler@kip.uni-heidelberg.de

## II. EXPERIMENTAL METHODS

All measurements were performed on two oriented cuboid-shaped single crystals of  $\text{GdRu}_2\text{Si}_2$ . The cuboids were cut from the same single crystalline boule which has been grown by the floating-zone method as described in Ref. [35]. The sample dimensions and orientations were  $0.590$  ( $\parallel a$ )  $\times$   $0.801$  ( $\parallel b$ )  $\times$   $1.182$  ( $\parallel c$ )  $\text{mm}^3$  (crystal 1) and  $0.761$  ( $\parallel [110]$ )  $\times$   $1.400$  ( $\parallel [-110]$ )  $\times$   $3.112$  ( $\parallel c$ )  $\text{mm}^3$  (crystal 2). Magnetisation measurements were performed using the vibrating sample magnetometer option (VSM) of Quantum Design's Physical Properties Measurement System (PPMS-14) and Quantum Design's Magnetic Properties Measurement System (MPMS3) in the temperature range of 2 K to 300 K and in fields up to 14 T and 7 T respectively. Specific heat data were obtained in the range of 1.8 K to 300 K and with high resolution on the smaller crystal 1 used for dilatometry in the range of 1.8 K to 50 K by means of a relaxation method using the PPMS. In order to account for differences in the absolute values due to mass and background errors, the latter data were scaled to the full temperature-range data at 50 K (see Fig. S1 in the SM [41]). High-resolution dilatometric measurements were performed in two different setups both using a three-terminal capacitance dilatometer from KÜchler Innovative Measurement Technologies [42, 43]. The first setup is home-built and placed in a Variable Temperature Insert (VTI) of an Oxford Instrument magnet system [44]. The second setup is an insert provided from KÜchler Innovative Measurement Technologies for the PPMS including an option to rotate the sample up to  $90^\circ$ . The linear thermal expansion coefficients  $\alpha_i = 1/L_i \times dL_i(T)/dT$  are derived from the relative length changes. Furthermore, magnetostriction, *i.e.*, the field induced relative length changes  $dL_i(B)/L_i$  are obtained for fields up to 15 T at various temperatures up to 150 K and the magnetostriction coefficients  $\lambda_i = 1/L_i \times dL_i(B)/dB$  are derived. For all dilatometric measurements the field is aligned parallel to the measured axis.

## III. RESULTS

### A. Magnetic order and magnetoelastic coupling in zero magnetic field

The static magnetic susceptibility  $\chi_i$  along the different crystallographic directions  $i$  follows a Curie-Weiss-like behaviour down to  $\sim 85$  K as shown in Fig. 1 as well as in Fig. S2 in the Supplemental Material (SM) [41]. The high-temperature behaviour evidences an isotropic  $g$ -factor as expected for  $\text{Gd}^{3+}$  systems. Upon further cooling, non-linear behaviour of  $\chi^{-1}$  below about 80 K and appearance of small anisotropy indicates the evolution of short range magnetic order. Pronounced peaks in  $\chi_i$  at  $T_N = 45.7(5)$  K signal the onset of the long range antiferromagnetic order. Below  $T_N$  two additional

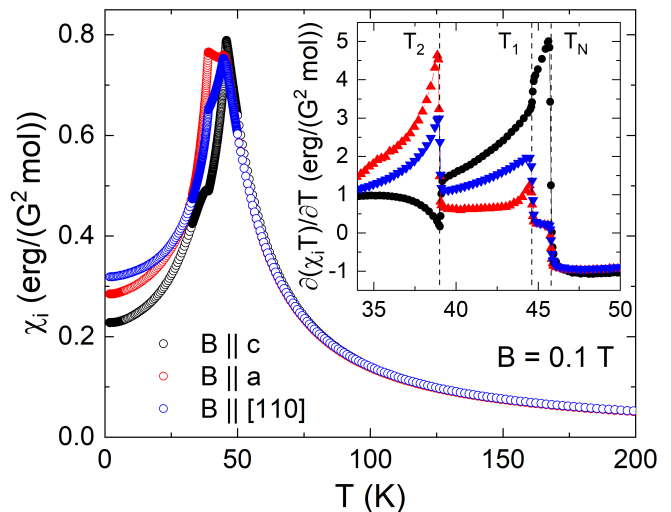


FIG. 1. Temperature dependence of the static magnetic susceptibility  $\chi = M/B$  measured at  $B = 0.1$  T applied along the crystallographic  $i$  axis ( $i = c, a, [110]$ ). The inset shows Fisher's specific heat  $\partial(\chi_i T)/\partial T$ . Dashed lines mark the anomalies at  $T_N$ ,  $T_1$ , and  $T_2$  (see the text).

anomalies evidence additional magnetic phase transitions at  $T_1 = 44.6(5)$  K and  $T_2 = 39.0(5)$  K, respectively. All observed phase transitions are of a continuous nature and are clearly visible as distinct jumps in Fisher's specific heat  $\partial(\chi_i T)/\partial T$  (see the inset of Fig. 1). Note, that anomalies at  $T_N$  and  $T_2$  have been observed before while the phase transition at  $T_1$  has not been reported yet [28, 36, 38]. Fitting the averaged static magnetic susceptibility  $\chi = (2\chi_a + \chi_c)/3$  between 200 and 300 K by means of an extended Curie-Weiss law  $C/(T + \Theta) + \chi_0$  yields the effective moment  $\mu_{\text{eff}} = 8.0(2) \mu_B/\text{f.u.}$  which agrees well with previous reports [45] and matches the expected value for free  $\text{Gd}^{3+}$  moments of  $7.94 \mu_B/\text{f.u.}$ . The obtained Weiss temperature  $\Theta = 42(1)$  K indicates predominant ferromagnetic interaction in  $\text{GdRu}_2\text{Si}_2$ .

The evolution of antiferromagnetic order in zero magnetic field is accompanied by pronounced anomalies in the relative length changes  $dL_i/L_i$  and in the thermal expansion coefficients  $\alpha_i$  as can be seen in Fig. 2. Monotonous shrinking of the  $c$  axis upon cooling, which we observe in the whole temperature regime under study up to 200 K, is superimposed by a clear kink at  $T_N$ . The corresponding thermal expansion coefficient  $\alpha_c$  shows three positive  $\lambda$ -like anomalies at  $T_N$ ,  $T_1$  and  $T_2$ . This observation agrees to a previous study where however only one anomaly, at  $T_N$ , was observed in  $\alpha_c$  [46]. Our data imply significant magnetoelastic coupling since the onset and changes of magnetic order are accompanied by distinct lattice changes. Similarly, there are also clear anomalies in  $dL_i/L_i$  at  $T_N$  for the  $a$  and  $[110]$  axis. Both axes show monotonous expansion upon cooling below 60 K. Again, three jump-like discontinuities can be seen in the thermal expansion coefficient  $\alpha_{[110]}$  indicating the distinct phase boundaries. The associated jumps upon cooling are neg-

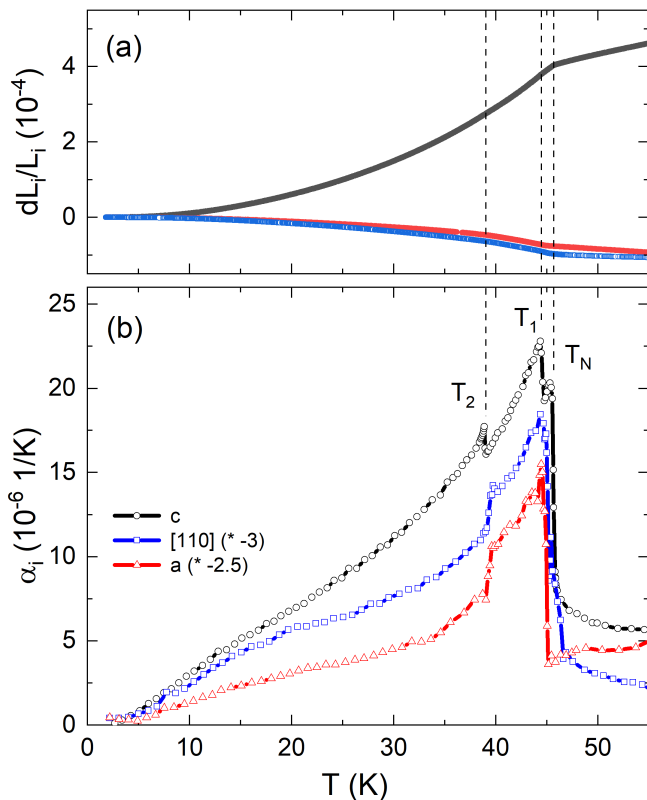


FIG. 2. (a) Relative length changes  $dL_i/L_i$  along the crystallographic  $c$ ,  $[110]$  and  $a$  axes, and (b) corresponding thermal expansion coefficients  $\alpha_i$ . For better visualisation, data for  $\alpha_{[110]}$  and  $\alpha_a$  have been multiplied by -3 and -2.5, respectively. Vertical dashed lines indicate the transition temperatures  $T_N$ ,  $T_1$ , and  $T_2$ .

ative at  $T_N$  and  $T_1$  but the one at  $T_2$  is positive (see Fig. 2 but note the negative scaling factor). For the  $a$  axis only two jumps are observed in  $\alpha_a$ : a negative one at  $T_N$  and a positive one at  $T_2$ . This indicates that the dependence of  $T_1$  on uniaxial pressure along the  $a$  axis is small so that the anomaly is not resolved in our measurement.

The Ehrenfest relation

$$\left. \frac{\partial T^*}{\partial p_i} \right|_B = T^* V_m \frac{\Delta \alpha_i}{\Delta c_p} \quad (1)$$

links the anomalies  $\Delta \alpha_i$  and  $\Delta c_p$  of a continuous phase transition to the uniaxial pressure dependence of the transition temperature  $T^*$ . Hence, the signs of thermal expansion anomalies imply the respective signs of the corresponding initial uniaxial pressure dependencies. The data in Fig. 2b hence signal the increase of  $T_N$ ,  $T_1$  and  $T_2$ , respectively, upon application of uniaxial pressure along the  $c$  axis, *i.e.*,  $\partial T_{N/1/2}/\partial p_c > 0$ . Likewise, we read off that uniaxial pressure applied along the  $a$  and  $[110]$  axis, respectively, will yield a decrease of  $T_N$ . This result is in agreement with theoretical predictions by Bouaziz *et al.* [39] which propose decrease of  $T_N$  when

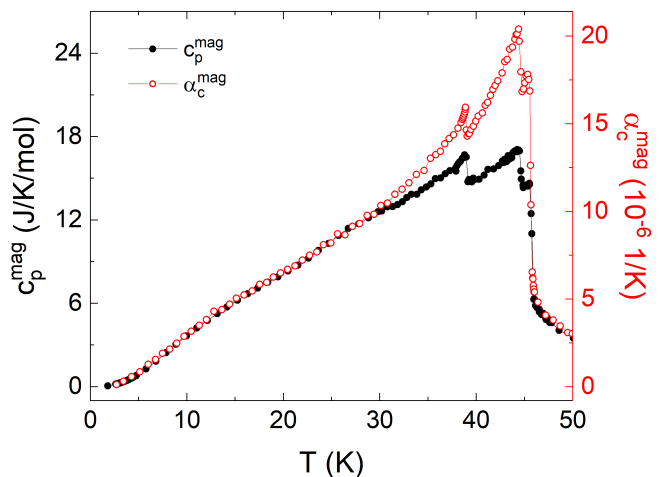


FIG. 3. Magnetic specific heat  $c_p^{\text{mag}}$  (filled black markers; left ordinate) and magnetic contribution to the thermal expansion coefficient  $\alpha_c^{\text{mag}}$  (open red markers; right ordinate).

compressing the lattice along the  $a$  direction. Notably, our data show that the effect of in-plane uniaxial pressure on  $T_2$  is opposite to the effect on  $T_N$  as both  $p_{[110]}$  and  $p_a$  yield an increase of  $T_2$  (*i.e.*,  $\partial T_2/\partial p_{a/[110]} > 0$ ).

To further investigate the successive ordering phenomena, the magnetic Grüneisen parameter  $\gamma_i = \alpha_i^{\text{mag}}/c_p^{\text{mag}}$  is evaluated which compares the magnetic contribution to the thermal expansion coefficient  $\alpha_i^{\text{mag}}$  and the magnetic heat capacity  $c_p^{\text{mag}}$ . [47, 48] The magnetic heat capacity is determined by subtracting the phononic contribution to the heat capacity  $c_p^{\text{phon}}$  from the experimental data, *i.e.*,  $c_p^{\text{mag}} = c_p - c_p^{\text{phon}}$ . In order to estimate the phononic contribution an Einstein-Debye model with one Einstein and one Debye mode is fitted to  $c_p$  between 80 K and 300 K (see Fig. S3 in the SM). The model yields  $\Theta_E = 598$  K and  $\Theta_D = 283$  K. Calculating the resulting magnetic entropy by integrating  $(c_p - c_p^{\text{ph}})/T$  yields  $S_{\text{mag}} = 16.6 \text{ J}/(\text{mol K})$ , which is in good agreement with the expected magnetic entropy changes of a  $\text{Gd}^{3+}$  system  $S_{\text{mag}}^{\text{theo}} = R \times \ln(8) = 17.3 \text{ J}/(\text{mol K})$  and confirms the reliability of the thus obtained background. The parameters  $\Theta_i$  were then used to approximate the phononic contribution to the thermal expansion coefficients with the prefactors as free fitting variables<sup>1</sup>. Figure 3 shows the resulting magnetic contributions of  $c_p$  and  $\alpha_c$  scaled such that they overlap at low temperatures. Our results imply that the magnetic Grüneisen ratio is constant up to  $\sim 30$  K with the Grüneisen parameter  $\gamma_c = 7.9(2) \times 10^{-7} \text{ mol/J}$ . We conclude the presence of a single dominant energy scale  $\epsilon$  for this temperature regime which uniaxial pressure dependence can be derived by using the Grüneisen relation [47, 50]

<sup>1</sup> For a detailed description of the general procedure see Ref. [49].

TABLE I. Jumps (see text as well as Fig. S4) in the thermal expansion coefficient  $\alpha_c$  and the heat capacity  $c_p$  at  $T_j$  ( $j = N, 1, 2$ ) as well as the resulting uniaxial pressure dependencies calculated using the Ehrenfest relation (Eq. 1).

	$\Delta\alpha_c$ [ $10^{-6}$ 1/K]	$\Delta c_p$ [J/K/mol]	$\partial T_j / \partial p_c$ [K/GPa]
$T_N$	13.2(1.2)	9.2(1.2)	3.3(5)
$T_1$	3.3(3)	2.8(4)	2.6(4)
$T_2$	1.2(2)	1.9(3)	1.2(3)

$$\frac{\partial \ln(\epsilon)}{\partial p_i} = V_m \frac{\alpha_i}{c_p}. \quad (2)$$

Using the molecular volume  $V_m = 5.02(1) \cdot 10^{-5} \text{ m}^3/\text{mol}$  [33], applying Eq. 2 yields  $\partial \ln(\epsilon) / \partial p_c = 4.0(1) \text{ \%}/\text{GPa}$ . In contrast, Grüneisen scaling by a single parameter fails for temperatures above 30 K up to  $T_N$ . This implies that neither in phase IV ( $T_2 \leq T \leq T_1$ ) nor in phase VI ( $T_1 \leq T \leq T_N$ ) magnetic order is driven by a single energy scale but there are competing degrees of freedom in both phases. In addition, the experimental observation that Grüneisen scaling fails at  $T \gtrsim 30 \text{ K}$ , *i.e.*, well below  $T_2$ , implies the presence of a competing energy scale in this temperature regime of the low-temperature phase I, too [51].

Comparing the jumps in the thermal expansion coefficient  $\Delta\alpha_i$  and heat capacity  $\Delta c_p$  at the phase transitions enables us to quantify the uniaxial pressure dependence of the respective transition via the Ehrenfest relation (Eq. 1). For a  $\lambda$ -shaped anomaly, the respective jumps are superimposed by fluctuations so that the height of the jumps at the phase transition are determined by fitting lines to the data in a regime below and above the phase transition temperatures respectively [52] (see Fig. S4 in the SM). The resulting jumps in  $\alpha_c$  and  $c_p$  as well as the calculated uniaxial pressure dependencies for uniaxial pressure along the  $c$  axis are listed in Table I.

### B. Effect of magnetic fields $B \parallel c$ and magnetic phase diagram

Applying a magnetic field parallel to the  $c$  axis induces significant changes to the magnetic phases as shown by the many anomalies in the thermal expansion coefficients  $\alpha_c$  and Fisher's specific heat at various fields displayed in Fig. 4. In addition to the measurements at constant magnetic field, isothermal magnetostriction and magnetisation data are shown in Figs. 5 and 6. The observed anomalies are used to construct the magnetic phase diagram in Figs. 8 and 9. A detailed analysis and discussion of the anomalies will be given in § III C and III D.

As shown in § III A, in zero magnetic field three distinct magnetic phases are observed: phase I at  $T \leq T_2$ , phase IV at  $T_2 \leq T \leq T_1$  and phase VI between  $T_1$  and  $T_N$  (labelling of phases is done in consistency with Ref. [38]).

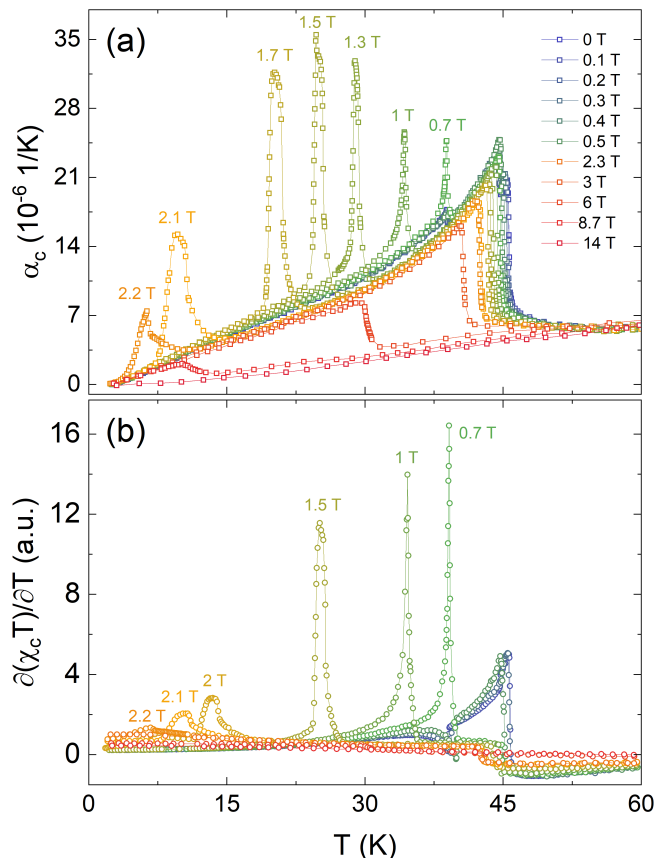


FIG. 4. (a) Linear thermal expansion coefficient  $\alpha_c$  for various magnetic fields  $B \parallel c$  up to 14 T. (b) Fisher's specific heat  $\partial(\chi_c T) / \partial T$  for various magnetic fields up to 8.7 T. For a more detailed view of each individual measurement see Fig. S6 and Fig. S8 in the SM.

Phase I consists of a double- $Q$  constant moment solution, with a helix and orthogonal spin density wave propagating on the principal magnetic propagation vectors  $\mathbf{q}_1$  and  $\mathbf{q}_2$ ; a second helix propagates along  $\mathbf{q}_1 + 2\mathbf{q}_2$ , which connects the arms of the star providing a constant moment solution [35, 37]. Phase IV has either a sinusoidal or a helical spin structure [37]. The spin structure of the phase VI is unknown. For small magnetic fields  $B \parallel c$ ,  $T_N$  decreases while  $T_1$  increases. Both phase boundaries merge at around 0.5 T thereby closing phase VI as summarised in Fig. 9. As indicated in this figure, the detailed slope of the phase boundaries around  $B \simeq 0.5 \text{ T}$  and  $T \simeq 45 \text{ K}$ , separating phases IV, VI (and III), are not exactly clarified by our measurements since the associated anomalies are weak and partly overlap. Similar to  $T_1$ ,  $T_2$  is shifted to higher temperatures with increasing field so that phase I is stabilized over phase IV.

At intermediate fields, anomalies in the magnetostriction and thermal expansion indicate the field-driven evolution of the square skyrmion lattice (phase II) and a fan structure (phase III). Specifically, isothermal magnetisation at  $T = 42 \text{ K}$  exhibits a jump at  $B_{\text{IV-III}} = 0.58(2) \text{ T}$  sig-

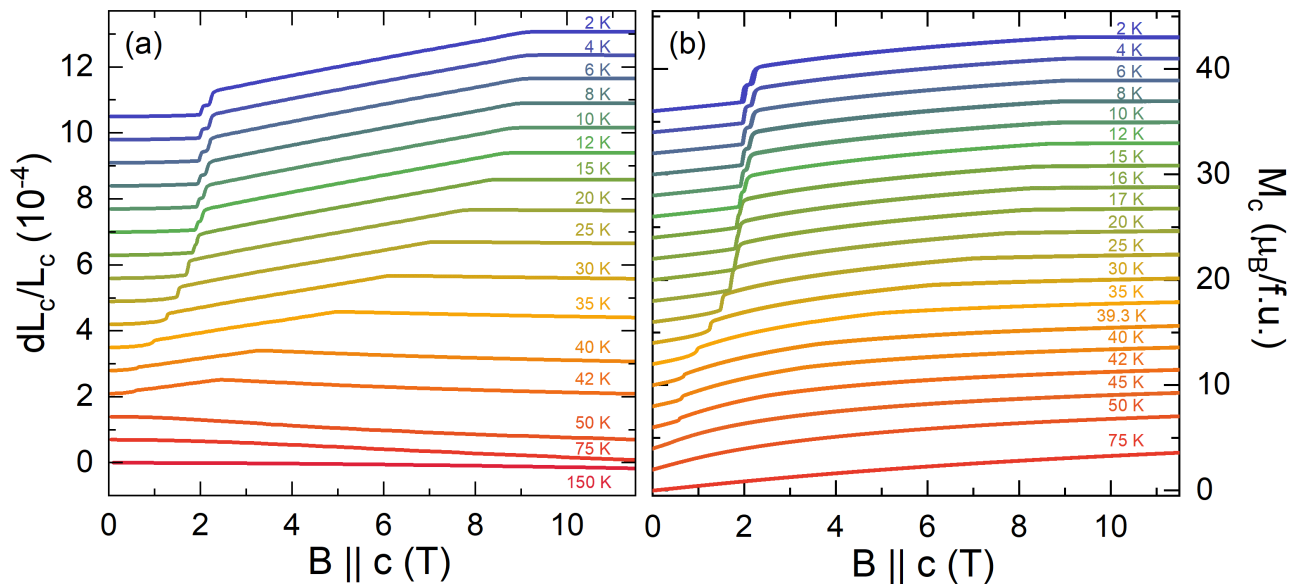


FIG. 5. (a) Magnetostriction  $dL_c(B)/L_c$  and (b) isothermal magnetisation  $M_c$  at various temperatures as a function of the magnetic field  $B \parallel c$ . For a detailed plot of the low-field region see Fig. S9 and Fig. S11 in the SM.

naling a first order phase transition from phase IV to III. Similarly, dilatometric and magnetic measurements at  $T \geq 20$  K and in fields between  $\sim 0.7$  T and  $\sim 2$  T enable us to investigate the phase boundary between phases I and III. Notably, the associated anomalies qualitatively change with decreasing temperature which implies that the nature of the phase transition changes from a continuous character to a discontinuous one upon cooling. This is seen in  $\lambda_c$  and  $\partial M_c/\partial B$  which show a  $\lambda$ -like behaviour at 35 K and 40 K (see Fig. 6). Concomitantly,  $\lambda$ -like anomalies are also visible in  $\alpha_c$  and  $\partial(\chi T)/\partial T$  at 1 T and 0.7 T (Fig. 4 and Fig. 10a,b). With decreasing temperature however the  $\lambda$ -like character of the magnetostriction anomaly vanishes and becomes more symmetric until it is undoubtedly symmetric around 25 K (Fig. 6a). In the temperature-dependent measurements, the anomaly in  $\alpha_c$  loses its  $\lambda$ -shape between 1 T and 1.3 T thereby further validating the observation in the isothermal studies. The symmetric peaks imply jumps in the  $c$  axis length and in the magnetisation, *i.e.*, they prove the first order nature of the phase transition in this region of the phase diagram. Our observations hence imply the presence of a tricritical point on the phase boundary between phase I and III at  $\sim 33$  K.

Below about 20 K, the evolution of the skyrmion lattice phase II is evidenced by the appearance of two subsequent jumps in magnetostriction and isothermal magnetisation signaling the discontinuous phase boundaries I-II and II-III. The behaviour at  $T = 2$  K is shown in detail in Fig. 7 which shows that phase II extends from  $B_{I-II}(2\text{K}) = 2.02(2)$  T to  $B_{II-III}(2\text{K}) = 2.23(2)$  T with  $B_{I-II}$  and  $B_{II-III}$  being the critical fields of the phase transition from phase I to II and phase II to III respec-

tively<sup>2</sup>. Both critical fields show hysteretic behaviour which further illustrates the discontinuous character of the phase boundaries (see Fig. S10 and Fig. S12 in the SM) with a field-hysteresis  $\sim 0.05(1)$  T. Upon heating, the skyrmion lattice phase is suppressed by phase III and becomes narrower for higher temperatures (see Fig. 8).

The transition temperature from the PM phase into the fan structure phase III is continuously suppressed in external magnetic fields as expected for an antiferromagnetically ordered state. In contrast to previously reported phase diagrams [28, 35, 38], phase III however does not extend to highest field since we observe a novel phase VII below about 15 K. The phase boundary III-VII is nearly temperature-independent as evidenced by a peak in  $\lambda_c$  and  $\partial M_c/\partial B$  at  $B_{III-VII} \simeq 8.5$  T. The observed symmetric anomaly (see inset Fig. 7) indicates a first order phase transition as also illustrated by the small hysteresis as shown in Fig. S10 and Fig. S12 in the SM. The respective jumps at  $T = 2$  K in  $\Delta L_c/L_c$  and  $\Delta M$  amount to  $1.9(5) \times 10^{-6}$  and  $3.9(9) \times 10^{-3} \mu_B/\text{f.u.}$ , respectively. Finally, at 2 K the fully polarised phase is reached above  $\sim 9.3$  T (cf. Fig 8).

<sup>2</sup> Similar behaviour is reported in Ref. [46] where magnetostriction shows two consecutive but smeared-out anomalies. The measurement temperature in Ref. [46] is not specified but the reported data suggest  $T < 10$  K.

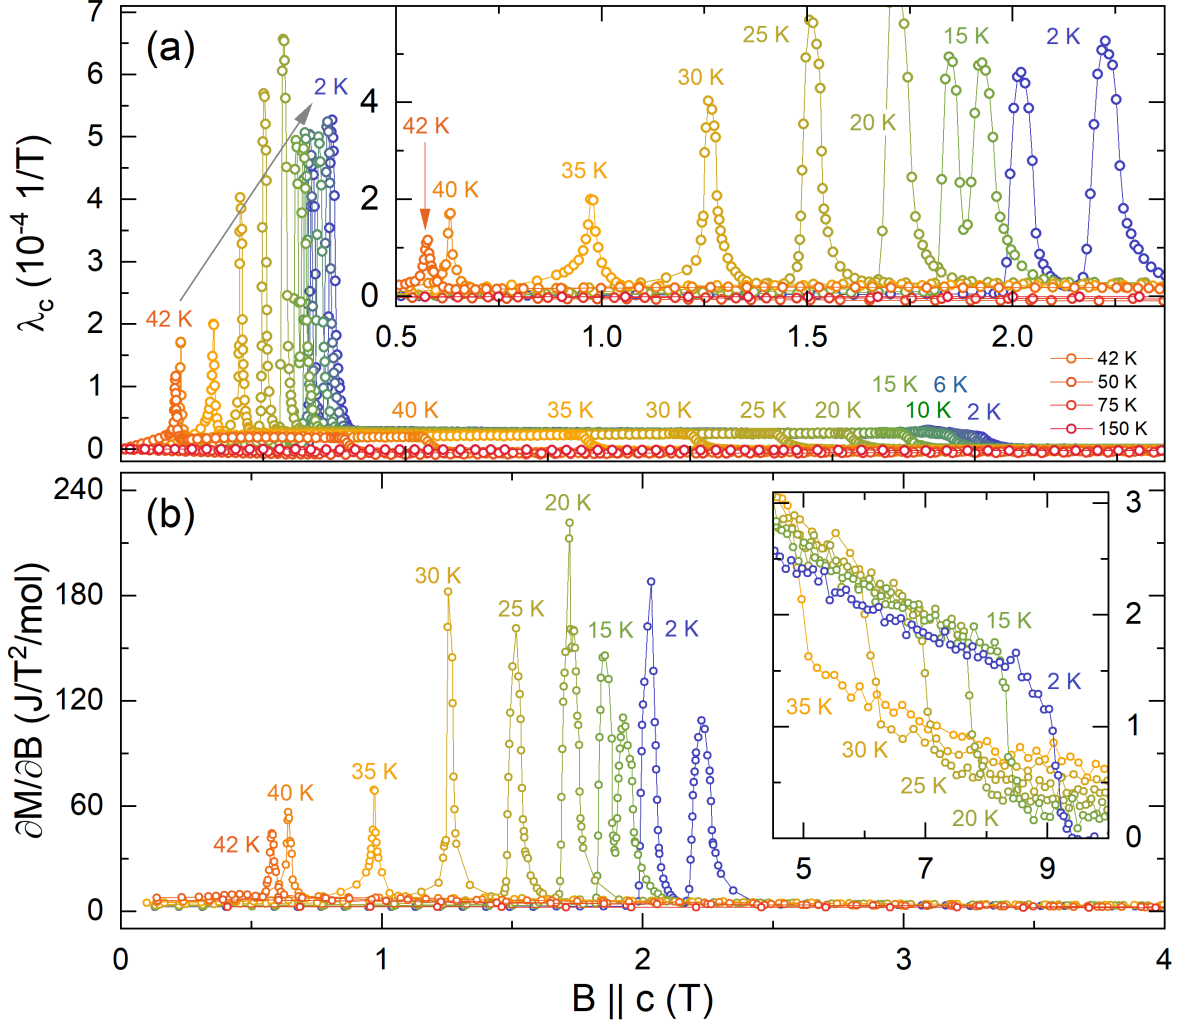


FIG. 6. (a) Magnetic field dependence of the magnetostriction coefficient  $\lambda_c$  for  $B \parallel c$  at temperatures between 2 K and 150 K. The inset shows the region between 0.5 T and 2.3 T in more detail. (b) Magnetic susceptibility  $\partial M_c/\partial B$  at various temperatures for  $B \parallel c$ . The inset shows the behaviour at the fully polarised state in more detail. See Figs. S8 and S10 in the SM [41] for separate plots of the data.

### C. Uniaxial pressure effects on the skyrmion lattice Phase

The response of the skyrmion lattice phase to uniaxial pressure can be deduced from the jump-like features in the data and quantified via Clausius-Clapeyron equations (e.g., [53]). For constant temperature the equations yield the dependence of the transition field  $B^*$  on uniaxial pressure applied along the  $i$  axis from the associated jumps in the length  $\Delta L_i$  and in the magnetisation  $\Delta M_{B \parallel i}$ :

$$\left. \frac{\partial B^*}{\partial p_i} \right|_T = V_m \frac{\Delta L_i/L_i}{\Delta M_{B \parallel i}}. \quad (3)$$

Analogously, when measuring at constant magnetic field  $B$ , the ratio of the jumps in the length  $\Delta L_i$  and the entropy jump  $\Delta S$  yield the uniaxial pressure dependence

of the ordering temperature  $T^*(B)$ :

$$\left. \frac{\partial T^*}{\partial p_i} \right|_B = V_m \frac{\Delta L_i/L_i}{\Delta S} \quad (4)$$

For our analysis, we deduce the  $\Delta S$  from the slope of the phase boundary at constant pressure at the respective magnetic field by exploiting  $\Delta S = -\Delta M_{B \parallel i}/(\partial T^*/\partial B|_p)$ . This finally yields:

$$\left. \frac{\partial T^*}{\partial p_i} \right|_B = -V_m \left. \frac{\partial T^*}{\partial B} \right|_p \frac{\Delta L_i/L_i}{\Delta M_{B \parallel i}} \quad (5)$$

Similarly to the above mentioned procedure to determine anomaly sizes, we have extracted the jumps  $\Delta L_c$  and  $\Delta M_{B \parallel c}$  from the experimental data by fitting lines to

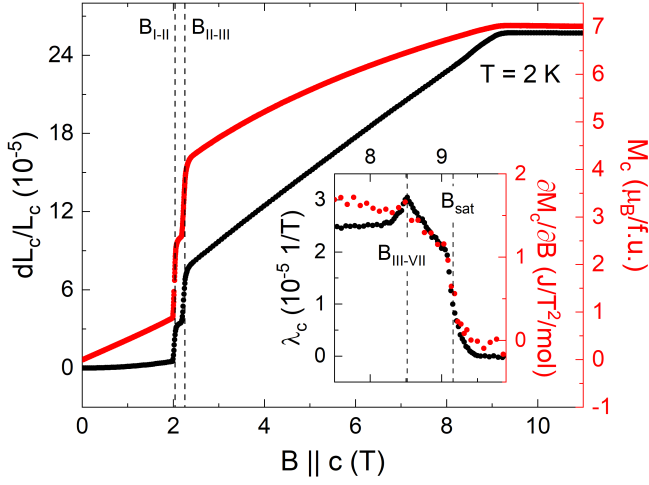


FIG. 7. Magnetostriction  $dL_c(B)/L_c$  (left ordinate) and isothermal magnetisation  $M_c$  (right ordinate) as a function of magnetic field  $B \parallel c$  at  $T = 2$  K. Inset: Magnetostriction coefficient  $\lambda_c$  (left ordinate) and magnetic susceptibility  $\partial M_c/\partial B$  (right ordinate) around the saturation field  $B_{\text{sat}}$ . Vertical dashed lines show the transitions into and out of the skyrmion lattice phase at  $B_{\text{I-II}}$  and  $B_{\text{II-III}}$ ,  $B_{\text{III-VII}}$ , and  $B_{\text{sat}}$ .

the data well below and above the anomalies. The resulting jumps and calculated uniaxial pressure dependencies obtained from the isothermal measurements at the phase boundaries into the SKL phase (I-II, *i.e.*,  $B_{\text{I-II}}$ ) and out of the SKL phase (II-III;  $B_{\text{II-III}}$ ) are displayed in Table S1. The calculated uniaxial pressure dependencies for the respective phase boundaries exhibit no significant changes with temperature, being  $\partial B_{\text{I-II}}/\partial p_c \simeq 0.17$  T/GPa and  $\partial B_{\text{II-III}}/\partial p_c \simeq 0.24$  T/GPa on average. Furthermore by extracting the slope of the respective phase boundary  $\partial T_j/\partial B$  ( $j = \text{I-II}, \text{II-III}$ ) the pressure dependency of the transition temperature  $\partial T_j/\partial p_c$  can be calculated using Eq. 5 and values from Table S1 in the SM. Specifically,  $\partial T_j/\partial B$  was approximated by fitting a polynomial to the respective phase boundary and determining the field derivative. Table S2 in the SM lists the approximated slopes of the respective phase boundaries and the obtained uniaxial pressure dependencies. For both phase boundaries I-II and II-III the uniaxial pressure dependencies of the transition temperatures  $T_{\text{I-II}}$  and  $T_{\text{II-III}}$  are positive being on the order of 10 K/GPa. Furthermore, for both boundaries,  $\partial T_j/\partial p_c$  increases for higher magnetic fields which can be mostly attributed to the increasing slope of the phase boundary  $\partial T_j/\partial B$ .

#### D. Discussion

The phase diagram in Fig. 8 shows the presence of six distinct ordered phases evolving below  $T_N$  in external magnetic fields  $B$  applied along the crystallographic  $c$  axis. Similar to the analysis of thermal expansion and

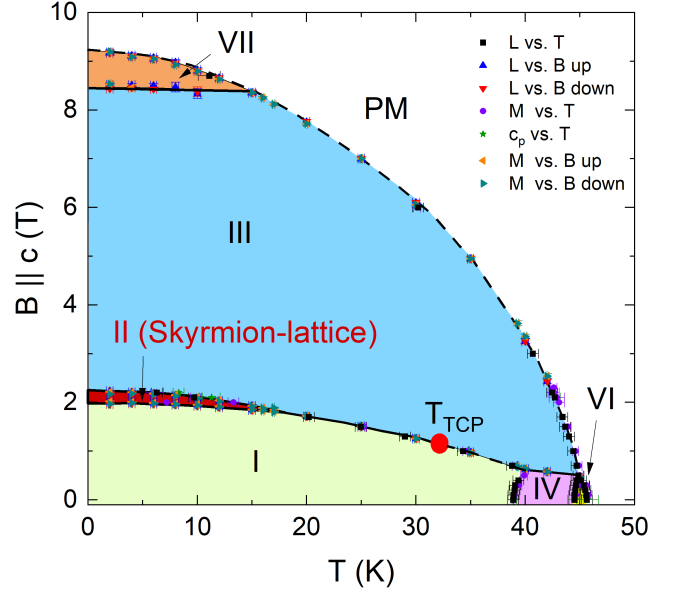


FIG. 8. Magnetic phase diagram of  $\text{GdRu}_2\text{Si}_2$  for  $B \parallel c$  axis constructed from magnetisation  $M(T, B)$ , dilatometry  $L(T, B)$  and specific heat  $c_p(T, B)$  data. Lines are guides to the eye. Solid/dashed lines represent first/second order phase boundaries;  $T_{\text{TCP}}$  approximates the position of the tricritical point. Phase II (red) marks the skyrmion lattice phase, PM (white) the paramagnetic phase, phase I (green) and III (blue) are double- $Q$ -states. The spin configuration in phase IV (purple) has not been resolved yet; phases VI (yellow) and VII (orange) have not been reported before.

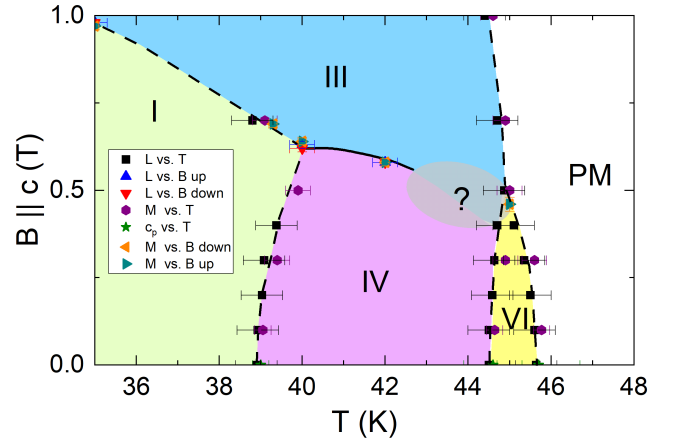


FIG. 9. Magnetic phase diagram for  $B \parallel c$  in more detail around  $T_N$  (see Fig. 8). The exact positions of the boundaries between phases III, IV, and VI at  $B \parallel c \simeq 0.5$  T cannot be precisely determined by our data.

magnetostriction anomalies at the boundaries of the SKL phase, the data in Figs. 2-6 as well as further data presented in the SM [41] imply the dependencies of the respective ordering phenomena upon application of uniaxial pressure along the  $c$  axis ( $p_c$ ). The results are

summarized in table II and, interestingly, show only positive values for the uniaxial pressure dependencies. This implies that phase I is stabilised over all adjacent phases II, III and IV in temperature and magnetic field. Phases IV and VI, the remaining zero field phases, are both shifted to higher temperatures (see Fig. 9.) and span over a larger temperature interval for  $p||c$  since  $\partial T_{I-IV}/\partial p_c < \partial T_{IV-VI}/\partial p_c < \partial T_{VI-PM}/\partial p_c$ . Furthermore, phase IV is stabilised over phase III under uniaxial pressure  $p_c$ . As already discussed above, the skyrmion lattice phase shifts to higher fields and widens in magnetic field. Also phases III and VII are stabilised towards higher temperatures and magnetic fields upon applying  $p||c$  axis. Notably, phase VII is particularly sensitive to  $p_c$  as  $\partial B_{III-VII}/\partial p_c$  is two orders of magnitude larger than the pressure dependencies of all other phase boundaries. It is of the order of 5 T/GPa, implying that phase VII is strongly suppressed in favour of phase III.

Pressure effects on the skyrmion lattice phase are of particular interest as they provide further insight into the microscopic mechanism stabilising this phase. The observed uniaxial pressure dependencies of the phase boundaries enclosing the skyrmion lattice phase are all positive, *i.e.*, uniaxial pressure along the  $c$  axis stabilizes the skyrmion lattice towards higher fields and temperatures. Furthermore, for all measured temperatures  $\partial B_{II-III}/\partial p_c$  is larger than  $\partial B_{I-II}/\partial p_c$  so that the skyrmion lattice phase also widens in magnetic field at an approximate rate of  $\Delta B_{\text{skyr}}/p_c \approx 0.07$  T/GPa. An enhancement of the skyrmion lattice phase under uniaxial pressure is also observed in materials such as  $\text{Gd}_2\text{PdSi}_3$  [54],  $\text{Cu}_2\text{OSeO}_3$  [55] and  $\text{MnSi}$  [56]. Especially interesting for comparison is  $\text{Gd}_2\text{PdSi}_3$  which also crystallises in a centrosymmetric structure and is predominantly governed by RKKY interactions [24]. Similar to the present case the SKL phase widens in magnetic field in  $\text{Gd}_2\text{PdSi}_3$  for uniaxial pressure parallel to the  $c$  axis at approximately half the rate compared to  $\text{GdRu}_2\text{Si}_2$ . However for  $\text{Gd}_2\text{PdSi}_3$  the sign of pressure dependence is opposite so that the SKL phase shifts towards lower magnetic fields. The pressure dependence of the critical fields is weaker by approximately one order of magnitude in  $\text{Gd}_2\text{PdSi}_3$  than in  $\text{GdRu}_2\text{Si}_2$  [54]. In contrast to the strongly differing pressure dependencies of the critical fields, the ordering temperatures of the SKL phases in both materials change is of similar magnitude of however again opposite signs: While in  $\text{Gd}_2\text{PdSi}_3$ ,  $\partial T_{\text{skyr}}/\partial p_c = -6.1$  K/GPa, in  $\text{GdRu}_2\text{Si}_2$  we find  $\partial T_{\text{skyr}}/\partial p_c \simeq +15$  K/GPa (see table II). In case of the two non-centrosymmetric systems  $\text{Cu}_2\text{OSeO}_3$  and  $\text{MnSi}$  the respective SKL phases also widen in magnetic field under pressure [55, 56]. Moreover, the SKL phase in  $\text{MnSi}$  shows the general shift towards higher fields, while for  $\text{Cu}_2\text{OSeO}_3$  the SKL phase extends towards higher temperatures as observed for  $\text{GdRu}_2\text{Si}_2$ .

While uniaxial pressure effects on all ordered phases are always positive, the effect of external magnetic fields  $B||c$  differs for the various phases not only quantitatively

but also with respect to its sign. At low magnetic field  $B \lesssim 0.5$  T phase I and IV are stabilised over their respective higher temperature phases, *i.e.*, the phase boundaries show positive slope  $\partial T_1/\partial B_c > 0$  and  $\partial T_2/\partial B_c > 0$  (see Fig. 9). Thermodynamically, this is associated with an increase of magnetisation or its derivative upon cooling at the respective phase boundaries which is indeed observed in the magnetisation data in Fig. 1. All other phase boundaries show negative slopes, *i.e.*, the underlying magnetic orders are suppressed by  $B||c$  (see Fig. 8).

Our results show that the previously unreported phase VII forms a pocket at high-fields and low-temperatures with an upper boundary to the fully polarized state,  $B_{\text{sat}}(T)$  is very similar to what would be expected for phase III (*cf.* Fig. 8). While the phase boundary  $B_{III-VII}(T)$  is nearly temperature independent, it displays a comparably giant uniaxial pressure dependence so that phase VII will be fully suppressed by applying  $p_c$  of a few tenth of GPa. By means of the Clausius-Clapeyron equation we obtain an upper limit of the entropy changes of  $\Delta S_{III-VII}(T = 2 \text{ K}) < 5 \times 10^{-4}$  J/(mol K) which uses the observed jump in  $M$  and the tiny slope ( $\ll 0.1$  T/K) of the phase boundary at the respective transition. Although the spin structure of the new phase has not been studied yet, first principal numerical studies by Bouaziz *et al.* [39] may reveal a possible nature of this phase. Their calculations for  $\text{GdRu}_2\text{Si}_2$  predict that in the fully polarized state close to the boundary of the cycloidal phase (phase III) single metastable skyrmions emerge. One might speculate whether such skyrmions form a superstructure which could be our observed phase VII. If so, it is very sensitive to and easily suppressed by pressure  $p_c$  while entropically it is very similar to phase III.

We finally discuss the phase boundary between phase I

TABLE II. Uniaxial pressure dependencies of the phase boundaries  $j$  shown in Fig. 8 for  $p||c$ . The presented values are from calculations using the Clausius-Clapeyron and Ehrenfest relations (see Eq. 1, Eq. 5 and Eq. 3). Values marked with an asterisk have been obtained from phase boundaries where more than one value could be calculated. In these cases, the averages are taken and the error bars include the variations at the phase boundary. If no quantitative values can be obtained the sign of the pressure dependence is given.

phase boundary $j$	$\partial B_j/\partial p_c$ [T/GPa]	$\partial T_j/\partial p_c$ [K/GPa]
I - IV	+	1.2(3)
IV - VI	+	2.6(4)
VI - PM	+	3.3(3)
I - III (1 <sup>st</sup> -order)	0.20(4)*	4.5(6)
I - III (2 <sup>nd</sup> -order)	0.13(3)*	+
IV - III	0.11(2)	+
III - PM	+	+
I - II	0.17(3)*	20(-13,+60)*
II - III	0.24(3)*	15(-11,+40)*
III - VII	4.3(1.5)	+
VII - PM	+	+



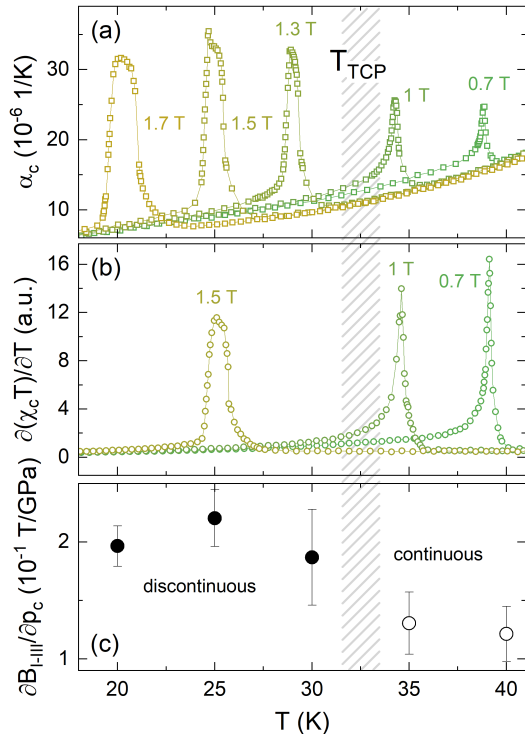


FIG. 10. Anomalies associated with the phase transition between phases I and III in (a) the linear thermal expansion coefficient  $\alpha_c$ , and (b) Fisher's specific heat  $\partial(\chi_c T)/\partial T$ . (c) Uniaxial pressure dependence  $\partial B_{I-III}/\partial p_c$  at the phase boundary I-III. The dashed region marks the temperature regime of the tricritical point.

and III which, as mentioned above, displays a continuous nature above 35 K as demonstrated by textbook-like anomalies at  $B_{I-III}$  while we observe 1<sup>st</sup> order discontinuities in  $M$  and  $L$  below 25 K (see Fig. 4 and 5). The evolution of the anomaly shape along the phase boundary is illustrated Fig. 10a and 10b which shows the change from asymmetric and clearly  $\lambda$ -shaped anomalies (confirming the continuous nature of the transition) for  $T > T_{TCP}$  to rather symmetric anomalies with sharp low-temperature flanks (indicating the 1<sup>st</sup> order character of the boundary) in  $\alpha_c$  and  $\partial(\chi_c T)/\partial T$  for  $T < T_{TCP}$ . Our findings suggest the existence of a tricritical point (TCP) at  $T_{TCP} \simeq 33$  K (see Fig. 8), *i.e.*, well above the triple point where the SKL evolves in between phases I and III. The existence of a TCP is further supported by the temperature dependence of the uniaxial pressure dependence of  $B_{I-III}(T)$  presented in Fig. 10c. Above and below  $T_{TCP}$  the uniaxial pressure dependence of the critical field

$\partial B_{I-III}/\partial p_c$  is fairly constant but its value changes by about 40% at  $T_{TCP}$ . Overall, the continuous transition between double- $Q$  magnetic structures in phases I and III evolves a discontinuous character upon cooling (see Fig. 10a,b) before the SKL phase evolves upon further cooling at  $T_{tri} \simeq 18$  K  $<$   $T_{TCP}$ . This behaviour shows slight similarities but essentially contrasts to findings in the skyrmion lattice systems MnSi [57, 58],  $\text{Cu}_2\text{OSeO}_3$  [59] and  $\text{GaV}_4\text{S}_8$  [60] where tricritical behaviour is reported only at triple points of the phase diagram. In all three examples, the TCP appears at a phase boundary towards the fully polarised phase which in case of the skyrmion-pocket phases in MnSi and  $\text{Cu}_2\text{OSeO}_3$  does not involve a phase boundary towards the skyrmion phase while only in  $\text{GaV}_4\text{S}_8$  [60] the TCP edges the SKL phase.

#### IV. SUMMARY

We report high-resolution capacitance dilatometry, specific heat, and magnetisation studies which are used to complete the magnetic phase diagram in  $\text{GdRu}_2\text{Si}_2$ . We observe three successive antiferromagnetic phases in zero magnetic field (phases I, IV, VI), with phase VI not yet reported and of unknown structure. In addition, we also find a new high-field phase (phase VII), which features a comparably giant uniaxial pressure dependence. By means of our dilatometric data we determine magneto-elastic effects as well as uniaxial pressure dependencies of the various phases. The skyrmion lattice phase is enhanced towards higher fields and temperatures and widens at a rate of 0.07 T/GPa when uniaxial pressure is applied along the  $c$  axis. Notably, the SKL pocket phase evolves through a triple point  $T_{tri}$  from a phase boundary between the double- $Q$  magnetic structures in phases I and III which in addition indicates a tricritical point at  $T_{TCP} \simeq 33$  K  $>$   $T_{tri} \simeq 18$  K, thereby highlighting the relevance of critical fluctuations for the evolution of the skyrmion lattice phase in  $\text{GdRu}_2\text{Si}_2$ .

#### ACKNOWLEDGMENTS

We acknowledge valuable experimental advice for the specific heat studies at the University of Warwick by Prof. Martin Lees. Support by Deutsche Forschungsgemeinschaft (DFG) under Germany's Excellence Strategy EXC2181/1-390900948 (the Heidelberg STRUCTURES Excellence Cluster) is gratefully acknowledged. L. G. acknowledges funding by the International Max-Planck Research School for Quantum Dynamics (IMPRS-QD) Heidelberg. The work at the University of Warwick was supported by EPSRC, UK through Grants EP/T005963/1 and EP/N032128/1.

- [1] T. Skyrme, A non-linear field theory, Proceedings of the Royal Society of London. Series A. Mathematical and Physical Sciences **260**, 127 (1961).
- [2] T. Skyrme, A unified field theory of mesons and baryons, Nuclear Physics **31**, 556 (1962).
- [3] A. N. Bogdanov and D. A. Yablonskii, Thermodynamically stable “vortices” in magnetically ordered crystals. the mixed state of magnets, Sov. Phys. JETP **68**, 101 (1989).
- [4] N. Nagaosa and Y. Tokura, Topological properties and dynamics of magnetic skyrmions (2013).
- [5] F. Büttner, C. Moutafis, M. Schneider, B. Krüger, C. M. Günther, J. Geilhufe, C. v. K. Schmising, J. Mohanty, B. Pfau, S. Schaffert, A. Bisig, M. Foerster, T. Schulz, C. A. F. Vaz, J. H. Franken, H. J. M. Swagten, M. Kläui, and S. Eisebitt, Dynamics and inertia of skyrmionic spin structures, Nature Physics **11**, 225 (2015).
- [6] J. Iwasaki, M. Mochizuki, and N. Nagaosa, Current-induced skyrmion dynamics in constricted geometries, Nature nanotechnology **8**, 742 (2013).
- [7] M. Lee, W. Kang, Y. Onose, Y. Tokura, and N. P. Ong, Unusual hall effect anomaly in mnsi under pressure, Physical Review Letters **102**, 186601 (2009).
- [8] G. Yin, Y. Liu, Y. Barlas, J. Zang, and R. K. Lake, Topological spin hall effect resulting from magnetic skyrmions, Physical Review B **92**, 10.1103/PhysRevB.92.024411 (2015).
- [9] M. Leroux, M. J. Stolt, S. Jin, D. V. Pete, C. Reichardt, and B. Maierov, Skyrmion lattice topological hall effect near room temperature, Scientific reports **8**, 15510 (2018).
- [10] C. Hanneken, F. Otte, A. Kubetzka, B. Dupé, N. Romming, K. von Bergmann, R. Wiesendanger, and S. Heinze, Electrical detection of magnetic skyrmions by tunnelling non-collinear magnetoresistance, Nature nanotechnology **10**, 1039 (2015).
- [11] D. Prychynenko, M. Sitte, K. Litzius, B. Krüger, G. Bourianoff, M. Kläui, J. Sinova, and K. Everschor-Sitte, Magnetic skyrmion as a nonlinear resistive element: A potential building block for reservoir computing, Physical Review Applied **9**, 10.1103/PhysRevApplied.9.014034 (2018).
- [12] K. M. Song, J.-S. Jeong, B. Pan, X. Zhang, J. Xia, S. Cha, T.-E. Park, K. Kim, S. Finizio, J. Raabe, J. Chang, Y. Zhou, W. Zhao, W. Kang, H. Ju, and S. Woo, Skyrmion-based artificial synapses for neuromorphic computing, Nature Electronics **3**, 148 (2020).
- [13] T. Yokouchi, S. Sugimoto, B. Rana, S. Seki, N. Ogawa, Y. Shiomi, S. Kasai, and Y. Otani, Pattern recognition with neuromorphic computing using magnetic field-induced dynamics of skyrmions, Science advances **8**, eabq5652 (2022).
- [14] S. Luo and L. You, Skyrmion devices for memory and logic applications, APL Materials **9**, 10.1063/5.0042917 (2021).
- [15] W. Koshibae, Y. Kaneko, J. Iwasaki, M. Kawasaki, Y. Tokura, and N. Nagaosa, Memory functions of magnetic skyrmions, Japanese Journal of Applied Physics **54**, 053001 (2015).
- [16] G. Yu, P. Upadhyaya, Q. Shao, H. Wu, G. Yin, X. Li, C. He, W. Jiang, X. Han, P. K. Amiri, and K. L. Wang, Room-temperature skyrmion shift device for memory application, Nano letters **17**, 261 (2017).
- [17] S. Luo, M. Song, X. Li, Y. Zhang, J. Hong, X. Yang, X. Zou, N. Xu, and L. You, Reconfigurable skyrmion logic gates, Nano letters **18**, 1180 (2018).
- [18] X. Zhang, M. Ezawa, and Y. Zhou, Magnetic skyrmion logic gates: conversion, duplication and merging of skyrmions, Scientific reports **5**, 9400 (2015).
- [19] N. Sisodia, J. Pelloux-Prayer, L. D. Buda-Prejbeanu, L. Anghel, G. Gaudin, and O. Boulle, Programmable skyrmion logic gates based on skyrmion tunneling, Physical Review Applied **17**, 10.1103/PhysRevApplied.17.064035 (2022).
- [20] S. Mühlbauer, B. Binz, F. Jonietz, C. Pfleiderer, A. Rosch, A. Neubauer, R. Georgii, and P. Böni, Skyrmion lattice in a chiral magnet, Science (New York, N.Y.) **323**, 915 (2009).
- [21] S. Seki, X. Z. Yu, S. Ishiwata, and Y. Tokura, Observation of skyrmions in a multiferroic material, Science (New York, N.Y.) **336**, 198 (2012).
- [22] I. Kézsmárki, S. Bordács, P. Milde, E. Neuber, L. M. Eng, J. S. White, H. M. Rønnow, C. D. Dewhurst, M. Mochizuki, K. Yanai, H. Nakamura, D. Ehlers, V. Tsurkan, and A. Loidl, Néel-type skyrmion lattice with confined orientation in the polar magnetic semiconductor  $\text{Gd}_2\text{V}_2\text{O}_7$ , Nature materials **14**, 1116 (2015).
- [23] X. Z. Yu, Y. Onose, N. Kanazawa, J. H. Park, J. H. Han, Y. Matsui, N. Nagaosa, and Y. Tokura, Real-space observation of a two-dimensional skyrmion crystal, Nature **465**, 901 (2010).
- [24] T. Kurumaji, T. Nakajima, M. Hirschberger, A. Kikkawa, Y. Yamasaki, H. Sagayama, H. Nakao, Y. Taguchi, T.-H. Arima, and Y. Tokura, Skyrmion lattice with a giant topological hall effect in a frustrated triangular-lattice magnet, Science (New York, N.Y.) **365**, 914 (2019).
- [25] M. Hirschberger, T. Nakajima, S. Gao, L. Peng, A. Kikkawa, T. Kurumaji, M. Kriener, Y. Yamasaki, H. Sagayama, H. Nakao, K. Ohishi, K. Kakurai, Y. Taguchi, X. Yu, T.-H. Arima, and Y. Tokura, Skyrmion phase and competing magnetic orders on a breathing kagomé lattice, Nature communications **10**, 5831 (2019).
- [26] R. Takagi, N. Matsuyama, V. Ukleev, Le Yu, J. S. White, S. Francoual, J. R. L. Mardegan, S. Hayami, H. Saito, K. Kaneko, K. Ohishi, Y. Ōnuki, T.-H. Arima, Y. Tokura, T. Nakajima, and S. Seki, Square and rhombic lattices of magnetic skyrmions in a centrosymmetric binary compound, Nature communications **13**, 1472 (2022).
- [27] N. D. Khanh, T. Nakajima, X. Yu, S. Gao, K. Shibata, M. Hirschberger, Y. Yamasaki, H. Sagayama, H. Nakao, L. Peng, K. Nakajima, R. Takagi, T.-H. Arima, Y. Tokura, and S. Seki, Nanometric square skyrmion lattice in a centrosymmetric tetragonal magnet, Nature nanotechnology **15**, 444 (2020).
- [28] Y. Yasui, C. J. Butler, N. D. Khanh, S. Hayami, T. Nomoto, T. Hanaguri, Y. Motome, R. Arita, T.-H. Arima, Y. Tokura, and S. Seki, Imaging the coupling between itinerant electrons and localised moments in the centrosymmetric skyrmion magnet  $\text{GdRu}_2\text{Si}_2$ , Nature

- communications **11**, 5925 (2020).
- [29] A. O. Leonov and M. Mostovoy, Multiply periodic states and isolated skyrmions in an anisotropic frustrated magnet, *Nature communications* **6**, 8275 (2015).
- [30] T. Okubo, S. Chung, and H. Kawamura, Multiple-q states and the skyrmion lattice of the triangular-lattice heisenberg antiferromagnet under magnetic fields, *Physical Review Letters* **108**, 017206 (2012).
- [31] S. Hayami, R. Ozawa, and Y. Motome, Effective bilinear-biquadratic model for noncoplanar ordering in itinerant magnets, *Physical Review B* **95**, 10.1103/PhysRevB.95.224424 (2017).
- [32] K. Hiebl, C. Horvath, P. Rogl, and M. J. Sienko, Magnetic properties and structural chemistry of ternary silicides (re, th, u)ru<sub>2</sub>si<sub>2</sub> (re = rare earth), *Journal of Magnetism and Magnetic Materials* **37**, 287 (1983).
- [33] I. Felner and I. Nowik, Itinerant and local magnetism, superconductivity and mixed valency phenomena in rm<sub>2</sub>si<sub>2</sub>, (r = rare earth, m = rh, ru)<sup>o</sup>, *Journal of Physics and Chemistry of Solids* **45**, 419 (1984).
- [34] M. Ślaski, A. Szytuła, J. Leciejewicz, and A. Zygmunt, Magnetic properties of reru<sub>2</sub>si<sub>2</sub> (re=pr, nd, gd, tb, dy, er) intermetallics, *Journal of Magnetism and Magnetic Materials* **46**, 114 (1984).
- [35] G. D. A. Wood, D. D. Khalyavin, D. A. Mayoh, J. Bouaziz, A. E. Hall, S. J. R. Holt, F. Orlandi, P. Manuel, S. Blügel, J. B. Staunton, O. A. Petrenko, M. R. Lees, and G. Balakrishnan, Double-q ground state with topological charge stripes in the centrosymmetric skyrmion candidate gdru<sub>2</sub>si<sub>2</sub>, *Physical Review B* **107**, 10.1103/PhysRevB.107.L180402 (2023).
- [36] A. Garnier, D. Gignoux, N. Iwata, D. Schmitt, T. Shigeoka, and F. Y. Zhang, Anisotropic metamagnetism in gdru<sub>2</sub>si<sub>2</sub>, *Journal of Magnetism and Magnetic Materials* **140-144**, 899 (1995).
- [37] J. A. M. Paddison, J. Bouaziz, A. F. May, Q. Zhang, S. Calder, D. Abernathy, J. B. Staunton, S. Blügel, and A. D. Christianson, arxiv:2406.04524.
- [38] N. D. Khanh, T. Nakaajima, S. Hayami, S. Gao, Y. Yamasaki, H. Sagayama, H. Nakao, R. Takagi, Y. Motome, Y. Tokura, T.-H. Arima, and S. Seki, Zoology of multiple-q spin textures in a centrosymmetric tetragonal magnet with itinerant electrons, *Advanced science (Weinheim, Baden-Wurttemberg, Germany)* **9**, e2105452 (2022).
- [39] J. Bouaziz, E. Mendive-Tapia, S. Blügel, and J. B. Staunton, Fermi-surface origin of skyrmion lattices in centrosymmetric rare-earth intermetallics, *Physical Review Letters* **128**, 157206 (2022).
- [40] S. V. Eremeev, D. Glazkova, G. Poelchen, A. Kraiker, K. Ali, A. V. Tarasov, S. Schulz, K. Kliemt, E. V. Chulkov, V. S. Stolyarov, A. Ernst, C. Krellner, D. Y. Usachov, and D. V. Vyalikh, Insight into the electronic structure of the centrosymmetric skyrmion magnet gdru<sub>2</sub>si<sub>2</sub>, *Nanoscale advances* **5**, 6678 (2023).
- [41] See supplemental material at [url will be inserted by publisher] which lists the anomaly sizes, pressure and field dependencies at the different phase boundaries. In addition, it contains further detailed data of magnetisation, thermal expansion and magnetostriction and illustrates how the anomaly sizes have been extracted from the experimental data.
- [42] R. Kuchler, T. Bauer, M. Brando, and F. Steglich, A compact and miniaturized high resolution capacitance dilatometer for measuring thermal expansion and magnetostriction, *The Review of scientific instruments* **83**, 095102 (2012).
- [43] R. Kuchler, A. Wörl, P. Gegenwart, M. Berben, B. Bryant, and S. Wiedmann, The world's smallest capacitive dilatometer, for high-resolution thermal expansion and magnetostriction in high magnetic fields, *The Review of scientific instruments* **88**, 083903 (2017).
- [44] J. Werner, W. Hergett, M. Gertig, J. Park, C. Koo, and R. Klingeler, Anisotropy-governed competition of magnetic phases in the honeycomb quantum magnet na<sub>3</sub>ni<sub>2</sub>sbo<sub>6</sub> studied by dilatometry and high-frequency esr, *Physical Review B* **95**, 10.1103/PhysRevB.95.214414 (2017).
- [45] T. Samanta, I. Das, and S. Banerjee, Comparative studies of magnetocaloric effect and magnetotransport behavior in gdru<sub>2</sub>si<sub>2</sub> compound, *Journal of Applied Physics* **104**, 10.1063/1.3043558 (2008).
- [46] J. Prokleška, J. Vejpravová, and V. Sechovský, Magnetostriction measurement of gdru<sub>2</sub>si<sub>2</sub> single crystal, *Journal of Physics: Conference Series* **51**, 127 (2006).
- [47] P. Gegenwart, Grüneisen parameter studies on heavy fermion quantum criticality, *Reports on Progress in Physics* **79**, 114502 (2016).
- [48] M. Hoffmann, K. Dey, J. Werner, R. Bag, J. Kaiser, H. Wadepohl, Y. Skourski, M. Abdel-Hafiez, S. Singh, and R. Klingeler, Magnetic phase diagram, magnetoelastic coupling, and grüneisen scaling in cotio<sub>3</sub>, *Phys. Rev. B* **104**, 014429 (2021).
- [49] S. Spachmann, P. Berdonosov, M. Markina, A. Vasiliev, and R. Klingeler, Linear magnetoelastic coupling and magnetic phase diagrams of the buckled-kagomé antiferromagnet Cu<sub>3</sub>Bi(SeO<sub>3</sub>)<sub>2</sub>O<sub>2</sub>Cl, *Physical Review B* **12**, 7383 (2022).
- [50] R. Klingeler, J. Geck, S. Arumugam, N. Tristan, P. Reutler, B. Büchner, L. Pinsard-Gaudart, and A. Revcolevschi, Pressure-induced melting of the orbital polaron lattice in la<sub>1-x</sub>sr<sub>x</sub>mno<sub>3</sub>, *Phys. Rev. B* **73**, 214432 (2006).
- [51] J. Werner, S. Sauerland, C. Koo, C. Neef, A. Pollithy, Y. Skourski, and R. Klingeler, High magnetic field phase diagram and failure of the magnetic grüneisen scaling in lifepo<sub>4</sub>, *Phys. Rev. B* **99**, 214432 (2019).
- [52] R. Kuchler, *Thermische Ausdehnung und divergierendes Grüneisenverhältnis in Schwere-Fermionen-Systemen*, Dissertation, Technische Universität Dresden, Dresden (2005).
- [53] U. Stockert, N. Leps, L. Wang, G. Behr, S. Wurmehl, B. Büchner, and R. Klingeler, Pr magnetism and its interplay with the fe spin-density wave in prfeaso<sub>1-x</sub>fx (x = 0,0.15), *Phys. Rev. B* **86**, 144407 (2012).
- [54] S. Spachmann, A. Elghandour, M. Frontzek, W. Löser, and R. Klingeler, Magnetoelastic coupling and phases in the skyrmion lattice magnet gd<sub>2</sub>pdsi<sub>3</sub> discovered by high-resolution dilatometry, *Physical Review B* **103**, 10.1103/PhysRevB.103.184424 (2021).
- [55] I. Levatić, P. Popčević, V. Šurija, A. Kruchkov, H. Berger, A. Magrez, J. S. White, H. M. Rønnow, and I. Živković, Dramatic pressure-driven enhancement of bulk skyrmion stability, *Scientific reports* **6**, 21347 (2016).
- [56] A. Chacon, A. Bauer, T. Adams, F. Rucker, G. Brandl, R. Georgii, M. Garst, and C. Pfleiderer, Uniaxial pressure dependence of magnetic order in mnsi, *Physical Review*

- Letters **115**, 267202 (2015).
- [57] A. Bauer, M. Garst, and C. Pfleiderer, Specific heat of the skyrmion lattice phase and field-induced tricritical point in mnsi, *Physical review letters* **110**, 177207 (2013).
- [58] L. Zhang, D. Menzel, C. Jin, H. Du, M. Ge, C. Zhang, L. Pi, M. Tian, and Y. Zhang, Critical behavior of the single-crystal helimagnet mnsi, *Physical Review B* **91**, 10.1103/PhysRevB.91.024403 (2015).
- [59] H. C. Chauhan, B. Kumar, J. K. Tiwari, and S. Ghosh, Multiple phases with a tricritical point and a lifshitz point in the skyrmion host cu2oseo3, *Physical Review B* **100**, 10.1103/PhysRevB.100.165143 (2019).
- [60] B. Liu, Z. Wang, Y. Zou, S. Zhou, H. Li, J. Xu, L. Zhang, J. Xu, M. Tian, H. Du, Y. Zhang, and Z. Qu, Field-induced tricritical behavior in the néel-type skyrmion host gav4s8, *Physical Review B* **102**, 10.1103/PhysRevB.102.094431 (2020).

## SUPPLEMENTAL INFORMATION

The supplemental information contains:

- Tables: Extracted values of the jumps in isothermal magnetisation  $M_c$ , magnetostriction  $dL_c/L_c$ , the respective slopes of the phase boundary  $\partial T/\partial B$  and the calculated pressure dependencies  $\partial B_{\text{crit}}/\partial p_c$  and  $\partial T_{\text{crit}}/\partial p_c$ .
- Scaling of the specific heat data with high temperature resolution.
- Inverse magnetic volume susceptibility including a Curie-Weiss-fit.
- Specific heat and fit of the phononic contribution by means of an Einstein-Debye model.
- Determination of the jumps in the specific heat and the thermal expansion coefficient.
- Thermal expansion and magnetostriction measurements in detail for  $B||c$  as well as their respective derivatives, *i.e.*, the thermal expansion and magnetostriction coefficients.
- Statistic magnetic susceptibility  $\chi_c$  and isothermal magnetisation  $M_c$  measurements in detail for  $B||c$  as well as Fisher's specific heat  $\partial(\chi_c T)/\partial T$  and the magnetic susceptibility  $\partial M_c/\partial B$ .

- Determination of the jumps in magnetostriction at the phase transitions in and out of the skyrmion lattice phase.

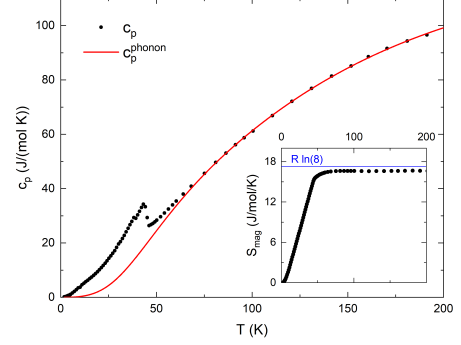


FIG. S1. Specific heat  $c_p$  vs. temperature in zero magnetic field measured on a large crystal up to 300 K. The red line represents the fitted lattice contribution  $c_p^{\text{ph}}$  by means of an Einstein-Debye model. The inset depicts the magnetic entropy changes obtained by integrating  $(c_p - c_p^{\text{ph}})/T$  which agree with the theoretically expected magnetic entropy for a  $\text{Gd}^{3+}$  system (blue line).

TABLE S1. Jumps in the isothermal magnetisation  $M_c(B)$  and the magnetostriction  $dL_c(B)/L_c$  (see text as well as Fig. S13 in the SM) at  $B_j$  ( $j = \text{I-II, II-III}$ ) for various temperatures  $T$  as well as the resulting uniaxial pressure dependencies calculated using the Clausius-Clapeyron equation at constant temperature (Eq. 3).

T [K]	$\frac{\Delta L_c}{L_c}$ [ $10^{-5}$ ]	$\Delta M_c$ [J/T/mol]	$\partial B_{\text{I-II}}/\partial p_c$ [T/GPa]	$\frac{\Delta L_c}{L_c}$ [ $10^{-5}$ ]	$\Delta M_c$ [J/T/mol]	$\partial B_{\text{II-III}}/\partial p_c$ [T/GPa]
I - II			II - III			
2	3.0(2)	8.8(2)	0.171(12)	4.2(2)	8.7(2)	0.242(13)
4	2.9(2)	8.8(3)	0.166(13)	4.2(2)	8.8(3)	0.240(14)
6	3.0(2)	8.6(3)	0.175(13)	4.1(2)	8.6(3)	0.239(14)
8	2.8(2)	8.4(3)	0.167(13)	4.0(2)	8.4(3)	0.240(14)
10	2.7(2)	8.2(3)	0.167(14)	3.9(2)	8.2(3)	0.240(15)
12	2.6(2)	8.1(3)	0.166(14)	3.8(2)	8.1(3)	0.236(15)
15	2.5(3)	7.7(3)	0.184(24)	3.4(3)	7.7(3)	0.223(22)

TABLE S2. Extracted slope from the two phase boundaries I-II and II-III (see text) at  $\partial T_j/\partial B$  ( $j = \text{I-II, II-III}$ ) for various magnetic fields  $B$  as well as the resulting uniaxial pressure dependencies calculated using the Clausius-Clapeyron equation at constant field (Eq. 5) and values from Table S1.

B [T]	$\partial T_{\text{I-II}}/\partial B$ [K/T]	$\partial T_{\text{I-II}}/\partial p_c$ [K/GPa]	B [T]	$\partial T_{\text{II-III}}/\partial B$ [K/T]	$\partial T_{\text{II-III}}/\partial p_c$ [K/GPa]
I - II			II - III		
1.85(1)	-45(5)	8.3(1.4)	1.93(1)	-26(4)	5.9(1.1)
1.91(1)	-56(4)	9.2(1.3)	2.04(1)	-32(4)	7.5(1.1)
1.95(1)	-70(5)	12(2)	2.10(1)	-35(4)	8.5(1.2)
1.97(1)	-81(8)	14(2)	2.15(1)	-43(4)	10.4(1.3)
1.99(1)	-102(20)	18(4)	2.18(1)	-53(4)	12.6(1.4)
2.01(1)	-162(100)	27(17)	2.21(1)	-85(10)	20(3)
2.02(1)	-316(150)	54(26)	2.22(1)	-154(75)	37(18)

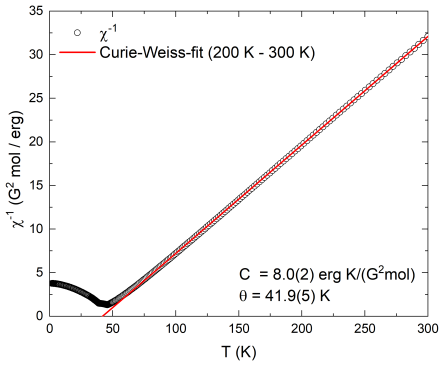


FIG. S2. Inverse magnetic volume susceptibility of  $\text{GdRu}_2\text{Si}_2$  and fit by means of a Curie-Weiss law. The obtained Curie constant  $C$  agrees well to the theoretically expected value of free  $\text{Gd}^{3+}$ .

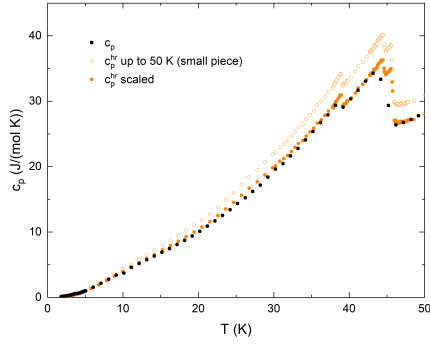


FIG. S3. Specific heat  $c_p$  vs. temperature in zero magnetic field measured on a large crystal up to 300 K (black filled dots) and on the small crystal 1 up to 50 K with higher resolution at temperatures in the vicinities of the phase transition (open orange circles). Orange filled circles show the data of crystal 1 scaled to the large crystal data. Scaling is performed so that both measurements match above  $T_N$ .

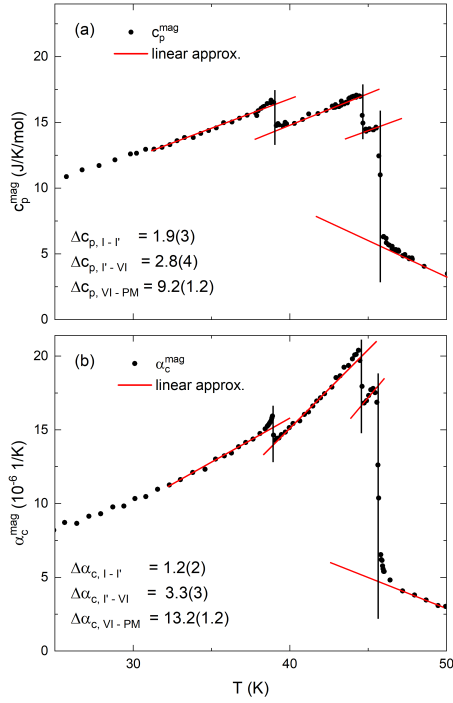


FIG. S4. Determination of the jumps at the zero-field phase transitions of  $\text{GdRu}_2\text{Si}_2$  in the (a) magnetic specific heat  $c_p^{\text{mag}}$  and (b) magnetic contribution to the thermal expansion coefficient  $\alpha_c^{\text{mag}}$ . The red lines are fits to regimes below and above the three phase transition to correct the jumps for the superimposed fluctuations at the respective phase transition.

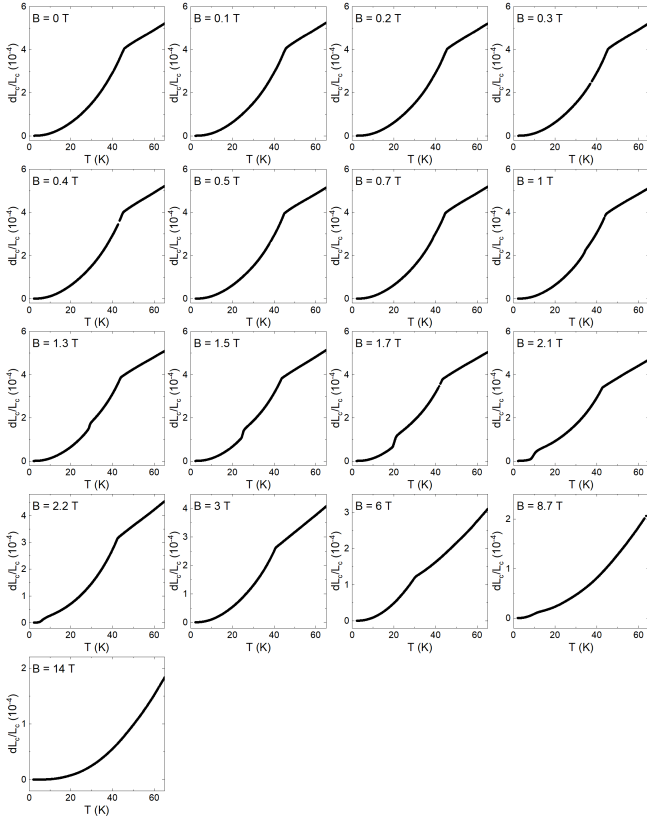


FIG. S5. Thermal expansion  $dL_c/L_c$  at various fields up to  $B \parallel c = 14$  T as a function of temperature  $T$ .



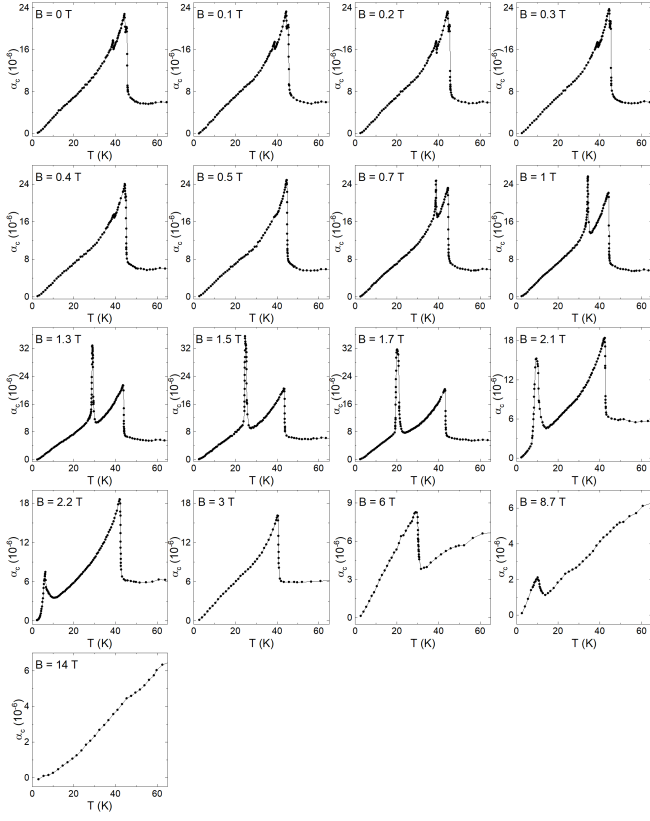


FIG. S6. Thermal expansion coefficient  $\alpha_c$  at various fields up to  $B \parallel c = 14$  T as a function of temperature  $T$ .

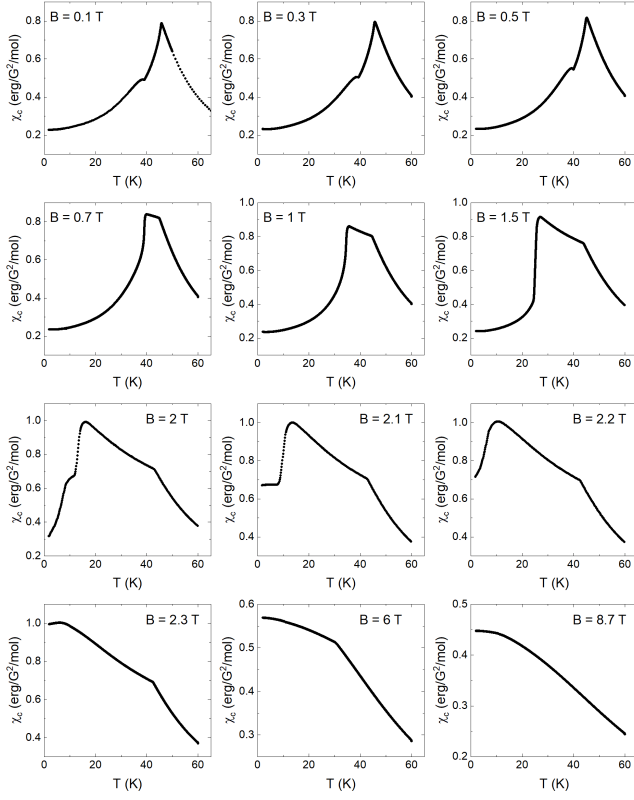


FIG. S7. Static magnetic susceptibility  $\chi_c$  at various fields up to  $B \parallel c = 8.7 \text{ T}$  as a function of temperature  $T$ .

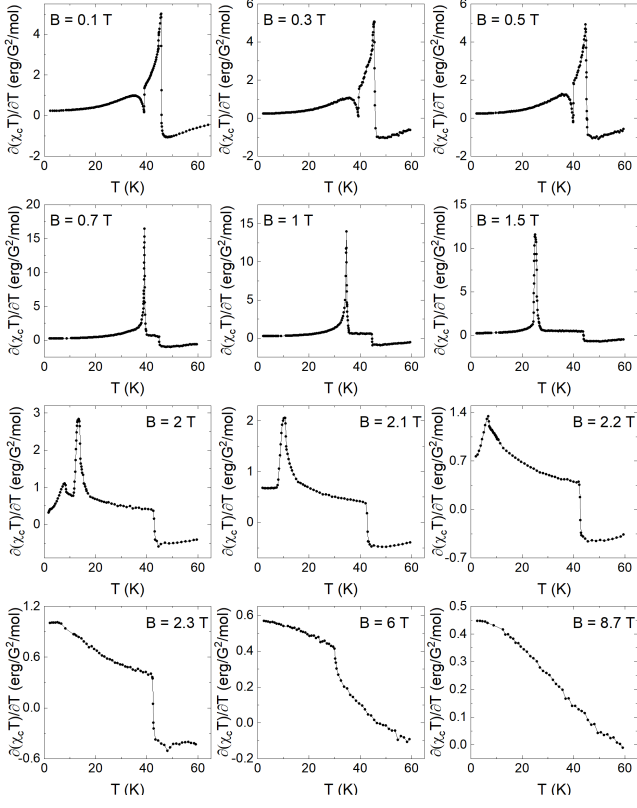


FIG. S8. Fisher's specific heat  $\partial(\chi_c T)/\partial T$  at various fields up to  $B \parallel c = 8.7$  T as a function of temperature  $T$ .

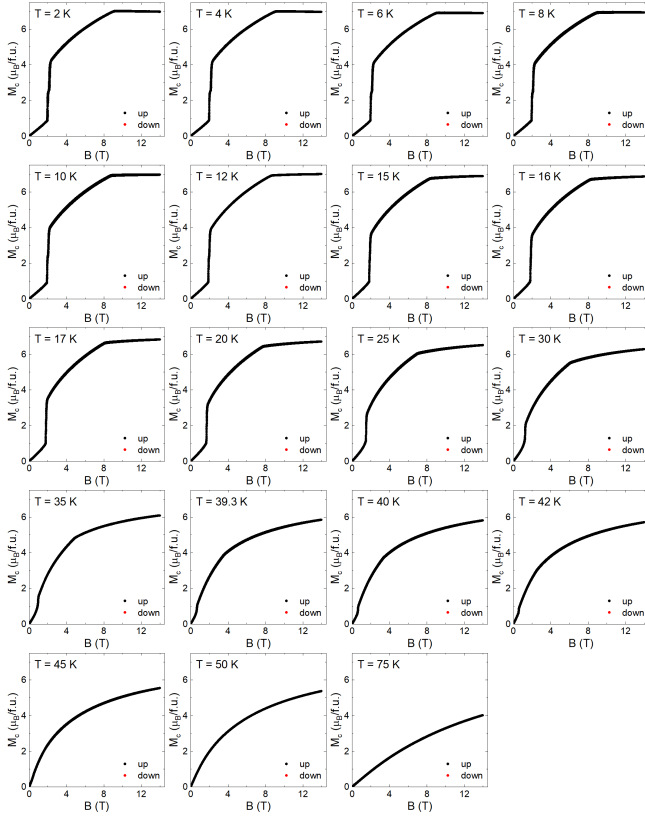


FIG. S9. Isothermal magnetisation  $M_c$  at various temperatures between  $T = 2$  K and  $T = 75$  K as a function of the magnetic field  $B \parallel c$ .

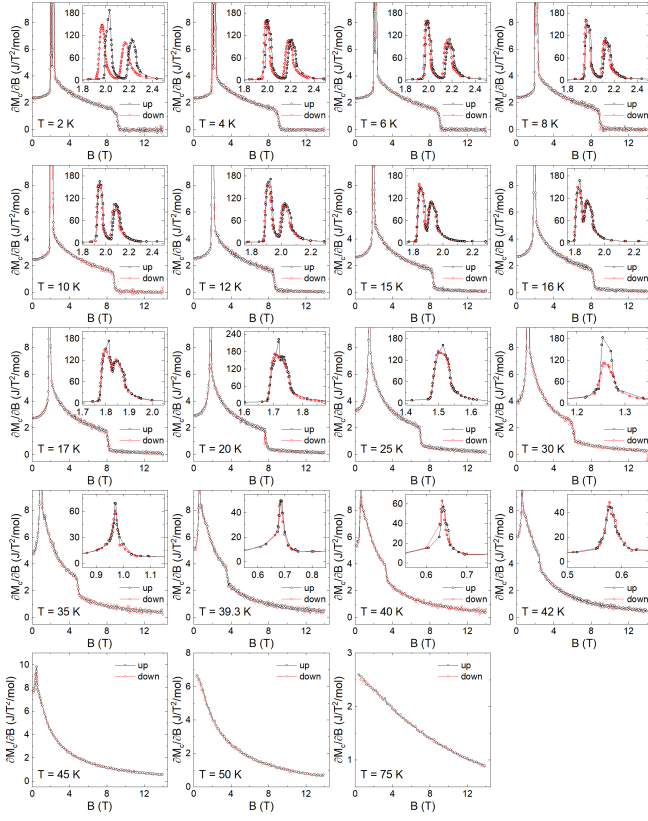


FIG. S10. Magnetic susceptibility  $\partial M_c/\partial B$  at various temperatures between  $T = 2$  K and  $T = 75$  K as a function of the magnetic field  $B \parallel c$ . The insets show the region around the low field transitions in more detail.

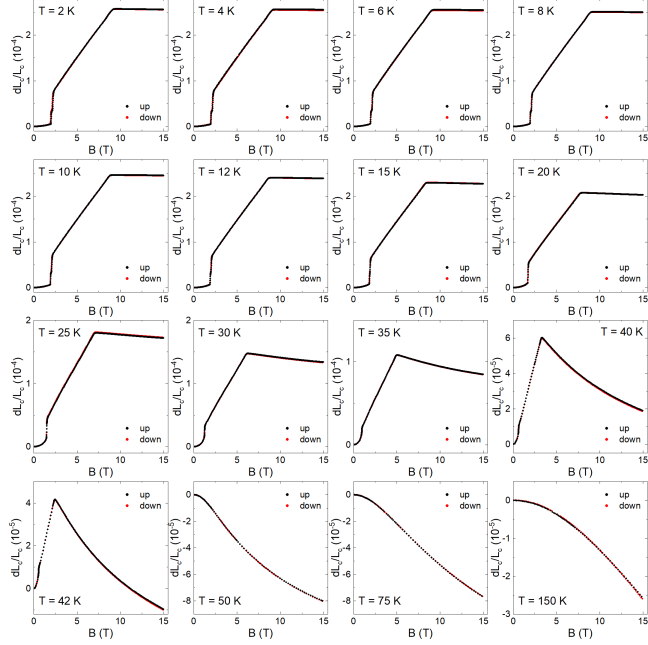


FIG. S11. Magnetostriction  $dL_c(B)/L_c$  at various temperatures between  $T = 2$  K and  $T = 150$  K as a function of the magnetic field  $B \parallel c$ .

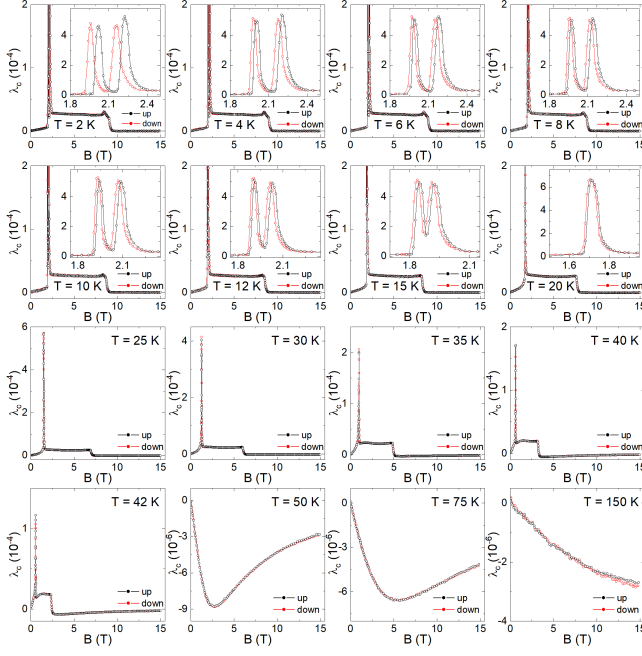


FIG. S12. Magnetostriction coefficient  $\lambda_c$  at various temperatures between  $T = 2$  K and  $T = 75$  K as a function of the magnetic field  $B \parallel c$ . The insets show the region around the low field transitions in more detail.

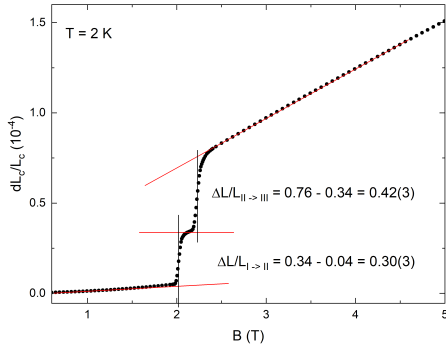


FIG. S13. Determination of the jumps in magnetostriction  $\Delta L_c/L_c$  vs. magnetic field  $B$  at the phase transitions into the SKL phase (I - II) and out of the SKL phase (II - III) at  $T = 2$  K. In order to correctly extract the jump at the respective phase transition intervals below and above the phase transitions are approximated by a linear fit (red lines) and extrapolated to the critical field.