

Cu Nuclear Quadrupole Resonance Study of the Spin-Peierls Compound $\text{Cu}_{1-x}\text{Mg}_x\text{GeO}_3$: A Possibility of Precursory Dimerization

Y. Itoh^{1,2}, T. Machi¹, N. Koshizuka¹, T. Masuda³, and K. Uchinokura³

¹*Superconductivity Research Laboratory, International Superconductivity Technology Center, 1-10-13 Shinonome, Koto-ku Tokyo 135-0062, Japan*

²*Japan Science and Technology Corporation, Japan*

³*Department of Advanced Materials Science, The University of Tokyo, 7-3-1 Hongo, Bunkyo-ku, Tokyo 113-8656, Japan*

We report on a zero-field ^{63}Cu nuclear quadrupole resonance (NQR) study of nonmagnetic Mg impurity substituted $\text{Cu}_{1-x}\text{Mg}_x\text{GeO}_3$ (single crystals; the spin-Peierls transition temperature $T_{sp} \sim 14, 13.5,$ and 11 K for $x=0, 0.0043,$ and 0.020) in a temperature range from 4.2 K to 250 K. We found that below $T^* \sim 77$ K, Cu NQR spectra are broadened and nonexponential Cu nuclear spin-lattice relaxation increases for undoped and more remarkably for Mg-doped samples. The results indicate that random lattice distortion and impurity-induced spins appear below T^* , which we associate with a precursor of the spin-Peierls transition. Conventional magnetic critical slowing down does not appear down to 4.2 K below T_{sp} .

75.50.Ee, 75.40.Gb, 76.60.-k

The discovery of the first inorganic spin-Peierls compound CuGeO_3 (the transition temperature $T_{sp} \sim 14$ K) [1] and subsequent reports on unprecedented impurity effects [2–7] have renewed the interests of a quasi-one-dimensional spin $S=1/2$ Heisenberg antiferromagnet coupled to phonons. No soft mode of phonon at T_{sp} is one of the characteristics of CuGeO_3 . An appreciable inter-chain exchange interaction [8], lattice and phonon anomaly perpendicular to the chain [9,10] are different from an ordinary spin-Peierls system or conventional theoretical result [11]. A pseudogap in the magnetic excitation spectrum below 20 K observed by inelastic neutron scattering [12] and a local dimerization until at least 40 K observed by diffusive X-ray scattering [13] resemble a pseudogap of the electronic Peierls materials [14]. In contrast to conventional competition between Néel ordering and lattice dimerization, the impurity substitution (Zn, Mg, Ni, or Si) for Cu or Ge induces a dimerized antiferromagnetic ordering state [3–6], where a spin-wave mode coexists in the spin-Peierls gap [7]. The coexistence at $T=0$ K is understood within the framework of the phase Hamiltonian [15].

Nuclear quadrupole resonance (NQR) and nuclear magnetic resonance (NMR) are unique and powerful techniques to study low frequency dynamics and local spin fluctuations in space. The intensive studies using Cu NQR and NMR techniques have revealed many aspects of CuGeO_3 [16–19]. The spin gap opening at T_{sp} was evidenced by an abrupt decrease of the Cu nuclear spin-lattice relaxation rate $1/T_1$ without any appreciable change of Cu NQR spectrum [16], although a singlet-triplet excitation, a spin gap and ion displacement were directly confirmed by neutron scattering [20,21]. The above T_{sp} spin dynamics, the Cu $1/T_1$, is understood by a quasi-one-dimensional $S=1/2$ antiferromagnetic correlation without spin-phonon coupling [16,22,23]. To our

knowledge, however, there are no reports of Cu NQR spectrum far above T_{sp} for CuGeO_3 nor of impurity effects on the low frequency spin dynamics, after the work on Zn doping [24].

In this Letter, we report the high temperature measurement of Cu NQR spectrum for undoped CuGeO_3 and the Cu NQR study of nonmagnetic Mg impurity substitution effect on $\text{Cu}_{1-x}\text{Mg}_x\text{GeO}_3$ (single crystals; $T_{sp} \sim 14, 13.5,$ and 11 K for $x=0, 0.0043,$ and 0.020) in a wide temperature range of $T=4.2-250$ K. We found that the broadening of Cu NQR spectra and the increase of nonexponential Cu nuclear spin-lattice relaxation occur below about 77 K much higher than T_{sp} , which suggest a precursor of the spin-Peierls transition. We did not observe critical divergence of $1/T_1$ for $x=0.020$ down to 4.2 K, although the magnetic ordering occurs at about 2.5 K [4].

The single crystals grown by a floating-zone method are well characterized in Ref. [4]. Zero-field ^{63}Cu NQR spin-echo measurements were carried out with a coherent-type pulsed spectrometer. NQR frequency spectra with quadrature detection were measured by integration of the ^{63}Cu nuclear spin-echoes as the frequency was changed point by point. Nuclear spin-lattice relaxation was measured by an inversion recovery spin-echo technique, where the ^{63}Cu nuclear spin-echo amplitude $M(t)$ was recorded as a function of time interval t , between an inversion π -pulse and a $\pi/2$ -pulse ($\pi - t - \pi/2 - \pi$ -echo).

Figure 1 shows ^{63}Cu NQR spectra for undoped $x=0$ (a) and for Mg doping of $x=0.020$ (b) in the temperature range of $T=4.2-250$ K. The observed Cu NQR spectra for Mg doping are nearly symmetrically broadened, not of Gaussian nor of Lorentzian type but rather have a triangle-shaped line profile for $x=0.020$ at 4.2 K. Implication of the characteristic line shape is not

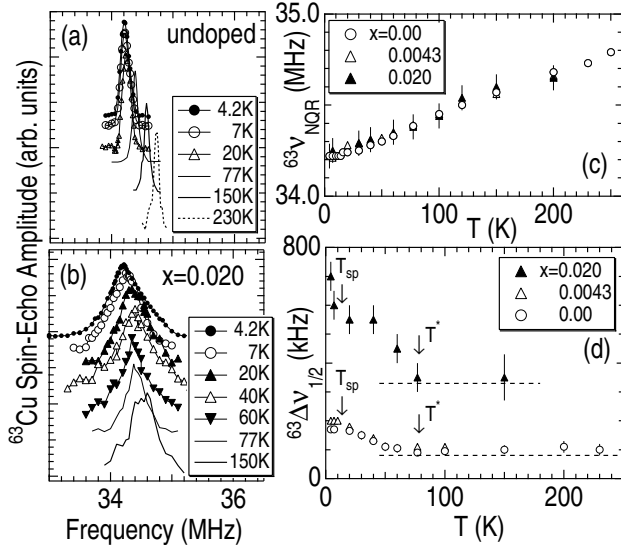


FIG. 1. The temperature dependence of ^{63}Cu NQR frequency spectrum for $x=0$ (a) and for $x=0.020$ (b). The temperature dependence of the peak frequency $^{63}\nu$ (c) and of the linewidth (full-width at half maximum) $^{63}\Delta\nu_{1/2}$ (d) for $x=0$, 0.0043, and 0.020. The dashed lines in (d) are guides to the eye.

clear. In general, the Cu NQR frequency ν is given by $\nu = (e^2qQ/2h)\sqrt{1 + \eta^2/3}$, where eq is the maximum component of the electric field gradient tensor at the nuclear site, Q is the nuclear quadrupole moment, and η ($0 \leq \eta \leq 1$) is an asymmetry factor [25]. The muon spin relaxation measurements have not detected any static internal magnetic field for Zn-doped samples above about 4 K [6]. Thus, it is likely that the random distribution of the electric field gradient (eq and η) is the origin of broadening.

Figure 1(c) shows the temperature dependence of the peak frequency $^{63}\nu$ for $x=0$, 0.0043, and 0.020. The observed linear temperature dependence of $^{63}\nu$, nearly independent of Mg content, is similar to that of the cuprate mono-oxide CuO [26]. Figure 1(d) shows the temperature dependence of the linewidth defined as full-width at half maximum $^{63}\Delta\nu_{1/2}$. The linewidth as well as the peak frequency does not show any appreciable change at T_{sp} , in agreement with the previous reports on CuGeO_3 [16,22,27]. The linewidth of the $x=0.020$ sample is about 3 times larger than that of $x=0$ at $T > T^*$. In Fig. 1(d), we obtain a significant result that $^{63}\Delta\nu_{1/2}$ increases rapidly below about 77 K $\gg T_{sp}$ (denoted as T^*) for all samples including CuGeO_3 . For each x , $^{63}\Delta\nu_{1/2}$ at 4.2 K is about 2 times larger than that above T^* .

NQR is a measure of deviation of charge distribution from cubic symmetry around the nuclear site, being quite sensitive to crystal imperfections. The observed nearly symmetric line shape implies a random distribution of local charge [25]. If the origin of $^{63}\Delta\nu_{1/2}$ is a static distri-

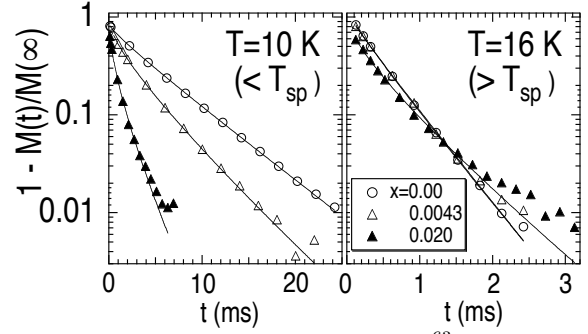


FIG. 2. Mg-doping dependence of ^{63}Cu recovery curves $1 - M(t)/M(\infty)$ at 10 K (a) and at 16 K (b) for $x=0$, 0.0043, and 0.020. The solid curves are the least-squares fitting results using eq. (1).

bution of lattice distortion around crystal imperfection, $^{63}\Delta\nu_{1/2}$ would decrease as the temperature is decreased so as to scale with the temperature dependence of $^{63}\nu$. However, the actual $^{63}\Delta\nu_{1/2}$ increases below T^* . Thus, the inhomogeneity of lattice distortion must depend on temperature and must increase rapidly below T^* . The pretransitional lattice fluctuations above T_{sp} observed by the diffraction experiment [13], which are explained by the random-phase approximation calculation [28], may be closely related with the increase of $^{63}\Delta\nu_{1/2}$. According to the recent quantum Monte Carlo simulation [29], a precursory dimerization takes place near the edges far above T_{sp} . T^* corresponds to the onset of preformed dimer bonds. In the soliton picture [30], T_{sp} is an order-to-disorder transition temperature of locally dimerized segments. T^* may correspond to the onset of development of the interchain correlation between the soliton and antisoliton.

Figure 2 shows Mg-doping effect on ^{63}Cu recovery curve $p(t) \equiv 1 - M(t)/M(\infty)$ of the ^{63}Cu nuclear magnetization $M(t)$ at 10 K ($< T_{sp}$) (a) and at 16 K ($> T_{sp}$) (b). The recovery curve changes from a single exponential function to nonexponential one as Mg is substituted and as the temperature is decreased. To account for the nonexponential function, we assume a minimal model, which consists of a host homogeneous relaxation process and of a single inhomogeneous relaxation one. The solid curves are the least-squares fitting results using the following equation [31],

$$p(t) = p(0)\exp[-(t/T_1)_{NQR} - \sqrt{t/\tau_1}]. \quad (1)$$

The fit parameters are $p(0)$, $(T_1)_{NQR}$ [32] and τ_1 . $p(0)$ is a fraction of an initially inverted magnetization, and $(T_1)_{NQR}$ is the nuclear spin-lattice relaxation time due to the host Cu spin fluctuations. τ_1 is an impurity-induced nuclear spin-lattice relaxation time, which is originally termed a longitudinal direct dipole relaxation time, because the second term of eq. (1) is derived from a random T_1 process of $1/T_1(r) = C/r^6$ (C is a constant, and r is a distance between an impurity-induced spin S and a Cu nuclear spin I) through a direct dipole coupling

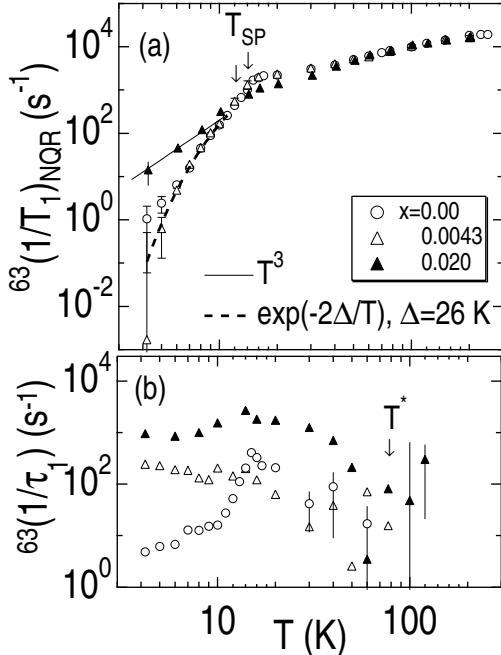


FIG. 3. Log-log plots of ${}^{63}(1/T_1)_{NQR}$ (a) and ${}^{63}(1/\tau_1)$ (b) as functions of temperature for undoped $x=0$ and for Mg-doped samples of $x=0.0043$ and 0.020 . In (a), the solid line is a T^3 function, and the dashed curve is the least-squares fitting result using a function of $1/T_1 = R_1 \exp(-2\Delta/T)$.

$\propto I_{\pm} S_z / r^3$ (S_z is the z -component of S , and I_{\pm} is a raising or lowering operator of I). The randomly distributed impurity-induced spins yield the stretched exponential function of eq. (1). The original Mg ion does not carry spin $1/2$. Atomic defects or Mg ions cut chains into segments. The existence of spatially extended staggered moment induced by an edge or an impurity has been pointed out for a finite or a semi-infinite chain [29,30,33]. The assumption of impurity-induced spins could be only a working hypothesis to introduce τ_1 . Since the essence of the stretched exponential function is randomness in the T_1 process, one may speculate that $T_1(r)$ with a local spin density induced by Mg is approximated by a power law, leading to the stretched exponential function. In the soliton picture [30], the soliton which stays in the middle of a segment or near the edges due to an interchain coupling, carries spin $1/2$, so that it can act as an impurity spin.

Figure 3 shows log-log plots of ${}^{63}(1/T_1)_{NQR}$ (a) and ${}^{63}(1/\tau_1)$ (b) as functions of temperature for $x=0$, 0.0043 and 0.020 . Far above T^* , ${}^{63}(1/T_1)_{NQR}$ for Mg-doped samples is nearly the same as that for an undoped one. For undoped and $x=0.0043$, the activation-type temperature dependence of ${}^{63}(1/T_1)_{NQR}$ is observed below T_{sp} . The spin gap Δ is estimated to be ~ 26 K by fits of $1/T_1 = R_1 \exp(-2\Delta/T)$ (R_1 and Δ are fitting parameters) [34], which agrees with the value estimated from

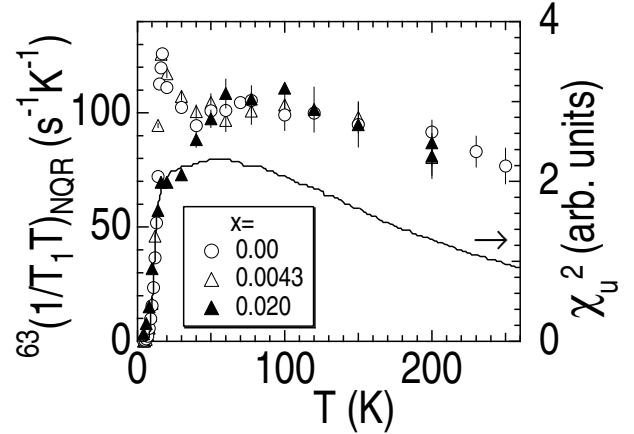


FIG. 4. The temperature and Mg-doping dependence of ${}^{63}(1/T_1 T)_{NQR}$. The solid curve is the squared static uniform susceptibility χ_u^2 of undoped CuGeO_3 reproduced from Ref. [1].

the static susceptibility [1]. For $x=0.020$, however, the temperature dependence of ${}^{63}(1/T_1)_{NQR}$ is changed into a power-law type ($\sim T^3$), probably because of an inhomogeneous distribution of $\Delta(r)$. Conventional critical divergence toward the magnetic ordering does not appear.

Below around T^* , ${}^{63}(1/\tau_1)$ immediately increases as the temperature is decreased down to T_{sp} even for $x=0$, which indicates the increase of the impurity-induced spin correlation. Far below T_{sp} , ${}^{63}(1/\tau_1)$ is systematically enhanced by Mg doping, which is due to an increase of the number of impurity relaxation centers. It is likely that the origin of ${}^{63}(1/\tau_1)$ for $x=0$ is due to non-intentionally introduced imperfections (defects, dislocations, ...). The actual sample is not a perfect crystal, because the observed linewidths of ${}^{63}\text{Cu}$ NQR spectra of our $x=0$ (~ 180 kHz at 4.2 K, ~ 100 kHz above 100 K) are broader than those expected from T_1 or T_2 broadening (a few kHz), i.e. inhomogeneous broadening. The estimated ${}^{63}\Delta\nu_{1/2}$ for $x=0$ is nearly the same as or somewhat sharper than the reported values below 40 K [16, 17, 22, 27]. In Fig. 3(b), ${}^{63}\tau_1$ for each x makes a kink at around T_{sp} . In terms of an impurity spin picture, ${}^{63}(1/\tau_1)$ is nearly proportional to the life time of the impurity spin scattered by the host magnetic excitations. Then, the kink of ${}^{63}(1/\tau_1)$ reflects a change in the host magnetic excitation spectrum at the true transition temperature T_{sp} , which is evident in ${}^{63}(1/T_1)_{NQR}$.

Figure 4 shows the Mg-doping effect on ${}^{63}(1/T_1 T)_{NQR}$. For comparison, the squared static susceptibility χ_u^2 of undoped CuGeO_3 (solid curve) is also reproduced from Ref. [1]. In general, $1/T_1 T$ is the low frequency dynamical spin susceptibility at an NQR frequency summed over a momentum space via a nuclear-electron coupling [35]. For $x=0$ above T_{sp} , ${}^{63}(1/T_1 T)_{NQR}$ is understood by the sum of the staggered spin susceptibility $\chi(q =$

$\pi) \sim 1/T$ and the Bonner-Fisher-type uniform spin susceptibility χ_u (to be exact, χ_u^2) [22,23]. The upturn of $^{63}(1/T_1T)_{NQR}$ just above T_{sp} , which is ascribed to the staggered $\chi(q = \pi) \sim 1/T$, is suppressed by Mg doping of $x=0.020$. Then, the contribution from the uniform mode $q=0$ is uncovered, being similar to the temperature dependence of χ_u^2 . The $q = \pi$ mode is easily affected by imperfection, comparatively more than the $q=0$ mode, as can be seen for $\text{La}_2\text{Cu}_{1-x}\text{Zn}_x\text{O}_4$ [36]. However, one should note that $^{63}(1/T_1T)_{NQR}$ for $x=0.020$ and χ_u^2 for $x=0$ above T_{sp} are similar but do not completely agree with each other. The suppression of $^{63}(1/T_1T)_{NQR}$ for $x=0.020$ begins from below 60-120 K more steeply than that of χ_u^2 below about 50 K. Thus, the further mechanism of the suppression is needed. The precursory dimerization enhanced by Mg below around T^* is a possible candidate. Our observations of the suppressed $\chi(q = \pi)$ and of the deviation between $^{63}(1/T_1T)_{NQR}$ and χ_u^2 for Mg doped samples will be constraints on dynamical theory toward the low temperature dimerized antiferromagnetic transition.

To conclude, below $T^* \sim 77$ K, the inhomogeneous broadening of Cu NQR spectra and the impurity-induced Cu nuclear spin-lattice relaxation occur for undoped and more remarkably for Mg-doped CuGeO_3 . Precursory dimerization, inhomogeneous in real space, is suggested. The host antiferromagnetic correlation above T_{sp} is suppressed by Mg doping of $x=0.020$. No magnetic critical divergence down to 4.2 K is a puzzle.

We thank Dr. J. Kikuchi, and Prof. M. Ogata for stimulating discussions. This work was supported by New Energy and Industrial Technology Development Organization (NEDO) as Collaborative Research and Development of Fundamental Technologies for Superconductivity Applications.

-
- [1] M. Hase, I. Terasaki, and K. Uchinokura, Phys. Rev. Lett. **70**, 3651 (1993).
- [2] M. Hase *et al.*, Phys. Rev. Lett. **71**, 4059 (1993); Physica B **215**, 164 (1995); S. B. Oseroff *et al.*, Phys. Rev. Lett. **74**, 1450 (1995).
- [3] L. P. Regnault *et al.*, Europhys. Lett. **32**, 579 (1995).
- [4] T. Masuda *et al.*, Phys. Rev. Lett. **80**, 4566 (1998); Phys. Rev. B **61**, 4103 (2000); Y. J. Wang *et al.*, Phys. Rev. Lett. **83**, 1676 (1999); H. Nakano *et al.*, J. Phys. Soc. Jpn. **68**, 3662 (1999).
- [5] N. Koide *et al.*, Czech. J. Phys. **46**, 1981 (1996); S. Coad, J-G. Lussier, and D. F. McK. Paul, J. Phys. Matter **8**, 6251 (1996).
- [6] K. M. Kojima *et al.*, Phys. Rev. Lett. **79**, 503 (1997).
- [7] M. C. Martin *et al.*, Phys. Rev. B **56**, 3173 (1997).
- [8] M. Nishi, O. Fujita, and J. Akimitsu, Phys. Rev. B **50**, 6508 (1994).
- [9] M. Braden *et al.*, Phys. Rev. Lett. **80**, 3634 (1998); *ibid.* **83**, 1858 (1999).
- [10] J. E. Lorenzo *et al.*, Phys. Rev. B **50**, 1278 (1994).
- [11] M. C. Cross, and D. S. Fisher, Phys. Rev. B **19**, 402 (1979).
- [12] L. P. Regnault *et al.*, Phys. Rev. B **53**, 5579 (1996).
- [13] J. P. Pouget *et al.*, Phys. Rev. Lett. **72**, 4037 (1994); J. P. Schoeffel *et al.*, Phys. Rev. B **53**, 14971 (1996).
- [14] P. A. Lee, T. M. Rice, and P. W. Anderson, Phys. Rev. Lett. **31**, 462 (1973).
- [15] H. Fukuyama, T. Tanimoto, and M. Saito, J. Phys. Soc. Jpn. **65**, 1182 (1996); M. Saito and H. Fukuyama, *ibid.* **66**, 3259 (1997).
- [16] J. Kikuchi *et al.*, J. Phys. Soc. Jpn. **63**, 872 (1994).
- [17] M. Itoh *et al.*, Phys. Rev. B **54**, R9631 (1996); *ibid.* **53**, 11606 (1996); Physica C **263**, 486 (1996).
- [18] Y. Fagot-Revurat *et al.*, Phys. Rev. Lett. **77**, 1861 (1996); M. Horvatic *et al.*, *ibid.* **83**, 420 (1999).
- [19] Y. Fagot-Revurat *et al.*, Phys. Rev. B **55**, 2964 (1997).
- [20] O. Fujita *et al.*, Phys. Rev. Lett. **74**, 1677 (1995); M. Arai *et al.*, Phys. Rev. Lett. **77**, 3649 (1996).
- [21] K. Hirota *et al.*, Phys. Rev. Lett. **73**, 736 (1994).
- [22] M. Itoh, S. Hirashima, and K. Motoya, Phys. Rev. B **52**, 3410 (1995).
- [23] A. Yu. Zavidonov, I. A. Larionov, and M. Itoh, Phys. Rev. B **61**, 11625 (2000).
- [24] M. Itoh *et al.*, Physica B **281&282**, 671 (2000).
- [25] M. H. Cohen and F. Reif, Solid State Phys. **5**, 321 (1964).
- [26] Y. Itoh *et al.*, J. Phys. Soc. Jpn. **59**, 1143 (1990).
- [27] A. A. Gippius *et al.*, J. Phys. Condens. Matter **12**, L71 (2000). In contrast to this report, we did not observe any split of the Cu NQR spectrum with quadrature detection for undoped CuGeO_3 , being in agreement with the other reports [16, 17, 22].
- [28] C. Gros and R. Werner, Phys. Rev. B **58**, R14677 (1998); M. Holicki, H. Fehske, and R. Werner, Phys. Rev. B **63**, 174417 (2001).
- [29] H. Onishi and S. Miyashita, J. Phys. Soc. Jpn. **69**, 2634 (2000).
- [30] D. Khomskii, W. Geertsma, and M. Mostovoy, Czech. J. Phys. **46**, 3239 (1996); M. Mostovoy, and D. Khomskii, Z. Phys. B **103**, 209 (1997).
- [31] M. R. McHenry, B. G. Silbernagel, and J. H. Wernick, Phys. Rev. Lett. **27**, 426 (1971); Phys. Rev. B **5**, 2958 (1972).
- [32] In Refs. [16, 17, 22], $1/T_1$ is estimated by $p(t) = p(0)\exp(-3t/T_1)$. But, under an asymmetric electric field gradient (an asymmetry factor $\eta \sim 0.16$ [16, 17]), all the x -, y -, and z -components of the local field fluctuations contribute to zero-field Cu $(T_1)_{NQR}$. Then, a numerical factor 3 is not needed.
- [33] S. Eggert and I. Affleck, Phys. Rev. Lett. **75**, 934 (1995); M. Takigawa *et al.*, Phys. Rev. B **55**, 14129 (1997).
- [34] E. Ehrenfreund and L. S. Smith, Phys. Rev. B **16**, 1870 (1977).
- [35] T. Moriya, J. Phys. Soc. Jpn. **18**, 516 (1963); Prog. Theor. Phys. **16**, 641 (1956).
- [36] K. Uchinokura *et al.*, Physica B **205**, 234 (1995); P. Carretta, A. Rigamonti, and R. Sala, Phys. Rev. B **55**, 3734 (1997).