

# Two energy scales and slow crossover in $\text{YbAl}_3$

J. M. Lawrence,<sup>1,\*</sup> T. Ebihara,<sup>2</sup> P. S. Riseborough,<sup>3</sup> C. H. Booth,<sup>4</sup> M. F. Hundley,<sup>5</sup> P. G. Pagliuso,<sup>5</sup> J. L. Sarrao,<sup>5</sup> J. D. Thompson,<sup>5</sup> M. H. Jung,<sup>6</sup> A. H. Lacerda,<sup>6</sup> and G. H. Kwei<sup>7</sup>

<sup>1</sup>*University of California, Irvine, CA 92697*

<sup>2</sup>*Shizuoka University, Shizuoka 422-8529, Japan*

<sup>3</sup>*Temple University, Philadelphia, PA 19122*

<sup>4</sup>*Lawrence Berkeley National Laboratory, Berkeley, CA 94720*

<sup>5</sup>*Los Alamos National Laboratory, Los Alamos, NM 87545*

<sup>6</sup>*National High Magnetic Field Laboratory,*

*Los Alamos National Laboratory, Los Alamos NM 87545*

<sup>7</sup>*Lawrence Livermore National Laboratory, Livermore CA 94551*

(Dated: November 21, 2018)

## Abstract

Experimental results for the susceptibility, specific heat, 4f occupation number, Hall effect and magnetoresistance for single crystals of  $\text{YbAl}_3$  show that, in addition to the Kondo energy scale  $k_B T_K \sim 670\text{K}$ , there is a low temperature scale  $T_{coh} < 50\text{K}$  for the onset of coherence. Furthermore the crossover from the low temperature Fermi liquid regime to the high temperature local moment regime is slower than predicted by the Anderson impurity model. These effects may reflect the behavior of the Anderson Lattice in the limit of low conduction electron density.

PACS numbers: 75.30.Mb 75.20.Hr 71.27.+a 71.28.+d 61.10.Ht

The low temperature transport behavior of periodic intermediate valent (IV) and heavy fermion (HF) compounds[1] is fundamentally different from that expected for the Anderson impurity model (AIM), in that it manifests vanishing resistivity (Bloch's law) and an optical conductivity[2] appropriate for renormalized band behavior. Similarly, the 4f electrons have a coherent effect on the Fermi surface, as seen in de Haas van Alphen (dHvA) measurements[3]. However the temperature dependence of the susceptibility, specific heat and 4f occupation number and the energy dependence of the dynamic susceptibility show behavior that is qualitatively very similar to the predictions of the AIM[4, 5]. Essentially this is because these properties are dominated by spin/valence fluctuations that are highly local and which exhibit a Lorentzian power spectrum[6] consistent with the AIM.

Nevertheless, recent theoretical studies[7, 8] of the Anderson lattice (AL) in the Kondo limit suggest that these latter properties can differ in at least two ways from the predictions of the AIM. First, as the background conduction electron density  $n_c$  decreases, the theory predicts[8] a new low temperature scale  $T_{coh}$  for the onset of Fermi liquid coherence, where  $T_{coh}$  is significantly smaller than the high temperature Kondo scale  $T_K$ . For  $T < T_{coh}$  peaks in addition to those expected on the high temperature scale  $T_K$  are predicted for the susceptibility and specific heat. Second, as  $n_c$  decreases the crossover from low temperature Fermi liquid behavior to high temperature local moment behavior becomes slower (i.e. more gradual) than predicted for the AIM[7].

Recently we have given evidence[5] for a slow crossover of the susceptibility and 4f occupation number in the IV compounds  $\text{YbXCu}_4$  ( $X = \text{Ag, Cd, Mg, Tl, Zn}$ ). In this paper we give evidence *both* for a slow crossover *and* for two energy scales in the IV compound  $\text{YbAl}_3$ . We show that both effects are observed not only for the susceptibility but also for the specific heat. We show that the magnetotransport gives clear evidence for a change in character on the low temperature scale and also suggests that the conduction electron density is low ( $n_c \sim 0.5/atom$ ).

The samples were single crystals of  $\text{YbAl}_3$  and  $\text{LuAl}_3$  grown by the "self-flux" method in excess Al. The quality of such samples, as measured by the resistance ratio ( $R(300\text{K})/R(2\text{K}) \sim 60$ ) is sufficiently high that dHvA signals are well-resolved[9]. The susceptibility was measured using a SQUID magnetometer and the specific heat was measured via a relaxation technique. The Hall coefficient was measured in a magnetic field of 1T using an a.c. resistance bridge. The magnetoresistance was measured at the Los Alamos Pulsed

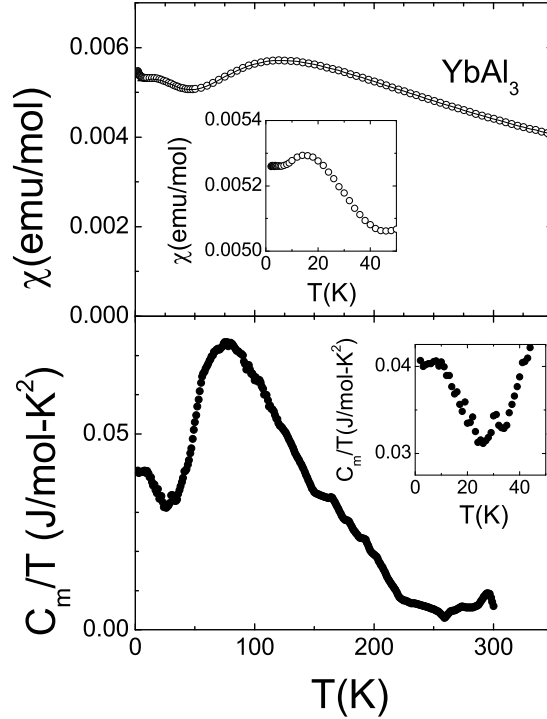


FIG. 1: (a) The magnetic susceptibility  $\chi(T)$  and (b) the magnetic contribution to the specific heat coefficient  $C_m/T$  for  $\text{YbAl}_3$ . The insets exhibit the low temperature behavior; a small Curie tail has been subtracted from the data in the inset for  $\chi(T)$ .

Field Facility of the National High Magnetic Field Laboratory using a 20T superconducting magnet and an a.c. bridge. The  $4f$  occupation number  $n_f(T)$  was determined from the Yb  $L_3$  x-ray absorption near-edge structure, measured at the Stanford Synchrotron Radiation Laboratory (SSRL) on beam line 4-3; the technique for extracting  $n_f$  from the data and other experimental details were similar to those discussed earlier [10]. We note here that the Lu  $L_3$  near-edge structure measured for  $\text{LuAl}_3$  was used as a standard.

In Fig. 1 we plot the susceptibility  $\chi(T)$  and the linear coefficient of the  $4f$  specific heat, where  $\gamma_m = C_m/T$  and  $C_m = C(\text{YbAl}_3) - C(\text{LuAl}_3)$ . (For  $\text{LuAl}_3$  at low temperatures,  $C = \gamma T + \beta T^2$  with  $\gamma = 4\text{mJ/mol-K}^2$  and  $\beta = 1.15 \times 10^{-4}\text{J/mol-K}^4$ , which implies a Debye temperature  $\Theta_D = 257\text{K}$ .) The broad peaks near 100K are typical of Yb IV compounds with  $T_K \sim 500\text{K}$ . In addition, there is a peak at 15K in the susceptibility (first reported by Heiss *et al.*[11]) and the specific heat coefficient displays an upturn below 25K which

saturates at  $T = 0$ . These additional features are the basic evidence for the existence of a low temperature scale,  $T_{coh} \lesssim 50\text{K}$  below which there is a significant change in the behavior of the compound.

Evidence for this change of character can also be seen in the magnetotransport (Fig. 2). The Hall coefficient of  $\text{LuAl}_3$  is typical of a metal, being constant and of a magnitude that in a one-band model implies a carrier density  $n_c = 1/eR_H = 2e^-/f.u.$ . The high temperature Hall coefficient of  $\text{YbAl}_3$  varies with temperature in a manner suggestive of scattering from Yb moments (although the data cannot be fit well with the standard skew scattering formula[12]). Near 50K the derivative  $dR_H/dT$  of the Hall coefficient changes sign. Similar anomalies in the low temperature Hall coefficient have been observed in a number of Ce compounds and have been attributed to the onset of coherence[12]. The magnetoresistance (Fig. 2b, inset) follows a  $B^2$  law above 50K and the magnitude is approximately the same for field parallel and transverse to the current. Below 50K, the magnetoresistance becomes more nearly linear and the transverse magnetoresistance becomes substantially larger ( $\Delta R/R \sim 0.75$ ) than the parallel magnetoresistance ( $\Delta R/R \sim 0.35$ ) at 2K. In Fig. 2b we plot  $\Delta R/R$  versus  $Br_0$  where  $r_0 = R(150\text{K})/R(T)$ ; this tests Kohler's rule, i.e. that at any temperature  $\Delta R/R = A f(Br_0)$  depends only on the product  $Br_0$ . The data violate this rule essentially because  $A$  varies with  $T$ , increasing by a factor of almost 1.5 between 40 and 80K; this crossover is seen most clearly in the data measured as a function of temperature at a fixed field 17.5T. These magnetotransport anomalies suggest that the anomalies in  $\chi$  and  $C/T$  may be associated with an alteration of the Fermi surface. The fact that the resistivity follows a  $T^2$  law below 30K[9] suggests that the anomalies are also connected with the full establishment of Fermi liquid coherence.

To demonstrate that the crossover from Fermi liquid behavior to local moment behavior is slower than predicted by the AIM we compare the experimental data to the AIM result that follows from the measured ground state values of the susceptibility and  $4f$  occupation number[5, 7]. For fixed spin-orbit splitting ( $\Delta_{so} = 1.3\text{eV}$ ), the theoretical results calculated in the non-crossing approximation (NCA) depend on three parameters: the  $f$ -level position  $E_f$ , the hybridization  $V$  between the  $4f$  and the conduction electrons, and the width  $W$  of the conduction band, assumed Gaussian  $N(E) = e^{-E^2/W^2}/\sqrt{\pi}W$ . Since only states within  $k_B T_K$  of the Fermi energy contribute significantly to the results, we argue that use of a Gaussian bandshape is acceptable as long as the density of states at the Fermi energy

is chosen appropriately. We choose  $W$  to give the same specific heat coefficient that we observe in  $\text{LuAl}_3$  ( $\gamma = 4\text{mJ/mol-K}^2$ ). Once  $W$  is fixed, the values of  $E_f$  and  $V$  that yield the appropriate  $n_f(0)$  and  $\chi(0)$  can be determined uniquely. The values of the parameters are given in Fig.3;  $T_K$  is determined from the formula

$$T_K = \left( \frac{V^2}{\sqrt{\pi}W |E_f|} \right)^{1/8} \left( \frac{W}{\Delta_{so}} \right)^{6/8} W e^{\sqrt{\pi}WE_f/8V^2}$$

which includes the effect of spin orbit splitting but ignores crystal field splitting since for IV compounds  $T_K \gg T_{cf}$ . It is clear from Fig. 3 that the susceptibility,  $4f$  occupation number and  $4f$  entropy  $S_m = \int dT C_m/T$  all *qualitatively* follow the predictions of the AIM. The calculated coefficient of specific heat ( $\gamma = 47.8\text{mJ/mol-K}^2$ ) is within 20% of the measured value ( $\gamma_m = 40.65\text{mJ/mol-K}^2$ ). Indeed the data even are in accord with the prediction that the entropy  $S_m(T)$  approaches the high temperature limit faster than the effective moment  $T\chi/C_J$  which in turn evolves more rapidly than  $n_f(T)$  (see Fig. 3). Nevertheless, it is also clear that the experimental data for these quantities approach the high temperature limit considerably more slowly than predicted by the AIM theory.

Thus we have demonstrated the existence of a new low temperature scale for  $\text{YbAl}_3$  and we have shown that the crossover to local moment behavior is slower than expected based on the Anderson Impurity Model. In the theory of the Anderson lattice, such results are expected[7, 8] as the conduction electron density decreases from the value  $n_c = 1$  appropriate to a half-filled band when  $n_f = 1$ . In our earlier work[5] on  $\text{YbXCu}_4$  we assumed that the background band in the Yb compound is the same as the measured band in the corresponding Lu compound. Using a one-band formula  $n_c = 1/eR_H(\text{LuXCu}_4)$  we found that the slow crossover emerged when the number of electrons per atom (the number per formula unit divided by the number of atoms in the formula unit) decreased below the value unity. Strong deviations occurred already for  $\text{YbMgCu}_4$  where  $n_c \sim 0.5/\text{atom}$ . Using the same approximations for  $\text{YbAl}_3$ , we deduce from the Hall coefficient of  $\text{LuAl}_3$  (Fig. 2a) that  $n_c \sim 0.5/\text{atom}$ . Hence, while the conduction electron density is not low for  $\text{YbAl}_3$ , it is (in this approximation) as low as in other compounds where strong deviations from the AIM are observed.

We believe that such effects are generic to IV compounds. A number of years ago we gave evidence[13] for a small coherence scale in the IV compound  $\text{CePd}_3$  based on a low temperature peak in the susceptibility and the extreme sensitivity of the transport behavior

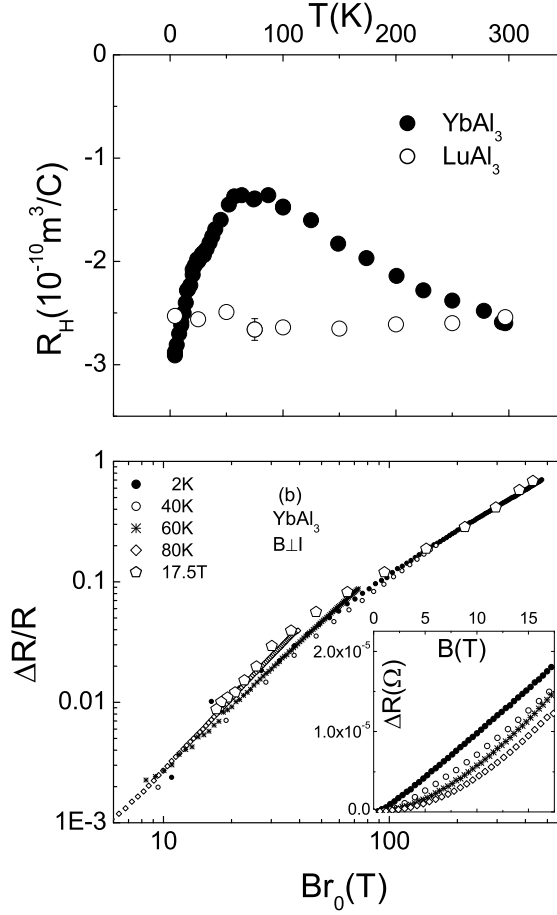


FIG. 2: a) The Hall coefficient of  $\text{YbAl}_3$  (closed circles) and  $\text{LuAl}_3$  (open circles) versus temperature. For  $\text{LuAl}_3$  a typical error bar is shown; for  $\text{YbAl}_3$  the error is smaller than the size of the symbols. b) Inset: The transverse magnetoresistance  $\Delta R/R = R(H, T) - R(0, T)$  versus magnetic field for four temperatures. Main panel: The relative magnetoresistance  $\Delta R/R$  versus  $Br_0$  where  $r_0 = R(150\text{K}/R(T))$ .

to Kondo hole impurities below 50K. A low temperature anomaly in the Hall coefficient also has been observed for this compound[12]. Optical conductivity measurements[2, 14, 15] showed both that the temperature scale for these effects is the same as for the renormalization of the effective mass and the onset of the hybridization gap and that the conduction electron density of  $\text{CePd}_3$  is less than 0.1 carrier/atom. Hence the anomalies appear to be associated both with the onset of the fully renormalized coherent ground state and with low conduction electron density. Measurement of the infrared optical conductivity is clearly a key future

experiment for YbAl<sub>3</sub>.

Neutron scattering measurements on polycrystals of YbAl<sub>3</sub>[16] indicate that in addition to the usual Lorentzian excitation centered at  $E_0 = 40\text{meV}$ , corresponding to the high temperature Kondo scale (for the parameters of Fig. 3 the AIM predicts  $E_0 = 39.6\text{meV}$ ), a new excitation centered at  $30\text{meV}$  arises below  $50\text{K}$ . Preliminary results[17] in single crystals also exhibit this excitation. However, the scattering does not exhibit the expected decrease with increasing  $|\mathbf{Q} = \mathbf{q} + \mathbf{G}|$  (where  $\mathbf{G}$  is a reciprocal lattice vector) for Yb  $4f$  scattering, which should follow the Yb  $4f$  form factor. Indeed the scattering appears to be independent of  $\mathbf{G}$ . Further work needs to address this issue.

The theoretical work on the Anderson lattice which predicts slow crossover and a low temperature coherence scale was motivated by the desire to understand "Nozières' exhaustion". This concept was raised[18] to try to understand how the conduction electrons could screen the  $4f$  spins when the number of conduction electrons  $n_c$  is smaller than the number  $n_f$  of  $4f$ 's in the lattice. The theoretical work to date has all been performed in the Kondo limit. We have examined the extension of the slave boson mean field theory for the Anderson lattice to the case  $n_f < 1$  and  $n_c < 1$  relevant to YbAl<sub>3</sub>, where  $n_f$  is the number of holes in the  $(2J + 1)$  fold degenerate  $f$  level. Following Millis and Lee[19], we define the Kondo temperature  $k_B T_K$  as the energy of the renormalized  $f$  level relative to the Fermi-energy. The coherence scale is defined as the renormalized (quasiparticle)  $T = 0$  bandwidth which for a background conduction band density of states  $\rho$  is given by  $k_B T_{coh} = \rho \tilde{V}^2$  where  $\tilde{V}$  is the renormalized hybridization  $\tilde{V} = \sqrt{1 - n_f} V$ . In the limit  $(\rho \tilde{V})^2 \ll n_c n_f / (2J + 1)^2$  we find that  $T_{coh}/T_K = n_f / (2J + 1)$  independent of  $n_c$ . For YbAl<sub>3</sub> this means that  $T_{coh}$  should be an order of magnitude smaller than  $T_K$ , in qualitative agreement with the data.

In any case we assert that the two energy scales and slow crossover predicted by the theory are features of our data, that these effects show some correlation with a standard measure of the conduction electron density and that they may be generic for IV compounds.

Work at UC Irvine was supported by UCDRD funds provided by the University of California for the conduct of discretionary research by the Los Alamos National Laboratory and by the UC/LANL Personnel Assignment Program. Work at Polytechnic was supported by DOE FG02ER84-45127. Work at Lawrence Berkeley National Laboratory was supported by DOE Contract No. DE-AC03-76SF00098. Work at Los Alamos was performed under the auspices of the DOE. The x-ray absorption experiments were performed at SSRL, which is

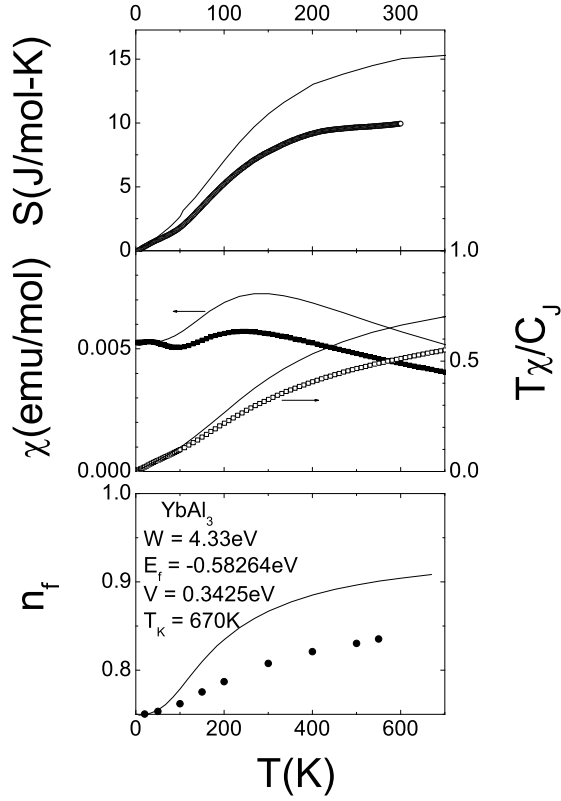


FIG. 3: (a) The  $4f$  entropy  $S_m$ , (b) the susceptibility  $\chi(T)$  (solid symbols) and the effective moment  $T\chi/C_J$  (open symbols) where  $C_J$  is the  $J = 7/2$  Curie constant and (c) the  $4f$  occupation number  $n_f(T)$  for  $\text{YbAl}_3$ . The symbols are the experimental data and the solid lines are the predictions of the Anderson Impurity Model (AIM), with input parameters given in the figure.

operated by the DOE/OBES.

---

\* Electronic address: jmlawrenc@uci.edu

- [1] A. C. Hewson, *The Kondo Problem to Heavy Fermions* (Cambridge University Press, 1993) p. 315.
- [2] B. C. Webb, A. J. Sievers and T. Mihalisin, *Phys. Rev. Lett.* **57**, 1951 (1986).
- [3] A. Hasegawa and H. Yamagami, *Progress of Theoretical Physics Supplement* **108**, 27 (1992).
- [4] N. E. Bickers, D. L. Cox and J. W. Wilkins, *Phys. Rev. B* **36**, 2036 (1987).
- [5] J. M. Lawrence, P. S. Riseborough, C. H. Booth, J. L. Sarrao, J. D. Thompson and R. Osborn,



- Phys. Rev. B **63**, 054427 (2001).
- [6] J. M. Lawrence, S. M. Shapiro, J. L. Sarrao and Z. Fisk, Phys. Rev. B **55**, 14467 (1997); J. M. Lawrence, R. Osborn, J. L. Sarrao and Z. Fisk, Phys. Rev. B **59**, 1134 (1999).
- [7] A. N. Tahvildar-Zadeh, M. Jarrell and J. K. Freericks, Phys. Rev. B **55**, R3332 (1997); Phys. Rev. Lett. **80**, (1998) 5168.
- [8] S. Burdin, A. Georges and D. R. Grempel, Phys. Rev. Lett. **85**, 1048 (2000).
- [9] T. Ebihara, S. Uji, C. Terakura, T. Terashima, E. Yamamoto, Y. Haga, Y. Inada and Y. Onuki, Physica B **281&282**, 754 (2000); T. Ebihara, Y. Inada, M. Murakawa, S. Uji, C. Terakura, T. Terashima, E. Yamamoto, Y. Haga, Y. Onuki and H. Harima, Journ. Phys. Soc. Japan **69**, 895 (2000).
- [10] J. L. Sarrao, C. D. Immer, Z. Fisk, C. H. Booth, E. Figueroa, J. M. Lawrence, R. Modler, A. L. Cornelius, M. F. Hundley, G. H. Kwei, J. D. Thompson and F. Bridges, Phys. Rev. B **59**, 6855 (1999).
- [11] A. Heiss, J. X. Boucherle, F. Givord and P. C. Canfield, Journal of Alloys and Compounds **224**, 33 (1995).
- [12] E. Cattaneo, Z. Physik B **64**, 305 (1986); *ibid*, 317.
- [13] J. M. Lawrence, Y.-Y. Chen and J. D. Thompson, in *Theoretical and Experimental Aspects of Valence Fluctuations and Heavy Fermions*, edited by L. C. Gupta and S. K. Malik (Plenum Press, New York, 1987) p. 169.
- [14] B. Bucher, Z. Schlesinger, D. Mandrus, Z. Fisk, J. Sarrao, J. F. DiTusa, C. Oglesby, G. Aeppli and E. Bucher, Phys. Rev. B **53**, R2948 (1996).
- [15] L. Degiorgi, F. B. B. Anders and G. Grüner, Eur. Phys. J. B **19**, 167 (2001).
- [16] A. P. Murani, Phys. Rev. B **50**, 9882 (1994).
- [17] S. M. Shapiro, private communication; E. A. Goremychkin and R. Osborn, private communication.
- [18] P. Nozières, Ann. Phys. (Paris) **10**, 19 (1985).
- [19] A. J. Millis and P. A. Lee, Phys. Rev. B **35**, 3394 (1987).