

Thermal conductivity of the $A_x\text{BO}_2$ type layered oxides $\text{Na}_{0.77}\text{MnO}_2$ and LiCoO_2

Kazumi TAKAHATA¹ and Ichiro TERASAKI^{1,2} *

¹*Department of Applied Physics, Waseda University,
3-4-1 Ohkubo, Shinjuku-ku, Tokyo, 169-8555, Japan*

²*Precursory Research for Embryonic Science and Technology,
Japan Science Technology, Tokyo 108-0075, Japan*

(Dated: October 29, 2018)

We prepared polycrystalline samples of the $A_x\text{BO}_2$ type layered oxides $\text{Na}_{0.77}\text{MnO}_2$ and LiCoO_2 , and measured thermal conductivity (κ) from 15 to 280 K. $\text{Na}_{0.77}\text{MnO}_2$ shows a low κ of 15 mW/cmK at 280 K, while LiCoO_2 shows a much higher κ of 40 mW/cmK at 280 K. By comparing them with κ of NaCo_2O_4 , we have found that the low κ of $A_x\text{BO}_2$ comes essentially from the A-ion deficiency, not from the layered structure itself.

PACS numbers: PACS numbers: 72.15.Eb, 72.15.Jf, 72.80.Ga, 72.15.Lh

Recently, thermoelectric energy conversion [1] has attracted renewed interest from the viewpoint of environmental concerns. In this respect, oxides are quite desirable, because they are stable in air and mostly harmless. Owing to the low efficiency, they have been thought to be unsuitable for thermoelectric applications, but the layered cobalt oxide NaCo_2O_4 has been found to show exceptionally high thermoelectric performance [2]. Previously we found that NaCo_2O_4 has a low thermal conductivity (κ) of 15 mW/cmK at 280 K, which was attributed to the short phonon mean free path arising from the Na deficiency [3].

An open question is whether the layered structure is effective for the κ reduction in NaCo_2O_4 or not, as in the case of the thermoelectric superlattice [4, 5, 6]. Although the phonon-scattering theory [7, 8] successfully fitted the data in the previous paper [3], we did not rule out the possibility of the layered-structure effects. The best way is perhaps to measure anisotropic κ using single crystals, but the crystals are too small and thin to measure κ accurately [9]. At least we can say that there is no reason to regard NaCo_2O_4 as a superlattice on the electric properties. The resistivity is anisotropic, but quantum confinement is unlikely to occur in the c-axis conduction [2].

In order to distinguish the layered-structure effects from the Na-deficiency effects, we focus on $\text{Na}_{0.77}\text{MnO}_2$ and LiCoO_2 , which have the same layered structure of $A_x\text{BO}_2$, but have different A-ion deficiency (see Fig.1): Na ions in NaCo_2O_4 ($\text{Na}_{0.5}\text{Co}_2\text{O}_2$) and $\text{Na}_{0.77}\text{MnO}_2$ are 50 % and 23% deficient, while Li ions in LiCoO_2 are nominally 100% occupied. Here we report on measurement and analysis of κ of $\text{Na}_{0.77}\text{MnO}_2$ and LiCoO_2 .

Polycrystalline samples of $\text{Na}_{0.77}\text{MnO}_2$ and LiCoO_2 were prepared through a solid-state reaction. For $\text{Na}_{0.77}\text{MnO}_2$, starting powders of NaCO_3 and Mn_3O_4 were mixed and calcined at 500°C for 12h. The product was pressed into a pellet, and sintered at 550°C

for 12h [10]. For LiCoO_2 , starting powders of LiCO_3 and Co_3O_4 were mixed and calcined at 450°C for 12h. The product was pressed into a pellet, and sintered at 900°C for 24h [11]. X-ray diffraction revealed no impurity phases in the obtained polycrystals, and resistivity measurement revealed that they were highly insulating. The thermal conductivity was measured using a steady-state technique described previously [3].

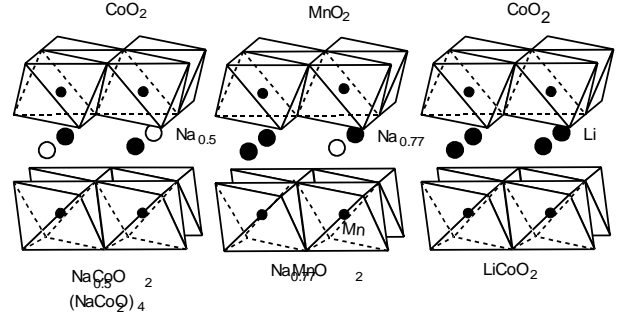


FIG. 1: Crystal structures of $\text{Na}_{0.5}\text{Co}_2\text{O}_2$ (NaCo_2O_4), $\text{Na}_{0.77}\text{MnO}_2$ and LiCoO_2 . The close and open circles represent the occupied and vacant ions, respectively.

Figure 2 shows κ of $\text{Na}_{0.77}\text{MnO}_2$ and LiCoO_2 , together with κ of NaCo_2O_4 from Ref.[3]. κ of the Na-deficient oxide $\text{Na}_{0.77}\text{MnO}_2$ is as low as 15 mW/cmK at 280 K, and is slightly lower than κ of NaCo_2O_4 . Since κ of NaCo_2O_4 includes the electron thermal conductivity (about 10 % of total), we think that the lattice thermal conductivity is nearly equal between the two. On the contrary, the fully Li-occupied oxide LiCoO_2 shows 3-4 times higher κ than $\text{Na}_{0.77}\text{MnO}_2$. This clearly indicates that the A-ion deficiency effectively reduces κ .

Let us fit the data with the phonon-scattering theory [7, 8]. The lattice thermal conductivity is written as

$$\kappa_{\text{ph}} = \frac{k_B}{2\pi^2v} \left(\frac{k_B}{\hbar} \right)^3 T^3 \int_0^{\Theta_D/T} \frac{x^4 e^x}{(e^x - 1)^2} \tau dx \quad (1)$$

where Θ_D is the Debye temperature, and v is the sound velocity, and $x = \hbar\omega/k_B T$. The total scattering rate τ^{-1}

*E-mail address: terra@mn.waseda.ac.jp

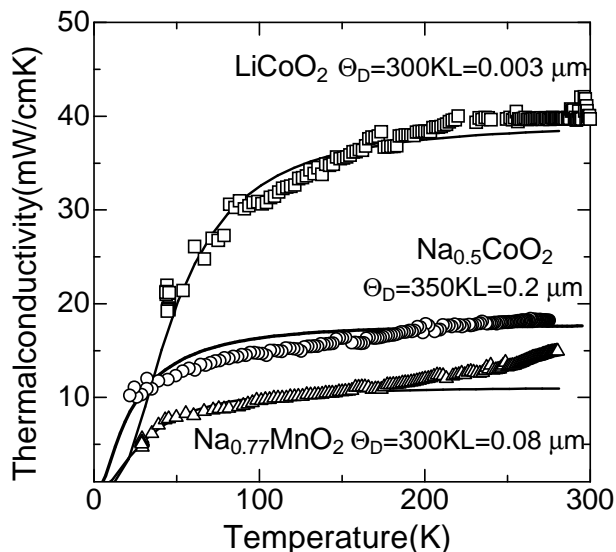


FIG. 2: The thermal conductivity of A_xBO_2 type layered oxides plotted as a function of temperature. The theoretical fitting by the phonon-scattering theory is shown by the solid curves. Note that the theoretical curves are functions as the Debye temperature Θ_D and the boundary scattering length L (see text).

is given as the sum of three scattering rates as

$$\tau^{-1} = \tau_{pd}^{-1} + \tau_{ph-ph}^{-1} + \tau_0^{-1} = a\omega^4 + b\omega^2 + v/L \quad (2)$$

where τ_{pd}^{-1} , τ_{ph-ph}^{-1} and τ_0^{-1} are the scattering rates for the point-defect scattering, the phonon-phonon scattering, and the boundary scattering, respectively. For a phonon frequency ω , the three scattering rates are written as $a\omega^4$, $b\omega^2$ and v/L , where a , b and L are characteristic parameters. According to Klemens [12], the coefficient a is calculated as

$$a = \Omega_0 \sum f_i (1 - M_i/M)^2 / 4v^3, \quad (3)$$

where Ω_0 is the unit cell volume, M_i and f_i are the mass

and the fraction of an atom, and $M = \sum f_i M_i$ is the average mass. Then a for $Na_{0.07}MnO_2$ can be calculated only by assuming that the Na ion and the vacancy make a solid solution, and a is calculated to be zero for $LiCoO_2$. As discussed in the previous paper [3], the temperature dependence of κ indicates negligibly small phonon-phonon scattering, and we safely assume $b = 0$. Consequently v and L are to be determined through fitting. Since v is related to Θ_D as

$$\Theta_D = \frac{\hbar v}{k_B} (6\pi^2 N)^{\frac{1}{3}}, \quad (4)$$

and thus we employed Θ_D instead of v as a fitting parameter (N is the number of atoms per unit cell).

The data fitting is satisfactory, as displayed in Fig.2 by the solid curves. Θ_D 's are fitted to be 300 K for $Na_{0.77}MnO_2$ and $LiCoO_2$, which are nearly equal to the value of 350 K for $NaCo_2O_4$ estimated from the specific-heat measurement [13]. L 's are fitted to be 0.2, 0.08, 0.003 μm for $NaCo_2O_4$, $Na_{0.77}MnO_2$ and $LiCoO_2$, respectively. It should be noted that L of $LiCoO_2$ is much shorter than the others. In this compound, we set $a = b = 0$ in Eq. (2), which means that only the boundary scattering dominates κ . Then L is reduced to be an ‘‘average’’ phonon mean free path ℓ in the sense of the classical argument $\kappa = Cv\ell/3$, where C is the phonon specific heat. From the very beginning, L is introduced as a phenomenological parameter, and cannot be evaluated from the first principle. The physical meaning of L is to be explored theoretically, as other researchers also pointed out [5, 6].

In summary, polycrystalline samples of $Na_{0.77}MnO_2$ and $LiCoO_2$ are prepared, and the thermal conductivity is measured from 15 to 280 K. We have successfully fitted the experimental data with the phonon-scattering theory, and have found that the reduction of the thermal conductivity is mainly determined by the vacancy (point defect), not by the layered structure.

The authors appreciate Y. Iguchi, A. Satake, W. Kobayashi and R. Kitawaki for collaboration.

-
- [1] For a review, see G. D. Mahan: Solid State Phys. **51** (1998) 81.
[2] I. Terasaki, Y. Sasago, and K. Uchinokura: Phys. Rev. B **56** (1997) R12685.
[3] K. Takahata, Y. Iguchi, D. Tanaka, T. Itoh, and I. Terasaki: Phys. Rev. B **61** (2000) 12551.
[4] L. D. Hicks and M. S. Dresselhaus: Phys. Rev. B **47** (1993) 12727.
[5] G. Chen: Phys. Rev. B **57** (1998) 14958.
[6] M. V. Simkin and G. D. Mahan: Phys. Rev. Lett. **84** (2000) 927.
[7] J. Callaway: Phys. Rev. **113** (1959) 1046.
[8] J. Callaway and H. C. von Baeyer: Phys. Rev. **120** (1960) 1149.
[9] Very recently Fujita, Mochida and Nakamura [Jpn. J. Appl. Phys. **40** (2001) 4644] measured κ for single crystals of $NaCo_2O_4$ which was unexpectedly high (400 mW/cm K at 300 K). They evaluated κ from thermal-diffusivity measurement, and other technique should be examined.
[10] J. P. Parant, R. Olazcuaga, M. Devalette, C. Fouassier and P. Hagenmuller: J. Solid State Chem **3** (1971) 1.
[11] C. Delmas, J-J. Braconner and P. Hagenmuller: Mat. Res. Bull. **17** (1982) 117.
[12] P. G. Klemens: Phys. Rev. **119** (1960) 507.
[13] Y. Ando, N. Miyamoto, K. Segawa, T. Kawata and I. Terasaki: Phys. Rev. B **60** (2000) 10580.